

Chemical Science

Accepted Manuscript

This article can be cited before page numbers have been issued, to do this please use: A. Tombrink, M. Semwal, T. Maisuradze, A. K. Mengele, D. Straub, A. Kuehne, S. Rau, S. Kupfer, B. Dietzek-Ivanši and B. Esser, *Chem. Sci.*, 2026, DOI: 10.1039/D5SC08675B.



This is an Accepted Manuscript, which has been through the Royal Society of Chemistry peer review process and has been accepted for publication.

Accepted Manuscripts are published online shortly after acceptance, before technical editing, formatting and proof reading. Using this free service, authors can make their results available to the community, in citable form, before we publish the edited article. We will replace this Accepted Manuscript with the edited and formatted Advance Article as soon as it is available.

You can find more information about Accepted Manuscripts in the [Information for Authors](#).

Please note that technical editing may introduce minor changes to the text and/or graphics, which may alter content. The journal's standard [Terms & Conditions](#) and the [Ethical guidelines](#) still apply. In no event shall the Royal Society of Chemistry be held responsible for any errors or omissions in this Accepted Manuscript or any consequences arising from the use of any information it contains.

A Donor-Acceptor Photosensitizer-catalyst Dyad for Light-Driven Nicotinamide Hydrogenation

Alexander Tombrink,^[a]+ Mohini Semwal,^[b,c]+ Tamar Maisuradze,^[c]+ Alexander K. Mengele,^[d] Daniel Straub,^[e] Alexander J. C. Kuehne,^[e] Sven Rau,^[d] Stephan Kupfer,^[c] Benjamin Dietzek-Ivanšić,^{*[b,c,f]} and Birgit Esser^{*[a]}

[a] Institute of Organic Chemistry II and Advanced Materials, Ulm University, Albert-Einstein-Allee 11, 89081 Ulm, Germany

[b] Leibniz Institute of Photonic Technology, Research Department Functional Interfaces, Albert-Einstein-Str. 9, 07745 Jena, Germany

[c] Institute of Physical Chemistry, Friedrich Schiller University Jena, Helmholtzweg 4, 07743 Jena, Germany

[d] Institute of Inorganic Chemistry I, Ulm University, Albert-Einstein-Allee 11, 89081 Ulm, Germany

[e] Institute of Organic Chemistry III, Ulm University, Albert-Einstein-Allee 11, 89081 Ulm, Germany

[f] Leibniz-Institut für Oberflächenmodifizierung e.V. (IOM), Permoserstraße 15, 04318 Leipzig, Germany

+ These authors contributed equally

Corresponding author Email addresses:

birgit.esser@uni-ulm.de; benjamin.dietzek@uni-jena.de

Abstract

Using light energy to drive chemical transformations is of great relevance, with nature's photosynthesis as grand example. In artificial light-driven catalysis, part of nature's complex supramolecular architecture is mimicked through so-called covalently linked photosensitizer-catalyst (PS-CAT) dyads. We herein report on a dyad using an organic donor-acceptor PS, with dipyrrophenazine as acceptor and *tert*-butylcarbazole as the donor (2^tBuCzDPPZ), that contains a coordination site for a rhodium(III)Cp* center as catalyst. The organic PS shows a charge-transfer transition upon visible-light irradiation and has redox properties similar to typically used ruthenium-based PSs. The resulting PS-CAT dyad 2^tBuCzDPPZRhCp* shows – with methoxy-substituted 1,3-dimethyl-2-phenyl-2,3-dihydro-1*H*-benzo[*d*]imidazole (BIH-OMe) as sacrificial electron donor – photocatalytic activity in the light-driven NAD⁺ reduction with a TON of 3.2 (after 4 h). Femtosecond transient absorption and resonance Raman spectroscopy, as well as time-dependent density functional theory (TDDFT) calculations, shed light into



the photophysical properties of the PS and PS-CAT dyad and reveal a high dependency of the photoluminescence quantum yield and excited state properties on solvent polarity – in line with its donor-acceptor structure. This work presents a new design concept for PS-CAT dyads in artificial light-driven catalysis and provides important insight into the interplay between solvation dynamics of organic donor-acceptor systems and their photophysics, paving the way for future design strategies.

View Article Online
DOI: 10.1039/D5SC08675B

Keywords

Photocatalysis; Photosensitizer-catalyst dyads; Donor-acceptor chromophores; Femtosecond transient absorption spectroscopy; Resonance Raman spectroscopy

Introduction

Nature's photosynthesis is arguably one of the most significant chemical transformation processes on earth, and it is consequently appealing for scientists to artificially recreate specific core processes in the laboratory.^[1] The interplay of light-harvesting and cascade-like energy transfer, photoinduced charge separation and catalytic turnover processes are of particular interest in this context, and researchers strive to exploit them for artificial systems. In homogeneous artificial light-driven catalysis, typically multicomponent systems are used, containing a photosensitizer (PS) and catalyst (CAT), among others, where the photoinduced electron transfer (PET) between these components is a key step in the photocatalytic cycle. Here, being of intermolecular nature, the PET is limited by the diffusional colliding of PS and CAT or sacrificial agents during the excited-state lifetime of the PS.^[2,3] By contrast, in nature a network of precisely positioned molecular cofactors within a photosynthetic protein efficiently couples light-harvesting, electron transfer and chemical transformation within a complex supramolecular architecture.^[4] Part of this complex assembly can be mimicked through so-called PS-CAT dyads, in which the photocatalyst and the catalytically active center are covalently linked *via* a bridging unit.^[5–7] An example is the ruthenium-based PS $[\text{Ru}(\text{tbbpy})_2(\text{tpphz})]^{2+}$ (Rutpphz; tbbpy = 4,4'-di-*tert*-butyl-2,2'-bipyridine, tpphz = tetrapyrido[3,2-*a*:2',3'-*c*:3'',2''-*h*:2''',3''']phenazine), which provides a second α -diimine coordination site to attach various types of metal centers to form



the respective PS-CAT architectures (Figure 1a).^[8] By coordinating PdCl_2 , PtCl_2 , or PtI_2 , these dyads showed activity in the hydrogen-evolution reaction (HER) with TONs (turn-over numbers) of up to 276 after 70 h.^[5,9] By altering the catalytic center to RhCp^*Cl (Cp^* : 1,2,3,4,5-pentamethylcyclopentadienyl), the resulting dyad RutpphzRhCp^* not only showed photocatalytic activity in HER, but also in the reduction of the nicotinamide co-factor NAD^+ with TONs up to 6 after 90 min.^[7,10]

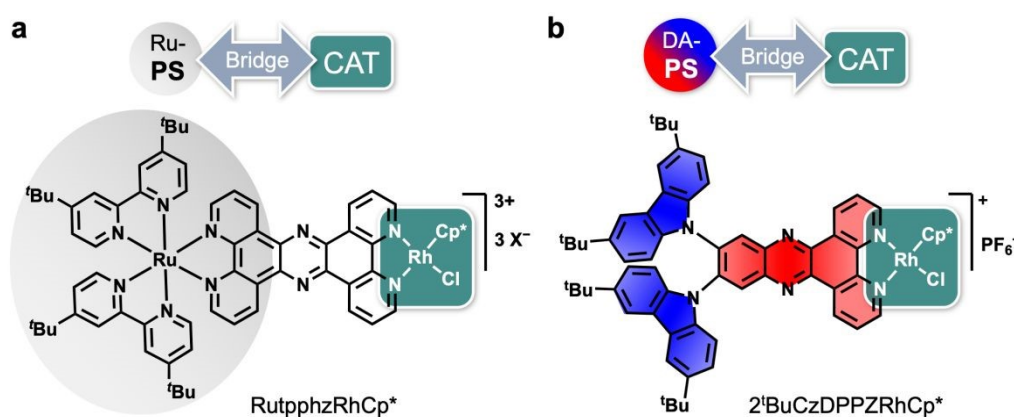


Figure 1. (a) Previously reported Ru-based dyad RutpphzRhCp^* and (b) design of the donor-acceptor (D-A)-based photosensitizer (PS)-catalyst (CAT) dyad 2^tBuCzDPPZRhCp^* .

A disadvantage of these dyads is the use of a Ru-based complex as a PS, containing a rare and expensive noble transition metal. Limited options for chemical modifications and low stability can also be problematic. Using organic chromophores as a PS that consist of abundant elements is an attractive goal, and has been realized on few occasions in PS-CAT dyads.^[6,11–14] Since the main first step in the light-driven catalysis of the Ru-based dyads is a $^1\text{MLCT}$ population upon photon absorption, we searched for a suitable replacement in form of an organic donor-acceptor (D-A) compound that also shows a vectorial charge-transfer transition upon visible-light irradiation and contains a coordination site for the CAT moiety. We choose a Rh(III)Cp^* center as a model CAT as it offers a broad variety of known catalytic functions^[15–18] and has been investigated with a multitude of spectroscopic tools.^[10,19–21] Such a coordination sphere can easily be employed for alternative CAT centers like Pt(I)_2 or Pd(II)Cl_2 . We identified 2^tBuCzDPPZ (bis(di-*tert*-butylcarbazole)dipyridophenazine), reported by Morgan *et al.*, to match our requirements (blue/red structure in Figure 1b). 2^tBuCzDPPZ is an organic red-light-emitting compound with a high molar absorptivity, featuring a dipyrro unit to attach RhCp^* as the catalytic center.^[22] In addition, its reported redox properties fit to earlier reported Ru-polypyridyl centers, as the oxidation potential at 0.94 V lies close to the oxidation of Ru^{II} to Ru^{III} at around 0.8 V (all redox



potentials given *versus* the ferrocene/ferrocenium redox couple (Fc/Fc^+). Also the reported reduction potential of -1.59 V is close to the reduction of the bridging ligand at -1.44 V of the Ru-dyad.^[10,22] Furthermore, the dipyrrophenazine coordination sphere provides an attractive interaction between the CAT-based metal center and the extended π -ligand system.^[23,24] This makes 2^tBuCzDPPZ highly desirable as a purely organic PS for the novel PS-CAT dyad 2^tBuCzDPPZRhCp^* (Figure 1b).^[10]


We herein set out to synthesize and investigate the photocatalytic activity of the new PS-CAT dyad 2^tBuCzDPPZRhCp^* . We report on its excited-state photophysics, in comparison to 2^tBuCzDPPZ , using resonance Raman (rR) spectroscopy, femtosecond transient absorption spectroscopy, and quantum chemical calculations (DFT and TDDFT as well as TDA-TDDFT) including scalar-relativistic effects as well as spin-orbit couplings, revealing strong solvent-dependent variations in the triplet-state character and lifetimes. We demonstrate that 2^tBuCzDPPZRhCp^* – with a suitable sacrificial electron donor – shows photocatalytic activity in the light-driven NAD^+ reduction. This work presents a new design concept for PS-CAT dyads in artificial light-driven catalysis since the TADF-like chromophore 2^tBuCzDPPZ features the crucial property of directional light-induced electron / energy transfer within the PS to the CAT entity. The understanding of the deactivation mechanism and proof of photocatalytic competence open a pathway to improved properties in artificial photosynthesis.

Results and Discussion

Synthesis

2^tBuCzDPPZ was synthesized in three steps in analogy to the literature^[22] starting with a condensation reaction^[25] between 1,10-phenanthroline-5,6-dione and 2-amino-4,5-difluoroaniline to form 2FDPPZ (Scheme 1) complementing the π -system of the chromophore. In a subsequent nucleophilic aromatic substitution^[22] the two 3,6-di-*tert*-butyl-9*H*-carbazoles ($t^t\text{BuCz}$) were attached, furnishing 2^tBuCzDPPZ . The PS-CAT dyad 2^tBuCzDPPZRhCp^* was obtained by reaction of the ligand with the pentamethylcyclopentadienyl rhodium(III)-dichloride dimer.^[11]



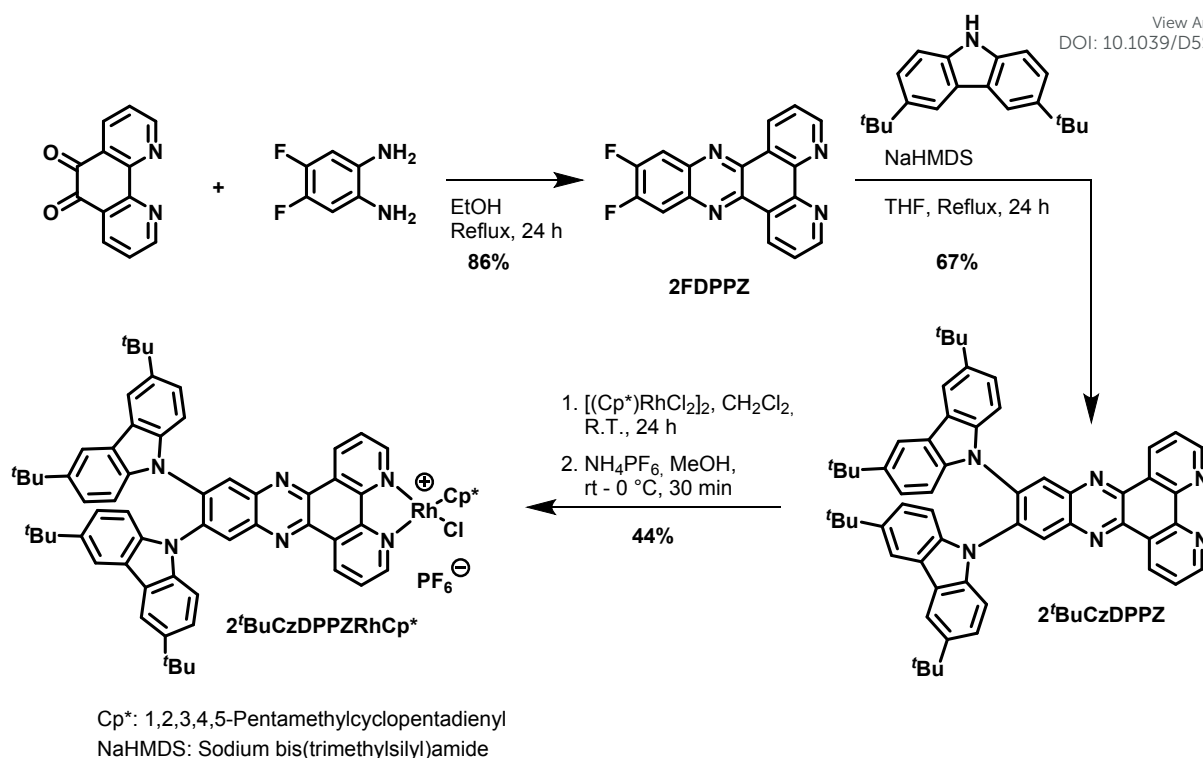

Scheme 1. Synthesis of the D-A-photosensitizer/ligand **2tBuCzDPPZ** and its Rh complex **2tBuCzDPPZRhCp*** as a PS-CAT dyad.

We also synthesized further modifications of the D-A-based PS-CAT dyad by varying the donor type and position (Scheme 1). The synthesis of the *para*-isomer **p2tBuCzDPPZRhCp*** started with a Buchwald-Hartwig amination of 4,7-dibromobenzo[*c*][1,2,5]thiadiazole with **tBuCz** (see SI for details). A reduction of the thiadiazole with LiAlH₄ gave the respective diamine, which was directly condensed with 1,10-phenanthroline-5,6-dione to the final ligand **p2tBuCzDPPZ**. This was then reacted with the pentamethylcyclopentadienyl rhodium dichloride dimer to form **p2tBuCzDPPZRhCp***.^[11] For the third dyad **2TPADPPZRhCp***, 1,10-phenanthroline-5,6-dione was condensed with 4,5-dibromo-*o*-phenylenediamine to form 11,12-dibromodipyridophenazine, which was converted to **2TPADPPZ** by Suzuki-Miyaura coupling with 4-diphenylaminophenylboronic acid (Scheme S1). Reaction with the pentamethylcyclopentadienyl rhodium dichloride dimer afforded **2TPADPPZRhCp***.^[11]

All compounds were characterized by NMR spectroscopy and high-resolution mass spectrometry (see SI Figures S1–24).

In the following, we report on the detailed optoelectronic and photophysical characterization and catalyst optimization of the PS-CAT dyad **2tBuCzDPPZRhCp*** as well as the ligand **2tBuCzDPPZ**. **p2tBuCzDPPZRhCp*** and **2TPADPPZRhCp*** were not considered further, as **p2tBuCzDPPZRhCp*** features only a weak charge-transfer band



in the UV-Vis spectrum at ca. 600 nm with a low extinction coefficient (Figure S54a), while for 2TPADPPZRhCp* initial photocatalysis tests revealed a low performance in the NAD⁺ reduction (Figure S54b).

Photophysics

We first investigated the optoelectronic properties of 2^tBuCzDPPZ and 2^tBuCzDPPZRhCp* to gain insight into their absorption characteristics and excited-state relaxation dynamics. Cyclic voltammetry (CV) in CH₂Cl₂ solution confirms a D-A character for 2^tBuCzDPPZ with oxidation half-wave potentials of 0.74 V and 1.06 V (all redox potentials are given *versus* the ferrocene/ferrocenium redox couple (Fc/Fc⁺)) and a reduction half-wave potential of -1.70 V (Table 1 and SI, Figure S25). The oxidations take place at the *tert*-butyl carbazoles,^[26] and the reduction occurs on the DPPZ core. In the PS-CAT dyad 2^tBuCzDPPZRhCp*, the potentials are slightly shifted, and, in addition, new irreversible processes were observed at 1.13, -1.28, and -0.22 V. However, the wave at -0.22 V was only visible when both the oxidative and reductive areas were scanned. The two-electron reduction of the Rh center (Rh^{III}/Rh^I) was observed at -1.21 V, which lies in the range of values reported in the literature.^[10,11] This indicates that after excitation the *tert*-butyl carbazoles can be re-reduced with common sacrificial electron donors (SEDs), since the oxidation potential of the SED is lower (e.g. E_{ox} (NEt₃): 0.31 V vs. Fc/Fc⁺)^[27] than $E_{1/2-\text{ox}}$ of 2^tBuCzDPPZRhCp*.



Table 1. Redox potentials of the PS-CAT dyad and its components (in CH_2Cl_2 (1 mM) with 0.1 M $n\text{-Bu}_4\text{NPF}_6$). View Article Online
DOI: 10.1039/D5SC08675B

Compound	$E_{1/2\text{-ox}}$ vs. $\text{Fc}/\text{Fc}^+ / \text{V}$	Peak-to-peak separation ^[a] / V	$E_{1/2\text{-red}}$ vs. $\text{Fc}/\text{Fc}^+ / \text{V}$	Peak-to-peak separation ^[a] / V
$t\text{BuCz}$ ^[26]	0.78 ^[b]	-	-	-
DPPZ ^[28]	-	-	-1.6 -2.06	-
$2t\text{BuCzDPPZ}$	0.74 1.06	0.31 0.16	-1.70	0.19
$2t\text{BuCzDPPZRhCp}^*$	0.81	0.09	-0.22 ^{[c][e]}	0.21
	1.13 ^{[c][d]}	-	-1.21	0.40 ^[f]
	1.21	0.73	-1.28 ^{[c][e]}	-
			-1.73	-

[a] Peak-to-peak separation for Fc/Fc^+ in the measurement: 0.45 V ($2t\text{BuCzDPPZ}$) and 0.35 V ($2t\text{BuCzDPPZRhCp}^*$); [b] From the literature-reported value of 1.12 V vs. SCE, 0.38 V were subtracted to obtain the value vs. Fc/Fc^+ ; ^[29] [c] Irreversible processes; [d] Anodic peak potential; [e] Cathodic peak potential; [f] Quasi-reversible.

The ground-state absorption spectrum of $2t\text{BuCzDPPZ}$ in toluene features an absorption band centered at 472 nm. Quantum-chemical calculations associate this absorption feature with a dipole-allowed intramolecular charge transfer excitation of $\pi_{\text{Cz}} \rightarrow \pi_{\text{dppz}}^*$ character into the S_2 state with an excitation wavelength of 499 nm (2.47 eV, Table S7). This band undergoes a hypsochromic shift to 452 nm in acetonitrile ($\Delta = -930 \text{ cm}^{-1}$, Figure 2a) without altering the character of the underlying electronic transition (S_2 at 490 nm, 2.54 eV, Table S3). Notably, the transition into the S_1 charge transfer state is dipole-forbidden (i.e. optically inactive) in both solvents. The emission maximum shifts from 563 nm in toluene to 645 nm in acetonitrile ($\Delta = 2140 \text{ cm}^{-1}$). Such red shift in a polar solvent is characteristic for CT emitters and suggests a stabilization of the lowest excited singlet state (S_1) due to its strong dipole moment.^[30,31]

A comparison of the fluorescence and phosphorescence spectra (recorded at 77 K in methylcyclohexane) provides a relatively small energy gap ($\Delta E_{\text{ST}} = 0.15 \text{ eV}$) between the first excited singlet and triplet states (Figure S34, Table S1). According to quantum chemical calculations at the Franck-Condon point, the vertical $\text{S}_1\text{-T}_1$ energy gaps are 0.25 and 0.26 eV in toluene and acetonitrile, respectively. In the case of toluene, the energy gap between the fully relaxed S_1 and T_1 states was predicted to be 0.25 eV,



i.e. identical to the ΔE_{ST} in the Franck-Condon geometry (S_0 equilibrium structure).
 Therefore, the subsequently discussed singlet-triplet energy gaps are exclusively obtained based on the vertical energy difference in the relaxed singlet ground state. Calculated rates of intersystem crossing (ISC) (k_{ISC} , SI, eq. 1) between lower lying singlet (S_1 and S_2) and triplet (T_1 and T_2) states, as well as rates of spontaneous emission (k_F , SI, eq. 2) were obtained in both acetonitrile and toluene and indicated rather slow and inefficient population transfer among low-lying singlet and triplet states as well as slow (spontaneous) emission based on the quasi dipole-forbidden $S_1 \rightarrow S_0$ transition (Table S2).

The photoluminescence quantum yield (PLQY) of 2^tBuCzDPPZ is strongly solvent-dependent, as typically observed for CT-emitters, where the excited CT state is stabilized in more polar solvents (Table 2): Whereas in toluene the PLQY amounts to 36%, in acetonitrile it is only 2% (both argon-purged). In non-argon-purged (aerated) solvents the PLQYs are slightly lower (29% in toluene and 1% in acetonitrile). A strong increase in PLQY upon argon-purging of a dye solution typically indicates participation of a triplet excited state. Further, a strong solvent (polarity) effect on PLQYs and on the excited-state properties is typical for photophysical properties of DPPZ like scaffolds.^[53,54]

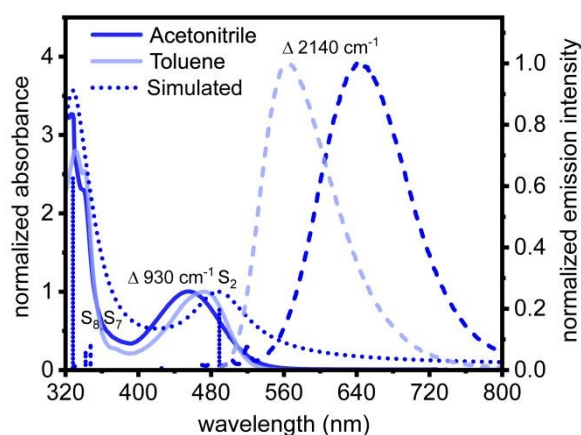


Figure 2. Electronic absorption (solid lines) and emission (dashed lines; $\lambda_{exc} = 450$ nm) spectra of 2^tBuCzDPPZ in acetonitrile (blue) and toluene (light blue) together with its simulated absorption spectra (dotted lines, blue).



Table 2. Photophysical properties of 2^tBuCzDPPZ and 2^tBuCzDPPZRhCp*.View Article Online
DOI: 10.1039/D5SC08675B

	2 ^t BuCzDPPZ		2 ^t BuCzDPPZRhCp*	
	Air-saturated	Argon-purged	Air-saturated	Argon-purged
PLQY / % (acetonitrile)	1	2	1	1
PLQY / % (toluene)	29	36	10	12
τ / ns (acetonitrile)	0.10, 3.87 ^[a]	0.10, 4.87 ^[a]	0.28, 1.42 ^[a]	0.34, 1.91 ^[a]
τ / ns (toluene)	8.63 ^[b]	9.74 ^[b]	0.09, 5.34 ^[a]	0.15, 8.74 ^[a]

[a] Bi-exponential decay; [b] Mono-exponential decay.

To characterize the Franck-Condon point of absorption of 2^tBuCzDPPZ and 2^tBuCzDPPZRhCp*, the resonance Raman (rR) spectra of both compounds were measured for their acetonitrile solution. The rR selectively enhances vibrations of the ligands that are involved in the electronic transitions, and enables an understanding of the localization of the initially excited state of the chromophore. The rR spectra recorded upon 405 nm excitation are shown in Figure 3. Both for 2^tBuCzDPPZ and 2^tBuCzDPPZRhCp* the Raman spectrum is dominated by sharp bands at 1536, 1577, 1602, and 1630 cm⁻¹, along with a shoulder at 1487 cm⁻¹ (Figure 3a). These features are attributed to C=C and C=N stretching vibrations of the DPPZ bridging ligand, indicating π - π^* or intramolecular CT transitions centered on the DPPZ chromophore.^[32,33] Carbazole contributions at this excitation energy are minimal. Upon 473 nm excitation, a broader set of vibrational features emerges, including DPPZ-associated modes at 1541, 1582, 1606, and 1633 cm⁻¹.^[34] Finally, the appearance of weak bands at 1219, 1271, 1315, 1455, and 1486 cm⁻¹ points to the involvement of the carbazole moieties.^[35,36] The latter spectral pattern aligns well with Raman bands of free carbazole in dichloromethane, which are assigned to the in-plane bending and C-N/C=C stretching modes of the carbazole framework.^[35,37,38] This suggests that the 405 nm excitation leads to CT transitions (from the carbazoles to the DPPZ). Upon longer-wavelength excitation at 473 nm, the intensity ratio of carbazole with DPPZ ligand increases as compared to 405 nm (Figure 3b; the Raman bands were normalized with respect to their absorption coefficient). The enhanced intensity of carbazole-based vibrational modes at 473 nm excitation suggests that this excitation could lead to mixed π -systems that involve both the terminal carbazole and the central DPPZ ligand. Overall, these results demonstrate that 405 nm excitation selectively enhances DPPZ-localized vibrations, while 473 nm excitation activates modes from both DPPZ and carbazole.



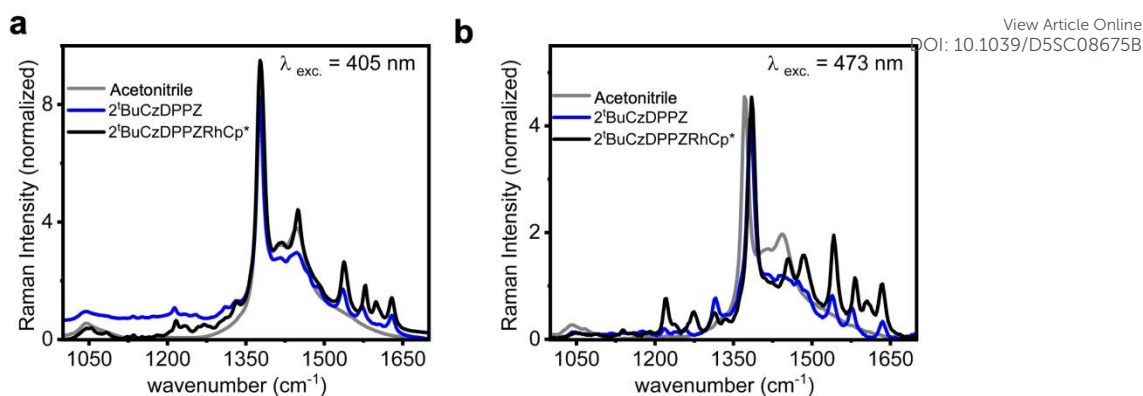


Figure 3. Resonance Raman spectra of 2^tBuCzDPPZ and 2^tBuCzDPPZRhCp^* in acetonitrile excited at (a) 405 nm and (b) 473 nm. All spectra are recorded in solution, normalized to the solvent band (acetonitrile) at 1370 cm^{-1} and with respect to the absorption coefficient of the corresponding excitation wavelength.

To gain insights into the excited-state dynamics of 2^tBuCzDPPZ , femtosecond transient absorption (fs-TA) measurements were performed upon excitation at 400 nm (Figure 4a). In acetonitrile, a pronounced ground-state bleach (GSB) is observed at 450 nm, consistent with the inverse of the steady-state absorption spectrum (Figure 2a). In parallel, excited-state absorption (ESA) bands emerge at both short (360–400 nm) and long (>500 nm) probe wavelengths (Figure S26 and S27). The long-wavelength ESA is assigned to an intramolecular CT transition from one carbazole unit to the phenazine core. Upon photoexcitation, both ESA bands rise rapidly, i.e. within the first 0.5 ps to 50 ps, followed by a decay onsetting after approximately 100 ps. As a result of this decay, approximately 95% of the initial excited-state population decays within 1 ns. The lifetime associated with the sub-ns decay is reminiscent of the fast, 0.1 to few ns component in the emission lifetime measurements (see Table 2).



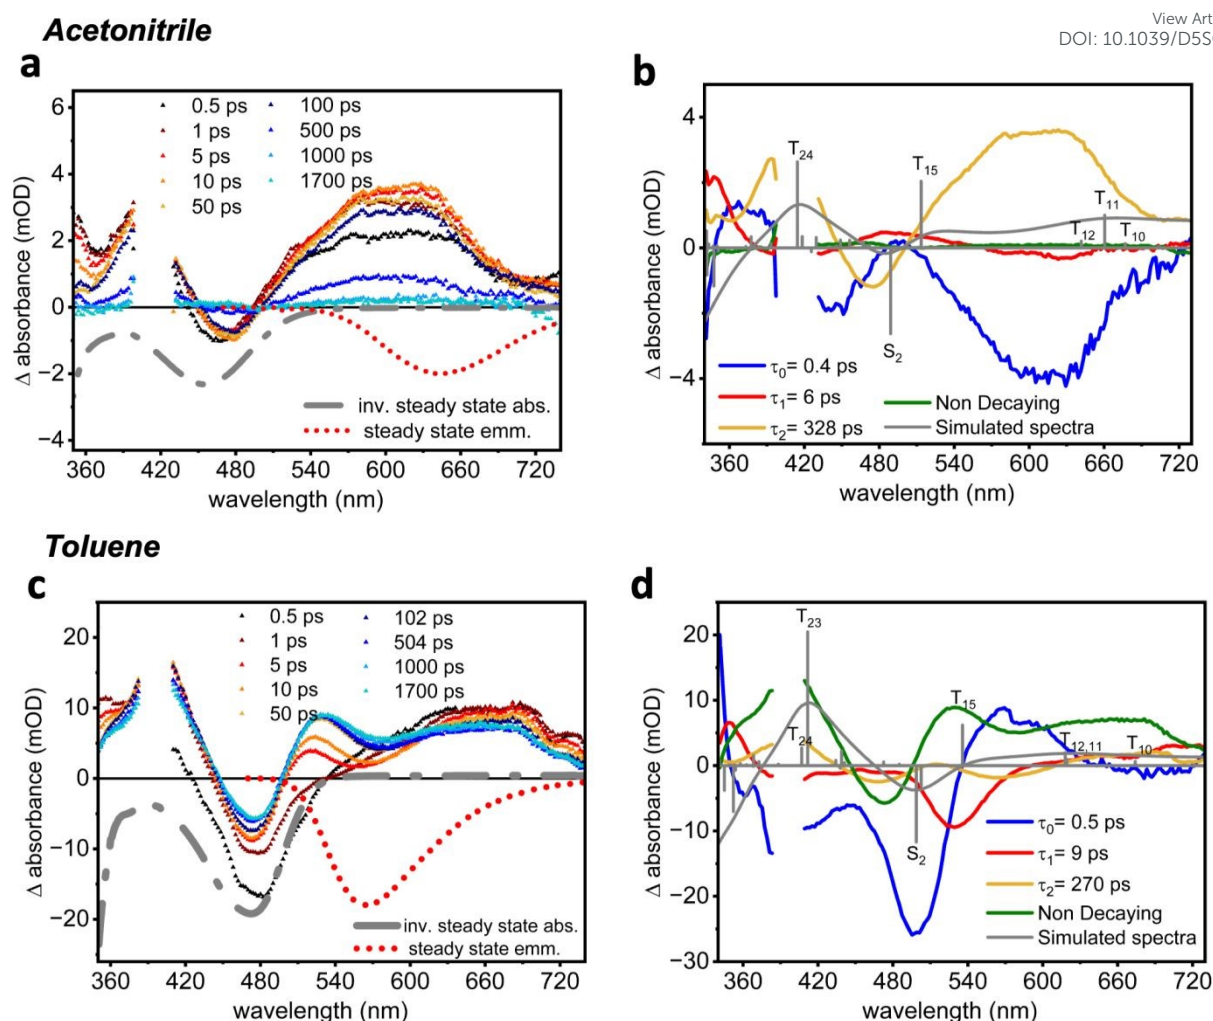


Figure 4. a, c) Transient absorption spectra of 2^tBuCzDPPZ in acetonitrile (a) and toluene (c) following excitation at 400 nm. b, d) Decay-associated spectra (DAS) in the wavelength range of 350 to 740 nm with its simulated TD (DFT) calculated spectra in acetonitrile (b) and toluene (d).

Global kinetic analysis was performed using three decay components in addition to a non-decaying (within our experimental window of 1.8 ns) component to reasonably fit the TA signal (see Figure 4). The resulting decay-associated spectra (DAS, Figure 4b and 4d) show that the first two components, associated with the decay time constants $\tau_0 = 0.4$ ps and $\tau_1 = 6$ ps, correspond to ultrafast vibrational and electronic relaxations, respectively, within the initially populated ^1CT state. According to DFT, the fully relaxed T_1 state features a prominent CT character in acetonitrile which is associated with a charge redistribution from the π -system of the carbazole moieties towards the lowest energy π_{dppz}^* orbital. Excitation of this T_1 state causes the ESA signal observed in the time-resolved measurements. More precisely, simulations of the TA spectra indicated that a 1:3 singlet-to-triplet ratio best accounts for the experimental data. According to TDA-TDDFT, the main contributions to the ESA stem from T_{24} , T_{15} , and T_{12-10} , resulting



in the major absorption at ~425 nm, ~520 nm, and 630–680 nm, respectively (Figure S49, Table S6). Excitations into T_{10-11} and T_{24} feature mixed CT and locally excited characters, while T_{12} is of pure CT and T_{15} is of $\pi_{dppz} \rightarrow \pi_{dppz}^*$ nature. Detailed information with respect to the electronic nature of the underlying transitions are collected in the Supporting Information, see Table S1. From this we assign the 328 ps component (τ_2) as the decay of a long-lived 3CT state, while the long-lived non-decaying component is nearly featureless and may represent a non-decaying offset or minor contribution from a weakly emissive state.

$2^tBuCzDPPZ$ in the nonpolar solvent toluene does not show the same results (Figure 4d): Within the first few picoseconds, an ESA band centered around 650 nm is observed, mirroring the early-time spectral feature in acetonitrile. However, at later delay times (after ca. 5 ps), the ESA feature at 520 nm progressively intensifies, while the ESA at 620 nm decays. This behavior leads to the appearance of an isosbestic point at 590 nm, which indicates internal conversion between two states, assigned to simulated T_{11} and T_{15} states (Table S10). According to TDA-TDDFT, the nature of the transition into T_{11} in toluene shifts from partial CT in acetonitrile to purely CT in toluene, while the respective transition dipole moment decreases significantly. In contrast, the CT nature of T_{15} remains unaffected. This solvent-dependent relaxation channels – as evident by means of the difference in the ESA spectral profile – highlights the influence of solvent polarity on the excited-state dynamics, especially impacting the triplet state behavior and interconversion of the involved CT states.

We next investigated the photophysical properties of the PS-CAT dyad $2^tBuCzDPPZRhCp^*$ in more details. Upon coordination of a Rh center to form the dyad $2^tBuCzDPPZRhCp^*$, the intramolecular charge-transfer absorption further red-shifts to 492 nm compared to $2^tBuCzDPPZ$, independent of solvent polarity (Figure 5a). According to the TDA-DFT calculations with the range-separated $\omega B97x-d3$ functional as well as using the PBE0 global hybrid functional, this band can be consistently associated with a dipole allowed CT $\pi_{Cz} \rightarrow \pi_{dppz}^*$ transition into the S_2 state (Table S1). However, as the excitation energies are over- and underestimated, respectively, depending on the functional used, thus a further assignment of the subsequent excited state processes in the PS-CAT dyad based on quantum chemical simulations was – unfortunately – not possible. The emission maxima of $2^tBuCzDPPZRhCp^*$ are observed at 647 nm in toluene and at 672 nm in acetonitrile, which corresponds to only



a small bathochromic shift in the more polar solvent ($\Delta = 575 \text{ cm}^{-1}$). This red shift is three times smaller than in 2^tBuCzDPPZ , indicating a notable impact of the Rh center on the excited states associated with the phenazine core.

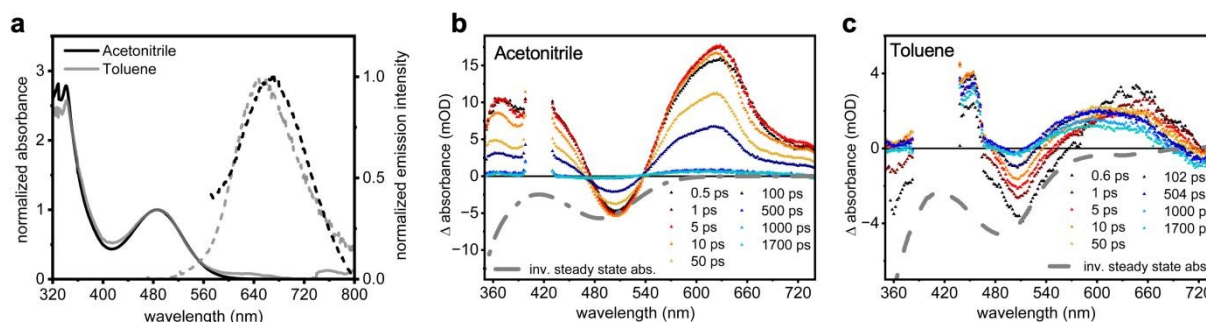


Figure 5. a) Electronic absorption (solid lines) and emission (dashed lines; $\lambda_{\text{exc.}} = 450 \text{ nm}$) spectra of 2^tBuCzDPPZRhCp^* in acetonitrile (black) and toluene (grey). b, c) Transient absorption spectra of 2^tBuCzDPPZ in acetonitrile (b) and toluene (c) following excitation at 400 nm.

Notably, the introduction of the Rh center significantly decreases the PLQY compared to the photosensitizer 2^tBuCzDPPZ (Table 2). The PLQY drops from 36% (2^tBuCzDPPZ) to 12% (2^tBuCzDPPZRhCp^*) in toluene (under an argon atmosphere), and from 2% to 1% in acetonitrile. This trend is consistent with the observed emission lifetimes (see SI Figure S36 and S37). In toluene, the lifetime decreases from 9.7 ns (2^tBuCzDPPZ) to 8.7 ns (2^tBuCzDPPZRhCp^*), whereas in acetonitrile it decreases from 4.9 ns (2^tBuCzDPPZ) to 1.9 ns (2^tBuCzDPPZRhCp^*). These experimental observations point towards excited-state electron transfer from the photosensitizer to the Rh center and are corroborated by calculations of the non-radiative decay rates (k_{nr}). In toluene, the non-radiative rate increases from $6.6 \times 10^7 \text{ s}^{-1}$ for 2^tBuCzDPPZ to $1.0 \times 10^8 \text{ s}^{-1}$ for 2^tBuCzDPPZRhCp^* —an approximate 50% increase. This effect is even more pronounced in acetonitrile, where k_{nr} dramatically rises from $2.0 \times 10^8 \text{ s}^{-1}$ (2^tBuCzDPPZ) to $5.2 \times 10^8 \text{ s}^{-1}$ (2^tBuCzDPPZRhCp^*). These values for k_{nr} reflect solvent effects and reveal an increase in non-radiative decay pathways, potentially mediated by the coordinated Rh center. A similar effect has been documented in ruthenium and perylene dyads, and it can be rationalized by the transfer of excited-state electrons to the Rh metal center^[7,11] – a prerequisite for photocatalysis, during which the Rh(III) center must undergo a twofold reduction *via* PET to a Rh-H species, which then reduces NAD^+ (see further below).

Femtosecond TA measurements on the dyad 2^tBuCzDPPZRhCp^* were performed both in acetonitrile and toluene (Figure 5b, c and SI Figure S31 and S33). Upon



coordination with the Rh center, the transient spectral features in acetonitrile resemble those of the PS 2^tBuCzDPPZ , including a characteristic ground-state bleach (GSB) at 505 nm and excited-state absorption (ESA) bands in the regions of 360–400 nm and >500 nm (Figure 5b). However, in acetonitrile the excited state of 2^tBuCzDPPZRhCp^* decays faster than that of 2^tBuCzDPPZ (cf. Figure 4a): The transient signals of 2^tBuCzDPPZRhCp^* decay almost completely (to 5% of the initial amplitude) within 92 ps. This stands in stark contrast to the comparably slow excited-state decay of 2^tBuCzDPPZ . The rapid deactivation in 2^tBuCzDPPZRhCp^* is attributed to an accelerated photoinduced energy transfer (PEnT) facilitated by the Rh center. This behavior is consistent with prior studies showing enhanced PEnT in heavy-atom-containing systems.^[39–41] Interestingly, in toluene, PEnT seems to be prolonged, with ESA features persisting beyond our experimental window of 2 ns (Figure 5c). Coordination of Rh significantly alters the excited-state dynamics of the 2^tBuCzDPPZ photosensitizer. While the free PS exhibits two distinct ESA bands in toluene—indicative of internal conversion between triplet excited states (as shown in Figure 4e)— 2^tBuCzDPPZRhCp^* displays only a single ESA feature centered at 650 nm (Figure 5c). This suggests that coordination to Rh simplifies the excited-state manifold so that only a single triplet state remains visible in the TA data. The complete recovery of the ground-state bleach within 1 ns in both solvents further supports the notion that the excited-state population fully relaxes back to the ground state. The polarization dependence of this process and the fact that such fast ground-state recovery is observed upon coordination of the Rh center suggest that the molecular origin of the excited-state relaxation is a PEnT towards the Rh(III) metal center, followed by fast charge recombination. This has also been supported by the emission lifetime (see Table 2), where the introduction of Rh significantly reduces the emission lifetime of the 2^tBuCzDPPZ chromophore.

View Article Online
DOI: 10.1039/D5SC08675B



Photocatalytic performance of the PS-CAT dyad

View Article Online
DOI: 10.1039/D5SC08675B

We next set out to investigate the photocatalytic performance of the new PS-CAT dyad. Prior to photocatalysis we checked the general activity of the catalytic Rh(III)Cp* center in 2^tBuCzDPPZRhCp* for NAD⁺ reduction in a “thermal” (dark) catalysis.^[42,43] For this, sodium formate was used as the reducing agent. It is anticipated that the dye center (PS) has no influence on the outcome of the thermal catalysis, as reported by Zedler and co-workers.^[17,41,44] They observed a similar performance for three PSs with different bridging ligands to the Rh metal center and a strong temperature dependence in accordance with an Arrhenius plot since the reaction only involved the Rh-metal center and not the bridging ligand or the PS part. In our case we could observe catalytic activity (TON: 8 (after 60 min, 45 °C), TOF: 21 h⁻¹ (after 5 min, 45 °C), see SI Figure S42) under similar conditions, which demonstrates that 2^tBuCzDPPZRhCp* is in principle capable of reducing NAD⁺ to NADH. However, in the literature higher TONs and TOFs were achieved by using different catalysts (e.g. RutcphzRhCp*: TON: 43 (after 50 min, 45 °C), TOF: 75 h⁻¹ (after 5 min, 45 °C)).^[41] One explanation for this might be the slightly more negative redox potential (100 mV) for the Rh(III)/Rh(I) couple of the 2^tBuCzDPPZRhCp* dyad in comparison to the Ru-based dyads.^[41] A more negative potential is associated with a lower NAD⁺ reduction rate.^[43] In addition, it has previously been shown for DPPZ containing Ru(II) polypyridine complexes that NADH is strongly stacking to the DPPZ moiety of the complex.^[45] This could potentially lead to it being readily available for reoxidation of NADH into NAD⁺ by Rh(III).

To assess the photocatalytic activity of the new PS-CAT dyad we studied the light-driven reduction of NAD⁺ to NADH. The mechanism of this process starts by exciting 2^tBuCzDPPZRhCp* with LED light ($\lambda_{\text{max}} = 465 \text{ nm}$, fwhm = 20 nm, P = 45 mW/cm²), which is assumed to cause a photo-induced electron transfer from the PS to the Rh center (Figure 6a). This process must occur twice, as the Rh(III) has to be reduced to Rh(I) under the loss of an anionic ligand. To regenerate the oxidized carbazole, a sacrificial electron donor (SED) is needed. Oftentimes triethylamine (TEA) fulfills the intended purpose, although it must be used in high quantities (24,000 eq. relative to the 2^tBuCzDPPZRhCp* dyad).^[10,11] After the oxidative addition of a proton to the Rh center (red in Figure 6a), the final hydride transfer from the latter to NAD⁺ can take place to afford NADH.^[10]



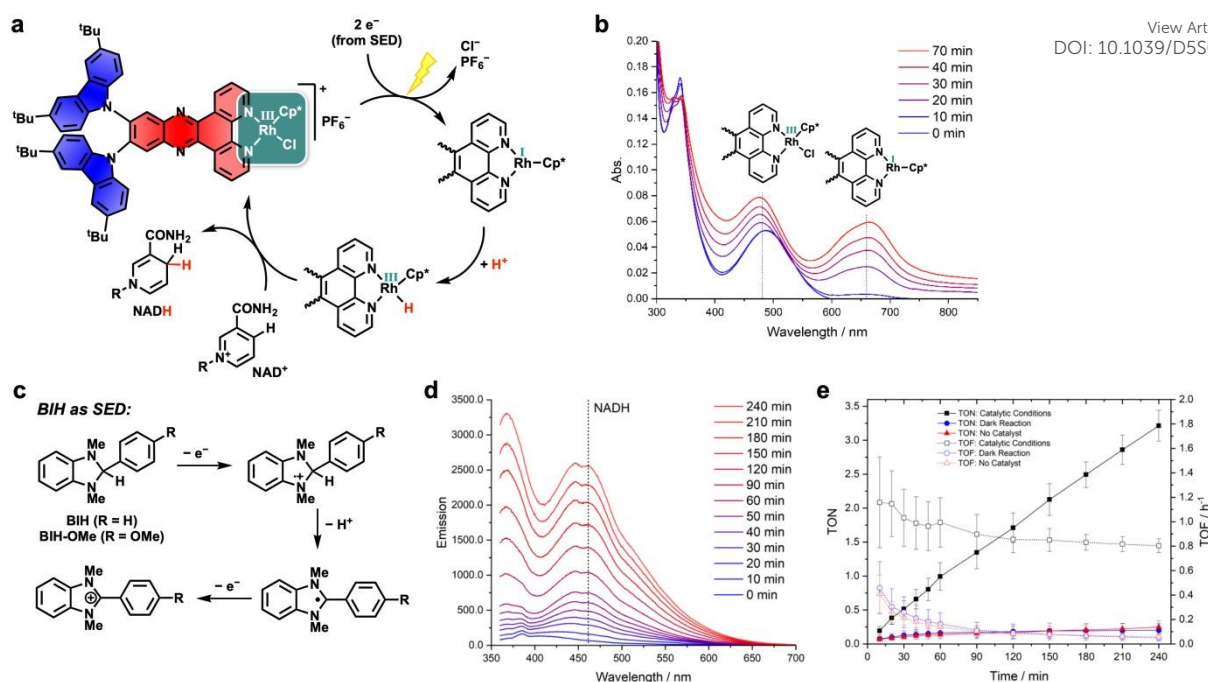


Figure 6. a) Proposed mechanism of the light-driven NAD⁺ reduction using the PS-CAT dyad 2tBuCzDPPZRhCp*.^[10] b) UV/Vis spectra of the catalytic mixture of dyad 2tBuCzDPPZRhCp* (5 μ M) with TEA (0.212 M) as an SED (0.17 M NaH₂PO₄, LED (λ_{max} = 465 nm, fwhm = 20 nm, P = 45 mW/cm²), acetonitrile/water (1/2, v/v)). c) Mechanism of BIH serving as the SED.^[27] d) Formation of NADH monitored by fluorescence spectroscopy with e) TON and TOF values for the following conditions in acetonitrile/water (1/2, v/v): 5 μ M 2tBuCzDPPZRhCp*, 400 μ M BIH-OMe, 250 μ M NAD⁺, LED (λ_{max} = 465 nm, fwhm = 20 nm, P = 45 mW/cm²); Dark reaction: 5 μ M 2tBuCzDPPZRhCp*, 400 μ M BIH-OMe, 250 μ M NAD⁺; No catalyst: 400 μ M BIH-OMe, 250 μ M NAD⁺, LED (λ_{max} = 465 nm, fwhm = 20 nm, P = 45 mW/cm²).

In our first experiments we tested the well-established conditions with TEA (pK_a (HNEt₃⁺): 10.76; E_{ox} (NEt₃): 0.31 V vs. Fc/Fc⁺)^[27] as an SED as its redox potential fits for reducing the oxidized carbazoles (cf. Table 1).^[10,11] However, with the 2tBuCzDPPZRhCp* dyad, no NADH was formed under these conditions. *In situ* spectroscopic investigations revealed that during photocatalysis a broad absorption band at 666 nm arises within minutes (Figure 6b). This can be attributed to formation of a Rh(I) species, which is an intermediate in the catalytic cycle (Figure 6a). The formation of this intermediate in a TEA/phosphate buffer could previously only be observed when no NAD⁺ was present but is typically found if dihydrogenphosphate is left out of the solution.^[10,11,20] Its accumulation indicates that the next step of the catalytic cycle is hindered, the oxidative addition of a proton. From this, one can conclude that the pK_a value of the Rh-H species is lower than the pK_a value of the buffer solution. Increasing the buffer concentration did not solve this problem. Shifting to other amine-based SEDs with lower pK_a values was also not successful. Triethanolamine (pK_a (HN(CH₂CH₂OH)₃⁺): 7.74; E_{ox} (N(CH₂CH₂OH)₃): 0.19–0.44 vs.



Fc/Fc^+)^[27,46] performed similar to TEA, and the aromatic amines dimethylaniline (pK_a (HNMe_2Ph^+): 5.15; E_{ox} (NMe_2Ph): 0.43 vs. Fc/Fc^+)^[27,47] and *N,N*-dimethyl-*p*-toluidine (pK_a ($\text{HNMe}_2(\text{C}_6\text{H}_4\text{Me})^+$): 5.63; E_{ox} ($\text{NMe}_2(\text{C}_6\text{H}_4\text{Me})$): 0.33 vs. Fc/Fc^+)^[27,48] showed neither NADH nor Rh(I) formation. Finally, modified benzimidazole SEDs brought success. 1,3-Dimethyl-2-phenyl-2,3-dihydro-1*H*-benzo[*d*]imidazole (BIH) is well known both as a hydride donor and as an SED (Figure 6c).^[27] BIH and its derivatives were for instance employed by Ishitani as an SED for HER and CO_2 reduction with Ru-RhCp* dyads.^[49,50] The mechanism of action when BIH serves as an SED is shown in Figure 6c and involves a stepwise oxidation via successive one-electron transfer processes as well as an associated deprotonation.^[27] BIH therefore supplies everything needed for the NAD^+ reduction. Initial tests with this SED showed promising results, although BIH was almost insoluble in the catalytic mixture.

To increase solubility, we attached a methoxy group to the phenyl substituent of BIH, resulting in BIH-OMe.^[51] Being sufficiently soluble in the acetonitrile/water mixture used in photocatalysis, BIH-OMe was finally able to serve as a functional SED in the light-driven NAD^+ reduction with dyad 2^tBuCzDPPZRhCp^* . The amount of NADH was determined by fluorescence spectroscopy (Figure 6d, $\lambda_{\text{max}}(\text{NADH})$: 461.5 nm, see SI Figure S38 and S39). Under the optimized conditions dyad 2^tBuCzDPPZRhCp^* delivered NADH with a TON of 3.2 after 4 h and a maximum TOF of 1.2 h^{-1} (after 10 min) (Figure 6e). For the literature-known Ru-based dyad RutpphzRhCp^* , TONs up to 8 (after 60 min) and TOFs of 9 h^{-1} (after 60 min) could be observed.^[41] In the case of the perylene-based dyad, TONs of 4 and TOFs of 4 h^{-1} (after 60 min) were reported.^[11] Despite the lower values of the herein reported dyad, it could be shown that 2^tBuCzDPPZRhCp^* works as a proof-of-concept D-A-PS-CAT dyad, and many design alterations are possible to improve performance in the future.

Control experiments with no catalyst and no LED irradiation demonstrated that all components are crucial to form NADH (Figure 6e). Prior to catalysis, BIH-OMe was also tested in emission quenching experiments of the PS 2^tBuCzDPPZ , which resulted in a bimolecular quenching constant of $k_{\text{q-l}} = 5.06 \times 10^9 \text{ M}^{-1} \text{ s}^{-1}$ for the emission quenching, and a bimolecular quenching constant of $k_{\text{q-}\tau} = 7.46 \times 10^9 \text{ M}^{-1} \text{ s}^{-1}$ for the lifetime quenching (see SI Figure S35). This is close to the diffusion-controlled limit of the quenching rate, which is $\sim 1 \times 10^{10} \text{ M}^{-1} \text{ s}^{-1}$ ^[52] and confirms that electron transfer from BIH-OMe to the CT-excited state of the PS 2^tBuCzDPPZ is a rapid event.



It is worth noting that BIH-OMe already performs well at a relatively low quantity of 80 equivalents of the PS-CAT dyad. When increasing the concentration from 250 μM to 400 μM , significantly more NADH is produced over time. However, beyond this point (3300 μM of BIH-OMe), no further NADH is formed, but the catalyst starts degrading (see SI Figure S47). In comparison to photocatalysis with other dyads using 12 mM TEA as an SED,^[10] in our case 300 times less SED is needed to run the reaction, meaning that less chemical waste is produced.

Performing the light-driven catalysis at a higher temperature, emission bands in the range from 370 to 385 nm can be observed, which can be attributed to a degradation product of BIH-OMe (SI, Figure S46). These bands increase in intensity with the irradiation time. This indicates that BIH-OMe undergoes some kind of side reaction, which is not coupled with the actual catalysis. This side reaction becomes dominant at higher temperatures making BIH-OMe not suitable as an SED under these conditions.

Conclusions

We herein present the donor-acceptor design of the photosensitizer-catalyst (PS-CAT) dyad 2'BuCzDPPZRhCp* for nicotinamide hydrogenation/reduction. PS-CAT dyads mimic part of nature's complex assembly active in photosynthesis. The organic PS part with a donor (carbazole)-acceptor (dipyrido[3,2-*a*:2,3-*c*]phenazine = DPPZ) structure and substantial visible-light absorption contains a bidentate coordination site for a catalytically active rhodium(III) center. The presented derivatives of this principal building block all show photoluminescence with lifetimes of 10 ns and 36% photoluminescence quantum yield. Photophysical investigations on the PS 2'BuCzDPPZ, including femtosecond transient absorption (fs-TA) measurements and supported by TDDFT calculations, revealed a strong solvent (polarity) effect on photoluminescence quantum yields and on the excited-state properties. In addition, we postulate that a fast excited-state energy transfer from the 2'BuCzDPPZ PS to the Rh center takes place. This can be considered as a deactivation pathway of the crucially important excited state and might be a reason for the low photocatalytic activity. The PS-CAT dyad was employed in the light-driven NAD⁺ to NADH reduction and showed – after identification of BIH-OMe as a suitable sacrificial electron donor (SED) – photocatalytic performance with a TON of 3.2 (after 4 h) and a TOF of up to 1.2 h⁻¹. The fact that only a strong SED resulted in catalytic turnover is an indication that the



lifetime of the charge-separated state is short and therefore limits the overall photocatalytic potential. This study provides a new approach to PS-CAT dyads using organic D-A chromophores as a PS, stimulating the future development of new types of organic-PS-based dyads. A future pathway for the optimization opened by this combined synthetic, theoretic and spectroscopic investigation is to close the energy transfer pathway between the charge-separated state and the Rh(III)Cp* center, to favor the required electron transfer pathway.

Acknowledgements

The authors thank Andrea Pannwitz (University of Jena) and Bernhard Putz (Ulm University) for help with TCSPC measurements and Linda Zedler (Leibniz-Institute of Photonic Technology) for assistance with resonance Raman experiments. This work was funded by the German Research Foundation (DFG, German Research Foundation) under project IDs 364549901 (SFB TRR 234 "CataLight" (projects A1, A4, A6)), 445471845, 445471097, and 445470598.

Data Availability

The data obtained in this study have been deposited in the repository Zenodo and are available under the digital object identifier: 10.5281/zenodo.17493527

Author Contributions

Conceptualization: B.E., A.T., B.D-I.; Data curation: All authors; Formal analysis: A.T., M.S., T.M.; Funding acquisition: B.E., B.D-I., S.K., S.R., A.J.C.K.; Investigation: A.T., M.S., T.M., D.S.; Methodology: All authors; Project administration: B.E., B.D-I., S.K.; Resources: B.E., B.D-I., S.K., S.R., A.J.C.K.; Supervision: B.E., B.D-I., S.K.; Validation: All authors; Visualization: A.T., M.S., T.M., B.E.; Writing – original draft: A.T., B.E.; Writing – review & editing: All authors.

References

- [1] W. W. Fischer, J. Hemp, J. E. Johnson, "Evolution of Oxygenic Photosynthesis" *Annu. Rev. Earth Planet. Sci.* **2016**, *44*, 647–683.



- [2] T. S. Teets, D. G. Nocera, "Photocatalytic hydrogen production" *Chem. Commun.* **2011**, 47, 9268. Chem. Commun. Article Online
DOI: 10.1039/D5SC08675B
- [3] M. Schmidt, B. Esser, "Cavity-promotion by pillar[5]arenes expedites organic photoredox-catalysed reductive dehalogenations" *Chem. Commun.* **2021**, 57, 9582–9585.
- [4] K. L. Mulfort, L. M. Utschig, "Modular Homogeneous Chromophore–Catalyst Assemblies" *Acc. Chem. Res.* **2016**, 49, 835–843.
- [5] M. G. Pfeffer, T. Kowacs, M. Wächtler, J. Guthmuller, B. Dietzek, J. G. Vos, S. Rau, "Optimization of Hydrogen-Evolving Photochemical Molecular Devices" *Angew Chem Int Ed* **2015**, 54, 6627–6631.
- [6] D. Costabel, R. De, F. Jacobi, J. Eichhorn, K. Hotzel, A. Nabiyan, C. Neumann, A. Turchanin, S. Kupfer, F. H. Schacher, S. Rau, B. Dietzek-Ivanšić, K. Peneva, "Bridging Platinum and Palladium to Bipyridine-Annulated Perylene for Light-Driven Hydrogen Evolution" *ACS Catal.* **2023**, 13, 7159–7169.
- [7] A. K. Mengele, S. Kaufhold, C. Streb, S. Rau, "Generation of a stable supramolecular hydrogen evolving photocatalyst by alteration of the catalytic center" *Dalton Trans.* **2016**, 45, 6612–6618.
- [8] W. Paw, W. B. Connick, R. Eisenberg, "Dipyridocatecholate-Bridged Complexes of Platinum and Ruthenium Diimine Chromophores" *Inorg. Chem.* **1998**, 37, 3919–3926.
- [9] S. Rau, B. Schäfer, D. Gleich, E. Anders, M. Rudolph, M. Friedrich, H. Görls, W. Henry, J. G. Vos, "A Supramolecular Photocatalyst for the Production of Hydrogen and the Selective Hydrogenation of Tolane" *Angew Chem Int Ed* **2006**, 45, 6215–6218.
- [10] L. Zedler, P. Wintergerst, A. K. Mengele, C. Müller, C. Li, B. Dietzek-Ivanšić, S. Rau, "Outpacing conventional nicotinamide hydrogenation catalysis by a strongly communicating heterodinuclear photocatalyst" *Nat Commun* **2022**, 13, 2538.
- [11] J. Brückmann, C. Müller, I. Friedländer, A. K. Mengele, K. Peneva, B. Dietzek-Ivansic, S. Rau, "Photocatalytic Reduction of Nicotinamide Co-factor by Perylene Sensitized RhII IComplexes**" *Chem. Eur. J.* **2022**, 23, e202201931.



- [12] P. Buday, C. Kasahara, E. Hofmeister, D. Kowalczyk, M. K. Farh, S. Riediger, M. Schulz, M. Wächter, S. Furukawa, M. Saito, D. Ziegenbalg, S. Gräfe, P. Bäuerle, S. Kupfer, B. Dietzek-Ivanšić, W. Weigand, "Activating a [FeFe] Hydrogenase Mimic for Hydrogen Evolution under Visible Light" *Angewandte Chemie International Edition* **2022**, *61*, e202202079. DOI: 10.1039/D2SC08675B
- [13] G.-G. Luo, K. Fang, J.-H. Wu, J.-C. Dai, Q.-H. Zhao, "Noble-metal-free BODIPY–cobaloxime photocatalysts for visible-light-driven hydrogen production" *Phys. Chem. Chem. Phys.* **2014**, *16*, 23884–23894.
- [14] B. S. Veldkamp, W.-S. Han, S. M. Dyar, S. W. Eaton, M. A. Ratner, M. R. Wasielewski, "Photoinitiated multi-step charge separation and ultrafast charge transfer induced dissociation in a pyridyl-linked photosensitizer–cobaloxime assembly" *Energy Environ. Sci.* **2013**, *6*, 1917.
- [15] M. B. Chambers, X. Wang, N. Elgrishi, C. H. Hendon, A. Walsh, J. Bonnefoy, J. Canivet, E. A. Quadrelli, D. Farrusseng, C. Mellot-Draznieks, M. Fontecave, "Photocatalytic Carbon Dioxide Reduction with Rhodium-based Catalysts in Solution and Heterogenized within Metal–Organic Frameworks" *ChemSusChem* **2015**, *8*, 603–608.
- [16] V. Ganesan, J. J. Kim, J. Shin, K. Park, S. Yoon, "Efficient Nicotinamide Adenine Dinucleotide Regeneration with a Rhodium–Carbene Catalyst and Isolation of a Hydride Intermediate" *Inorg. Chem.* **2022**, *61*, 5683–5690.
- [17] C. L. Pitman, O. N. L. Finster, A. J. M. Miller, "Cyclopentadiene-mediated hydride transfer from rhodium complexes" *Chem. Commun.* **2016**, *52*, 9105–9108.
- [18] C. Park, C. Kwon, Y. H. Hong, "Designing biomimetic catalytic systems for CO₂ reduction to formate using NAD(P)H" *Inorg. Chem. Front.* **2025**, *12*, 4544–4568.
- [19] E. J. Askins, A. Sarkar, P. Navabi, K. Kumar, S. J. Finkelmeyer, M. Presselt, J. Cabana, K. D. Glusac, "Interfacial Electrochemistry of Catalyst-Coordinated Graphene Nanoribbons" *J. Am. Chem. Soc.* **2024**, *146*, 22360–22373.
- [20] L. Zedler, A. K. Mengele, K. M. Ziems, Y. Zhang, M. Wächter, S. Gräfe, T. Pascher, S. Rau, S. Kupfer, B. Dietzek, "Unraveling the Light-Activated Reaction Mechanism in a Catalytically Competent Key Intermediate of a Multifunctional



Molecular Catalyst for Artificial Photosynthesis" *Angewandte Chemie International Edition* **2019**, *58*, 13140–13148. View Article Online
DOI: 10.1039/D5SC08675B

[21] G. E. Shillito, S. Rau, S. Kupfer, "Plugging the 3MC Sink in RuII-Based Photocatalysts" *ChemCatChem* **2023**, *15*, e202201489.

[22] L. Morgan, G. Pavan, N. Demitri, C. Alberoni, T. Scattolin, M. Roverso, S. Bogialli, A. Aliprandi, "Tailoring thermally activated delayed fluorescence emitters for efficient electrochemiluminescence with tripropylamine as coreactant" *RSC Adv.* **2023**, *13*, 34520–34523.

[23] S. Amthor, D. Hernández-Castillo, B. Maryasin, P. Seeber, A. K. Mengele, S. Gräfe, L. González, S. Rau, "Strong Ligand Stabilization Based on π -Extension in a Series of Ruthenium Terpyridine Water Oxidation Catalysts" *Chemistry – A European Journal* **2021**, *27*, 16871–16878.

[24] M. Lämmle, A. K. Mengele, G. E. Shillito, S. Kupfer, S. Rau, "Stability of Catalytic Centres in Light-Driven Hydrogen Evolution by Di- and Oligonuclear Photocatalysts" *Chemistry – A European Journal* **2023**, *29*, e202202722.

[25] Y. Zhang, J. Zhang, C. Shi, N. Sun, Q. Wang, "Dipyrido[3,2-a:2',3'-c]phenazine acceptor based thermally activated delayed fluorescence emitters" *Dyes and Pigments* **2022**, *206*, 110634.

[26] H. Zhang, S. Wang, Y. Li, B. Zhang, C. Du, X. Wan, Y. Chen, "Synthesis, characterization, and electroluminescent properties of star shaped donor–acceptor dendrimers with carbazole dendrons as peripheral branches and heterotriangulene as central core" *Tetrahedron* **2009**, *65*, 4455–4463.

[27] Y. Pellegrin, F. Odobel, "Sacrificial electron donor reagents for solar fuel production" *Comptes Rendus Chimie* **2017**, *20*, 283–295.

[28] Y. Liang, M. T. Nguyen, B. J. Holliday, R. A. Jones, "Electrocatalytic reduction of CO₂ using rhenium complexes with dipyrido[3,2-a:2',3'-c]phenazine ligands" *Inorganic Chemistry Communications* **2017**, *84*, 113–117.

[29] V. V. Pavlishchuk, A. W. Addison, "Conversion constants for redox potentials measured versus different reference electrodes in acetonitrile solutions at 25°C" *Inorganica Chimica Acta* **2000**, *298*, 97–102.



- [30] R. Ishimatsu, S. Matsunami, K. Shizu, C. Adachi, K. Nakano, T. Imato, "Solvent Effect on Thermally Activated Delayed Fluorescence by 1,2,3,5-Tetrakis(carbazol-9-yl)-4,6-dicyanobenzene" *J. Phys. Chem. A* **2013**, *117*, 5607–5612. View Article Online
DOI: 10.1039/D3SC08675B
- [31] Y. Yang, Z. Jiang, Y. Liu, T. Guan, Q. Zhang, C. Qin, K. Jiang, Y. Liu, "Transient Absorption Spectroscopy of a Carbazole-Based Room-Temperature Phosphorescent Molecule: Real-Time Monitoring of Singlet–Triplet Transitions" *J. Phys. Chem. Lett.* **2022**, *13*, 9381–9389.
- [32] J. R. Schoonover, W. D. Bates, T. J. Meyer, "Application of Resonance Raman Spectroscopy to Electronic Structure in Metal Complex Excited States. Excited-State Ordering and Electron Delocalization in Dipyrido[3,2-a:2',3'-c]phenazine (dppz): Complexes of Re(I) and Ru(II)" *Inorg. Chem.* **1995**, *34*, 6421–6422.
- [33] W. R. Browne, J. J. McGarvey, "Raman scattering and photophysics in spin-state-labile d6 metal complexes" *Coordination Chemistry Reviews* **2006**, *250*, 1696–1709.
- [34] C. Kuhnt, M. Karnahl, S. Tschierlei, K. Griebenow, M. Schmitt, B. Schäfer, S. Kriek, H. Görls, S. Rau, B. Dietzek, J. Popp, "Substitution-controlled ultrafast excited-state processes in Ru–dppz-derivatives" *Phys. Chem. Chem. Phys.* **2010**, *12*, 1357–1368.
- [35] A. Bree, R. Zwarich, "Vibrational Assignment of Carbazole from Infrared, Raman, and Fluorescence Spectra" *The Journal of Chemical Physics* **1968**, *49*, 3344–3355.
- [36] M. Wächtler, J. Guthmüller, L. González, B. Dietzek, "Analysis and characterization of coordination compounds by resonance Raman spectroscopy" *Coordination Chemistry Reviews* **2012**, *256*, 1479–1508.
- [37] L. Zhao, P. Wagner, A. B. S. Elliott, M. J. Griffith, T. M. Clarke, K. C. Gordon, S. Mori, A. J. Mozer, "Enhanced performance of dye-sensitized solar cells using carbazole-substituted di-chromophoric porphyrin dyes" *J. Mater. Chem. A* **2014**, *2*, 16963–16977.
- [38] L. Kortekaas, F. Lancia, J. D. Steen, W. R. Browne, "Reversible Charge Trapping in Bis-Carbazole-Diimide Redox Polymers with Complete Luminescence



Quenching Enabling Nondestructive Read-Out by Resonance Raman Spectroscopy *J. Phys. Chem. C* **2017**, *121*, 14688–14702. View Article Online
DOI: 10.1039/C6SC08675B

J. Phys. Chem. C **2017**, *121*, 14688–14702.

[39] J. K. McCusker, “Femtosecond Absorption Spectroscopy of Transition Metal Charge-Transfer Complexes” *Acc. Chem. Res.* **2003**, *36*, 876–887.

[40] J. G. Santaclara, F. Kapteijn, J. Gascon, M. A. van der Veen, “Understanding metal–organic frameworks for photocatalytic solar fuel production” *CrystEngComm* **2017**, *19*, 4118–4125.

[41] L. Zedler, P. Wintergerst, A. K. Mengele, C. Müller, C. Li, B. Dietzek-Ivanšić, S. Rau, “Outpacing conventional nicotinamide hydrogenation catalysis by a strongly communicating heterodinuclear photocatalyst” *Nat Commun* **2022**, *13*, 2538.

[42] H. C. Lo, C. Leiva, O. Buriez, J. B. Kerr, M. M. Olmstead, R. H. Fish, “Bioorganometallic Chemistry. 13. Regioselective Reduction of NAD⁺ Models, 1-BenzylNicotinamide Triflate and β -Nicotinamide Ribose-5'-methyl Phosphate, with in Situ Generated [Cp^{*}Rh(Bpy)H]⁺: Structure–Activity Relationships, Kinetics, and Mechanistic Aspects in the Formation of the 1,4-NADH Derivatives” *Inorg. Chem.* **2001**, *40*, 6705–6716.

[43] V. Ganesan, D. Sivanesan, S. Yoon, “Correlation between the Structure and Catalytic Activity of [Cp^{*}Rh(Substituted Bipyridine)] Complexes for NADH Regeneration” *Inorg. Chem.* **2017**, *56*, 1366–1374.

[44] A. Marrone, R. H. Fish, “DFT Mechanism Studies: Biomimetic 1,4-NADH Chemoselective, Co-factor Regeneration with [Cp^{*}Rh(bpy)H]⁺, in Tandem with the Biocatalysis Pathways of a Core Model of the (HLADH)-Zn(II) Mediated Enzyme, in the Enantioselective Reduction of Achiral Ketones to Chiral S-Alcohols” *Journal of Organometallic Chemistry* **2021**, *943*, 121810.

[45] A. K. Mengele, D. Weixler, A. Chettri, M. Maurer, F. L. Huber, G. M. Seibold, B. Dietzek, B. J. Eikmanns, S. Rau, “Switching the Mechanism of NADH Photooxidation by Supramolecular Interactions” *Chemistry – A European Journal* **2021**, *27*, 16840–16845.

[46] M. R. Simond, K. Ballerat-Busserolles, Y. Coulier, L. Rodier, J.-Y. Coxam, “Dissociation Constants of Protonated Amines in Water at Temperatures from 293.15 K to 343.15 K” *J Solution Chem* **2012**, *41*, 130–142.



- [47] H. P. Marshall, E. Grunwald, "The Measurement and Correlation of Acid Dissociation Constants for Ammonium and Anilinium Salts in the System Dioxane-Water¹" *J. Am. Chem. Soc.* **1954**, *76*, 2000–2004.
- [48] M. M. Fickling, A. Fischer, B. R. Mann, J. Packer, J. Vaughan, "Hammett Substituent Constants for Electron-withdrawing Substituents: Dissociation of Phenols, Anilinium Ions and Dimethylanilinium Ions" *J. Am. Chem. Soc.* **1959**, *81*, 4226–4230.
- [49] D. Ghosh, D. C. Fabry, D. Saito, O. Ishitani, "Photochemical H₂ Evolution Using a Ru–Rh Supramolecular Photocatalyst" *Energy Fuels* **2021**, *35*, 19069–19080.
- [50] D. Ghosh, H. Takeda, D. C. Fabry, Y. Tamaki, O. Ishitani, "Supramolecular Photocatalyst with a Rh(III)-Complex Catalyst Unit for CO₂ Reduction" *ACS Sustainable Chem. Eng.* **2019**, *7*, 2648–2657.
- [51] L. Gimeno, C. Queffelec, E. Blart, Y. Pellegrin, "Copper(I) Bis(diimine) Complexes with High Photooxidation Power: Reductive Quenching of the Excited State with a Benzimidazoline Sacrificial Donor" *ACS Omega* **2022**, *7*, 13112–13119.
- [52] P. Du, J. Schneider, G. Luo, W. W. Brennessel, R. Eisenberg, "Visible Light-Driven Hydrogen Production from Aqueous Protons Catalyzed by Molecular Cobaloxime Catalysts" *Inorg. Chem.* **2009**, *48*, 4952–4962.
- [53] D. A. McGovern, A. Selmi, J. E. O'Brien, J. M. Kelly, C. Long, "Reduction of dipyrrodo-[3,2-a:2',3'-c]-phenazine (dppz) by photolysis in ethanol solution" *Chem. Commun.* **2005**, 1402–1404.
- [54] T. Phillips, C. Rajput, L. Twyman, I. Haq, J. A. Thomas, "Water-soluble organic dppz analogues—tuning DNA binding affinities, luminescence, and photo-redox properties" *Chem. Commun.* **2005**, 4327.



Data Availability

The data obtained in this study have been deposited in the repository Zenodo and are available under the digital object identifier: 10.5281/zenodo.17493527

