

# Energy Advances

Accepted Manuscript

This article can be cited before page numbers have been issued, to do this please use: A. F. V. Fonseca, L. Frolova, P. Troshin, J. Yuan and A. F. Nogueira, *Energy Adv.*, 2026, DOI: 10.1039/D5YA00315F.



This is an Accepted Manuscript, which has been through the Royal Society of Chemistry peer review process and has been accepted for publication.

Accepted Manuscripts are published online shortly after acceptance, before technical editing, formatting and proof reading. Using this free service, authors can make their results available to the community, in citable form, before we publish the edited article. We will replace this Accepted Manuscript with the edited and formatted Advance Article as soon as it is available.

You can find more information about Accepted Manuscripts in the [Information for Authors](#).

Please note that technical editing may introduce minor changes to the text and/or graphics, which may alter content. The journal's standard [Terms & Conditions](#) and the [Ethical guidelines](#) still apply. In no event shall the Royal Society of Chemistry be held responsible for any errors or omissions in this Accepted Manuscript or any consequences arising from the use of any information it contains.

## PERSPECTIVE

## Perovskites Beyond Efficiency: Stability Challenges from Space to Earth

André F. V. Fonseca,<sup>a</sup> Lyubov A. Frolova,<sup>b</sup> Pavel A. Troshin,<sup>b,c</sup> Jianyu Yuan<sup>d</sup> and Ana F. Nogueira<sup>\*a</sup>Received 00th January 20xx,  
Accepted 00th January 20xx

DOI: 10.1039/x0xx00000x

To advance in metal halide perovskite (MHP) optoelectronics beyond efficiency, international collaboration is essential, with an emphasis on stability, cost, and scalability. MHPs demonstrate remarkable stability in extreme space-level radiation; nevertheless, their stability under everyday conditions, particularly when exposed to humidity and thermal cycling, remains a significant challenge. Strategies such as low-dimensional interface passivation, quantum-dot integration, and *in situ* synchrotron studies are among the methods emphasized in this Perspective to mitigate these problems. We propose pathways of collaborative research aimed at accelerating the development of durable, high-performance perovskite devices by synthesizing insights from the broader literature in conjunction with findings from a BRICS joint initiative project. This perspective is dedicated to the achievements of Professor Nam-Gyu Park, whose extensive and remarkable work on MHP has inspired this BRICS group to collaborate in addressing the challenges of this fascinating material.

## Introduction

A delicate balance exists between economic growth and sustainable development, shaping the current global energy landscape. The expansion of economic activity, coupled with rising energy consumption and the effects of globalization, exerts increasing pressure on the environment.<sup>1</sup> As a result, addressing environmental degradation and advancing sustainability have become global priorities.<sup>2</sup>

The BRICS initiative was launched in 2006 to promote political and economic cooperation among the world's leading emerging economies: Brazil, Russia, India, China, and South Africa. The Gross Domestic Product (GDP) of the BRICS countries in 2024, as reported by the International Monetary Fund (IMF), is approximately US\$28 trillion, representing around 24.8% of global GDP.<sup>3</sup> As significant producers and also consumers of energy, these countries are undergoing a substantial transition toward renewable energy adoption and environmental sustainability.<sup>4</sup> Recently, it was reported that in 2024 the BRICS coalition accounted for 51% of global solar electricity generation, marking a significant increase from the 15% recorded a decade earlier.<sup>5</sup> China was the principal leader of this expansion, accounting for 39% of global solar electricity generation in 2024, up from 12% in 2014. Significant growth

was also observed in India and Brazil, which accounted for 6.3% (up from 2.5% in 2014) and 3.5% (from 0.01% in 2014), respectively.<sup>5</sup>

Given the BRICS nations' accelerating solar deployment, there is growing interest in emerging photovoltaic technologies (e-PV) that could combine efficiency, scalability, and low production costs.<sup>6</sup> Among the most promising e-PV technologies, metal halide perovskite (MHP)-based technologies have achieved certified efficiencies of 27% for single-junction and 30.1% for all-perovskite tandem configurations.<sup>7</sup>

In this perspective, we summarize the main findings and discussions from the *I Workshop on Perovskite Technologies*, which emerged from a joint project involving researchers from MHP-PV technology from Brazil, Russia, and China.

## The Core Perspective: Divergent Pathways for Stability

A critical, yet often overlooked, perspective in perovskite photovoltaics is the fundamental divergence in stability requirements between different application environments. Research reveals a striking paradox: metal halide perovskites (MHPs) can exhibit exceptional tolerance to extreme stressors encountered in space—such as high-energy particle radiation and severe thermal cycling—while degrading rapidly under moderate terrestrial conditions like ambient humidity and mild thermal fluctuations. This dichotomy is not a mere contradiction but a crucial insight. It indicates that the dominant degradation mechanisms are application-specific. Consequently, the future research and development pathway must evolve from a singular pursuit of a universally "stable"

<sup>a</sup> Laboratório de Nanotecnologia e Energia Solar, Instituto de Química, Universidade Estadual de Campinas (UNICAMP), Campinas, Brazil

<sup>b</sup> Federal Research Center for Problems of Chemical Physics and Medicinal Chemistry RAS, Chernogolovka, Moscow region, Russia

<sup>c</sup> Zhengzhou Research Institute of HIT, 26 Longyuan East 7<sup>th</sup>, Jinshui District, Zhengzhou, Henan Province, 450000, China

<sup>d</sup> State Key Laboratory of Bioinspired Interfacial Materials Science, Institute of Functional Nano & Soft Materials (FUNSOM), Soochow University, Suzhou, Jiangsu, China



perovskite towards the targeted design of materials, interfaces, and devices optimized for distinct operational regimes. This Perspective argues that recognizing and embracing this divergence is key to transitioning perovskite solar cells from high-performance lab prototypes to durable technologies for both terrestrial and space-based power generation.


## Efficiency Alone Isn't Enough Anymore

Recent non-certified PV research, highlighted in the 5th annual *Emerging PV Report*, underscores the growing importance of operational stability as a key metric for assessing long-term device durability.<sup>6</sup> While Perovskite Solar Cells (PSCs) have achieved impressive power conversion efficiency (PCE) values, their stability under continuous operation remains a significant challenge. A common issue found in the literature is the lack of detailed stability reporting, especially in outdoor conditions, which hinders accurate comparisons. Therefore, including both test conditions and initial PCE values is crucial for estimating energy generation and degradation rates, enabling reliable benchmarking of device longevity across different studies.<sup>6,8</sup> Liu et al. recently evaluated the commercialization potential of PSCs, focusing on efficiency, stability, and cost-effectiveness. Based on current industrial processes, they estimated a manufacturing cost of \$0.57/W and a levelized cost of electricity (LCOE) of \$0.22/kWh, with materials accounting for ~70% of the total cost (see **Figure 1a**).<sup>9</sup> Their analysis highlights that PSCs could surpass silicon solar cells if efficiencies exceed 25% and lifetimes reach at least 25 years. The first milestone has already been achieved, as certified efficiencies of above 25% were reported in 2019,<sup>7</sup> underscoring the realistic potential for PSCs to become a commercially available technology with further advances in stability and fabrication.<sup>9</sup> Thus, while reducing the fabrication costs of perovskite solar modules, particularly through improvements in the electron

transfer layer (ETL) and transparent conductor oxide (TCO), remains essential,<sup>9</sup> enhancing the device stability is more critical than ever. This likely explains the growing research focus on stability over the efficiency record race since 2017, as illustrated in **Figure 1b**. At the workshop on perovskite technologies, organized by the BRICS researchers involved in the joint project, one of the most frequently mentioned terms was indeed 'stability'. It was also the focus of several discussions on film- and device-level characterizations, as well as on the application of low-dimensional materials, such as 2D and 0D nanomaterials, in this context. The following sections will offer a detailed discussion of these subjects.

## Promising for Space, Still Challenging on Earth

To illustrate the stability issues in practical applications, we focus on extremely high-altitude applications (aerospace). The PSCs are very attractive for these applications due to their lightweight and flexible design. The principal metric for space solar arrays, in addition to high efficiency, is the power-to-weight ratio, which significantly affects payload weight and space launch costs. Flexibility can also improve the system's adaptability, thereby simplifying spacecraft design. These metrics are vital for the growing market of high-altitude Unmanned Aerial Vehicles (UAVs), where lower power input requirements are permissible owing to shorter operational lifetimes. In this context, the characteristics of MHPs enable PSCs to surpass the actual competitors, such as silicon and  $A_3B_5$  (also known as III-V) solar cells.<sup>10,11</sup> Additionally, the ability of perovskite-based PV technology to integrate scalable printing deposition techniques, such as roll-to-roll or inkjet printing, can enable the complete in situ production of photovoltaic modules during space missions.<sup>12,13</sup>

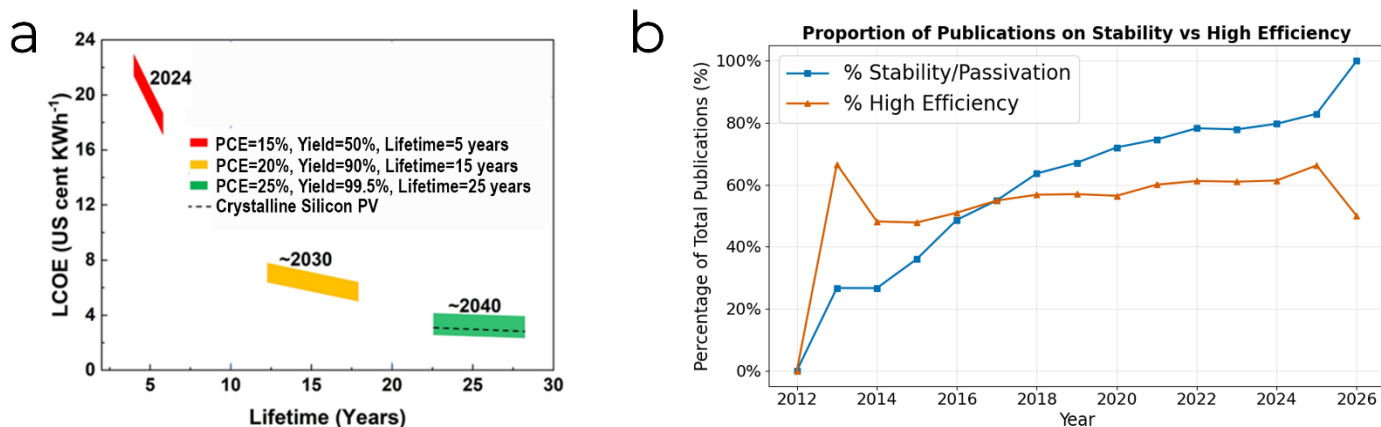


**Figure 1:** (a) Reported results of LCOE of PSCs at different stages.<sup>9</sup> Reproduced from Ref. [9] under the Creative Commons CC BY license. © 2025 The Author(s). Published by Springer Nature. (b) Distribution of publications\* reporting high-efficiency PSCs and those explicitly addressing device stability. \*Data included herein are derived from Clarivate™ (Web of Science™). © Clarivate 2025. All rights reserved.



A satellite in low-Earth orbit (LEO) typically has a mission life of 3 to 5 years, which is significantly shorter than the 25-year minimum working life required for photovoltaic panels, as

exhibited radiation-induced phase segregation into MA- and FA-rich regions, revealing a previously unrecognized degradation pathway. Among all these compositions, FAPbI<sub>3</sub>

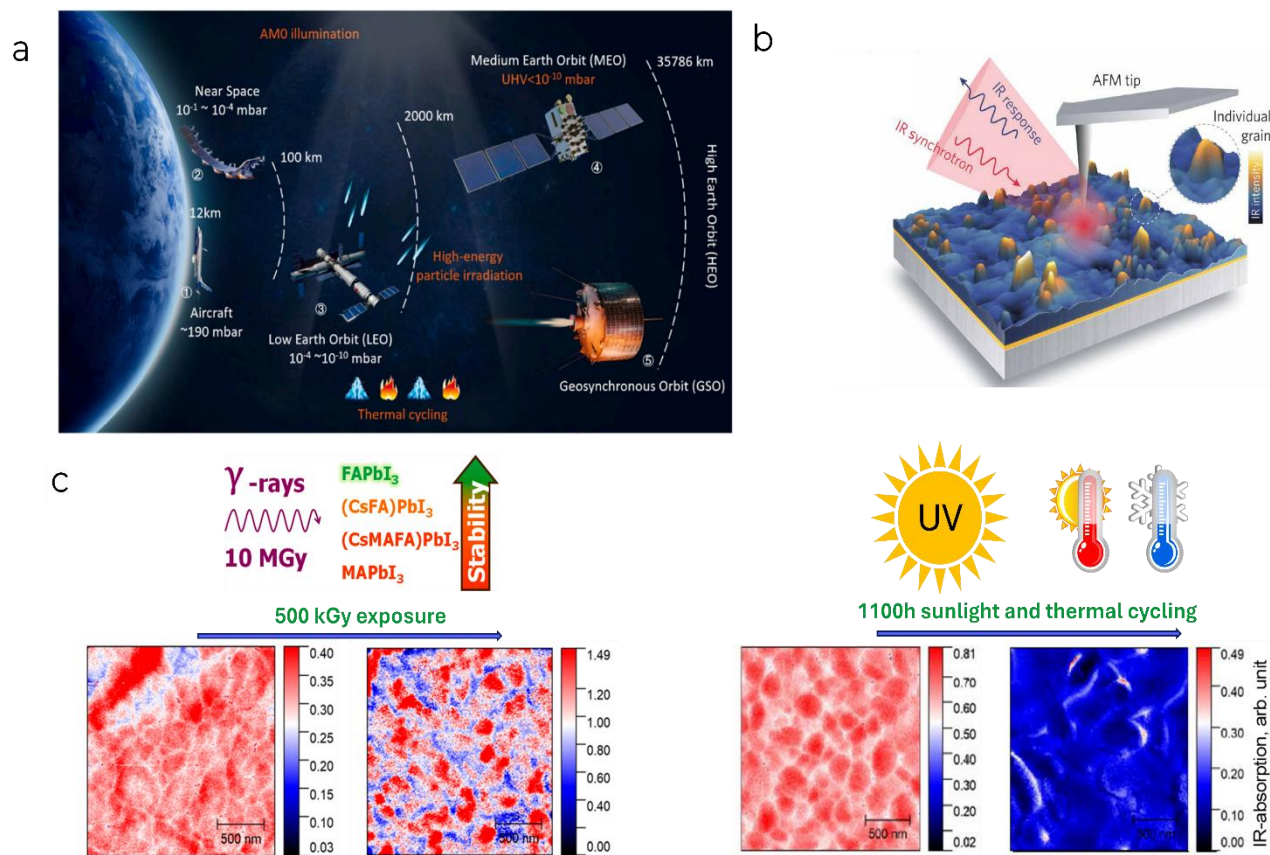

**Figure 2:** (a) Space environment of various satellite orbits,<sup>11</sup> Reproduced with permission. Copyright © 2020 Elsevier Ltd.; (b) Broadband IR radiation from a synchrotron is focused onto a metallic tip, which tightly confines the fields at its apex to interact with the sample surface in standard tapping-mode AFM.<sup>104</sup> Reproduced under the Creative Commons CC BY-NC license. © 2019 The Authors. Published by the American Association for the Advancement of Science. (c) IR s-SNOM of the MHP films after exposure to gamma-rays and under thermal-cycling and photostability tests.<sup>18,104</sup> Reproduced with permission. Copyright © 2025 American Chemical Society.

discussed above.<sup>14</sup> However, a concern about perovskites and this kind of application is that the harsh conditions of space, including thermal cycling, high vacuum, and cosmic radiation, can lead to rapid degradation in device performance (Figure 2a).<sup>15</sup> As also discussed above, although metal-halide PSCs have achieved very high PCEs, their durability under real-world conditions remains the critical limitation. Outdoor perovskite devices are commonly exposed to temperature cycles of varying intensity, driven by diurnal fluctuations or geographic conditions, which can induce crystal lattice changes, interfacial reactions, and photocatalyzed thermal degradation.<sup>16</sup> It is necessary to develop strategies to enhance thermal resilience, including improving perovskite crystallinity, relieving interlayer stress with buffer layers, and emphasizing standardized temperature-cycling protocols for meaningful cross-study comparisons.<sup>17,8,14</sup> Interestingly, the MHPs can withstand extremely high  $\gamma$ -ray doses of up to 10 MGy. Using infrared near-field optical microscopy (IR s-SNOM, Figure 2b), Troshin et al. observed that in MAPbI<sub>3</sub>, organic cations were depleted from the grains and accumulated at grain boundaries after 50 kGy. In contrast, in FAPbI<sub>3</sub>, FA cations were primarily lost from grain boundaries. The triple-cation (CsMAFA)PbI<sub>3</sub> composition

was reported to exhibit exceptional radiation hardness (Figure 2c), remaining free of metallic lead even under harsh conditions.<sup>18</sup> This is a promising finding, as, among the many studies on the composition of MHPs, the FAPbI<sub>3</sub> composition has recently been highlighted as the optimal absorber material not only for single-junction PSCs but also for the narrow-bandgap absorber in perovskite tandems.<sup>19</sup> These findings highlight IR s-SNOM as a powerful method for spatially resolved analysis of degradation pathways and aging mechanisms in perovskite materials, enabling assessment of ion segregation via nanoscale mapping.<sup>20–22</sup> A less explored strategy involving the relatively easy partial replacement of the Pb<sup>2+</sup> with other elements<sup>23</sup> was explored by Troshin et al., demonstrating that europium (Eu) or dysprosium (Dy) incorporation suppresses the degradation, showing remarkable radiation resistance under extreme gamma-ray (5.5 MGy) and 8.5 MeV electron exposures (up to  $3 \times 10^{16} \text{ e}^- \text{ cm}^{-2}$ ).<sup>10,24</sup> Further extending this strategy, the group systematically investigated partial substitution of Pb<sup>2+</sup> in double-cation Cs<sub>0.12</sub>FA<sub>0.88</sub>PbI<sub>3</sub> perovskites.<sup>25</sup> They found that incorporating specific rare-earth cations, such as Nd<sup>3+</sup>, Er<sup>3+</sup>, and Tb<sup>3+</sup>, could dramatically suppress light-induced



recrystallization and photodegradation, with the best formulations maintaining their optical properties and phase purity after an impressive 9000 hours of sun-simulated light exposure. Optimized loadings of  $\text{Er}^{3+}$  and  $\text{Zn}^{2+}$  enabled solar cells that retained 67–70% of their initial efficiency after 5000 hours of continuous operation, underscoring the power of this approach for enhancing device longevity. The primary effect of the electron beam on perovskites is a reduction in the charge-carrier diffusion length. However, the lowest value is still greater than the thickness of the films used in solar cells, resulting in no significant impact on PSC performance.<sup>26</sup> It was also observed that PSCs based on triple-cation perovskite are tolerant to high-energy proton (14 MeV) and electron (> 1 MeV) radiation in both glass-based and flexible substrates.<sup>14</sup> Tests under 68 MeV proton irradiation demonstrate very low degradation (< 6%) at a dosage of  $10^{13}$  p<sup>+</sup> cm<sup>-2</sup> where commercially available space PV degrades > 22%.<sup>27</sup> Other study reports that PSCs are also resilient “fast neutrons” (i.e., with an energy > 10 MeV), which represent one of the most drastic forms of radiation in space environments.<sup>12,27</sup> CsFAPbI<sub>3</sub> mainly degrades through  $\delta$ -phase segregation of FAPbI<sub>3</sub>, forming a Cs-rich phase; Cu<sup>+</sup>-doped films instead produce an FA-rich phase, demonstrating remarkable resistance to  $\gamma$ -rays and high-energy electrons (8.5 MeV).<sup>28,29</sup>


Taking advantage of this tolerance, perovskite high-energy sensors are increasingly recognized as superior alternatives to conventional chalcogenide-based detectors for gamma and X-ray detection. They provide exceptional energy resolution, cost efficiency, scalable manufacturing, and enhanced spectral quality.<sup>30–32</sup>

However, upon exposure to AM1.5 solar-simulated light, MAPbI<sub>3</sub> films exhibited a gradual loss of MA<sup>+</sup> cations, starting at the grain boundaries and progressing inward toward the grain cores and the bulk material.<sup>20–22</sup> Troshin et al. investigated the tunability of the optoelectronic properties of lead halide perovskites through halide mixing. The mixed-halide perovskites tend to be unstable under illumination due to segregation into Br-rich and I-rich domains, leading to performance loss and reduced operational stability. Using IR s-SNOM, they directly visualized the real-time dynamics of

segregation, showing that iodoplumbate species are expelled from the grains and form a separate I-rich phase along the grain boundaries.<sup>33</sup> Addressing this is a fundamental challenge for tandem solar cells. Frolova et al. demonstrated that light-induced halide phase segregation in wide-bandgap CsPbI<sub>2</sub>Br can be suppressed entirely through partial Pb<sup>2+</sup> substitution with Sr<sup>2+</sup>, Sn<sup>2+</sup>, In<sup>3+</sup>, or Bi<sup>3+</sup>.<sup>34</sup> Troshin and colleagues also examined the intrinsic photostability of lead halides and showed that PbI<sub>2</sub> undergoes substantial photolysis under prolonged illumination, leading to the formation of metallic lead, whereas PbBr<sub>2</sub> remains notably stable under similar conditions. This fundamental difference was linked to PbBr<sub>2</sub>'s higher vacancy formation energy.<sup>35,36</sup>


Frolova et al. reduced the photoinduced degradation of complex lead halides through a systematic screening of more than 30 modifying cations introduced as 5% Pb<sup>2+</sup> substitutes in the PbI<sub>2</sub> lattice. The most effective stabilizing cations preserved the optical absorbance of films and completely prevented Pb<sup>0</sup> formation even after 400 hours of continuous illumination. Incorporating optimized ions such as Bi<sup>3+</sup>, Eu<sup>2+/3+</sup>, and Ag<sup>+</sup> effectively reduces metallic lead formation, thereby supporting the development of highly efficient, durable perovskite solar cells with extended operational lifespans.<sup>37,38</sup>

In terms of thermal-cycling stability, space cells undergo more rapid daily cycles (light and temperature) and experience greater temperature fluctuations: from –120 to +120 °C every 90 minutes in LEO.<sup>39</sup> Mechanical residual strains in multilayer thin-film device stacks become problematic during thermal cycling due to differing thermal expansion coefficients.<sup>40</sup> Troshin *et al.* investigated the stability of PSCs under space-like conditions using an *in situ* characterization system capable of ultrahigh vacuum ( $10^{-8}$  Pa) and a wide temperature range, thereby excluding the effects of moisture and oxygen. They observed that under repeated thermal cycling (150–430 K), the perovskite absorber irreversibly decomposed. Elevated temperatures also triggered phase transitions and enhanced ion migration across interfaces. These structural and compositional changes resulted in a decline in device PCE primarily due to a reduction in short-circuit current.<sup>15</sup>



To examine how temperature affects the light-induced degradation of MAPbI<sub>3</sub> and PbI<sub>2</sub> thin films under anoxic (i.e.,

space are subjected to high-energy particle radiation, ultra-high vacuum conditions, and severe thermal cycling. As a

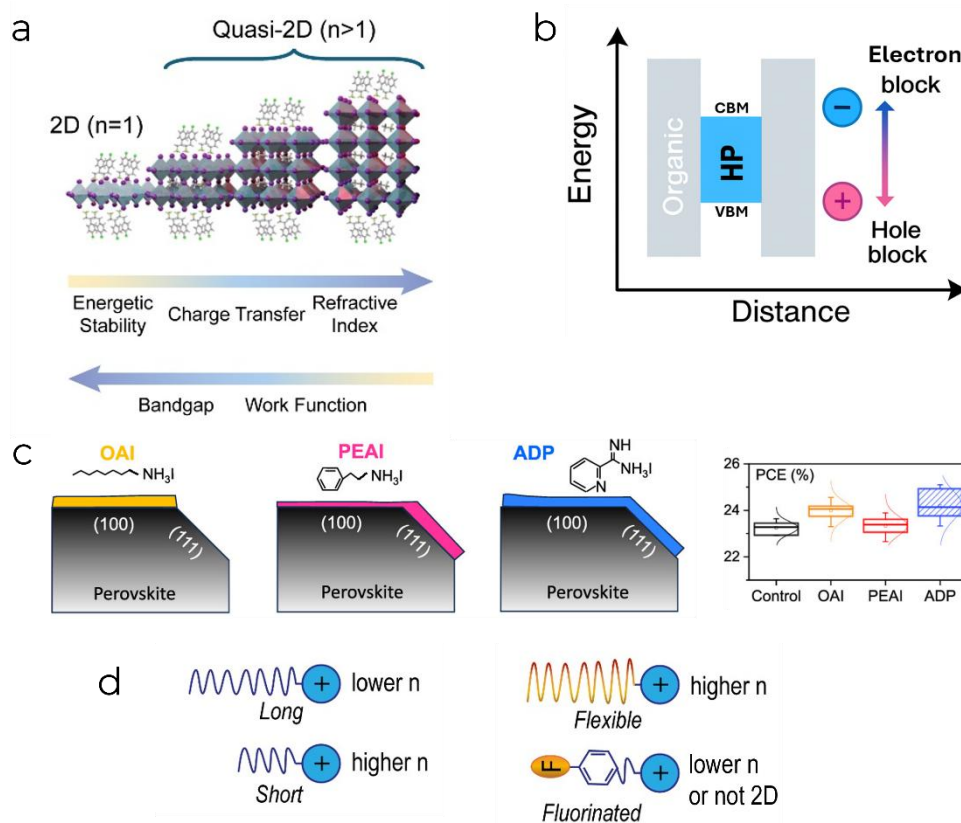

**Figure 3:** (a) Schematic representation of 2D and quasi-2D perovskites and the corresponding trends in their properties;<sup>48</sup> Reproduced under the CC-BY 4.0 license. © 2025 The Authors. Published by American Chemical Society. (b) quantum-well behavior of excitons in 2D and quasi-2D perovskites; (c) facet-dependent 2D passivation in PSCs employing different organic cations.<sup>63</sup> Reproduced with permission. Copyright © 2023 American Chemical Society; (d) general observed trend of 2D phase formation as a function of the organic cation structure.

inert-atmosphere) conditions, Troshin et al. investigated the effects of temperature on the degradation of these films. The study revealed that both MAPbI<sub>3</sub> and PbI<sub>2</sub> photolysis exhibit relatively high activation energies, approximately 85 and 106 kJ mol<sup>-1</sup>, respectively. As a result, lowering the operating temperature from 55 to 30 °C would increase the material's estimated lifetime by more than one to two orders of magnitude.<sup>41</sup>

Therefore, it is noted that exposing perovskite films to heat and light causes significant degradation, even in the absence of oxygen and moisture, with fully inorganic perovskites being the most stable absorber type.<sup>42</sup> Therefore, despite PSCs achieving high efficiency nowadays, they still exhibit intrinsic instability, mainly under light stress and thermal cycling.

The disparities in stability challenges between terrestrial and space applications are dependent on the specific stressors associated with each context. On Earth, the primary concerns include protection against humidity, oxygen, and daily photothermal degradation. Conversely, devices deployed in

result, the optimal perovskite solar cell may vary depending on the application. For terrestrial use, a wide array of compositional options is available, with interfacial passivation using 2D or quasi-2D structures as a predominant strategy. In space applications, FAPI is considered the most suitable absorber due to its exceptional radiation tolerance, particularly when doped with alternative cations.

However, the MHPs are more stable even under harsh conditions, making them promising for high-altitude applications, such as space PV; they still require improvements in fundamental terrestrial stability issues (Figure 2c). Some strategies to address these problems are presented in the following sections.

### Low-Dimensional Structures for Improving Stability



As mentioned above, although PSCs have reached efficiencies of 27%,<sup>7</sup> their stability remains a significant barrier to adoption in the photovoltaic market. External factors, including oxygen, moisture, light, and heat, primarily drive PSC degradation.<sup>35,36</sup>

A scalable strategy to address this stability problem is the usage of long-chain organic molecules to passivate perovskite grain boundaries, thereby preventing exposure to oxygen and moisture,<sup>43–46</sup> a well-known Achilles' heel of PSCs. When using bulky cation molecules for passivation, their large size prevents them from fitting into the cuboctahedral spaces of a 3D perovskite without disrupting its regular lattice. Once the 3D structure is sliced along different crystallographic planes, it can form lower-dimensional structures,<sup>47</sup> such as two-dimensional (2D,  $n = 1$ ) and quasi-2D (when  $n > 1$ ) perovskites, as shown in **Figure 3a**. In general, there is a reported trend of the refractive index increasing with the number of inorganic layers, along with enhanced thermodynamic stability and charge transfer.<sup>48,49</sup> Conversely, due to quantum confinement, the bandgap and work function increase as  $n$  decreases.<sup>47,50</sup>

Since the formation energy of the quasi-2D phase is typically lower than that of the pure 2D phase, it is common to observe a mixture of 2D phases under different confinement regimes, which can sometimes be detrimental to PSC efficiency due to irregularities in the energy landscape.<sup>51</sup> Thus, controlling the orientation of 2D layers within 3D–2D heterostructures remains a considerable challenge.<sup>52</sup>

This difficulty is particularly relevant because 2D halide perovskites exhibit strong anisotropy between in-plane and out-of-plane directions, which directly impacts electronic transport.<sup>51,53</sup> The exciton experiences quantum confinement due to reduced dimensionality, as well as dielectric confinement arising from the significant difference in dielectric constants between the inorganic framework and the organic cation layers (see **Figure 3b**).<sup>53</sup> For this reason, they are also referred to as quantum wells, and although the Förster Resonant Energy Transfer (FRET) mechanism is a plausible mechanism of energy transfer between well-packed films,<sup>54</sup> electrically extracting photogenerated charges from these low-dimensional phases is not straightforward.<sup>55</sup>

A recent study used  $\pi$ -conjugated organic spacers to extract these excitons. The extended cation chain enables  $\pi$ – $\pi$  stacking and improved orbital alignment between layers, promoting hybridization and facilitating efficient exciton movement throughout the structure.<sup>50</sup> There are limited publications on this subject; however, numerous studies focus on controlling 2D formation and stability to prevent charge blockage.<sup>55,56</sup>

Molecular additives can also be designed to stabilize the 3D perovskite lattice. For instance, Dremova *et al.* demonstrated that modifying MHP films with isonipecotic acid effectively stabilizes the photoactive phase, leading to remarkable long-term operational stability in solar cells.<sup>57</sup> This highlights the potential of targeted molecular engineering as a versatile tool for enhancing phase stability without necessarily inducing low-dimensional structuring. The growth of the 2D phase is reported to be governed by the concentration of the bulky cation, the pKa of the ammonium group, and the subsequent

thermal annealing.<sup>47,58,59</sup> However, the formation and stability of 2D and quasi-2D perovskite layers are also strongly influenced by the chemical structure of the organic spacer cation.<sup>48</sup> Cations with extended alkyl chains promote the formation of the 2D perovskite phase and augment steric hindrance, thereby improving thermal stability. They impede the transition to higher-dimensional phases during thermal aging, which are advantageous for the overall performance.<sup>60,61</sup> Choghahi *et al.* recently investigated the influence of alkylammonium spacer cation length on the electronic and optical properties of 2D perovskites. They observed notable odd–even effects, in which even-numbered chains exhibit efficient packing, whereas odd-numbered chains cause distortions in the Pb–I–Pb bond angles, thereby affecting ionization energy, optical bandgap, and charge-carrier mobility.<sup>62</sup> Park *et al.* observed that passivation occurs selectively on specific facets of the MHP (**Figure 3c**). The atomic configuration of each facet influences the orientation of the passivation layer. This facet dependence facilitated the identification of 2-amidinopyridine hydroiodide as an effective passivation agent, capable of providing uniform coverage on both the (100) and (111) facets.<sup>63</sup> Recent studies by Nogueira and colleagues indicate that chain flexibility, rather than length alone, critically influences phase purity and crystallization pathways, with flexible cations favoring the formation of mixed- $n$  phases.<sup>58</sup> Investigations have been conducted into the structural implications of substituting the phenethylammonium (PEA) spacer with a bromine atom at different positions on the phenyl ring in two-dimensional hybrid perovskites (2D MHPs). 2D MHPs with a 'gauche' conformation exhibit slower dynamics and stronger hydrogen-bonding interactions with inorganic frameworks, leading to lower band gaps, lower defect densities, and superior thermal stability.<sup>64</sup>

Therefore, both the formation and stability of the 2D layers are complex and dynamic. To address these complexities in 2D/3D compositions, advanced *in situ* techniques such as photoluminescence (PL) and grazing-incidence wide-angle X-ray scattering (GIWAXS) are increasingly employed, enabling real-time monitoring of phase formation and transformation and providing insights into crystallization and 2D/3D interfacial dynamics.<sup>59,65</sup> Also, due to the low concentration of the salts commonly used to passivate MHPs, it is not always possible to confirm or rule out the formation of 2D phases using traditional methods such as XRD or PL techniques.<sup>47</sup> In this context, synchrotron-based techniques can aid in elucidating the passivation mechanism of low-dimensional materials.<sup>20,66</sup> For instance, Nogueira *et al.* reported that 2D/3D perovskite interfaces undergo dynamic structural transformations under thermal stress, in which the 2D layer partially converts to a mixed 2D/3D phase while the 3D bulk remains intact. *In situ* synchrotron X-ray scattering revealed that this process suppresses lead iodide formation and maintains device performance, underscoring the importance of 2D passivation in enhancing thermal stability and extending device lifetime.<sup>67</sup> A recent study by Tan *et al.* demonstrated that the octylammonium-based 2D/3D perovskite heterostructure




undergoes dynamic evolution during device degradation. Initially, phase-pure 2D interlayers evolve along distinct pathways, leading to varied device stabilities. By employing mixed solvents to modulate crystallinity and phase purity, they achieved a robust 2D interlayer formation. The optimized 2D/3D devices reached a power conversion efficiency of 25.9% and maintained 91% of their initial performance after more than 1000 hours at 85 °C under maximum power point tracking.<sup>16,68</sup>

Recent studies by Nogueira et al. using *in situ* PL also demonstrated that a higher ratio of quasi-2D phases improves device performance. In contrast, pure 2D layers can hinder current extraction due to the quantum-well behavior described above. In this context, highly concentrated 2-thiophenemethylammonium (TMA) provides more effective surface passivation than PEA due to a more balanced formation energy among 2D and quasi-2D phases.<sup>69</sup> In this context, the use of small secondary ammonium cations, such as dipropylammonium (DPA), has been reported to yield materials with  $n > 10$  that are not only efficient and thermodynamically stable but also robust under heat stress.<sup>70</sup>

the formation of a two-dimensional perovskite that passivates defects associated with  $\text{Pb}^{2+}$  and iodine vacancies, thereby minimizing ion migration.<sup>71</sup>

It is also important to point out that some bulky organic ions are reported to be effective passivating agents but do not form 2D perovskites (Figure 3d).<sup>72–75</sup> These compounds can passivate the grain boundaries of the MHP film without creating a crystalline phase, a process referred to as ‘amorphous passivation’.<sup>66</sup> A recent study compared two fluorinated benzamidinium salts, both containing the same perovskite anchoring group, benzamidinium, but differing in the degree of fluorination at the opposite extremity: a monofluoro and a trifluoro derivative. The less-fluorinated cation formed a 3D/2D heterojunction, whereas the more-fluorinated salt produced an amorphous passivation layer on the perovskite films. Nevertheless, the more fluorinated salt achieved an efficiency of 24%. Interestingly, the 2D-passivated perovskite devices demonstrated greater longevity under various storage conditions.<sup>66</sup>

Even lower-dimensional systems, such as 1D and 0D structures, tend to form in molecules with highly sterically

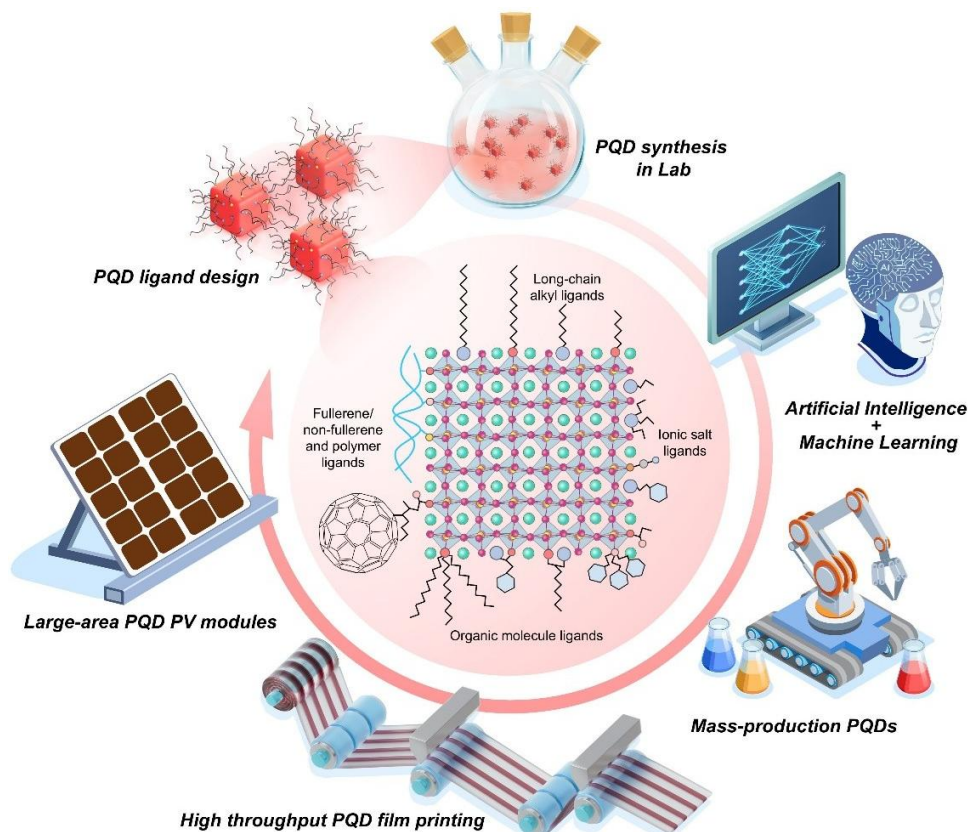

**Figure 4:** Summary of the state-of-the-art applications of PQDs in photovoltaics.<sup>106</sup> Reproduced with permission from the Royal Society of Chemistry. Copyright © 2025

In the context of bottom passivation (buried interface), a recent study introduces interfacial guanidine-based molecular layers onto  $\text{NiO}_x$ . The synergistic effect of functional groups that interact with Ni species and surface hydroxyls enhances hole extraction. Concurrently, the guanidine groups interact with residual  $\text{PbI}_2$  at the buried perovskite interface, promoting

hindered ammonium groups or in bulkier  $A'$  cations. The 1D and 0D perovskites are promising candidates, although research on them is still in its early stages.<sup>47</sup> A possible passivation strategy is to form the 0D phase, such as perovskite quantum dots (PQDs), and then deposit them onto the MHP film to create the heterojunction. Recently, Fonseca



et al. reported the deposition of CsPbBr<sub>3</sub> PQDs onto a triple-cation MHP for n-i-p configuration PSCs.<sup>76</sup> Passivation of interfacial defects and grain boundaries enhanced charge injection, thereby improving efficiency. A key aspect was the 3D/0D halide exchange, which, in this case, did not have the adverse effects often reported in the literature. The hysteresis remained unaffected, and the halide movement helped to maintain halide equilibrium under stress, likely acting as an ion reservoir.<sup>76</sup>

The literature remains controversial about whether low-dimensional (LD) structures improve or hinder PSC stability. We believe this stems from sensitive processing parameters that determine the phase distribution, n-value, and crystallographic orientation. These factors are often under-reported in the literature. Studies reveal that 2D/quasi-2D passivation improves stability when spacer cations remain confined to surfaces in low-n well-oriented phases that block moisture and/or ion ingress while allowing charge extraction. However, the same interfaces can destabilize devices when spacers intercalate into the bulk, form high-n phases, or adopt random orientations that introduce energetic barriers and trap states. Furthermore, post-fabrication migration progressively increases n-values, causing initially beneficial passivation layers to evolve into less stable phases under thermal stress, explaining why efficiency improvements are reproduced, but stability gains are not. Reproducibility failures may arise because variations in precursor stoichiometry, ligand purity, solvent timing, and annealing protocols change whether spacers remain at the surface or diffuse into the bulk of the MHP, yet these processing details are not always well documented with sufficient precision for replication.

In general, some open questions remain regarding the use of LD materials for PSC passivation, which can undergo (or not) formation of a heterostructure, including:

- **Spatial distribution:** The arrangement of 2D layers, particularly at grain boundaries, and their evolution under thermal stress, is still not fully understood.
- **Engineered heteroatom ligands:** Fluorination and mixed-cation treatments could thermodynamically favor stable low-n phases and prevent ion migration.
- **N-value control:** Limiting interdiffusion enables more precise regulation of the n-value, potentially leading to higher-purity structures and expanding the range of possible device designs.
- **Band alignment:** Adjusting the n-value, combined with A'-site engineering, enables fine-tuning of band offsets between 3D and 2D domains and the regulation of the quantum-wells.
- **Functional bulky cations:** Designing bulky cations that simultaneously passivate the perovskite interface and introduce complementary functionalities, such as enhanced hydrophobicity, dipole-induced field effects, or energy-level alignment, could improve both stability and efficiency.
- **2D/3D interface dynamics:** The 2D/3D interface is highly dynamic and changes after thermal stress, with the type of organic cation playing a significant role.

Can such interfaces withstand current accelerated heating tests and/or outdoor conditions?

## Quantum Dots – Tiny Building Blocks for Stable Solar Cells?

Beyond layered 2D/3D architectures, zero-dimensional PQDs offer an alternative and complementary approach to advancing perovskite photovoltaic technology. One of the most attractive features of the PQDs is their solution crystallinity. They are pre-crystallized materials, ready for deposition, suitable for printing techniques, and offer additional opportunities through room-temperature processing, serving as building blocks for the deposition of perovskite-absorbing layers.<sup>77</sup> The QD inks could, for example, enable space missions by providing pre-crystallized materials for further deposition in new PSCs or even for repairing damaged devices.

Usually, the synthesis of these PQDs is carried out via the hot injection (HI) method, in which the long-chain ligand-passivated FA precursor is injected into a solution of Pb and I salts at high temperature.<sup>78,79</sup> However, the HI synthesis typically requires high temperatures, an inert gas atmosphere, and long-chain insulating ligands, which limit scalability and practical application. To overcome these drawbacks, Yuan et al. reported a scalable and straightforward method for preparing PQDs under ambient conditions, thereby eliminating the need for a polar solvent and yielding a 40-fold increase in production. The resulting short-ligand-passivated PNC inks are compatible with various solution-deposition techniques, such as spray coating, allowing for the fabrication of large-area films.<sup>80</sup>

Once the PQDs are prepared, a suitable method for altering their composition is to utilize the fast ionic exchange enabled by their ionic character.<sup>16,81</sup> Yuan et al. explored fast cross-cation exchange in PQDs based on MA<sup>+</sup> and FA<sup>+</sup>. The mixed-cation PQDs demonstrate enhanced photostability and can be used directly in one-step-coated photovoltaic devices, achieving a PCE of 15.05% with MA<sub>0.5</sub>FA<sub>0.5</sub>PbI<sub>3</sub> PQDs.<sup>82</sup> The halide composition can also be tuned through simple ion-exchange post-treatments.<sup>83</sup>

Among the PQD compositions, FAPbI<sub>3</sub> is distinguished by its narrow band gap, high ambient stability, and extended carrier lifetimes, making it an attractive contender for high-performance QD photovoltaics. However, the efficiency and stability of PQD photovoltaic technologies are significantly limited by a trade-off between carrier transport blockage caused by protective ligands and nonradiative recombination losses due to defects or trap states when researchers attempt to remove these ligands in order to improve dot-to-dot charge coupling during film formation.<sup>84–86</sup> A common strategy employed by many researchers is first to synthesize high-quality PQDs and then perform ligand exchange, which can be carried out either in the liquid phase or in the solid state after film formation.<sup>87,88</sup>



Kong *et al.* recently developed an organic–inorganic hybrid active layer combining a conjugated polymer PCDDOT-T with FAPbI<sub>3</sub> QDs, providing complementary absorption and a favorable interface/morphology for efficient charge separation and transport. The champion device achieves a record efficiency of 13.11% using a one-step-coated organic/QD hybrid bulk heterojunction blend.<sup>89</sup> Yuan *et al.* recently explored dual-site molecular ligands based on thiophene amines, utilizing a dual-phase synergistic ligand exchange (DSLE) method in both the solution and solid states. The FAPbI<sub>3</sub> PQDs native insulating ligands (OA/OAm) were successfully exchanged, resulting in efficient electronic coupling and charge transport, yielding a PCE of 18.21%. The devices also exhibit enhanced stability, with a T<sub>80</sub> of ~1400 h (20–30% humidity, 25 °C).<sup>84</sup>

Recently, Yuan *et al.* employed a passivation strategy based on the exchange with fluorinated pseudo-halide anion ligand, hexafluorophosphate (PF<sub>6</sub><sup>-</sup>) for FAPbI<sub>3</sub> PQDs. The pseudo-halide simultaneously passivates iodide vacancies, enhances electronic coupling by reducing the interdot distance, suppresses ion migration, and provides a hydrophobic barrier. An unprecedented 19.01% efficiency is achieved with good operational stability.<sup>90</sup>

It is well known that buried interface engineering in PSCs actively directs the crystallization of the bulk-MHP films, controlling grain orientation, suppressing phase segregation under stress, and enhancing charge extraction; this also applies to PQDs.<sup>91–93</sup> Yuan *et al.* reported the use of a cyclic passivator (CyP) for modifying buried interfaces. CyP's ability to bind chemically to defect sites results from its isotropic nature, which enhances defect passivation and facilitates effective interfacial charge extraction and transport, leading to a PCE of 17.50% for CsPbI<sub>3</sub> PQD solar cells. Furthermore, the CyP-assisted buried-interface modulation enables the reuse of costly TiO<sub>2</sub>/FTO electrodes, thereby supporting the refurbishment of QD solar cells, maintaining more than 90% of their initial efficiency after four cycles of device recycling.<sup>94</sup>

Nevertheless, recent progress in PQD inks helps address the limitations of the traditional, labor-intensive layer-by-layer fabrication process, which is a significant barrier to the development of scalable, printable QD solar cells, according to Yuan *et al.* They prepared conductive PQD inks by introducing a sequential acylation–coordination technique that combined Lewis's base-mediated surface restoration with amine-assisted ligand removal. Without the need for solid-state ligand exchange, this method enables direct one-step film deposition, producing films with a homogeneous energy landscape, improved electronic coupling, uniform morphology, and structural order. Consequently, FAPbI<sub>3</sub> QD solar cells outperformed devices made with traditional QD inks and layer-by-layer techniques, achieving a champion efficiency of 16.61% (certified 16.20%). Additionally, the conductive inks demonstrated compatibility with scalable blade coating, enabling the high-speed fabrication of large-area devices (up to 50 mm/s) and (9 × 9 cm<sup>2</sup>).<sup>95</sup>

The use of artificial intelligence (AI), especially machine learning (ML) models, in the context of QDs is widely explored

today.<sup>96–98</sup> Some researchers are applying these concepts in real time to optimize the synthesis of PQDs in microfluidic synthesis.<sup>99–101</sup> The ML-assisted synthesis not only provides insight into the nucleation, growth, and ripening processes but also enables the precise preparation of PQDs with targeted emission wavelength and full width at half maximum (FWHM) under optimized, time- and energy-efficient, and environmentally friendly conditions (**Figure 4**).<sup>102</sup> With the rapid advancements in AI, deep learning, reinforcement learning, and large language models, research in PSCs is increasingly shifting from a predominantly data-driven to an intelligence-driven approach, automating the production of materials until the device assembly using automated platforms.<sup>98,103</sup>

## Conclusions

The BRICS nations are assuming an increasingly strategic role in the global transition to renewable energy, accounting for over half of the world's solar electricity generation in 2024. In this context, halide perovskite photovoltaics emerge as transformative technologies capable of democratizing access to clean energy owing to their low fabrication costs, tunable optoelectronic properties, and rapidly advancing efficiency metrics. Nevertheless, despite significant performance gains, the intrinsic and extrinsic stability of perovskite materials continues to pose limitations to their widespread adoption, particularly under operational and environmental stress.

Discussions from a BRICS joint project workshop on perovskite technologies underscored the consensus that achieving commercial viability requires shifting the research emphasis from record-breaking efficiencies to durability, reproducibility, and scalability.

Notably, PSCs exhibit an intriguing paradox: while they demonstrate exceptional stability under extreme space conditions (radiation doses up to 10 MGy and thermal cycling from -120 °C to +120 °C), they degrade rapidly under moderate terrestrial conditions (humidity and modest thermal cycles). This dichotomy suggests that moisture- and oxygen-induced degradation mechanisms are more critical than thermal stress or high-energy radiation. Understanding this apparent contradiction is essential for designing more effective encapsulation and stabilization strategies.

Innovative methods for analyzing stability now could be based on characterization techniques, including IR s-SNOM, which facilitates nanoscale spatial mapping of degradation mechanisms, and *in situ* synchrotron radiation analyses for real-time monitoring of structural transformations. Furthermore, enhancing durability can be achieved by integrating the recent advances in AI to accelerate the discovery of stable materials.

The integration of advanced characterization techniques, especially *in situ* and synchrotron-based techniques, offers a pathway to expedite the discovery of stable compositions and interfaces. Low-dimensional engineering, employing 2D, quasi-2D, and 0D nanostructures, has demonstrated the ability to suppress ion migration, passivate defects, and enhance



thermal and photochemical stability. Furthermore, recent advances in ligand chemistry and quantum dot inks are enabling scalable, low-temperature processes compatible with industrial coating methodologies. By integrating these approaches synergistically, BRICS nations have a unique opportunity to help the transition from “efficiency to resilience,” which represents not merely a scientific challenge but a strategic imperative for energy security and environmental sustainability.

### Conflicts of interest

There are no conflicts to declare.

### Acknowledgements

The authors thank all participants in the I BRICS Workshop on Perovskite Technologies for their valuable discussions, which contributed to this work. AFVF acknowledges support from the São Paulo Research Foundation (FAPESP) under grants 2023/10395-4 and 2024/05914-5. AFN acknowledges support from FAPESP (grant 2017/11986-5), CNPq (grant 440177/2022-7), Shell, and the strategic importance of the support provided by ANP (Brazil's National Oil, Natural Gas, and Biofuels Agency). J Yuan acknowledges the support of the Natural Science Foundation of China (No. 52261145696). PAT and LAF acknowledge support from the Russian Science Foundation (project No. 19-73-30020P). Grammarly software was used to assist with grammar and spelling checks during the preparation of this work.

### References

- 1 A. F. Nogueira, G. Doubek and H. Zanin, *Mater. Adv.*, 2025, **6**, 3368–3370.
- 2 Q. Sun, R. Ma, Z. Xi, H. Wang, C. Jiang and H. Chen, *J. Clean. Prod.*, 2023, **396**, 136488.
- 3 International Monetary Fund (IMF) Database, <https://data.imf.org/>, (accessed 1 September 2025).
- 4 S. Ali, N. S. Al-Nassar, M. I. Sindhu and M. Naveed, *Res. Int. Bus. Finance*, 2025, **74**, 102698.
- 5 N. Fulghum, C. Bruce-Lockhart and L. Orso, Solar BRICS: Emerging economies now lead the world's clean energy race, *Ember*, 3 July 2025, <https://ember-energy.org/latest-insights/solar-brics-emerging-economies-now-lead-the-worlds-clean-energy-race/> (accessed 3 March 2026).
- 6 O. Almora, G. C. Bazan, C. I. Cabrera, L. A. Castriotta, S. Erten-Ela, K. Forberich, K. Fukuda, F. Guo, J. Hauch, A. W. Y. Ho-Baillie, T. J. Jacobsson, R. A. J. Janssen, T. Kirchartz, R. R. Lunt, X. Mathew, D. B. Mitzi, M. K. Nazeeruddin, J. Nelson, A. F. Nogueira, Ulrich. W. Paetzold, B. P. Rand, U. Rau, T. Someya, C. Sprau, L. Vaillant-Roca and C. J. Brabec, *Adv. Energy Mater.*, 2025, **15**, 2404386.
- 7 NREL, Chart of Best Research-Cell Efficiencies Provided by NREL. <https://www.nrel.gov/pv/cell-efficiency.html>, <https://www.nrel.gov/pv/cell-efficiency.html>, (accessed 1 August 2025).
- 8 M. V. Khenkin, E. A. Katz, A. Abate, G. Bardizza, J. J. Berry, C. Brabec, F. Brunetti, V. Bulović, Q. Burlingame, A. Di Carlo, R. Checharoen, Y. B. Cheng, A. Colsmann, S. Cros, K. Domanski, M. Dusza, C. J. Fell, S. R. Forrest, Y. Galagan, D. Di Girolamo, M. Grätzel, A. Hagfeldt, E. von Hauff, H. Hoppe, J. Kettle, H. Köbler, M. S. Leite, S. (Frank) Liu, Y. L. Loo, J. M. Luther, C. Q. Ma, M. Madsen, M. Manceau, M. Matheron, M. McGehee, R. Meitzner, M. K. Nazeeruddin, A. F. Nogueira, Ç. Odabaşı, A. Osherov, N. G. Park, M. O. Reese, F. De Rossi, M. Saliba, U. S. Schubert, H. J. Snaith, S. D. Stranks, W. Tress, P. A. Troshin, V. Turkovic, S. Veenstra, I. Visoly-Fisher, A. Walsh, T. Watson, H. Xie, R. Yıldırım, S. M. Zakeeruddin, K. Zhu and M. Lira-Cantu, *Nat. Energy*, 2020, **5**, 35–49.




- 9 Y. Liu, Z. Zhang, T. Wu, W. Xiang, Z. Qin, X. Shen, Y. Peng, W. Shen, Y. Li and L. Han, *Nanomicro Lett.*, 2025, **17**, 1–11.
- 10 M. I. Ustinova, L. A. Frolova, A. V. Rasmetyeva, N. A. Emelianov, M. N. Sarychev, G. V. Shilov, P. P. Kushch, N. N. Dremova, G. A. Kichigina, A. I. Kukhareenko, D. P. Kiryukhin, E. Z. Kurmaev, I. S. Zhidkov and P. A. Troshin, *J. Mater. Chem. A Mater.*, 2024, **12**, 13219–13230.
- 11 J. Yang, Q. Bao, L. Shen and L. Ding, *Nano Energy*, 2020, **76**, 105019.
- 12 G. M. Paternò, V. Robbiano, L. Santarelli, A. Zampetti, C. Cazzaniga, V. Garcia Sakai and F. Cacialli, *Sustain. Energy Fuels*, 2019, **3**, 2561–2566.
- 13 L. McMillon-Brown, J. M. Luther and T. J. Peshek, *ACS Energy Lett.*, 2022, **7**, 1040–1042.
- 14 D. Angmo, S. Yan, D. Liang, A. D. Scully, A. S. R. Chesman, M. Kellam, N. W. Duffy, N. Carter, R. Chantler, C. Chen and M. Gao, *ACS Appl. Energy Mater.*, 2024, **7**, 1777–1791.
- 15 X. Lu, Z. Wang, Q. Lin, J. Sheng, A. F. Akbulatov, S. M. Aldoshin, P. Troshin, Y. Shi and L. Li, *Authorea (preprint)*, DOI:10.22541/au.175547361.10502563/v1.
- 16 J. Y. Kim, J. W. Lee, H. S. Jung, H. Shin and N. G. Park, *Chem. Rev.*, 2020, **120**, 7867–7918.
- 17 L. Wu, S. Hu, F. Yang, G. Li, J. Wang, W. Zuo, J. J. Jerónimo-Rendon, S.-H. Turren-Cruz, M. Saba, M. Saliba, M. K. Nazeeruddin, J. Pascual, M. Li and A. Abate, *Nat. Rev. Mater.*, 2025, **10**, 536–549.
- 18 V. V Ozerova, N. A. Emelianov, D. P. Kiryukhin, P. P. Kushch, G. V Shilov, G. A. Kichigina, S. M. Aldoshin, L. A. Frolova and P. A. Troshin, *J. Phys. Chem. Lett.*, 2023, **14**, 743–749.
- 19 Y. Ahmed, X. Qi, P. Moazzezi and M. I. Saidaminov, *ACS Energy Lett.*, 2026, **11** (1), 79–89. DOI:10.1021/acseenergylett.5c03275.
- 20 M. G. D. Guaita, R. Szostak, F. M. C. da Silva, A. de Morais, R. F. Moral, T. Kodalle, V. C. Teixeira, C. M. Sutter-Fella, H. C. N. Tolentino and A. F. Nogueira, *Adv. Funct. Mater.*, 2024, **34**, 1–11.
- 21 N. A. Emelianov, V. V. Ozerova, Y. S. Fedotov, M. V. Zhidkov, R. R. Saifutyarov, M. S. Malozovskaya, M. S. Leshchev, E. V. Golosov, L. A. Frolova and P. A. Troshin, *Materials*, 2023, **16**, 1–10.
- 22 M. Lee, L. Wang, D. Zhang, J. Li, J. Kim, J. S. Yun and J. Seidel, *Advanced Materials*, 2024, **36**, 2407291. <https://doi.org/10.1002/adma.202407291>
- 23 T. A. de Souza Carvalho, L. F. Magalhaes, C. I. do Livramento Santos, T. A. Z. de Freitas, B. R. Carvalho Vale, A. F. Vale da Fonseca and M. A. Schiavon, *Chemistry - A European Journal*, 2023, **29**, e202202518.
- 24 M. I. Ustinova, L. A. Frolova, A. V. Rasmetyeva, N. A. Emelianov, M. N. Sarychev, P. P. Kushch, N. N. Dremova, G. A. Kichigina, A. I. Kukhareenko, D. P. Kiryukhin, E. Z. Kurmaev, I. S. Zhidkov and P. A. Troshin, *Chemical Engineering Journal*, 2024, **493**, 152522.
- 25 M. I. Ustinova, G. V Shilov, D. V Korchagin, N. N. Dremova, P. A. Troshin, S. M. Aldoshin



- and L. A. Frolova, *Mendeleev Communications*, 2025, **35**, 569–572.
- 26 D. Pérez-del-Rey, C. Dreessen, A. M. Igual-Muñoz, L. van den Hengel, M. C. Gélvez-Rueda, T. J. Savenije, F. C. Grozema, C. Zimmermann and H. J. Bolink, *Solar RRL*, 2020, **4**, 1–6.
- 27 F. Lang, G. E. Eperon, K. Frohna, E. M. Tennyson, A. Al-Ashouri, G. Kourkafas, J. Bundesmann, A. Denker, K. G. West, L. C. Hirst, H. C. Neitzert and S. D. Stranks, *Adv. Energy Mater.*, 2021, **11**, 2102246. DOI:10.1002/aenm.202102246.
- 28 M. I. Ustinova, M. N. Sarychev, N. A. Emelianov, Y. Li, Y. Zhuo, T. Zheng, S. D. Babenko, E. D. Tarasov, P. P. Kushch, N. N. Dremova, G. A. Kichigina, A. V Rasmetyeva, A. I. Kukharenko, D. P. Kiryukhin, E. Z. Kurmaev, X. Xu, P. A. Troshin, L. A. Frolova and I. S. Zhidkov, *EcoMat*, 2025, **7**, e12512.
- 29 M. I. Ustinova, A. V Rasmetyeva, A. I. Kukharenko, M. V Lobanov, P. P. Kushch, N. A. Emelianov, D. V Korchagin, G. A. Kichigina, M. N. Sarychev, D. P. Kiryukhin, E. Z. Kurmaev, P. A. Troshin, L. A. Frolova and I. S. Zhidkov, *Mater. Today Energy*, 2024, **45**, 101687.
- 30 G. Kakavelakis, M. Gedda, A. Panagiotopoulos, E. Kymakis, T. D. Anthopoulos and K. Petridis, *Adv. Sci.*, 2020, **7**, 2002098. DOI:10.1002/adv.202002098.
- 31 N. Shen, X. He, T. Gao, B. Xiao, Y. Wang, R. Ren, H. Qin, K. S. Bayikadi, Z. Liu, J. A. Peters, B. W. Wessels, L. Wang, X. Ouyang, S. Wei, Q. Sun, X. Liu, Y. Lai, X. Ouyang, Z. Chai, M. G. Kanatzidis and Y. He, *Nature Communications*, 2025, **16**, 8113. View Article Online DOI: 10.1039/D5YA00315F  
DOI:10.1038/s41467-025-63400-7.
- 32 Md. H. Miah, M. U. Khandaker, P. Saengkaew, A. Numan and M. A. Islam, *RSC Adv.*, 2025, **15**, 43446–43486.
- 33 L. A. Frolova, S. Y. Luchkin, Y. Lekina, L. G. Gutsev, S. A. Tsarev, I. S. Zhidkov, E. Z. Kurmaev, Z. X. Shen, K. J. Stevenson, S. M. Aldoshin and P. A. Troshin, *Adv. Energy Mater.*, 2021, **11**, 2002934.
- 34 M. I. Ustinova, G. V Shilov, D. V Korchagin, P. A. Troshin, S. M. Aldoshin and L. A. Frolova, *Mendeleev Communications*, 2025, **35**, 573–576.
- 35 I. S. Zhidkov, A. F. Akbulatov, A. I. Poteryaev, A. I. Kukharenko, A. V. Rasmetyeva, L. A. Frolova, P. A. Troshin and E. Z. Kurmaev, *Coatings*, 2023, **13**, 2–9.
- 36 A. F. Akbulatov, M. I. Ustinova, L. Gutsev, S. A. Tsarev, N. N. Dremova, I. Zhidkov, S. Yu. Luchkin, B. R. Ramachandran, L. Frolova, E. Z. Kurmaev, K. J. Stevenson, S. M. Aldoshin and P. A. Troshin, *Nano Energy*, 2021, **86**, 106082.
- 37 M. I. Ustinova, G. V Shilov, P. A. Troshin, S. M. Aldoshin and L. A. Frolova, *Inorganics*, 2025, **13** (1), 13. DOI: 10.3390/inorganics13010013.
- 38 M. I. Ustinova, M. V Lobanov, G. V Shilov, N. N. Dremova, A. F. Akbulatov, L. G. Gutsev, I. S. Zhidkov, E. Z. Kurmaev, F. A. Prudnov, A. V Ivanov, L. A. Frolova, S. M. Aldoshin and P. A. Troshin, *Adv. Funct. Mater.*, 2025, **35**, 2407571.
- 39 A. W. Y. Ho-Baillie, H. G. J. Sullivan, T. A. Bannerman, H. P. Talathi, J. Bing, S. Tang, A.




- Xu, D. Bhattacharyya, I. H. Cairns and D. R. McKenzie, *Adv. Mater. Technol.*, 2022, **7**, 2101059. DOI: 10.1002/admt.202101059.
- 40 M. Chen, Y. Dong, Y. Zhang, X. Zheng, G. R. McAndrews, Z. Dai, Q. Jiang, S. You, T. Liu, S. P. Harvey, K. Zhu, V. Oliveto, A. Jackson, R. Witteck, L. M. Wheeler, N. P. Padture, P. J. Dyson, M. D. McGehee, M. K. Nazeeruddin, M. C. Beard and J. M. Luther, *ACS Energy Lett.*, 2024, **9**, 2582–2589.
- 41 A. F. Akbulatov, M. I. Ustinova, G. V. Shilov, N. N. Dremova, I. S. Zhidkov, E. Z. Kurmaev, L. A. Frolova, A. F. Shestakov, S. M. Aldoshin and P. A. Troshin, *Journal of Physical Chemistry Letters*, 2021, **12**, 4362–4367.
- 42 A. F. Akbulatov, L. A. Frolova, N. N. Dremova, I. Zhidkov, V. M. Martynenko, S. A. Tsarev, S. Y. Luchkin, E. Z. Kurmaev, S. M. Aldoshin, K. J. Stevenson and P. A. Troshin, *Journal of Physical Chemistry Letters*, 2020, **11**, 333–339.
- 43 J. S. Yun, J. Kim, T. Young, R. J. Patterson, D. Kim, J. Seidel, S. Lim, M. A. Green, S. Huang and A. Ho-Baillie, *Adv. Funct. Mater.*, 2018, **28**, 1705363.
- 44 Q. An, F. Paulus, D. Becker-Koch, C. Cho, Q. Sun, A. Weu, S. Bitton, N. Tessler and Y. Vaynzof, *Matter*, 2021, **4**, 1683–1701.
- 45 D. W. DeQuilettes, S. M. Vorpahl, S. D. Stranks, H. Nagaoka, G. E. Eperon, M. E. Ziffer, H. J. Snaith and D. S. Ginger, *Science*, 2015, **348**, 683–686. DOI:10.1126/science.aaa5333
- 46 F. L. de Araujo, M. Stefanelli, A. Agresti, S. Pescetelli, A. Di Vito, M. A. Der Maur, L. Vesce, A. F. Nogueira and A. Di Carlo, *Nano Energy*, 2025, **142**, 111279. View Article Online  
DOI: 10.1039/D5YA00315F  
DOI:10.1016/j.nanoen.2025.111279.
- 47 L. Scalon and Y. Vaynzof, *Adv. Energy Mater.*, 2025, **2502686**, 1–15. DOI:10.1002/aenm.202502686
- 48 I. C. Ribeiro, F. D. Picoli, P. I. R. Moraes, A. F. V. Fonseca, L. N. Oliveira, A. F. Nogueira and J. L. F. Da Silva, *ACS Appl. Energy Mater.*, 2025, **8**, 3346–3359.
- 49 J. Ryeom, D. Y. Park, Y. M. Bahk, G. Choi and M. S. Jeong, *J. Alloys Compd.*, 2025, **1030**, 180811.
- 50 Y. Boeijs, F. Lie, M. Dubajić, E. Garip, A. Maufort, R. I. Biega, S. Lenaers, M. Sauty, P. Ghosh, A. Radić, A. Loher, P. La Magna, H. Salway, A. Ashoka, X. W. Chua, Q. Gu, K. Van Hecke, L. Lutsen, D. Vanderzande, A. Rao, W. T. M. Van Gompel, L. Leppert and S. D. Stranks, *J. Am. Chem. Soc.*, 2025, **147**, 31541–31557.
- 51 Z. Shi, S. Liu, R. Luo, J. Ma, H. Tian, X. Wang, Z. Dong, X. Guo, J. Chen, J. Feng, C. Xiao, Y. Wu, W. Hu and Y. Hou, *J. Am. Chem. Soc.*, 2025, **147** (1), 1055–1062. DOI:10.1021/jacs.4c14473.
- 52 M. G. D. Guaita, R. Szostak, F. M. C. da Silva, Z. Feng, L. Scalon, V. C. Teixeira, T. Kodalle, C. M. Sutter-Fella, S. S. Jang, H. C. N. Tolentino and A. F. Nogueira, *Solar RRL*, 2025, **9**, 1–16. DOI: 10.1002/solr.202500404
- 53 I. Metcalf, S. Sidhik, H. Zhang, A. Agrawal, J. Persaud, J. Hou, J. Even and A. D. Mohite, *Chem. Rev.*, 2023, **123**, 9565–9652.
- 54 R. F. Moral, A. A. Malfatti-Gasperini, L. G. Bonato, B. R. C. Vale, A. F. V. Fonseca, L. A.



- Padilha, C. L. P. Oliveira and A. F. Nogueira, *Mater. Horiz.*, 2023, **10**, 5822–5834.
- 55 R. Wang, X. Dong, Q. Ling, Z. Hu, Y. Gao, Y. Chen and Y. Liu, *Angew. Chem. Int. Ed.*, 2023, **62**, e202314690. DOI:10.1002/ange.202314690.
- 56 Y. Tang, X. Dong, X. Li, Y. Zhou, C. Ran and Z. Wu, *Chemical Engineering Journal*, 2024, **499**, 156503.
- 57 N. N. Dremova, G. V. Shilov, P. A. Troshin and L. A. Frolova, *Mendeleev Communications*, 2024, **34**, 481–483.
- 58 L. Scalon, C. A. Nogueira, A. F. V. Fonseca, P. E. Marchezi, R. F. Moral, G. Grancini, T. Kodalle, C. M. Sutter-Fella, C. C. Oliveira, L. F. Zagonel and A. F. Nogueira, *ACS Appl. Mater. Interfaces*, 2024, **16**, 51727–51737.
- 59 T. Kodalle, M. M. Byranvand, M. Goudreau, C. Das, R. Roy, M. Kot, S. Briesenick, M. Zohdi, M. Rai, N. Tamura, J. I. Flege, W. Hempel, C. M. Sutter-Fella and M. Saliba, *Advanced Materials*, 2024, **36**, 1–12.
- 60 J. Zhang, J. Wu, S. Langner, B. Zhao, Z. Xie, J. A. Hauch, H. A. Afify, A. Barabash, J. Luo, M. Sytnyk, W. Meng, K. Zhang, C. Liu, A. Osvet, N. Li, M. Halik, W. Heiss, Y. Zhao and C. J. Brabec, *Adv. Funct. Mater.*, 2022, **32**, 1–9.
- 61 B. P. Kore, W. Zhang, B. W. Hoogendoorn, M. Safdari and J. M. Gardner, *Commun. Mater.*, 2021, **2**, 1–10.
- 62 M. Choghaei, M. Schiffer, V. Tyagi, M. Righetto, J. Du, M. Buchmüller, K. O. Brinkmann, G. Brocks, P. Görrn, L. M. Herz, S. Tao, T. Riedl and S. Olthof, *J. Mater. Chem. A*, 2025, **13**, 18935–18947.
- 63 C. Ma, M. C. Kang, S. H. Lee, Y. Zhang, D. H. Kang, W. Yang, P. Zhao, S. W. Kim, S. J. Kwon, C. W. Yang, Y. Yang and N. G. Park, *J. Am. Chem. Soc.*, 2023, **145**, 24349–24357. DOI:10.1039/D5YA00315F
- 64 B. Toon, S. Ong, B. Febriansyah, T. J. N. Hooper, A. Kurkin, Y. Lekina, Y. Li, Z. Tan, N. Mathews and Z. Shen, *Chemistry of Materials*, 2025, **37** (18), 7178–7192. DOI:10.1021/acs.chemmater.5c01245.
- 65 R. Szostak, A. de Souza Gonçalves, J. N. de Freitas, P. E. Marchezi, F. L. de Araújo, H. C. N. Tolentino, M. F. Toney, F. das Chagas Marques and A. F. Nogueira, *Chem. Rev.*, 2023, **123**, 3160–3236.
- 66 X. Zheng, S. Ahmed, Y. Zhang, G. Xu, J. Wang, D. Lu, T. Shi, J. Tang, L. Yan, W. Chen, P. Han, Z. Liu, D. Khan, X. Wang, Z. Tang, *Nano-Micro Lett.*, 2026, **18**, 62. DOI:10.1007/s40820-025-01913-y
- 67 A. A. Sutanto, R. Szostak, N. Drigo, V. I. E. Queloz, P. E. Marchezi, J. C. Germino, H. C. N. Tolentino, M. K. Nazeeruddin, A. F. Nogueira and G. Grancini, *Nano Lett.*, 2020, **20**, 3992–3998.
- 68 S. Tan, M. C. Shih, Y. Lu, S. G. Choi, Y. Dong, J. H. Lee, I. Yavuz, B. W. Larson, S. Y. Park, T. Kodalle, R. Zhang, M. J. Grotevent, Y. K. Lin, H. Zhu, V. Bulović, C. M. Sutter-Fella, N. G. Park, M. C. Beard, J. W. Lee, K. Zhu and M. G. Bawendi, *Science*, 2025, **388**, 639–645.
- 69 T. Kodalle, R. F. Moral, L. Scalon, R. Szostak, M. Abdelsamie, P. E. Marchezi, A. F. Nogueira and C. M. Sutter-Fella, *Adv. Energy Mater.*, 2023, **13**, 1–14.
- 70 J. Rodríguez-Romero, J. Sanchez-Diaz, C. Echeverría-Arrondo, S. Masi, D. Esparza, E.



- M. Barea and I. Mora-Seró, *ACS Energy Lett.*, 2020, **5**, 1013–1021.
- 71 H. Baishya, R. Das Adhikari, M. J. Patel, S. Laha, D. Yadav, K. Bhattacharyya and P. K. Iyer, *Small*, 2025, **07345**, 1–14.
- 72 J. C. Germino, R. Szostak, S. G. Motti, R. F. Moral, P. E. Marchezi, H. S. Seleghini, L. G. Bonato, F. L. De Araújo, T. D. Z. Atvars, L. M. Herz, D. Fenning, A. Hagfeldt and A. F. Nogueira, *ACS Photonics*, 2020, **7**, 2282–2291.
- 73 L. Scalon, R. Szostak, F. L. Araújo, K. F. Adriani, J. F. R. V. Silveira, W. X. C. Oliveira, J. L. F. Da Silva, C. C. Oliveira and A. F. Nogueira, *JACS Au*, 2022, **2**, 1306–1312.
- 74 R. J. E. Westbrook, T. J. Macdonald, W. Xu, L. Lanzetta, J. M. Marin-Beloqui, T. M. Clarke and S. A. Haque, *J. Am. Chem. Soc.*, 2021, **143**, 12230–12243.
- 75 Z. Min, B. Wang, Y. Kong, J. Guo, X. Ling, W. Ma and J. Yuan, *ChemSusChem*, 2025, **18**(4), e202401852 DOI:10.1002/cssc.202401852.
- 76 A. F. V. Fonseca, L. Scalon, B. R. C. Vale, M. G. D. Guaita, J. Bettini, Z. C. Brandão, L. F. Zagonel, L. A. Padilha and A. F. Nogueira, *ACS Energy Lett.*, 2024, **9**, 3177–3186.
- 77 J. Yuan, A. Hazarika, Q. Zhao, X. Ling, T. Moot, W. Ma and J. M. Luther, *Joule*, 2020, **4**, 1160–1185.
- 78 C. de Mayrinck, A. F. V. da Fonseca and M. A. Schiavon, *Quim. Nova*, 2020, **43**, 1264–1276.
- 79 L. Protesescu, S. Yakunin, M. I. Bodnarchuk, F. Krieg, R. Caputo, C. H. Hendon, R. X. Yang, A. Walsh and M. V. Kovalenko, *Nano Lett.*, 2015, **15**, 3692–3696. DOI: 10.1039/D5YA00315F
- 80 X. Zhao, D. Li, X. Zhang, H. Huang, C. Zhao, W. Ma and J. Yuan, *Journal of Energy Chemistry*, 2024, **92**, 87–94.
- 81 S. Y. Park, G. Seo, T. Kim *et al.*, *Adv. Optical Mater.*, 2025, **13**, e00968. DOI:10.1002/adom.202500968.
- 82 C. Zhao, C. Cazorla, X. Zhang, H. Huang, X. Zhao, D. Li, J. Shi, Q. Zhao, W. Ma and J. Yuan, *J. Am. Chem. Soc.*, 2024, **146**, 4913–4921.
- 83 Q. A. Akkerman, V. D’Innocenzo, S. Accornero, A. Scarpellini, A. Petrozza, M. Prato and L. Manna, *J. Am. Chem. Soc.*, 2015, **137**, 10276–10281.
- 84 D. Li, C. Zhao, X. Zhang, X. Zhao, H. Huang, H. Li, F. Li and J. Yuan, *Adv. Mater.* 2025, **37**, 2417346. DOI: 10.1002/adma.202417346.
- 85 A. F. V. da Fonseca, B. R. C. Vale, T. A. de S. Carvalho, J. Bettini, A. C. Pereira and M. A. Schiavon, *Journal of Physical Chemistry C*, 2021, **125**, 27363–27371.
- 86 J. M. Burrell, B. Adhikari, S. L. Abiodun and A. B. Greytak, *ACS Energy Lett.*, 2025, **10** (9), 4158–4183.
- 87 Y. Xu, X. Zhang, C. Zhu and Q. Yu, *J. Mater. Chem. A*, 2025, **13**, 29688–29705.
- 88 L. M. Wheeler, E. M. Sanehira, A. R. Marshall, P. Schulz, M. Suri, N. C. Anderson, J. A. Christians, D. Nordlund, D. Sokaras, T. Kroll, S. P. Harvey, J. J. Berry, L. Y. Lin and J. M. Luther, *J. Am. Chem. Soc.*, 2018, **140**, 10504–10513.



- 89 Y. Kong, H. Li, B. Li, D. Li, J. Guo, Q. Zhou, Z. Wang, W. Ma and J. Yuan, *Journal of Energy Chemistry*, 2025, **109**, 1–7.
- 90 C. Zhao, D. Li, X. Zhang, H. Huang, C. Cazorla, X. Zhao, H. Li, Y. Chen, W. Zhu, T. Wu and J. Yuan, *Adv. Mater.*, 2025, **37**, e12201. DOI:10.1002/adma.202512201.
- 91 M. H. de M. Rodrigues, D. M. Guilhermitti Neto, I. D. Barcelos, C. Labre, C. A. R. Costa, J. B. de Souza, J. A. Sobrinho and A. F. Nogueira, *J. Mater. Chem. A*, 2025, **13**, 17799–17809.
- 92 C. Zhang, Y. Son, H. Kim, S. H. Lee, X. Liang, G. Fu, S. U. Lee, D. A. Park, Q. Jiang, K. Zhu and N. G. Park, *Joule*, 2024, **8**, 1394–1411.
- 93 A. F. V. Fonseca, G. M. Germano, L. Scalon, C. A. N. de Almeida, A. C. C. Barra, D. S. Ribeiro, Z. C. Brandão, F. C. Marques, I. Mora-Seró and A. F. Nogueira, *Mater. Today Chem.*, 2025, **50**, 103238.
- 94 H. Li, H. Huang, D. Li, X. Zhang, C. Zhao, X. Zhao, W. Ma and J. Yuan, *Energy Environ. Sci.*, 2024, **18**, 972–981.
- 95 X. Zhang, H. Huang, C. Zhao, L. Jin, C. Lee, Y. Li, D.-H. Ko, W. Ma, T. Wu and J. Yuan, *Nat. Energy*, 2024, **9**, 1378–1387.
- 96 A. F. V. Fonseca, C. E. Giarola, T. A. de S. Carvalho, F. S. Hojo de Souza and M. A. Schiavon, *Journal of Chemical Physics*, 2023, **159**, 184705.
- 97 Y. Han, B. Tang, L. Wang, H. Bao, Y. Lu, C. Guan, L. Zhang, M. Le, Z. Liu and M. Wu, *ACS Nano*, 2020, **14**, 14761–14768.
- 98 S. Diao, Q. Wu, S. Li, G. Xu, X. Ren, L. Tan, G. Jiang, P. Song and X. Meng, *Mater. Horiz.*, 2025, **12**, 4133–4164. DOI: 10.1039/D5YA00315F
- 99 Y. Deng, Y. Yuan, J. Ni, L. Zheng, J. Bi, J. Guo, R. Wang, H. Li, S. Zhang, H. Cai and J. Zhang, *ACS Appl. Energy Mater.*, 2025, **8**, 4701–4710.
- 100 Y. Ning, S. Guan, C. Cheng, B. Zhang, B. Qin and B. Huang, *J. Mater. Chem. C*, 2024, **13**, 758–765.
- 101 R. M. MacEiczyk, K. Dümbgen, I. Lignos, L. Protesescu, M. V. Kovalenko and A. J. Demello, *Chemistry of Materials*, 2017, **29**, 8433–8439.
- 102 G. Chen, X. Zhu, C. Xing, Y. Wang, X. Xu, J. Bao, J. Huang, Y. Zhao, X. Wang, X. Zhou, X. Du and X. Wang, *Adv. Photonics Res.*, 2023, **4**, 2200230. DOI:10.1002/adpr.202200230.
- 103 A. Li and C. Yi, *Solar RRL*, 2025, **9**, e202500681. DOI: 10.1002/solr.202500681.
- 104 R. Szostak, J. C. Silva, S. H. Turren-Cruz, M. M. Soares, R. O. Freitas, A. Hagfeldt, H. C. N. Tolentino and A. F. Nogueira, *Sci. Adv.*, 2019, **5**, 2–9.
- 105 N. A. Emelianov, V. V. Ozerova, I. S. Zhidkov, D. V. Korchagin, G. V. Shilov, A. L. Litvinov, E. Z. Kurmaev, L. A. Frolova, S. M. Aldoshin and P. A. Troshin, *Journal of Physical Chemistry Letters*, 2022, **13**, 2744–2749.
- 106 X. Zhang, H. Huang, C. Zhao and J. Yuan, *Chem. Soc. Rev.*, 2025, **54**, 3017–3060.





Data Availability Statement No new data were created or analyzed in this study. Data sharing is not applicable to this article.

View Article Online  
DOI: 10.1039/C5YA00315F

Open Access Article. Published on 12 March 2016. Downloaded on 4/3/2026 8:10:19 PM.  
This article is licensed under a Creative Commons Attribution-NonCommercial 3.0 Unported Licence.

