

# Dalton Transactions

Accepted Manuscript



This is an *Accepted Manuscript*, which has been through the Royal Society of Chemistry peer review process and has been accepted for publication.

*Accepted Manuscripts* are published online shortly after acceptance, before technical editing, formatting and proof reading. Using this free service, authors can make their results available to the community, in citable form, before we publish the edited article. We will replace this *Accepted Manuscript* with the edited and formatted *Advance Article* as soon as it is available.

You can find more information about *Accepted Manuscripts* in the [Information for Authors](#).

Please note that technical editing may introduce minor changes to the text and/or graphics, which may alter content. The journal's standard [Terms & Conditions](#) and the [Ethical guidelines](#) still apply. In no event shall the Royal Society of Chemistry be held responsible for any errors or omissions in this *Accepted Manuscript* or any consequences arising from the use of any information it contains.

Cite this: DOI: 10.1039/c0xx00000x

www.rsc.org/xxxxxx

ARTICLE TYPE

## Synthesis, structure and luminescence properties of a cadmium(II)-based coordination polymer with (*S*)-4,4'-bis(4-carboxyphenyl)-2,2'-bis(diphenylphosphinoyl)-1,1'-binaphthyl as chiral linker

5 **Witri Wahyu Lestari,<sup>a</sup> Huayna Cerqueira Streit,<sup>b</sup> Peter Lönnecke,<sup>a</sup> Claudia Wickleder,<sup>\*b</sup> and Evamarie Hey-Hawkins<sup>\*a</sup>**

Received (in XXX, XXX) Xth XXXXXXXXX 20XX, Accepted Xth XXXXXXXXX 20XX

DOI: 10.1039/b000000x

10 Solvothermal reaction of cadmium(II) nitrate with (*S*)-4,4'-bis(4-carboxyphenyl)-2,2'-bis(diphenylphosphinoyl)-1,1'-binaphthyl (**H<sub>2</sub>L**) in dimethylformamide (dmf) gave the two-dimensional chiral coordination polymer [ $\{\text{Cd}_2(\text{L})_2(\text{H}_2\text{O})\} \cdot 18 \text{ dmf} \}_n$  (**1**), which is thermally stable up to 400 °C according to DTA/TG analysis. According to single-crystal X-ray analysis, **1** forms layers in the  $[\bar{1}01]$  direction, which are relatively well separated from each other. Compound **1** exhibits ligand-based bluish  
15 luminescence, assigned to the  $S_1 \rightarrow S_0$  transition of the aromatic units in **L**. Emission spectra consist of nearly Gaussian shaped bands with maxima at 25574 and 24767  $\text{cm}^{-1}$  for **H<sub>2</sub>L** and **1**, respectively. Quantum efficiency reaches a remarkably high value of 42% for the Cd-based coordination polymer and 33% for the respective ligand. Emission intensity of **1** increases from 10 K to room temperature and decreases exponentially for temperatures up to 650 K.

20

### Introduction

Extended structures with permanent porosity, so-called metal-organic frameworks (MOFs)<sup>1</sup> have received much attention during the past decade. These coordination polymers can be one-dimensional structures such as chains, ladders, or tapes,<sup>2</sup> or two- and three-dimensional porous networks containing metal cations linked by suitable ligands to give infinite arrays,<sup>2,3,4</sup> which can exhibit diverse properties for a broad range of applications. Specific properties, such as gas sorption, separation and catalytic  
30 function, are influenced by the structure.<sup>5</sup> To modify these properties, the topology, rigidity and functionality of the ligands, as well as the metal cations, can be varied. Physical properties such as magnetism and luminescence result from combining intrinsic properties of the metal cations and the organic  
35 ligands.<sup>2b,5</sup>

Different approaches have been applied to explore the luminescence properties of coordination polymers and MOFs.<sup>6</sup> The ligand-based approach utilises the emission of light by extended conjugated  $\pi$  systems of the organic linker.<sup>6,7</sup> Another  
40 possibility is the use of emitting ions, e.g., lanthanides, as connecting points in the framework<sup>6,8</sup> or as guests within the pores of the framework.<sup>6,9</sup> Luminescence of coordination

polymers and MOFs containing transition metals ions is typically centred on the linker rather than on the metal. Thus, transition  
45 metal ions without unpaired electrons, such as  $\text{Zn}^{\text{II}}$  and  $\text{Cd}^{\text{II}}$ , can yield linker-based highly emissive materials.<sup>6,10,11</sup> Furthermore, molecular interactions can bring luminophores closer together in the solid state and thus enable electronic interactions between them (e.g., ligand-to-ligand charge transfer), which can cause  
50 spectral shifts, emission broadening, loss of vibronic structure, and increased emission lifetimes and quantum yields. Controlling these ligand–ligand interactions is important for applications that involve charge transport and to obtain tuneable emission colours.<sup>6</sup>



Employment of aromatic systems such as functionalised  
55 binaphthyl-derived ligands<sup>12,13,14,15</sup> as rigid linkers yields homochiral coordination polymers that have been studied in enantioselective processes<sup>13a</sup> and asymmetric catalysis,<sup>14a-d</sup> for chiral sensing<sup>13d,15</sup> and as luminescent materials.<sup>13b-c</sup> Furthermore, some one- and two-dimensional coordination polymers  
60 containing phosphorus or the oxygen atom of phosphine oxides as donors and silver(I),<sup>16</sup> gold(I)<sup>17</sup> and indium(III)<sup>18</sup> exhibit strong luminescence properties. Herein, we present the synthesis, structure and optical properties of a chiral coordination polymer, namely, [ $\{\text{Cd}_2(\text{L})_2(\text{H}_2\text{O})\} \cdot 18 \text{ dmf} \}_n$  (**1**), which is based on  $\text{Cd}^{\text{II}}$   
65 and (*S*)-4,4'-bis(4-carboxyphenyl)-2,2'-bis(diphenylphosphinoyl)-1,1'-binaphthyl as linker. Some Cd-based MOFs with 1,3- or 1,4-

benzenedicarboxylate (BDC) and its derivatives,<sup>19</sup> 2,2'-, 3,3'-, 3,4' or 4,4'-biphenyl dicarboxylate (BPDC)<sup>19d,20</sup> or modified 2,2'-, 4,4'-, 6,6'- or 3,3'-di- and tetracarboxylate binaphthyl linkers and their derivatives<sup>11,15</sup> exhibit versatile geometrical arrangements


around the Cd<sup>II</sup> cation, showing coordination numbers of 4 to 8.<sup>11,15,19,20</sup> Even a coordination number of 9 was observed with oxalato ligands as linkers giving rise to a diamondoid network.<sup>21</sup>

## Results and Discussion

The reaction of **H<sub>2</sub>L**<sup>22</sup> with cadmium(II) nitrate under solvothermal conditions in dmf progressively heated to 65, 75 and 85 °C (each for 24 h) gave 2D coordination polymer **1**, which is insoluble in water and organic solvents (Scheme 1). Compound **1** crystallises in the monoclinic space group C2 with four molecules in the unit cell.

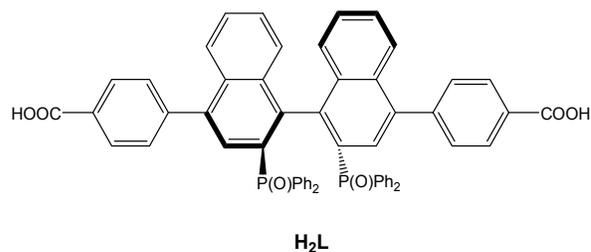

Scheme 1 Synthesis of **1**.

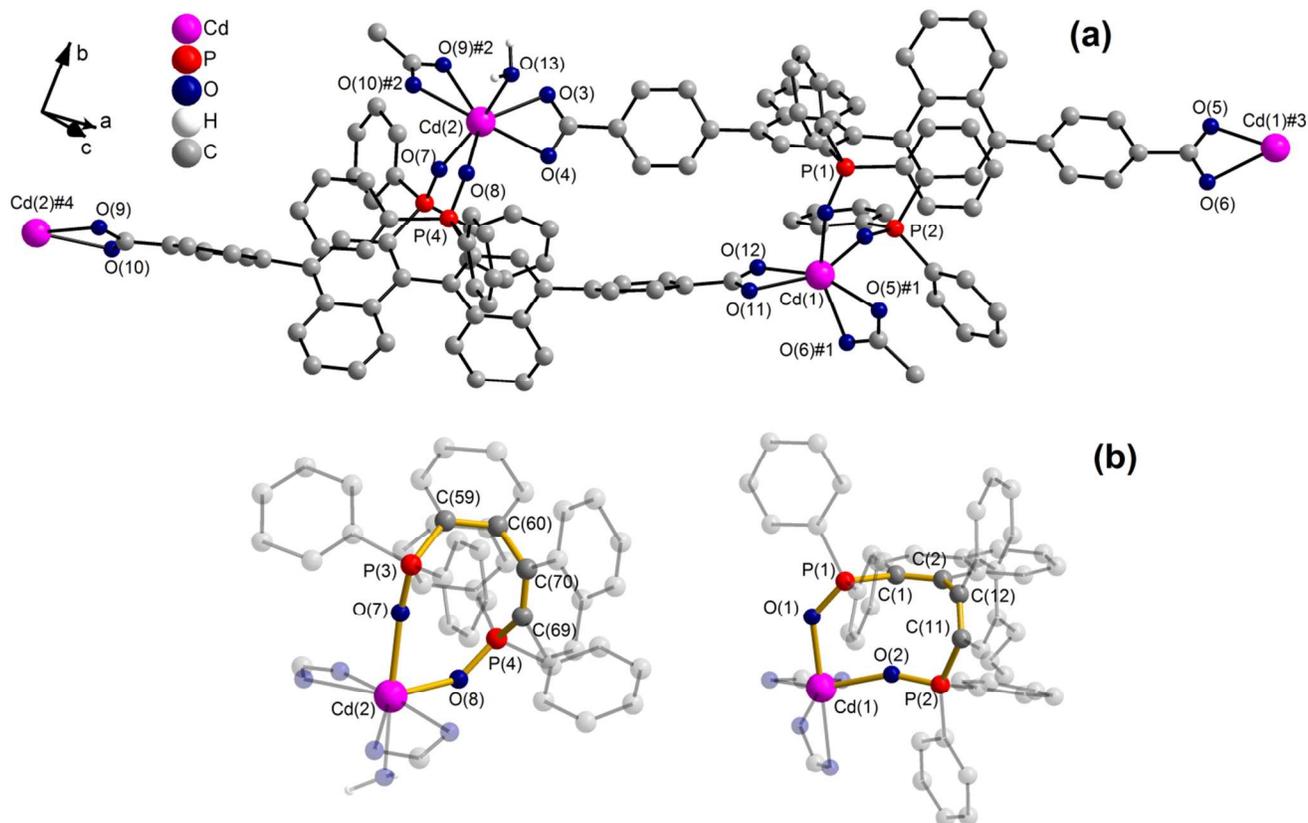

**Fig. 1** a) Section of the two-dimensional network of **1**, showing hexa- (Cd1) and heptacoordinated (Cd2) metal centres, with an  $\mu_3, \eta^2-\eta^2$  coordination mode of the dianionic ligand. Symmetry transformations used to generate equivalent atoms: #1:  $-x+3/2, y-1/2, -z+2$ ; #2:  $-x+1/2, y+1/2, -z+1$ ; #3:  $-x+3/2, y+1/2, -z+2$ ; #4:  $-x+1/2, y-1/2, -z+1$ ; b) Nine-member rings formed from Cd1 and Cd2 with phosphine-oxide moiety.

**1** forms layers in  $[\bar{1}01]$  (Figure 2) in which two differently coordinated cadmium atoms are linked via dianionic **L** ligands. One cadmium atom (Cd1) is hexacoordinate, and the other (Cd2) heptacoordinate. Both cadmium atoms are coordinated by two bidentate COO groups (O-Cd-O 57.1(2)–53.2(2)°, Cd1–O 2.209(5)–2.336(5) Å and Cd2–O from 2.253(5) to 2.437(7) Å, Table 1). The O-Cd-O bond angles and Cd–O bond lengths are in a good agreement with those reported in the literature for similar compounds.<sup>19c-f,20a,c</sup> Additionally, the two oxygen atoms of the

bis(phosphine oxide) fragment coordinate to both cadmium atoms in a chelating fashion, forming nine-membered rings (Cd1–O1–P1–C1–C2–C12–C11–P2–O2 and Cd2–O7–P3–C59–C60–C70–C69–O8, Figure 1b) with O–Cd–O bond angles of 79.8(2) and 81.5(2)° and Cd–O bond lengths of 2.209(5) (Cd1–O1) to 2.301(6) (Cd2–O7) Å, respectively. The dihedral angles between the binaphthyl rings are slightly smaller (76.7(3) and 79.6(4)°) than the dihedral angle of the free ligand (82.05(4)°).<sup>22</sup> Furthermore, one water molecule is coordinated to Cd2 (Cd2–O13 2.409(8) Å) (Figure

1a). The topology of the resulting two-dimensional network shows a 3-c net with point (Schläfli) symbol  $\{4.8^2\}$  according to TOPOS<sup>23</sup> (Figure 3) and the RCSR database.<sup>24</sup>

5 **Table 1** Selected bond lengths and bond angles of **1**

Bond lengths [Å]		Bond angles [°]	
Cd(1)–O(1)	2.209(5)	O(1)–Cd(1)–O(2)	79.8(2)
Cd(1)–O(2)	2.234(5)	O(1)–Cd(1)–O(5)#1	98.0(2)
Cd(1)–O(5)#1	2.283(5)	O(2)–Cd(1)–O(5)#1	91.5(2)
Cd(1)–O(6)#1	2.336(5)	O(5)#1–Cd(1)–O(6)#1	57.1(2)
Cd(1)–O(11)	2.297(6)	O(1)–Cd(1)–O(11)	94.7(2)
Cd(1)–O(12)	2.292(5)	O(12)–Cd(1)–O(11)	55.9(2)
Cd(2)–O(3)	2.437(7)	O(4)–Cd(2)–O(3)	53.2(2)
Cd(2)–O(4)	2.291(5)	O(9)#2–Cd(2)–O(10)#2	53.9(2)
Cd(2)–O(7)	2.301(6)	O(10)#2–Cd(2)–O(13)	81.4(2)
Cd(2)–O(8)	2.253(5)	O(8)–Cd(2)–O(7)	81.5(2)
Cd(2)–O(9)#2	2.349(6)	P(1)–O(1)–Cd(1)	133.3(3)
Cd(2)–O(10)#2	2.409(6)	P(2)–O(2)–Cd(1)	157.4(3)
Cd(2)–O(13)	2.409(8)	P(3)–O(7)–Cd(2)	163.8(3)
P(1)–O(1)	1.520(6)	P(4)–O(8)–Cd(2)	138.9(4)
P(2)–O(2)	1.497(5)		
P(3)–O(7)	1.495(6)		
P(4)–O(8)	1.476(6)		

Symmetry transformations used to generate equivalent atoms:

#1:  $-x+3/2, y-1/2, -z+2$ ; #2:  $-x+1/2, y+1/2, -z+1$

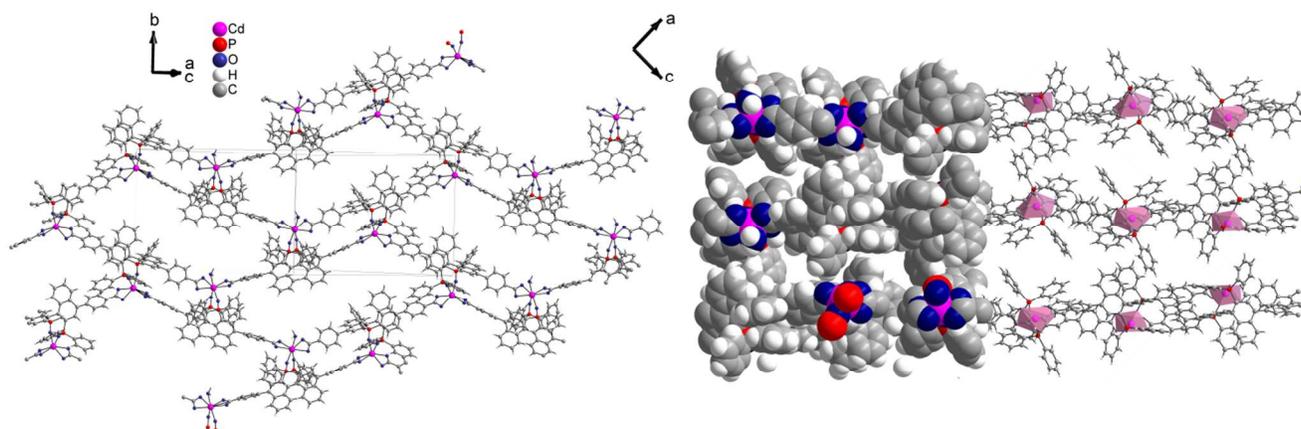


Fig. 2  $[101]$  layers of **1** (left) and space-filling model and polyhedral design (right), Diamond<sup>25</sup>.

## Luminescence properties


The free organic linker **H<sub>2</sub>L** and compound **1** show violet-blue emission on excitation with a UV lamp (Fig. 4a and 5a) at room temperature as solids. All emission bands are slightly unsymmetrical Gaussian-shaped. For **H<sub>2</sub>L**, the emission spectrum is centred invariably at 25574 cm<sup>-1</sup> for different excitation energies, e.g., 30864 cm<sup>-1</sup>, with full width at half maximum (FWHM) of 3812 cm<sup>-1</sup> (Fig. 4b). A comparable behaviour is observed for the emission spectrum of **1** (Fig. 5b), which is centred at 24767 cm<sup>-1</sup>, about 807 cm<sup>-1</sup> red-shifted in comparison to **H<sub>2</sub>L** and the width reduced (FWHM = 3370 cm<sup>-1</sup>). The similar positions of the emission bands in **H<sub>2</sub>L** and **1** result in similar colour coordinates (**H<sub>2</sub>L**:  $x = 0.1697, y = 0.0801$  and **1**:  $x = 0.1595, y = 0.0396$ , Fig. 6).

The dmf molecules occupy the space between the layers. The water molecule coordinated to Cd2 forms hydrogen bonds with two dmf molecules (O13–H13B···O202 and O13–H13A···O205;  $d(\text{H}\cdots\text{A}) = 1.75$  and  $1.65$  Å,  $d(\text{D}\cdots\text{A}) = 2.73(1)$  and  $2.63(2)$  Å and  $\angle(\text{D}–\text{H}\cdots\text{A}) = 169.7$  and  $172.0^\circ$ , respectively). In addition, very weak  $\pi\cdots\pi$  interactions are observed between the layers. Removal of the solvent (by exposing the crystals to air for a couple of minutes) results in destruction of the structure (confirmed by single-crystal and powder X-ray diffraction; see ESI).


The IR spectrum of **1** shows the bands for the coordinated carboxylate group at 1669 and 1594 cm<sup>-1</sup>, the coordinated water molecule at 3442 cm<sup>-1</sup> and the P=O group at 1181 cm<sup>-1</sup>.

Thermogravimetric analysis (TGA) of **1** after drying overnight in air indicated loss of one water molecule and three dmf molecules (calcd. and observed 7.09%) in the range of 100 to 200 °C. No mass loss was detected between 200 and 400 °C, confirming the thermal stability of **1** up to 400 °C. Gradual decomposition occurred above 400 °C; the free ligand **H<sub>2</sub>L** is thermally stable up to 420 °C<sup>22</sup> (see ESI).

As discussed previously,<sup>20f</sup> the positions of the bands can be explained by the different dihedral angles of the aromatic rings in **1** and **H<sub>2</sub>L**. In general, a smaller dihedral angle results in enhanced interactions of the  $\pi$  electrons, shifting the emission bands to lower energies. Here, the smaller dihedral angles between the binaphthyl rings in **1** ( $76.7(3)^\circ$  and  $79.6(4)^\circ$ ) compared to that of  $82.05(4)^\circ$  in the corresponding 4,4'-substituted binaphthyl,<sup>22</sup> explain the red shift of **1** (Fig. 5b). Although the dihedral angles in the excited states are unknown, it can be assumed that the conformations will not change remarkably during the excitation processes in the rigid structures. The differences in widths of the emission bands can most probably be explained by distinct interatomic distances of the excited states relative to the ground states of these two compounds. Obviously, this interatomic distance is smaller for **1** than for **H<sub>2</sub>L**, perhaps due to the more rigid structure of **1**.

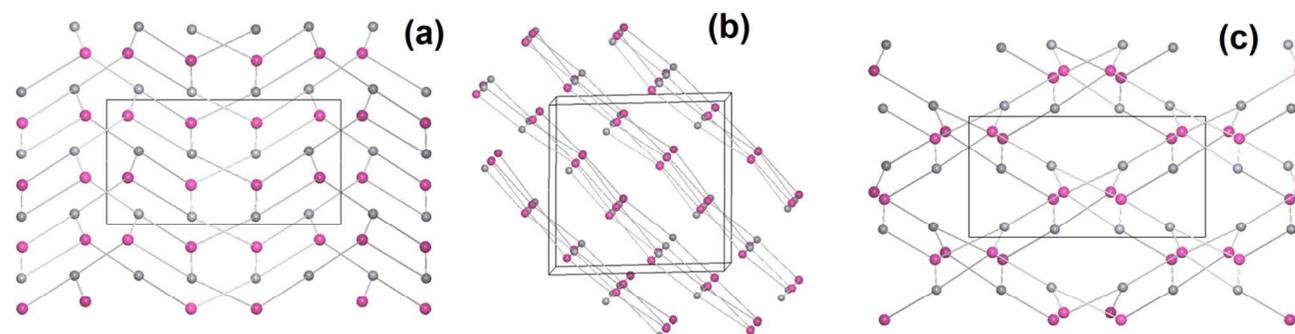

**Fig. 3** Simplified two-dimensional network of **1**, 3-c net, with Schläfli symbol  $\{4.8^2\}$ , with views along the (a) [100], (b) [010] and (c) [001] direction; red spheres: Cd, grey spheres and lines: ligand representations.

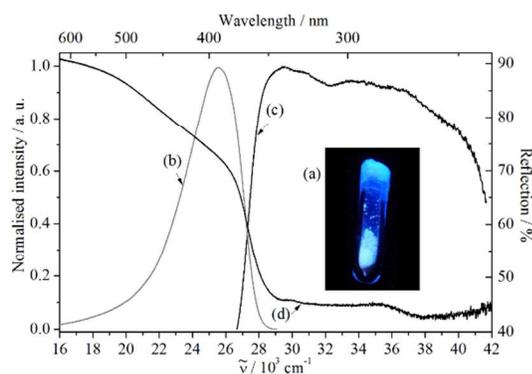


**Fig. 4** (a) Violet-blue luminescence of (*S*)-4,4'-bis(4-carboxyphenyl)-2,2'-bis(diphenylphosphinoyl)-1,1'-binaphthyl (**H<sub>2</sub>L**), when illuminated with UV light. (b) Emission ( $\tilde{\nu}_{ex} = 30864 \text{ cm}^{-1}$ ), (c) excitation ( $\tilde{\nu}_{em} = 25445 \text{ cm}^{-1}$ ), and (d) reflection spectra of **H<sub>2</sub>L**.

Similarly, in both cases, the excitation spectra consist of a broad band which extends over the UV range. The onsets of the excitation bands are at  $26625 \text{ cm}^{-1}$  (**H<sub>2</sub>L**) and  $25325 \text{ cm}^{-1}$  (**1**) and they show intensity maxima at  $29464 \text{ cm}^{-1}$  (**H<sub>2</sub>L**) and  $27475 \text{ cm}^{-1}$  (**1**), followed by an intensity decrease at higher excitation energies ( $> 36000 \text{ cm}^{-1}$ ). Therefore, the similarity in position and shape of the excitation and emission spectra of **H<sub>2</sub>L** and **1** provide reliable evidence for assigning the optical properties of **1** to ligand-based excitation and emission. A further indication for this assignment is the similarity between the excitation spectrum of **1** ( $\tilde{\nu}_{em} = 24752 \text{ cm}^{-1}$ , Fig. 5d) and the reflection spectrum of **H<sub>2</sub>L** (Fig. 4d). Thus, a decrease of the reflection intensity of **H<sub>2</sub>L** is observed for energies larger than  $20000 \text{ cm}^{-1}$ , more pronounced for energies higher than  $26000 \text{ cm}^{-1}$ . Moreover, there is a maximum in the absorption intensity at  $29000 \text{ cm}^{-1}$ , strongly overlapping in position and shape with the excitation spectrum of **1**. In this context, ligand-based luminescence is generally expected for coordination compounds in which the metal ion does not show d-d or f-f electronic transitions, e.g., metal ions with a  $d^{10}$  configuration, such as  $\text{Cd}^{2+}$ ,  $\text{Zn}^{2+}$  and  $\text{Ag}^+$ , and little or no electronic interaction between the metal ion and the organic ligand is observed.<sup>5</sup>

The strong excitation bands are therefore caused by  $S_0 \rightarrow S_1$  transition of the aromatic units in **L** or **H<sub>2</sub>L**. Also, the emission

bands can be assigned to  $S_1$  rather than  $T_1$  emission due to the relatively small differences between the emission and excitation maxima ( $3980 \text{ cm}^{-1}$  for **H<sub>2</sub>L** and  $2708 \text{ cm}^{-1}$  for **1**). If this assumption is true, the larger Stokes shift of **H<sub>2</sub>L** compared to **1** also indicates a larger increase in the interatomic distance of the excited state relative to the ground state in **H<sub>2</sub>L** and would agree with the observation of different widths of the emission bands.

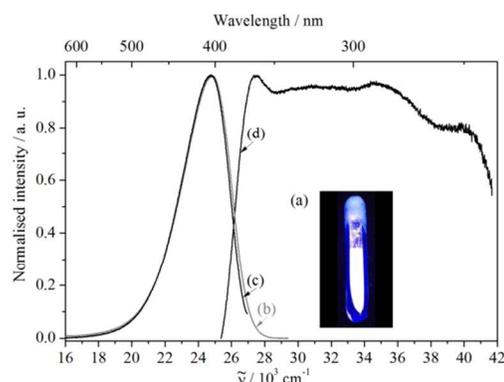

**Fig. 5** (a) Violet-blue luminescence of **1**, when illuminated with UV light. Emission (b)  $\tilde{\nu}_{ex} = 27397 \text{ cm}^{-1}$  and (c)  $\tilde{\nu}_{ex} = 30769 \text{ cm}^{-1}$  as well as (d) excitation ( $\tilde{\nu}_{em} = 24752 \text{ cm}^{-1}$ ) spectra of compound **1**.

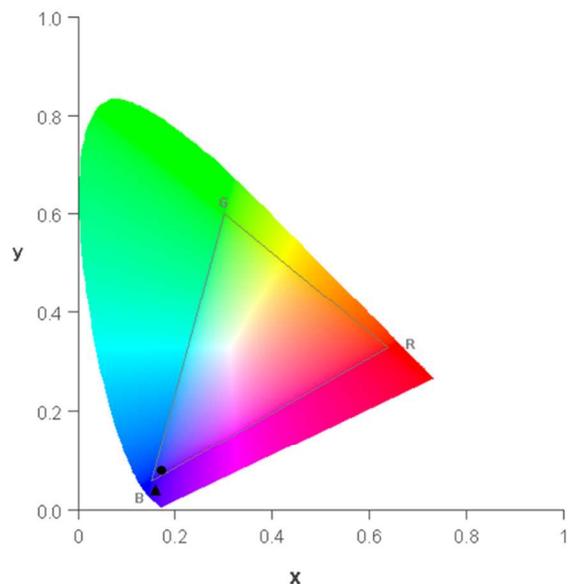


Fig. 6 Plot of colour coordinates in the CIE 1931 chromaticity diagram for  $\text{H}_2\text{L}$  (●) and **1** (▲).

The quantum yields (QY) of solid  $\text{H}_2\text{L}$  (33%) and **1** (42%) are considerably high, and indicate decreased loss of efficiency of the ligand-based luminescence in **1**. This enhancement is related to an increase in structural rigidity in the coordination polymer **1**. In general, there is relatively low vibrational quenching in the case of both compounds, which is quite uncommon for such kind of compounds with large vibrational energies.

Luminescence measurements at low temperatures, e.g., at 10 K, are important for studying possible additional electronic transitions, which may be quenched at room temperature. Furthermore, **1** was heated close to the decomposition temperature (650 K, see ESI) to investigate the effect of temperature on the emission intensity and the maximum shift. As shown in Figure 7, the emission spectrum of **1** is very similar in shape and position at temperatures between 10 and 650 K and no additional electronic transitions were detected. The maximum of the emission band located at  $25439\text{ cm}^{-1}$  at 10 K is red-shifted to  $25192\text{ cm}^{-1}$  at 650 K. Such red shifts are generally observed and can be explained by different effects: by occupation of higher vibronic levels and partly by distortion of the harmonic potentials of the excited electronic state at high temperatures.

Between 10 K and room temperature (300 K), the emission intensity of **1** shows an unusual behaviour. In order to roughly quantify the variation of the emission intensity, the curves of the emission spectra presented in Figure 7 were integrated and plotted against the temperature (Figure 8).

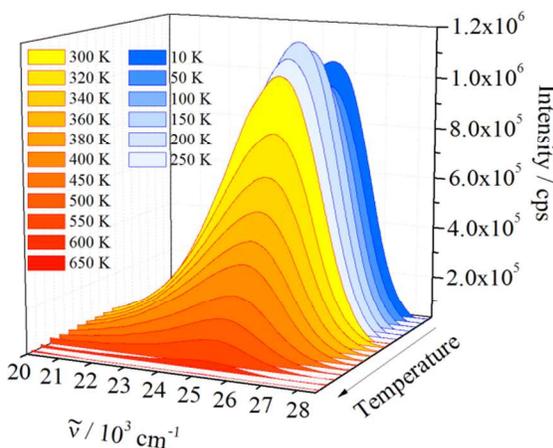


Fig. 7 Effect of temperature increase on the emission spectrum ( $\tilde{\nu}_{\text{ex}} = 30769\text{ cm}^{-1}$ ) of **1**.

Initially, the intensity decreases by ca. 10% from 10 to 50 K, gradually increases by about 20%, reaching the maximum value at 200 K, and is approximately constant up to 300 K. The initial decrease in emission intensity is expected due to the enhanced loss of excitation energy by non-radiative transitions. However, the increase in emission intensity between 50 and 200 K is rather unusual. Probably, the excited states of the ligands and the states of quenching moieties are arranged relative to each other in such a way that quenching is reduced in this temperature range

compared to low temperatures, while quenching processes become dominant at higher temperatures. However, further experiments are necessary to investigate and prove this assumption. Between 300 and 650 K an exponential decrease of the emission intensity is observed. Such a large energy loss caused by non-radiative transitions is commonly observed for luminescence materials at high temperatures.

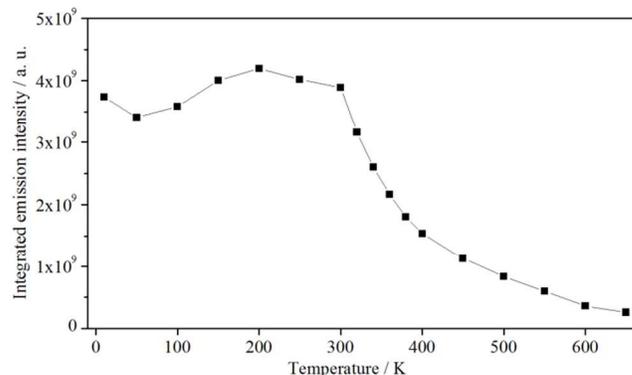


Fig. 8 Exponential decay of the integrated emission intensity ( $\tilde{\nu}_{\text{ex}} = 30303\text{ cm}^{-1}$ ) of **1** with increasing temperature.

## Experimental Section

### Materials and general methods

Commercial reagents were used as purchased without further purification. (*S*)-4,4'-bis(4-carboxyphenyl)-2,2'-bis(diphenylphosphinoyl)-1,1'-binaphthyl ( $\text{H}_2\text{L}$ ) was prepared according to the literature procedure.<sup>22</sup> The IR spectra were recorded on a Perkin-Elmer Spectrum 2000 FTIR spectrometer by using KBr pellets in the range of  $4000\text{--}500\text{ cm}^{-1}$ . Elemental analysis was performed with a Heraeus Vario EL CHN-O analyzer. Thermal analyses were carried out on a Netzsch STA/QMS system 409/429-403 thermal analyzer from room temperature to  $900\text{ }^\circ\text{C}$  with a heating rate of  $10\text{ }^\circ\text{C}/\text{min}$  under helium atmosphere.

### Synthesis of $[\{\text{Cd}_2(\text{L})_2(\text{H}_2\text{O})\}\cdot 18\text{ dmf}]_n$ (**1**)

Solvothermal synthesis of **1** was accomplished in a stainless steel autoclave under autogenic pressure with an appropriate Teflon vessel (Parr), 15 mL volume. The temperature program in a ULE400 oven (Mettler) was regulated by using the software Celsius 2005 (Version 6.1). A mixture of  $\text{Cd}(\text{NO}_3)_2\cdot 4\text{ H}_2\text{O}$  (0.024 g, 0.078 mmol), (*S*)- $\text{H}_2\text{L}$  (0.02 g, 0.022 mmol) and dmf (10 mL) was progressively heated to 65, 75 and 85  $^\circ\text{C}$  (each for 24 h), and cooled to room temperature over 3 d. Colourless crystals of **1** were obtained, collected by filtration, washed with dmf ( $3 \times 5\text{ mL}$ ) and dried at room temperature. Yield: 23 mg (62.5 % based on  $\text{H}_2\text{L}$ ). Anal. Calcd. for **1**-3 dmf (%): C, 61.88; H, 5.90; N, 6.72; Found: C, 60.00, H, 5.90, N, 6.50. IR (KBr pellet,  $\text{cm}^{-1}$ ): 3442 (br, OH), 3055 (w, C-H aryl), 2928 (w, C-H), 2342 (w), 1670 (s,  $\nu_{\text{as}}\text{COO}$ ), 1594 (m,  $\nu_{\text{s}}\text{COO}$ ), 1540 (m), 1498 (w), 1438 (m, P-C<sub>6</sub>H<sub>5</sub>), 1389 (s), 1256 (s), 1181 (s, P=O), 1098 (s), 1019 (m), 974 (w), 865 (s), 792 (s), 756 (w, C-H), 722 (s), 698 (s, P-C), 663 (s), 594 (s), 545 (s, C-H), 471 (w).

### Crystal structure determination

Data collection for colourless crystals of **1** was performed on a Gemini-S CCD diffractometer (Agilent Technologies) with Cu- $K_{\alpha}$ -radiation ( $\lambda = 1.54184 \text{ \AA}$ ) at 130(2) K and omega scan rotation. Data collection and data reduction were done with CrysAlisPro including the program SCALE3 ABSPACK for empirical absorption correction.<sup>26</sup> Anisotropic refinement of all non-hydrogen atoms, except dmf molecules, with SHELXL-97.<sup>27</sup> All hydrogen atoms were calculated on idealised positions by using the riding model. It was possible to locate the water and eight non-disordered of the 18 dmf molecules of the asymmetric unit. With the exception of water, these eight solvent molecules were refined isotropically. 181 restraints were used to model the highly disordered dmf molecules. All other solvent molecules were found to be extremely disordered and poorly defined. The *hkl* file was corrected for these disordered solvent molecules by using the program SQUEEZE.<sup>28</sup> The total SQUEEZE electron count revealed 1586 electrons for a volume of  $5924 \text{ \AA}^3$  (voids smaller than  $50 \text{ \AA}^3$  were not taken into account). Due to this electron count, 40 dmf molecules of the unit cell, i.e. 10 dmf molecules of the asymmetric unit were removed. The resulting volume of approximately  $148 \text{ \AA}^3$  for one of these disordered dmf molecules correlates well with the reported volume for non-disordered dmf molecules ( $102 \text{ \AA}^3$ ).<sup>29</sup> Structure figures were generated with Diamond-3.<sup>25</sup> Crystallographic data for  $[\{\text{Cd}_2(\text{L})_2(\text{H}_2\text{O})\} \cdot 18\text{dmf}]_n$  (**1**):  $\text{C}_{170}\text{H}_{204}\text{Cd}_2\text{N}_{18}\text{O}_{31}\text{P}_4$ ,  $M = 3344.19 \text{ g/mol}$ , space group  $C2$ ,  $a = 32.8047(8)$ ,  $b = 16.8286(5)$ ,  $c = 31.6834(8) \text{ \AA}$ ,  $\alpha = 90$ ,  $\beta = 91.867(2)$ ,  $\gamma = 90^\circ$ ,  $V = 17481.8(8) \text{ \AA}^3$ ,  $Z = 4$ ,  $\rho_{\text{calcd}} = 1.271 \text{ Mg/m}^3$ ,  $\mu(\text{Cu}_{K\alpha}) = 2.894 \text{ mm}^{-1}$ . Least-squares refinements based on 48559 reflections (18286 independent reflections and 1360 parameters) led to convergence. For  $I > 2\sigma(I)$  the final  $R1 = 0.0604$ ,  $wR2 = 0.1578$ , Flack parameter = 0.009(6) and GOF = 1.000. The crystal data can be obtained free of charge (CCDC 958436) from The Cambridge Crystallographic Data Centre via [www.ccdc.cam.ac.uk/data\\_request/cif](http://www.ccdc.cam.ac.uk/data_request/cif).

### Luminescence measurements

Photoluminescence investigations at room and low temperature (ca. 10 K) on solid samples sealed in silica ampoules were carried out with a Jobin Yvon fluorescence spectrometer (Fluorolog 3) equipped with two 0.22 m double monochromators (SPEX, 1680) and a 450 W xenon lamp. Cooling to 10 K was achieved by a closed-cycle He cryostat (Janis Research). Measurements at high temperature (up to 650 K) were carried out with a Jobin Yvon fluorescence spectrometer (FluoroMax), equipped with two monochromators and a 150 W xenon lamp, combined with an attached oven. The emission spectra were corrected for photomultiplier sensitivity, the excitation spectra for lamp intensity and both for the transmission of the monochromators. Quantum yields of solid samples were measured with a Fluorolog 3 fluorescence spectrometer having an additional Ulbricht sphere. For reflection measurements in the UV/Vis range, a Cary 5000 instrument (Varian) was used.

### Conclusions

Chiral coordination polymer **1** based on cadmium(II) and (*S*)-4,4'-bis(4-carboxyphenyl)-2,2'-bis(diphenylphosphinoyl)-1,1'-

binaphthyl (**H<sub>2</sub>L**) as linker was synthesised solvothermally and fully characterised. The **H<sub>2</sub>L** ligand and compound **1** show intense blue emission when excited with UV light. Emission spectra consist of nearly Gaussian shaped bands at  $25574 \text{ cm}^{-1}$  for **H<sub>2</sub>L** and  $24767 \text{ cm}^{-1}$  for **1**. Similarities between the excitation and emission spectra of **1** and **H<sub>2</sub>L** are indicative of  $S_1 \leftrightarrow S_0$  transitions of **L**. Moreover, the quantum efficiency increases from 33% in **H<sub>2</sub>L** to the remarkably high value of 42% in **1**, which indicates that incorporation of **L** into the rigid framework prevents the loss of excitation energy by non-radiative transitions. The emission intensity of **1** increases between 10 K and room temperature, and decreases exponentially up to 650 K.

### Acknowledgements

This work was supported by the Faculty for The Future (FFTF-Schlumberger Foundation for Women in Science and Engineering, doctoral fellowship for W.W.L). Support from the EU COST Action CM0802 PhoSciNet is gratefully acknowledged. We thank Chemetall GmbH and BASF SE for generous donations of chemicals. We thank MSc Marcel Handke and MSc Carola Stenz for PXRD measurement and TOPOS analysis.

### Notes and references


<sup>a</sup> Institut für Anorganische Chemie, Fakultät für Chemie und Mineralogie, Universität Leipzig, Johannisallee 29, D-04103 Leipzig, Germany. Fax: +49 341 9739319; E-mail: [hey@rz.uni-leipzig.de](mailto:hey@rz.uni-leipzig.de)  
<sup>b</sup> Anorganische Chemie II, Naturwissenschaftlich-Technische Fakultät, Department Chemie-Biologie, Universität Siegen, Adolf-Reichwein-Straße, D-57068 Siegen, Germany. Fax: +49 271 4702555; E-mail: [wickleder@chemie.uni-siegen.de](mailto:wickleder@chemie.uni-siegen.de)

<sup>†</sup> Electronic Supplementary Information (ESI) available: [powder X-ray diffraction and thermal analysis of **1**]. See DOI: 10.1039/b000000x/

### References

- (a) O. M. Yaghi, H. Li, *J. Am. Chem. Soc.*, 1995, **117**, 10401–10402; (b) O. M. Yaghi, D. A. Richardso, G. Li, E. Davis, T. L. Groy, *Mater. Res. Soc. Symp. Proc.*, 1995, **371**, 15–19; (c) H. Li, M. Eddaoudi, M. O'Keeffe, O. M. Yaghi, *Nature*, 1999, **402**, 276–279.
- (a) M. J. Zaworotko, *Nat. Chem.*, 2009, **1**, 267–268; (b) J. J. Perry IV, J. A. Perman, M. J. Zaworotko, *Chem. Soc. Rev.*, 2009, **38**, 1400–1417 and references therein.
- S. R. Batten, D. R. Turner, M. S. Neville, in *Coordination Polymers: Design, Analysis and Application*, RSC, Cambridge, 2009
- (a) S.-i. Noro, S. Kitagawa, M. Kondo, K. Seki, *Angew. Chem.*, 2000, **112**, 2161–2164; *Angew. Chem., Int. Ed.*, 2000, **39**, 2082–2084; (b) S. Shimomura, S. Horike, S. Kitagawa, *Stud. Surf. Sci. Catal.*, 2007, **170B**, 1983–1990.
- D. Farrusseng, in *Metal-Organic Frameworks – Applications from Catalysis to Gas Storage*, Wiley-VCH, Weinheim, 1<sup>st</sup> edn, 2011.
- (a) M. D. Allendorf, C. A. Bauer, R. K. Bhakta, R. J. T. Houk, *Chem. Soc. Rev.*, 2009, **38**, 1330–1352; (b) Y. Cui, Y. Yue, G. Qian, B. Chen, *Chem. Rev.*, 2012, **112**, 1126–1162.
- (a) C. A. Bauer, T. V. Timofeeva, T. B. Settersten, B. D. Patterson, V. H. Liu, B. A. Simmons, M. D. Allendorf, *J. Am. Chem. Soc.* 2007,

- 129, 7136–7144; (b) X.-L. Wang, Y.-F. Bi, H.-Y. Lin, G.-C. Liu, *Cryst. Growth Des.* 2007, **7**, 1086–1091; (c) Y.-Q. Huang, B. Ding, H.-B. Song, B. Zhao, P. Ren, P. Cheng, H.-G. Wang, D.-Z. Liao, S.-P. Yan, *Chem. Commun.*, 2006, 4906–4908; (d) X. Li, X.-W. Wang, Y.-H. Zhang, *Inorg. Chem. Commun.*, 2008, **11**, 832–834.
- 8 (a) C. J. Holler, P. R. Matthes, M. Adlung, C. Wickleder, K. Müller-Buschbaum., *Eur. J. Inorg. Chem.* 2012, **33**, 5479–5484; (b) P. J. Calderonea, A. M. Plonka, D. Banerjee, Q. A. Nizami, J. B. Parise, *Solid State Sci.*, 2013, **15**, 36–41; (c) X.-H. Zhou, L. Li, H.-H. Li, A. Li, T. Yanga, W. Huang, *Dalton Trans.*, 2013, **42**, 12403–12409; (d) J. Rocha, L. D. Carlos, F. A. A. Paz, D. Ananias, *Chem. Soc. Rev.*, 2011, **40**, 926–940; (e) H.-M. Wang, Y.-Y. Yang, C.-H. Zeng, T.-S. Chu, Y.-M. Zhu, S. W. Ng, *Photochem. Photobiol. Sci.*, 2013, **12**, 1700–1706.
- 9 (a) H. C. Streit, M. Adlung, O. Shekhah, X. Stammer, H. K. Arslan, O. Zybalyo, T. Ladnorg, H. Gliemann, M. Franzreb, C. Woell, C. Wickleder. *Chem. Phys. Chem.*, 2012, **13**, 2699–2702; (b) W.-G. Lu, L. Jiang, X.-L. Feng, T.-B. Lu, *Inorg. Chem.* 2009, **48**, 6997–6999.
- 10 (a) C.-J. Chen, X.-P. Ye, J.-Y. Gao, W.-P. Xie, X.-R. Ran, S.-T. Yue, Y.-P. Cai, *Inorg. Chem. Commun.*, 2013, **29**, 4–10; (b) H. Wang, W. Shi, B. Zhai, J. Ma, J. Xia, P. Cheng, *J. Mol. Struct.* 2007, **833**, 102–107; (c) Q.-R. Fang, G.-S. Zhu, Z. Jin, Y.-Y. Ji, J.-W. Ye, M. Xue, H. Yang, Y. Wang, S.-L. Qiu, *Angew. Chem.*, 2007, **119**, 6758–6762; *Angew. Chem. Int. Ed.*, 2007, **46**, 6638–6642; (d) L. Wen, Z. Lu, J. Lin, Z. Tian, H. Zhu, Q. Meng, *Cryst. Growth Des.* 2007, **7**, 93–99.
- 11 W.-Y. Huang, Z.-L. Chen, H.-H. Zou, D.-C. Liu, F.-P. Liang, *Polyhedron*, 2013, **50**, 1–9.
- 12 (a) Y. Cui, H. L. Ngo, W. Lin, *Chem. Commun.*, 2003, 1388–1389; (b) Y. Cui, S. J. Lee, W. Lin, *J. Am. Chem. Soc.*, 2003, **125**, 6014–6015; (c) C.-D. Wu, W. Lin, *Chem. Commun.*, 2005, 3673–3675; (d) C.-D. Wu, L. Ma, W. Lin, *Inorg. Chem.* 2008, **47**, 11446–11448; (e) C.-D. Wu, L. Zhang, W. Lin, *Inorg. Chem.* 2006, **45**, 7278–7285; (f) O. R. Evans, H. L. Ngo, W. Lin, *J. Am. Chem. Soc.* 2001, **123**, 10395–10396.
- 13 (a) B. Kesanli, W. Lin, *Coord. Chem. Rev.*, 2003, **246**, 305–326; (b) Q. Gao, F.-L. Jianga, M.-Y. Wua, Y.-G. Huang, L. Chena, W. Wie, M.-C. Hong, *J. Solid State Chem.* 2009, **182**, 1499–1505; (c) C.-D. Wu, H. L. Ngo, W. Lin, *Chem. Commun.*, 2004, 1588–1589; (d) S. J. Lee, W. Lin, *J. Am. Chem. Soc.*, 2002, **124**, 4554–4555.
- 14 (a) A. Hu, H. L. Ngo, W. Lin, *J. Am. Chem. Soc.* 2003, **125**, 11490–11491; (b) C.-D. Wu, A. Hu, L. Zhang, W. Lin, *J. Am. Chem. Soc.* 2005, **127**, 8940–8941; (c) L. Ma, C.-D. Wu, M. M. Wanderley, W. Lin, *Angew. Chem.*, 2010, **122**, 8420–8424; *Angew. Chem. Int. Ed.*, 2010, **49**, 8244–8248; (d) L. Ma, J. M. Falkowski, C. Abney, W. Lin, *Nat. Chem.* 2010, **20**, 838–846; (e) Y. Cui, O. R. Evans, H. L. Ngo, P. S. White, W. Lin, *Angew. Chem.*, 2002, **114**, 1207–1210; *Angew. Chem. Int. Ed.* 2002, **41**, 1159–1162; (f) L. Ma, D. J. Mihalcik, W. Lin, *J. Am. Chem. Soc.* 2009, **131**, 4610–4612.
- 15 (a) M. M. Wanderley, C. Wang, C.-D. Wu, W. Lin, *J. Am. Chem. Soc.* 2012, **134**, 9050–9053; (b) X. Ouyang, Z. Chen, X. Liu, Y. Yang, M. Deng, L. Weng, Y. Zhou, Y. Jia, *Inorg. Chem. Commun.*, 2008, **11**, 948–950.
- 16 (a) L. Li, Z.-G. Ren, N.-Y. Li, Y. Zhang, J.-P. Lang, *Inorg. Chim. Acta*, 2009, **362**, 3910–3914; (b) N.-Y. Li, Z.-G. Ren, D. Liu, R.-X. Yuan, L.-P. Wei, L. Zhang, H.-X. Lia, J.-P. Lang, *Dalton Trans.*, 2010, **39**, 4213–4222.
- 17 (a) M.-C. Brandys, R. J. Puddephatt, *J. Am. Chem. Soc.* 2001, **123**, 4839–4840; (b) M. Frik, J. Jiménez, I. Gracia, L. R. Falvello, S. Abi-Habib, K. Suriel, T. R. Muth, M. Contel, *Chem. Eur. J.* 2012, **18**, 3659–3674.
- 18 Q. Gao, M.-Y. Wu, L. Chen, F.-L. Jiang, M.-C. Hong, *Inorg. Chem. Commun.*, 2009, **12**, 1238–1241.
- 19 (a) J. J. Zhang, L. Wojtas, R. W. Larsen, M. Eddaoudi, M. J. Zaworotko, *J. Am. Chem. Soc.* 2009, **131**, 17040–17041; (b) J.-D. Lin, X.-F. Long, P. Lin, S.-W. Du, *Cryst. Growth Des.* 2010, **10**, 146–157; (c) A. D. Burrows, K. Cassar, T. Düren, R. M. W. Friend, M. F. Mahon, S. P. Rigby, T. L. Savarese, *Dalton Trans.*, 2008, 2465–2474; (d) X. Shi, G. Zhu, X. Wang, G. Li, Q. Fang, G. Wu, G. Tian, M. Xue, X. Zhao, R. Wang, S. Qiu, *Cryst. Growth Des.*, 2005, **5**, 207–213; (e) R.-Q. Zou, X.-H. Bu, R.-H. Zhang, *Inorg. Chem.* 2004, **43**, 5382–5386; (f) O. A. Michaelides, D. Tsaousis, S. Skoulika, C. P. Raptopoulou, A. Terzis, *Acta Cryst.* 1998, **B54**, 657–662; (g) I. Grosu, P. Lönnecke, L. Silaghi-Dumitrescu, E. Hey–Hawkins, *Z. Anorg. Allg. Chem.* 2011, **637**, 1722–1727.
- 20 (a) F. Guo, F. Wang, H. Yang, X. Zhang, J. Zhang, *Inorg. Chem.* 2012, **51**, 9677–9682; (b) H. Xu, W. Bao, Y. Xu, X. Liu, X. Shen, D. Zhu, *CrystEngComm*, 2012, **14**, 5720–5722; (c) F. A. A. Paz, Y. Z. Khimyak, A. D. Bond, J. Rocha, J. Klinowski, *Eur. J. Inorg. Chem.* 2002, 2823–2828; (d) Q.-R. Fang, G.-S. Zhu, Z. Jin, Y.-Y. Ji, J.-W. Ye, M. Xue, H. Yang, Y. Wang, S.-L. Qiu, *Angew. Chem.*, 2007, **119**, 6758–6762; *Angew. Chem. Int. Ed.* 2007, **46**, 6638–6642; (e) R. Wang, M. Hong, J. Luo, R. Cao, J. Weng, *Chem. Commun.*, 2003, 1018–1019; (f) W. W. Lestari, P. Lönnecke, M. B. Sárosi, H. C. Streit, M. Adlung, C. Wickleder, M. Handke, W. D. Einicke, R. Gläser, E. Hey-Hawkins. *CrystEngComm*, 2013, **15**, 3874–3884.
- 21 R.-Q. Zhonga, R.-Q. Zoua, D. S. Pandey, T. Kiyobayashi, Q. Xua, *Inorg. Chem. Commun.*, 2008, **11**, 951–953.
- 22 W. W. Lestari, H. Zaake–Hertling, P. Lönnecke, E. Hey–Hawkins. *Z. Anorg. Allg. Chem.*, 2013, **639**, 2589–2596.
- 23 TOPOS 4.0; V.A. Blatov, *IUCr CompComm Newsletter* 2006, **7**, 4–38.
- 24 M. O’Keeffe, M. A. Peskov, S. J. Ramsden, O. M. Yaghi, *Acc. Chem. Res.* 2008, **41**, 1782–1789.
- 25 Diamond, Version 3.2i, Klaus Brandenburg, Crystal Impact GbR, Bonn, Germany.
- 26 CrysAlisPro, Data Collection and Data Reduction Software Package Including SCALE3 ABSPACK for Empirical Absorption Correction using Spherical Harmonics, version 1.171.35.21, release 20-01-2012 CrysAlis171.NET, Agilent Technologies.
- 27 G. M. Sheldrick, *SHELXTL-97 Program for Structure Refinement*, University of Göttingen, Germany, 1997.
- 28 SQUEEZE, P. van der Sluis, A. L. Spek, *Acta Cryst.*, 1990, **A46**, 194–201.
- 29 H. Borrmann, I. Persson, M. Sandström, C. M. V. Stålhandske, *J. Chem. Soc., Perkin Trans.*, 2000, **2**, 393–402.

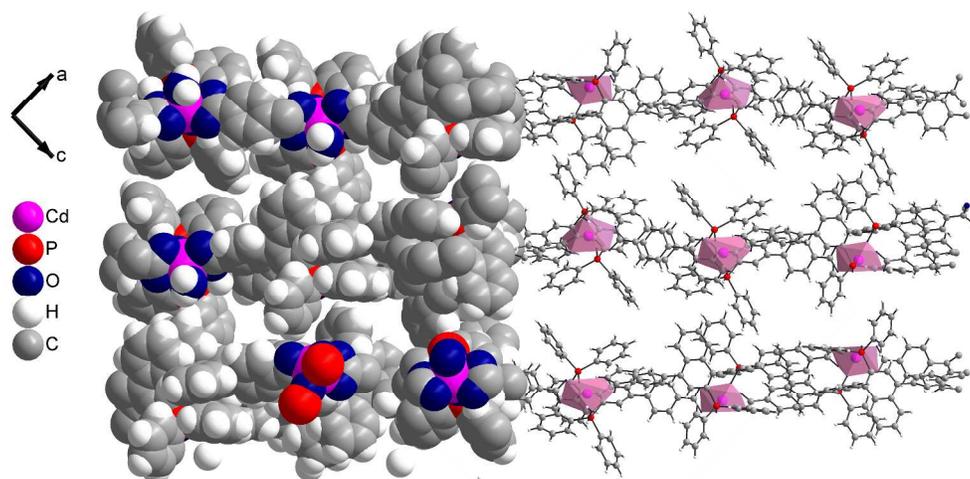

1420x698mm (96 x 96 DPI)

Sentence for graphical abstract:

Solvothermal reaction of  $\text{Cd}(\text{NO}_3)_2$  with (*S*)-4,4'-bis(4-carboxyphenyl)-2,2'-bis(diphenylphosphinoyl)-1,1'-binaphthyl (**H<sub>2</sub>L**) gave the two-dimensional chiral coordination polymer  $[\{\text{Cd}_2(\text{L})_2(\text{H}_2\text{O})\} \cdot 18 \text{ dmf}]_n$ .