

# Energy & Environmental Science

Accepted Manuscript



This is an *Accepted Manuscript*, which has been through the Royal Society of Chemistry peer review process and has been accepted for publication.


*Accepted Manuscripts* are published online shortly after acceptance, before technical editing, formatting and proof reading. Using this free service, authors can make their results available to the community, in citable form, before we publish the edited article. We will replace this *Accepted Manuscript* with the edited and formatted *Advance Article* as soon as it is available.

You can find more information about *Accepted Manuscripts* in the [Information for Authors](#).

Please note that technical editing may introduce minor changes to the text and/or graphics, which may alter content. The journal's standard [Terms & Conditions](#) and the [Ethical guidelines](#) still apply. In no event shall the Royal Society of Chemistry be held responsible for any errors or omissions in this *Accepted Manuscript* or any consequences arising from the use of any information it contains.

**The table of contents entry**

A **conductive Al-doped ZnO inverse opal network** has been introduced into  $\text{BiVO}_4$  photoanode to improve photogenerated electron transport and collection.

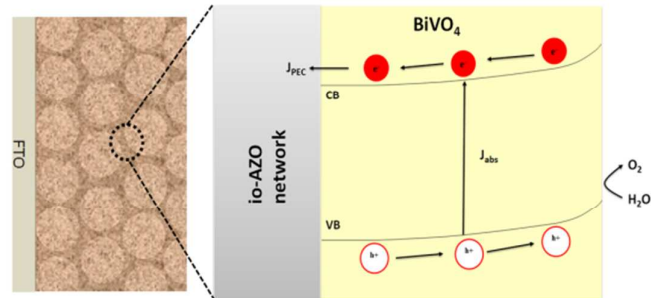**ToC figure**

## Al-doped ZnO Inverse Opal Networks as Efficient Electron Collectors in BiVO<sub>4</sub> Photoanodes for Solar Water Oxidation

Liwu Zhang, Erwin Reisner, Jeremy J. Baumberg

Dr. L.-W. Zhang, Prof. J. J. Baumberg  
Cavendish Laboratory, Department of Physics, University of Cambridge  
Cambridge, CB3 0HE (UK)  
E-mail: jjb12@cam.ac.uk

Dr. E. Reisner  
Department of Chemistry, University of Cambridge  
Cambridge, CB2 1EW (UK)  
E-mail: reisner@ch.cam.ac.uk

Keywords: Water splitting; BiVO<sub>4</sub>; Al-doped ZnO; Inverse opal


**The short diffusion length of photogenerated charge carriers limits the performance of photoelectrodes for solar water splitting. To reduce the distance between where the charges are generated and the location they are scavenged, a conductive Al-doped ZnO inverse opal network is introduced into a BiVO<sub>4</sub> photoanode. The conductive inverse opal network serves as an electron collector for the BiVO<sub>4</sub> film, which suffers from poor electron transport. The combined heterostructure provides a photocurrent of 1.5 mA/cm<sup>2</sup> at 1.23 V vs RHE, which is threefold higher than a BiVO<sub>4</sub> photoanode without any conducting inverse opal network. The significantly enhanced photocurrent produced without intentional doping or oxygen-evolving catalysts, indicates the importance of charge transport and collection in photoelectrodes. Our design has the potential to be applied to other photoelectrochemical systems to improve charge collection and solar energy conversion efficiency.**

Artificial photosynthesis is an attractive approach to meet the urgent goal of efficiently and inexpensively converting solar energy into a storable and transportable form<sup>1,2</sup>. Photoelectrochemical water splitting is a promising and environmentally friendly route for the conversion of solar energy into hydrogen. The development of solar water splitting devices provides also an important first step towards the goal of developing artificial leaves capable of converting CO<sub>2</sub> directly into liquid fuels<sup>3</sup>. Currently, a lack of efficient, inexpensive and scalable photoelectrodes limits the practical application and development of this technology.


Metal oxides are inexpensive, robust and easily fabricated and they are therefore frequently studied photoelectrode materials<sup>4-9</sup>. Post-transition metal cations having electronic configurations with  $ns^2$  [e.g., PbO (2.1 eV) and Bi<sub>2</sub>O<sub>3</sub> (2.5 eV)] or transition metal cations with  $d^n$  [e.g., Fe<sub>2</sub>O<sub>3</sub> ( $E_g = 2.0$

eV) and  $\text{Cu}_2\text{O}$  (2.0 eV)] can produce binary metal oxides with narrow band gap energies. However, the former metal oxides show unfavourable indirect band gap transitions resulting from the coupling between the filled cation  $s$  and anion  $p$  states, whereas the latter oxides suffer from high resistivities due to the small polaron-dominated conductivity. To overcome the intrinsic limitations of binary metal oxides, multiple cations can be combined to form multinary oxides<sup>10, 11</sup>. Among these multinary metal oxides, bismuth vanadate ( $\text{BiVO}_4$ ) has been identified as one of the most promising n-type semiconductors as photoanodes for water splitting.  $\text{BiVO}_4$ , with a band gap of 2.4 eV, was first reported by Kudo and coworkers as a photocatalyst for water oxidation<sup>12</sup>. Since then  $\text{BiVO}_4$  has been studied as a visible-light-driven photocatalyst for the degradation of organic compounds and water oxidation<sup>13-16</sup>. Recently, extensive attention has focused on  $\text{BiVO}_4$  as a photoanode for photoelectrochemical water splitting<sup>17-21</sup>. To improve the charge transport properties and reduce the surface recombination of the photogenerated carriers in  $\text{BiVO}_4$ , great efforts have been made by doping, introducing water oxidation cocatalysts, constructing nanostructures, etc<sup>18, 20, 22-26</sup>. It has been demonstrated by van de Krol and coworkers that, contrary to  $\alpha\text{-Fe}_2\text{O}_3$  which has a short hole diffusion length,  $\text{BiVO}_4$  suffers from poor electron transfer and collection in the photoelectrode<sup>27</sup>. Poor electron transport results in high bulk recombination of photogenerated charge carriers and thus a low solar-to- $\text{H}_2$  conversion efficiency.

To address this issue, we introduce here a conductive network into the  $\text{BiVO}_4$  film to improve the photogenerated electron collection. An Al-doped ZnO inverse opal (io-AZO) structure is for the first time employed to serve as a charge-transport pathway in the photoelectrode. The inverse opal conductive network is prepared by an opal template by evaporation-induced self-assembly of polystyrene spheres (PS). The crystallized io-AZO structure is obtained after removing the PS opal template by annealing. The pores in the AZO inverse opal structure are then filled with  $\text{BiVO}_4$  to achieve a  $\text{BiVO}_4/\text{io-AZO}$  heterostructured photoanode. The procedure for this heterostructure fabrication is illustrated in Scheme 1.

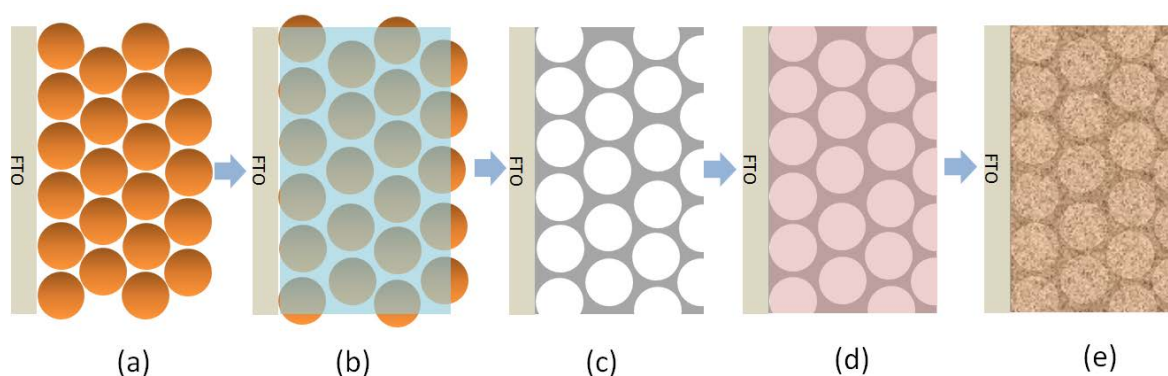


**Scheme 1.** Synthesis of the  $\text{BiVO}_4/\text{io-AZO}$  heterostructure photoanode. a) Opal template formed on FTO by evaporation-induced self-assembly of PS. b) Infiltration of AZO precursor into the void of the opal template. c) Removal of template and crystallizing AZO network by annealing. d) Filling pores of io-AZO with  $\text{BiVO}_4$  precursor. e) Formation of  $\text{BiVO}_4/\text{io-AZO}$  heterostructure by annealing.

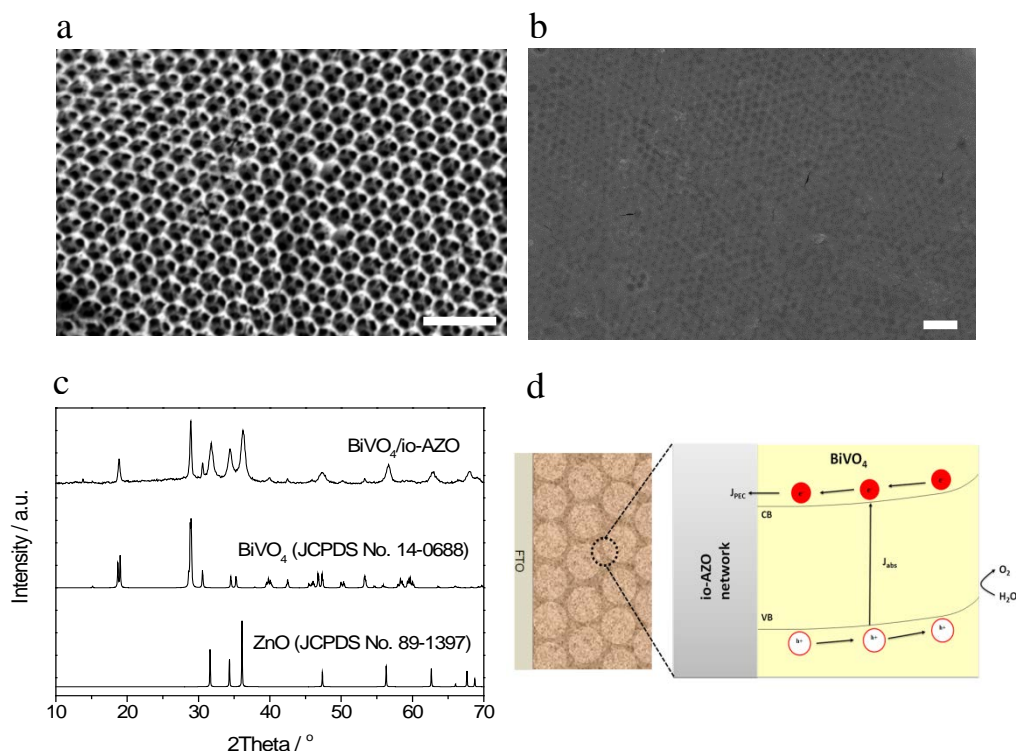

**Figure 1.** a) SEM image of the io-AZO electrode. b) SEM image of the BiVO<sub>4</sub>/io-AZO heterostructure. c) XRD pattern of the BiVO<sub>4</sub>/io-AZO heterostructure. d) Schematic illustration of the BiVO<sub>4</sub>/io-AZO heterostructure, where the conductive io-AZO network can readily collect the photogenerated electrons. The scale bars in 1a and 1b are 1  $\mu$ m.

The morphology and crystal structure of the io-AZO charge-collecting support structure and BiVO<sub>4</sub>/io-AZO heterostructures are investigated by scanning electron microscope (SEM) and X-ray diffraction (XRD). Figure 1a displays the three-dimensionally-ordered macroporous structure of the io-AZO film. The hexagonal close-packed structure shows a pore size of approximately 300 nm with each pore connected to an adjacent pore by a small hole of about 80 nm in diameter. This continuous structure allows infiltration of the BiVO<sub>4</sub> precursor solution into the entire film and formation of a uniform heterostructure. In this hybrid architecture, the inverse opal structure serves as a charge-collecting support structure. The SEM image of the assembled BiVO<sub>4</sub>/io-AZO heterostructure is shown in Figure 1b. BiVO<sub>4</sub> is found both inside and on the surface of the io-AZO film. The framework of the io-AZO can still be clearly observed underneath the layer of BiVO<sub>4</sub> on the top surface. Compared with the io-AZO without BiVO<sub>4</sub> (Figure 1a), it is found that upon deposition of BiVO<sub>4</sub> onto the walls of io-AZO, the structure of io-AZO is well maintained. Figure 1c shows the X-ray diffraction (XRD) patterns of a BiVO<sub>4</sub>/io-AZO electrode. The peaks are assigned to the scheelite-monoclinic phase of BiVO<sub>4</sub> (JCPDS No. 14-0688) and the zincite structure of ZnO (JCPDS No. 89-1397), indicating the formation of the desired BiVO<sub>4</sub>/io-AZO heterostructure in the photoelectrode. Zn-doping of BiVO<sub>4</sub> could have occurred during the annealing process and Zn-doping was previously

shown to give a negative effect on the photocatalytic performance of  $\text{BiVO}_4$ .<sup>24</sup> However, significant Zn-doping of  $\text{BiVO}_4$  is not observed in the  $\text{BiVO}_4/\text{io-AZO}$  heterostructure with no significant peak shifts in the XRD spectra in  $\text{BiVO}_4/\text{io-AZO}$ . Figure 1d illustrates the advantage of this design of solar water oxidation. In a planar  $\text{BiVO}_4$  film, the electrons excited in the bulk film (where the thickness is longer than the electron diffusion length) cannot be collected by FTO due to the poor electron transport in  $\text{BiVO}_4$ . However, in the  $\text{BiVO}_4/\text{io-AZO}$  heterostructure design, the distance needed for the electron transport is much shorter. The conductive io-AZO network can thus effectively collect the photogenerated electrons.

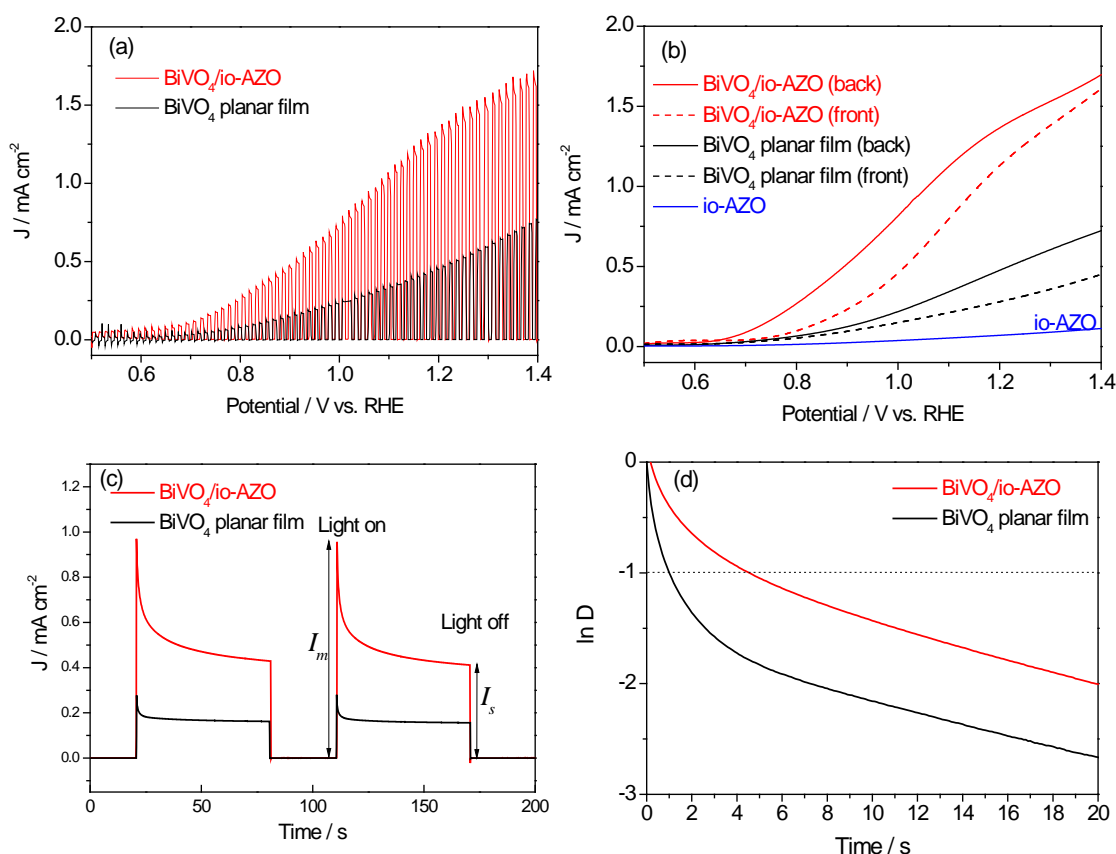

**Figure 2.** (a) Linear voltammetry sweeps under chopped illumination for planar  $\text{BiVO}_4$  and  $\text{BiVO}_4/\text{io-AZO}$  photoelectrodes. (b) Linear voltammetry sweeps under back-side or front-side illuminations of the electrode. (c) Transient photocurrent decay that occurs immediately upon illumination. (d) Transient decay times of planar  $\text{BiVO}_4$  film and  $\text{BiVO}_4/\text{io-AZO}$  heterostructure electrodes (see text for definition of parameter D).

The photoelectrochemical response of the planar  $\text{BiVO}_4$  and  $\text{BiVO}_4/\text{io-AZO}$  heterostructure electrodes were studied both in the dark and under AM 1.5G illumination ( $100 \text{ mW/cm}^2$ ). A conventional three electrode configuration was used with  $\text{BiVO}_4$  on FTO as working electrode, a Pt wire as the counter electrode, and a Ag/AgCl reference electrode. All the potentials are reported against the reversible hydrogen electrode (RHE). The electrolyte was aqueous phosphate buffer at pH 7 without any additive. Figure 2a shows the linear voltammetry sweeps (scan rate:  $10 \text{ mV/s}$ ) on the

planar  $\text{BiVO}_4$  and  $\text{BiVO}_4/\text{io-AZO}$  anodes under chopped illumination from the backside of the electrodes. The anodic photocurrent was observed once the open-circuit potential of 0.5 V was exceeded and the photocurrent increased steadily with the applied positive potential, whereas the currents are negligible in the dark. It is evident that an enhanced photocurrent is obtained essentially over the entire potential range for the  $\text{BiVO}_4/\text{io-AZO}$  heterostructure. In particular, for both electrodes, the photocurrent increased more or less linearly as the potential rises from 0.8 to 1.2 V. It is notable that there is a threefold difference in the slope (photocurrent vs. potential) between the two films. The slope corresponds to the inverse resistance of contact between the working electrode material and the electrolyte<sup>28</sup>, implying the  $\text{BiVO}_4/\text{io-AZO}$  heterostructure has lower resistance, and as a consequence, the photocurrent increased rapidly with applied potential.


Figure 2b shows the photocurrents of  $\text{BiVO}_4$  electrodes under front-side illumination or back-side illumination. A dependence of the photocurrent on the illumination direction can indicate either electron or hole transport limitations in the photoelectrode<sup>27</sup>. As shown in Figure 2b, for the planar  $\text{BiVO}_4$  film, the front-side illumination generates a photocurrent density of  $0.28 \text{ mA cm}^{-2}$  at 1.23 V, whereas the back-side illumination shows an almost 100% higher photocurrent density ( $0.53 \text{ mA cm}^{-2}$ ) at the same applied potential. Under front-side illumination, most charge carriers are generated near the semiconductor/electrolyte interface where most of the light is absorbed, and, consequently, the photogenerated electrons have to travel a longer distance before being collected by the FTO back contact. Based on the absorption coefficient of  $\text{BiVO}_4$ <sup>29</sup> we can estimate that the light penetration depth of  $\text{BiVO}_4$  is in the range of 100 to 500 nm in the visible range (420 to 530 nm) and even shorter in the UV region. The short penetration length of light in  $\text{BiVO}_4$  therefore results in a different response between front and back illumination (Figure 2b). This observation suggests that the overall photoresponse in the planar  $\text{BiVO}_4$  photoelectrode is limited by electron transport, which is consistent with previous reports<sup>27, 30, 31</sup>. By comparison, the electron transport problem seems to be significantly improved when the io-AZO conducting network is combined with the  $\text{BiVO}_4$  bulk film. In the case of the  $\text{BiVO}_4/\text{io-AZO}$  electrode, the photocurrent density under front-side illumination at 1.23 V is only 13% lower than back-side illumination. Compared with planar  $\text{BiVO}_4$  films, the photogenerated electrons can be readily collected by the conducting AZO inverse opal network, which provides a channel for the electron transport, as illustrated in Figure 1d. A control experiment with io-AZO in the absence of  $\text{BiVO}_4$  displays a low photocurrent response (back-side illumination) due to the large band gap of ZnO (3.2 eV), which supports that the photocurrent enhancement in  $\text{BiVO}_4/\text{io-AZO}$  heterostructure is not induced by an additional contribution from io-AZO (Figure 2b).

To gain a qualitative understanding of the charge recombination behavior in planar  $\text{BiVO}_4$  and heterostructured  $\text{BiVO}_4/\text{io-AZO}$ , the transient photocurrent decay occurring immediately upon illumination was investigated (Figure 2c). When the light is switched on, a photocurrent spike is observed due to the sudden generation of charge carriers, which quickly recombine after generation. The photocurrent decay can thus be attributed to recombination processes. Charge recombination can

be caused either by accumulation of electrons in the bulk or accumulation of holes at the surface. The accumulation of holes would cause an equally large cathodic transient when the light is switched off and electrons in the conduction band react with the accumulated holes<sup>32</sup>. However, cathodic transients can barely be observed in Figure 2c, indicating accumulation of holes is not the main recombination process in planar BiVO<sub>4</sub> film and BiVO<sub>4</sub>/io-AZO heterostructure electrodes. The transients in Figure 2c are thus attributed to the accumulation of electrons due to the poor electron transportation in BiVO<sub>4</sub>, which is consistent with the results observed from the front-/back-side illumination experiments (Figure 2b). The transient decay time can be calculated from a logarithmic plot of parameter  $D$ , given by the equation<sup>33,34</sup>

$$D = (I_t - I_s)/(I_m - I_s),$$

where  $I_m$  is the photocurrent spike,  $I_t$  is the photocurrent at time  $t$  and  $I_s$  is the steady state photocurrent.  $I_s$  is achieved as the recombination and charge generation reaches equilibrium<sup>34</sup>. The transient decay time is defined as the time at which  $\ln D = -1$ .<sup>33</sup> Therefore, based on the photocurrent profiles measured in Figure 2c, the transient decay times of planar BiVO<sub>4</sub> film and BiVO<sub>4</sub>/io-AZO heterostructure electrodes are calculated and plotted in Figure 2d. The transient decay time for BiVO<sub>4</sub>/io-AZO heterostructure electrode is 4.6 s, which is more than four times longer than the transient decay time of planar BiVO<sub>4</sub> films (1.0 s). Generally, the photocurrent decay rate is determined by the degree to which recombination dominates the charge generation process<sup>34</sup>. Therefore, we expect that a slower recombination rate gives rise to longer transient decay times and a significantly longer transient decay time is observed for the BiVO<sub>4</sub>/io-AZO heterostructure, suggesting a lower charge-carrier recombination rate in the heterostructure compared to the planar BiVO<sub>4</sub> film.

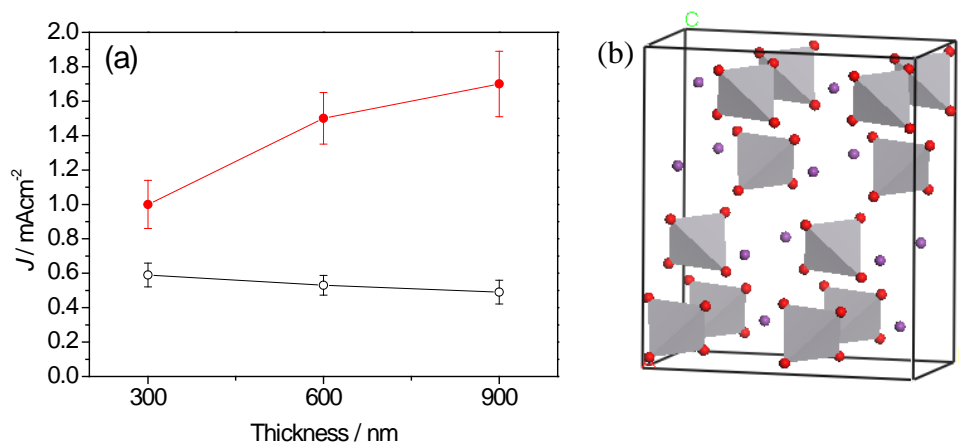


**Figure 3.** (a) Thickness dependence of the performance of planar BiVO<sub>4</sub> and BiVO<sub>4</sub>/io-AZO heterostructure electrodes. The photocurrent densities were measured at 1.23 V vs. RHE. (b) Crystal structure of BiVO<sub>4</sub>, purple ball represents Bi and red ball is O.

The dependence of the performance of planar BiVO<sub>4</sub> and BiVO<sub>4</sub>/io-AZO heterostructure




electrodes on the film thickness is further studied and displayed in Figure 3. Although light absorption might further improve with increasing film thickness for planar  $\text{BiVO}_4$ , a photocurrent decrease is found with a thicker film. The reason could be attributed to the poor electron transport in this film, which is caused by the crystal structure of  $\text{BiVO}_4$ . In  $\text{BiVO}_4$ , as displayed in Figure 3b, the  $\text{BiVO}_4$  crystal is composed of non-interconnecting  $\text{VO}_4$  tetrahedra. The conduction band of  $\text{BiVO}_4$  consists mainly of V 3d orbitals, and, consequently, the photogenerated electrons have to hop between  $\text{VO}_4$  tetrahedra in  $\text{BiVO}_4$ , as proposed by van de Krol and coworkers.<sup>27</sup> In the case of  $\text{BiVO}_4/\text{io-AZO}$  heterostructure electrodes, an increase in photocurrent density is observed with the thickness of the film from 300 to 900 nm, suggesting a good electron transport in the  $\text{BiVO}_4/\text{io-AZO}$  heterostructure. The io-AZO network has a pore size of 300 nm and the distance for the charge carrier in  $\text{BiVO}_4$  to reach the io-AZO network is therefore less than 150 nm and therefore equal or less than the charge carrier diffusion length in  $\text{BiVO}_4$  of approximately 100 to 200 nm.<sup>25</sup> In contrast, the electrons need to travel more than 300 nm to reach the FTO conductive substrate during front-illumination with a planar  $\text{BiVO}_4$  films of more than 300 nm thickness.

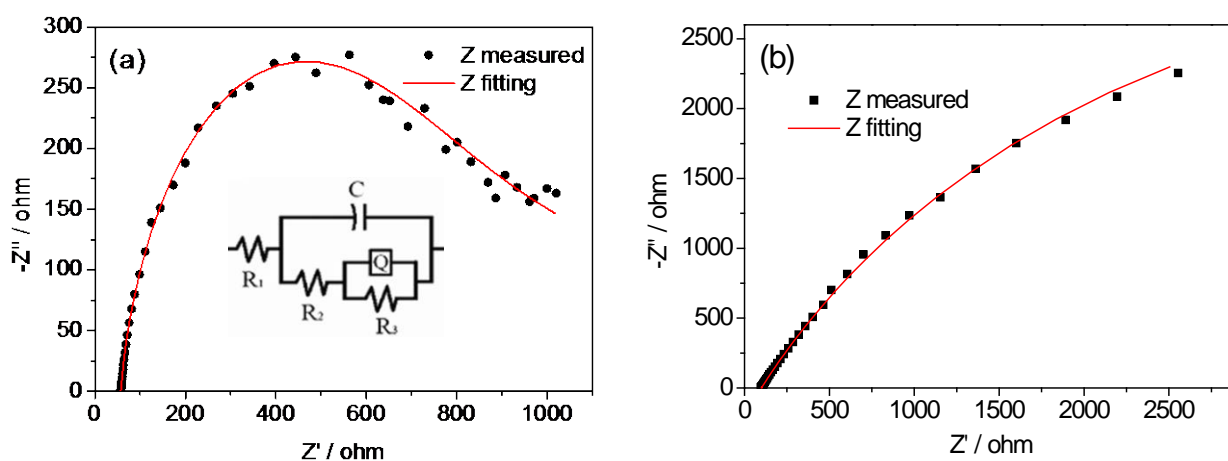

**Figure 4.** Nyquist EIS plots of (a)  $\text{BiVO}_4/\text{io-AZO}$  heterostructure and (b) planar  $\text{BiVO}_4$  without io-AZO framework. The inset of (a) is the equivalent circuit used to analyze the data, the red solid line is the fitted curve based on the proposed equivalent circuit.

To further confirm the charge-collecting improvement of the AZO inverse opal network, electrochemical impedance spectroscopy (EIS) studies are carried out at 1.23 V vs. RHE to investigate the impedance across the interface between  $\text{BiVO}_4$  and AZO inverse opal networks. A sinusoidal alternating-current (AC) perturbation of 5 mV was applied to the electrode over the frequency range of 0.1 to 65,000 Hz, and the impedance changes in response to the perturbation were measured. The EIS of planar  $\text{BiVO}_4$  films and  $\text{BiVO}_4/\text{io-AZO}$  heterostructures are plotted in the form of a Nyquist plot and displayed in Figure 4. An equivalent circuit (inset of Figure 4a) based on a mid-gap charge

carrier trapping mechanism<sup>35</sup>, was employed to analyze the data. In the employed equivalent circuit,  $R_1$  is the series resistance (including the resistance between  $\text{BiVO}_4$  and io-AZO),  $R_2$  is the resistance to trapping/detrapping electrons in/out of the mid-gap state,  $R_3$  represents the charge transfer resistance at the interface, whereas  $C$  is the capacitance of the space-charge region and  $Q$  represents the constant phase element. The fitted  $R_1$  for the planar  $\text{BiVO}_4$  films and  $\text{BiVO}_4/\text{io-AZO}$  heterostructures are  $99 \pm 2$  and  $42 \pm 3 \Omega$ , respectively. The small series resistance in  $\text{BiVO}_4/\text{io-AZO}$  suggests efficient charge transfer from  $\text{BiVO}_4$  to the charge collecting io-AZO network. A lower value of  $R_2$  suggests more efficient charge transfer across the electrode/electrolyte interface, reducing the possibility of charge recombination and thus enhancing the photocurrent response.<sup>36</sup> The fitted  $R_2$  values for planar  $\text{BiVO}_4$  films and  $\text{BiVO}_4/\text{io-AZO}$  heterostructures are  $9,200 \pm 60$  and  $1,560 \pm 10 \Omega$ , respectively. The charge transfer resistance is 83% lower in  $\text{BiVO}_4/\text{io-AZO}$  than planar  $\text{BiVO}_4$ , indicating that the  $\text{BiVO}_4/\text{io-AZO}$  heterostructure possesses more efficient charge transfer than that of the bare  $\text{BiVO}_4$  film due to the existence of the conductive charge collecting network.

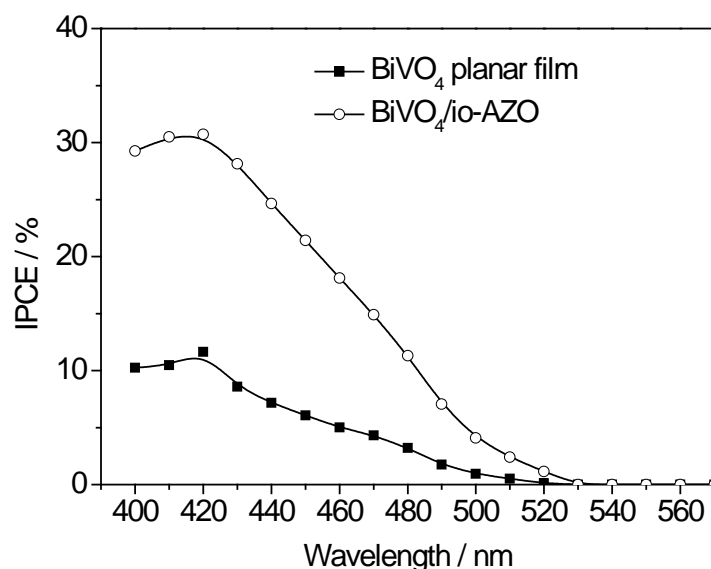

**Figure 5.** IPCE of  $\text{BiVO}_4/\text{io-AZO}$  heterostructure and planar  $\text{BiVO}_4$  without io-AZO.

The incident photon-to-charge conversion efficiencies (IPCEs) of the planar  $\text{BiVO}_4$  film and  $\text{BiVO}_4/\text{io-AZO}$  heterostructure are measured and plotted as a function of wavelength, as shown in Figure 5. The IPCE spectra of the planar and heterostructure electrodes both exhibit photoresponse up to 530 nm, as expected from the absorption edge of  $\text{BiVO}_4$ . For both electrodes, the maximum IPCE is achieved at 420 nm with 11.6% and 30.7% for the planar and  $\text{BiVO}_4/\text{io-AZO}$  electrode, respectively. We emphasize that the performance of the  $\text{BiVO}_4/\text{io-AZO}$  heterostructure is almost three times as high as that of the planar  $\text{BiVO}_4$  film, suggesting the introduction of conductive inverse opal networks into the  $\text{BiVO}_4$  film significantly improve the IPCE. A comparison of the UV-Vis

absorbance spectra (Figure S1 in SI) of the planar BiVO<sub>4</sub> and BiVO<sub>4</sub>/io-AZO heterostructure electrodes reveals that light absorption is enhanced by approximately 10% at 450 nm in the BiVO<sub>4</sub>/io-AZO heterostructure electrode compared to planar BiVO<sub>4</sub>, which may be attributed to light scattering within the io-AZO inverse opal network. This enhanced light absorption may also contribute to a small extent to the improved photocurrent. The heterostructure displays good photostability and the photocurrent only decreased by 6% at an applied potential of 1.23 V vs. RHE after 4 hours photoelectrochemical water splitting (see Figure S2 in the Supporting information).

In conclusion, to address the photogenerated electron transport problems in BiVO<sub>4</sub> photoanodes, an inverse opal structured Al-doped ZnO network with continuous pores and good conductivity is prepared and employed as charge transporter in BiVO<sub>4</sub> photoanodes to improve charge collection. The BiVO<sub>4</sub>/io-AZO heterostructure shows a photocurrent of 1.5 mA/cm<sup>2</sup> at 1.23 V vs RHE, which is a threefold enhancement compared to that of planar BiVO<sub>4</sub> photoanodes. The introduction of the conducting io-AZO network into BiVO<sub>4</sub> thereby significantly improves the charge collection in the BiVO<sub>4</sub>/io-AZO hybrid photoelectrode. Our approach has wide potential to be applied to other solar fuels systems to improve charge collection and solar energy conversion efficiency.

## Experimental

**Synthesis of AZO inverse opal.** Monodisperse PS (polystyrene) spheres with diameters of 320 nm (Sigma-Aldrich Chemie GmbH) were diluted to 0.2 wt%. The FTO glass slide was held vertically in a 10 mL vial containing the suspension of the monodisperse PS spheres. As the water evaporates and the meniscus sweeps down the substrate and capillary forces induce ordering of the spheres on the surface of the FTO glass slide.

The precursor for AZO was prepared by dissolving 0.02 mol zinc acetate dihydrate and  $6 \times 10^{-4}$  mol aluminium nitrate in 100 mL deionized water. To achieve a homogeneous infiltration of the transparent precursor into opal template, dip-coating infiltration was employed. The FTO glass with opal template was dipped into the precursor, and this process repeated until the template was well infiltrated with the precursor. Finally, the templates and organic components in the precursor were removed by heating at 450°C for 3 hours in air.

**Synthesis of BiVO<sub>4</sub>/io-AZO heterostructure.** The amorphous complex precursor used for the infiltration of the void volume of the io-AZO is produced as follows: 0.02 mol of diethylenetriaminepenta-acetic acid (H<sub>5</sub>DTPA) and 7.5 mL ammonia in water (13.0 mol/L) were added to 200 mL hot distilled water. After dissolution, 10 mmol of Bi(NO<sub>3</sub>)<sub>3</sub> (Sigma-Aldrich) and 4.850 mmol of V<sub>2</sub>O<sub>5</sub> powder (Sigma-Aldrich) were added. The resulting mixture was stirred and heated at 80 °C to promote complexation of Bi<sup>3+</sup> and V<sup>5+</sup> with DTPA and formation of a transparent solution.

The as-prepared io-AZO was dipped into the precursor, and this process repeated until the io-AZO was well infiltrated with the precursor. Then BiVO<sub>4</sub> is formed from the precursor and crystallized by heating at 500°C for 3 hours in air. A planar BiVO<sub>4</sub> with a comparable thickness was prepared for comparison employing the same method but without io-AZO network.

**Photoelectrochemical (PEC) measurement.** Photoelectrochemical measurements were carried out on an

electrochemical workstation (IVIUMSTAT). A conventional three electrodes configuration was used with BiVO<sub>4</sub>, Pt wire and Ag/AgCl electrode as working electrode, counter electrode and reference electrode, respectively. The electrolyte was an aqueous phosphate buffer at pH 7. The working electrodes were illuminated from the back side unless otherwise noted. The light source is a 100 mW/cm<sup>2</sup> solar light simulator equipped with an air mass 1.5 global filter and an IR water filter (Newport Oriel, 150 W). For IPCE measurements an Oriel Cornerstone 130 monochromator was used. All the potentials are reported against the reversible hydrogen electrode (RHE) by using the equation  $E \text{ (V vs. RHE)} = E \text{ (V vs. Ag/AgCl)} + 0.059\text{pH} + 0.197$ . The software ZSimpWin is employed to analyze the EIS data.

## Acknowledgements

This work was financially supported by the UK Engineering and Physical Science Research Council (EP/H00338X/2 to E.R., EP/G060649/1 to J.J.B.), the Christian Doppler Research Association (Austrian Federal Ministry of Economy, Family and Youth and National Foundation for Research, Technology and Development), the OMV Group (to E.R.), a Marie Curie Intra-European Fellowship (FP7-PEOPLE-2011-IEF 298012 to L.Z.) and the ERC (ERC LINASS 320503 to J.J.B.).

## Notes and references

1. M. Pagliaro, A. G. Konstandopoulos, R. Ciriminna and G. Palmisano, *Energy Environ. Sci.*, 2010, **3**, 279-287.
2. P. D. Tran, L. H. Wong, J. Barber and J. S. C. Loo, *Energy Environ. Sci.*, 2011, **5**, 5902-5918.
3. S. Bensaid, G. Centi, E. Garrone, S. Perathoner and G. Saracco, *ChemSusChem*, **5**, 500-521.
4. A. Paracchino, V. Laporte, K. Sivula, M. Gratzel and E. Thimsen, *Nat Mater*, 2011, **10**, 456-461.
5. A. J. Cowan, C. J. Barnett, S. R. Pendlebury, M. Barroso, K. Sivula, M. Gratzel, J. R. Durrant and D. R. Klug, *J. Am. Chem. Soc.*, 2011, **133**, 10134-10140.
6. A. Kay, I. Cesar and M. Gratzel, *J. Am. Chem. Soc.*, 2006, **128**, 15714-15721.
7. K. Sivula, F. Le Formal and M. Gratzel, *ChemSuschem*, 2011, **4**, 432-449.
8. G. M. Wang, Y. C. Ling, D. A. Wheeler, K. E. N. George, K. Horsley, C. Heske, J. Z. Zhang and Y. Li, *Nano Lett.*, 2011, **11**, 3503-3509.
9. D. K. Zhong and D. R. Gamelin, *J. Am. Chem. Soc.*, 2010, **132**, 4202-4207.
10. A. Walsh, Y. Yan, M. N. Huda, M. M. Al-Jassim and S. H. Wei, *Chem. Mater.*, 2009, **21**, 547-551.
11. L. W. Zhang, C. Baumanis, L. Robben, T. Kandiel and D. Bahnemann, *Small*, 2011, **7**, 2714-2720.
12. A. Kudo, K. Ueda, H. Kato and I. Mikami, *Catal. Lett.*, 1998, **53**, 229-230.
13. A. Kudo, K. Omori and H. Kato, *J Am Chem Soc*, 1999, **121**, 11459-11467.
14. R. G. Li, F. X. Zhang, D. G. Wang, J. X. Yang, M. R. Li, J. Zhu, X. Zhou, H. X. Han and C. Li, *Nat Commun*, 2013, **4**.
15. H. Ye, J. Lee, J. S. Jang and A. J. Bard, *J Phys Chem C*, 2010, **114**, 13322-13328.
16. S. Kohtani, M. Tomohiro, K. Tokumura and R. Nakagaki, *Appl Catal B-Environ*, 2005, **58**, 265-272.
17. Q. X. Jia, K. Iwashina and A. Kudo, *P Natl Acad Sci USA*, 2012, **109**, 11564-11569.
18. W. J. Luo, Z. S. Yang, Z. S. Li, J. Y. Zhang, J. G. Liu, Z. Y. Zhao, Z. Q. Wang, S. C. Yan, T. Yu and Z. G. Zou, *Energy Environ Sci*, 2011, **4**, 4046-4051.
19. K. J. McDonald and K. S. Choi, *Energy Environ Sci*, 2012, **5**, 8553-8557.
20. S. K. Pilli, T. E. Furtak, L. D. Brown, T. G. Deutsch, J. A. Turner and A. M. Herring, *Energ Environ Sci*, 2011, **4**, 5028-5034.
21. L. Tong, A. Iwase, A. Nattestad, U. Bach, M. Weidelener, G. Gotz, A. Mishra, P. Bauerle, R. Amal, G. G. Wallace and A. J. Mozer, *Energy Environ Sci*, 2012, **5**, 9472-9475.
22. F. F. Abdi, L. Han, A. H. M. Smets, M. Zeman, B. Dam and R. van de Krol, *Nat Commun*, 2013, **4**, DOI: 10.1038/ncomms3195.
23. W. J. Jo, J. W. Jang, K. J. Kong, H. J. Kang, J. Y. Kim, H. Jun, K. P. S. Parmar and J. S. Lee, *Angew Chem Int Edit*, 2012, **51**, 3147-3151.
24. K. P. S. Parmar, H. J. Kang, A. Bist, P. Dua, J. S. Jang and J. S. Lee, *ChemSuschem*, 2012, **5**, 1926-1934.
25. D. K. Zhong, S. Choi and D. R. Gamelin, *J. Am. Chem. Soc.*, 2011, **133**, 18370-18377.
26. H. S. Park, K. E. Kweon, H. Ye, E. Paek, G. S. Hwang and A. J. Bard, *J. Phys. Chem. C*, 2011, **115**, 17870-

- 17879.
27. Y. Liang, T. Tsubota, L. P. A. Mooij and R. van de Krol, *J. Phys. Chem. C*, 2011, **115**, 17594-17598.
  28. L.-W. Zhang, Y.-J. Wang, H.-Y. Cheng, W.-Q. Yao and Y.-F. Zhu, *Adv. Mater.*, 2009, **21**, 1286.
  29. S. Stoughton, M. Showak, Q. Mao, P. Koirala, D. A. Hillsberry, S. Sallis, L. F. Kourkoutis, K. Nguyen, L. F. J. Piper, D. A. Tenne, N. J. Podraza, D. A. Muller, C. Adamo and D. G. Schlom, *APL Materials*, 2013, **1**, 042112
  30. L. Chen, E. Alarcon-Llado, M. Hettick, I. D. Sharp, Y. Lin, A. Javey and J. W. Ager, *J Phys Chem C*, 2013, **117**, 21635-21642.
  31. F. F. Abdi, T. J. Savenije, M. M. May, B. Dam and R. van de Krol, *J Phys Chem Lett*, 2013, **4**, 2752-2757.
  32. R. v. d. Krol and M. Grazel, *Photoelectrochemical Hydrogen Production*, Springer, 2012.
  33. A. Hagfeldt, H. Lindstroem, S. Soedergren and S.-E. Lindquist, *J. Electroanal. Chem.*, 1995, **381**, 39-46.
  34. N. J. Bell, Y. H. Ng, A. Du, H. Coster, S. C. Smith and R. Amal, *J. Phys. Chem. C*, 2011, **115**, 6004-6009.
  35. K. J. Pyper, J. E. Yourey and B. M. Bartlett, *J Phys Chem C*, 2013, 10.1021/jp408434v.
  36. S. J. Hong, S. Lee, J. S. Jang and J. S. Lee, *Energy Environ. Sci.*, 2011, **4**, 1781-1787.

**Broader context**

Photoelectrochemical water splitting is an attractive approach to meet the urgent goal of efficiently and inexpensively converting solar energy into a storable and transportable fuel. A lack of efficient and inexpensive photoelectrodes inhibits the practical application of this technology. The short diffusion length of photogenerated charge carriers limits the performance of photoelectrodes for solar water splitting. We introduce a conductive Al-doped ZnO inverse opal network into a BiVO<sub>4</sub> photoanode, which has poor electron transport performance. The conductive inverse opal network serves as an electron collector for the BiVO<sub>4</sub> film and this approach enhances the photocurrent by three times compared to a planar BiVO<sub>4</sub> film. The enhanced performance is attributed to the improved charge transport and collection in the photoelectrode with the conductive inverse opal network. This design has the potential to improve the performance of other solar water splitting systems.