

Green Chemistry

Accepted Manuscript



This is an *Accepted Manuscript*, which has been through the Royal Society of Chemistry peer review process and has been accepted for publication.

Accepted Manuscripts are published online shortly after acceptance, before technical editing, formatting and proof reading. Using this free service, authors can make their results available to the community, in citable form, before we publish the edited article. We will replace this *Accepted Manuscript* with the edited and formatted *Advance Article* as soon as it is available.


You can find more information about *Accepted Manuscripts* in the [Information for Authors](#).

Please note that technical editing may introduce minor changes to the text and/or graphics, which may alter content. The journal's standard [Terms & Conditions](#) and the [Ethical guidelines](#) still apply. In no event shall the Royal Society of Chemistry be held responsible for any errors or omissions in this *Accepted Manuscript* or any consequences arising from the use of any information it contains.



www.rsc.org/greenchem

We report the synthesis of new aromatic biobased building-blocks from vanillin, for promising use in polymer synthesis

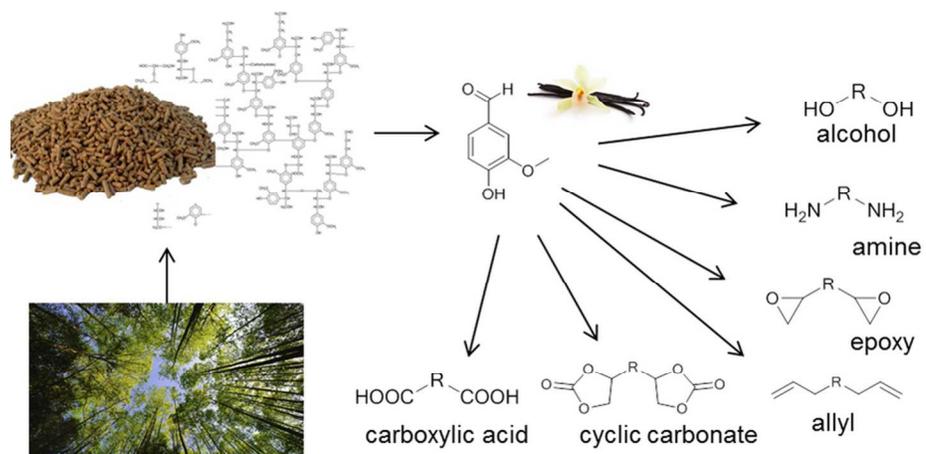

ARTICLE

Vanillin, a promising biobased building-block for monomer synthesis

Cite this: DOI: 10.1039/x0xx00000x

Maxence Fache,^a Emilie Darroman,^a Vincent Besse,^b Rémi Auvergne,^a Sylvain Caillol*^a and Bernard Boutevin^a

Received 00th January 2012,
Accepted 00th January 2012

DOI: 10.1039/x0xx00000x

www.rsc.org/

Vanillin was used as a renewable building-block to develop a platform of 22 biobased compounds for polymer chemistry. Vanillin-derived biobased monomers bearing epoxy, cyclic carbonates, allyl, amine, alcohol and carboxylic acid moieties were synthesized. They can be used, among many other, in epoxy, polyester, polyurethanes, and Non-Isocyanate PolyUrethanes (NIPU) polymer synthesis. The epoxy-functionalized compounds were synthesized under solvent-free conditions and are original biobased aromatic epoxy monomers. Cyclic carbonates were prepared through a catalytic reaction between epoxy compounds and CO₂. Thiol-ene reactions allowed the functionalization of allylated compounds with amines, acids and alcohols. The amine-functionalized compounds are to our knowledge the first non-aliphatic biobased amine hardeners, usable either in epoxy or NIPU materials.

Introduction

Recent years have witnessed an increasing demand on renewable resource-derived polymers (biobased polymers) owing to increasing environmental concern and restricted availability of petrochemical resources^{1,2}. Some solutions are already industrially available but most of these biobased polymers are aliphatic or cycloaliphatic polymers, for instance derived from cellulose¹, starch¹ or triglycerides³. However, many key commercial chemicals are aromatic compounds, ultimately derived from petrochemical feedstocks².

More recently, great attention was paid to renewable resource-derived thermosetting materials⁴, especially since they are crosslinked polymers and thus cannot be recycled. Also, most of thermosetting materials contain aromatic monomers, able to confer high mechanical and thermal properties to the network. Moreover, some base chemicals used nowadays are proven harmful and need to be replaced. For instance, bisphenol A is extensively used for the manufacturing of epoxy resins even if it is a reprotoxic substance⁵. Therefore, the access to biobased and non-harmful aromatic monomers is one of the main challenges of the years to come.

The three main sources of renewable aromatic compounds available are cashew nutshell liquid, polyphenols and lignin. Even if literature reports some very interesting works based on cardanol⁶ or natural flavonoids^{7,8} to synthesize promising materials, lignin is the most abundant feedstock⁹. Lignin is an amorphous cross-linked polymer that gives structural integrity to plants, making up 25 to 35% of woody biomass¹⁰. Thus, depolymerization of lignin is an alluring route to give access to

biobased aromatics needed by the chemical industry. Unfortunately, this route is deceptive. Despite extensive research¹¹, there are very few reports of efficient ways of recovering such aromatic products.

The only notable commercial process has been the historical production of vanillin from lignosulfonates contained in the "brown liquor", a by-product of the sulfite pulping paper industry. Even though this process uses cheap and available waste materials, it declined because of environmental concerns. Nowadays, Solvay dominates the vanillin market using the petroleum-based catechol-guaiacol process. 85% of the vanillin is produced from this method and 15% still from lignin^{12,13}.

Most recently, however, lignin-to-vanillin routes regained a lot of interest¹²⁻¹⁴ with technical advances in processes¹⁵ as well as in waste management. For instance, Borregaard, the second largest vanillin producer in the world and the only one with a vanillin-from-lignin process, employs an ultrafiltration technology, achieving a reduction in waste stream volumes¹⁶. Therefore, instead of expecting various biobased aromatics from lignin depolymerization, which is not a mature technology, the improvement of lignin-to-vanillin processes and the use of vanillin as a biobased building-block for polymer chemistry seems a better perspective.


Even though the lignin-derived vanillin is becoming relatively easily accessible, still there are only a handful of reports on attempts to utilize vanillin as monomers for biobased polymer synthesis. Amarasekara et al. reported the dimerization and electrochemical reductive polymerization with horseradish peroxidase¹⁷. The Schiff base synthesized was used for metal ions chelation applications¹⁸. Schiff bases from vanillin were

also prepared by Issam et al. and transformed in epoxies in a second step¹⁹. Concerning epoxy compounds, Aouf et al. prepared the allylated vanillic acid and worked on its epoxidation by a chemo-enzymatic process with *Candida Antartica* lipase²⁰. Koike described an interesting process allowing the synthesis of an epoxy monomer from vanillin²¹. Other teams reported the synthesis of various biobased polymers from vanillin. Thus, Meier et al. reported the synthesis of polymers from vanillin and fatty acids by acyclic diene metathesis (ADMET)²². Starting from vanillin, Mialon et al. synthesized polyesters such as polydihydroferulic acid²³ and polyethylene vanillate²⁴. Photoactive liquid crystalline polyesters and polyethers were also prepared from vanillin^{25, 26}. An original benzoxazine monomer was prepared from vanillin and furfurylamine by Sini et al. and then polymerized²⁷. Additionally, vanillin was methacrylated and used in the preparation of UV-curable palladium-chelating chitosan derivatives²⁸. Vanillin methacrylate also replaced styrene in vinyl-ester resins for composite application²⁹. Composites were synthesized directly from vanillin, sorbitol, pyrogallol with wood flour³⁰.

From the few but interesting works cited, it is clear that vanillin has a huge potential to meet the aforementioned challenge concerning biobased monomers. It is biobased, potentially abundantly available and does not compete with edible

resources. Its aromatic structure could provide the desired thermal and mechanical properties to materials and its different substituents lead us to consider it as a versatile biobased platform chemical. Our approach in this work was thus to synthesize from vanillin a wide range of difunctional monomers directly usable in polymer synthesis. These synthesis routes were chosen in order to optimize the yields and with a reduced number of steps, to show the industrial potential of this platform.

We designed this platform with three vanillin derivatives as base chemicals, owing to their different oxidation state. This choice was based on the fact that lignin depolymerization often requires harsh oxidative or reductive conditions³¹. Thus, it is mandatory to consider not only vanillin itself, as it is common in the literature, but also its different oxidative states as potentially available. On the one hand, a vanillin **1** oxidation leads to vanillic acid **3** or even to a methoxyhydroquinone **2** in the case of a decarboxylation (strong oxidative and alkaline conditions³²). On the other hand, reduction leads to vanillyl alcohol **4**. Our team functionalized these three molecules, transforming them into a number of original biobased monomers bearing well-known polymerizable functions and thus creating the above-mentioned platform shown in **Scheme 1**. Many of these compounds were prepared for the first time.

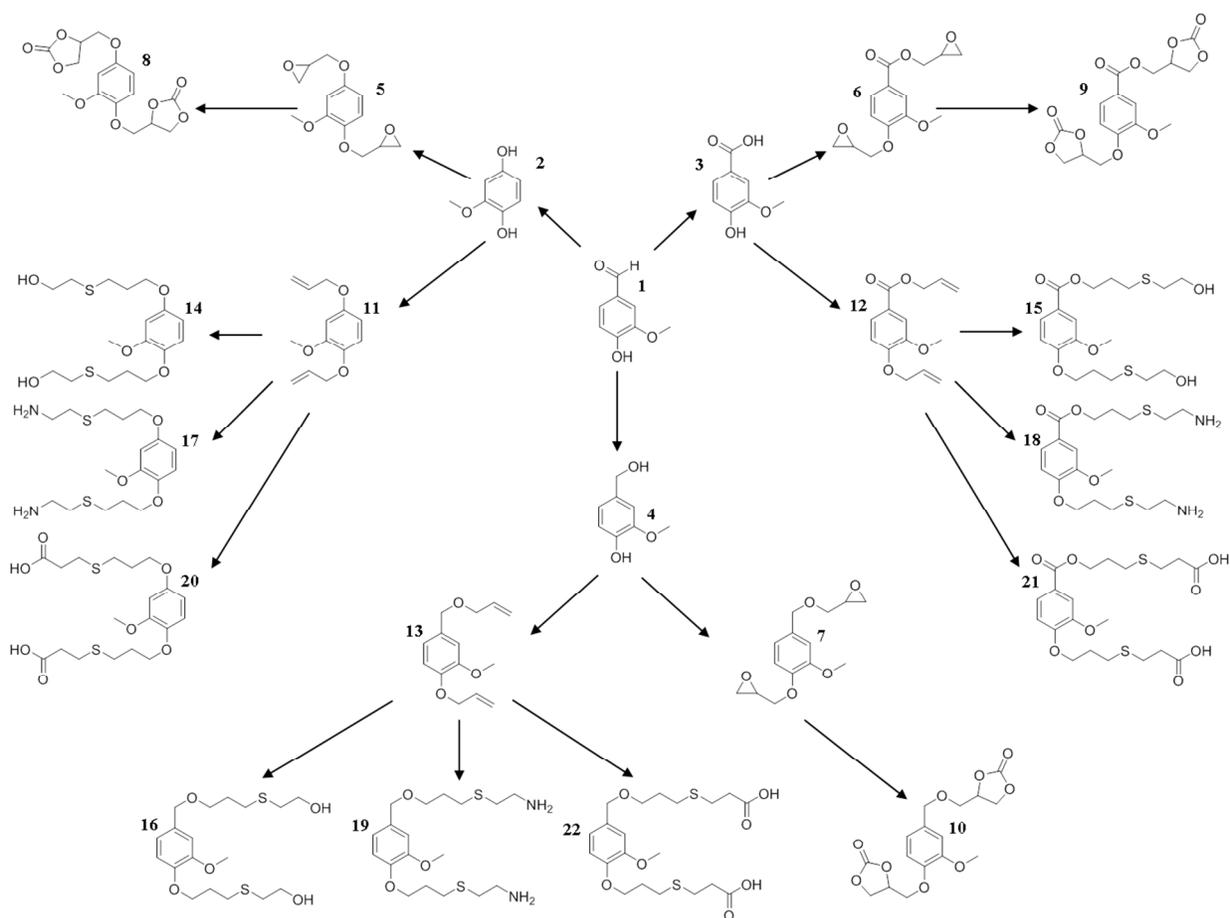

Scheme 1: Vanillin platform for polymer synthesis

The functions introduced in this platform and the types of polymers in which they could be used are summarized in **Table 1**.


Table 1: Functions present in the platform and their use in polymer chemistry

Function of monomers	Compounds	Targeted polymers
	5, 6, 7	Epoxy resins
	8, 9, 10	PolyHydroxyUrethanes (PHUs); Polycarbonates
	11, 12, 13	Polymers obtained by radical polymerization
	14, 15, 16	PolyUrethanes (PUs), polyesters, polyacrylates, polycarbonates
	17, 18, 19	Epoxy resins, PHUs, polyimides, polyureas, polyamides
	20, 21, 22	Epoxy resins, polyamides, poly(vinyl-esters), polyesters

Results and discussion

Platform base chemicals

Among the three platform base chemicals, vanillic acid **3** and vanillyl alcohol **4** are quite common commercial compounds. However, to the best of our knowledge, 2-methoxyhydroquinone **2** is not commercially available. It was thus prepared in 97% yield from vanillin by the Dakin reaction, ultimately leading to one carbon loss. The reaction proceeds *via* the mechanism shown in **Scheme 2**:

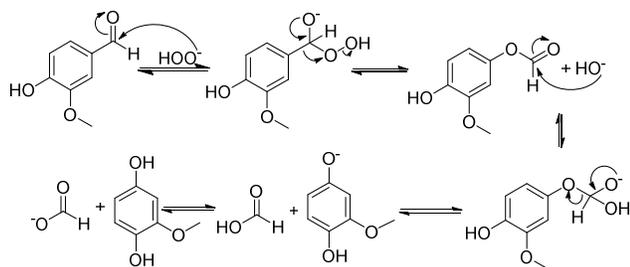


Scheme 2: Mechanism of the vanillin Dakin oxidation

Sodium percarbonate dissociates in solution into H_2O_2 and carbonate anions. As the solution is basic, a hydroperoxide anion can exist. The reaction starts with a nucleophilic addition of this hydroperoxide anion onto the aldehyde carbonyl. The final acidification of the mixture is important for two reasons. Firstly, the pH of the solution becomes acid, carbonates and hydroperoxide anions no longer exist in solution, thus stopping any further reaction. Secondly, the aqueous phase must be acid for the phenol form to predominate over the phenolate one in order to perform the extraction efficiently.

The protocol used³² is very efficient and the handling simple. Moreover, the oxidation reagent used, sodium percarbonate, has major advantages: it is inexpensive, large-scale available as it is extensively used in the detergent industry as a bleaching agent, easier to handle than a classic H_2O_2 solution and finally respectful towards sustainable development principles due to its safety and environmental innocuity.

Glycidylation reactions


Glycidyl ethers **5**, **6** and **7** were obtained respectively from the three base chemicals **2**, **3**, and **4** in very good yields ($\geq 87\%$). We are the first, to our knowledge, to synthesize compounds **5** and **7**. In a previous paper, Aouf et al. proved that aromatic hydroxyl and acid functions readily react with epichlorohydrin in the absence of solvent³³. We adapted this method for the synthesis of **5** and **6**. The reaction mechanism is explained in **Scheme 3**:

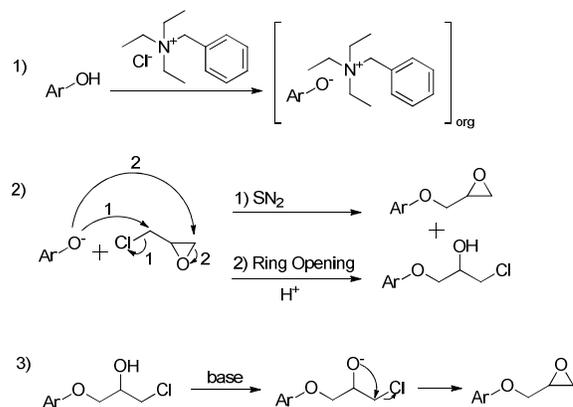

Scheme 3: Phenol glycidylation mechanism under solvent-free conditions

In a first step, a phase transfer catalyst (triethylbenzylammonium chloride - TEBAC) is used to allow the phenolate ion to exist in organic solution. In a second step, this phenolate ion reacts with epichlorohydrin *via* two possible mechanisms, namely $\text{S}_{\text{N}}2$ and ring opening. $\text{S}_{\text{N}}2$ gives the expected glycidylated product and ring opening leads to a chlorinated intermediate. In a third step, this chlorinated intermediate is closed by an intramolecular $\text{S}_{\text{N}}2$ reaction in the presence of an aqueous solution of NaOH and phase transfer catalyst.

The synthesis of **7** starting from **4** was attempted with this method. **4** possesses both a phenol and a benzyl alcohol. Glycidylation only occurred on the phenol, and not on the benzyl alcohol. This was explained by the fact that protons from phenols are more acidic than protons from aliphatic alcohols. Thus, contrary to phenolates, benzyl alcoholates cannot form an ion pair with the phase transfer catalyst to exist in the organic medium. It is worthy to note that although this reactivity difference is problematic here, it could be an advantage in another context. In our case, **7** was synthesized using a biphasic phase transfer catalysis system³⁴. The mechanism is shown in **Scheme 4**:

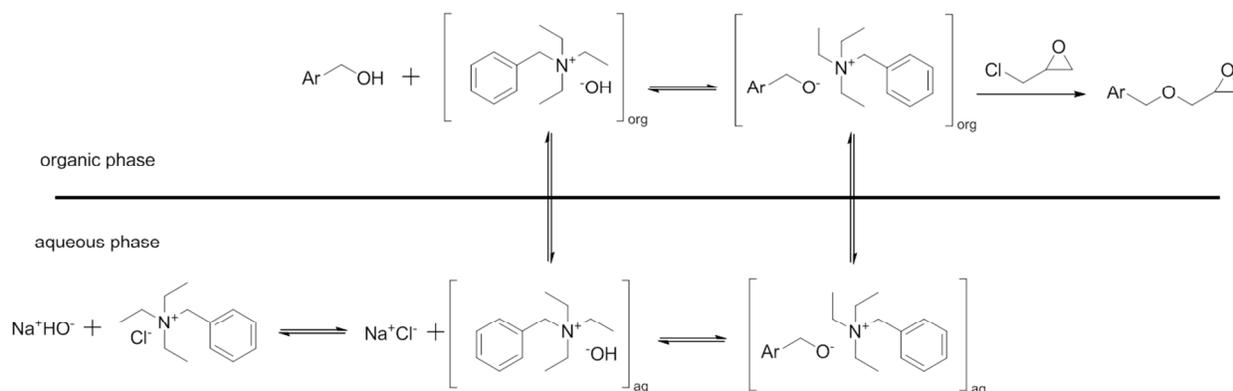


Scheme 4: Mechanism of phenol glycidylation by a phase transfer catalysis system

Careful temperature control is mandatory as the reaction is exothermic and any rise of temperature resulted in a colored, crosslinked product.

These reactions do not require organic solvents since epichlorohydrin is used as a reactive solvent. Epichlorohydrin was employed as it is an industrial biobased compound *via* the Epicerol® process from Solvay. Epoxy compounds **5**, **6** and **7** have potential uses in high performance epoxy resins and composites as they are biobased aromatic diglycidyl ethers. Indeed, they are structurally similar to current petrobased epoxy monomers. They need to be tested as Bisphenol A substitutes in terms of safety and of material performances.

Carbonation reactions

Cyclic carbonate compounds **8**, **9** and **10** were respectively synthesized from the epoxy compounds **5**, **6**, and **7** previously obtained. Compounds **8** and **10** were obtained quantitatively. In the case of **9**, undetermined side products were detected by ^1H NMR, making this synthesis less interesting from an industrial standpoint. However, there is, as far as we know, no other description of compounds **8**, **9** and **10**. These bifunctional cyclic carbonates were obtained by a LiBr-catalyzed CO_2 insertion into the oxirane rings³⁵ as shown in **Scheme 5**:

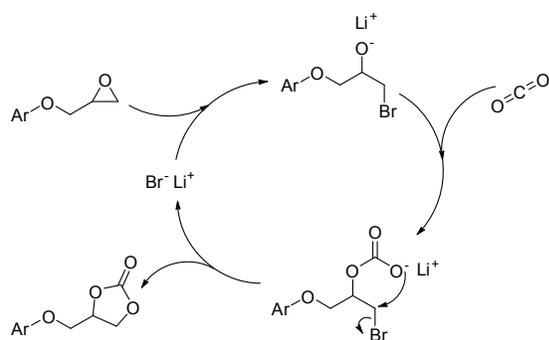

Scheme 5: Cyclic carbonate synthesis from an epoxy compound

The two advantages of this reaction are a CO_2 consumption driven by a catalytic system. From a sustainable chemistry

point of view, two major challenges concern the polyurethane industry. The first one, true for the whole polymer industry, is to switch from petrobased to biobased resources. The second one, more specific to polyurethanes, is to avoid the use of isocyanate compounds since most of them (methylene diisocyanate - MDI, toluene diisocyanate - TDI) are highly toxic or CMR, and are synthesized from phosgene, also highly toxic. Therefore, NIPUs (Non-Isocyanate PolyUrethanes) systems received a great deal of interest over the past years. These systems are actually synthesized by reaction between poly(cyclic carbonates) with polyamines³⁵, leading to polyhydroxyurethanes (PHUs). As these systems are shifting from academic studies to industrial use, there is a growing need of bis(cyclic carbonates) monomers and especially aromatic ones in substitution to MDI or TDI for the synthesis of linear polymers. We thus synthesized **8**, **9** and **10** which are biobased, aromatic bis(cyclic carbonates) usable in NIPU systems.

Allylation reactions

Allylated compounds **11**, **12** and **13** were respectively synthesized from base chemicals **2**, **3** and **4**. A method used for the allylation of gallic acid was already reported by our team⁸. Compounds **11** and **12** were prepared quantitatively using this method. A phenolate (or carboxylate) is first formed by the action of suspended potassium carbonate K_2CO_3 . This phenolate (or carboxylate) is then allylated by an easy nucleophilic attack on allyl bromide. As in the case of glycidylation, the benzylic alcohol moiety in **4** is less reactive than phenols or benzoic acids. Compound **4** was thus allylated by using the same phase transfer catalysis system. The mechanism is also the same as the one described in **Scheme 4**, the only difference being the use of allyl bromide instead of epichlorohydrin. It was found that phase transfer catalysis is a mild and efficient process for the synthesis of **13** (86% yield). Allyl bromide is not a biobased compound. Since allylated compounds can undergo radical polymerization and thiol-ene click chemistry, compounds **11**, **12** and **13** are therefore essential building-blocks to establish our vanillin-based platform for polymer chemistry.

Alcohol functionalization

Alcohol-functionalized compounds **14**, **15** and **16** were obtained in yields $\geq 90\%$ in solvent-free conditions by thiol-ene “click” addition of mercaptoethanol onto allylated compounds **11**, **12** and **13** respectively. This work is the first example, to the best of our knowledge, to report the synthesis of compounds **14**, **15** and **16**.

Click chemistry is a concept now well established and received a lot of attention lately, especially in the field of sustainable chemistry. Indeed, the click chemistry concepts of efficient, versatile, and safe procedures with a high atom economy fit with sustainable chemistry principles. Click chemistry reactions are thus more and more applied to renewable resources³⁶.

Thiol-ene coupling is considered as a click chemistry reaction and has been extensively used in the polymer field³⁷. It consists in the radical addition of a thiol onto a C-C double bond. This coupling was for instance used by our team to synthesize new biobased polyols from vegetable oils. Thiol-ene coupling displays high yields and outstanding functional group tolerance under simple reaction conditions. The reaction can either be initiated by heat or UV irradiation, as in our case.

Molecules **14**, **15** and **16** are alcohol-functionalized biobased compounds bearing an aromatic ring. The aromatic ring provides better thermo-mechanical properties to the material than an aliphatic structure. They also bear primary aliphatic alcohols, making them very reactive. Molecules **14**, **15**, and **16** could therefore bring interesting properties to polyesters or to PU formulations.

Amine functionalization

Amine-functionalized compounds **17**, **18** and **19** were synthesized by thiol-ene addition of cysteamine hydrochloride onto respectively **11**, **12** and **13** in yields $\geq 88\%$. Compounds **17**, **18** and **19** are also, as far as we know, described here for the first time. Cysteamine hydrochloride was preferred over cysteamine because the amine moiety catalyzes the formation of disulfide bonds. Interestingly, thiol-ene addition was slower with cysteamine hydrochloride than with mercaptoethanol. Amine-functional compounds were obtained by simple deprotonation of the ammonium in a basic aqueous solution followed by an extraction with an organic solvent.

17, **18** and **19** are of great interest for epoxy thermosets and NIPU manufacturing as they are biobased aromatic compounds bearing two highly reactive primary amines. They can thus react with epoxy and cyclocarbonates moieties. Moreover, hardeners with an aromatic structure will improve thermo-mechanical properties. Concerning epoxy thermosets, good thermo-mechanical properties are one of their characteristic features. As for NIPU systems, tunable properties are needed to fit to the application. These compounds are, to our knowledge, the first non-aliphatic and biobased amine hardeners. They could thus prove very useful from an industrial standpoint.

Carboxylic acid functionalization

Acid-functionalized compounds **20**, **21** and **22** were synthesized by thiol-ene addition of 3-mercaptopropionic acid onto respectively **11**, **12** and **13** in solvent-free conditions. To the best of our knowledge, compounds **20**, **21** and **22** are not mentioned in previous literature.


In the first place, the reaction was attempted with thioglycolic acid and was much faster but gave rise to unwanted side-products. Literature reports such side-products, especially thioesters, in the case of thioglycolic acid³⁸. Thus, the use of 3-mercaptopropionic acid was preferred over thioglycolic acid.

This reaction was slower than the other thiol-ene reactions performed, especially in the case of **11** where only 68% were converted to **20**. **12** and **13** gave good conversions. However, no side-products were detected.

Compounds **20**, **21** and **22** also bear an aromatic ring that may improve thermo-mechanical properties of materials. They are dicarboxylic acids and can thus be used as epoxy resins hardeners but also as monomers in biobased polyesters.

Example of material synthesized

Each type of compound is currently evaluated for the synthesis of materials, especially NIPUs and epoxy polymers. These studies will be reported in detail in future articles. However, as an example of the potential use of these compounds, we chose to prepare an epoxy material (**Scheme 6**) from **Product 5**. The amine hardener chosen was the one most reported in the literature, IsoPhorone DiAmine (IPDA):

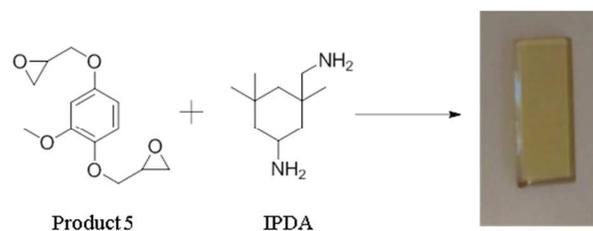

Scheme 6: Material prepared from **Product 5** and IPDA

Preliminary DSC results indicate a T_g of 117°C for this material. By improving the formulation and the process, the T_g could reach a value close to the one of the epoxy polymer prepared from DiGlycidylEther of Bisphenol A (DGEBA) and IPDA, namely 158°C ³⁹. This material is the most described in the literature and the most used in industry. However, DGEBA is derived from bisphenol A, a reprotoxic substance⁵ and thus need to be replaced. The material prepared from **Product 5** is a high- T_g , biobased alternative to the DGEBA-IPDA system that will be investigated in future works.

Experimental


Materials and methods

Vanillin (99%) and vanillic acid (99%) were purchased from ABCR. Vanillyl alcohol (98%), sodium percarbonate $\text{Na}_2\text{CO}_3 \cdot 1.5\text{H}_2\text{O}_2$ (available H_2O_2 20-30%), triethylbenzylammonium chloride (TEBAC) (99%), LiBr

(99%), mercaptoethanol (>99%), thioglycolic acid (>99%), 3-mercaptopropionic acid (>99%), potassium carbonate K_2CO_3 (>99%), allyl bromide (99%), IPDA (>99%), anhydrous sodium sulfate Na_2SO_4 (99%) and HCl (37.5% wt.) and all solvents used (>99.5%) were purchased from Sigma-Aldrich. Cysteamine hydrochloride (>97%) and epichlorohydrin (>99%) were purchased from Fluka. Sodium hydroxide NaOH (99%) was purchased from Fisher. All reactives were used as received. 1H and ^{13}C (APT mode) NMR spectra were recorded on a 400MHz Bruker Aspect Spectrometer at room temperature. Deuterated solvents used are given for each molecule. Chemical shifts are in ppm. Silica gel flash chromatography was performed on a Grace Davison Reveleris device. UV irradiation was performed in a Rayonet RPR-200 UV reactor equipped with a cooling fan and 16 lamps of 35W each with a $\lambda_{max} = 254nm$. A 50mL Paar autoclave equipped with an overhead stirrer was used for carbonation reactions. MS measurements were performed on a Waters Synapt G2-S High Resolution Mass Spectrometer (HRMS) equipped with an ESI ionization source. DSC analyses were carried out on a NETZSCH DSC200 calorimeter at 20°C/min.

Synthesis of methoxyhydroquinone 2 from vanillin 1

A two-necked round-bottomed flask was charged with a solution of vanillin (0.25 mol.L⁻¹, 1.0 eq.) in THF. Deionized water (40% vol.) was added. The mixture was degassed with nitrogen. Sodium percarbonate ($Na_2CO_3 \cdot 1.5H_2O_2$, 1.1 eq.) was then added by portions under nitrogen and agitation. The reaction was conducted for 3 hours at room temperature. Portions of a HCl solution (0.1 mol.L⁻¹) were added to the mixture under vigorous stirring until pH = 3 to quench the reaction. THF was evaporated and the aqueous phase was extracted with ethyl acetate. The organic phases were collected, washed with brine, dried on anhydrous Na_2SO_4 and ethyl acetate was removed under reduced pressure.



Product 2: methoxyhydroquinone (97%, m.p. 88°C)

1H NMR (400.1MHz, acetone-d₆, ppm) δ : 3.77 (s, 3H, H₇); 6.27 (dd, $^3J_{H_6H_5}=8.4$ Hz, $^4J_{H_6H_2} = 2.6$ Hz, 1H, H₆); 6.46 (d, $^4J_{H_2H_6}=2.6$ Hz, 1H, H₂); 6.63 (d, $^3J_{H_5H_6}=8.4$ Hz, 1H, H₅); 6.86 (broad s, 1H, H₈); 7.73 (broad s, 1H, H₉).


^{13}C NMR (100.6 MHz, acetone-d₆, ppm) δ : 56.38 (s, C₇); 101.40 (s, C₂); 107.64 (s, C₆); 116.13 (s, C₅); 140.71 (s, C₄); 149.07 (s, C₃); 151.82 (s, C₁).

HRMS (m/z, AP+): Calculated: 140.0473; Found: 140.0473.

Procedures for glycidylation (5, 6, 7)

This protocol was used for the preparation of 5 and 6 from 2 and 3. A round-bottomed flask was charged with 2 or 3 (1.0 eq.) and TEBAAC (0.1 eq.). Epichlorohydrin (10.0 eq.) was

added and the mixture was stirred for 1 hour after reaching 80°C. The solution was then cooled down to room temperature. An aqueous solution of TEBAAC (0.1 eq.) and NaOH (4.0 eq., 5.0 mol.L⁻¹) was added and the mixture was stirred 30 minutes at room temperature. Ethyl acetate and deionized water were then added. The mixture was stirred and the aqueous phase was extracted with ethyl acetate. Organic phases were combined, rinsed with brine and dried on anhydrous Na_2SO_4 . Ethyl acetate and epichlorohydrin excess were removed on rotary evaporator. Further purification was achieved by silica gel flash chromatography using a hexane/ethyl acetate gradient as eluent.




Product 5: 2,2'-(((3-methoxy-1,4-phenylene)bis(oxy))bis(methylene)) bis(oxirane) (87%, m.p. 87°C)

1H NMR (400.1 MHz, acetone-d₆, ppm) δ : 2.66 (m, 2H, H_{10a}, H_{13a}); 2.81 (m, 2H, H_{10b}, H_{13b}); 3.27 (m, 2H, H₉, H₁₂); 3.81 (m, 2H, H_{8a}, H_{11a}); 3.81 (s, 3H, H₇); 4.23 (m, 2H, H_{8b}, H_{11b}); 6.43 (dd, $^3J_{H_6H_5} = 8.8$ Hz, $^4J_{H_6H_2} = 2.8$ Hz, 1H, H₆); 6.63 (d, $^4J_{H_2H_6} = 2.8$ Hz, 1H, H₂); 6.88 (d, $^3J_{H_5H_6} = 8.8$ Hz, 1H, H₅).

^{13}C NMR (100.6 MHz, acetone-d₆, ppm) δ : 44.91 (s, C₁₀, C₁₃); 51.16 (s, C₁₂); 51.32 (s, C₉); 56.63 (s, C₇); 71.09 (s, C₁₁); 72.89 (s, C₈); 102.57 (s, C₂); 105.90 (s, C₆); 117.37 (s, C₅); 144.29 (s, C₄); 152.51 (s, C₃); 155.66 (s, C₁).

HRMS (m/z, ES+, [M+H⁺]): Calculated: 253.1079; Found: 253.1076.




Product 6: oxiran-2-ylmethyl 3-methoxy-4-(oxiran-2-ylmethoxy) benzoate (95%, m.p. 77°C)

1H NMR (400.1 MHz, CDCl₃, ppm) δ : 2.72 (m, 1H, H_{14a}); 2.77 (m, 1H, H_{10a}); 2.91 (m, 2H, H_{10b}, H_{14b}); 3.34 (m, 1H, H₁₃); 3.40 (m, 1H, H₉); 3.92 (s, 3H, H₁₁); 4.09 (m, 2H, H_{8a}, H_{12a}); 4.34 (dd, 1H, H_{12b}); 4.64 (m, 1H, H_{8b}); 6.94 (d, $^3J_{H_5H_6} = 8.4$ Hz, 1H, H₅); 7.57 (d, $^4J_{H_2H_6} = 2.0$ Hz, 1H, H₂); 7.69 (dd, $^3J_{H_6H_5} = 8.4$ Hz, $^4J_{H_6H_2} = 2.0$ Hz, 1H, H₆).

^{13}C NMR (100.6 MHz, CDCl₃, ppm) δ : 44.68 (s, C₁₀); 44.78 (s, C₁₄); 49.52 (s, C₉); 49.90 (s, C₁₃); 56.04 (s, C₁₁); 65.37 (s, C₈); 69.86 (s, C₁₂); 112.29 (s, C₅); 112.63 (s, C₂); 122.85 (s, C₁); 123.65 (s, C₆); 149.05 (s, C₃); 152.16 (s, C₄); 165.92 (s, C₇).

HRMS (m/z, ES+, [M+H⁺]): Calculated: 281.1025; Found: 281.1025.

For the preparation of **7** from **4**, a phase transfer catalysis system was used. A round-bottomed flask was charged with **4** (1.0 eq.) and TEBAC (0.1 eq.). Epichlorohydrin (10.0 eq.) was added and the mixture was stirred for 4 hours until obtention of a limpid pink solution. This solution was cooled down to 0°C with an ice bath. A NaOH solution (33% w., 15.0 eq.) in deionized water was prepared and poured into the cold mixture under vigorous stirring. The reaction was conducted overnight at room temperature (the ice bath was left to melt over time). Deionized water was added to the mixture to dilute 4 times the NaOH solution. An equal volume of ethyl acetate was added. The mixture was stirred and the aqueous phase was extracted 2 more times with ethyl acetate. Organic phases were combined, rinsed with brine and dried on anhydrous Na₂SO₄. Ethyl acetate and epichlorohydrin excess were removed on rotary evaporator. Further purification was achieved by silica gel flash chromatography using a hexane/ethyl acetate gradient as eluent.



Product 7: 2-((3-methoxy-4-((oxiran-2-ylmethoxy) methyl) phenoxy) methyl)oxirane (89%, m.p. 53°C)


¹H NMR (400.1 MHz, acetone-d₆, ppm) δ: 2.53 (dd, 1H, H_{14a}); 2.69 (m, 2H, H_{10a}, H_{14b}); 2.81 (m, 1H, H_{10b}); 3.10 (m, 1H, H₁₃); 3.30 (m, 2H, H₉, H_{12a}); 3.73 (dd, 1H, H_{12b}); 3.82 (s, 3H, H₇); 3.87 (dd, 1H, H_{8a}); 4.28 (dd, 1H, H_{8b}); 4.47 (d, 2H, H₁₁); 6.86 (dd, ³J_{H₆H₅} = 8.0 Hz, ⁴J_{H₆H₂} = 1.6 Hz, 1H, H₆); 6.94 (d, ³J_{H₅H₆} = 8.0 Hz, 1H, H₅); 6.98 (d, ⁴J_{H₂H₆} = 1.6 Hz, 1H, H₂).

¹³C NMR (100.6 MHz, acetone-d₆, ppm) δ: 44.16 (s, C₁₄); 44.49 (s, C₁₀); 50.76 (s, C₉); 51.28 (s, C₁₃); 56.16 (s, C₇); 71.39 (s, C₈); 71.82 (s, C₁₂); 73.42 (s, C₁₁); 112.91 (s, C₅); 114.76 (s, C₂); 120.99 (s, C₆); 132.93 (s, C₁); 148.86 (s, C₄); 150.75 (s, C₃).

HRMS (m/z, ASAP⁻, [M]⁻): Calculated: 266.1153; Found: 266.1154.

Procedures for carbonation (8, 9, 10)

Epoxy-functionalized compound **8**, **9** or **10** (1.0 eq.) and LiBr (0.05 eq.) were stirred in acetone (35 mL) and introduced in the autoclave. The atmosphere was replaced with CO₂ (P = 12 bar), then the solution was heated at 80°C with continuous stirring during 12 hours. The solvent was distilled under vacuum (P = 0.01 bar) at 60°C. Deionized water was added and the aqueous phase was extracted with ethyl acetate. The organic phase was washed with brine, dried on anhydrous Na₂SO₄ and ethyl acetate was removed on rotary evaporator.

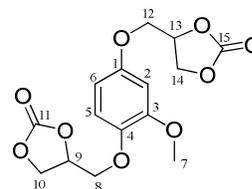


Product 8 : 4,4'-(((3-methoxy-1,4-phenylene) bis(oxy)) bis(methylene))bis(1,3-dioxolan-2-one) (100%, m.p. n.d.)

¹H NMR (400.1 MHz, DMSO-d₆, ppm) δ: 3.76 (s, 3H, H₇); 4.16 (m, 4H, H₈, H₁₂); 4.39 (m, 2H, H_{10a}, H_{14a}); 4.61 (q, 2H, H_{10b}, H_{14b}); 5.11 (m, 2H, H₉, H₁₃); 6.47 (dd, ³J_{H₆H₅} = 8.8 Hz, ⁴J_{H₆H₂} = 2.8 Hz, 1H, H₆); 6.63 (d, ⁴J_{H₂H₆} = 2.8 Hz, 1H, H₂); 6.93 (d, ³J_{H₅H₆} = 8.8 Hz, 1H, H₅).

¹³C NMR (100.6 MHz, DMSO-d₆, ppm) δ: 55.77 (s, C₇); 65.95 (s, C₁₄); 66.00 (s, C₁₀); 67.91 (s, C₁₂); 69.73 (s, C₈); 74.88 (s, C₁₃); 75.12 (s, C₉); 101.25 (s, C₂); 104.76 (s, C₆); 116.29 (s, C₅); 142.08 (s, C₄); 150.53 (s, C₃); 153.57 (s, C₁); 154.87 (s, C₁₁, C₁₅).

HRMS (m/z, ASAP⁺, [M+H]⁺): Calculated: 341.0871; Found: 341.0873.

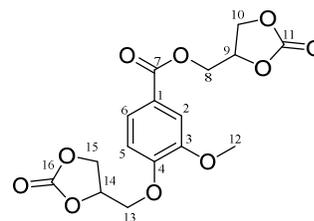


Product 9: (2-oxo-1,3-dioxolan-4-yl)methyl 3-methoxy-4-((2-oxo-1,3-dioxolan-4-yl)methoxy) benzoate (50%, m.p. n. d.)

¹H NMR (400.1 MHz, acetone-d₆, ppm) δ: 3.87 (s, 1H, H₁₂); 4.42 (m, 2H, H_{13a}, H_{13b}); 4.58 (m, 4H, H_{8a}, H_{8b}, H_{10a}, H_{15a}); 4.75 (m, 2H, H_{10b}, H_{15b}); 5.26 (m, 2H, H₉, H₁₄); 7.13 (d, ³J_{H₅H₆} = 8.4 Hz, 1H, H₅); 7.55 (d, ⁴J_{H₂H₆} = 2.0 Hz, 1H, H₂); 7.62 (dd, ³J_{H₆H₅} = 8.4 Hz, ⁴J_{H₆H₂} = 2.0 Hz, 1H, H₆).

¹³C NMR (100.6 MHz, acetone-d₆, ppm) δ: 56.44 (s, C₁₂); 65.08 (s, C₈); 66.76 (s, C₁₀); 67.29 (s, C₁₅); 69.59 (s, C₁₃); 75.29 (s, C₉); 75.65 (s, C₁₄); 113.76 (s, C₅); 114.32 (s, C₂); 123.87 (s, C₁); 124.23 (s, C₆); 150.45 (s, C₃); 153.27 (s, C₄); 155.62 (s, C₁₁); 155.74 (s, C₁₆); 165.93 (s, C₇).

HRMS (m/z, ES⁺, [M+Na]⁺): Calculated: 391.0549; Found: 391.0549

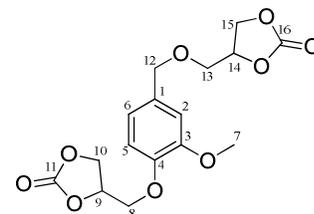

Product 10: 4-((2-methoxy-4-(((2-oxo-1,3-dioxolan-4-yl) methoxy) methyl)phenoxy)methyl)-1,3-dioxolan-2-one (100%, pale yellow liq.)


$^1\text{H NMR}$ (400.1 MHz, CDCl_3 , ppm) δ : 3.62 (dd, 1H, H_{13a}); 3.72 (dd, 1H, H_{13b}); 3.86 (s, 3H, H₇); 4.23 (dd, 2H, H₈); 4.40 (dd, 1H, H_{15a}); 4.60 (t, H_{15b}); 4.54 (s, 2H, H₁₂); 4.61 (d, 1H, H_{10a}); 4.63 (s, 1H, H_{10b}); 4.83 (m, 1H, H₁₄); 5.02 (m, 1H, H₉); 6.82 (dd, $^3J_{\text{H6H5}} = 8.0$ Hz, $^4J_{\text{H6H2}} = 1.2$ Hz, 1H, H₆); 6.90 (d, $^4J_{\text{H2H6}} = 1.2$ Hz, 1H, H₂); 6.91 (d, $^3J_{\text{H5H6}} = 8.0$ Hz, 1H, H₅).

$^{13}\text{C NMR}$ (100.6 MHz, CDCl_3 , ppm) δ : 55.84 (s, C₇); 66.15 (s, C₁₀); 66.19 (s, C₁₉); 68.67 (s, C₁₃); 69.22 (s, C₈); 73.17 (s, C₁₂); 74.48 (s, C₉); 75.05 (s, C₁₄); 111.78 (s, C₂); 116.13 (s, C₅); 120.14 (s, C₆); 132.27 (s, C₁); 147.10 (s, C₄); 150.36 (s, C₃); 154.76 (s, C₁₁); 154.98 (s, C₁₆).

HRMS (m/z, ES⁺, [M+Na⁺]): Calculated: 377.0854; Found: 377.0849.

Procedures for allylation (11, 12, 13)

A first protocol was used for the preparation of **11** and **12** from **2** and **3**. A two-necked round-bottomed flask was charged with **2** or **3** (1.0 eq.). Ethanol was added to obtain a 0.5 mol.L⁻¹ solution. The solution was cooled with an ice bath and K₂CO₃ (4.0 eq.) was added. After 10 minutes, allyl bromide (4.0 eq.) was added dropwise by a syringe. The solution was stirred for 30 minutes at 0°C and then at room temperature during seven days. Deionized water was added and the aqueous phase was extracted with pentane. The organic phase was washed with brine, dried on anhydrous Na₂SO₄ and pentane was removed on rotary evaporator. Further purification was achieved by silica gel flash chromatography using a pentane/dichloromethane gradient as eluent.




Product 11: 1,4-bis(allyloxy)-3-methoxybenzene (100%, pale yellow liq.)

$^1\text{H NMR}$ (400.1 MHz, acetone-d₆, ppm) δ : 3.80 (s, 3H, H₇); 4.48 (m, 4H, H₈, H₁₁); 5.20 (m, 2H, H_{10a}, H_{13a}); 5.38 (m, 2H, H_{10b}, H_{13b}); 6.05 (m, 2H, H₉, H₁₂); 6.42 (dd, $^3J_{\text{H6H5}} = 8.6$ Hz, $^4J_{\text{H6H2}} = 2.8$ Hz, 1H, H₆); 6.60 (d, $^4J_{\text{H2H6}} = 2.8$ Hz, 1H, H₂); 6.85 (d, $^3J_{\text{H5H6}} = 8.6$ Hz, 1H, H₅).

$^{13}\text{C NMR}$ (100.6 MHz, acetone-d₆, ppm) δ : 56.68 (s, C₇); 70.27 (s, C₁₁); 71.98 (s, C₈); 102.73 (s, C₂); 106.03 (s, C₆); 117.24 (s, C₅); 117.57 (s, C₁₀); 117.71 (s, C₁₃); 135.61 (s, C₁₂); 136.02 (s, C₉); 144.09 (s, C₄); 152.56 (s, C₃); 155.41 (s, C₁).

HRMS (m/z, ES⁺, [M+H⁺]): Calculated: 221.1178; Found: 221.1178.




Product 12: allyl 4-(allyloxy)-3-methoxybenzoate (100%, brown liq.)

$^1\text{H NMR}$ (400.1 MHz, CDCl_3 , ppm) δ : 3.93 (s, 3H, H₁₁); 4.68 (dt, 2H, H₁₂); 4.81 (dt, 2H, H₈); 5.30 (m, 2H, H_{10a}, H_{14a}); 5.42 (m, 2H, H_{10b}, H_{14b}); 6.06 (m, 2H, H₉, H₁₃); 6.89 (d, $^3J_{\text{H5H6}} = 8.4$ Hz, 1H, H₅); 7.58 (d, $^4J_{\text{H2H6}} = 2.0$ Hz, 1H, H₂); 7.68 (dd, $^3J_{\text{H6H5}} = 8.4$ Hz, $^4J_{\text{H6H2}} = 2.0$ Hz, 1H, H₆).

$^{13}\text{C NMR}$ (100.6 MHz, CDCl_3 , ppm) δ : 56.02 (s, C₁₁); 65.50 (s, C₈); 69.69 (s, C₁₂); 111.95 (s, C₂); 112.40 (s, C₅); 118.04 (s, C₁₀); 118.49 (s, C₁₄); 122.81 (s, C₁); 123.44 (s, C₆); 132.44 (s, C₉); 132.54 (s, C₁₃); 148.95 (s, C₃); 152.04 (s, C₄); 166.01 (s, C₇).

HRMS (m/z, ES⁺, [M+H⁺]): Calculated: 249.1126; Found: 249.1127.

As in the case of the glycidylation of a benzyl alcohol moiety, a phase transfer catalysis system was used for the preparation of **13** from **4**. A round-bottomed flask was charged with **4** (1.0 eq.) and TEBAC (0.1 eq.). NaOH (5.0 eq.) was dissolved in water to obtain a 20% wt. solution. This solution was poured into the flask and the suspension was stirred for 10 minutes while heating to 50°C. Allyl bromide (4.0 eq.) was then added to the mixture and the reaction was conducted for 5 hours. Deionized water was added and the mixture was extracted with pentane. The organic phase was washed with brine, dried on anhydrous Na₂SO₄ and pentane was removed on rotary evaporator. Further purification was achieved by silica gel flash chromatography using a pentane/dichloromethane gradient as eluent.



Product 13: 4-(allyloxy)-1-((allyloxy)methyl)-3-methoxybenzene (86%, pale yellow liq.)

$^1\text{H NMR}$ (400.1 MHz, acetone-d₆, ppm) δ : 3.81 (s, 3H, H₇); 3.98 (m, 2H, H₁₂); 4.43 (s, 2H, H₁₁); 4.55 (m, 2H, H₈); 5.11-5.16 (m, 1H, H_{14a}); 5.20-5.25 (m, 1H, H_{10a}); 5.25-5.32 (m, 1H, H_{14b}); 5.38-5.45 (m, 1H, H_{10b}); 5.94 (m, 1H, H₁₃); 6.08 (m, 1H, H₉); 6.84 (dd, $^4J_{\text{H6H2}} = 2.0$ Hz, $^3J_{\text{H6H5}} = 8.0$ Hz, 1H, H₆); 6.91 (dd, $^3J_{\text{H5H6}} = 8.0$ Hz, 1H, H₅); 6.96 (dd, $^3J_{\text{H2H6}} = 2.0$ Hz, 1H, H₂).


$^{13}\text{C NMR}$ (100.6 MHz, acetone-d₆, ppm) δ : 56.7 (s, C₇); 70.9 (s, C₈); 71.9 (s, C₁₂); 73.0 (s, C₁₁); 113.4 (s, C₂); 115.2 (s, C₅); 116.9 (s, C₁₄); 117.8 (s, C₁₀); 121.4 (s, C₆); 133.3 (s, C₁); 135.6 (s, C₉); 136.9 (s, C₁₃); 149.2 (s, C₄); 151.3 (s, C₃).

HRMS (m/z, ASAP⁻, [M-H⁻]): Calculated: 233.1180; Found: 233.1178.

Procedures for alcohol functionalization (14, 15, 16)

Allylated compound **11**, **12** or **13** (1.0 eq.) and mercaptoethanol (6.0 eq.) were mixed without adding any solvent. The solution

was irradiated in the UV reactor. The reactions were monitored by ^1H NMR.

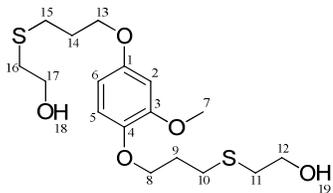


Product 14: 2,2'-((((3-methoxy-1,4-phenylene) bis(oxy)) bis(propane-3,1-diyl)) bis(sulfanediy)) diethanol (92%, pale yellow liq.)

^1H NMR (400.1 MHz, DMSO- d_6 , ppm) δ : 1.91 (m, 4H, H₉, H₁₄); 2.57 (dt, 4H, H₁₁, H₁₆); 2.65 (dt, 4H, H₁₀, H₁₅); 3.53 (dt, 4H, H₁₂, H₁₇); 3.74 (s, 3H, H₇); 3.93 (t, 2H, H₈); 3.97 (t, 2H, H₁₃); 4.76 (m, 2H, H₁₈, H₁₉); 6.40 (dd, $^3J_{\text{H6H5}} = 8.8$ Hz, $^4J_{\text{H6H2}} = 2.8$ Hz, 1H, H₆); 6.56 (d, $^4J_{\text{H2H6}} = 2.8$ Hz, 1H, H₂); 6.84 (d, $^3J_{\text{H5H6}} = 8.8$ Hz, 1H, H₅).

^{13}C NMR (100.6 MHz, DMSO- d_6 , ppm) δ : 27.95 (s, C₁₀, C₁₅); 29.12 (s, C₁₄); 29.29 (s, C₉); 33.90 (s, C₁₆, C₁₁); 55.54 (s, C₇); 60.86 (s, C₁₂, C₁₇); 66.33 (s, C₁₃); 67.86 (s, C₈); 101.02 (s, C₂); 104.28 (s, C₆); 115.03 (s, C₅); 142.10 (s, C₄); 150.26 (s, C₃); 153.41 (s, C₁).

HRMS (m/z, ES⁺, [M+Na⁺]): Calculated: 399.1277; Found: 399.1276.

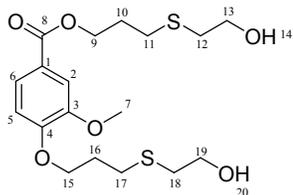


Product 15: 3-((2-hydroxyethyl)thio)propyl-4-((2-hydroxyethyl)thio)propoxy-3-methoxybenzoate (96%, pale yellow liq.)

^1H NMR (400.1 MHz, DMSO- d_6 , ppm) δ : 1.97 (m, 4H, H₁₀, H₁₆); 2.58 (2*t, 4H, H₁₂, H₁₈); 2.66 (2*t, 4H, H₁₁, H₁₇); 3.52 (m, 4H, H₁₃, H₁₉); 3.81 (s, 3H, H₇); 4.11 (t, 2H, H₁₅); 4.30 (t, 2H, H₉); 4.87 (broad m, 2H, H₁₄, H₂₀); 7.07 (d, $^3J_{\text{H5H6}} = 8.4$ Hz, 1H, H₅); 7.45 (d, $^4J_{\text{H2H6}} = 2.0$ Hz, 1H, H₂); 7.57 (dd, $^3J_{\text{H6H5}} = 8.4$ Hz, $^4J_{\text{H6H2}} = 2.0$ Hz, 1H, H₆).

^{13}C NMR (100.6 MHz, DMSO- d_6 , ppm) δ : 27.78, 27.97 (2*s, C₁₁, C₁₇); 28.85, 28.54 (2*s, C₁₀, C₁₆); 33.83, 33.89 (2*s, C₁₈, C₁₂); 55.59 (s, C₇); 60.82, 60.87 (2*s, C₁₃, C₁₉); 63.22 (s, C₈); 66.87 (s, C₁₅); 111.95, 112.10 (2*s, C₂, C₅); 121.97 (s, C₁); 123.14 (s, C₆); 148.54 (s, C₃); 152.20 (s, C₄); 165.47 (s, C₉).

HRMS (m/z, ES⁺, [M+K⁺]): Calculated: 443.0962; Found: 443.0964.

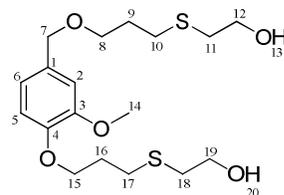

Product 16: 2-(((3-((4-(3-((2-hydroxyethyl)thio)propoxy)-3-methoxybenzyl)oxy)propyl)thio)ethan-1-ol (100%, pale yellow liq.)

^1H NMR (400.1 MHz, DMSO- d_6 , ppm) δ : 1.76 (m, 2H, H₉); 1.93 (m, 2H, H₁₆); 2.56 (m, 6H, H₁₀, H₁₁, H₁₈); 2.66 (t, 2H, H₁₇); 3.45 (t, 2H, H₈); 3.52 (m, 4H, H₁₂, H₁₉); 3.75 (s, 3H, H₁₄); 4.00 (t, 2H, H₁₅); 4.36 (s, 2H, H₇); 4.77 (m, 2H, H₁₃, H₂₀); 6.81 (dd, $^3J_{\text{H6H5}} = 8.0$ Hz, $^4J_{\text{H6H2}} = 1.2$ Hz, 1H, H₆); 6.90 (d, $^4J_{\text{H2H6}} = 1.2$ Hz, 1H, H₂); 6.91 (d, $^3J_{\text{H5H6}} = 8.0$ Hz, 1H, H₅).


^{13}C NMR (100.6 MHz, DMSO- d_6 , ppm) δ : 28.08 (s, C₁₇); 28.43 (s, C₁₀); 29.31 (s, C₁₆); 29.84 (s, C₉); 35.25 (s, C₁₈); 35.29 (s, C₁₁); 55.93 (s, C₁₄); 60.30 (s, C₁₉); 60.34 (s, C₁₂); 67.38 (s, C₁₅); 68.34 (s, C₈); 72.89 (s, C₇); 111.65 (s, C₅); 113.27 (s, C₂); 120.32 (s, C₆); 131.36 (s, C₁); 147.80 (s, C₃); 149.56 (s, C₄).

HRMS (m/z, ES⁺, [M+H⁺]): Calculated: 391.1611; Found: 391.1613.

Procedures for amine functionalization (17, 18, 19)

Allylated compound **11**, **12** or **13** (1.0 eq.) and cysteamine hydrochloride (6.0 eq.) were dissolved in a minimum of methanol. The solution was irradiated in the UV reactor. The reactions were monitored by ^1H NMR.

When the reaction was complete, the resulting mixture was dissolved in water and K₂CO₃ was added to reach pH = 9. The solution was then extracted with ethyl acetate, dried on anhydrous Na₂SO₄ and ethyl acetate was evaporated under reduced pressure.

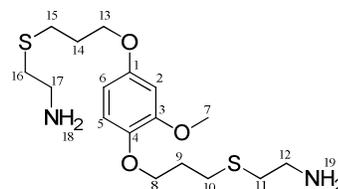


Product 17: 2,2'-((((3-methoxy-1,4-phenylene) bis(oxy)) bis(propane-3,1-diyl)) bis(sulfanediy)) diethanamine (96%, pale yellow liq.)

^1H NMR (400.1 MHz, DMSO- d_6 , ppm) δ : 1.90 (m, 4H, H₉, H₁₄); 2.45-2.70 (m, 12H, H₁₀, H₁₁, H₁₂, H₁₅, H₁₆, H₁₇); 3.72 (s, 3H, H₇); 3.94 (m, 4H, H₈, H₁₃); 6.39 (dd, $^3J_{\text{H6H5}} = 8.8$ Hz, $^4J_{\text{H6H2}} = 2.8$ Hz, 1H, H₆); 6.54 (d, $^4J_{\text{H2H6}} = 2.8$ Hz, 1H, H₂); 6.83 (d, $^3J_{\text{H5H6}} = 8.8$ Hz, 1H, H₅).

^{13}C NMR (100.6 MHz, DMSO- d_6 , ppm) δ : 27.50 (s, C₁₅); 27.52 (s, C₁₀); 29.14 (s, C₁₄); 29.30 (s, C₉); 35.23 (s, C₁₆); 35.25 (s, C₁₁); 41.55 (s, C₁₇); 41.57 (s, C₁₂); 55.56 (s, C₇); 66.34 (s, C₁₃); 67.85 (s, C₈); 101.00 (s, C₂); 104.26 (s, C₆); 114.98 (s, C₅); 142.12 (s, C₄); 150.27 (s, C₃); 153.42 (s, C₁).

HRMS (m/z , ES^+ , $[M+H]^+$): Calculated: 375.1779; Found: 375.1776.

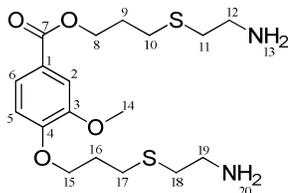


Product 18: 3-((2-aminoethylthio)propyl)-4-(3-((2-aminoethylthio)propoxy)-3-methoxybenzoate (93%, pale yellow liq.)

1H NMR (400.1 MHz, DMSO- d_6 , ppm) δ : 1.97 (m, 4H, H₉, H₁₆); 2.52 (2*t, 4H, H₁₁, H₁₈); 2.63 (2*t, 4H, H₁₀, H₁₇); 2.68 (t, 4H, H₁₂, H₁₉); 3.82 (s, 3H, H₁₄); 4.11 (t, 2H, H₁₅); 4.30 (t, 2H, H₈), 7.09 (d, $^3J_{H_5H_6}$ = 8.6 Hz, 1H, H₅); 7.45 (d, $^4J_{H_2H_6}$ = 2.0 Hz, 1H, H₂); 7.58 (dd, $^3J_{H_6H_5}$ = 8.6 Hz, $^4J_{H_6H_2}$ = 2.0 Hz, 1H, H₆).

^{13}C NMR (100.6 MHz, DMSO- d_6 , ppm) δ : 27.28 (s, C₁₀); 27.47 (s, C₁₇); 28.52 (s, C₉); 28.83 (s, C₁₆); 35.14, 35.16 (2*s, C₁₁, C₁₈); 41.52 (s, C₁₂, C₁₉); 55.59 (s, C₁₄); 63.19 (s, C₁₅); 66.87 (s, C₈); 111.94 (s, C₅); 112.09 (s, C₂); 121.95 (s, C₁); 123.13 (s, C₆); 148.55 (s, C₃); 152.20 (s, C₄); 165.44 (s, C₇).

HRMS (m/z , ES^+ , $[M+H]^+$): Calculated: 403.1721; Found: 403.1725.

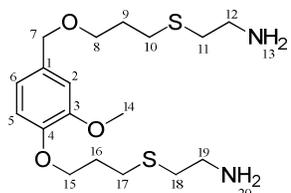

Product 19: 2-((3-((4-(3-((2-aminoethylthio)propoxy)-3-methoxybenzyl)oxy)propylthio)ethan-1-amine (88%, pale yellow liq.)


1H NMR (400.1 MHz, DMSO- d_6 , ppm) δ : 1.76 (tt, 2H, H₉); 1.94 (tt, 2H, H₁₆); 2.52 (m, 3H, H₁₀, H₁₁, H₁₈); 2.66 (m, 3H, H₁₂, H₁₇, H₁₉); 3.46 (t, 1H, H₈); 3.75 (s, 3H, H₁₄); 4.01 (t, 1H, H₁₅); 4.36 (s, 2H, H₇); 6.81 (dd, $^3J_{H_6H_5}$ = 8.0 Hz, $^4J_{H_6H_2}$ = 1.2 Hz, 1H, H₆); 6.90 (d, $^4J_{H_2H_6}$ = 1.2 Hz, 1H, H₂); 6.91 (d, $^3J_{H_5H_6}$ = 8.0 Hz, 1H, H₅).

^{13}C NMR (100.6 MHz, DMSO- d_6 , ppm) δ : 27.41 (s, C₁₇); 27.78 (s, C₁₀); 29.10 (s, C₁₆); 29.57 (s, C₉); 35.19 (s, C₁₈); 35.26 (s, C₁₁); 41.54 (s, C₁₂, C₁₉); 55.49 (s, C₁₄); 66.91 (s, C₁₅); 67.88 (s, C₈); 71.77 (s, C₇); 111.72 (s, C₅); 113.11 (s, C₂); 119.93 (s, C₆); 131.25 (s, C₁); 147.33 (s, C₄); 148.96 (s, C₃).

HRMS (m/z , ES^+ , $[M+H]^+$): Calculated: 389.1932; Found: 399.1933.

Procedures for acid functionalization (20, 21, 22)

Allylated compound **11**, **12** or **13** (1.0 eq.) and 3-mercaptopropionic acid (6.0 eq.) were mixed without adding any solvent. The solution was irradiated in the UV reactor. The reactions were monitored by 1H NMR.

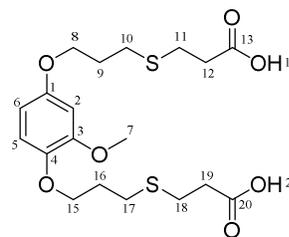


Product 20: 3,3'-(((3-methoxy-1,4-phenylene)bis(oxy))bis(propane-3,1-diyl))bis(sulfanediyl)dipropionic acid (68%, pale yellow liq.)

1H NMR (400.1 MHz, DMSO- d_6 , ppm) δ : 1.91 (q, 4H, H₉, H₁₆); 2.51 (m, 4H, H₁₃, H₂₀); 6.66 (m, 8H, H₁₀, H₁₁, H₁₇, H₁₈); 3.73 (s, 3H, H₇); 3.93 (t, 2H, H₈); 3.96 (t, 2H, H₁₅); 6.39 (dd, $^3J_{H_6H_5}$ = 8.8 Hz, $^4J_{H_6H_2}$ = 2.8 Hz, 1H, H₆); 6.56 (d, $^4J_{H_2H_6}$ = 2.8 Hz, 1H, H₂); 6.84 (d, $^3J_{H_5H_6}$ = 8.8 Hz, 1H, H₅); 12.28 (broad s, 2H, H₁₄, H₂₁).

^{13}C NMR (100.6 MHz, DMSO- d_6 , ppm) δ : 26.36, 26.39 (2*s, C₁₁, C₁₈); 27.59, 27.62 (2*s, C₁₀, C₁₇); 28.92, 29.08 (2*s, C₉, C₁₆); 34.45, 34.49 (2*s, C₁₂, C₁₉); 55.55 (s, C₇); 66.33 (s, C₈); 67.85 (s, C₁₅); 101.04 (s, C₂); 104.31 (s, C₆); 115.06 (s, C₅); 142.11 (s, C₄); 150.30 (s, C₃); 153.44 (s, C₁); 172.66 (s, C₁₃, C₂₀).

HRMS (m/z , ES^+ , $[M+H]^+$): Calculated: 433.1357; Found: 433.1355.

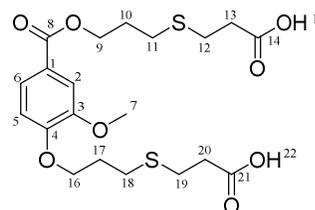


Product 21: 3-((3-((4-(3-((2-carboxyethylthio)propoxy)-3-methoxybenzyl)oxy)propylthio)propanoic acid (92%, m.p. 68°C)

1H NMR (400.1 MHz, DMSO- d_6 , ppm) δ : 1.97 (m, 4H, H₁₀, H₁₇); 2.51 (m, 4H, H₁₃, H₂₀); 2.67 (m, 8H, H₁₁, H₁₂, H₁₈, H₂₀); 3.81 (s, 3H, H₇); 4.10 (t, 2H, H₁₆); 4.29 (t, 2H, H₉), 7.06 (d, $^3J_{H_5H_6}$ = 8.6 Hz, 1H, H₅); 7.45 (d, $^4J_{H_2H_6}$ = 2.0 Hz, 1H, H₂); 7.58 (dd, $^3J_{H_6H_5}$ = 8.6 Hz, $^4J_{H_6H_2}$ = 2.0 Hz, 1H, H₆).

^{13}C NMR (100.6 MHz, DMSO- d_6 , ppm) δ : 26.31, 26.34 (2*s, C₁₂, C₁₉); 27.39, 27.63 (2*s, C₁₁, C₁₈); 28.34, 28.64 (2*s, C₁₀, C₁₇); 34.42, 34.46 (2*s, C₁₃, C₂₀); 55.60 (s, C₇); 63.22 (s, C₉); 63.8 (s, C₁₆); 111.94, 112.09 (2*s, C₅, C₂); 121.99 (s, C₁); 123.18 (s, C₆); 148.57 (s, C₃); 152.20 (s, C₄); 165.49 (s, C₇); 173.03 (s, C₁₄, C₂₁).

HRMS (m/z , ES^+ , $[M+H]^+$): Calculated: 461.1302; Found: 461.1304.

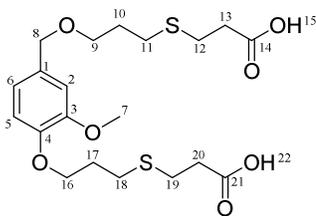

Product 22: 3-((3-((4-(3-((2-carboxyethyl)thio)propoxy)-3-methoxybenzyl)oxy)propyl)thio)propanoic acid (90%, liq.)

$^1\text{H NMR}$ (400.1 MHz, DMSO- d_6 , ppm) δ : 1.76 (quint., 2H, H_{10}); 1.93 (quint., 2H, H_{17}); 2.51 (m, 6H, H_{11} , H_{13} , H_{20}); 2.66 (m, 6H, H_{12} , H_{18} , H_{19}); 3.45 (t, 2H, H_9); 3.75 (s, 3H, H_7); 4.00 (t, 2H, H_{16}); 4.36 (s, 2H, H_8); 6.81 (dd, $^3J_{\text{H}_6\text{H}_5} = 8.0$ Hz, $^4J_{\text{H}_6\text{H}_2} = 2.0$ Hz, 1H, H_6); 6.90 (d, $^4J_{\text{H}_2\text{H}_6} = 2.0$ Hz, 1H, H_2); 6.91 (d, $^3J_{\text{H}_5\text{H}_6} = 8.0$ Hz, 1H, H_5).

$^{13}\text{C NMR}$ (100.6 MHz, DMSO- d_6 , ppm) δ : 26.32, 26.42 (2*s, C_{12} , C_{19}); 27.52, 27.91 (2*s, C_{11} , C_{18}); 28.91, 29.39 (2*s, C_{10} , C_{17}); 34.46, 34.51 (s, C_{13} , C_{20}); 55.49 (s, C_7); 66.87 (s, C_{16}); 67.88 (s, C_9); 71.82 (s, C_8); 111.67 (s, C_2); 113.04 (s, C_5); 119.99 (s, C_6); 131.25 (s, C_1); 147.32 (s, C_3); 148.96 (s, C_4); 173.09 (s, C_{14} , C_{21}).

HRMS (m/z, ES $^+$, [M+H $^+$]): Calculated: 447.1505; Found: 447.1511.

Material preparation

Epoxy compound **5** (1.20 g, 2.0 eq.) was molten at 100°C. IPDA (0.81 g, 1.0 eq) was quickly added and the mixture was vigorously stirred for 1 min. at 100°C. The liquid and homogeneous mixture was then poured in a rectangular silicon mold. The formulation was cured in an oven for 1.5 hours at 100°C. The polymer obtained was then cooled down to room temperature and post-cured at 160°C for 1 hour. A DSC analysis was performed and showed a complete reticulation and a Tg of 117°C.

Conclusions

Vanillin was used as a building-block to develop a platform of biobased compounds usable in the polymer field. The lack of biobased aromatic monomers, necessary to reach good thermo-mechanical properties was the major identified challenge. Vanillin was chosen as the starting point of the platform as it is one of the few monoaromatic biobased compounds that are abundantly available. Indeed, vanillin is already industrially produced by lignin depolymerization.

Three vanillin derivatives in different oxidation states were chosen as starting materials to take into account differences in lignin depolymerization processes and the possible resulting products. These chemicals were functionalized with epoxy, cyclic carbonates, allyl, amine, alcohol and carboxylic acid moieties. Original biobased monomers useful for epoxy, polyester, PU, and NIPU polymer synthesis were obtained. The epoxy-functionalized compounds could be tested as biobased substitutes for Bisphenol A-based epoxy resins. The amine-functionalized compounds are to our knowledge the first non-aliphatic biobased amine hardeners, useful either in epoxy or

NIPU materials. The cyclic carbonates-functionalized compounds could be useful to tune NIPU properties.

Products from the vanillin-derived methoxyhydroquinone are especially interesting and versatile. The industrialization is possible thanks to clean and straightforward syntheses and there is no fragile bond on the methoxyhydroquinone that could impact polymer properties.

In future works, compounds from this platform should be used in polymer formulations and thermo-mechanical properties of the corresponding materials should be tested.

Notes and references

^a Institut Charles Gerhardt, UMR CNRS 5253, Equipe Ingénierie et Architectures Macromoléculaires, ENSCM, 8 rue de l'Ecole Normale, 34296 Montpellier, France

^b COLAS S.A., 7 place René Clair, 92653 Boulogne-Billancourt, France

* E-mail : sylvain.caillol@enscm.fr

1. A. Gandini, *Green Chemistry*, 2011, **13**, 1061.
2. C. O. Tuck, E. Perez, I. T. Horvath, R. A. Sheldon and M. Poliakov, *Science*, 2012, **337**, 695-699.
3. L. Montero de Espinosa and M. A. R. Meier, *European Polymer Journal*, 2011, **47**, 837-852.
4. J. M. Raquez, M. Deléglise, M. F. Lacrampe and P. Krawczak, *Progress in Polymer Science*, 2010, **35**, 487-509.
5. , Bisphenol A MSDS.
6. V. S. Balachandran, S. R. Jadhav, P. K. Vemula and G. John, *Chemical Society reviews*, 2013, **42**, 427-438.
7. H. Nouailhas, C. Aouf, C. Le Guernevé, S. Caillol, B. Boutevin and H. Fulcrand, *Journal of Polymer Science Part A: Polymer Chemistry*, 2011, **49**, 2261-2270.
8. C. Aouf, H. Nouailhas, M. Fache, S. Caillol, B. Boutevin and H. Fulcrand, *European Polymer Journal*, 2013, **49**, 1185-1195.
9. C. Brazinha, D. S. Barbosa and J. G. Crespo, *Green Chemistry*, 2011, **13**, 2197.
10. M. Carrier, A. Loppinet-Serani, D. Denux, J.-M. Lasnier, F. Ham-Pichavant, F. Cansell and C. Aymonier, *Biomass and Bioenergy*, 2011, **35**, 298-307.
11. H. Lange, S. Decina and C. Crestini, *European Polymer Journal*, 2013, **49**, 1151-1173.
12. E. A. Borges da Silva, M. Zabkova, J. D. Araújo, C. A. Cateto, M. F. Barreiro, M. N. Belgacem and A. E. Rodrigues, *Chemical Engineering Research and Design*, 2009, **87**, 1276-1292.
13. Z. Wong, K. Chen and J. Li, *BioResources*, 2010, **5**, 1509-1516.
14. J. D. P. Araújo, C. A. Grande and A. E. Rodrigues, *Chemical Engineering Research and Design*, 2010, **88**, 1024-1032.
15. H.-R. M. Björsvik, Francesco, *Organic Process Research & Development*, 1999, **3**, 330-340.
16. M. B. Hocking, *Journal of Chemical Education*, 1997, **74**, 1055-1059.
17. A. S. Amarasekara, B. Wiredu and A. Razzaq, *Green Chemistry*, 2012, **14**, 2395.
18. A. S. Amarasekara and A. Razzaq, *ISRN Polymer Science*, 2012, **2012**, 1-5.
19. A. M. Issam and M. H. Rashidah, *Molecules*, 2012, **17**, 645-656.

20. C. Aouf, J. Lecomte, P. Villeneuve, E. Dubreucq and H. Fulcrand, *Green Chemistry*, 2012, **14**, 2328.
21. T. Koike, *Polymer Engineering & Science*, 2012, **52**, 701-717.
22. M. Firdaus and M. A. R. Meier, *European Polymer Journal*, 2013, **49**, 156-166.
23. L. Mialon, A. G. Pemba and S. A. Miller, *Green Chemistry*, 2010, **12**, 1704.
24. L. Mialon, R. Vanderhenst, A. G. Pemba and S. A. Miller, *Macromolecular rapid communications*, 2011.
25. V. Srinivasa Rao and A. B. Samui, *Journal of Polymer Science Part A: Polymer Chemistry*, 2008, **46**, 7637-7655.
26. V. Srinivasa Rao and A. B. Samui, *Journal of Polymer Science Part A: Polymer Chemistry*, 2009, **47**, 2143-2155.
27. N. K. Sini, J. Bijwe and I. K. Varma, *Journal of Polymer Science Part A: Polymer Chemistry*, 2014, **52**, 7-11.
28. E. Renbutsu, M. Hirose, Y. Omura, F. Nakatsubo, Y. Okamura, Y. Okamoto, H. Saimoto, Y. Shigemasa and S. Minami, *Biomacromolecules*, 2005, **6**, 2385-2388.
29. J. F. Stanzione III, J. M. Sadler, J. J. La Scala, K. H. Reno and R. P. Wool, *Green Chemistry*, 2012, **14**, 2346.
30. T. Shimasaki, S. Yoshihara and M. Shibata, *Polymer Composites*, 2012, **33**, 1840-1847.
31. P. Azadi, O. R. Inderwildi, R. Farnood and D. A. King, *Renewable and Sustainable Energy Reviews*, 2013, **21**, 506-523.
32. G. W. Kabalka, N. K. Reddy and C. Narayana, *Tetrahedron Letters*, 1992, **33**, 865-866.
33. C. Aouf, C. Le Guernevé, S. Caillol and H. Fulcrand, *Tetrahedron*, 2013, **69**, 1345-1353.
34. J. K. Cho, J.-S. Lee, J. Jeong, B. Kim, B. Kim, S. Kim, S. Shin, H.-J. Kim and S.-H. Lee, *Journal of Adhesion Science and Technology*, 2012, **27**, 2127-2138.
35. V. Besse, G. Foyer, R. Auvergne, S. Caillol and B. Boutevin, *Journal of Polymer Science Part A: Polymer Chemistry*, 2013, **51**, 3284-3296.
36. O. Türünç and M. A. R. Meier, *European Journal of Lipid Science and Technology*, 2013, **115**, 41-54.
37. B. Boutevin, R. Auvergne and G. David, in *Thiol-X Chemistries in Polymer and Materials Science*, The Royal Society of Chemistry, Editon edn., 2013, pp. 217-235.
38. F. Jaillet, M. Desroches, R. Auvergne, B. Boutevin and S. Caillol, *European Journal of Lipid Science and Technology*, 2013, **115**, 698-708.
39. F. Jaillet, E. Darroman, A. Ratsimihety, R. Auvergne, B. Boutevin and S. Caillol, *European Journal of Lipid Science and Technology*, 2014, **116**, 63-73.