


ChemComm

Accepted Manuscript



This is an *Accepted Manuscript*, which has been through the Royal Society of Chemistry peer review process and has been accepted for publication.

Accepted Manuscripts are published online shortly after acceptance, before technical editing, formatting and proof reading. Using this free service, authors can make their results available to the community, in citable form, before we publish the edited article. We will replace this *Accepted Manuscript* with the edited and formatted *Advance Article* as soon as it is available.

You can find more information about *Accepted Manuscripts* in the [Information for Authors](#).

Please note that technical editing may introduce minor changes to the text and/or graphics, which may alter content. The journal's standard [Terms & Conditions](#) and the [Ethical guidelines](#) still apply. In no event shall the Royal Society of Chemistry be held responsible for any errors or omissions in this *Accepted Manuscript* or any consequences arising from the use of any information it contains.

COMMUNICATION

Nanopapers for Organic Solvent Nanofiltration

Cite this: DOI: 10.1039/x0xx00000x

A. Mautner,^a K.-Y. Lee,^{b,c} P. Lahtinen,^d T. Tammelin,^d K. Li^e and A. Bismarck^{a,c,*}Received 00th January 2014,
Accepted 00th January 2014

DOI: 10.1039/x0xx00000x

www.rsc.org/

Would it not be nice to have an organic solvent nanofiltration membrane made from renewable resources that can be manufactured as simple as producing paper? Here the production of nanofiltration membranes made from nanocellulose by applying a papermaking process is demonstrated. Manufacture of the nanopapers was enabled by inducing flocculation of nanofibrils upon addition of trivalent ions.

Organic solvent nanofiltration (OSN) has found both widespread scientific and industrial interest since its emergence at the beginning of this century.¹ OSN describes the process of separating molecules or particles with a molecular weight (M_w) of some hundreds to thousands Da – i.e. particles or molecules with nanometer dimensions – from an organic solvent.¹⁻² Applications such as product purification and concentration, solvent exchange and recycling as well as recovery of homogenous catalysts have been reported and compare favorably to classical methods, such as distillation, due to the lower energy consumption and milder conditions chemical compounds experience during separation.² However, the utilization of organic solvents in NF operations still provides a significant challenge for the membranes from the materials point of view, in particular due to the required solvent-stability, which many traditional polymer membranes lack.³ Several different engineering and high performance polymers have been tested for OSN membranes.³⁻⁵ Typically polymer membranes do require a mechanical support, which is often made of polyamide, polysulfone or polyimide.⁶ Besides polymer membranes, ceramics⁷ or organic-inorganic hybrid materials⁸ have been explored. Unfortunately, all these materials suffer from drawbacks; the production processes involve the use of large quantities of solvents and chemicals as well as extensive energy usage in the case of ceramics.⁹ Thus, simple, clean and fast

production processes would be desirable to manufacture solvent stable nanofiltration membranes.

In general, both everyday life and laboratory operations depend on filtering processes that are performed with membranes or cellulose filters. However, there are certain limitations when it comes to the removal of small M_w compounds using filter papers. In recent years, nanofibrillated cellulose (NFC) has gained significant attention due to its outstanding mechanical and chemical properties,¹⁰ especially when used in composites.¹¹ NFC, when used in paper form, also known as nanopaper, possesses outstanding mechanical properties, low thermal expansion coefficients, high optical transparency and good gas barrier properties.¹²⁻¹⁵ These barrier properties have been exploited in food packaging films.¹⁶ Nanopapers might offer potential for separation applications due to the inherent pore dimensions in the nm range.¹³ For example, NFC paper was explored as separator in Li-ion batteries.¹⁷

Here we introduce solvent stable nanofiltration (NF) membranes entirely made from nanocellulose. These membranes are produced using a papermaking process utilizing an aqueous suspension of nanocellulose thus avoiding vast amounts of organic solvents that are usually necessary for the production of conventional OSN polymer membranes.⁵ Manufacture of these nanopapers is enabled by inducing flocculation of nanofibrils upon addition of multivalent ions. This type of nanocellulose membranes represents a step forward within this important domain and demonstrates the utilization of a well-known material for an advanced application.

We discuss the use of nanopapers made entirely from (2,2,6,6-tetramethylpiperidin-1-yl)oxy (TEMPO) oxidized NFC (herein

termed NFC-O) with fibre diameters ranging from 5 to 30 nm (UPM-Kymmene Oyj, Helsinki, Finland) for NF membranes. The production method of NFC-O is described in detail elsewhere.¹⁸ It can be anticipated that these nanofibrils can be densely compacted to form a framework structure with pore-dimensions in the range of the diameter of the nanofibrils. This concept has been mathematically proven by Zhang.¹⁹ To demonstrate the possibility of controlling the pore size and thus the molecular weight cut-off (*MWCO*) and permeance of the nanocellulose membranes, we also used another NFC grade produced by mechanical grinding (MKZA10-15J Supermasscolloider, Masuko Sangyo Co., Kawaguchi, Japan) of never-dried bleached kraft birch pulp as described in Lee et al.¹⁴ Herein, we call these fibrils NFC-K, which possess fibre diameters of 50 to 100 nm (more details about the NFC grades can be found in the SI).

In general, for the production of paper, cellulose fibres are suspended in water. This suspension is filtered, the resulting filter cake, i.e. the fibre mat, pressed and water removed until the desired quality is achieved. As for usual paper, the production of nanopapers started from an NFC in water suspension with a consistency of 0.3 wt%. This suspension was produced by blending (Breville VBL065-01, Oldham, UK) of NFC feedstock for 2 min, which had an original consistency of 2.5 wt% and 1.8 wt%, respectively, for NFC-O and NFC-K. Nanopapers with the desired grammage were produced by vacuum-filtration of NFC suspensions containing a pre-determined amount of nanocellulose onto cellulose filter papers (VWR 413, 5-13 μm pore size, Lutterworth, UK). However, we observed that NFC-O passed through both the filter paper and the supporting glass frit (Schott, porosity No. 1, Mainz, Germany) due to the extremely small size of NFC-O. This effect was not observed for the filtration of the larger diameter NFC-K fibrils, which was consistent with our previous observations.¹⁴ In order to facilitate the filtration of NFC-O, flocculation of the fibrils by changing the surface charge was required. Thus, we measured the ζ -potential of NFC as function of pH in a 1 mM KCl electrolyte using electrophoresis (Brookhaven ZetaPALS analyzer, Holtsville, USA). It can be inferred from the $\zeta = f(\text{pH})$ curve that it is impossible to induce flocculation of NFC-O by changing the pH of the NFC-O suspension, since the isoelectric point (iep), where $\zeta = 0$, at which significant flocculation would occur, is very low (Fig. 1, left). To reach the iep, a pH of 1.5 (extrapolated) would be required, which could possibly result in acid hydrolysis of NFC.²⁰

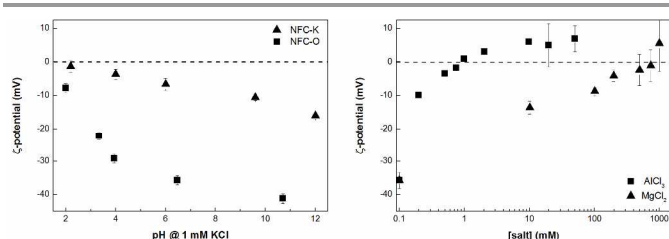


Fig. 1. ζ -potential of NFC-O and -K in 1 mM KCl aqueous solution as function of pH (left) and of NFC-O as function of MgCl_2 and AlCl_3 concentration (right).

The ζ -potential as measure of surface charge is dependent on the ionic strength, which is most effectively increased by addition of multivalent ions. Therefore, we measured ζ as function of salt (MgCl_2 and AlCl_3) concentration, from which the point of zero charge (pzc) was determined (Figure 1, right). At the pzc, the NFC-O fibrils have zero net surface charge and, therefore, no electrostatic repulsion exists between NFC-O fibrils, which causes the whole NFC-O suspension to form a single gel. Multivalent cations will specifically adsorb on negatively charged NFC-O surfaces causing the ζ -potential to decrease by effectively reducing the Debye-length. Ultimately, the pzc was reached upon adjusting the electrolyte concentration to 800 mM for MgCl_2 and 1 mM for AlCl_3 , respectively (Figure 1, right), because the ionic strength of the electrolyte increases exponentially with increasing charge of the cations. To produce NFC-O filter cakes, AlCl_3 was added to achieve a concentration of 1 mM.

Wet NFC-O and -K filter cakes of 125 mm in diameter were pressed between blotting papers (Whatman 3MM Chr, Kent, UK) for 5 min under a weight of 10 kg to increase the NFC solid content to 15 wt%. These filter cakes were then sandwiched between blotting papers and metal plates for further hot pressing at 120 $^\circ\text{C}$ for 1 h under a weight of 1 t to dry and consolidate the filter cakes. The hot pressing also prevents the shrinkage of nanopapers and increases the density of the sheets, resulting in better mechanical properties of the papers.¹⁵ Nanopapers with grammages between 10 and 70 g m^{-2} (gsm) were produced from both types of nanocellulose. The thickness of these nanopapers was found to increase linearly with its grammage (see Fig. S1). The nanopapers produced were used as membrane directly.

Exemplarily, the permeance (P) of tetrahydrofuran (THF), n-hexane and water through the nanopapers was measured in a dead end cell (Sterlitech HP 4750, Kent, USA). The solvent was forced through the nanopapers at 20 $^\circ\text{C}$ by nitrogen at a head pressure of 0.2 MPa and 1 MPa for nanopapers with grammages < 20 gsm and > 20 gsm, respectively. The amount of solvent that passed through the nanopaper for a given time interval was measured gravimetrically and used to determine P [$\text{L m}^{-2} \text{h}^{-1} \text{MPa}^{-1}$]. For these measurements, discs of 49 mm in diameter were cut from the nanopapers and placed in the dead end cell on a ceramic support. In the beginning of the measurement, P decreased significantly (see Fig. S2) caused by membrane compaction due to the applied pressure.²¹

The permeance of different solvents is exemplarily shown for NFC-O nanopapers in Fig. 2 (a). These measurements showed that P of the tested solvents through nanopapers increases in the following order: water < THF < n-hexane. Thus, irrespective of the hydrophilic nature of nanocellulose and the hydrophobicity of some of the solvents, P increases inversely with increasing hydrophobicity of the solvent. It should be noted that the calculation of P does not take into account the viscosity of the solvent.

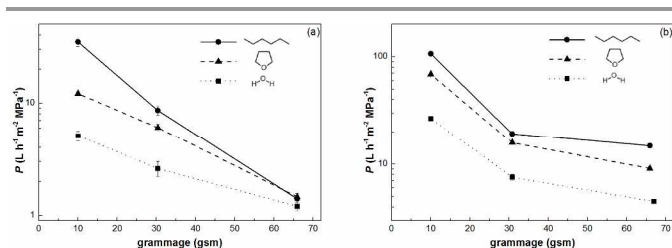


Fig. 2. Permeance P of different solvents for NFC-O (a) and NFC-K (b) nanopapers for different grammages.

In addition to this, we also observed that P is dependent on the grammage and, thus the thickness, of the nanopapers as well as the diameter of the fibrils (Fig. 2). Using nanofibrils with larger diameters (NFC-K) for membrane fabrication resulted in nanopapers with larger pore dimensions as compared to NFC-O, which, in conjunction with varying the grammage of the nanopapers, allows the permeance to be controlled over a wide range. Varying the aspect ratio of randomly packed high aspect ratio cylinders hardly affects the porosity of a mat.²² Since the number of fibrils per unit mass within the same volume element is higher for smaller fibrils, this results in a larger number of pores, which are smaller in diameter due to the constant porosity (around 35 %).

The nanofiltration membrane performance is generally quantified by the $MWCO$, which was determined by passing solutions of polymer standards with known concentration through the nanopapers. The amount of rejected polymer molecules was quantified using gel permeation chromatography (GPC, aqueous: Viscotek GPCmax VE2001, VE3580 RI detector, Malvern, UK; organic: Waters 515 HPLC pump, Waters 2410 RI detector, Milford, USA). The $MWCO$ is defined as the molecular weight of a molecule, which is rejected by 90 %.²³ Poly(ethylene glycol) (PEG) dissolved in deionized water and polystyrene (PS) standards dissolved in THF with molecular weights ranging from 1 to 13 kDa were used to determine the $MWCO$ for NFC-O nanopapers with a grammage of 65 gsm. The retention of PEG and PS standards as a function of the M_w is shown in Fig. 3 (a).

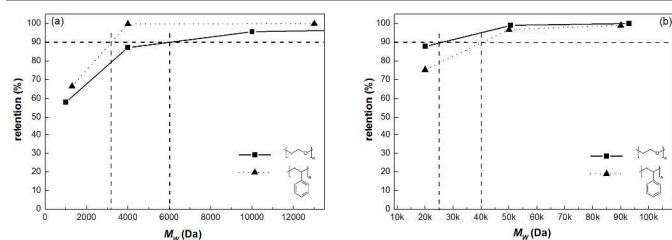


Fig. 3. Retention of PS & PEG = $f(M_w)$ for NFC-O (a) and NFC-K (b) nanopapers: $MWCO$ is the molecular weight of which 90 % is rejected.

For PS and PEG, the $MWCO$ were found to be 3.2 kDa and 6 kDa, corresponding to a hydrodynamic radius of 1.6 nm^{24} and 2.4 nm^{25} , respectively, which does represent the pore size. Thus, our nanopaper membranes have a $MWCO$ on the upper end of the NF range. In the case of NFC-K papers (Fig. 3 (b)), the $MWCO$ of PEG was 25 kDa, which corresponds to a hydrodynamic

radius of 5 nm^{25} and 40 kDa equivalent to a hydrodynamic radius of 5.5 nm^{24} for PS, respectively. This demonstrated that by using differently sized cellulose nanofibrils, around 50 nm for NFC-K and down to 2 nm for NFC-O, it is possible to adjust the pore dimensions of the resulting nanopapers, which is due to a reduced pore size in the random packing of cylinders with smaller diameter.

To summarize, we produced nanocellulose based nanofiltration membranes by simply using a papermaking process. These nanopapers are suitable for NF of organic solvents and water. It was observed that the permeance of nanopapers was dependent on the hydrophilicity of the solvents and that P was governed by the grammage of the nanopapers and the dimensions of the nanofibrils. We also observed that the $MWCO$ was determined by the diameter of the nanofibrils, which affects the pore dimensions of the nanopapers. It is thus possible to tailor the membrane performance over a wide range of applications by selecting nanofibrils with different diameters. In conclusion, we can prepare, as simple as making paper, solvent-stable OSN membranes from renewable resources. If it eventually becomes possible to produce NFC with fibrils of evenly distributed lengths, potentially even thinner active membrane layers with smaller $MWCO$ could be created, which would drastically improve the performance of these types of NF membranes.

The authors greatly acknowledge the funding provided by EU FP7 project NanoSelect (Grant No. 280519) and University of Vienna for funding KYL. We thank Maria Schachner and Dr. Ivan Zadrzil for performing the GPC-measurements.

Notes and references

^a Department of Chemical Engineering, Polymer & Composite Engineering (PaCE) Group, Imperial College London, South Kensington Campus, SW7 2AZ London, UK, E-mail: a.bismarck@imperial.ac.uk; Fax: +44 20759 45638; Tel: +44 20759 45578.

^b Department of Chemical Engineering, University College London, Torrington Place, WC1E 7JE London, UK.

^c Polymer & Composite Engineering (PaCE) group, Institute for Materials Chemistry and Research, Faculty of Chemistry, University of Vienna, Währingerstraße 42, A-1090 Vienna, Austria.

^d VTT Technical Research Centre of Finland, Biologinkuja 7, FL-02044 Espoo, Finland.

^e Department of Chemical Engineering, Imperial College London, South Kensington Campus, SW7 2AZ London, UK.

† Electronic Supplementary Information (ESI) available: Further characterisation of the membranes and membrane compaction. See DOI: 10.1039/c000000x/

1. P. Vandezande, L. E. M. Gevers and I. F. J. Vankelecom, *Chem. Soc. Rev.*, 2008, **37**, 365-405.
2. R. Othman, A. W. Mohammad, M. Ismail and J. Salimon, *J. Membr. Sci.*, 2010, **348**, 287-297; A. G. Livingston, L. Peeva, S. Han, D. Nair, S. S. Luthra, L. S. White and L. M. Freitas Dos Santos, *Ann. N.Y. Acad. Sci.*, 2003, **984**, 123-141; D. Peshev, L. G. Peeva, G. Peev, I. I. R. Baptista and A. T. Boam, *Chem.*

- Eng. Res. Des.*, 2011, **89**, 318-327; M. Priske, K.-D. Wiese, A. Drews, M. Kraume and G. Baumgarten, *J. Membr. Sci.*, 2010, **360**, 77-83; A. Cano-Odena, P. Vandezande, D. Fournier, W. Van Camp, F. E. Du Prez and I. F. J. Vankelecom, *Chem. Eur. J.*, 2010, **16**, 1061-1067; J. C.-T. Lin and A. G. Livingston, *Chem. Eng. Sci.*, 2007, **62**, 2728-2736; L. S. White and C. R. Wildemuth, *Ind. Eng. Chem. Res.*, 2006, **45**, 9136-9143.
- M. Sairam, X. X. Loh, K. Li, A. Bismarck, J. H. G. Steinke and A. G. Livingston, *J. Membr. Sci.*, 2009, **330**, 166-174.
 - X. Li, P. Vandezande and I. F. J. Vankelecom, *J. Membr. Sci.*, 2008, **320**, 143-150; X. X. Loh, M. Sairam, J. H. G. Steinke, A. G. Livingston, A. Bismarck and L. Kang, *Chem. Comm.*, 2008, 6324-6326; M. Peyravi, A. Rahimpour and M. Jahanshahi, *J. Membr. Sci.*, 2012, **423-424**, 225-237; H. Siddique, L. G. Peeva, K. Stoikos, G. Pasparakis, M. Vamvakaki and A. G. Livingston, *Ind. Eng. Chem. Res.*, 2013, **52**, 1109-1121; S. Zeidler, U. Kätzel and P. Kreis, *J. Membr. Sci.*, 2013, **429**, 295-303.
 - I. Soroko, Y. Bhole and A. G. Livingston, *Green Chem.*, 2011, **13**, 162-168.
 - M. F. Jimenez-Solomon, P. Gorgojo, M. Munoz-Ibanez and A. G. Livingston, *J. Membr. Sci.*, 2013, **448**, 102-113; M. F. Jimenez Solomon, Y. Bhole and A. G. Livingston, *J. Membr. Sci.*, 2012, **423-424**, 371-382.
 - A. Buekenhoudt, F. Bisignano, G. De Luca, P. Vandezande, M. Wouters and K. Verhulst, *J. Membr. Sci.*, 2013, **439**, 36-47; P. Marchetti, A. Butté and A. G. Livingston, *J. Membr. Sci.*, 2012, **415-416**, 444-458.
 - F. Peng, L. Lu, H. Sun, Y. Wang, J. Liu and Z. Jiang, *Chem. Mat.*, 2005, **17**, 6790-6796; T. C. Merkel, B. D. Freeman, R. J. Spontak, Z. He, I. Pinnau, P. Meakin and A. J. Hill, *Science*, 2002, **296**, 519-522.
 - K. Li, *Ceramic Membranes for Separation and Reaction*, John Wiley & Sons, Ltd., Chichester, UK, 2007.
 - P. Chen, S. Y. Cho and H.-J. Jin, *Macromol. Res.*, 2010, **18**, 309-320; D. Klemm, F. Kramer, S. Moritz, T. Lindstroem, M. Ankerfors, D. Gray and A. Dorris, *Angew. Chem., Int. Ed.*, 2011, **50**, 5438-5466.
 - J. J. Blaker, K.-Y. Lee and A. Bismarck, *J. Biobased Mater. Bioenergy*, 2011, **5**, 1-16; S. J. Eichhorn, A. Dufresne, M. Aranguren, N. E. Marcovich, J. R. Capadona, S. J. Rowan, C. Weder, W. Thielemans, M. Toman, S. Renneckar, W. Gindl, S. Veigel, J. Keckes, H. Yano, K. Abe, M. Nogi, A. N. Nakagaito, A. Mangalam, J. Simonsen, A. S. Benight, A. Bismarck, L. A. Berglund and T. Peijs, *J. Mater. Sci.*, 2010, **45**, 1-33.
 - S.-J. Chun, S.-Y. Lee, G.-H. Doh, S. Lee and J. H. Kim, *J. Ind. Eng. Chem.*, 2011, **17**, 521-526; A. Dufresne, *Nanocellulose: From Nature to High Performance Tailored Materials*, Walter de Gruyter & Co, Berlin/Boston, 2012; J. Gutierrez, S. C. M. Fernandes, I. Mondragon and A. Tercjak, *ChemSusChem*, 2012, **5**, 2323-2327; L. Hu, G. Zheng, J. Yao, N. Liu, B. Weil, M. Eskilsson, E. Karabulut, Z. Ruan, S. Fan, J. T. Bloking, M. D. McGehee, L. Wagberg and Y. Cui, *Energy Environ. Sci.*, 2013, **6**, 513-518; J. Huang, H. Zhu, Y. Chen, C. Preston, K. Rohrbach, J. Cumings and L. Hu, *ACS Nano*, 2013, **7**, 2106-2113.
 - M. Henriksson, L. A. Berglund, P. Isaksson, T. Lindstroem and T. Nishino, *Biomacromolecules*, 2008, **9**, 1579-1585.
 - K.-Y. Lee, T. Tammelin, K. Schultfer, H. Kiiskinen, J. Samela and A. Bismarck, *ACS Appl. Mater. Interfaces*, 2012, **4**, 4078-4086.
 - M. Österberg, J. Vartiainen, J. Lucenius, U. Hippi, J. Seppälä, R. Serimaa and J. Laine, *ACS Appl. Mater. Interfaces*, 2013, **5**, 4640-4647.
 - A. Khan, T. Huq, R. A. Khan, B. Riedl and M. Lacroix, *Cr. Rev. Food Sci.*, 2012, **54**, 163-174.
 - S.-J. Chun, E.-S. Choi, E.-H. Lee, J. H. Kim, S.-Y. Lee and S.-Y. Lee, *J. Mater. Chem.*, 2012, **22**, 16618-16626.
 - WO Pat.*, WO 2012/168562 A1, 2012.
 - W. Zhang, PhD Thesis, Louisiana State University, 2006.
 - J. F. Saeman, *Ind. Eng. Chem.*, 1945, **37**, 43-52.
 - E. Gibbins, M. D'Antonio, D. Nair, L. S. White, L. M. Freitas dos Santos, I. F. J. Vankelecom and A. G. Livingston, *Desalination*, 2002, **147**, 307-313.
 - M. Novellani, R. Santini and L. Tadrist, *Eur. Phys. J. B*, 2000, **13**, 571-578.
 - Y. H. See Toh, X. X. Loh, K. Li, A. Bismarck and A. G. Livingston, *J. Membr. Sci.*, 2007, **291**, 120-125.
 - E. Uliyanchenko, P. J. Schoenmakers and S. van der Wal, *J. Chromatogr. A*, 2011, **1218**, 1509-1518.
 - J. K. Armstrong, R. B. Wenby, H. J. Meiselman and T. C. Fisher, *Biophys. J.*, 2004, **87**, 4259-4270.