

# ChemComm

Accepted Manuscript



This is an *Accepted Manuscript*, which has been through the Royal Society of Chemistry peer review process and has been accepted for publication.

*Accepted Manuscripts* are published online shortly after acceptance, before technical editing, formatting and proof reading. Using this free service, authors can make their results available to the community, in citable form, before we publish the edited article. We will replace this *Accepted Manuscript* with the edited and formatted *Advance Article* as soon as it is available.

You can find more information about *Accepted Manuscripts* in the [Information for Authors](#).

Please note that technical editing may introduce minor changes to the text and/or graphics, which may alter content. The journal's standard [Terms & Conditions](#) and the [Ethical guidelines](#) still apply. In no event shall the Royal Society of Chemistry be held responsible for any errors or omissions in this *Accepted Manuscript* or any consequences arising from the use of any information it contains.

## COMMUNICATION

## Bottom-up solution synthesis of narrow nitrogen-doped graphene nanoribbons

Cite this: DOI: 10.1039/x0xx00000x

Timothy H. Vo,<sup>a</sup> Mikhail Shekhirev,<sup>a</sup> Donna A. Kunkel,<sup>b</sup> François Orange,<sup>c</sup>  
Maxime J.-F. Guinel,<sup>c,d</sup> Axel Enders,<sup>b,e</sup> and Alexander Sinitskii<sup>\*a,e</sup>

Received 00th January 2014,  
Accepted 00th January 2014

DOI: 10.1039/x0xx00000x

www.rsc.org/


**Large quantities of narrow graphene nanoribbons with edge-incorporated nitrogen atoms can be synthesized via Yamamoto coupling of molecular precursors containing nitrogen atoms followed by cyclodehydrogenation using Scholl reaction.**

Graphene nanoribbons (GNRs), narrow strips of graphene with high aspect ratios, attract a great deal of attention because of their interesting electronic and magnetic properties.<sup>1</sup> According to the theoretical studies, these properties strongly depend on the width of GNRs as well as their edge structure and termination, and are also very sensitive to the edge disorder.<sup>2-5</sup> Thus, it is very important to precisely control the structure of GNRs on the atomic scale. Numerous top-down fabrication approaches have been developed to produce GNRs from graphite, graphene or carbon nanotubes, as discussed in the recent review papers,<sup>6-8</sup> but the resulting ribbons typically have relatively large and non-uniform widths and disordered edges. Narrow atomically precise GNRs could be synthesized *via* bottom-up approaches that employ decomposition of molecules inside carbon nanotubes,<sup>9, 10</sup> or rely on the surface-assisted<sup>11-14</sup> or solution polymerization<sup>8, 15-22</sup> of molecular precursors followed by cyclodehydrogenation of the resulting polymers. While surface-assisted bottom-up synthesis of GNRs yields small quantities of ribbons on metallic substrates in ultrahigh vacuum conditions that are ideal for scanning tunnelling microscopy (STM) characterization, solution-based approaches are preferred for the bulk synthesis of GNRs, so these two groups of methods could be considered as complimentary.


Electronic properties of GNRs could be further tuned *via* their doping with heteroatoms, such as boron or nitrogen.<sup>23</sup> This possibility has been extensively studied theoretically,<sup>24-30</sup> but only a few experimental attempts to synthesize nitrogen-doped GNRs (N-GNRs) by bottom-up approaches have been reported.<sup>14, 20</sup> Bronner *et al.* prepared chevron-like N-GNRs by the surface-assisted approach on Au(111) substrate and performed their spectroscopic characterization.<sup>14</sup> Kim *et al.* synthesized N-GNRs with a different structure in solution *via*

Suzuki coupling of molecular precursors, one of which was dibrominated pyrazine, and cyclodehydrogenation of the resulting polymers.<sup>20</sup> Here we demonstrate that high-quality chevron-like N-GNRs could be synthesized *via* Yamamoto coupling of molecular precursors containing nitrogen atoms followed by cyclodehydrogenation *via* Scholl reaction (Fig. 1).

The structure of the N-GNR that we studied in this work is shown in Fig. 1a. Since the unit cell of this ribbon contains four nitrogen atoms, we refer to it as “4N-GNR”. The monomer molecule **3** used as a precursor for the 4N-GNR synthesis is not symmetric relative to the axis perpendicular to the direction of coupling (Fig. 1b), so as the result, the positions of nitrogen atoms in the ribbon edge could vary, *i.e.* the nitrogens could also occupy the positions highlighted with red circles in Fig. 1a instead of the ones shown in the schematic. However, the N:C ratio of 1:20 in this ribbon should be the same regardless of how the monomer molecules couple with each other.

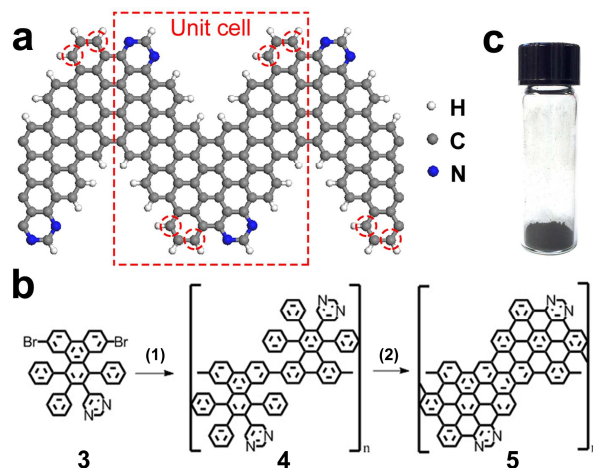

**Fig. 1** Synthesis of 4N-GNRs. (a) Schematic of 4N-GNR. (b) Reaction scheme used in this work: (1) Yamamoto coupling, (2) Scholl reaction; see text and ESI for details. (c) Optical photograph of a 4N-GNR powder.

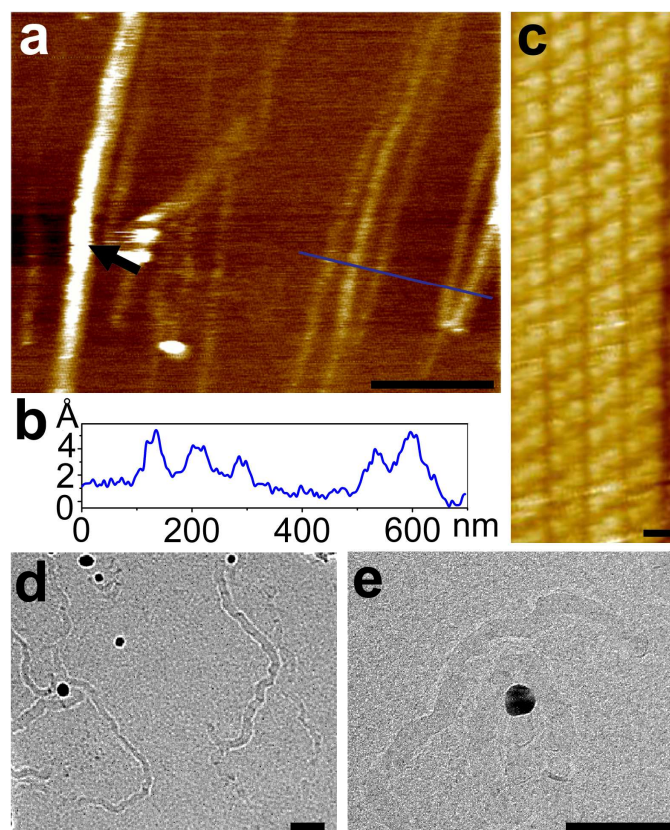


**Fig. 2** Microscopic characterization of 4N-GNRs. (a) AFM image of 4N-GNRs deposited on mica. Scale bar is 400 nm. (b) Height profile along the blue line shown in (a). (c) STM image of 4N-GNRs deposited on a Au(111) single crystal. Scale bar is 1 nm. (d, e) TEM images of 4N-GNRs. Scale bars are 50 nm.

The synthesis and characterization of the precursor molecule **3**, as well as the reactions used to convert monomer **3** to polymer **4** to 4N-GNR **5** (Fig. 1b) are described in detail in the Electronic Supplementary Information (ESI). About 100 mg of 4N-GNRs was obtained in a single reaction (Fig. 1c). Previously, we have demonstrated that similar procedure could be used to obtain > 1 g of chevron-type GNRs (nitrogen-free analogues of 4N-GNRs shown in Fig. 1a) in a single reaction,<sup>21</sup> so we believe that the synthesis of 4N-GNRs could also be scaled up to at least a gram scale. Though not soluble in any solvents that we tried, these ribbons could be suspended in various solvents, such as toluene or mesitylene, by sonication and then deposited on different substrates for microscopic and spectroscopic characterization.

It was previously demonstrated that when chevron-type GNRs are deposited from dispersion to a substrate, they could be found in a form of elongated self-assembled nanostructures, referred to as “GNR nanobelts”.<sup>21</sup> These nanobelts are only one carbon atom thick and comprise multiple GNRs arranged in a side-by-side fashion.<sup>21</sup> We deposited 4N-GNRs on a variety of substrates (mica, Au(111), copper TEM grid with ultrathin carbon support film) and observed similar nanobelts. Fig. 2a shows an atomic force microscopy (AFM) image of 4N-GNRs that were dispersed in toluene by sonication, deposited on freshly cleaved mica and dried prior to imaging. Observed in this image are spatially oriented high-aspect-ratio nanobelts that are several  $\mu\text{m}$  long. The alignment of 4N-GNR nanobelts likely happens in the contact angle between a droplet of 4N-GNR dispersion and a substrate during the solvent drying. As shown in the height profile measured along the blue line in Fig.

2a, the majority of these nanobelts have heights < 5 Å, which corresponds to the thickness of a single layer or graphene (Fig. 2b). In fact, in multiple AFM images we observed only one structure with a thickness ( $t$ ) larger than 5 Å, which is indicated by the black arrow in Fig. 2a. This structure ( $t \sim 1$  nm) is likely a rare stack of 2-3 nanobelts. Fig. 2c shows an STM image of the fragment of a 4N-GNR nanobelt on Au(111), which illustrates the side-by-side arrangement of individual ribbons that are over 40 nm long. As we indicated in the previous study of solution-synthesized chevron-like GNRs, it remains unclear if these nanobelts exist in solution or form directly on a substrate by capillary forces during the solvent evaporation.<sup>21</sup> 4N-GNR nanobelts were also imaged by transmission electron microscopy (TEM), see Fig. 2d,e. The nanobelts found on the TEM grids are 8 to 20 nm wide, which corresponds to 8-12 4N-GNRs arranged in a side-by-side fashion, and up to 1  $\mu\text{m}$  long.

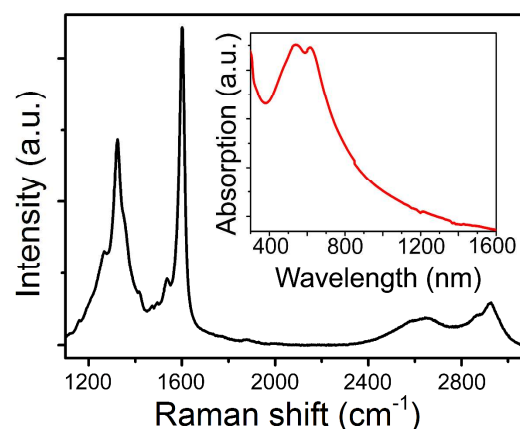

**Fig. 3** Raman spectrum of 4N-GNRs. The inset shows UV-vis-NIR absorption spectrum of 4N-GNRs suspended in mesitylene by sonication.


Raman spectroscopy is very sensitive to the disorder (edges and other structural defects, chemical functionalization, etc.) in carbon materials,<sup>31</sup> so we used this method to confirm the high structural quality of 4N-GNRs. Fig. 3 shows the Raman spectrum of 4N-GNRs, where in addition to the most intense lines at 1324 and 1600  $\text{cm}^{-1}$  that are typically referred to as D and G bands, respectively,<sup>31</sup> a series of smaller peaks around the D and G lines could be observed. This fine structure is a direct result of the low dimensionality of a nanoribbon, and the relative intensities and positions of the lines are characteristic for each specific polycyclic aromatic hydrocarbon (PAH).<sup>32</sup> 4N-GNRs synthesized in this work are structurally close to chevron-like GNRs, so this is not surprising that the Raman spectrum of 4N-GNRs is very similar to that of chevron-like GNRs synthesized by the solution approach.<sup>21</sup> Since disordered carbon materials usually show only broad D and G lines without any fine features, the spectrum shown in Fig. 3 indicates the high structural quality of 4N-GNRs.

The inset in Fig. 3 shows a UV-vis-NIR absorption spectrum of 4N-GNRs that were suspended in mesitylene by sonication. This spectrum is qualitatively similar to the UV-vis-NIR spectra of other solution-synthesized GNRs, showing a strong absorption in the visible range that gradually decreases with the wavelength increasing toward the infrared region.<sup>19, 21</sup> The optical band gap of 4N-GNRs determined from this spectrum is  $\sim 1.6$  eV.

In order to confirm the presence of nitrogen atoms in the structure of 4N-GNRs we characterized the ribbons by energy-dispersive X-ray spectroscopy (EDX) and X-ray photoelectron



spectroscopy (XPS). Fig. 4a shows an EDX spectrum of 4N-GNRs deposited on a gold foil. The nitrogen peak is detectable although small, which is not surprising, considering the expected N:C ratio of 1:20. The only foreign peak observed in the spectrum is the low intensity O line, which is likely caused by atmospheric adsorbates. The XPS survey spectrum (Fig. 4b) of the same sample demonstrates only the peaks associated with the GNRs and the gold substrate. XPS N 1s spectrum of 4N-GNRs (Fig. 4c) shows a single peak at 397.1 eV, which is close to pyridinic nitrogen peaks in N-doped CVD graphenes.<sup>33</sup> XPS C 1s spectrum (Fig. 4d) contains the main peak corresponding to the C-C bond and the weaker peak at ~288.5 eV likely representing C-N bonds.<sup>33, 34</sup>

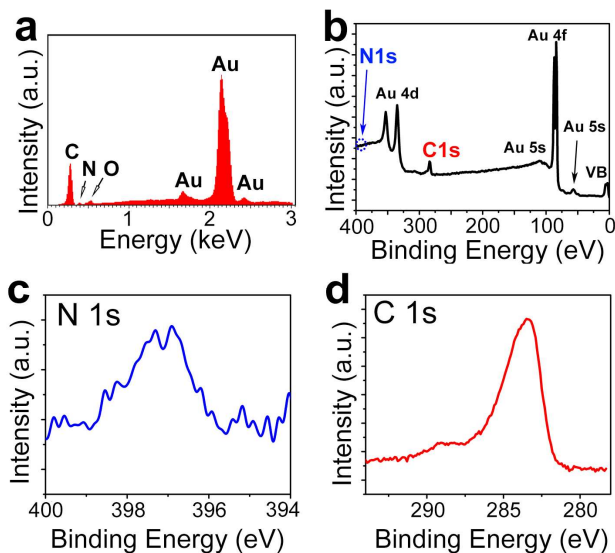

**Fig. 4.** Spectroscopic characterization of 4N-GNRs. (a) EDX spectrum of 4N-GNRs deposited on a gold substrate. (b-d) XPS spectra of 4N-GNRs deposited on a gold substrate: (b) survey spectrum, (c) N 1s spectrum and (d) C 1s spectrum.

In summary, we demonstrate that a synthetic approach based on Yamamoto coupling of N-doped molecular precursors and cyclodehydrogenation *via* Scholl reaction could be used to synthesize high-quality 4N-GNRs. The ribbons were investigated by the combination of microscopic (STM, AFM, TEM) and spectroscopic (UV-vis-NIR, XPS, EDX and Raman spectroscopy) techniques. In the future studies, we will investigate if this approach could also be employed for the synthesis of N-GNRs with other structures and N:C ratios.

This work was supported by the Nebraska Center for Energy Sciences Research (#12-00-13), the Nebraska Research Initiative and the NSF through Nebraska MRSEC (DMR-0820521) and EPSCoR (EPS-1004094).

## Notes and references

<sup>a</sup>Department of Chemistry, University of Nebraska – Lincoln, Lincoln, NE 68588, USA E-mail: sinitskii@unl.edu

<sup>b</sup>Department of Physics, University of Nebraska – Lincoln, Lincoln, NE 68588, USA

<sup>c</sup>Department of Physics and Nanoscopy Facility, University of Puerto Rico, PO Box 70377, San Juan, Puerto Rico 00936-8377, USA

<sup>d</sup>Department of Chemistry, University of Puerto Rico, PO Box 70377, San Juan, Puerto Rico 00936-8377, USA

<sup>e</sup>Nebraska Center for Materials and Nanoscience, University of Nebraska – Lincoln, Lincoln, NE 68588, USA

† Electronic Supplementary Information (ESI) available: Experimental details (synthesis and characterization). See DOI: 10.1039/c000000x/

- O. V. Yazyev, *Accounts of Chemical Research*, 2013, **46**, 2319-2328.
- L. Yang, C.-H. Park, Y.-W. Son, M. L. Cohen and S. G. Louie, *Phys. Rev. Lett.*, 2007, **99**, 186801.
- V. Barone, O. Hod and G. E. Scuseria, *Nano Lett.*, 2006, **6**, 2748-2754.
- D. A. Areshkin, D. Gunlycke and C. T. White, *Nano Lett.*, 2006, **7**, 204-210.
- E. R. Mucciolo, A. H. Castro Neto and C. H. Lewenkopf, *Phys. Rev. B*, 2009, **79**, 075407.
- M. Terrones, A. R. Botello-Méndez, J. Campos-Delgado, F. López-Urías, Y. I. Vega-Cantú, F. J. Rodríguez-Macias, A. L. Elias, E. Muñoz-Sandoval, A. G. Cano-Márquez, J.-C. Charlier and H. Terrones, *Nano Today*, 2010, **5**, 351-372.
- L. Chen, Y. Hernandez, X. L. Feng and K. Mullen, *Angew. Chem.-Int. Edit.*, 2012, **51**, 7640-7654.
- A. Chuvilin, E. Bichoutskaia, M. C. Gimenez-Lopez, T. W. Chamberlain, G. A. Rance, N. Kuganathan, J. Biskupek, U. Kaiser and A. N. Khlobystov, *Nat. Mater.*, 2011, **10**, 687-692.
- T. W. Chamberlain, J. Biskupek, G. A. Rance, A. Chuvilin, T. J. Alexander, E. Bichoutskaia, U. Kaiser and A. N. Khlobystov, *ACS Nano*, 2012, **6**, 3943-3953.
- J. M. Cai, P. Ruffieux, R. Jaafar, M. Bieri, T. Braun, S. Blankenburg, M. Muoth, A. P. Seitsonen, M. Saleh, X. L. Feng, K. Mullen and R. Fasel, *Nature*, 2010, **466**, 470-473.
- S. Blankenburg, J. M. Cai, P. Ruffieux, R. Jaafar, D. Passerone, X. L. Feng, K. Mullen, R. Fasel and C. A. Pignedoli, *ACS Nano*, 2012, **6**, 2020-2025.
- Y.-C. Chen, D. G. de Oteyza, Z. Pedramrazi, C. Chen, F. R. Fischer and M. F. Crommie, *ACS Nano*, 2013, **7**, 6123-6128.
- C. Bronner, S. Stremmlau, M. Gille, F. Brauße, A. Haase, S. Hecht and P. Tegeder, *Angew. Chem.-Int. Edit.*, 2013, **52**, 4422-4425.
- J. Sakamoto, J. van Heijst, O. Lukin and A. D. Schluter, *Angew. Chem.-Int. Edit.*, 2009, **48**, 1030-1069.
- X. Y. Yang, X. Dou, A. Rouhanipour, L. J. Zhi, H. J. Rader and K. Mullen, *J. Am. Chem. Soc.*, 2008, **130**, 4216-4217.
- Y. Fogel, L. Zhi, A. Rouhanipour, D. Andrienko, H. J. Rader and K. Mullen, *Macromolecules*, 2009, **42**, 6878-6884.
- L. Dossel, L. Gherghel, X. L. Feng and K. Mullen, *Angew. Chem.-Int. Edit.*, 2011, **50**, 2540-2543.
- M. G. Schwab, A. Narita, Y. Hernandez, T. Balandina, K. S. Mali, S. De Feyter, X. L. Feng and K. Mullen, *J. Am. Chem. Soc.*, 2012, **134**, 18169-18172.
- K. T. Kim, J. W. Lee and W. H. Jo, *Macromol. Chem. Phys.*, 2013, **214**, 2768-2773.
- T. H. Vo, M. Shekhirev, D. A. Kunkel, M. D. Morton, E. Berglund, L. M. Kong, P. M. Wilson, P. A. Dowben, A. Enders and A. Sinitskii, *Nat. Commun.*, 2014, **5**, 3189.
- A. Narita, X. Feng, Y. Hernandez, S. A. Jensen, M. Bonn, H. Yang, I. A. Verzhbitskiy, C. Casiraghi, M. R. Hansen, A. H. R. Koch, G. Fytas, O. Ivasenko, B. Li, K. S. Mali, T. Balandina, S. Mahesh, S. De Feyter and K. Mullen, *Nat. Chem.*, 2014, **6**, 126-132.
- R. Lv and M. Terrones, *Materials Letters*, 2012, **78**, 209-218.
- F. Cervantes-Sodi, G. Csányi, S. Piscanec and A. C. Ferrari, *Phys. Rev. B*, 2008, **77**, 165427.
- S. S. Yu, W. T. Zheng, Q. B. Wen and Q. Jiang, *Carbon*, 2008, **46**, 537-543.
- Y. Li, Z. Zhou, P. Shen and Z. Chen, *ACS Nano*, 2009, **3**, 1952-1958.
- X.-L. Wei, H. Fang, R.-Z. Wang, Y.-P. Chen and J.-X. Zhong, *Appl. Phys. Lett.*, 2011, **99**, 012107.
- H. Kim, K. Lee, S. I. Woo and Y. Jung, *Phys. Chem. Chem. Phys.*, 2011, **13**, 17505-17510.
- E. Cruz-Silva, Z. M. Barnett, B. G. Sumpter and V. Meunier, *Phys. Rev. B*, 2011, **83**, 155445.
- X. H. Zheng, X. L. Wang, T. A. Abtey and Z. Zeng, *The Journal of Physical Chemistry C*, 2010, **114**, 4190-4193.
- A. C. Ferrari and D. M. Basko, *Nat. Nanotechnol.*, 2013, **8**, 235-246.
- F. Negri, C. Castiglioni, M. Tommasini and G. Zerbi, *J. Phys. Chem. A*, 2002, **106**, 3306-3317.
- D. Wei, Y. Liu, Y. Wang, H. Zhang, L. Huang and G. Yu, *Nano Letters*, 2009, **9**, 1752-1758.
- A. P. Dementjev, A. de Graaf, M. C. M. van de Sanden, K. I. Maslakov, A. V. Naumkin and A. A. Serov, *Diamond Relat. Mater.*, 2000, **9**, 1904-1907.