

# ChemComm

Accepted Manuscript



This is an *Accepted Manuscript*, which has been through the Royal Society of Chemistry peer review process and has been accepted for publication.

*Accepted Manuscripts* are published online shortly after acceptance, before technical editing, formatting and proof reading. Using this free service, authors can make their results available to the community, in citable form, before we publish the edited article. We will replace this *Accepted Manuscript* with the edited and formatted *Advance Article* as soon as it is available.

You can find more information about *Accepted Manuscripts* in the [Information for Authors](#).

Please note that technical editing may introduce minor changes to the text and/or graphics, which may alter content. The journal's standard [Terms & Conditions](#) and the [Ethical guidelines](#) still apply. In no event shall the Royal Society of Chemistry be held responsible for any errors or omissions in this *Accepted Manuscript* or any consequences arising from the use of any information it contains.

Cite this: DOI: 10.1039/c0xx00000x

www.rsc.org/xxxxxx

ARTICLE TYPE

# An efficient triazole-pyridine-bistetrazolate platform for highly luminescent lanthanide complexes

S. Di Pietro,<sup>a,b</sup> D. Imbert,<sup>a,b\*</sup> and M. Mazzanti<sup>a,b\*</sup>

Received (in XXX, XXX) Xth XXXXXXXXX 20XX, Accepted Xth XXXXXXXXX 20XX

DOI: 10.1039/b000000x


Two new triazole-pyridine-bistetrazolate ligands were synthesized via a versatile procedure that allows for further derivatization; their corresponding homoleptic tris-ligand nona-coordinated lanthanide complexes are highly luminescent in the solid state and in a PVA polymeric matrix with measured values for the luminescence quantum yield of 70(7) and 98(9)% for Eu<sup>III</sup> and Tb<sup>III</sup>, respectively.

Due to their remarkable intrinsic photophysical properties (narrow emission lines, large quantum yields and high resistance to photobleaching), lanthanide ions have attracted increasing attention for a broad range of applications ranging from material science to bioanalysis.<sup>1</sup> However, due to their low absorption coefficients, the stable complexation of lanthanide ions with sensitizing ligands such as  $\beta$ -diketonates, aromatic carboxylates or heterocyclic compounds, capable of efficient energy-transfer to the lanthanide excited state, is essential for the development of such applications.<sup>2</sup> Numerous efforts have been directed towards the understanding of the energy transfer between ligands and lanthanide ions with the aim of obtaining high luminescence quantum yields. Indeed high photoluminescence quantum yields and reasonable stability are crucial for the technological application of lanthanide complexes in the areas of energy conversion (luminescent dyes or solar concentrators) or in devices such as light emitting diodes.<sup>3</sup> However, lanthanide complexes showing a quantitative ligand to metal energy transfer leading to luminescence quantum yields higher than 90%, remain extremely rare.<sup>4</sup> Recently we have reported a new class of ditetrazolate ligands containing bipyridine, terpyridine, hydroxyquinoline and pyridine chromophores.<sup>5</sup> These complexes demonstrated an extension of the absorption windows and higher luminescence quantum yields compared to analogous dicarboxylate derivatives such as dpa<sup>2-</sup> for both the Eu and Tb ions while maintaining a comparable stability with respect to dissociation.

Here we report two new triazole-pyridine-bistetrazolate ligands prepared via a versatile synthetic procedure (Scheme 1) which show that the derivatization of the pyridine-ditetrazolate scaffold with a 1,2,3-triazole using click chemistry leads to an optimized energy transfer, affording lanthanide complexes with very high luminescent quantum yields, up to 70% for Eu and 98% for Tb.

The ligands H<sub>3</sub>L<sub>1</sub> and H<sub>2</sub>L<sub>2</sub> were synthesized in six and seven steps from chelidamic acid with global yields of 38 and 22%

respectively. The chosen synthetic route allows the synthesis of both ligands from the same alkyne intermediate in just one or two steps based on click chemistry. We anticipate that this versatile route can be used for the synthesis of a wide range of N-substituted triazole derivatives. The <sup>1</sup>H NMR in d<sub>6</sub>-DMSO shows, for both the ligands, the labile tetrazole protons and in the case of L<sub>1</sub> also the triazole proton (Figure S1). The pK<sub>a</sub>'s of L<sub>1</sub> (pK<sub>a1</sub> = 7.7(1) pK<sub>a2</sub>+pK<sub>a3</sub> = 9.2(1)) were determined in water by UV absorption spectroscopy. These values indicate that the tetrazole group can be deprotonated using triethylamine as a base while in these conditions the triazole remains protonated.

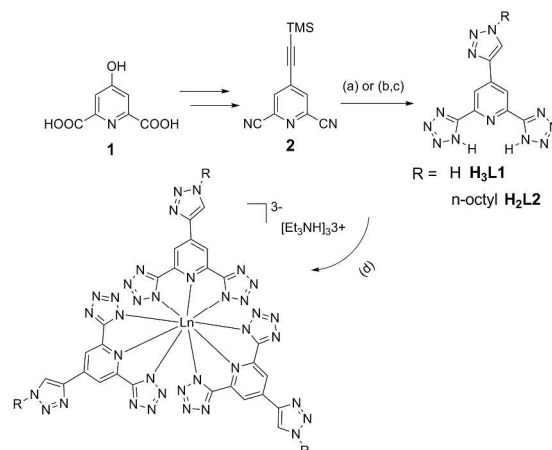

**Scheme 1.** (a) NaN<sub>3</sub>/NH<sub>4</sub>Cl, DMF (b, c) n-octyl-N<sub>3</sub>/K<sub>2</sub>CO<sub>3</sub>/CuSO<sub>4</sub>/t-BuOH/H<sub>2</sub>O and NaN<sub>3</sub>/NH<sub>4</sub>Cl/DMF (d) Et<sub>3</sub>N, 0.33 eq Ln(OTf)<sub>3</sub>


The UV-visible absorption spectra of H<sub>2</sub>L<sub>1</sub> and H<sub>2</sub>L<sub>2</sub> feature two main bands located around 227 and 303 nm assigned to the  $\pi \rightarrow \pi^*$  transitions mainly located on the pyridine. Upon ligand deprotonation these bands are slightly shifted with the appearance of an additional absorption band at 250 nm. The absorption bands of the deprotonated ligands are slightly red-shifted by ca. 15-20 nm upon complexation to Eu<sup>III</sup> (Figure S7). The complexation of Eu<sup>III</sup> was monitored in MeOH (2.5 · 10<sup>-5</sup> M) by UV spectroscopy and the titration data could be fitted to the following model with L<sub>i</sub> = L<sub>1</sub> and L<sub>2</sub> (charges omitted for the sake of simplicity):



consistent with the presence of four absorbing species (L<sub>i</sub>, [Ln(L<sub>i</sub>)<sub>3</sub>], [Ln(L<sub>i</sub>)<sub>2</sub>] and [Ln(L<sub>i</sub>)]). The lower values of log $\beta$ <sub>1</sub>, log $\beta$ <sub>2</sub>, and log $\beta$ <sub>3</sub> determined for L<sub>1</sub> (6.3(2), 10.2(5), 17.2(3)) compared to L<sub>2</sub> (7.2(3), 11.8(3), 18.6(4)) indicates a slightly

reduced stability of the complexes formed by  $L_1$ . These values are similar to those reported for the trianionic homoleptic Eu(III) complexes of the dipicolinate ligand ( $dpa^{2-}$ ).<sup>6</sup> These results are in line with that observed for terpyridine based tetrazolate ligands<sup>5a</sup> and indicate that tetrazolate and carboxylate-based ligands afford lanthanide complexes of comparable stability. A sizeable increase of both the absorbance red-shift and the absorption coefficient is also observed for the triazole-substituted  $L_1$  and  $L_2$  compounds compared to the pyridine-bistetrazolate analogues (Figure S8).<sup>5b</sup>

The homoleptic complexes  $[Ln(L_i)_3](Et_3NH)_3$  ( $Ln = La, Pr, Eu, Tb, L_i = L_1, L_2$ ) have been prepared by reacting three equivalents of  $L_1$  or  $L_2$  with one equivalent of lanthanide triflate in methanol solution in the presence of triethylamine as shown in Scheme 1. Both complexes are soluble in methanol, those of  $L_1$  are also soluble in water while the n-octyl group in  $L_2$  renders its complexes highly soluble in  $CH_2Cl_2$ . The complexes have been characterized by proton NMR spectroscopy and mass spectrometry. The  $^1H$  spectra of all complexes in MeOD (Figure S2-S6) show the presence of only one set of signals with two and six resonances respectively for  $L_1$  and  $L_2$ . These features are consistent with the presence of the undissociated, rigid,  $D_3$ -symmetric  $[Ln(L_i)_3]^{3-}$  solution species on the NMR timescale. Similar features were found in the closely related homoleptic complex  $[Ln(pytz)_3](Et_3NH)_3$  ( $H_2pytz=2,6$ -bis-tetrazolyl-pyridine).<sup>5b</sup>

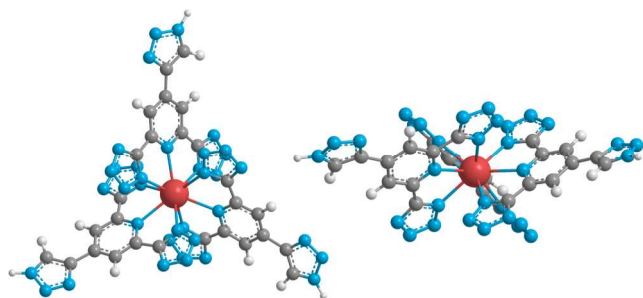

**Figure 1.** Diagram of the PERSEUS optimized solution structure of  $[Eu(L_1)_3]^{3-}$  (colour code: europium, red; nitrogen, blue; carbon grey; hydrogen, white). View along the threefold symmetry axis (left) and perpendicular to it (right).

The solution structure of the anion  $[Eu(L_1)_3]^{3-}$  was determined by paramagnetic NMR spectroscopy.<sup>7</sup> The proton and carbon resonances of the  $[Ln(L_1)_3](Et_3NH)_3$  ( $Ln = La, Pr, Eu$ ) complexes were assigned using 1D- and 2D-NMR experiments (HSQC, HMBC,  $^{13}C$ -NMR) with  $Ln = La, Pr$  and  $Eu$ . The separation of the PCS terms from the FC term, crucial for the structural determination, was achieved using the NMR data of the  $Pr$  and  $Eu$  complexes with the “two lanthanide method” developed by Di Bari et al.<sup>8</sup> These PCS values were used together with the relaxation rates for the structural optimization by means of the program PERSEUS.<sup>9</sup>

This structure (Figure 1) compares well (see ESI) with the solid state structure of the closely related complexes  $[Ln(pytz)_3](Et_3NH)_3$  reported by our group in 2012.<sup>5b</sup> The coordination polyhedron around the  $Eu$  cation is best described as a slightly distorted tricapped trigonal prism. The similarity of the chemical shifts of the paramagnetic complexes  $[Ln(L_i)_3](Et_3NH)_3$  indicates that, as anticipated, the presence of the n-octyl substituent on the triazole does not significantly affect the

solution structure.

Photophysical data have been collected both in the solid state and in methanol solution for the  $[Ln(L_i)_3](NH_4)_3$  ( $Ln = Eu, Tb, Nd, Yb$ , Figure 2a and ESI) and they show that the ligands  $L_1$  and  $L_2$  efficiently sensitize the lanthanide emission both in the visible and NIR range. In solution, the ligand emission levels were determined for  $L_1$  and  $L_2$  through UV excitation in the  $(n, \pi) \rightarrow \pi^*$  absorption bands. For  $L_2$  the emission of the  $^1\pi\pi^*$  and  $^3\pi\pi^*$  states occur at  $28\,600\text{ cm}^{-1}$  and  $24\,800\text{ cm}^{-1}$ , respectively. For  $L_1$  they are found at  $28\,450$  and  $23\,900\text{ cm}^{-1}$  ( $23\,100\text{ cm}^{-1}$  in solid state), respectively, in agreement with the increased conjugation. The  $^3\pi\pi^*$  mono-exponential luminescence decay is unusually long at  $3.4(1)\text{ s}$ , close to that obtained for benzoic acid.<sup>10</sup>

The luminescence emission spectra of the  $Ln^{III}$  complexes of  $L_1$  and  $L_2$  are consistent with the empirical rules defined for an optimal ligand-to-metal transfer process,<sup>2b, 11</sup> since emission from both the singlet and triplet states are not observed. It is worth noting that the metal-centered luminescence is efficiently sensitized, in spite of the relatively large energy gaps between the ligand triplet state and the  $Eu^{III}$  accepting level with  $\Delta E(^3\pi\pi^* - ^5D_0) \approx 6600$  for  $L_1$  and  $7560\text{ cm}^{-1}$  for  $L_2$ . The energy gap between the  $Tb^{III}$  accepting level and the  $L_1$  and  $L_2$  triplet state is optimum for a quantitative energy transfer with  $\Delta E(^3\pi\pi^* - ^5D_4) \approx 3410$  and  $4310\text{ cm}^{-1}$ , respectively.<sup>2b</sup> The emission spectra of  $[Eu(L_i)_3](Et_3NH)_3$  in MeOH (see Figure 2a and ESI), through direct excitation of the ligand, exhibit the characteristic  $^5D_0 \rightarrow ^7F_j$  transitions and in spite of the low resolution of the emission spectrum, the crystal field splitting can be interpreted in terms of an average  $D_3$  symmetry point group (in which  $^7F_0$  is forbidden), in agreement with the solution structure determined by NMR. The solid state emission spectra are identical to those observed in solution both in shape and intensity, indicating the presence of the same structure for all the complexes.

The luminescence decays for  $[Eu(L_i)_3](Et_3NH)_3$  are monoexponential in the 2.21-3.02 ms range and confirm the absence of solvent in the first coordination sphere of the lanthanide ion. The values of the absolute luminescence quantum yield  $\Phi_{tot}^{Eu}$  measured in MeOH amounts to 40-42% and increase from 41 to 70% passing from  $L_1$  to  $L_2$  in solid state. The latter value is among the highest reported in the literature for europium complexes (60-76%).<sup>5b, 12</sup> Since  $\Phi_{tot}^{Eu} = n_{sens} \cdot \Phi_{Eu}^{Eu}$ , we have determined the intrinsic quantum yield  $\Phi_{Eu}^{Eu}$  of  $Eu^{III}$  upon direct f-f excitation, in order to better understand the origin of the high measured absolute quantum yields.<sup>6a, 13 14</sup>

Table 1. Lifetimes (ms for  $Eu$ - $Tb$  and s for  $Gd$  complexes) and absolute quantum yields (%) measured at 298K in solid state, MeOH ( $\lambda_{ex} = 325\text{ nm}$ ) and in PVA film ( $\lambda_{ex} = 335\text{ nm}$ ).

$L_i$	$Ln$	$\tau_{solid}$	$\tau_{PVA}$	$\tau_{MeOH}$	$\Phi_{solid}$	$\Phi_{PVA}$	$\Phi_{MeOH}$
$L_2$	$Gd(^3\pi\pi^*)$	-	-	1.85(1)	-	-	3.4(1)
	$Eu(^5D_0)$	2.68(4)	2.80(6)	2.98(9)	70(7)	70(3)	43(4)
	$Tb(^5D_4)$	1.29(2)	1.29(3)	1.61(5)	98(9)	96(4)	94(9)
$L_1$	$Gd(^3\pi\pi^*)$	-	-	2.05(2)	-	-	3.4(1)
	$Eu(^5D_0)$	2.21(3)	-	3.02(5)	42(4)	-	41(5)
	$Tb(^5D_4)$	0.93(2)	0.70(2)	1.62(2)	9(1)	18(1)	79(8)

The obtained values of  $n_{sens}$  at 0.9 and 0.73 in the solid state and MeOH respectively for  $L_2$  (0.65 and 0.71 for  $L_1$ ) are in perfect agreement with a very efficient metal-centred emission.

The  $[Tb(L_i)_3](Et_3NH)_3$  complexes display the typical lanthanide emission spectrum  $^5D_4 \rightarrow ^7F_J$  transitions (Figure 2a and ESI) and monoexponential luminescence decays (1.6 ms in MeOH and 0.93-1.29 ms in the solid state for  $L_1$  and  $L_2$ , respectively). The values of the absolute luminescence quantum yield of  $[Tb(L_2)_3](Et_3NH)_3$  both in MeOH and in solid state are very high at 98(9)%. Only one example of a ligand architecture leading to quantitative quantum yield for terbium emission has been reported to date.<sup>4</sup> The values of the luminescence quantum yield measured for  $[Tb(L_1)_3](Et_3NH)_3$  is very high at 79% in MeOH but is dramatically reduced to 9% in the solid state. This can be explained by the decrease of the  $\Delta E(^3\pi\pi^* - ^5D_4)$  energy gaps going from solution to solid state, allowing the mixing of the  $^3\pi\pi^*$  states with the 4f levels and a subsequent back-transfer from the excited state of the metal to the ligand (decrease of the lifetime).<sup>12a, 15</sup> Additional molecular packing interactions in the solid state might also lead to quenching effects as suggested by the increase of the quantum yields (9 to 18%) from solid to PVA (polyvinyl acetate) films. Preliminary studies show that these ligands can also sensitize the  $Nd^{III}$ - and  $Yb^{III}$ - centered NIR luminescence emission in MeOH (Fig. 3) with sizeable measured luminescence quantum yields of 0.023 and 0.13%.

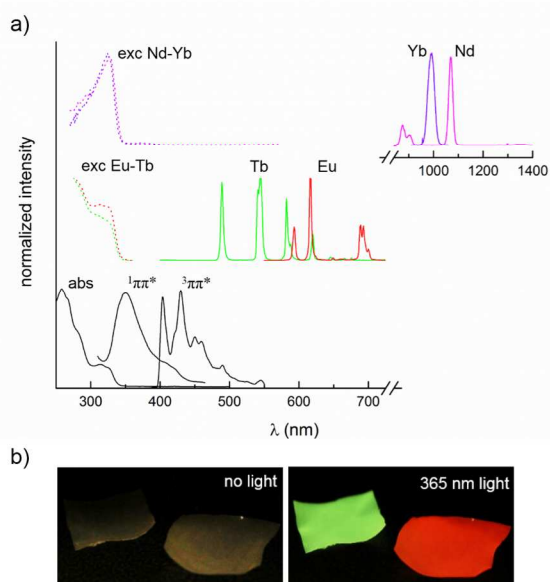


Figure 2. a) absorption, excitation, singlet, triplet and emission spectra of  $[Ln(L_2)_3](Et_3NH)_3$  in MeOH (Ln=Eu, Tb, Nd, Yb, Gd); b) flexible PVA films doped with  $[Ln(L_2)_3](Et_3NH)_3$  complexes excited or not with the UV lamp (Tb left, Eu right).

The  $[Ln(L_2)_3](Et_3NH)_3$  complexes (Ln = Eu and Tb) are easily incorporated within flexible PVA films affording doped polymers (Figure 2b) with photophysical properties matching those obtained for the pure complexes in the solid state (Table 1). Thus, the excellent brightness of these systems is preserved in the polymer and could be useful for photonic device applications.

In conclusion, we have shown that  $L_1$  and  $L_2$  form soluble and stable homoleptic 3:1 complexes and sensitize very efficiently the

emission of  $Eu^{III}$  and  $Tb^{III}$ . For the Tb complex, the measured value of the absolute quantum yield at  $\sim 100\%$  indicates the presence of a quantitative energy transfer from the ligand to the metal which has only been observed once before. The versatile procedure developed for the synthesis of  $L_1$  and  $L_2$  allows access to complexes with different solubilities and provides a facile route for grafting or encapsulating these complexes in different substrates. Thus, the triazole-pyridine-bistetrazolate motif provides a very attractive platform with optimum energy transfer which is crucial for the application of lanthanide complexes in optical devices.


The authors thank Colette Lebrun and Lydia Plassais (CEA-Grenoble) for the support in synthesis and ES-MS spectroscopy and prof. L. Di Bari for the fruitful discussion. The authors gratefully acknowledge financial support from the "French Agence Nationale de la Recherche", grant ANR-13-BS08-0011-01 and from Labex Arcane, ANR-11-LABX-003-01.

## Notes and references

- <sup>a</sup> CEA, INAC-SCIB, F-38000 Grenoble, France. Fax: 04 38 78 50 90; Tel: 04 38 78 38 87; E-mail: [Daniel.imbert@cea.fr](mailto:Daniel.imbert@cea.fr)
- <sup>b</sup> [Marinella.mazzanti@cea.fr](mailto:Marinella.mazzanti@cea.fr)
- <sup>c</sup> Univ. Grenoble Alpes, INAC-SCIB, F-38000 Grenoble, France
- † Electronic Supplementary Information (ESI) available: [general methods, synthesis, equipment, absorption, emission and excitation spectra.]. See DOI: 10.1039/b000000x/
1. a) S. V. Eliseeva and J. C. G. Bunzli, *Chem. Soc. Rev.*, 2010, **39**, 189-227; b) J. C. G. Bunzli, *Chem. Rev.*, 2010, **110**, 2729-2755; c) G. J.-C. Bünzli and A. S. Chauvin, *Lanthanides in Solar Energy Conversion*, Amsterdam, 2014; d) S. Faulkner and J. L. Matthews, *Comprehensive Coordination Chemistry II*, Elsevier, Oxford, UK, 2004; e) J. Feng and H. Zhang, *Chem. Soc. Rev.*, 2013, **42**, 387-410; f) E. G. Moore, A. P. S. Samuel and K. N. Raymond, *Acc. Chem. Res.*, 2009, **42**, 542-552.
  2. a) K. Binnemans, *Chem. Rev.*, 2009, **109**, 4283-4374; b) M. Latva, H. Takalo, V. M. Mikkala, C. Matachescu, J. C. Rodriguez-Ubis and J. Kankare, *J. Lumin.*, 1997, **75**, 149-169; c) A. De Bettencourt-Dias, P. S. Barber and S. Viswanathan, *Coord. Chem. Rev.*, doi.org/10.1016/j.ccr.2014.04.010; d) A. D'Aleo, A. Picot, A. Beeby, J. A. G. Williams, B. Le Guennic, C. Andraud and O. Maury, *Inorg. Chem.*, 2008, **47**, 10258-10268.
  3. a) A. de Bettencourt-Dias, *Dalton Trans.*, 2007, 2229-2241; b) J. C. G. Bunzli and S. V. Eliseeva, *Chem. Sci.*, 2013, **4**, 1939-1949.
  4. a) M. Starck, P. Kadjane, E. Bois, B. Darbouret, A. Incamps, R. Ziessel and L. J. Charbonnière, *Chem. Eur. J.*, 2011, **17**, 9164-9179; b) E. Brunet, O. Juanes, R. Sedano and J.-C. Rodriguez-Ubis, *Photochem. Photobiol. Sci.*, 2002, **1**, 613-618.
  5. a) E. S. Andreiadis, R. Demadrille, D. Imbert, J. Pecaut and M. Mazzanti, *Chem. Eur. J.*, 2009, **15**, 9458-9476; b) E. S. Andreiadis, D. Imbert, J. Pecaut, R. Demadrille and M. Mazzanti, *Dalton Trans.*, 2012, **41**, 1268-1277; c) G. Bozoklu, C. Marchal, J. Pecaut, D. Imbert and M. Mazzanti, *Dalton Trans.*, 2010, **39**, 9112-9122.
  6. a) A. Aebischer, F. Gumy and J. C. G. Bunzli, *Phys. Chem. Chem. Phys.*, 2009, **11**, 1346-1353; b) A. S. Chauvin, F. Gumy, D. Imbert and J. C. G. Bunzli, *Spectrosc. Lett.*, 2007, **40**, 193-193.
  7. a) I. Bertini and C. Luchinat, *Coord. Chem. Rev.*, 1996, **150**, R7; b) L. Di Bari and P. Salvadori, *Coord. Chem. Rev.*, 2005, **249**, 2854-2879.

8. S. Di Pietro, S. Lo Piano and L. Di Bari, *Coord. Chem. Rev.*, 2011, **255**, 2810-2820.
9. L. Di Bari, G. Pintacuda, S. Ripoli and P. Salvadori, *Magn. Reson. Chem.*, 2002, **40**, 396-405.
- 5 10. H. J. Maria and S. P. McGlynn, *J. Chem. Phys.*, 1970, **52**, 3399-3402.
11. F. J. Steemers, W. Verboom, D. N. Reinhoudt, E. B. Vandertol and J. W. Verhoeven, *J. Am. Chem. Soc.*, 1995, **117**, 9408-9414.
12. a) G. S. Kottas, M. Mehlstaubl, R. Froehlich and L. De Cola, *Eur. J. Inorg. Chem.*, 2007, 3465-3468; b) A. de Bettencourt-Dias, *J. Am. Chem. Soc.*, 2007, **129**, 15436-15437; c) G. F. de Sà, O. L. Malta, d. M. C. Donegà, A. M. Simas, R. L. Longo, P. A. Santa-Cruz and E. F. da Silva Jr, *Coord. Chem. Rev.*, 2000, **196**, 165-195; d) O. Moudam, B. C. Rowan, M. Alamiry, P. Richardson, B. S. Richards, A. C. Jones and N. Robertson, *Chem. Commun.*, 2009, 6649-6651; e) J. W. Walton, A. Bourdolle, S. J. Butler, M. Soulie, M. Delbianco, B. K. McMahon, R. Pal, H. Puschmann, J. M. Zwier, L. Lamarque, O. Maury, C. Andraud and D. Parker, *Chem. Commun.*, 2013, **49**, 1600-1602; f) S. J. Butler, L. Lamarque, R. Pal and D. Parker, *Chem. Sci.*, 2014, **5**, 1750-1756; g) E. G. Moore, J. Xu, C. J. Jocher, E. J. Werner and K. N. Raymond, *J. Am. Chem. Soc.*, 2006, **128**, 10648-10649.
13. J. M. Senegas, G. Bernardinelli, D. Imbert, J. C. G. Bunzli, P. Y. Morgantini, J. Weber and C. Piguet, *Inorg. Chem.*, 2003, **42**, 4680-4695.
14. G. Zucchi, O. Maury, P. Thuery, F. Gumy, J.-C. G. Buezli and M. Ephritikhine, *Chem. Eur. J.*, 2009, **15**, 9686-9696.
15. C. Piguet, A. F. Williams, G. Bernardinelli and J. C. G. Bunzli, *Inorg. Chem.*, 1993, **32**, 4139-4149.

## Graphical abstract

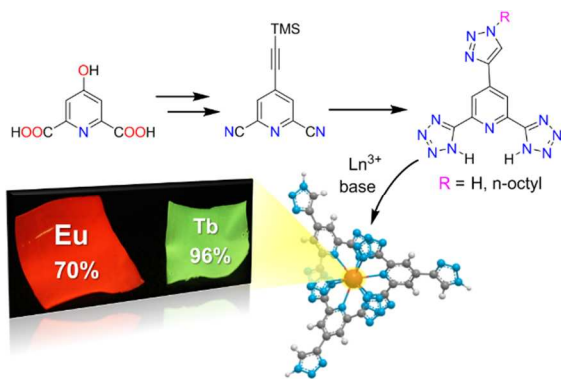

Two new triazole-pyridine-bistetrazolate ligands were synthesized via a versatile procedure that allows for further derivatization; their corresponding homoleptic tris-ligand nona-coordinated lanthanide complexes are highly luminescent in the solid state and in a PVA polymeric matrix with measured values for the luminescence quantum yield of 70(7) and 98(9)% for Eu<sup>III</sup> and Tb<sup>III</sup>, respectively.

10