ChemComm

Accepted Manuscript



This is an *Accepted Manuscript*, which has been through the Royal Society of Chemistry peer review process and has been accepted for publication.

Accepted Manuscripts are published online shortly after acceptance, before technical editing, formatting and proof reading. Using this free service, authors can make their results available to the community, in citable form, before we publish the edited article. We will replace this Accepted Manuscript with the edited and formatted Advance Article as soon as it is available.

You can find more information about *Accepted Manuscripts* in the **Information for Authors**.

Please note that technical editing may introduce minor changes to the text and/or graphics, which may alter content. The journal's standard <u>Terms & Conditions</u> and the <u>Ethical guidelines</u> still apply. In no event shall the Royal Society of Chemistry be held responsible for any errors or omissions in this *Accepted Manuscript* or any consequences arising from the use of any information it contains.



Cite this: DOI: 10.1039/c0xx00000x

www.rsc.org/xxxxxx

Communication

Defined Macromolecules Photo-Induced Sequence Hetero via **Bifunctional Synthons**

Nicolas Zydziak, ab Florian Feist, Birgit Huber, Jan O. Mueller, and Christopher Barner-Kowollik*ab

Received (in XXX, XXX) Xth XXXXXXXXX 20XX, Accepted Xth XXXXXXXX 20XX


5 DOI: 10.1039/b000000x

We report the first photochemical protocol for the generation of sequence defined macromolecules employing two hetero bifunctional photoreactive synthons, exploiting orthogonal nature of photochemical - via the use of caged 10 dienes - and thermally driven ligation protocols. We demonstrate that the iterative alternating synthon addition to an initial bifunctional core under irradiation at ambient temperature enables the generation of a macromolecule with up to 10 units ($M = 3231.58 \text{ g} \cdot \text{mol}^{-1}$, D = 1.00). The resulting 15 macromolecules are monodisperse and feature absolute chain end fidelity. The unit-by-unit construction of the macromolecule is evidenced by Nuclear Magnetic Resonance spectroscopy, Electrospray Ionization Mass Spectrometry and Size Exclusion Chromatography. The fundamental 20 principle demonstrated herein paves the way for employing photochemical strategies for the design of sequence defined polymers.

Achieving sequence control in synthetic polymers is considered as one of the most challenging tasks in contemporary 25 macromolecular chemistry. 1-2 In the past years, several synthetic avenues have been followed, some relying on effectively generating multi-block copolymers with short individual block lengths by carefully optimizing reversible deactivation polymerization protocols, e.g. via Reversible Addition ³⁰ Fragmentation chain Transfer (RAFT) polymerization^{3–5} or Cu(0) mediated polymerization, 6-9 as well as time-controlled sequential polymerization. 10-12 Despite the elegance of these approaches, the obtained macromolecules suffer from either an inherent dispersity associated with the individual polymer blocks, a very short 35 sequence length or both. 13 The provision of truly sequence defined polymers has been recently advanced by promising innovations - although based on highly demanding synthetic strategies with elaborative purification protocols - some exploiting templates,14 DNA templates,15-17 solid supports18 or 40 even complex biomimetic system such as molecular machines. 19 Only few examples describe sequence defined macromolecules synthesized in a simple and direct manner, e.g. via copper assisted alkyne-azide cycloaddition polymer blocks²⁰ or small molecule reactions.21

A facile method to generate high molecular weight sequence defined macromolecules, inspired by efficient modular ligation chemistry concepts, 22-23 would advance the field

macromolecular chemistry to elaborate fully spatially controlled synthetic proteins, enzymes or DNA mimics. Herein, we present 50 a novel concept for the generation of sequence defined synthetic macromolecules based on the use of hetero bifunctional photoreactive molecular synthons, as tools for defined macromolecular design. Indeed, photochemically induced reactions have thus far not been exploited for the provision of 55 sequence defined macromolecules, despite the inherent advantages these reactions may provide, including operation at ambient temperature and quantitative yields under equimolar reaction conditions as well as spatial and temporal control, 23,24 Our team has recently exploited the photochemical provision of 60 caged dienes and dienophiles from photoenol and phenacylsulfide precursors in modular Diels-Alder reactions²³ for the design of complex macromolecular architectures²⁵⁻²⁸ as well as spatially resolved surface modification.²⁹ Scheme 1 illustrates the synthetic pathway taken in the current approach for the generation of a 65 sequence defined macromolecule based on the aforementioned photoreactive species.

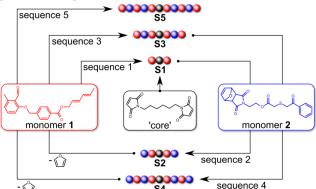

Scheme 1. Overview of the iterative synthesis of the sequence defined macromolecule S5 based on orthogonal molecular synthons: 1 reacts with the core in the first sequence to provide 70 S1, then reacting with synthon 2 in the second sequence to provide S2. Subsequent to the deprotection steps, the cycle is repeated up to the fifth sequence.

Both hetero bifunctional monomers, synthons 1 and 2, carry a 75 photoreactive unit, i.e. a photoenol or a phenacylsulfide respectively, and a diene or dienophilic unit. It should be emphasized that the judicious combination of the reactive groups is of key importance: the open chain diene is combined with the ChemComm Page 2 of 4

photoenol species 1, whereas the dienophile releasing phenacylsulfide is combined with a dienophile (furan protected maleimide function) 2. The synthetic key that makes the current concept viable is the inherent orthogonality of photo-triggered 5 and thermally induced Diels-Alder reactions, i.e. the non-reactive presence of an open chain diene and an activated dienophile that do not undergo a ligation process, and are separately addressable via photochemical approaches. The attractiveness of the employed route to both synthons (esterification) with the 10 dienophilic/diene unit is its simplicity and versatility. Both criteria suggest the potential diversity of chemical structures in monomer design. For instance, selected side functions can be introduced into the design on demand or molecules can be employed – via the inherently reactive chain end functionality of 15 the resulting macromolecules – for grafting reactions. By employing trilinkers, the linear sequence defined macromolecule may be transformed into 3D networks with a completely controlled topology.

The sequence commences by reacting synthon 1 with the 20 bifunctional maleimide core via irradiation with a lamp featuring a wavelength maximum of $\lambda_{max} = 350 \text{ nm}$. The photoligation²⁴ leads to the first product S1. Importantly, this first photoreaction is orthogonal with regard to a potential thermally driven Diels-Alder ligation between the maleimide functions with the open 25 chain diene groups of 1 (refer to the Supporting Information section). The dimer S1, featuring two open chain diene functionalities as chain termini, reacts in a subsequent photoreaction (employing the identical lamp) with synthon 2, involving an in situ highly reactive dienophile (thioaldehyde)²⁷ to 30 afford the tetramer S2, and providing a molecule of acetophenone (Fig. 1, a). The thermal deprotection of S2 via a retro-Diels-Alder (rDA) reaction leads to the product S2d, bearing two maleimide chain termini (Fig. 1, b), which are able to react under

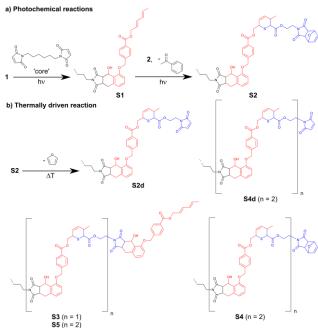


Fig. 1. Synthetic pathway for the photochemical construction (a) 35 of the sequence defined polymer and intermediate retro-Diels-Alder (rDA) deprotection (b). For clarity, only one part of the synthesized symmetrical molecules is represented.

the same conditions as in the first sequence with synthon 1. The described cycle is repeated in order to obtain the third sequence 40 product S3 (hexamer), which is reacted with the synthon 2 in the fourth sequence to generate S4. S4 undergoes a rDA reaction as described for S2 in order to afford the deprotected maleimide chain ended S4d. Again, the photoreaction with 1 is repeated to generate the fifth sequential product S5, featuring a total of 10 45 subsequently incorporated units.

The ¹H NMR spectra of the novel bifunctional photoreactive species 1 and 2 are depicted in Fig. 2, respectively. Synthon 1 features - on the one hand - a photoreactive moiety, i.e. photoenol, evidenced via the resonances associated with protons 50 m and n (2.51 and 10.67 ppm, respectively) and – on the other hand – an open chain diene, i.e. sorbyl group, associated with the resonances of protons c, d and f (6.01, 6.27 and 4.75 ppm, respectively). Similarly for 2, the resonances of protons related to the photoreactive moiety, i.e. phenacylsulfide group, are 55 recognizable (g to j protons), as well as those connected with the protected maleimide (protons a and b located at 6.42 and 5.18 ppm respectively). In the following, the cited protons c and d from synthon 1 are labelled 1c and 1d. The same convention is employed for the protons m and n (1m and 1n), as well as for the 60 protons a, b and c from synthon 2 (2a, 2b and 2c).

Following the synthetic pathway, the first sequence to afford S1 (Fig. 1a) after the reaction of the bifunctional maleimide core with monomer 1 was successful. The ¹H NMR spectrum of S1 depicts the success of the photoreaction, since the resonances of 65 the photoreactive moiety (protons Im and In) disappear and are shifted according to the newly formed covalent bonds upon reaction with the core (refer to Fig. S13 to S16). Importantly, the unreacted sorbyl groups of 1 are still present, and the resonances assigned to the protons 1c, 1d and 1f remain unchanged (Fig. 3a, 70 top), implying that the photoreaction between the maleimide and photoenol groups is orthogonal without interfering with the sorbyl groups.

A detailed analysis via ¹H NMR demonstrating the orthogonal nature of the sorbyl end groups in the reaction mixture under 75 different thermal conditions is included in Fig. S12. For the second sequence (product S2), the sorbyl termini of dimer S1 react with the in situ formed thioaldehyde, leading to the disappearance of the resonances assigned to the protons 1c, 1d and If, shifted according to the newly created covalent bonds 80 (refer to Fig. S19 to S21), and the presence of the unreacted protected maleimide group of 2 with the protons 2a and 2b (Fig. 3a, second spectrum from the top). Subsequent to the successful furan cleavage (refer to Fig. S23 and S24), an iteration of both photoreactions is carried out, leading to S3 (photoreaction 85 between S2d and 1) and S4 (photoreaction between S3 and 1). Once more, the iteration of the furan cleavage (leading to S4d, refer to Fig. S27) and a subsequent photoreaction with synthon 1 lead to S5. After the odd ordered sequences (third and fifth), the proton resonances of the sorbyl termini (1c, 1d and 1f) are 90 observed as is the case for the first sequence resulting in S1 (Fig. 3, further details available in Fig. S25 and S28). Similarly, after the even ordered sequence (i.e. fourth), the proton resonances of the furan protected maleimide termini from S4 (2a and 2b) are observed analogous to S2 generated after the second sequence 95 (Fig. 3, further details available in Fig. S26). The presence of the

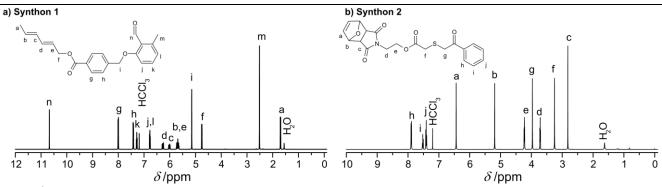


Fig. 2. ¹H Nuclear Magnetic Resonance (NMR) spectra of the two hetero bifunctional photoreactive monomers 1 (a) and 2 (b) (500 MHz, CDCl₃).

alternating resonances of the chain termini of 1c, 1d and 1f, on $_5$ the one hand, and 2a and 2b on the other hand, confirm the success of the sequence defined synthesis, reflecting the alternating addition of monomer 1 and 2 to the starting core. A more detailed analysis of the signal assignment of the end groups and the constituting backbone is included in the Supporting 10 Information section via two-dimensional NMR spectroscopy.

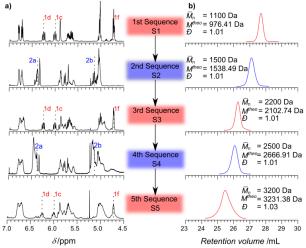


Fig. 3. Evolution of ¹H Nuclear Magnetic Resonance (NMR) spectra (a) and Size Exclusion Chromatography (SEC) traces (b) of the sequence defined products S1 to S5. (a) The NMR resonance of the key protons of synthon 1 (1c, 1d and 1f) and 2 15 (2a and 2b) are shown (500 MHz, CDCl₃). (b) SEC performed in THF (PS calibration).

A further analysis of the sequence synthesized molecules via SEC additionally confirms the success of the proposed procedure 20 to generate highly defined macromolecules. Along the ¹H NMR spectra depicted in Fig. 3, the corresponding SEC traces of S1 to S5 are shown (Fig. 3b). The average molecular weight (M_n) of each sequence product is increasing (retention volume decreasing) from 1100 g·mol⁻¹ for S1 to 3200 g·mol⁻¹ for S5. 25 Despite the non-universal character of SEC for determining the molecular weight (necessity of calibration), the reported M_n are surprisingly accurate values (reported in Fig. 3), closely corresponding to the theoretical molecular weight (M^{theo}) of each product. The increase of the molecular weight is in complete 30 agreement with the increasing size of the sequence defined macromolecule. Importantly, the dispersity (D) which is close to 1 (reported 1.01 until **S4d**) underpins the monodispersity of each

sequential product, which is below unambiguously demonstrated by mass-spectrometry. This observation highlights the unique 35 character of the designed macromolecule S5, as well as of lower order products, and thus the precision of the applied strategy.

The monodisperse nature of the sequence defined products is evident via the final characterization performed via ESI-MS. Fig. 4 depicts an overlay of ESI-MS spectra from S1 to S3, each 40 featuring a single molecular ion peak.

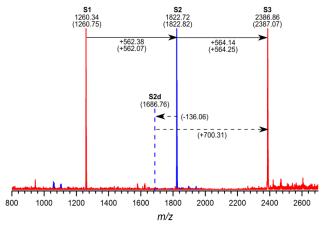


Fig. 4. Electrospray ionization mass spectra (ESI-MS) of the sequence products S1 to S3 (theoretical values in brackets). For clarity, the theoretical peak for S2d is provided (see text).

In the presence of a counter ion, the evolution of the molecular weight after the consecutive reactions enables to accurately observe the addition of the expected synthon fragments, showing that the monodisperse character of the sequence defined products remains unchanged. The first reported mass of 1260.34 m/z for S1 50 is in complete agreement with the theoretical value of the single charged molecule with the counter ion (1260.75 m/z^{theo}, further details in the Table S5) obtained from the bifunctional maleimide core ligated to two molecules of synthon 1. Detailed ESI-MS spectra with the simulated isotopic pattern of the expected 55 molecules, as well as Collision Induced Decay (CID) experiments are described in the Supporting Information section. Subsequent to the second sequence, the mass increases by 562.38 m/z, corresponding to two additional furan protected maleimide fragments from synthon 2 (562.07 m/z^{theo}). The mass shift for the 60 third sequence from S2 to S3, via S2d (shown by the dashed line in Fig. 4) corresponds to the cleavage of two furan groups $(136.06 \, m/z^{\text{theo}})$, and the gain of two molecules of synthon 1 (700.31 m/z^{theo}), leading to a total of 564.14 m/z experimentally

and $564.25 \ m/z$ (=-136.06+700.31 m/z)theoretically. Unfortunately, the higher ordered sequences S4 and S5 could not be characterized via ESI-MS, due to their high molecular weight. However, mass-spectrometry conducted with Matrix Assisted 5 Laser Desorption Ionization (MALDI) enabled the identification of the molecular ion peak for S5 (refer to Table S6). The accuracy of the presented results (mass differences from 0.1 to 0.41 m/zbetween the experimental and theoretical values) fully correlates the observed mass shifts with the conducted reactions, i.e. the 10 first and third sequences leading to the addition of two synthons 1, and the second sequence to two additional fragments from synthon 2.

In summary, a conceptually new synthetic platform based on 15 photoligation is introduced to access sequence defined macromolecules at ambient temperature. The orthogonality of the proposed photoreactive system based on complementary dienophile/diene synthons enabled to systematically introduce alternating groups at the chain ends, allowing the sequence order 20 (the molecular weight) to gradually increase. The unit-by-unit synthesized products were isolated after each sequence (up to the fifth order) and characterized, hence evidencing the validity of the proposed strategy, and underlining the specific properties of such compounds related to their exactly defined nature. 25 Importantly, the products feature a monodisperse character and absolute chain end fidelities. We have thus proven that photochemical ligation protocols are viable tools for generating sequence defined macromolecules, holding substantial promise.

C. B.-K. is grateful for support from the Helmholtz association 30 via the BIF program of the Karlsruhe Institute of Technology. The authors are grateful to A. Hochgesand (KIT) and Dr. S. Afonin (KIT) for their help with MALDI-TOF-MS experiments.

Notes and references

- ^a Soft Matter Synthesis Laboratory, Institut für Biologische Grenzflächen, 35 Karlsruhe Institute of Technology (KIT), Hermann-von-Helmholtz-Platz Eggenstein-Leopoldshafen, Germany, christopher.barner-kowollik@kit.edu, Homepage: www.macroarc ^b Preparative Macromolecular Chemistry, Institut für Technische Chemie
- und Polymerchemie, Karlsruhe Institute of Technology (KIT), 40 Engesserstr. 18, 76131 Karlsruhe, Germany.
- † Electronic Supplementary Information (ESI) available: all experimental data concerning the synthesis of the monomers and the sequential products, as well as their complementary characterization via NMR 45 spectroscopy, ESI-MS and MALDI-TOF-MS mass spectrometry, SEC and UV-VIS spectroscopy. See DOI: 10.1039/b000000x/
 - J.-F. Lutz, M. Ouchi, D. R. Liu and M. Sawamoto, Science 2013, **341**. 1238149.
- 50 2 N. Badi and J.-F. Lutz, Chem. Soc. Rev. 2009, 38, 3383-3390.
 - J. Vandenbergh, G. Reekmans, P. Adriaensens and T. Junkers, Chem. Commun. 2013, 49, 10358-10360.
 - G. Gody, T. Maschmeyer, P. B. Zetterlund and S. Perrier, Macromolecules 2014, 47, 639-649.
- G. Gody, T. Maschmeyer, P. Zetterlund and S. Perrier, Nature Commun. 2013, 4, 2505.
 - Q. Zhang, A. Anastasaki, G.-Z. Li, A. J. Haddleton, P. Wilson and D. M. Haddleton, Polym. Chem. 2014, 5, 3876-3883.
- C. Boyer, P. B. Zetterlund and M. R. J. Whittaker, J. Polymer Sci. Polymer Chem. 2014, 52, 2083-2098.

- A. Anastasaki, V. Nikolaou, G. S. Pappas, Q. Zhang, C. Wan, P. Wilson, T. P. Davis, M. R. Whittaker and D. M. Haddleton, Chem. Sci. 2014, 5, 3536-3542.
- S. Srichan, N. Kayunkid, L. Oswald, B. Lotz and J.-F. Lutz, Macromolecules 2014, 47, 1570-1577.
- 10 M. Zamfir and J.-F. Lutz, Nature Commun. 2012, 3, 1138.
- S. Srichan, H. Mutlu, N. Badi and J.-F. Lutz, Angew. Chem. Int. Ed. 2014, 53, 9231-9235.
- 12 R. K. Roy and J.-F. Lutz J. Am. Chem. Soc. 2014, 136, 12888-12891.
- 70 13 B. V. K. J. Schmidt and C. Barner-Kowollik, Nat. Chem. 2013, 5. 990-992.
- 14 S. Ida, M. Ouchi and M. Sawamoto, J. Am. Chem. Soc. 2010, 132, 14748-14750
- T. G. W. Edwardson, K. M. M. Carneiro, C. J. Serpell and H. F. Sleiman, Angew. Chem. Int. Ed. 2014, 53, 4567-4571.
- 16 D. M. Rosenbaum and D. R. Liu, J. Am. Chem. Soc. 2003, 125, 13924-13925
- 17 J. Niu, R. Hili and D. R. Liu, Nat. Chem. 2013, 5, 282-292.
- 18 P. Espeel, L. L. G. Carrette, K. Bury, S. Capenberghs, J. C. Martins and F. E. Du Prez, A. Madder, Angew. Chem. Int. Ed. 2013, 52, 13261-13264.
- B. Lewandowski, G. De Bo, J. W. Ward, M. Papmeyer, S. Kuschel, M. J. Aldegunde, P. M. E. Gramlich, D. Heckmann, S. M. Goldup, D. M. D'Souza, A. E. Fernandes and D. A. Leigh, Science 2013, 339, 189-193
- T. T. Trinh, L. Oswald, D. Chan-Seng and J.-F. Lutz, Macromol. Rapid Commun. 2014, 35, 141-145.
- 21 S. C. Solleder and M. A. R. Meier, Angew. Chem. Int. Ed. 2014, 53, 711-713.
- H. C. Kolb, M. G. Finn and K. B. Sharpless, Angew. Chem. Int. Ed. 2001, 40, 2004-2021.
- C. Barner-Kowollik, F. E. Du Prez, P. Espeel and C. J. Hawker, Angew. Chem. Int. Ed. 2001, 50, 60-62.
- R. Göstl and S. Hecht, Angew. Chem. Int. Ed. 2014, 53, 8784-8787.
- T. Gruendling, K. K. Oehlenschlaeger, E. Frick, M. Glassner, C. Schmid and C. Barner-Kowollik, Macromol. Rapid Commun. 2011, **32**, 807-812.
- 26 K. K. Oehlenschlaeger, J. O. Mueller, N. B. Heine, M. Glassner, N. K. Guimard, G. Delaittre, F. G. Schmidt and C. Barner-Kowollik, Angew. Chem. Int. Ed. 2013, 52, 762-766.
- M. Winkler, J. O. Müller, K. K. Oehlenschläger, L. Montero de Espinosa, M. A. R. Meier, C. Barner-Kowollik, Macromolecules 2012, 45, 5012-5019.
- M. Glassner, K. K. Oehlenschlaeger, A. Welle, M. Bruns and C. Barner-Kowollik, Chem. Commun. 2013, 49, 633-635.
- 29 T. Pauloehrl, G. Delaittre, V. Winkler, A. Welle, M. Bruns, H. G. Börner, A. M. Greiner, M. Bastmeyer and C. Barner-Kowollik, Angew. Chem. Int. Ed. 2012, 51, 1071-1074.