

ChemComm

Accepted Manuscript



This is an *Accepted Manuscript*, which has been through the Royal Society of Chemistry peer review process and has been accepted for publication.

Accepted Manuscripts are published online shortly after acceptance, before technical editing, formatting and proof reading. Using this free service, authors can make their results available to the community, in citable form, before we publish the edited article. We will replace this *Accepted Manuscript* with the edited and formatted *Advance Article* as soon as it is available.

You can find more information about *Accepted Manuscripts* in the [Information for Authors](#).

Please note that technical editing may introduce minor changes to the text and/or graphics, which may alter content. The journal's standard [Terms & Conditions](#) and the [Ethical guidelines](#) still apply. In no event shall the Royal Society of Chemistry be held responsible for any errors or omissions in this *Accepted Manuscript* or any consequences arising from the use of any information it contains.

COMMUNICATION

Triphenylarsonium-functionalised gold nanoparticles: potential nanocarriers for intracellular therapeutics

Cite this: DOI: 10.1039/x0xx00000x

Received 00th January 2012,
Accepted 00th January 2012

DOI: 10.1039/x0xx00000x

www.rsc.org/

Nikhil Lalwani,^a Yu-Su Chen,^a Gemma Brooke,^a Neil A. Cross,^a David W Allen,^a Alan Reynolds,^b Jesus Ojeda,^b Graham J. Tizzard,^c Simon J. Coles^c and Neil Bricklebank^{a*}

Two new triphenylarsonium alkylthiolate precursors, a thiosulfate zwitterion and a thioacetate salt, have been structurally characterised and their cytotoxicity evaluated against PC3 cells. The arsonium compounds have been used to prepare gold nanoparticles decorated with triphenylarsonium groups.

Arsenic has attracted the attention of scientists for centuries and its compounds have a variety of applications ranging from electronic and semiconductor materials¹ to organic reagents, arsonium ylides finding utility in the Wittig reaction.² Historically, arsenic compounds have been widely investigated for their medicinal properties although interest declined as greater understanding of their toxicity became apparent.^{3,4} Generally inorganic As(III) and As(V) species are highly toxic, whereas organic arsenic compounds are significantly less toxic.^{1,5} More recently there has been a resurgence of interest in the medicinal properties of arsenic compounds, including the use of arsenic trioxide and organic arsenic derivatives as treatments for leukaemia and other cancers,^{1,3,4} the characterisation of an arsenic trioxide analogue of cisplatin,⁶ and the observation that ⁷²As and ⁷⁴As radiopharmaceuticals could be useful in positron emission tomography (PET).¹

The chemistry of arsenic is broadly similar to that of phosphorus, and organic phosphonium salts are known to act as lipophilic cations that are preferentially accumulated in the mitochondria of cells.⁷ Similarly, arsonium cations are also


lipophilic and lipophosphoramidate derivatives containing arsonium head-groups (**1**)⁸ have been studied as gene delivery systems, and ⁶⁴Cu-labelled complexes of 1,4,7,10-tetraazacyclododecane-4,7,10-triacetic acid-conjugated triphenylarsonium cations (**2**) have been found to act as tumour-selective PET imaging agents.⁹ Phosphonium species have been found to be extremely valuable for mitochondria-targeted therapeutics and diagnostics. Mitochondrial dysfunction is associated with a number of disorders and there is increasing awareness of the importance of targeting drugs to this organelle.⁷ Recent work has demonstrated the potential of combining phosphonium compounds with nanotechnological approaches to traffic pharmaceutical and diagnostic moieties into mitochondria.¹⁰ For example, incorporation of phosphonium groups into the lipid bilayer of liposomes,¹¹ or onto the surface of dendrimers¹² and polymer nanoparticles,¹³ facilitates their preferential uptake by mitochondria. We have prepared phosphonium-functionalised gold nanoparticles¹⁴⁻¹⁶ which are accumulated by cells and shown by TEM to be localised in the mitochondria.¹⁷ Inspired by the success of arsonium systems such as **1** and **2** we decided to broaden the scope of our studies to include triphenylarsonium compounds and herein report our preliminary results on the biological properties of triphenylarsonium alkylthiosulfate zwitterions (**3**) and salts (**4**) and their application in the synthesis of triphenylarsonium-functionalised gold nanoparticles (AuNPs).



^a Biomedical Research Centre, Sheffield Hallam University, City Campus, Sheffield S1 1WB, UK.

^b Experimental Techniques Centre, Brunel University, Kingston Lane, Uxbridge, Middlesex, UB8 3PH, UK.

^c EPSRC National Crystallography Service, School of Chemistry, University of Southampton, Southampton, SO17 1BJ, UK

†Electronic Supplementary Information (ESI) available: [details of any supplementary information available should be included here]. See DOI: 10.1039/c000000x/

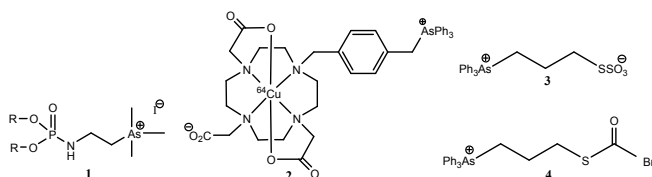

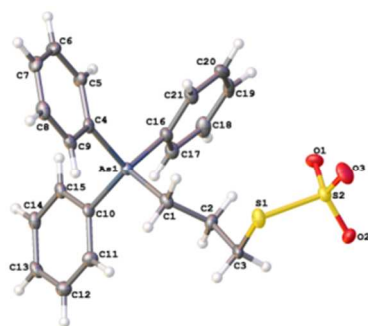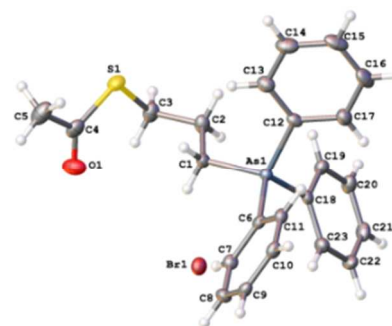Fig. 1. Molecular structure of zwitterion **3**.Fig. 2. Molecular structure of thioacetate salt **4**.

The synthesis of **3**, **4** and the triphenylarsoniumalkylthiolate-functionalised AuNPs are described in the supplementary information. The structures of **3** and **4** were confirmed by x-ray crystallography. Perhaps surprisingly, the structures of few organic thiosulfate zwitterions have been reported.¹⁸ Both compounds display the expected tetrahedral geometry around the arsenic atoms with mean C-As-C bond angles of 109.5(2)^o in **3** and 109.46(11)^o in **4**. In zwitterion **3** (Fig.1), the S-O bonds in the thiosulfate group are similar with a mean length of 1.447(4)Å, indicative of multiple bond character, and that the negative charge is delocalised over the entire sulfate group. The mean O-S-O angle [113.8(2)^o] is consistent with those in other thiosulfate ions.¹⁸ The S-S bond length [2.1081(18)Å], is slightly shorter than that of the corresponding phosphonium compound [2.1117(9)Å],¹⁵ but longer than the S-S bond in ionic thiosulfate ions such as Me₂HN(CH₂S₂O₃)₂Na⁺.¹⁸ Within the crystal lattice the zwitterions pack fairly loosely, held together by hydrogen-bonding interactions between the sulfate oxygens and the phenyl hydrogens, but there is no close interaction between the arsonium and the thiosulfate moieties. The bond lengths and angles of the thioacetate group in salt **4** (Fig. 2), are as expected. The molecular packing shows no significant interactions between the arsonium centre and the bromide anion or between the bromide and the carbonyl group.

In order to evaluate the efficacy of the triphenylarsonium-functionalised AuNPs as cellular transport systems we first screened the parent arsonium compounds **3** and **4** against the PC3 prostate cancer cell line. Cell viability was assessed using MTT and CellTitre-Glo[®] assays (Fig. 3.). MTT measures mitochondrial activity to determine the *in vitro* cytotoxic effects of chemical entities. The results showed **3** and **4** to have IC₅₀ values of 75 μM and 72 μM, respectively, after 72 hours. These values compare very favourably with those of phosphonium compounds, a large number of which have been screened using MTT against PC3 cells, and which displayed IC₅₀ values in the range 0.4 - 5 μM.¹⁹ These results are also in accordance with cellular toxicity data for lipophosphoramidate derivatives, where phosphonium compounds show greater cytotoxicity than the corresponding arsonium compounds.⁸ We also used the CellTitre-Glo[®] assay to confirm the MTT cytotoxicity data. This uses luminescence to determine the number of viable cells based on a quantification of ATP levels. The data showed a similar trend to that determined using MTT.

The cytotoxicity of arsenic compounds is crucially dependent on the nature and oxidation state of the species. Inorganic compounds, such as arsenite and arsenate, show acute toxicity; for example, the IC₅₀ of sodium arsenate was reported as 6μM.²⁰ In contrast, the organic derivative arsenobetaine, Me₃As⁺CH₂CO₂⁻, an important metabolite of arsenic which is widely distributed in marine ecosystems and found in comparatively high levels in seafood, is reported to have no toxic effects and was found to significantly enhance the cell viability of bone marrow cells *in vitro* in a concentration-dependent manner.²⁰

Phosphonioalkylthiosulfate zwitterions,¹⁵ and phosphonium alkylthioacetate salts,¹⁶ are known to act as ‘masked thiolates’ and under reductive conditions cleavage of the thiosulfate S-S or thioacetate S-C bonds, respectively, takes place, generating phosphonioalkylthiolate zwitterions that can coordinate to the surface of gold films.

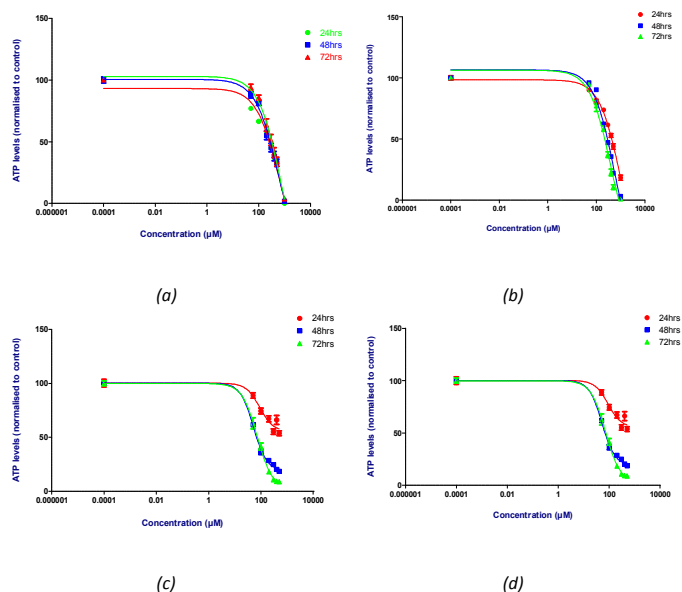


Fig. 3. Cell viability studies of triphenylarsonium derivatives **3** and **4**: (a), Cell Titre Glo assay of zwitterion **3**; (b) Cell Titre Glo assay of thioacetate salt **4**; (c), MTT assay of **3**; (d) MTT assay of **4**.

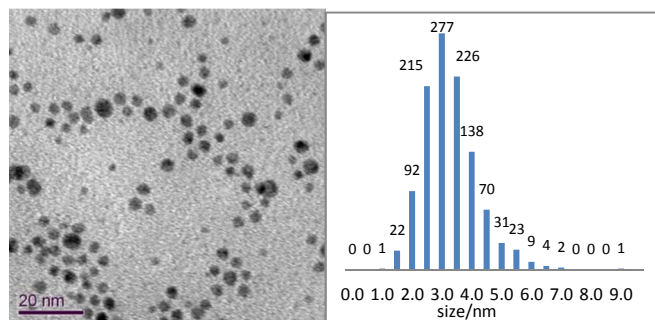


Fig. 4. TEM image of arsonium-AuNP derived from zwitterion **3** and associated particle size histogram.

We have exploited this chemistry to generate water-soluble cationic gold nanoparticles functionalised with alkylthiolate ligands bearing phosphonium head-groups. We have now extended this approach to the analogous arsonium compounds. Reduction of tetrachloroaurate salts *in situ* with sodium borohydride in the presence of **3** or **4** in a biphasic water/dichloromethane mixture yields the triphenylarsonium-capped AuNPs. Recent work has reported rare examples of the coordination chemistry of tertiary arsine ligands bearing pendant thiolate groups towards Ni(II), Pt(II) and Pd(II).²¹ However, to the best of our knowledge, there are no reports of the coordination chemistry of triorganoarsonium thiolate species or of the use of tertiary arsines or arsonium compounds as capping ligands in the formation of functionalised nanoparticles, although nanoscale liposomes or nanobins, composed of lipids and metal salts, have been used to encapsulate and stabilise arsenic trioxide in order to extend the clinical utility of this compound.²² The triphenylarsonium-AuNPs can be purified by extraction with dichloromethane followed by freeze drying. The UV-Vis spectrum of a typical sample of arsonium-capped nanoparticles shows an absorption band with λ_{\max} of 520 nm. High resolution TEM analysis of the AuNPs derived from the thiosulfate zwitterions is shown in Fig.4, and revealed the AuNPs to have spherical shapes. Size distribution analysis of 1000 particles using Abel imaging software revealed a mean diameter of 2.7 ± 0.9 nm. This compares favourably with the corresponding phosphonium-capped AuNPs which have an average particle size of 3.0 ± 1.2 nm. Wide scan XPS spectra of the arsonium-AuNPs contained signals due to Au, S, As and C, with the gold displaying the characteristic doublet for Au ($4f_{7/2}$) and Au ($4f_{5/2}$) with binding energies of *ca* 83.9 and 87.5 eV respectively, indicative of the presence of Au(0).¹⁴ Research is now ongoing to understand the cellular uptake of the triphenylarsonium-AuNPs and confirm their presence inside the cells using TEM to realise their potential intracellular transport properties.

We are grateful to Sheffield Hallam University and Indian Institute of Science (NL) for financial support.

Notes and references

- 1 A. Mudhoo, S.K. Sharma, V.K. Garg and C-H Tseng, *Critical Reviews in Environmental Science and Technology*, 2011, **41**, 435 - 519.
- 2 H.S.He, C.W.Y. Chung, T.Y.S. But and P.H. Toy, *Tetrahedron*, 2005, **61**, 1385 - 1405.
- 3 S-J.Chen, G-B.Zhou, X-W.Zhang, J-H.Mao, H. de Thé and Z. Chen, *Blood*, 2011, **117**, 6425 - 6437.
- 4 E.P. Swindell, P. L. Hankins, H. Chen, Đ.U. Miodragović and T.V. O'Halloran, *Inorg. Chem.*, 2013, **52**, 12292 - 12304.
- 5 K. Jomova, Z. Jenisova, M. Festerova, S. Baros, J. Liska, D. Hudecova, C.J. Rhodes and M. Valko, *J. Applied Toxicology*, 2011, **31**, 95 - 107.
- 6 Đ.U. Miodragović, J.A. Quentzel, J.W. Kurutz, C.L. Stern, R.W. Ahn, I. Kandela, A. Mazar and T.V. O'Halloran, *Angew. Chem., Int. Ed.* 2013, **52**, 10749–10752.
- 7 (a) A.T. Hoyle, J.E. Davoren, P. Wipf, M.P. Fink and V.E. Kagan, *Acc. Chem. Res.*, 2008, **41**, 87 - 97; (b) V. Weissig, *Pharmaceutical Research*, 2011, **28**, 2657 - 2668.
- 8 (a) E. Picquet, K. Le Ny, P. Delépine, T. Montier, J-J Yaouanc, D. Cartier, H des Abbayes, C. Férec and J-C. Clément, *Bioconjugate Chem.*, 2005, **16**, 1051 - 1053; (b) T. Le Gall, D. Loizeau, E. Picquet, N. Carmoy, J-J Yaouanc, L. Burel-Deschamps, P. Delépine, P. Giamarchi, P-A. Jaffrès, P. Lehn and T. Montier, *J. Med. Chem.*, 2010, **53**, 1496 - 1508; (c) M. Berchel, T. Le Gall, H. Couthon-Gourvès, J-P.Haelters, T. Montier, P. Midoux, P. Lehn and P-A. Jaffrès, *Biochimie*, 2012, **94**, 33 - 41.
- 9 J. Wang, C.T. Yang, Y.S. Kim, S.G. Sreerama, Q. Cao, Z. Li, Z. He, X. Chen and S. Liu, *J. Med. Chem.*, 2007, **50**, 5057 - 5069.
- 10 S.S. Malhi and R.S.R. Murthy, *Expert Opinion Drug Delivery*, 2012, **9**, 909 - 935.
- 11 (a) S.V. Boddapati, G.G.M. D'Souza, S. Erdogan, V. P. Torchilin and V. Weissig, *Nano Letters*, 2008, **8**, 2559 - 2563; (b) S. Biswas, N.S. Dodwadkar, P.P. Deshpande and V.P. Torchilin, *J. Controlled Release*, 2012, **159**, 393 - 402; (c) S.V. Boddapati, P. Tongcharoensirikul, R.N. Hanson, G.G.M. D'Souza, V. P. Torchilin and V. Weissig, *J. Liposome Research*, 2005, **15**, 49 - 58.
- 12 S. Biswas, N.S. Dodwadkar, A. Piroyan and V.P. Torchilin, *Biomaterials*, 2012, **33**, 4773 - 4782.
- 13 X-H. Wang, H-S. Peng, L. Yang, F-T. You, F. Teng, A-W. Tang, F-J. Zhang and X-H. Li, *J. Mater. Chem. B*, 2013, **1**, 5143 - 5152.
- 14 Y. Ju-Nam, Y-S. Chen, J.J. Ojeda, D.W. Allen, N.A. Cross, P.H. E. Gardiner, and N. Bricklebank, *RSC Advances*, 2012, **2**, 10345 - 10351.
- 15 Y. Ju-Nam, N. Bricklebank, D.W. Allen, P. H. E. Gardiner, M. E. Light and M.B. Hursthouse, *Organic and Biomolecular Chemistry*, 2006, **4**, 4345 - 4351.
- 16 Y. Ju-Nam, D. W. Allen, P. H. E. Gardiner and N. Bricklebank, *J. Organomet. Chem.*, 2008, **693**, 3504 - 3508.
- 17 Y-S. Chen, PhD Thesis, Sheffield Hallam University, 2014.
- 18 J-X. Chen, Q-F. Xu, Y. Zhang, S.M. Zain, S.W. Ng and P-P. Lang, *Acta Cryst., Sect. C.*, 2004, **C60**, 0572-0574.
- 19 M. Millard, D. Pathania, Y. Shabaik, L. Taheri, J. Deng and N. Neamati, *PLoS One*, 2010, **5**, e13131.
- 20 T. Sakurai and K. Fujiwara, *British Journal of Pharmacology*, 2001, **132**, 143 - 150.
- 21 (a) A. Hildebrand, I. Sárosi, P. Lönnecke, L. Silaghi-Dumitrescu, M.B. Sárosi, I. Silaghi-Dumitrescu and E. Hey-Hawkins, *Inorg. Chem.*, 2012,

- 51, 7125 - 7133; (b) A-M. Valean, S. Gomex-Ruiz, L. Silaghi-Dumitrescu and E. Hey-Hawkins, *Z. Anorg. Chem.*, 2013, **639**, 1220 - 1226.
- 22 (a) R.W. Ahn, S.L. Barrett, M.R. Raja, J.K. Jozefik, L. Spaho, H. Chen, A.P. Mazar, M.J. Avram, J.N. Winter, L.I. Gordon, L.D. Shea, T.V. O'Halloran and T.K. Woodruff, *PLoS One*, 2013, **8**, e58491–e58491; (b) S-M. Lee, O-S. Lee, T.V. O'Halloran, G.C. Schatz and S.T. Nguyen, *ACS Nano*, 2011, 3961–3969; (c) H. Chen, S. Pazicni, N.L. Krett, R.W. Ahn, J. Penner-Hahn, S.T. Rosen and T.V. O'Halloran, *Angew. Chem., Int. Ed.* 2009, **121**, 9459–9463; (d) H. Chen, R.C. MacDonald, S. Li, N.L. Krett, S.T. Rosen and T.V. O'Halloran, *J. Am. Chem. Soc.* 2006, **128**, 13348–13349.