


CrystEngComm

Accepted Manuscript



This is an *Accepted Manuscript*, which has been through the Royal Society of Chemistry peer review process and has been accepted for publication.

Accepted Manuscripts are published online shortly after acceptance, before technical editing, formatting and proof reading. Using this free service, authors can make their results available to the community, in citable form, before we publish the edited article. We will replace this *Accepted Manuscript* with the edited and formatted *Advance Article* as soon as it is available.

You can find more information about *Accepted Manuscripts* in the [Information for Authors](#).

Please note that technical editing may introduce minor changes to the text and/or graphics, which may alter content. The journal's standard [Terms & Conditions](#) and the [Ethical guidelines](#) still apply. In no event shall the Royal Society of Chemistry be held responsible for any errors or omissions in this *Accepted Manuscript* or any consequences arising from the use of any information it contains.

Cite this: DOI: 10.1039/c0xx00000x

www.rsc.org/xxxxxx

ARTICLE TYPE

Stereoisomeric semiconducting radical cation salts of chiral bis(2-hydroxypropylthio)ethylenedithioTTF with tetrafluoroborate anions

Lee Martin,^{*a} John D. Wallis,^a Milena A. Guziak,^{a,b} Jack Oxspring,^a Jordan R. Lopez,^a Shin'ichi Nakatsuji,^c Jun'ichi Yamada^c and Hiroki Akutsu^c

⁵ Received (in XXX, XXX) Xth XXXXXXXXXX 200X, Accepted Xth XXXXXXXXXX 200X

DOI: 10.1039/b000000x

The new chiral TTF-based donor molecule bis(2-hydroxypropylthio)ethylenedithiotetrafulvalene has produced enantiopure *R,R* and *S,S* radical cation salts with the tetrafluoroborate anion as well as the nearly isostructural *meso*/racemate mixture. The enantiopure *R,R* or *S,S* salts are both 1:1 semiconducting salts with activation energies of 0.19-0.24 eV, both crystallising in the orthorhombic space group *C222*₁. The semiconducting salt containing both *meso* and racemic donor cations has a very similar crystal structure but crystallising in the monoclinic space group *C2/c* ($\beta = 91.39^\circ$) with similar *S...S* interactions but a smaller activation energy of 0.15-0.17 eV. This is in contrast to previous families of this type where the disordered racemate has a larger activation energy than its enantiopure salts.

15 Introduction

The organosulphur donors TTF (**2**) and BEDT-TTF (**3**) have produced a large number of radical cation salts combining a variety of electrical properties.¹ The TTF based molecular conductors provide an excellent opportunity to explore the combination of chirality and conductivity in the same crystal lattice which is of importance in understanding magnetochiral anisotropy as seen in carbon nanotubes.² In order to explore the effect of handedness on a conducting material a number of approaches have been taken to introduce chirality into TTF based conductors. Chiral radical cation salts have included a variety of chiral anions, chiral donors, or have been electrocrystallised from a chiral solvent.³ Differences in the conductivities have been observed between the racemic and enantiopure forms owing to structural disorder in the former. Radical cation salts have previously been synthesized from a variety of chiral anions including [Sb₂(L-tartrate)₂]²⁻, [Fe(croconate)₃]³⁻, [Cr(2,2'-bipy)(oxalate)₂]⁻, TRISPHAT, D-camphorsulfonate, and Co^{III} complexes of optically pure pyridinecarboxamide anions. There is an extensive family of metal trisoxalate salts of the formula BEDT-TTF₄[(NH₄/H₃O)M(oxalate)₃].guest in which the distribution of the Δ and Λ enantiomers of M(oxalate)₃³⁻ (M = Fe, Cr, Co, Al, Ga) leads to different polymorphs exhibiting either superconducting or semiconducting behaviour.⁴ The guest molecules included in the anion layer can lead to different donor packing motifs and thus different conducting properties. When either racemic (*R/S*)- or enantiopure (*S*)-*sec*-phenethyl alcohol is included as a guest molecule isostructural salts are obtained. A more pronounced metal-insulator transition is observed for the racemate owing to the enantiomeric disorder in the *R/S* salt. Crystallisation from chiral solvents has also led to salts of the form (BEDT-TTF)₃[NaCr(oxalate)₃].guest which contain a single enantiomer of the Cr(oxalate)₃ anion through chiral induction.⁵

Dunitz *et al.* synthesized the first enantiopure TTF-based donor molecule with (*S,S,S,S*)-tetramethyl-BEDT-TTF (**4**)⁶. In recent 50 years there has been increased interest in the synthesis of chiral donor molecules, of particular note being the selective transformation of a TTF sulphur atom to its sulfoxide giving a chiral sulfur (**5**)⁷, TTF-oxazolines (**6**)⁸, bis(pyrrolo)TTF (**7**)⁹, and pinene-BEDT-TTF (**8**) (Scheme 1).¹⁰ Effects of structural disorder on conducting properties have also been evidenced in salts of TTF-oxazolines.^{8d,e,11}

We have recently reported the synthesis of the novel enantiopure donor molecule bis((*2S*)-2-hydroxypropylthio)ethylenedithiotetrafulvalene **1** which has both chirality and the potential to form hydrogen bonds in its 2-hydroxypropylthio sidechains (Scheme 2). We previously reported the first examples of radical cation salts from this enantiopure *S,S*-donor molecule including one with the *meso* stereoisomer of the Fe₂(oxalate)₅⁴⁻ anion.¹² Following the method reported previously for the *S,S*-donor of **1** we have synthesised the *R,R* enantiomer and also a statistical mixture of the *meso*/racemate forms (1:1:2 *R,R*:*S,S*:*R,S*), the latter being prepared by using racemic methyl-oxirane as a starting material.

Through electrocrystallisation with the anion BF₄⁻ we have synthesised the first family of radical cation salts from enantiopure ***R,R*-1**, ***S,S*-1** and ***meso*/rac-1**. All three materials are semiconducting, and it is of interest that the two enantiopure stereoisomers have similar activation energies whilst the almost isostructural *meso*/racemate has a smaller activation energy and a slightly higher room temperature conductivity. This is opposite to what was observed previously in TTF-oxazoline-PF₆^{8d,e}, TM-BEDT-TTF-I₃^{6e} and BEDT-TTF₄[(NH₄)Fe(oxalate)₃].*sec*-phenethyl alcohol⁵ where the structural disorder had the effect of reducing the conductivity. Attempts to produce crystals from a 50:50 mixture of enantiopure ***RR*-1**:***SS*-1** donor mixture did not

produce crystals suitable for X-ray or resistivity measurement.

Experimental

Enantiopure donor **R,R-1** and the mixture of racemic and *meso* forms of **1** were synthesized using the method described previously for **S,S-1** starting from the *R*- or *rac*-methyloxirane respectively.¹² At no stage in the syntheses could the racemic and *meso* isomers be separated. Single crystals of **(S,S)-1.BF₄**, **(R,R)-1.BF₄**, and **meso/rac-1.BF₄** were grown by electrocrystallisation using donor **(S,S)-1**, **(R,R)-1**, and the *meso*/racemic mixture of **1**, respectively, as follows:

100 mg of tetrabutylammonium tetrafluoroborate was dissolved in 20 ml of chlorobenzene and then added to the cathode side of a H-shaped cell. 10mg of donor **1** was dissolved in 20 ml of chlorobenzene and added to the anode side of the H-shaped cell. Chlorobenzene and tetrabutylammonium tetrafluoroborate were purchased from Aldrich and used as received.

The H-shaped cells had two platinum electrodes separated by a porous glass frit to prevent contamination. The electrodes were cleaned by applying a voltage across the electrodes in 1 M H₂SO₄ in each direction resulting in the evolution of H₂ and O₂ at the electrodes. Finally the electrodes were washed in distilled water and thoroughly dried. The cells were fixed inside sand-filled compartments on a vibration-free table and kept at a constant temperature of 293 K.

A current of 0.1 μA was passed through the platinum electrodes and black needle crystals of the **1.BF₄**⁺ radical cation salts grew on the anode over 3 weeks.

Four-probe DC transport measurements were made on several crystals of **(S,S)-1.BF₄**, **(R,R)-1.BF₄**, and **meso/rac-1.BF₄** using a HUSO HECS 994C multi-channel conductometer. Gold wires (15 μm diameter) were attached to the crystal, and the attached wires were connected to an four-pin integrated circuit plug with gold conductive cement.

Table 1 Crystallographic data for BF₄ salts of **1**[†]

	meso/rac-1.BF₄	(S,S)-1.BF₄	(R,R)-1.BF₄
Formula	C ₁₄ H ₁₈ O ₂ S ₈ .BF ₄	C ₁₄ H ₁₈ O ₂ S ₈ .BF ₄	C ₁₄ H ₁₈ O ₂ S ₈ .BF ₄
<i>M_r</i> / g mol ⁻¹	561.58	561.58	561.58
Temp / K	300.1	293.1	293.1
<i>μ</i> / cm ⁻¹	8.416	8.416	8.401
Crystal System	Monoclinic	Orthorhombic	Orthorhombic
Space Group	<i>C2/c</i>	<i>C22₂</i>	<i>C22₂</i>
<i>a</i> /Å	7.807(3)	7.8100(13)	7.8172(13)
<i>b</i> /Å	21.223(6)	21.238(4)	21.232(4)
<i>c</i> /Å	26.992(7)	26.989(5)	26.987(5)
<i>α</i> /°	90	90	90
<i>β</i> /°	91.394(7)	90	90
<i>γ</i> /°	90	90	90
<i>V</i> / Å ³	4471(3)	4476.6(13)	4479.1(13)
<i>Z</i>	8	8	8
<i>ρ</i> / g cm ⁻³	1.669	1.666	1.665
Flack parameter		-0.08(15)	-0.03(17)
<i>R</i> 1 [<i>I</i> > 2σ(<i>I</i>)]	0.106	0.0486	0.0603
<i>wR</i> [all data]	0.335	0.123	0.142
CCDC No.	981724	981726	981725

40

Results and Discussion

Both **(S,S)-1.BF₄** and **(R,R)-1.BF₄** crystallise in the orthorhombic system in chiral space group *C22₂* (Fig. 1), whilst **meso/rac-1.BF₄** crystallises in monoclinic *C2/c* (Fig. 2). The crystals of all three salts have one donor molecule and two crystallographically independent BF₄⁻ anions, but both anions lie on symmetry elements, a 2-fold axis for the enantiomers and a centre of symmetry for the *meso*/racemate. For the enantiopure salts the BF₄⁻ anions are disordered and for the *meso*/rac-salt they are placed on centres of symmetry of the *C2/c* space group, and thus must appear disordered.

In all three salts the donor molecules form stacks in the *a* direction (Fig. 3-5) with neighbouring stacks segregated in the *b* direction by BF₄⁻ anions. In the enantiopure salts, the best planes of donor cations lie at *ca* 68° to the stacking axis. Pairs of donors, related by a 2-fold axis, are dimerised face-to-face with short S...S contacts between the four central TTF sulfur atoms as shown in Fig. 5. S...S contacts are similar in both enantiopure and *rac/meso* salts. The plane-plane distance between donors in all three salts are similar: *ca* 3.37 Å within a pair, and *ca* 3.77 Å between pairs, despite the different crystal systems, and adjacent pairs are slipped by *ca* 2.3 Å, while within a pair the slip distance is *ca* 0.9 Å (Table 3).

Table 2 Short S...S contacts for BF₄ salts of **1**

	meso/rac-1.BF₄	(S,S)-1.BF₄	(R,R)-1.BF₄
S3...S5	3.560(4) Å	3.557(2) Å	3.562(2) Å
S4...S6	3.476(4) Å	3.466(2) Å	3.468(2) Å

The central C=C bond lengths in all cases are close to the value expected for a TTF donor charge of 1⁺: **(S,S)-1.BF₄** 1.400(5) Å, **(R,R)-1.BF₄** 1.398(6) Å, and **meso/rac-1.BF₄** 1.389(10) Å.

For the enantiopure salts the two hydroxylated side chains adopt different conformations, one lies in the donor plane and directed out from the donor towards a BF₄⁻ anion, while the other bends down under the donor. Dimer pairs are likely to be connected by hydrogen bonding, since two symmetry related oxygen atoms from the latter type of side chains lie 2.877(6) Å apart in the *R,R* enantiomer (2.876(5) Å in the *S,S*). It was not possible to detect hydroxyl hydrogen atom positions from the difference Fourier maps arising from the room temperature diffraction data for either enantiomer. There is a long O...H-C contact from the other side chain to the ethylene bridge of a donor molecule (2.57 Å *R,R*-isomer). For the *rac/meso* salt, the overall conformation of the donors is very similar to that in the enantiomeric salts, but there are two positions for each hydroxyl oxygen atom. For the side chain directed out for the donor, both O positions are directed towards BF₄⁻ anions (O...F: 2.671, 2.922 Å). For the other side chain, one oxygen position corresponds to those involved in a hydrogen bond between donor pairs, while the other is directed towards a BF₄⁻ anion (O...F: 2.671 Å).

Table 3 The plane-plane distance of D₁ and D₂ (see Fig. 5) and the corresponding slip distances of S₁ and S₂.¹³

	D ₁	D ₂	S ₁	S ₂
<i>meso/rac</i> -1.BF ₄	3.378 Å	3.658 Å	0.957 Å	2.343 Å
(<i>S,S</i>)-1.BF ₄	3.368 Å	3.665 Å	0.974 Å	2.385 Å
(<i>R,R</i>)-1.BF ₄	3.371 Å	3.665 Å	0.978 Å	2.391 Å

Four-probe transport measurements performed parallel to the longest axis of several needle-shaped crystals show that (*S,S*)-1.BF₄, (*R,R*)-1.BF₄, and *meso/rac*-1.BF₄ are all semiconducting (Fig. 6). Room temperature resistivities are similar but the activation energy for the racemate is significantly smaller than for either the *S,S* or *R,R*. It has been observed recently in the case of DM-EDT-TTF-PF₆ that the racemic salt is metallic whilst the enantiopure salts are semiconducting due to the differences between the packing.¹⁴ However in the case of **1** although the enantiopure and *meso/racemate* have different crystal systems they are almost isostructural, differing slightly in the donor molecule slip distances (Fig. 5).

Table 4 E_a and room temperature resistivity values for crystals of (*S,S*)-1.BF₄, (*R,R*)-1.BF₄, and *meso/rac*-1.BF₄

<i>meso/rac</i> -1.BF ₄	(<i>S,S</i>)-1.BF ₄	(<i>R,R</i>)-1.BF ₄
0.156 eV	0.218 eV	0.244 eV
1.6 x 10 ³ Ohm cm	1.3 x 10 ³ Ohm cm	2.9 x 10 ⁴ Ohm cm
0.167 eV	0.205 eV	0.202 eV
8.6 x 10 ² Ohm cm	2.0 x 10 ³ Ohm cm	1.1 x 10 ³ Ohm cm

Conclusions

We report the first family of semiconducting salts of the enantiopure donor bis(2-hydroxypropylthio)ethylenedithio-tetrathiafulvalene and observe a lower activation energy for the racemic analogue compared to both single enantiomers. This new donor molecule shows promise for the synthesis of many families of conducting chiral radical cation salts to investigate magnetochiral anisotropy. The hydrogen bonding ability of the 2-hydroxypropylthio side-chains, with the multitude of anions available has the potential to produce a variety of novel TTF packing arrangements.

Acknowledgements

LM and SN would like to thank the Royal Society for an International Joint Project Grant (JP0869972) and a Royal Society Research Grant (RG100853). LM would also like to thank the Royal Society of Chemistry for a Journal Grant for International Authors. JDW would like to thank EPSRC for grant EP/C510488/1.

Notes and references

^a School of Science and Technology, Nottingham Trent University, Clifton Lane, Nottingham, NG11 8NS, United Kingdom; E-mail: lee.martin@ntu.ac.uk

^b Low Temperature Condensed State Physics, Institute for Material Research, Tohoku University, Katahira 2-1-1, Sendai 980-8577, Japan

^c Graduate School of Material Science, University of Hyogo, Kamigori-cho, Ako-gun, Hyogo, 678-1297, Japan

† X-ray single crystal diffraction measurements were performed by a Rigaku Mercury 2 CCD configured with Rigaku MicroMax-007HF generator and VariMax confocal mirror using MoK α radiation ($\lambda = 0.71073$ Å). Structures were solved by direct methods (SIR2004, SIR2008 and SIR92 for *meso/rac*-, (*S,S*)- and (*R,R*)-salts, respectively and refined by full-matrix least squared techniques based on F^2 (SHELX97). Non-hydrogen atoms were refined with anisotropic displacement parameters apart from BF₄ anions of *meso/rac*-salt, which were refined with isotropic displacement parameters.

1 a) E. Coronado, J. R. Galan-Mascaros, C. J. Gomez-Garcia and V. Laukhin, *Nature*, 2000, **408**, 447; b) A. Alberola, E. Coronado, J. R. Galan-Mascaros, C. Gimenez-Saiz and C. Gomez-Garcia, *J. Am. Chem. Soc.* 2003, **125**, 40, 10774; c) A. Akutsu-Sato, H. Akutsu, S. S. Turner, P. Day, M. R. Probert, J. A. K. Howard, T. Akutagawa, S. Takeda, T. Nakamura and T. Mori, *Angew. Chem., Int. Ed.*, 2005, **44**, 292.

2 V. Krstić, S. Roth, M. Burghard, K. Kern and G. L. J. A. Rikken, *J. Phys. Chem.*, 2002, **117**, 11315.

3 N. Avarvari and J. D. Wallis, *J. Mater. Chem.*, 2009, **19**, 4061.

4 a) L. Martin, S. S. Turner, P. Day, K. M. Abdul Malik, S. J. Coles and M. B. Hursthouse, *J. Chem. Soc., Chem. Commun.*, 1999, 513; b) L. Martin, S.S. Turner, P. Day, P. Guionneau, J.K. Howard, D.E. Hibbs, M.E. Light, M.B. Hursthouse, M. Uruichi and K. Yakushi, *Inorg. Chem.*, 2001, **40**, 1363; c) E. Coronado, J. R. Galán-Mascarós, C. J. Gómez-García, A. Murcia-Martinez and E. Canadell, *Inorg. Chem.*, 2004, **43**, 8072; d) A. M. Madalan, E. Canadell, P. Auban-Senzier, D. Brânzea, N. Avarvari and M. Andruh, *New J. Chem.*, 2008, **32**, 333; e) M. Clemente-León, E. Coronado, C. J. Gómez-García, A. Soriano-Portillo, S. Constant, R. Frantz and J. Lacour, *Inorg. Chim. Acta*, 2007, **360**, 955; f) C. J. Gómez-García, E. Coronado, S. Curreli, Carlos Giménez-Saiz, P. Deplano, M. L. Mercuri, L. Pilia, A. Serpe, C. Faulmann and E. Canadell, *Chem. Commun.*, 2006, 4931; g) M. Brezgunova, K.-S. Shin, P. Auban-Senzier, O. Jeannin and M. Fourmigué, *Chem. Commun.*, 2010, **46**, 3926; h) N. P. Chmel, L. E. N. Allana, J. M. Becker, G. J. Clarkson, S. S. Turner and P. Scott, *Dalton Trans.*, 2011, **40**, 1722.

5 a) L. Martin, P. Day, H. Akutsu, J.-i. Yamada, S.-i. Nakatsuji, W. Clegg, R. W. Harrington, P. N. Horton, M. B. Hursthouse, P. McMillan and S. Firth, *CrystEngComm*, 2007, **10**, 865; b) L. Martin, P. Day, S.-i. Nakatsuji, J.-i. Yamada, H. Akutsu and P. Horton, *CrystEngComm*, 2010, **12**, 1369; c) L. Martin, S.-i. Nakatsuji, J.-i. Yamada, H. Akutsu and P. Day, *J. Mater. Chem.*, 2010, **20**, 2738.

6 a) J. D. Dunitz, A. Karrer and J. D. Wallis, *Helv. Chim. Acta*, 1986, **69**, 69; b) A. Karrer, J. D. Wallis, J. D. Dunitz, B. Hilti, C. W. Mayer, M. Burkle and J. Pfeiffer, *Helv. Chim. Acta*, 1987, **70**, 942; c) J. R. Galán-Mascarós, E. Coronado, P. A. Goddard, J. Singleton, A. I. Coldea, J. D. Wallis, S. J. Coles and A. Alberola, *J. Am. Chem. Soc.*, 2010, **132**, 9271; d) F. Riobé, F. Piron, C. Réthoré, A. M. Madalan, C. J. Gómez-García, J. Lacour, J. D. Wallis and N. Avarvari, *New J. Chem.*, 2009, **35**, 2279; e) F. Pop, S. Laroussi, T. Cauchy, C. J. Gómez-García, J. D. Wallis and N. Avarvari, *Chirality*, 2013, **25**, 466.

- 7 a) M. Chas, M. Lemarié, M. Gulea and N. Avarvari, *Chem. Commun.*, 2008, 220; b) M. Chas, F. Riobé, R. Sancho, C. Minguillón and N. Avarvari, *Chirality*, 2009, **21**, 818.
- 5
- 8 a) C. Réthoré, M. Fourmigué and N. Avarvari, *Chem. Commun.*, 2004, 1384; b) C. Réthoré, M. Fourmigué and N. Avarvari, *Tetrahedron*, 2005, **61**, 10935; c) C. Réthoré, A. Madalan, M. Fourmigué, E. Canadell, E. B. Lopes, M. Almeida, R. Clérac and N. Avarvari, *New J. Chem.*, 2007, **31**, 1468; d) C. Réthoré, N. Avarvari, E. Canadell, P. Auban-Senzier and M. Fourmigué, *J. Am. Chem. Soc.*, 2005, **127**, 5748; e) A. M. Madalan, C. Réthoré, M. Fourmigué, E. Canadell, E. B. Lopes, M. Almeida, P. Auban-Senzier and N. Avarvari, *Chem. Eur. J.*, 2010, **16**, 528.
- 10
- 9 S. Yang, A. C. Brooks, L. Martin, P. Day, H. Li, L. Male, P. Horton and J. D. Wallis, *CrystEngComm*, 2009, **11**, 993.
- 10 S. Yang, A. C. Brooks, L. Martin, P. Day, M. Pilkington, W. Clegg, R. W. Harrington, L. Russo, J. D. Wallis, *Tetrahedron*, 2010, **66**, 6977.
- 20
- 11 N. Avarvari, *Rev. Roum. Ch.*, 2009, **54**(6), 411.
- 25
- 12 I. Awgheda, S. Krivickas, S. Yang, L. Martin, M. A. Guziak, A. C. Brooks, F. Pelletier, M. Le Kerneau, P. Day, P. Horton, H. Akutsu and J. D. Wallis, *Tetrahedron*, 2013, **69**, 8738.
- 13 T. Mori, *Bull. Chem. Soc. Jpn.*, 1998, **71**, 2509.
- 30
- 14 F. Pop, P. Auban-Senzier, A. Frąckowiak, K. Ptaszyński, I. Olejniczak, J. D. Wallis, E. Canadell and N. Avarvari, *J. Am. Chem. Soc.*, 2013, **135**, 17176.

Scheme 1

Scheme 2

Fig. 1 ORTEP image of (a) **(S,S)-1.BF₄** and (b) **(R,R)-1.BF₄**.


45 **Fig. 2** ORTEP image of **meso/rac-1.BF₄**

Fig.3 Crystal structure of **(S,S)-1.BF₄** viewed down the *a* axis. Hydrogen atoms removed for clarity.


50 **Fig.4** Crystal structure of **(S,S)-1.BF₄** viewed down the *b* axis. Hydrogen atoms removed for clarity.

Fig.5 Face-to-face packing of donors viewed down the *b* axis showing close S...S contacts for **(S,S)-1.BF₄**. BF₄ anions have been removed for clarity.


Fig.6 Temperature dependence of electrical resistivity $\rho/\rho(\text{RT})$ for two single crystals (A and B) for each of **(S,S)-1.BF₄**, **(R,R)-1.BF₄**, and **meso/rac-1.BF₄**.




2




3




4




5




6





7





8

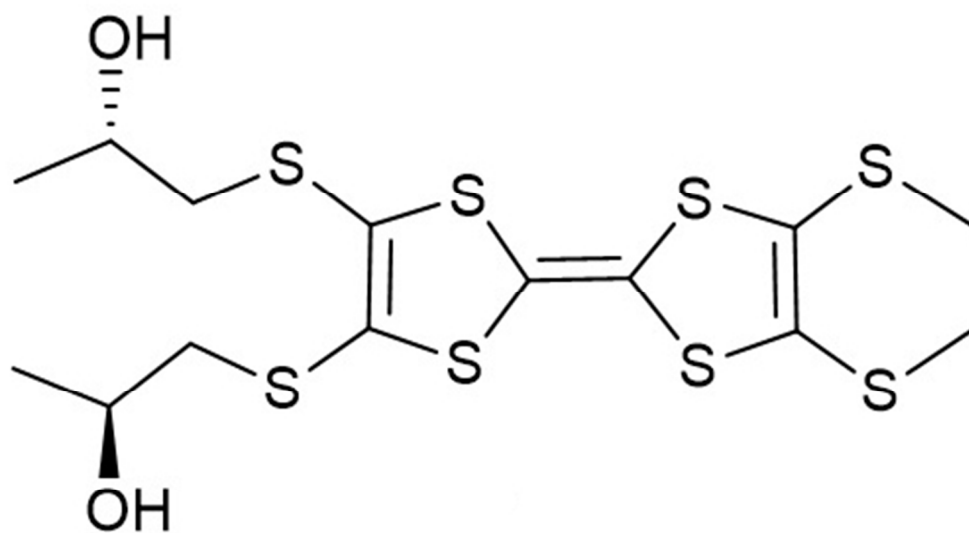

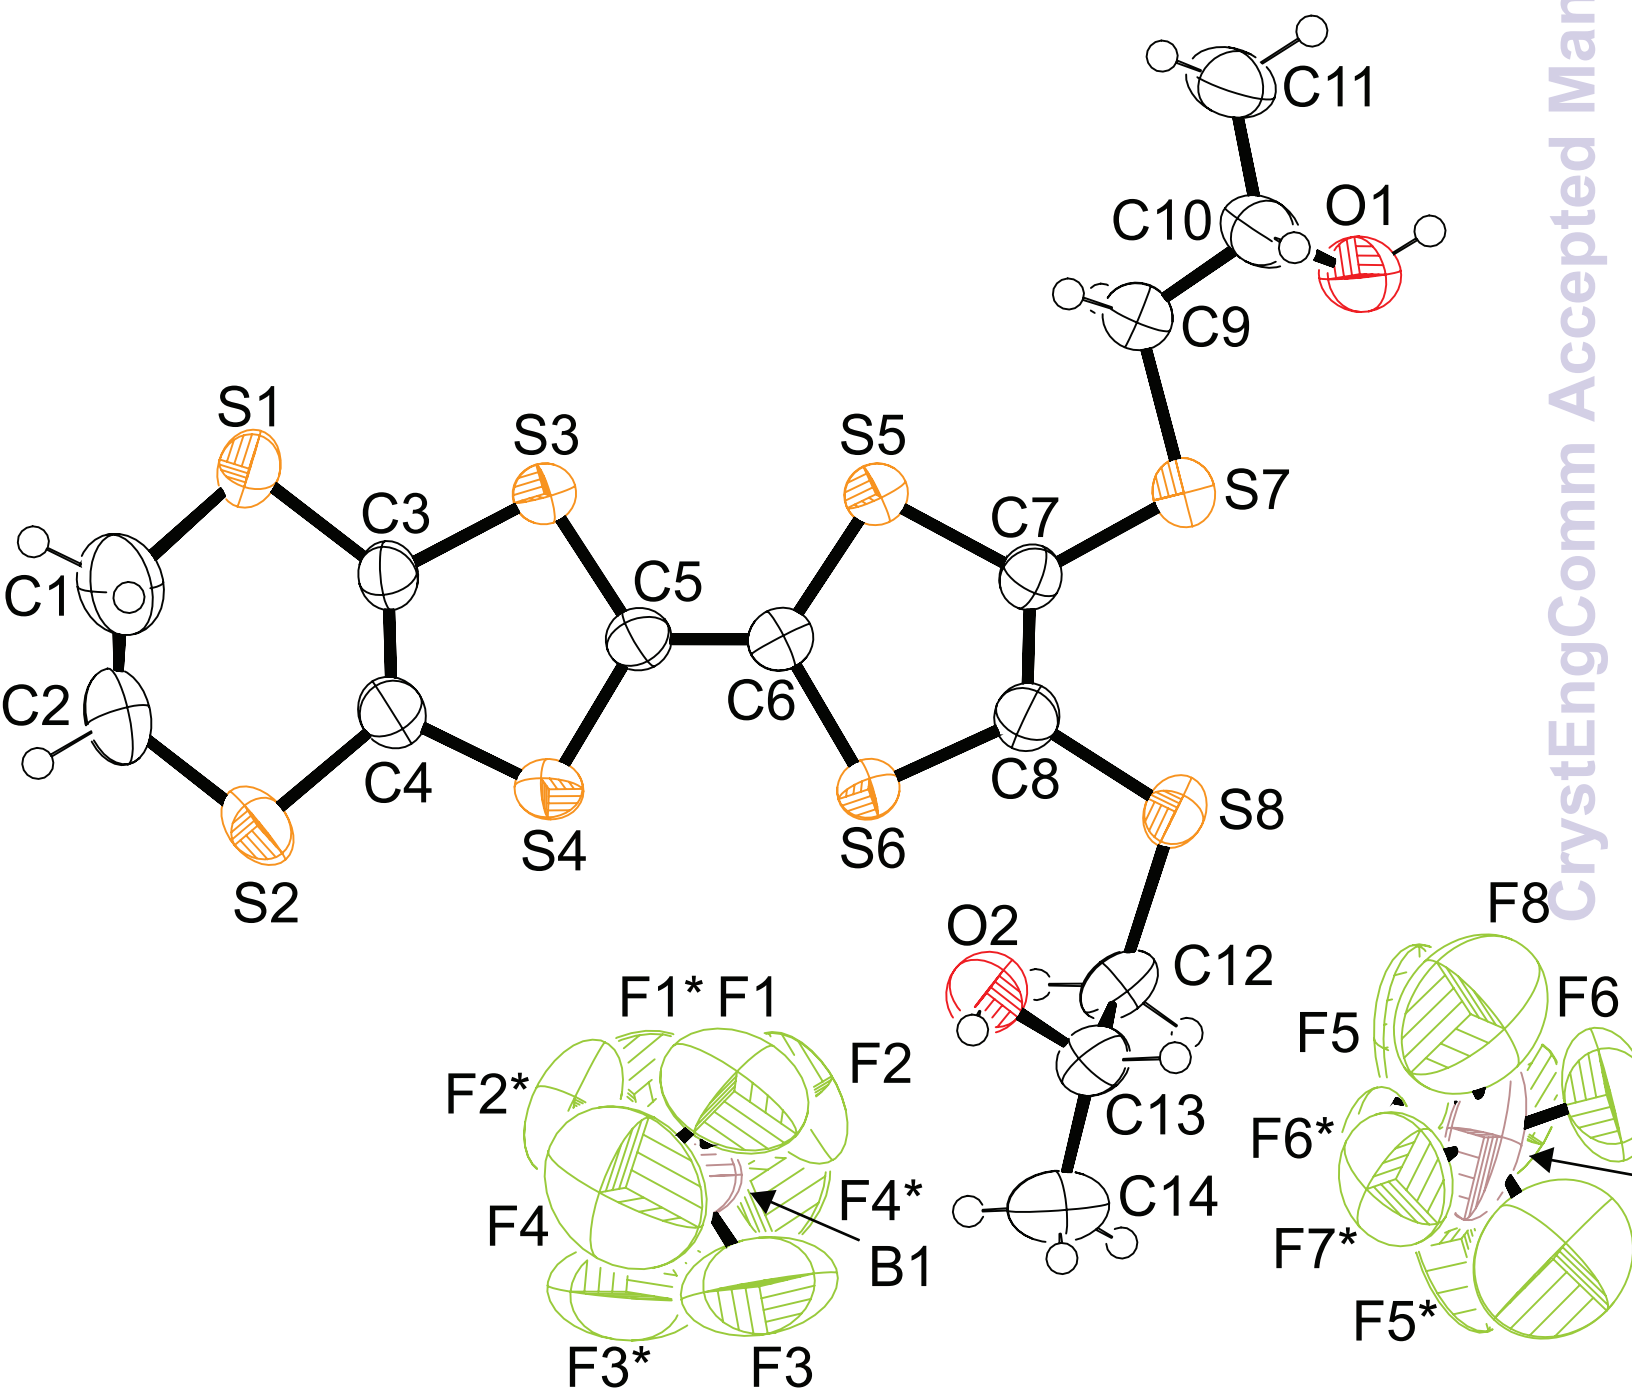


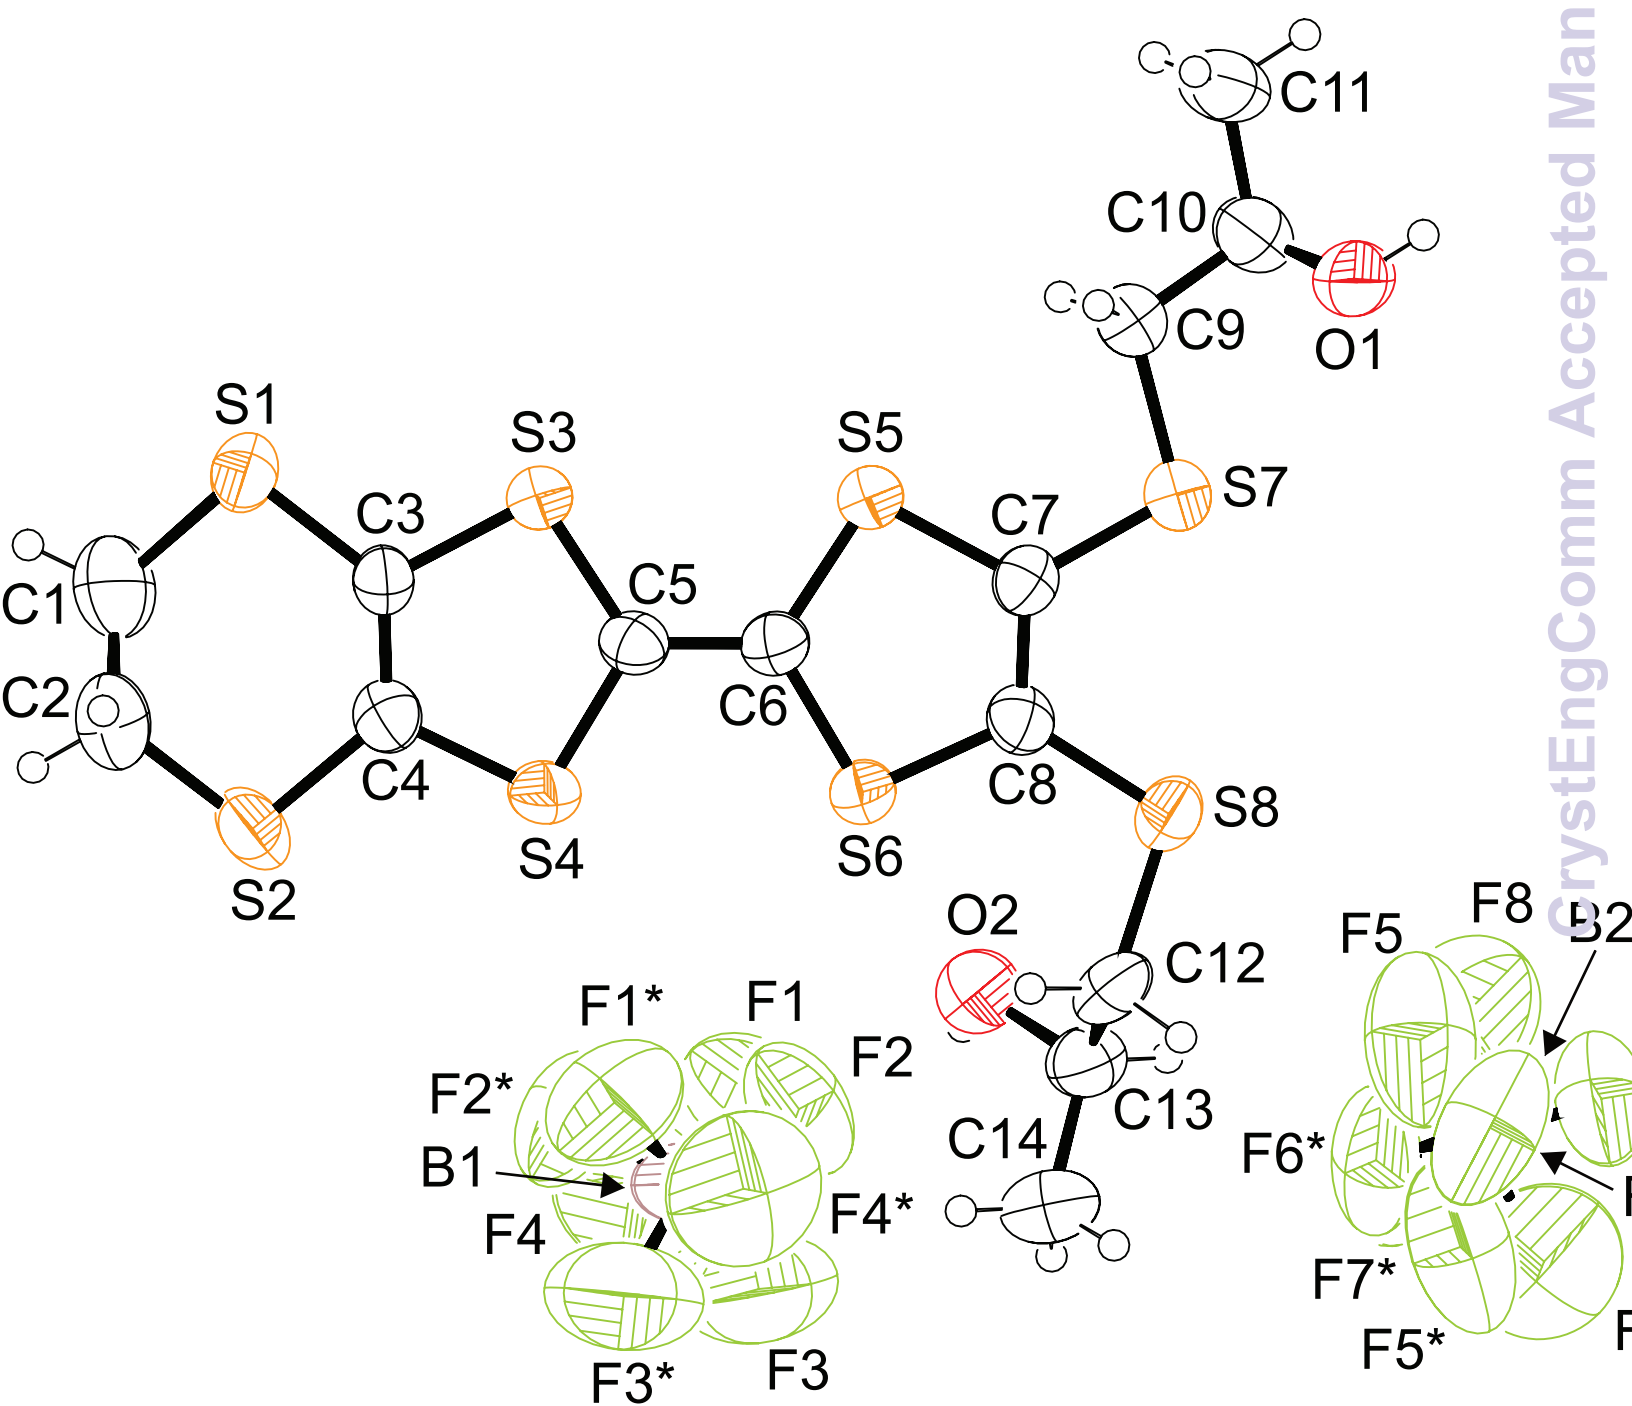

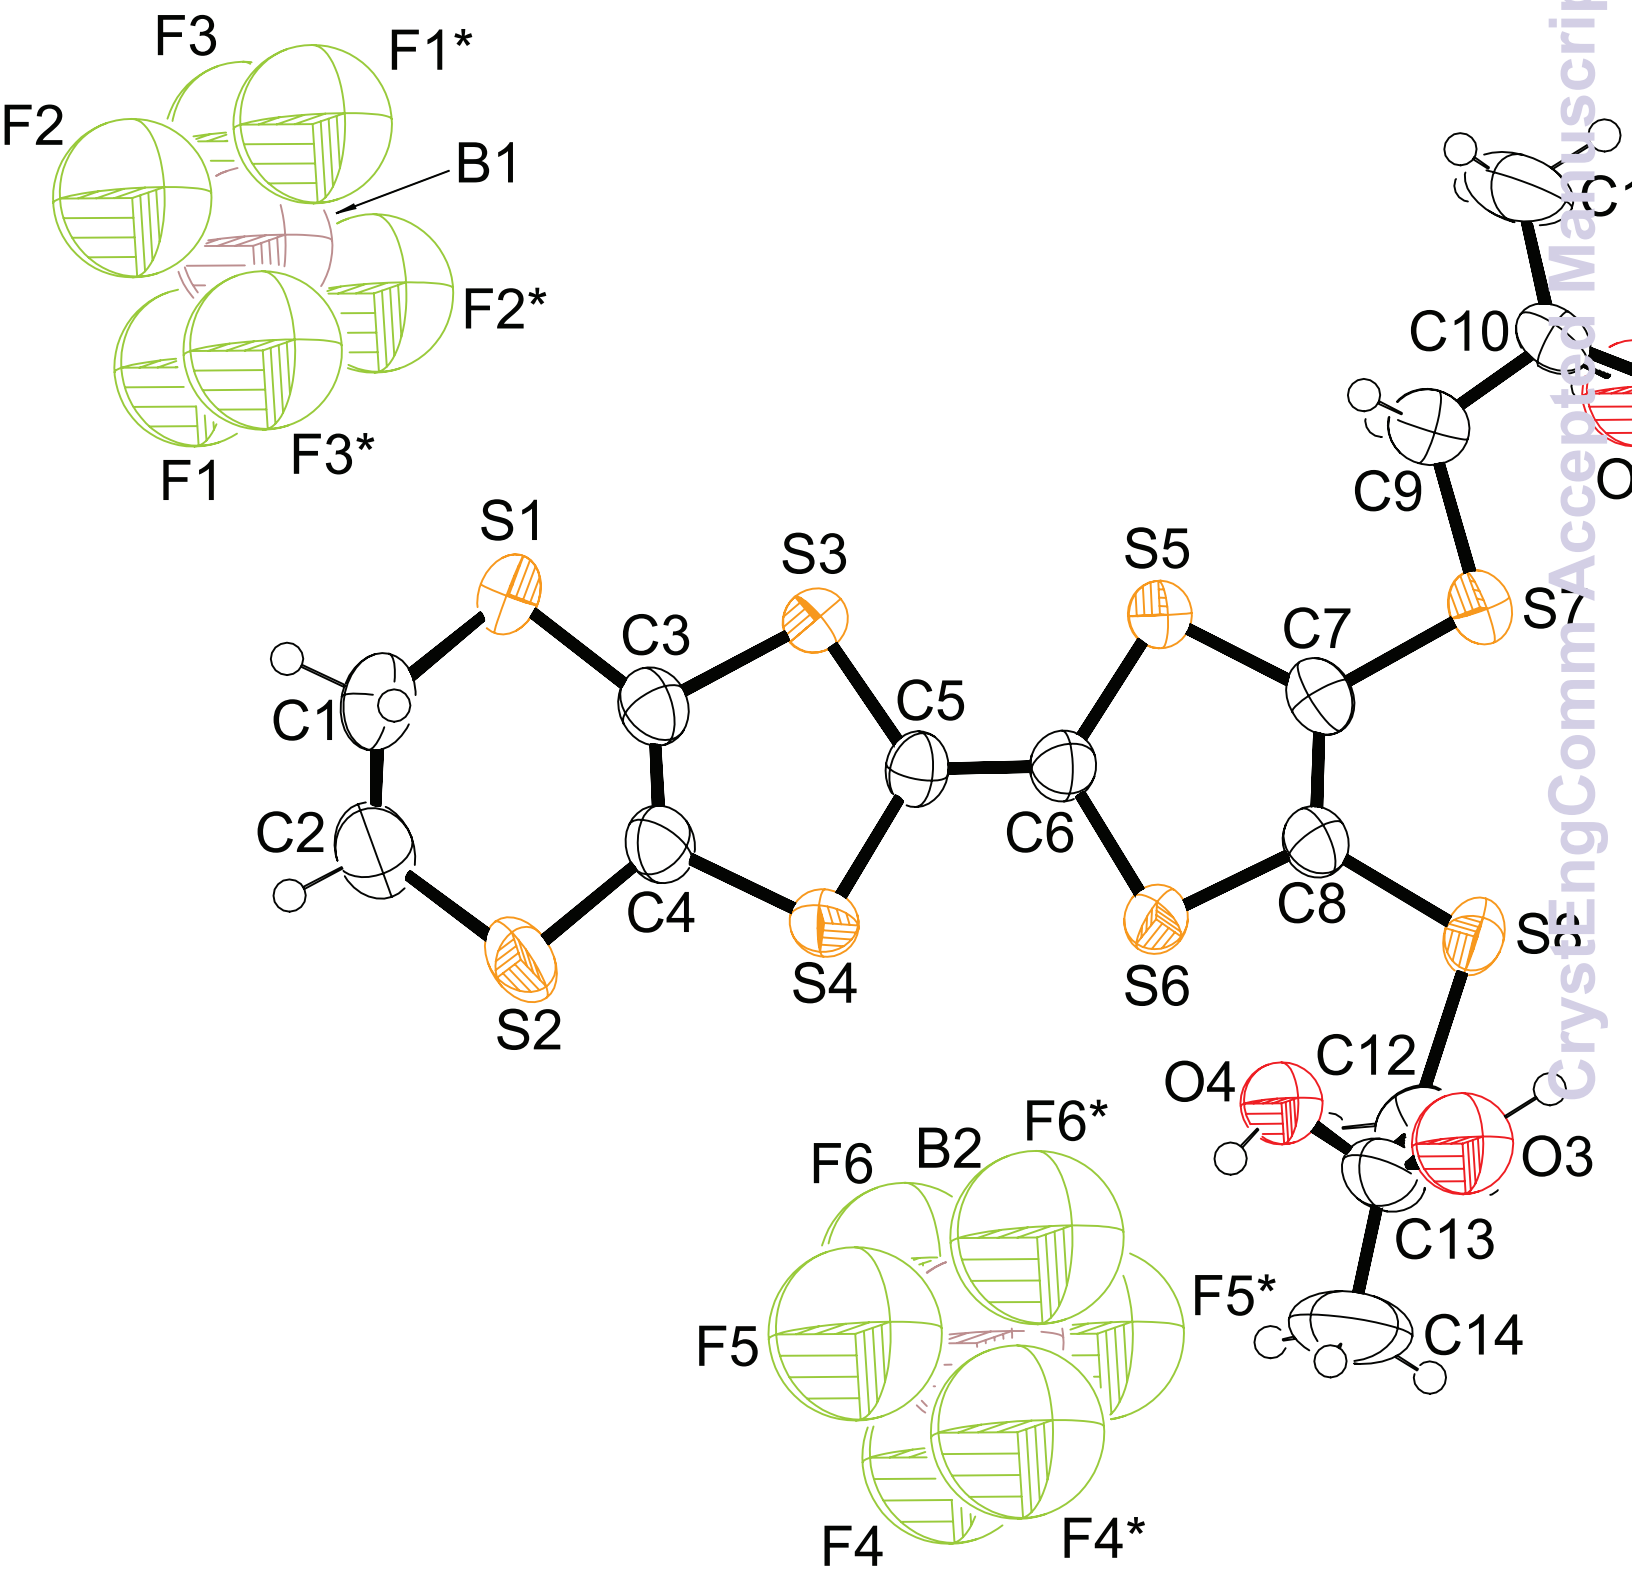


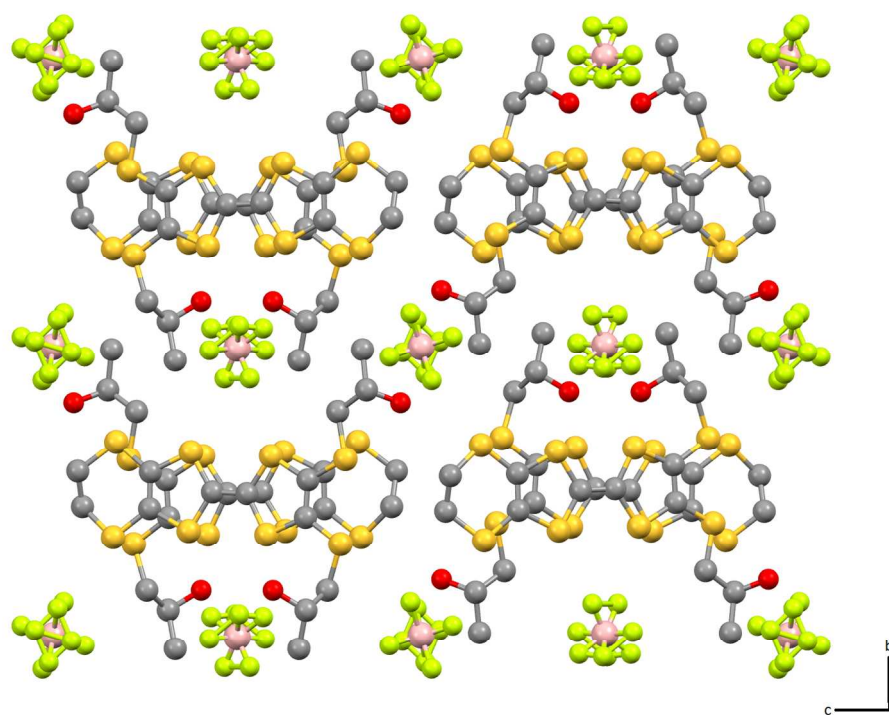


367x280mm (120 x 120 DPI)

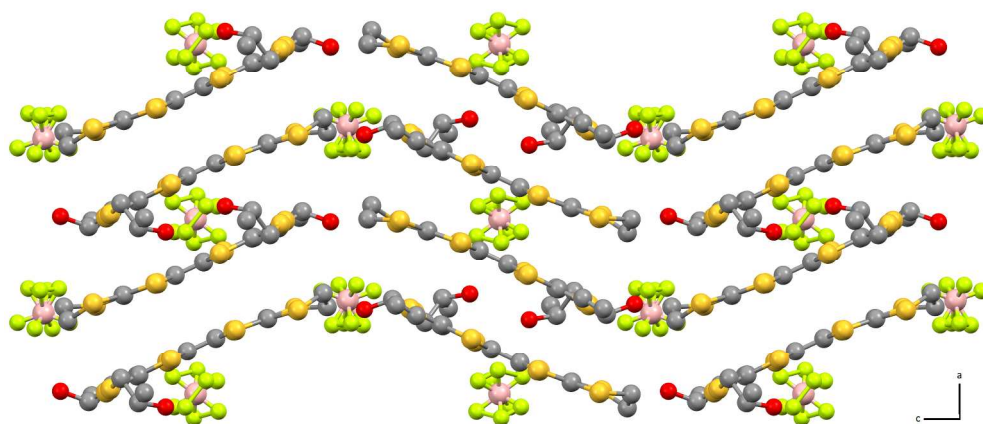


555x260mm (120 x 120 DPI)

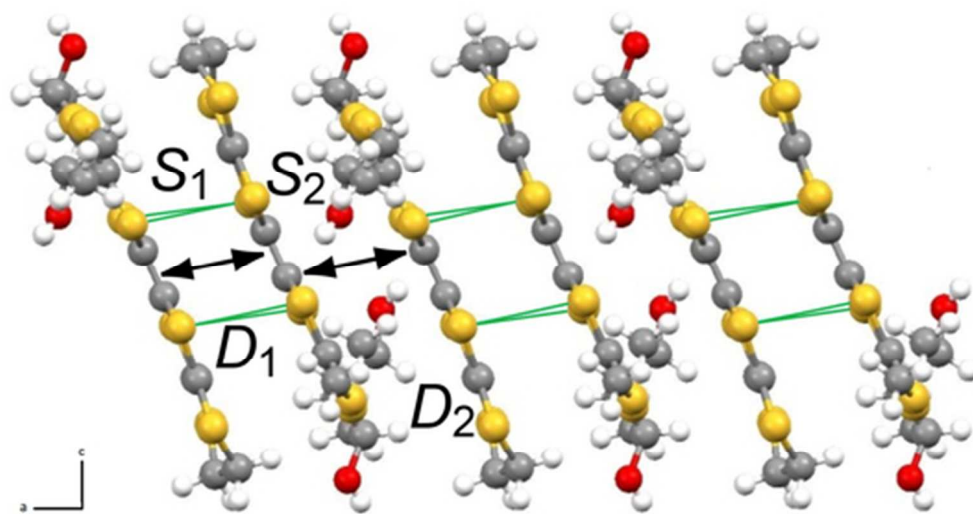

45x25mm (300 x 300 DPI)

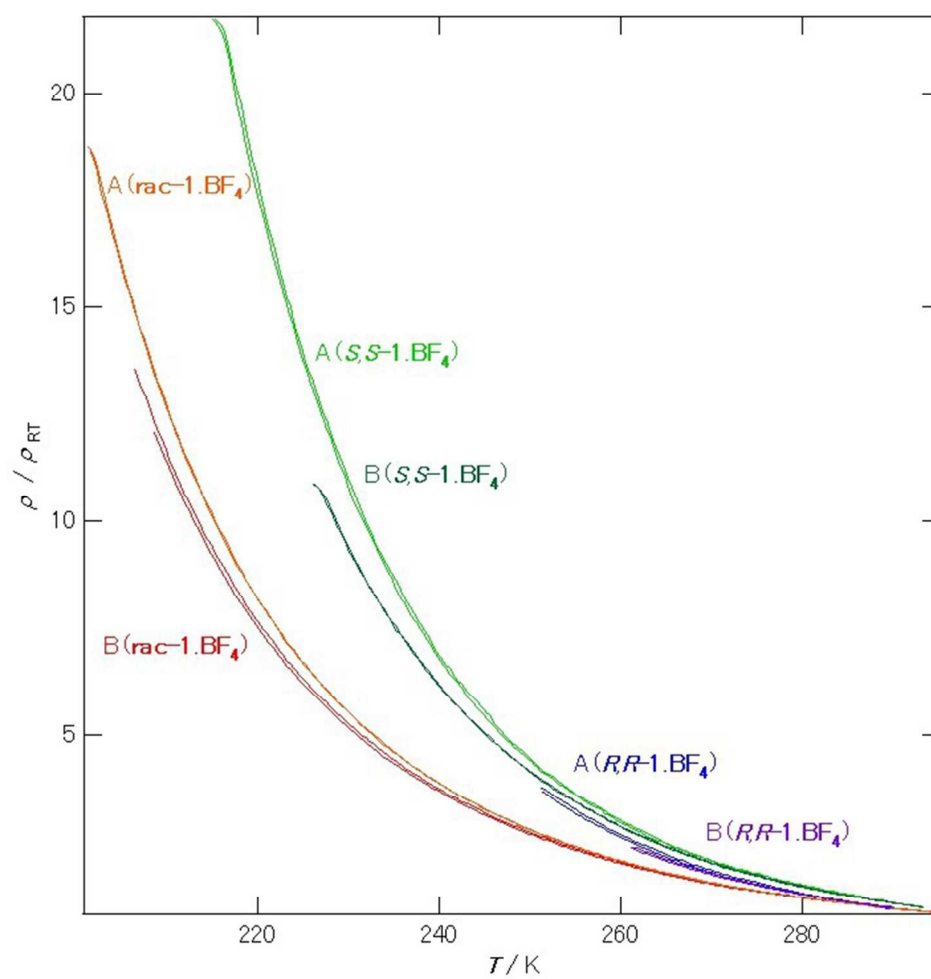

266x266mm (72 x 72 DPI)

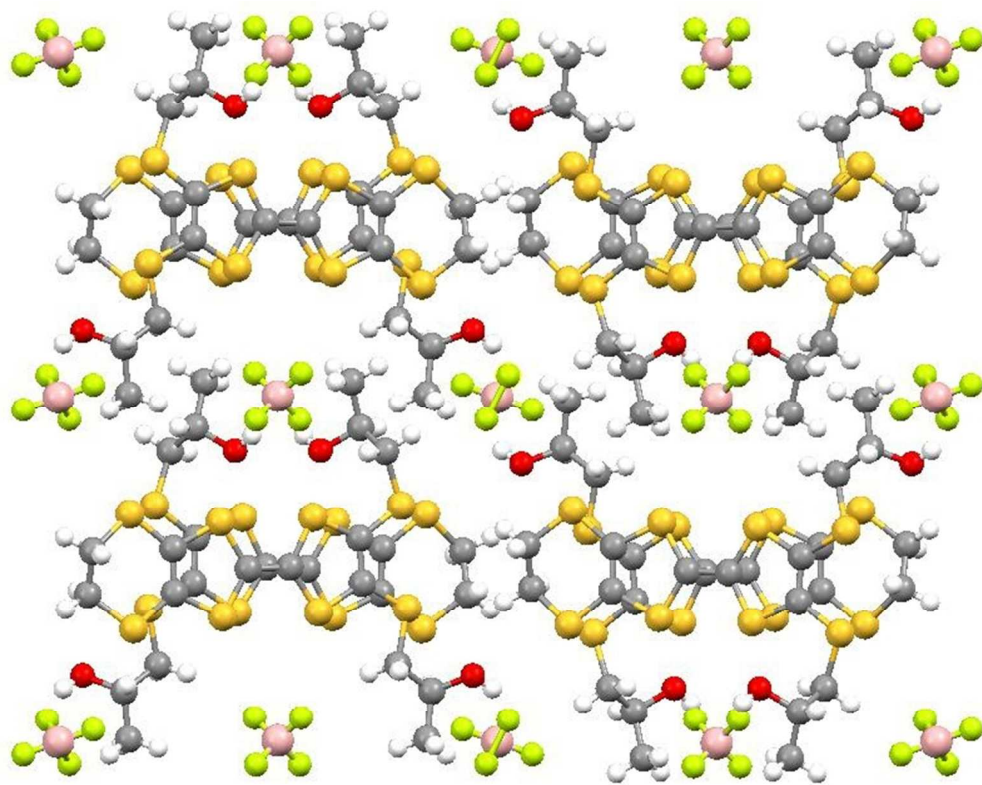

169x137mm (120 x 120 DPI)