

CrystEngComm

Accepted Manuscript



This is an *Accepted Manuscript*, which has been through the Royal Society of Chemistry peer review process and has been accepted for publication.

Accepted Manuscripts are published online shortly after acceptance, before technical editing, formatting and proof reading. Using this free service, authors can make their results available to the community, in citable form, before we publish the edited article. We will replace this *Accepted Manuscript* with the edited and formatted *Advance Article* as soon as it is available.

You can find more information about *Accepted Manuscripts* in the [Information for Authors](#).

Please note that technical editing may introduce minor changes to the text and/or graphics, which may alter content. The journal's standard [Terms & Conditions](#) and the [Ethical guidelines](#) still apply. In no event shall the Royal Society of Chemistry be held responsible for any errors or omissions in this *Accepted Manuscript* or any consequences arising from the use of any information it contains.

Structural and chemical changes of Zn-doped CeO₂ nanocrystals upon annealing at ultra-high temperatures

Cite this: DOI: 10.1039/x0xx00000x

Fangjian Lin,^a Ivo Alxneit^{*a} and Alexander Wokaun^b

Received 00th xxxx,
Accepted 00th xxxx

DOI: 10.1039/x0xx00000x

www.rsc.org/

The structure of doped ceria plays an important role in its chemical reactivity and catalytic performance. However, for the majority of the dopants studied, whether a monophasic solid solution is formed or not is typically determined only by standard x-ray diffraction (XRD). In-depth structural characterization is lacking. In this paper we have prepared Zn-doped ceria nanocrystals exhibiting twice the oxygen storage capacity (OSC) of pure ceria. X-ray photoelectron spectroscopy (XPS) shows that the material is chemically inhomogeneous with zinc enrichment in the surface layer. X-ray fluorescence (XRF) reveals significant compositional inhomogeneity of the material after annealing in air at 1300 °C for 24 h. The standard structural characterization of this material using room temperature XRD and transmission electron microscopy (TEM) fails to reveal its correct phase composition. Based on clear evidence from *in-situ* high temperature XRD we show that, after calcination at 500 °C, the material is not monophasic: x-ray amorphous ZnO is present within the material. The amorphous ZnO crystallizes at 800 °C and undergoes second-stage incorporation at even higher temperatures. This second-stage incorporation is not complete after annealing and trace amounts of ZnO remain according to synchrotron-based XRD. Our work provides valuable insight into the incorporation mechanism of zinc into the ceria lattice, and in particular, raises some doubts on the phase compositions reported in many previous studies on doped ceria.

Introduction

Ceria (CeO₂) is one of the most important functional rare earth oxides and widely used in a number of technological applications, particularly in catalysis.^[1] A key feature of ceria is its oxygen storage capacity (OSC),^[2] resulting from its reversible and relatively easy reduction to the non-stoichiometric CeO_{2-δ}. Ceria and related oxides are applied as catalysts or as support oxides, notably in three-way catalytic converters that catalyse CO oxidation,^[3-5] soot oxidation,^[6-8] and NO_x reduction.^[9,10] Ceria has also been exploited as an electrolyte for solid oxide fuel cells (SOFCs)^[11,12] and recently as a redox material for two-step thermochemical cycles to split H₂O and CO₂ to H₂ and CO.^[13-15]

A lot of effort has been devoted to improving the physico-chemical properties of ceria by introducing heterocations into its lattice. Doping ceria with aliovalent cations such as Ca²⁺, Sr²⁺, Y³⁺, Sm³⁺, and Gd³⁺ was shown to significantly increase its ionic conductivity,^[16] which is required for the electrolytes of SOFCs. Enhanced OSC and lattice oxygen mobility of ceria by doping Pr³⁺ and La³⁺ promote their catalytic activities for soot^[6,7,17] and CO oxidation.^[18,19] Thermochemical fuel

production is enhanced by doping ceria with Zr⁴⁺,^[20-22] or a combination of Zr⁴⁺ and Gd³⁺/La³⁺.^[22] DFT calculations have shown that the incorporation of heterocations can introduce structural distortions in the lattice and thus enhance the OSC of ceria,^[23,24] revealing a close link between the structure of doped ceria and its chemical properties.

Despite the important role of the structure of doped ceria, the focus in the literature is mostly on its chemical properties and catalytic activities. For the majority of the dopants studied, the formation of single-phased solid solution (or not) is typically determined only by x-ray powder diffraction (XRD). In-depth structural characterization is lacking. For instance, among the few available reports on Zn-doped ceria, the focus has been on its UV shielding property,^[25] and its activity for CO oxidation.^[26-28] A doping level of 56.1% has been reported based only on standard XRD.^[25] This number seems very high in the view of very different charge and radius of Zn²⁺ with respect to Ce⁴⁺. Recently, Schmale et al. estimated a solubility limit of 3±0.7% of Zn²⁺ in ceria based also on XRD.^[29] Thus, a clear picture of the incorporation of Zn²⁺ into the ceria lattice is still missing. It also seems that the standard characterization

of doped ceria by room temperature XRD (often coupled with TEM) is not sufficient to determine its true phase composition.

In this study, we have prepared Zn-doped ceria nanocrystals that exhibit twice the oxygen storage capacity of pure ceria. The standard characterization of the material by room temperature XRD and TEM fails to reveal their correct phase composition. Based on clear evidence from *in-situ* high temperature XRD we show that, after calcination at 500 °C, the materials are not single-phased: x-ray amorphous ZnO is present within the materials. The amorphous ZnO crystallizes at 800 °C and undergoes second-stage incorporation at even higher temperatures. Our work also raises some doubts on the phase compositions reported in many previous studies on doped ceria.

Experimental

Materials and synthesis

Analytical grade cerium nitrate $\text{Ce}(\text{NO}_3)_3 \cdot 6\text{H}_2\text{O}$ (99.99%) and zinc nitrate $\text{Zn}(\text{NO}_3)_2 \cdot 6\text{H}_2\text{O}$ (99.99%) were purchased from Sigma Aldrich. They were directly used as precursors without further purification. Zn-doped ceria samples ($\text{Ce}_{1-x}\text{Zn}_x\text{O}_{2-\delta}$, nominal values of $x=0.05$, 0.1 and 0.2) were synthesized via a modified co-precipitation method. For simplicity they are designated as 05Zn, 10Zn and 20Zn in this paper. Desired quantities of the precursors were dissolved in an excess amount of de-ionized water and stirred continuously for about 10 min to achieve complete dissolution. Diluted aqueous ammonia solution (28 vol%) was then added drop-wise to the precursor solution under vigorous stirring until pH=10 was reached and stabilized. The precipitate was aged for one day under stirring and then allowed to settle for another day. After the clear supernatant was decanted, the precipitates were filtered and rinsed several times until a pH below 7 was reached. The filter cake was then dried at 80 °C in static air for about 12 hours. The dry cake was crushed in an agate mortar, and the powder sample was calcined in air for 5 hours at 500 °C. Pure ceria was also synthesized following the same procedure, except that the precipitation pH was 9. The materials after calcination are designated as “as-prepared” in this paper. The actual chemical compositions of the as-prepared samples were determined by ICP-OES (inductively coupled plasma-optical emission spectrometry), and the results are summarized in Table 1.

Table 1. Target and actual chemical compositions of the synthesized materials with associated names

Sample name	Target composition	Actual composition (mol%)
Ceria	CeO_2	—
05Zn	$\text{Ce}_{0.95}\text{Zn}_{0.05}\text{O}_{2-\delta}$	Zn:Ce = 4.97: 95.03
10Zn	$\text{Ce}_{0.90}\text{Zn}_{0.10}\text{O}_{2-\delta}$	Zn:Ce = 9.53: 90.47
20Zn	$\text{Ce}_{0.80}\text{Zn}_{0.20}\text{O}_{2-\delta}$	—

Standard characterization

Crystalline phases of all the materials were identified by x-ray powder diffraction using an X'Pert diffractometer from PANalytical. The diffraction patterns were collected with Cu K α radiation ($\lambda=1.5405 \text{ \AA}$) at 45 kV and 20 mA. An integration time of 5 s and a step size of 0.05° were set for all measurements unless indicated otherwise. TEM images of selected samples were recorded with JEOL JEM 2010 transmission electron microscope equipped with a LaB₆ filament and a slow scan CCD camera (Gatan Inc.) at an acceleration voltage of 200 kV. Each sample was prepared by depositing a droplet of sample and isopropanol suspension on a copper grid coated with lacey carbon. The OSCs of selected samples as-prepared were determined using a Netzsch thermogravimetric analyser (TGA) (TA409). The samples were exposed alternatively to reducing (10% H_2/Ar) and oxidizing conditions (10% O_2/Ar) at 500 °C for 4 cycles. XPS spectra were measured using a KRATOS ESCA model AXIS 165 spectrometer with Mg K α (1253.6 eV) radiation as the excitation source. Chemical shifts caused by the charging of the samples were corrected by using the binding energy of the adventitious carbon (C 1s) at 284.6 eV as internal reference. XRF measurements were carried out using an EDAX ORBIS micro x-ray fluorescence analyser equipped with a Rhodium anode and a solid-state multi-channel photon detector. The instrument was operated at 35 kV and 400 μA with a beam diameter of 2 mm for spectra collection and 30 μm for elemental mapping.

High temperature XRD and synchrotron-based μ -XRD

High temperature XRD patterns were collected in ambient air with the same aforementioned diffractometer equipped with an HDK2.4 chamber. Samples were deposited on resistively heated platinum strips, which were under mechanical tension to minimize buckling caused by thermal expansion. Synchrotron-based XRF and μ -XRD characterization of selected samples (in forms of pressed pellets) was carried out at the MicroXAS beamline of Swiss Light Source (SLS). The beam size was approximately $5 \times 5 \mu\text{m}^2$. The photon energy was set to 10 keV for both fluorescence mapping and micro x-ray diffraction experiments.

Results and discussion

Standard characterization

In Figure 1a room temperature XRD patterns for two samples as-prepared are reported. For simplicity, results for 5Zn and 10Zn are not included. Diffraction patterns for all samples exhibit only reflections characteristic of cubic ceria. It thus appears that Zn^{2+} is completely incorporated into the host lattice even at a doping level of 20 mol%. Zn-doped samples also exhibit lower reflection intensities and increased peak widths relative to pure ceria, indicating reduced crystallinity. Estimations of the crystallite size using the Scherrer equation

reveals a decrease from approximately 11.9 nm (ceria) to 7.7 nm (20Zn) (see Table 2). To evaluate the thermal stability of Zn-doped ceria, the as-prepared samples were annealed at 1300 °C in air for 24 h. The corresponding XRD patterns are presented in Figure 1b. Again, ZnO cannot be detected. Thus, it seems that Zn-doped ceria is structurally stable in air at least up to 1300 °C. As is evident from the narrower peaks, the crystallinity of the samples after annealing is increased.

Figure 1. XRD patterns of $\text{Ce}_{1-x}\text{Zn}_x\text{O}_{2-\delta}$ (a) as-prepared and (b) annealed in air at 1300 °C for 24 h.

Lattice parameters were calculated based on the positions of the first four peaks. In general, doped samples exhibit lattice contraction compared to pure ceria. After the annealing a small increase of the lattice constant with increasing doping level is suggested. This is consistent with the results reported previously.^[25,29] It was proposed that Zn^{2+} (90 pm) can be incorporated via two mechanisms: 1) substitution of Ce^{4+} (97 pm) leading to lattice contraction and the formation of charge compensating oxygen vacancies, and 2) Zn^{2+} occupying interstitial lattice sites, which causes the lattice to expand.^[25] However, further evidence is needed to verify this proposal. The incorporation of Zn^{2+} into the ceria lattice not only modifies its structural properties such as the lattice dimensions, but also affects its chemical properties. For instance, the reducibility of ceria is enhanced by doping with ZnO. TGA studies reveal that the OSC of 20Zn is nearly double the value of pure ceria. The experimental protocol used here to determine the OSC of ceria is similar to the one by Wang et al.^[2] The mass decrease when the sample is exposed to reducing conditions (10 vol% H_2 in Ar in present study) corresponds to the oxygen release due to the reduction of Ce^{4+} to Ce^{3+} . Accordingly, the mass increase when the sample is exposed to oxidizing conditions (10 vol% O_2 in Ar) corresponds to the oxygen uptake by cerium oxidation. The OSC values are calculated based on the mass changes averaged over four redox cycles. The exact values are listed in Table 2.

Figure 2. Lattice constants calculated based on XRD patterns.

The nanocrystalline nature of the as-prepared samples is confirmed by TEM. Figure 3a shows a representative image of 20Zn at lower magnification. Crystallites of a relatively uniform size around 10 nm are easily recognized, in agreement with the value calculated using the Scherrer equation. All the calculated sizes of crystal domains are included in Table 2. The selected area electron diffraction (SAED) pattern shown as inset a1 confirms the presence of polycrystalline cubic ceria. However it shows no evidence of ZnO, consistent with the observation from the x-ray diffraction measurements shown in Figure 1a. Figure 3b shows a typical high resolution TEM image for 20Zn. Lattice fringes with a spacing of about 0.30 nm, indexed as the ceria (111) planes, are clearly visible in the image. The increased crystallinity of 20Zn after annealing, evident from the narrower diffraction peaks seen in Figure 1b, is also observed by TEM. Figure 3c shows a much larger grain with a diameter of a few hundreds of nanometers. Here in the image individual single crystals cannot be distinguished anymore. The two images (Figure 3a and 3c) are roughly at the same magnification. The growth of crystals is further evidenced by the electron diffraction pattern (inset c1) exhibiting only bright discrete spots instead of rings, and by the dark field image showing clusters of crystals as seen in Figure 3d. Note that the two electron diffraction patterns in Figure 3 were obtained from sample areas of similar sizes.

Figure 3. TEM images of 20Zn as-prepared (upper row): (a) low magnification, inset (a1) electron diffraction pattern from selected area, (b) high resolution image showing lattice fringes with lattice spacings ($d=D/N$) calculated over multiple lattice planes. TEM images of 20Zn annealed (lower row): (c) bright field image, inset (c1) SAED pattern, and (d) dark field image showing clusters of larger crystals.

Table 2. Crystallite sizes (d) and surface zinc concentrations of ceria, 05Zn, 10Zn and 20Zn as-prepared and annealed. Oxygen storage capacities (OSC) of samples as-prepared are also included.

Sample		As-prepared			Annealed	
sample name	bulk zinc (%) ^{a)}	d (nm) ^{b)}	surface zinc (%) ^{c)}	OSC ($\mu\text{mol O g}^{-1}$)	d (nm)	surface zinc (%)
CeO ₂	—	11.9 \pm 0.7	—	135.5 \pm 3.5	49.6 \pm 2.2	—
05Zn	4.97	8.8 \pm 1.0	17.44	—	50.1 \pm 2.4	25.19
10Zn	9.53	8.4 \pm 1.1	25.56	—	50.1 \pm 2.4	26.18
20Zn	—	7.7 \pm 0.7	29.05	267.7 \pm 9.0	53.0 \pm 5.4	38.11

^{a)} Zinc concentration in the bulk is the actual composition determined by ICP-OES as shown in Table 1. ^{b)} Crystallite sizes are calculated from 3 or 4 peaks in the diffraction patterns using the Scherrer equation, where the shape factor $K=0.94$ for cubic crystals. ^{c)} Zinc concentration in the surface layer is quantified from XPS spectra.

Chemical inhomogeneity

To check for possible changes in the chemical composition of Zn-doped ceria caused by annealing, we collected cerium 3d and zinc 2p XPS spectra for 05Zn, 10Zn and 20Zn. The results of the quantification of surface zinc are presented in Table 2. The concentration of zinc in the surface layer of the as-prepared samples probed by XPS is about 2 to 3 times as high as the bulk concentration measured by ICP-OES. This suggests enrichment of zinc at the surface. This chemical inhomogeneity is further enhanced by annealing at 1300 °C, after which the concentration of zinc in the surface layer is up to 5 times as high as the bulk concentration. This increase in chemical inhomogeneity suggests bulk-to-surface migration and thus high mobility of zinc in ceria.

Figure 4. Cerium XRF maps of 20Zn (a) as-prepared and (c) annealed, plotted in same color scale. Zinc XRF maps of 20Zn (b) as-prepared and (d) annealed, plotted in the same scale.

The high mobility of zinc in ceria is observed not only in the nanometer range but also on the scale of microns. Figure 4 shows the cerium and zinc XRF maps of 20Zn for an area of approximately $2.3 \times 1.8 \text{ mm}^2$. For 20Zn as-prepared, the distribution of zinc inside the material is very homogeneous, as seen in Figure 4b. However, once the sample is annealed at 1300 °C for 24 hours, zinc-rich patches on the order of 10 μm in diameter become clearly visible (see Figure 4d, plotted in the same scale as Figure 4b). XRF spectroscopic studies also show that ZnO sublimation in air at temperatures between 1200 °C and 1300 °C for extended period (48 h) is negligible. Thus it is reasonable to assume that Figure 4b and 4d show the same average zinc concentration (nominally 20 mol%). Then the zinc-rich regions clearly seen in Figure 4d must

correspond to an even higher zinc concentration. However, surprisingly no ZnO is detected by the standard XRD (Figure 1b) with an illuminated area of about $10 \times 10 \text{ mm}^2$. In contrast, the distribution of cerium is very homogeneous and is not influenced by annealing.

High temperature x-ray diffraction

To verify the structural stability of Zn-doped ceria and to shed light on the lattice expansion of 20Zn observed after annealing (see Figure 2), we performed *in-situ* high temperature XRD studies in air. At first, diffraction patterns were recorded at every 200 °C at temperatures in the range 200–1400 °C for 20Zn. The results are presented in Figure 5. At temperatures below 800 °C only peaks attributed to ceria and the substrate platinum are observed. However, at temperatures between 800 °C and 1200 °C new features close to the ceria (200) peak are observed. Careful examination on the positions of these new features relative to ceria (200) reveals that they originate from wurzite ZnO. ZnO then disappears and is no longer observed at 1400 °C, suggesting its incorporation into the ceria lattice. This is likely to be the cause of the observed lattice expansion of 20Zn after annealing. The origin of the intermediately formed ZnO is from either phase segregation above 800 °C or the crystallization of x-ray amorphous, unincorporated ZnO present after calcination at 500 °C.

Figure 5. *In-situ* high temperature XRD patterns of 20Zn ($x=0.2$) in air from 200 °C to 1400 °C.

In order to confirm the formation of ZnO at 800 °C to 1200 °C, and to determine its origin, we conducted a more detailed high temperature diffraction study for 20Zn. The sample was subjected to two consecutive heating cycles, each with isothermal segments at 800 °C, 1000 °C, and 1200 °C (heating rate 60 °C min^{-1}). To increase the signal-to-noise ratio and to obtain a better angular resolution, the integration time was increased to 7 s and the step size was decreased to 0.01°.

The 2θ range was limited to $30\text{--}42^\circ$ covering CeO_2 (200), ZnO (100), (002), (101) and Pt (111). Four consecutive patterns were collected at each temperature. The results are presented in Figure 6 for 20Zn ($x=0.2$). In the first heating cycle ZnO is present at 800°C and 1000°C . Once the sample is further heated to 1200°C ZnO disappears during the collection of the first pattern (red pattern in a-1200) within about 60 min. The disappearance of ZnO can only be due to its incorporation into the ceria host lattice since ZnO sublimation in air at 1200°C is negligible. In fact the XRF spectrum of 20Zn after annealing for 48 h at 1250°C shows almost no decrease of the zinc concentration. Once the sample is cooled to 800°C the second heating cycle starts. During this cycle no ZnO was detected. Similar results were obtained for 10Zn and 5Zn , but only traces of ZnO could be observed for 5Zn at 800°C and 1000°C . The irreversible disappearance of the ZnO intermediate at about 1200°C strongly suggests that the origin of the intermediate is not due to phase segregation but due to the crystallization of the un-incorporated x-ray amorphous ZnO present after synthesis. More than 40% of Zn^{2+} seems to be initially present as un-incorporated x-ray amorphous ZnO based on the ratio of ZnO (101) and ceria (200) areas (pattern at 1000°C) in comparison to a calibration performed with known mixtures of pure ceria and ZnO .

Further evidence is obtained by comparing the positions of the ceria (200) peak in 10Zn ($x=0.1$) diffraction patterns recorded at the same temperature but in different heating cycles, as presented in Figure 7. At each temperature the positions of the ceria (200) peak recorded during the second cycle are shifted to lower angles compared to the first cycle, indicating an expansion of the lattice. The shift becomes

smaller with increasing temperatures. At 1200°C the positions roughly coincide. From Figure 2, we know that the lattice constant of doped ceria after annealing increases with increasing doping level. Based on the findings presented in Figure 7, a clear picture can be obtained: During the first heating cycle the un-incorporated x-ray amorphous ZnO that is present after synthesis crystallizes around 800°C and becomes visible in the diffraction patterns. This ZnO is partly incorporated into the ceria lattice by a solid-solid reaction between 800°C and 1000°C , thus increasing the doping level of the sample. The incorporation of ZnO is nearly completed at 1200°C . Thus, the doping level of 10Zn increases during the first cycle while the temperature is increased as incorporation proceeds but remains constant during the second cycle. At 800°C samples with slightly different doping level and thus different peak positions are compared in Figure 7. Since complete incorporation of ZnO is achieved by the end of the first cycle, samples with nearly identical doping levels are compared at 1200°C . Thus nearly identical positions of the ceria (200) peak are expected in this case. Thus far, we have presented clear evidence showing that only a fraction of the Zn^{2+} is incorporated into the ceria lattice after calcination at 500°C . The remaining is present as x-ray amorphous ZnO in substantial quantities. Temperatures of 800°C – 1200°C or higher is required for its seemingly complete incorporation.

Figure 7. Comparison of ceria (200) peak positions of 10Zn between two cycles at (a) 800°C , (b) 1000°C and (c) 1200°C .

Figure 6. *In-situ* high temperature XRD patterns of 20Zn ($x=0.2$) in air for 2 cycles of heating from 800°C to 1200°C : (a) 1st cycle and (b) 2nd cycle.

Synchrotron based $\mu\text{-XRF}$ and $\mu\text{-XRD}$

In order to verify the findings of the standard characterization, 20Zn as-prepared and after annealing were characterized by spatially resolved $\mu\text{-XRF}$ and $\mu\text{-XRD}$. This offers a few advantages over the standard XRD and XRF. For instance, the photon flux and brightness from a synchrotron source is orders of magnitude higher, increasing its capability of detecting trace phases. Due to the micron-sized beam of $5 \times 5 \mu\text{m}^2$, an almost 30 times better spatial resolution is achieved. The $\mu\text{-XRD}$ capability allows the detection of structural inhomogeneity or changes in the phase composition at the same spatial resolution. In addition, it is possible to estimate the local thickness of the sample by measuring and mapping the beam attenuation. This is important because XRF maps can be also influenced by sample thickness due to different escape depths of $\text{Ce L}\alpha$ and $\text{Zn K}\alpha$ photons. Results for 20Zn

as-prepared show that the spatial distribution of cerium and zinc is homogeneous, consistent with XRF measurements using traditional x-ray sources (Figure 4a and 4b). Synchrotron XRD also agrees with standard XRD (Figure 1a), showing no crystalline ZnO . Results for 20Zn after annealing are presented in Figure 8. Figure 8a and 8b show the spatial distribution of cerium for an area of approximately $340 \times 500 \mu\text{m}^2$, while Figure 8c shows the zinc distribution in the same area. Figure 8d shows the beam transmission map as an indicator of local sample thickness. These maps generally confirm the findings of XRF using traditional x-ray sources, but with much better resolution. Zn-rich patches have sizes ranging from a few μm to $50 \mu\text{m}$ in diameter. Two areas ("1" and "2") exhibiting similar beam transmission (Figure 8d), indicating a similar sample thickness, were analysed in detail. It is easy to recognize from Figure 8a and 8c that area "1" is

cerium-rich and area “2” is zinc-rich. Figure 8e shows a typical μ -XRD pattern recorded within the cerium-rich area. The prominent phase is found to be fluorite CeO_2 (denoted by white lattice plane index). Upon a closer inspection (see zoom-in as Figure 8f), very faint but discernible diffraction spots (marked by arrows) are visible close to the CeO_2 (200) diffraction ring. They are due to single crystals of wurzite ZnO with orientations of (101) and (100). These traces of ZnO were not detected by the standard XRD (Figure 1b). The presence of ZnO in the Zn-rich area is more pronounced, although still minute compared to the CeO_2 phase, as seen in a typical μ -XRD pattern shown as Figure 8g and 8h. ZnO single crystals

with orientation (002) are also detected, with the orientation (100) being most pronounced.

Characterization by synchrotron-based μ -XRF and μ -XRD confirmed that the spatial distribution of zinc in the sample becomes very inhomogeneous (on a scale of a few tens of micrometers) after annealing at ultra-high temperatures (1300-1400 °C). Moreover, these results clearly show that the second-stage incorporation of substantial amounts of initially x-ray amorphous ZnO into the ceria lattice at high temperatures is not complete as suggested by standard XRD. Trace amounts of crystalline ZnO are still present within the material.

Figure 8. Synchrotron-based XRF maps (a) and (b): Ce $L\alpha$ plotted in two scales, and (c): Zn $K\alpha$. Beam transmission (I_1/I_0) presented in (d). The area “1” correspond to a Ce-rich region, and “2” a Zn-rich region. Typical μ -XRD pattern for a $5 \times 5 \mu\text{m}^2$ area in the Ce-rich region: (e) full detector area, and (f) zoom-in of marked area. Typical μ -XRD pattern in the Zn-rich region: (g) full detector area and (h) zoom-in of marked area. White lattice plane index denote CeO_2 , and red wurzite ZnO .

Conclusions

In summary, we have synthesized Zn-doped ceria nanocrystals that exhibit twice the OSC of pure ceria. It is shown by XPS that these materials are chemically inhomogeneous on the nanometer scale, with zinc enrichment at the surface. After annealing at 1300 °C the spatial distribution of zinc on the micrometer scale becomes also inhomogeneous. Our work also shows that a combination of commonly applied characterization techniques (such as room temperature XRD and TEM) is not sufficient to determine the correct phase composition of Zn-doped ceria after calcined at 500 °C. With *in-situ* high temperature XRD, we are able to reveal the presence of substantial amounts of un-incorporated x-ray amorphous ZnO in the as-prepared samples. This amorphous ZnO crystallizes at 800 °C and is then incorporated in the ceria lattice at higher temperatures. However, this second-stage incorporation is not complete according to spatially resolved μ -XRD measurements using a combination of synchrotron radiation and micro-beam configuration. It is not clear whether the presence of x-ray amorphous dopant oxide after lower-temperature synthesis is specific to the Zn-O-Ce system. However, preliminary studies reveal similar observations for Cu-doped ceria: CuO forms at 800 °C and disappears irreversibly at higher temperatures. We thus suggest that caution be applied when one interprets XRD data to determine true phase composition of similar doped ceria materials. Interestingly, we have indications from TGA studies that the soot combustion activity of 20Zn is

markedly enhanced after additional treatment with ~5 M hydrochloric acid, suggesting a detrimental effect of the un-incorporated x-ray amorphous ZnO in this specific case. Based on our findings the catalytic activity of doped ceria can be influenced by an amorphous dopant phase possibly present after low-temperature calcination.

Acknowledgements

This work was funded by the Indo Swiss Joint Research Program (grant #138852). The authors are grateful for the help of Dr. Elisabeth Müller, Ms. Irena Papachella and Mr. Andrea Wismer with TEM, synthesis and TGA studies respectively. The authors acknowledge the Paul Scherrer Institute, Villigen, Switzerland for provision of synchrotron radiation beamtime at the MicroXAS beamline of SLS and would like to thank Dr. Camelia N. Borca, Dr. Daniel Grolmund and Dr. Vallerie Ann Samson for assistance.

Notes and references


^a Solar Technology Laboratory, Paul Scherrer Institute, CH-5232 Villigen PSI, Switzerland. Email: ivo.alxneit@psi.ch; Fax: +41 56 310 2688; Tel: +41 56 310 4092.

^b General Energy Research Department, Paul Scherrer Institute, CH-5232 Villigen PSI, Switzerland.

[1] A. Trovarelli, ed., *Catalysis by Ceria and Related Materials*, Imperia College Press, London, UK **2002**.


- [2] D. Wang, Y. Kang, V. Doan-Nguyen, J. Chen, R. Küngas, N. L. Wieder, K. Bakmutsky, R. J. Gorte and C. B. Murray, *Angew. Chem. Int. Ed.*, **2011**, 50, 4378.
- [3] Q. Yuan, H.-H. Duan, L.-L. Li, Z.-X. Li, W.-T. Duan, L.-S. Zhang, W.-G. Song and C.-H. Yan, *Adv. Mater.*, **2010**, 22, 1475.
- [4] S. Carrettin, P. Concepcion, A. Corma, J. M. L. Nieto and V. F. Puentes, *Angew. Chem. Int. Ed.*, **2004**, 43, 2538.
- [5] D. A. J. M. Ligthart, R. A. van Santen and E. J. M. Hensen, *Angew. Chem. Int. Ed.*, **2011**, 50, 5306.
- [6] A. Bueno-Lopez, K. Krishna, M. Makkee and J. Moulijn, *J. Catal.*, **2005**, 230, 237.
- [7] L. Katta, P. Sudarsanam, G. Thrimurthulu and B. M. Reddy, *Appl. Catal. B*, **2010**, 101, 101.
- [8] P. A. Kumar, M. D. Tanwar, N. Russo, R. Pirone and D. Fino, *Catal. Today*, **2012**, 184, 279.
- [9] G. Qi and R. T. Yang, *J. Catal.*, **2003**, 217, 434.
- [10] M. Casapu, O. Kröcher and M. Elsener, *Appl. Catal. B*, **2009**, 88, 413.
- [11] V. V. Kharton, F. M. Figueiredo, L. Navarro, E. N. Naumovich, A. V. Kovalevsky, A. A. Yaremchenko, A. P. Viskup, A. Carneiro, F. M. B. Marques and J. R. Frade, *J. Mater. Sci.*, **2001**, 36, 1105.
- [12] Y. Ma, X. Wang, S. Li, M. S. Toprak, B. Zhu and M. Muhammed, *Adv. Mater.*, **2010**, 22, 1640.
- [13] S. Abanades and G. Flamant, *Sol. Energy*, **2006**, 80, 1611.
- [14] W. C. Chueh, C. Falter, M. Abbott, D. Scipio, P. Furler, S. M. Haile and A. Steinfeld, *Science*, **2010**, 330, 1797.
- [15] P. Furler, J. R. Scheffe and A. Steinfeld, *Energy Environ. Sci.*, **2012**, 5, 6098.
- [16] H. Inaba and G. Tagawa, *Solid State Ionics*, **1996**, 83, 1.
- [17] K. Harada, T. Oishi, S. Hamamoto and T. Ishihara, *J. Phys. Chem. C*, **2014**, 118, 559.
- [18] B. M. Reddy, G. Thrimurthulu, L. Katta, Y. Yamada and S.-E. Park, *J. Phys. Chem. C*, **2009**, 113, 15882.
- [19] B. M. Reddy, L. Katta and G. Thrimurthulu, *Chem. Mater.*, **2010**, 22, 467.
- [20] S. Abanades, A. Legal, A. Cordier, G. Peraudeau, G. Flamant and A. Julbe, *J. Mater. Sci.*, **2010**, 45, 4163.
- [21] N. D. Petkovich, S. G. Rudisill, L. J. Venstrom, D. B. Boman, J. H. Davidson and A. Stein, *J. Phys. Chem. C*, **2011**, 115, 21022.
- [22] A. Le Gal and S. Abanades, *J. Phys. Chem. C*, **2012**, 116, 13516.
- [23] A. Gupta, U. V. Waghmare and M. S. Hegde, *Chem. Mater.*, **2010**, 22, 5184.
- [24] A. N. Kehoe, D. O. Scanlon and G. W. Watson, *Chem. Mater.*, **2011**, 23, 4464.
- [25] R. Li, S. Yabe, M. Yamashita, S. Momose, S. Yoshida, S. Yin and T. Sato, *Mater. Chem. Phys.*, **2002**, 75, 39.
- [26] G. Avgouropoulos, M. Manzoli, F. Boccuzzi, T. Tabakova, J. Papavasiliou, T. Ioannides and V. Idakiev, *J. Catal.*, **2008**, 256, 237.
- [27] O.H. Laguna, M.A. Centeno, F. Romero-Sarria and J.A. Odriozola, *Catal. Today*, **2011**, 172, 118.
- [28] S.-L. Zhong, L.-F. Zhang, L. Wang, W.-X. Huang, C.-M. Fan and A.-W. Xu, *J. Phys. Chem. C*, **2012**, 116, 13127.
- [29] K. Schmale, M. Daniels, A. Buchheit, M. Grünebaum, L. Haase, S. Koops and H.-D. Wiemhöfer, *J. Electrochem. Soc.*, **2013**, 160, F1081.

Intensity [a.u.]

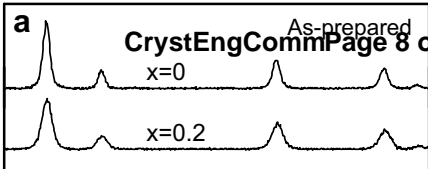

Ceria

20Zn

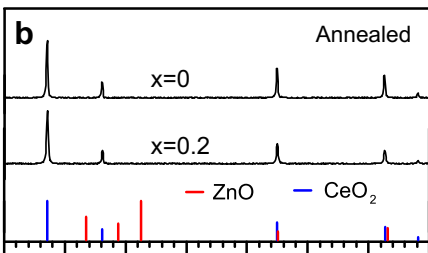



Ceria


20Zn

25 30 35 40 45 50 55 60

2θ [deg]

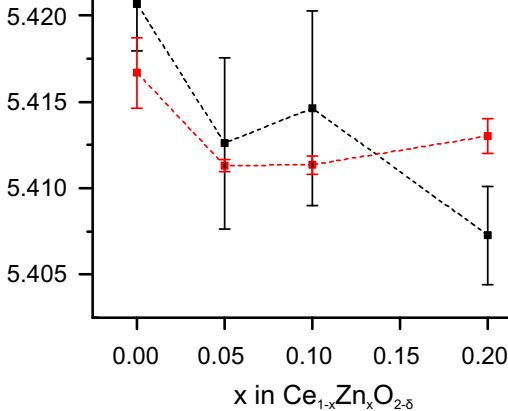a [Å]

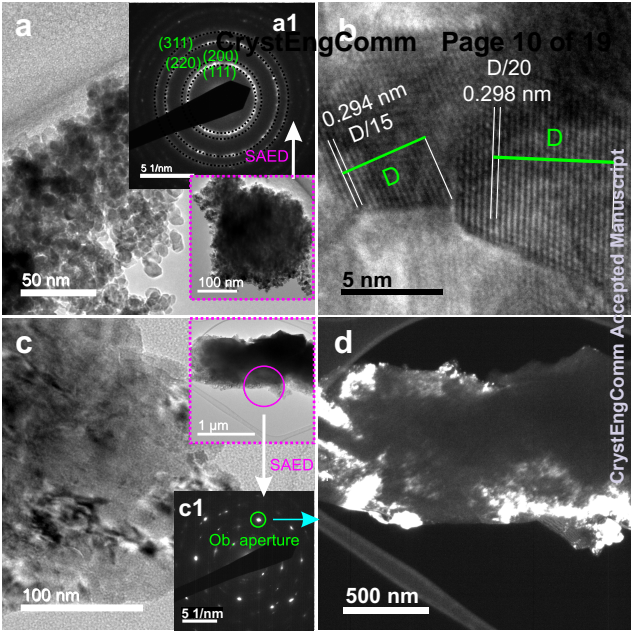


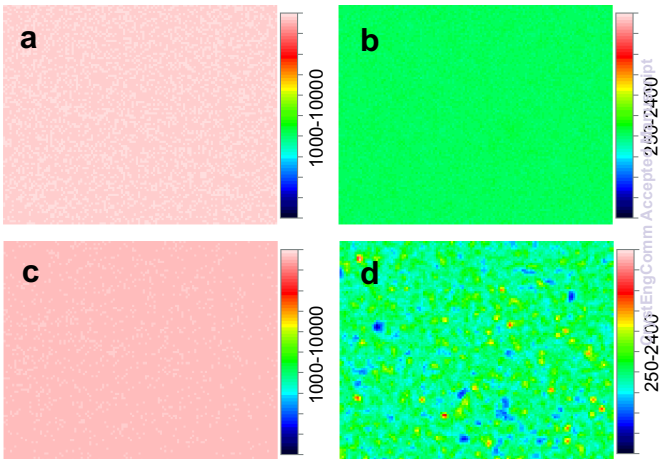


■ Ceria □ Pt ● ZnO


CrystEngComm Page 12 of 19









Intensity [a.u.]

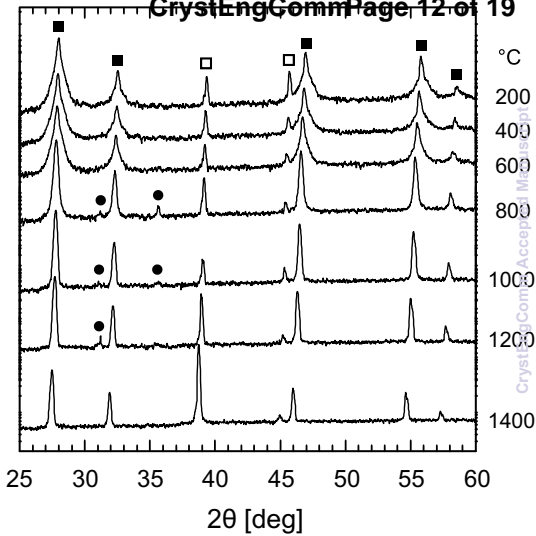

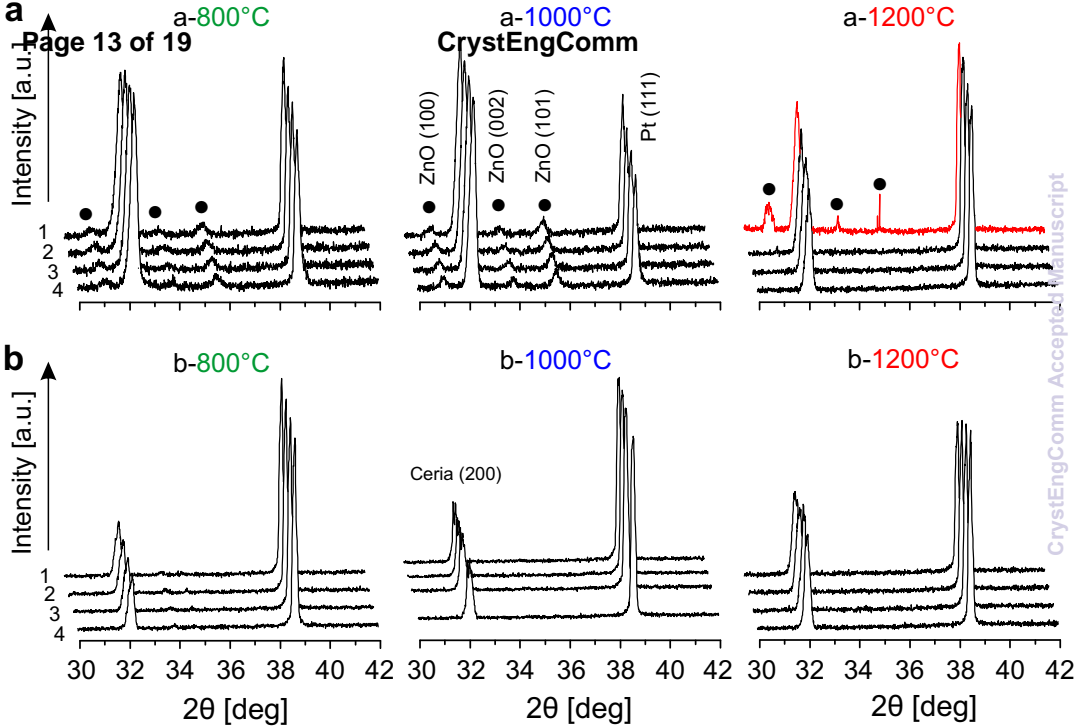

Intensity [a.u.]

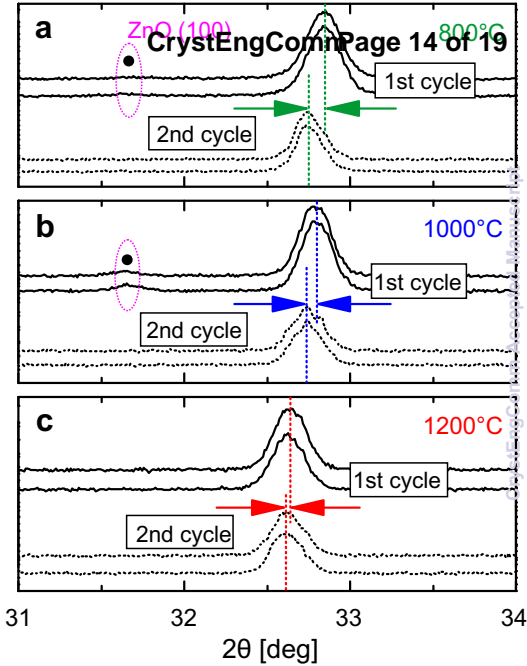

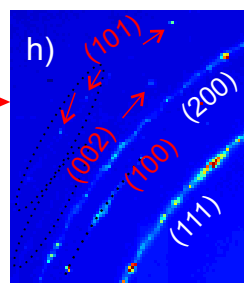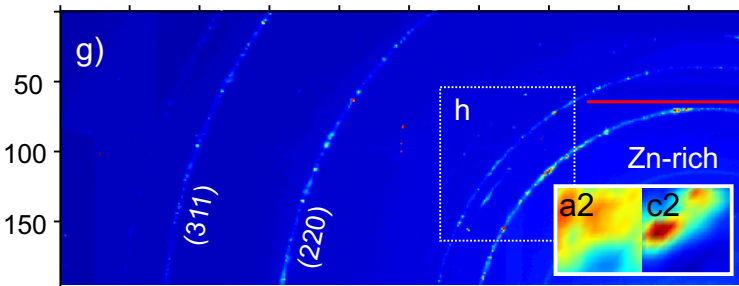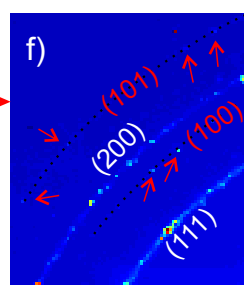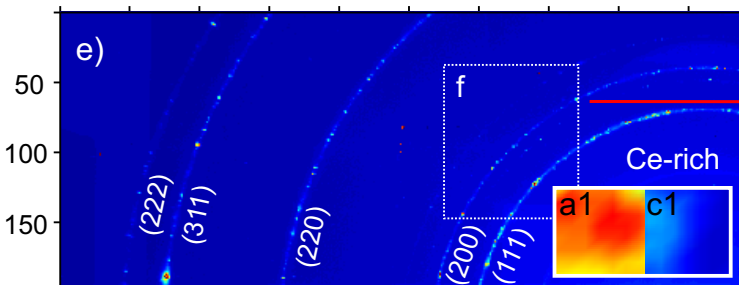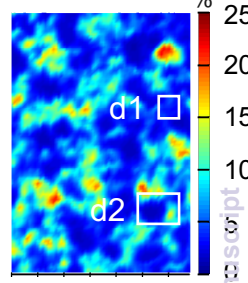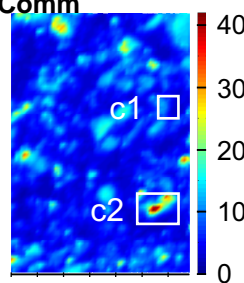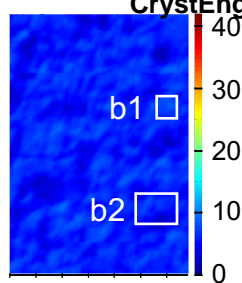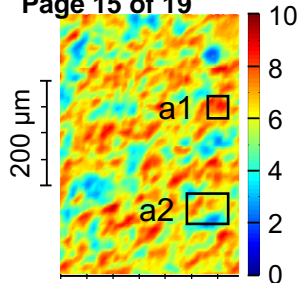

Seemingly monophasic Zn-doped ceria nanocrystals contain substantial amounts of x-ray amorphous ZnO not detectable by standard XRD. This ZnO can be incorporated upon annealing at temperatures up to 1300 °C.

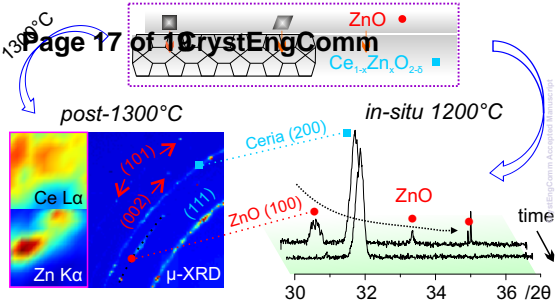


Table 1. Target and actual chemical compositions of the synthesized materials with associated names

Sample name (mol%)	Target composition	Actual composition
Ceria	CeO ₂	—
05Zn	Ce _{0.95} Zn _{0.05} O _{2-δ}	Zn:Ce = 4.97: 95.03
10Zn	Ce _{0.90} Zn _{0.10} O _{2-δ}	Zn:Ce = 9.53: 90.47
20Zn	Ce _{0.80} Zn _{0.20} O _{2-δ}	—

Table 2. Crystallite sizes (d) and surface zinc concentrations of ceria, 05Zn, 10Zn and 20Zn as-prepared and annealed. Oxygen storage capacities (OSC) of samples as-prepared are also included.

Sample			As-prepared		
Annealed					
sample name	bulk zinc (%) a)	d (nm) b)	surface zinc (%) c)	OSC	
($\mu\text{mol O g}^{-1}$)			surface zinc(%)		
CeO ₂	—	11.9±0.7	—	135.5±3.5	
	49.6±2.2	—			
05Zn	4.97	8.8±1.0	17.44	—	
	50.1±2.4	25.19			
10Zn	9.53	8.4±1.1	25.56	—	
	50.1±2.4	26.18			
20Zn	—	7.7±0.7	29.05		
	267.7±9.0	53.0±5.4	38.11		

a) Zinc concentration in the bulk is the actual composition determined by ICP-OES as shown in Table 1. b) Crystallite sizes are calculated from 3 or 4 peaks in the diffraction patterns using the Scherrer equation, where the shape factor K=0.94 for cubic crystals. c) Zinc concentration in the surface layer is quantified from XPS spectra.