

PCCP

Accepted Manuscript



This is an *Accepted Manuscript*, which has been through the Royal Society of Chemistry peer review process and has been accepted for publication.

Accepted Manuscripts are published online shortly after acceptance, before technical editing, formatting and proof reading. Using this free service, authors can make their results available to the community, in citable form, before we publish the edited article. We will replace this *Accepted Manuscript* with the edited and formatted *Advance Article* as soon as it is available.

You can find more information about *Accepted Manuscripts* in the [Information for Authors](#).

Please note that technical editing may introduce minor changes to the text and/or graphics, which may alter content. The journal's standard [Terms & Conditions](#) and the [Ethical guidelines](#) still apply. In no event shall the Royal Society of Chemistry be held responsible for any errors or omissions in this *Accepted Manuscript* or any consequences arising from the use of any information it contains.

Cite this: DOI: 10.1039/c0xx00000x

www.rsc.org/xxxxxx

ARTICLE TYPE

In-situ x-ray Raman spectroscopy study of the hydrogen sorption properties of lithium borohydride nanocomposites

Piter S. Miedema,^{*a‡} Peter Ngene,^{a‡} Ad M.J. van der Eerden,^a Dimosthenis Sokaras,^b Tsu-Chien Weng,^b Dennis Nordlund,^b Yuen S. Au^a and Frank M.F. de Groot^a

⁵ Received (in XXX, XXX) Xth XXXXXXXXXX 20XX, Accepted Xth XXXXXXXXXX 20XX

DOI: 10.1039/b000000x

Nanoconfined alkali metal borohydrides are promising materials for reversible hydrogen storage applications, but the characterization of hydrogen sorption in these materials is difficult. Here we show that with in-situ x-ray Raman spectroscopy (XRS) we can track the relative amounts of intermediates and final products formed during de- and re-hydrogenation of nanoconfined lithium borohydride (LiBH₄) and therefore we can possibly identify the de- and re-hydrogenation pathways. In the XRS of nanoconfined LiBH₄ at different points in the de- and re-hydrogenation, we identified phases that lead to the conclusion that de- and re-hydrogenation pathways in nanoconfined LiBH₄ are different from bulk LiBH₄: Intercalated lithium (LiCx), boron and lithium hydride were formed during de-hydrogenation, but as well Li₂B₁₂H₁₂ was observed indicating that there is possibly some bulk LiBH₄ present in the nanoconfined sample LiBH₄/C as prepared. Surprisingly, XRS revealed that the de-hydrogenated products of the LiBH₄/C nanocomposites can be partially rehydrogenated to about 90% of Li₂B₁₂H₁₂ and 2-5% of LiBH₄ at a mild condition of 1 bar H₂ and 350°C. This suggests that re-hydrogenation occurs via the formation of Li₂B₁₂H₁₂. Our results show that XRS is an elegant technique that can be used for in- and ex-situ study of the hydrogen sorption properties of nanoconfined and bulk light-weight metal hydrides in energy storage applications.

Introduction

Hydrogen has the potential to play a vital role in future sustainable-energy scenarios¹. It can be produced in a sustainable way from water using solar, wind and geothermal energy; and also via catalytic conversion of biomass. Hydrogen has the highest gravimetric energy density and can be used in combination with fuel cells to produce electrical energy for automobiles, stationary applications such as power generators and portable electronics. A major challenge that prevents the widespread use of hydrogen as a fuel, is its storage and in particular the storage efficiency, safety and cost. Several methods have been proposed to store hydrogen, including pressurized gas, liquefied hydrogen and hydrogen storage in solids. Among these options, storing hydrogen as metal hydrides is interesting from the view point of safety, energy density and volume density. As the gravimetric density of the material is an important consideration, many studies have focused on hydrides of light-weight elements or alloys such as MgH₂, LiBH₄, NaBH₄, NaAlH₄ and Mg(BH₄)₂. Especially, the alkali-metal borohydrides have been widely investigated for reversible hydrogen storage due to their high hydrogen content^{1, 2}: for example LiBH₄ contains 18.5 wt% hydrogen. However, these light weight complex hydrides are rather stable and as a consequence they start to release hydrogen only at elevated temperatures (370 °C for LiBH₄)^{3, 4}.

These temperatures are too high for practical commercial applications. Additionally the hydrogen sorption reaction of the alkali-metal borohydride suffers from poor reversibility.

In an effort to improve the hydrogen storage properties of these complex hydrides, strategies such as nanosizing / nanoconfinement, destabilization/product stabilization, addition of suitable catalysts and core shell strategy have been explored⁵⁻¹⁵. These strategies generally led to an improvement in their hydrogen sorption properties. However, for practical application further improvement of these materials is required. A good understanding of the hydrogenation and de-hydrogenation pathway by measuring the development of different phases during de- and re-hydrogenation of these materials would be beneficial in improving their hydrogen storage properties. Unfortunately, LiBH₄ and many other complex hydrides undergo multiple desorption steps with often amorphous and sometimes volatile intermediates that cannot be characterized using standard techniques such as X-ray diffraction (XRD). Transmission electron microscopy (TEM) is also ineffective due to the weak scattering of electrons by the light elements Li, Na and B. Additionally, confinement of LiBH₄ in nanoporous carbon materials, which was shown to be a promising strategy to improve hydrogen release and uptake in these complex hydrides^{8, 10, 11}, often leads to nanocomposites that are amorphous after preparation. This also complicates the study of the decomposition mechanisms since the starting material and de-hydrogenation

products are both amorphous. Additionally, due to light absorption by the carbon scaffold, the use of techniques such as Infrared (IR) and Raman spectroscopy is difficult for these systems confined in nanoporous carbon. Another complication is that the measurements on these complex metal hydrides have to be performed under inert atmosphere, which is another challenging but not impossible requirement for all the above mentioned techniques.

Consequently the exact origin for the enhancements in hydrogen sorption properties and change in thermodynamics or decomposition pathway(s) relative to the bulk that is often observed in nanoconfined complex hydrides, is still not well understood⁸. To this end theoretical calculations combined with techniques such as NMR and inelastic neutron scattering methods are increasingly being used to study the decomposition mechanism of bulk and nanoconfined metal borohydrides¹⁶⁻¹⁹. However using NMR or inelastic neutron scattering, it is very challenging to experimentally follow the decomposition of these metal hydrides by in-situ measurements, which would be required to reliably unravel their decomposition reactions, its phases and mechanisms.

In our previous paper we demonstrated the feasibility of X-Ray Raman Spectroscopy (XRS) as a new technique to study the electronic properties of bulk and LiBH₄/carbon nanocomposites (LiBH₄/C) during de-hydrogenation²⁰. The XRS technique applies tuneable hard x-ray radiation. Hard x-ray (absorption) spectroscopies can be performed in-situ and supply element-specific electronic structure information^{20, 21} and the main difficulty is that synchrotron radiation is required. In our previous paper²⁰ the presence of oxygen in the gas stream during the experiments had a huge impact on the spectral shape and influenced the interpretation of the results. Nevertheless, it was demonstrated that XRS is a promising tool to study the decomposition mechanism of LiBH₄/C nanocomposites. Using an in-situ cell, this hard x-ray technique allows the probing of the electronic transitions taking place in the boron, lithium and carbon during hydrogen release and uptake from LiBH₄/C nanocomposites.

For the present research paper we improved the experimental conditions so as to minimize the effect of oxygen by preparing ex-situ de-hydrogenated and re-hydrogenated samples and we extended our approach by comparison with reference materials. In addition, we tested this technique to study the decomposition of NaBH₄/C nanocomposites (shown in the Supplementary Information, section 10), for which only few literature exists regarding their de-hydrogenation and re-hydrogenation behaviour.

In this paper we show that using XRS, the changes in the electronic properties of Li, B and C during the de-hydrogenation reactions of LiBH₄ confined in nanoporous carbon can reliably be measured in-situ and the decomposition products can be assigned with reasonable accuracy by comparing with reference materials.

Experimental section

Reference materials

The following materials were used as received from the supplier: Boron powder (99.5 % pure, crystalline < 20 nm, ABCR),

Lithium metaborate (LiBO₂) powder (99.995 % pure, Aldrich), B₂O₃ powder (99.995 % pure, Chempur), Lithium hydride (LiH) powder (99.4 % pure, 30 mesh, Alfa), Lithium borohydride (LiBH₄, 95 % pure, Acros-organics) and sodium borohydride (NaBH₄, 99.99 % trace metals basis, Acros-organics) and lithium metal foil (Li, 99.9 % pure, Sigma-Aldrich). Some of these compounds were used for the sample preparations mentioned below.

Nanoconfined LiBH₄ and NaBH₄

To minimize the effect of oxygen, three types of ex-situ samples were prepared:

(1) 25 wt% LiBH₄/C nanocomposites were prepared by melt infiltration as described previously^{10, 11}. In short, 0.25 gram of LiBH₄ was mixed with 0.75 g of nanoporous carbon (High surface area graphite: HSAG-500 provided by Timcal Switzerland, pore volume 0.65 cm³/g, broad pore size contribution, majority of pore sizes is 2-3 nm). The LiBH₄-porous carbon mixture was heated in an autoclave to 295 °C with an initial pressure of 50 bar hydrogen. The samples were cooled down under hydrogen pressure and transferred into an argon filled glove box. These samples are further called “LiBH₄/C as prep”.

(2) Part of the LiBH₄/C as prep sample was de-hydrogenated by heating under 25 ml/min argon flow, 5 °C/min with a dwell time of 30 minutes at the maximum de-hydrogenation temperature (400 °C for LiBH₄/C). These de-hydrogenated samples are labelled “LiBH₄/C deh”.

(3) Part of the LiBH₄/C deh was re-hydrogenated by heating in an autoclave to 325 °C under 60 bar hydrogen for 3 hours. This sample will further on be referred to as “LiBH₄/C reh”.

Preparation of Li₂B₁₂H₁₂

Li₂B₁₂H₁₂ was prepared by the reaction between LiBH₄ and decaborane:



Stoichiometric amounts of LiBH₄ and decaborane (B₁₀H₁₄) were properly mixed and placed into a stainless steel reactor. The reactor was placed in an oven and heated to 420 °C, with a dwell time of 1 hr at 420 °C. The reactor was then cooled down to ambient conditions and a white reaction product was collected and analyzed using x-ray diffraction (XRD). This type of preparation was published before by He et al.²². The XRD pattern of the Li₂B₁₂H₁₂ prepared in the way mentioned above is shown besides the starting components in the Supplementary information (Figure S1) and it shows a Bragg peak around 18 degrees which is observed as well in the Li₂B₁₂H₁₂ synthesized by Friedrichs et al.²³ by reacting B₂H₆ and LiBH₄ above 200 °C. However Friedrichs also finds a stronger Bragg peak around 15.8 degrees, which would suggest that we don't have pure crystalline, but more likely, that we have synthesized amorphous Li₂B₁₂H₁₂. For our purpose of measuring XRS this does not matter much and we actually believe that it is more convenient to have amorphous Li₂B₁₂H₁₂ as a reference material.

All samples preparations and handling was conducted in an argon filled glove box (typically < 1 ppm of oxygen and moisture) to avoid contamination. All prepared samples and

reference materials mentioned above were sent to the Stanford Synchrotron Radiation Lightsource (SSRL) in an air-tight container and directly brought into an argon filled glove box present at the SSRL.

5 In-situ cell

The in-situ cell used for the XRS measurements has been described elsewhere²⁰. In short, this cell was optimized for a large solid angle of the (high momentum transfer q) inelastic scattered X-rays through a large exit window. The exit window is wide enough to record both high and low q inelastic scattered X-rays without changing the cell position. For the XRS measurements, samples were pressed in a sample holder and subsequently attached inside the unscrewed in-situ cell remaining inside the argon filled glove-box at SSRL. After pressing the sample in the sample holder, the in-situ cell was screwed air-tight and the complete in-situ cell was taken out of the glove-box and ready for XRS experiments.

X-ray Raman Spectroscopy (XRS) measurements

In X-ray Raman Spectroscopy (XRS) an incident (hard) x-ray photon is inelastically scattered and part of its energy is transferred to excite an inner shell electron into an unoccupied state. Under the dipole approximation, which is for XRS valid for small forward x-ray scattering angles, the resulting features are identical to the x-ray absorption spectroscopy and the energy loss associated with the inelastic scattering is equal to the x-ray absorption energy. In the case of light elements, where the x-ray edges are in the low soft x-ray energy regime, XRS is a wonderful alternative for x-ray absorption spectroscopy²¹.

Lithium (Li), boron (B) and carbon (C) K-edge XRS were collected at SSRL beamline BL6-2 ES2²⁴. The in-situ cell was mounted such that the angle with the beam was the same at every measurement. The XRS measurements were performed using the inverse energy scan technique, i.e., the scattered photons were analysed at fixed energy (here 6462.2 eV) whereas the energy transfer is controlled by tuning the incident photon energy. The XRS spectra were measured in forward scattering angles (low q), using only the four lowest momentum transfer (q) rows of the 40-crystal spectrometer (0.8 \AA^{-1} , 1.2 \AA^{-1} , 1.5 \AA^{-1} and 1.9 \AA^{-1} respectively). This had two goals: first to minimize the non-dipole contributions within the XRS of the Li K-edge, and secondly to reduce background noise in the B K-edge XRS or in other words to improve the B K-edge XRS signal-to-noise ratio. The background noise reduction is important to obtain more information on changes in the B K-edge after de- and re-hydrogenation compared to our former experiments²⁰. The XRS measurements were plotted as scattered intensity versus energy loss, which is the incident energy minus the elastic energy of the (fixed energy) analyzer and the energy resolution of the XRS spectra was about 0.2 eV. During the XRS measurements the in-situ cell was under a helium atmosphere flow (99.999% pure) or in some cases under a hydrogen flow of 10 ml/min, which was used as a carrier gas.

The Li and B K-edge XRS of reference compounds, bulk LiBH_4 and of LiBH_4/C as prep, deh ex-situ and reh ex-situ were measured under 10 ml/min helium flow. The LiBH_4/C as prep sample was de-hydrogenated in-situ by heating under helium to 370 °C and the Li, B and C K-edges measured at different

temperatures during decomposition. The ex-situ de-hydrogenated sample (LiBH_4/C deh) was partially re-hydrogenated in-situ by heating under 1 bar of (pure) hydrogen (99.999%) with a flow of 10 ml/min. to 370 °C with a ramp of 10 °C/min. and after a dwell time of 30 minutes at 370 °C, the sample was cooled down to room temperature. Li and B K-edge XRS measurements were performed at both 370 °C and at room temperature. Note that we mention that the LiBH_4/C nanocomposites were only partially re-hydrogenated in this case, since the in-situ cell can only handle 1 bar hydrogen and much higher pressures are required for a (close to) full re-hydrogenation.

70 Results and discussion

B K-edge XRS of LiBH_4/C

Figure 1 shows the B K-edge XRS spectra of LiBH_4/C as prep, bulk LiBH_4 and the LiBO_2 reference. The B K-edge of bulk LiBH_4 powder (red line) and the melt-infiltrated nanoconfined sample LiBH_4/C as prep (black line) have a similar peak at 191.8 eV. This implies that the electronic properties and structure of LiBH_4 in the as-prepared LiBH_4/C nanocomposite remain mostly unchanged, which is in line with literature reports on LiBH_4 confined in similar nanoporous carbon material^{12,13,25}. However for LiBH_4/C as prep, there is also a peak at 194 eV and extra features at higher energy loss which resembles the B K-edge of LiBO_2 . There is a variety of oxidic lithium and boron species, but the most stable and therefore relevant ones are LiBO_2 and B_2O_3 . The experimental spectrum of B_2O_3 is given in the Supp. Info, Figure S4.

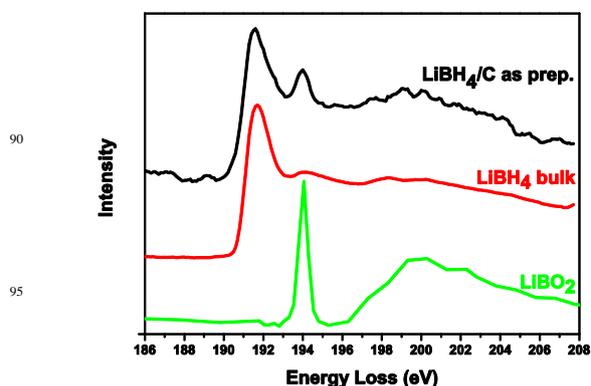


Figure 1. Boron (B) K-edge XRS of LiBH_4/C as prepared (LiBH_4/C as prep., black), compared to the B K-edge XRS of bulk LiBH_4 powder (LiBH_4 bulk, red) and lithium metaborate powder (LiBO_2 , green)

The peak at 194 eV in the LiBH_4/C as prep is already present in the first measurement, but time evolution of the B K-edge XRS (Supplementary Information, figure S2) shows that this peak increases with time. Since oxygen was excluded as much as possible during the preparation and handling of the LiBH_4/C nanocomposite, we attribute the presence of the oxidic boron to possible reactions between traces of carbon surface oxygen groups and LiBH_4 at high temperatures during the melt infiltration process for the preparation of the LiBH_4/C nanocomposites. This is supported by the fact that the 194 eV peak is observed in the first B K-edge measurement already and the time evolution of the 194 eV peak to the <1ppm oxygen in the

helium carrier gas used for the hydrogen desorption of the LiBH₄/C nanocomposites. On one side all the B K-edge XRS measurements of reference materials do not show oxygenation after prolonged exposure to x-rays. On the other side, we cannot completely exclude x-ray induced oxidation, since the nanoconfined materials are expected to be more reactive. Recent NMR studies on similar NaBH₄/C nanocomposites also indicate the presence of minor amounts of NaBO₂ in the as-prepared nanocomposites¹⁰. The present results show that the B K-edge XRS is highly sensitive to boron oxides, because the peak at 194 eV is quite intense and already present even when small amounts of oxygen react with the LiBH₄. This observation also indicates that the presence of even a trace amount of oxygen could be detrimental to the accurate evaluation of the decomposition mechanism of borohydride since the decomposition pathways and products could be changed. We also measured the oxygen K-edge XRS of some of the samples (see Suppl. Info. S15) and the results confirm that the increase of the peak at 194 eV is indeed due to oxidation and very likely from a continuing source of oxygen (120 ppm of oxygen in helium or hydrogen flow).

However, based on the B K-edge of the oxygen-containing reference materials, the electronic information below 194 eV in the B K-edge can be used for further analysis on de- and re-hydrogenation and in the further qualitative and quantitative analysis we focus mainly on the B K-edge XRS spectra below 194 eV. All the XRS spectra with the full measured B K-edge energy loss range can be found in the Supplementary Information (figure S9).

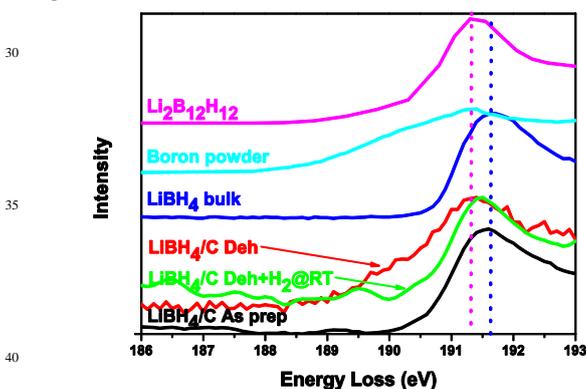


Figure 2. B K-edge XRS spectra with energy loss range till 193 eV of: LiBH₄/C as prepared (As prep, black), after de-hydrogenation (Deh, red) and after partial re-hydrogenation under 1 bar pressure of hydrogen flow (Deh+H₂@RT, green) compared with the B K-edge XRS of the reference materials LiBH₄ bulk (blue), boron powder (light blue) and Li₂B₁₂H₁₂ (magenta). The vertical blue and magenta dotted lines refer to the maximum of LiBH₄ bulk (blue) and Li₂B₁₂H₁₂ (magenta) respectively.


Figure 2 shows the B K-edge XRS energy loss range till 193 eV of LiBH₄/C as prep, LiBH₄/C deh and after partial re-hydrogenation, further called LiBH₄/C Deh+H₂@RT. We focus first on the differences between the LiBH₄/C as prep (black) and LiBH₄/C deh (red). The main peak at 191.5 eV for LiBH₄/C as prep shifts to lower energy for the LiBH₄/C deh. This peak was attributed to LiBH₄ based on Figure 1 and in that sense LiBH₄ has disappeared and de-hydrogenation leads to a shifted peak, in other words to a modified material where boron is more negatively (or less positively) charged.

Comparing the B K-edge XRS of the LiBH₄/C deh (red) with the

bulk LiBH₄ (blue), Li₂B₁₂H₁₂ (magenta) and boron powder (light blue) shows that LiBH₄/C deh contains boron and / or Li₂B₁₂H₁₂. Bulk LiBH₄ is generally believed to decompose according to equations 2a and 2b²⁵⁻²⁸:



In the case of nanoconfined LiBH₄, lithium intercalation in the graphitic carbon has been reported^{11, 12, 19, 29}, therefore lithium could be stabilized, leading to the following possible decomposition reactions:



Note that for reactions (3a) and (3b), LiC_x represents intercalated lithium and does not imply the formation of Li-C bonds.

It is clear that the B K-edge XRS spectrum of LiBH₄/C deh (figure 2, red) does not completely match either the B K-edge XRS of Boron powder (light blue) or the Li₂B₁₂H₁₂ (magenta) reference materials but the B K-edge XRS spectrum of LiBH₄/C deh seems a combination of both materials. To estimate the fraction of both materials in the de-hydrogenated sample, the B K-edge XRS spectra of the different reference materials were area-normalized to their boron content with the area below the XRS curves as mentioned and shown in the Supplementary Information (figure S5). The slope of the first peak in the B K-edge of LiBH₄/C deh is strongly linked to the content of boron powder and the height of the XRS peak is connected to the Li₂B₁₂H₁₂ reference. Based on the relative combinations of the two references, all the ranges between 20% and 80% of boron and Li₂B₁₂H₁₂ show reasonable agreement with the B K-edge XRS of LiBH₄/C deh (figure 3 A) with the best fit shown as green dashed line (50% boron and 50% Li₂B₁₂H₁₂). We estimate from the B K-edge XRS that there is 50±30% of boron and 50%±30% of Li₂B₁₂H₁₂ present in the LiBH₄/C deh sample. For an assignment with smaller error bars we might have to consider the Li K-edge XRS deconvolution of LiBH₄/C deh as well (see next section). Note that the presence of both B and Li₂B₁₂H₁₂ in the de-hydrogenated sample is in line with the fact that only limited lithium intercalation (lithium insertion) occurs in this graphitic carbon^{11, 30}, so a combination of reactions (2a,2b) and (3a,3b) could be expected. Another possibility is that the 25 wt% LiBH₄/C contains a small amount of bulk LiBH₄ (that did not go into the pores of the nanoporous carbon and thus is not nanoconfined), which does not completely de-hydrogenate under the present temperature conditions and that is why we observe more Li₂B₁₂H₁₂ than expected based on reaction equation (3a). One can imagine that LiBH₄ close to the carbon surface could be de-hydrogenated following (3b) while the remaining LiBH₄ will de-hydrogenate either according to reaction equations (2a, 2b) or with a ratio of 12:1 for LiBH₄ to carbon via reaction equation (3a). The Li K-edge XRS could as well be informative on this aspect, since whenever boron is present also LiH or Li in some form should be present.

In addition to de-hydrogenation ex-situ, we performed in-situ partial re-hydrogenation of the de-hydrogenated sample under 1

bar of hydrogen pressure, and 400 °C for half an hour and measure the B and Li K-edge XRS of the in-situ partially re-hydrogenated products after cooling down. The green line in figure 2 presents the B K-edge XRS spectrum of LiBH₄/C deh that was subsequently partially re-hydrogenated in-situ (LiBH₄/C deh+H₂@RT). Note the similarity with the LiBH₄/C As prep (black line), During the in-situ partial re-hydrogenation, the B K-edge XRS peak at 194 eV assigned to oxidic boron increases even more (figure 3B, black).

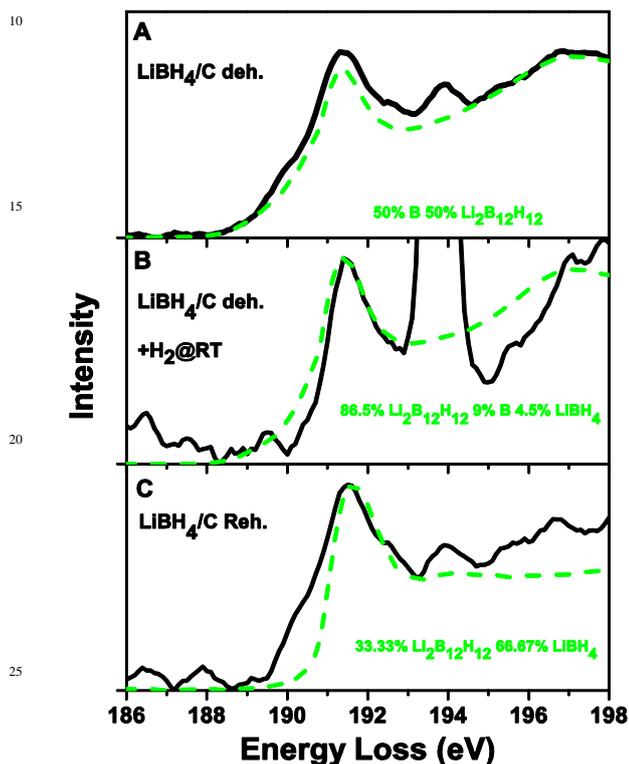


Figure 3. Fits of the deconvolution of the B K-edge XRS of (A) LiBH₄/C deh, (B) LiBH₄/C deh+H₂@RT and (C) LiBH₄/C Reh. Black lines correspond to the experimental B K-edge XRS of the LiBH₄/C at different points in the re-hydrogenation process and green dashed lines are the best convolution fit with their different percentages of reference materials. More deconvolution results are shown in the Supplementary Information (figure S14).

That means that the reaction to form LiBO₂ continues during the re-hydrogenation process, which is expected as the dehydrogenated sample is even more reactive and sensitive to oxygen. This also affects the accuracy of the B K-edge measurements as the background becomes higher relative to the main peak close to 191.5 eV (figure 2, green line). Nevertheless, the start of the band around 190–191 eV shifts back to higher energy loss values for the B K-edge XRS of LiBH₄/C deh+H₂@RT. The distinct B K-edge slope of boron powder is almost lacking for the LiBH₄/C deh.+H₂@RT. The deconvolution of LiBH₄/C deh.+H@RT with the best fit is shown in figure 3B. Based on this deconvolution result there is about 10% boron present, a majority (>80%) Li₂B₁₂H₁₂ and a little amount (~5%) of LiBH₄. This result seems to suggest that with 1 bar of hydrogen, partial re-hydrogenation to LiBH₄ can be achieved for these nanoconfined LiBH₄/C samples. It is likely that this occurs with the reverse route of reaction equation (3b). While a large

proportion of the boron is not present anymore, it is also likely that the reverse route of reaction equation (2b) occurred. This implies that LiBH₄/C follows the same de-/re-hydrogenation route as bulk LiBH₄, but that in addition there is a more direct way for re-hydrogenation to LiBH₄ (reverse route of reaction equation (3b)) for the LiBH₄ confined in nanoporous carbon compared to de- and re-hydrogenation of bulk LiBH₄.

The B K-edge XRS of the ex-situ re-hydrogenated sample, LiBH₄/C reh (figure 3C, black line; full B K-edge range Supp. Info. figure S8) relates to a combination of the B K-edge XRS spectra of the LiBH₄/C as prep and LiBH₄/C deh spectra. Note that the ex-situ re-hydrogenation was done by heating the dehydrogenated sample at 60 bar of H₂ and 325 °C for 3 hrs while the partial in-situ re-hydrogenation was done by heating the in-situ cell de-hydrogenated samples to 370°C under a constant 10 mL flow of 1 bar H₂. After deconvolution analysis of the LiBH₄/C reh, the best fit (blue line) is shown in figure 3C. It is estimated that the ex-situ re-hydrogenated LiBH₄/C contains 20±10% boron, 40±20% Li₂B₁₂H₁₂ and 40±20% LiBH₄. This implies that the sample has not been fully rehydrogenated to LiBH₄ based on the B K-edge XRS of LiBH₄/C reh. Formation of 40±20% LiBH₄ after ex-situ rehydrogenation is also in-line with the fact that only about 6.5wt% H₂/g LiBH₄ was realised from the ex-situ rehydrogenated sample during the second cycle of hydrogen release experiment conducted ex-situ³⁰.

Li K-edge XRS of LiBH₄/C

The Li K-edge XRS spectra of the LiBH₄/C as prep (pink line) and LiBH₄/C deh (brown line) are shown in figure 4 together with LiBO₂, Li, LiH and LiBH₄ references. The Li–LiH–LiBH₄ series shows its first peak shifting to higher energies indicating an increased Li charge/valence. According to our knowledge, this is the first time that the Li K edge of LiH is published, which is possible due to the in-situ reactor that can prevent the oxidation or decomposition of LiH in (humid) air.

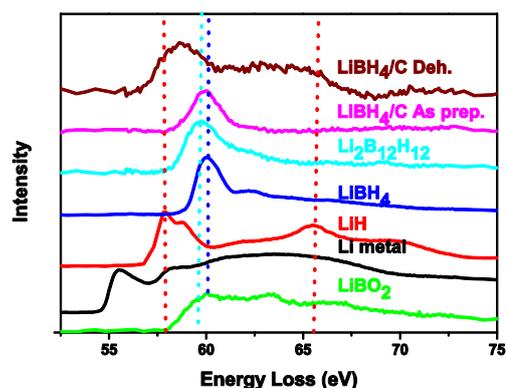


Figure 4. Lithium K-edge XRS spectra of the reference materials bulk LiBO₂ powder (green), Li metal (black), LiH powder (red), bulk LiBH₄ powder (blue) and Li₂B₁₂H₁₂ (light blue) in comparison with the LiBH₄/C as prepared (LiBH₄/C as prep, pink) and the de-hydrogenated LiBH₄/C (LiBH₄/C deh., brown). The main peaks of LiBH₄, LiH and Li₂B₁₂H₁₂ are indicated with dotted lines corresponding to the color of the XRS.

The Li K-edge XRS spectrum of LiBH₄/C as prep (figure 4, pink line) agrees well with the Li K-edge XRS spectrum of the LiBH₄ bulk reference, supporting the B K-edge assignment above for LiBH₄/C as prep (figure 1) and the assignment in an earlier report^[25]. The LiBH₄/C deh (figure 4, brown line) has a band which is

slightly broader than for the LiH reference, but at first glance it seems that the Li K-edge XRS spectrum of LiBH₄/C deh contains all the features of the XRS spectrum of LiH. According to the comparison between the Li K-edge XRS spectrum of LiBH₄/C deh and the Li K-edge XRS of lithium, there is no metallic lithium present in the LiBH₄/C deh sample, which would suggest that the de-hydrogenation reaction did not go further than the formation of B and LiH (equation 2a-2b). However on the contrary, about 15wt% H₂ was released from the sample during an ex-situ hydrogen release measurement conducted under similar conditions, but with Ar carrier gas instead of He (see e.g.,³⁰). This would suggest further decomposition of some part of LiH or Li₂B₁₂H₁₂ into Li or intercalated Li according to equations (3a or 3b). Furthermore, using XRD, reversible Li intercalation has been demonstrated earlier in these samples^{11, 30}. Therefore if reaction (3a or 3b) did occur to some extent, the lithium is likely intercalated in the carbon. Unfortunately, we do not know how the Li K-edge XRS features of intercalated lithium will look like in the present carbon nano-framework and therefore we do not know its features in Li XRS, but we expect that this is also present in Li XRS spectrum of the LiBH₄/C deh due to the broader band area between 60 and 62 eV. That area cannot be assigned to any of the reference materials measured by us, but the Li K-edge EELS spectrum of intercalated lithium of Wang et al.³¹ shows qualitative agreement with these unassigned features. It seems there is also a partial contribution of Li₂B₁₂H₁₂ in the de-hydrogenated sample. The Li K-edge XRS spectrum of LiBH₄/C deh also should show some LiBO₂ (green line) features as we saw before in the B K-edge, but it is difficult to make the oxide influence quantitative, because the Li K-edge XRS of LiBO₂ does not contain sharp features. As there is no reference material for the intercalated lithium in the nanoporous carbon used here (which might be slightly different from Ref.³¹), it is not straightforward to perform a proper deconvolution of the Li K-edge XRS spectrum of LiBH₄/C deh. However as a careful guess the Li K-edge XRS of LiBH₄/C deh can be deconvoluted into 70±30% of LiH and 20±30% of Li₂B₁₂H₁₂, while we consider an extra error due the possibility that there can be 10±10% of intercalated lithium present, also in line with results obtained based on previous XRD³⁰ and ⁷Li NMR results¹⁹.

In the Li K-edge XRS spectra of the LiBH₄/C deh+H₂@RT and LiBH₄/C reh (Supplementary Information figure S10B), the deconvolution is possible again, since the feature between 60-62 eV disappeared and apparently all the intercalated lithium reacted to something else under 1 or 50 bar of hydrogen. The result of the deconvolution of LiBH₄/C deh+H₂@RT (Supplementary Information, figure S12) is: 5±3% LiH, 95±3% Li₂B₁₂H₁₂ and ~2±3% LiBH₄, which is consistent with the >80% Li₂B₁₂H₁₂ and 5% LiBH₄ deconvolution results from the B K-edge XRS of LiBH₄/C deh+H₂@RT (figure 3B).

Concerning the deconvolution of the Li K-edge XRS of the LiBH₄/C reh in 20±20% LiH, 20±20% Li₂B₁₂H₁₂ and 60±20% of LiBH₄ (Supp. Info., figure S13) there is agreement with the B K-edge XRS deconvolution assignments concerning amounts of LiBH₄ and Li₂B₁₂H₁₂, but there is an unexpected increase in amount of LiH compared to the partially re-hydrogenated sample LiBH₄/C deh+H₂@RT.

Discussion

The de-hydrogenation of LiBH₄ to Li₂B₁₂H₁₂, boron, LiH and intercalated lithium and re-hydrogenation back to LiBH₄ can be followed with the resemblance of the 190-191 eV band in the B K-edge XRS and the bands between 58-60 and 60-62 eV (intercalated lithium) in the Li K-edge XRS in comparison to spectra of reference materials. The XRS results provide evidence that the nanoconfined material partially re-hydrogenates to LiBH₄ under 1 bar of hydrogen, but it remains only a small percentage of the overall amount of compounds (See Table 1, fourth column).

Table 1. Summary of deconvolution results of the B and Li K-edge XRS of LiBH₄/C as prep., deh, deh+H₂@RT and reh.

XRS	As prep	Deh	Part. Reh.	Reh.
B K-edge	~100% LiBH ₄	50±30% Boron,	10±10% boron,	20±10% boron,
		50±30% Li ₂ B ₁₂ H ₁₂	>80±10% Li ₂ B ₁₂ H ₁₂ ,	40±20% Li ₂ B ₁₂ H ₁₂
			~5±5% LiBH ₄	40±20% LiBH ₄ ,
Li K-edge	~100% LiBH ₄	70±30% LiH,	5±3% LiH,	20±20% LiH,
		20±30% Li ₂ B ₁₂ H ₁₂ ,	95±3% Li ₂ B ₁₂ H ₁₂ ,	20±20% Li ₂ B ₁₂ H ₁₂ ,
		~10±10% LiC _x	~2±3% LiBH ₄	60±20% LiBH ₄

Combining the information from the Li and B K-edge XRS, it can be concluded that the nanoconfined LiBH₄/C dehydrogenates into 50 to 80% boron and LiH and 20 to 50% of Li₂B₁₂H₁₂ and there is likely some amount of lithium intercalated in the carbon (estimate ~10%). Since we do not see any metallic lithium, but only intercalated lithium or lithium compounds that still contain an amount of hydrogen (LiH and Li₂B₁₂H₁₂) we underline the suggestion that nanoporous carbon material stabilizes the Li de-hydrogenation products (and in particular metallic-like lithium) as reported previously^{12,13}. The unknown feature in the Li K-edge, presently assigned to intercalated lithium (LiC_x) disappears with (partial) re-hydrogenation. The deconvolution analysis of the B K-edge XRS of LiBH₄/C that was partially re-hydrogenated (LiBH₄/C deh+H₂@RT) demonstrated with reference to the LiBH₄/C deh, that there is a lower boron content (<10±10%), some formation (2%) of LiBH₄ in this case and the major component is Li₂B₁₂H₁₂. The deconvolution of the Li K-edge XRS of LiBH₄/C deh+H₂@RT supports that the formation of about 2-5% of LiBH₄, and also suggests that the major component is Li₂B₁₂H₁₂.

Based on both the Li K-edge and B K-edge XRS of LiBH₄/C reh, it is estimated that the nanoconfined LiBH₄ after full de- and re-hydrogenation ex-situ consists of approximately 60% of LiBH₄, 20-30% of Li₂B₁₂H₁₂, 10% of boron and 10-20% of LiH. Interestingly, these numbers are in line with the amount of H₂ released from the rehydrogenated sample during ex-situ temperature programmed hydrogen release measurements.

In summary the B and Li K-edge XRS spectra show that LiBH₄/C changes from LiBH₄ to a combination of intercalated lithium, LiH, and B and some Li₂B₁₂H₁₂ and in the first re-

hydrogenation step (under a small hydrogen pressure) a small amount of LiBH_4 is reformed, but mainly $\text{Li}_2\text{B}_{12}\text{H}_{12}$ is formed and after full re-hydrogenation at least 60% of LiBH_4 is reformed, while still some amounts of LiH , B and $\text{Li}_2\text{B}_{12}\text{H}_{12}$ are present. Thus XRS shows that partial re-hydrogenation of LiBH_4 is possible under the in-situ 1 bar H_2 , which is most likely due to the recombination of the LiC_x and some B in the presence of H_2 . As well under the ex-situ full re-hydrogenation conditions it is observed that there is no complete re-hydrogenation which has been reported before¹². Remaining questions are: What does the increase of the amount of LiH between partial re-hydrogenation and full re-hydrogenation conditions mean? Is this due to the much stronger stability of LiH compared to the other intermediate and final phases? And: Is there a change in the second de- and re-hydrogenation cycle?

We mentioned in the experimental section that also the carbon (C) K-edge XRS of the LiBH_4/C materials was measured under the different as prepared, de- and re-hydrogenation conditions. We do not see clear differences in the C K-edge XRS (shown in the Supplementary information, figure S16) meaning that the carbon material is stable under all the different conditions or that the differences are smaller than the obtained C K-edge XRS resolution.

As mentioned in the introduction, B and C K-edge XRS measurements were also performed on nanoconfined sodium borohydride (NaBH_4/C) under different de- and re-hydrogenation conditions (Figures S17, S19 and S21). Similar to nanoconfined LiBH_4 , we also saw a shift in the B K-edge energy of the dehydrogenated nanocomposites as compared to the sample as prepared or the NaBH_4 bulk (fig S19), suggesting the formation of $\text{Na}_2\text{B}_{12}\text{H}_{12}$ as earlier reported (for example¹⁰). Also slight shift towards the original value occurred in the ex-situ rehydrogenated samples due to partial reversibility of these samples^{10, 30}. However detailed quantification of the phases was not possible due to the lack of data on other standard reference materials like $\text{Na}_2\text{B}_{12}\text{H}_{12}$ during the XRS measurements. Nevertheless, these results demonstrate that XRS can be applied as well for the study of the decomposition of other borohydrides and B-based hydrogen storage materials.

Conclusions

Using X-Ray Raman Spectroscopy it was found that the spectrum of LiBH_4/C is similar to the spectrum of bulk LiBH_4 powder, in agreement with other experiments^{11, 12}. During and after dehydrogenation, the LiBH_4/C decomposes mainly in LiH and boron and there is also a substantial amount of $\text{Li}_2\text{B}_{12}\text{H}_{12}$. In addition we observed a signature of intercalated Li in carbon, based on features in the Li K-edge XRS that resemble the Li K-edge EELS features of intercalated lithium³¹. During rehydrogenation, the first step (observed under 1 bar of hydrogen pressure) suggest the formation of LiH and $\text{Li}_2\text{B}_{12}\text{H}_{12}$ and already a small amount of LiBH_4 formed from the combination of intercalated Lithium in carbon, boron and hydrogen. This suggests that the nanoconfined LiBH_4 has a different hydrogen re-absorption mechanism (reverse reaction of equation 3b) which is different from that of bulk de-hydrogenated LiBH_4 , since under normal conditions the presence of LiBH_4 is unexpected under 1

bar of hydrogen pressure. After full re-hydrogenation, there is mainly LiBH_4 and there are minor contributions from $\text{Li}_2\text{B}_{12}\text{H}_{12}$, LiH and boron still present. All these conclusions are based on the combined deconvolution of the B and Li K-edge XRS.

Summarized in general, the results presented here on the XRS of nanoconfined LiBH_4 and NaBH_4 in the Supplementary Information, combined with the XRS of reference materials, shows that XRS may soon become an important tool for characterizing the different phases of the complex hydrogen storage materials based on B and other light elements such as Li and Na. This is particularly very useful for the characterization of the often non-crystalline phases present in nano-confined hydrogen storage materials.

Corresponding Author

*Piter S. Miedema, p.s.miedema@gmail.com,

Acknowledgments

PSM and FMFdG acknowledge NWO- CW/VICI and PN and acknowledge NWO-CW/VIDI 016.072.316 for financial support. We would like to thank the Stanford Synchrotron Radiation Lightsource (SSRL) for beamtime. The SSRL is a National User Facility operated by Stanford University on behalf of the U.S. Department of Energy, Office of Basic Energy Sciences. Timcal Switzerland is acknowledged for the provision of the graphite and porous carbon.

Notes and references

- ^a Department of Inorganic Chemistry and Heterogeneous Catalysis, Debye Institute for Nanomaterials Science, Utrecht University, Universiteitsweg 99, 3584 CG Utrecht, The Netherlands; E-mail: p.s.miedema@gmail.com
- ^b Stanford Synchrotron Radiation Lightsource, SLAC National Accelerator Laboratory, 2575 Sand Hill Road, Menlo Park, CA 94025, USA
- † Electronic Supplementary Information (ESI) available: [$\text{Li}_2\text{B}_{12}\text{H}_{12}$ XRD, time evolution B and Li K-edge XRS spectra, comparison of different fractions of references with the B and Li K-edge XRS of LiBH_4/C under different conditions, B K-edge XRS experiments and XAS calculations on NaBH_4 and $\text{Na}_2\text{B}_{12}\text{H}_{12}$ and the C K-edge XRS of NaBH_4/C and LiBH_4/C under different conditions can be found in the supplementary information.]. See DOI: 10.1039/b000000x/
- ‡ The present address for dr. Piter S. Miedema is the Institute for Methods and Instrumentation for Synchrotron Radiation Research G-100 ISRR, Helmholtz-Zentrum für Materialien und Energie GmbH, Albert-Einstein-Strasse 15, 12489 Berlin, Germany. The present address for Peter Ngene is the Group for Materials for Energy Conversion and Storage, Chemical Engineering, Faculty of Applied Sciences, Delft University of Technology, Julianalaan 136, 2628 BL Delft, The Netherlands.
1. Y. Nakamori, K. Miwa, H. W. Li, N. Ohba, S. I. Towata and S. I. Orimo, Mater. Res. Soc. Symp. Proc., 2006.
 2. H. W. Li, Y. G. Yan, S. Orimo, A. Züttel and C. M. Jensen, *Energies*, 2011, **4**, 185-214.
 3. P. Martelli, R. Caputo, A. Remhof, P. Mauron, A. Borgschulte and A. Züttel, *J. Phys. Chem. C*, 2010, **114**, 7173-7177.
 4. P. Mauron, F. Buchter, O. Friedrichs, A. Remhof, M. Biemann, C. N. Zwicky and A. Züttel, *J. Phys. Chem. B*, 2008, **112**, 906-910.
 5. M. Aoki, K. Miwa, T. Noritake, G. Kitahara, Y. Nakamori, S. I. Orimo and S. Towata, *Applied Physics A* 2005, **80**, 1409.

6. M. Au, A. Jurgensen and K. Zeigler, *J. Phys. Chem. B*, 2006, **110**, 26482.
7. Z. Z. Fang, X. D. Kang, P. Wang and H. M. Cheng, *J. Phys. Chem. C*, 2008, **112**, 17023.
8. A. F. Gross, J. J. Vajo, S. L. Van Atta and G. L. Olson, *Journal of Physical Chemistry C*, 2008, **112**, 5651-5657.
9. X. D. Kang, P. Wang, L. P. Ma and H. M. Cheng, *Applied Physics A*, 2007, **89**, 963.
10. P. Ngene, R. Van Den Berg, M. H. W. Verkuijlen, K. P. De Jong and P. E. De Jongh, *Energy and Environmental Science*, 2011, **4**, 4108-4115.
11. P. Ngene, R. Van Zwielen and P. E. De Jongh, *Chemical Communications*, 2010, **46**, 8201-8203.
12. P. Ngene, M. H. W. Verkuijlen, Q. Zheng, J. Kragten, P. J. M. van Bentum, J. H. Bitter and P. E. de Jongh, *Faraday discussions*, 2011, **151**, 47.
13. G. L. Xia, X. B. Yu, Z. Q. Zou, Z. L. Li, Z. Wu, D. L. Akins and H. Yang, *Chemical Communications*, 2008, **44**, 5740.
14. J. Xu, X. B. Yu, Z. Q. Zou, Z. L. Li, Z. Wu, D. L. Akins and H. Yang, *Chemical Communications*, 2008, **44**, 5470.
15. M. L. Christian and K.-F. Aguey-Zinsou, *ACS Nano*, 2012, **6**, 7739.
16. D. B. Ravnsbaek, Y. Filinchuk, R. Cerný and T. R. Jensen, *Zeitschrift für Kristallography*, 2010, **225**, 557.
17. A. Remhof, P. Mauron, A. Züttel, J. P. Embs, Y. Lodziana, A. J. Ramirez-Cuesta, P. Ngene and P. E. de Jongh, *J. Phys. Chem. C*, 2013, **117**, 3789.
18. A. Remhof, Z. Lodziana, P. Martelli, O. Friedrichs, A. Züttel, A. V. Skripov, J. P. Embs and T. Strässle, *Physical Review B*, 2010, **81**, 214304.
19. M. H. W. Verkuijlen, P. Ngene, D. W. de Kort, C. Barré, A. Nale, E. R. H. van Eck, P. J. M. van Bentum, P. E. de Jongh and A. P. M. Kentgens, *J. Phys. Chem. C*, 2012, **116**, 22169.
20. P. S. Miedema, P. Ngene, A. M. J. Van Der Eerden, T. C. Weng, D. Nordlund, D. Sokaras, R. Alonso-Mori, A. Juhin, P. E. De Jongh and F. M. F. De Groot, *Physical Chemistry Chemical Physics*, 2012, **14**, 5581-5587.
21. U. Bergmann, P. Glatzel and S. P. Cramer, *Microchemical Journal*, 2002, **71**, 221-230.
22. L. He, H.-W. Li, S.-J. Hwang and E. Akiba, *The Journal of Physical Chemistry C*, 2014, **118**, 6084-6089.
23. O. Friedrichs, A. Remhof, S. J. Hwang and A. Züttel, *Chemistry of Materials*, 2010, **22**, 3265-3268.
24. D. Sokaras, D. Nordlund, T.-C. Weng, R. Alonso-Mori, P. Velikov, D. Wenger, A. Garachtchenko, M. George, V. Borzenets, B. C. Johnson, Q. Qian, T. Rabedeau and U. Bergmann, *Review of Scientific Instruments*, 2012, **83**, 043112.
25. S. I. Orimo, Y. Nakamori, N. Ohba, K. Miwa, M. Aoki, S. I. Towata and A. Züttel, *Applied Physics Letters*, 2006, **89**.
26. S. J. Hwang, R. C. Bowman Jr, J. W. Reiter, J. Rijssenbeek, G. L. Soloveichik, J. C. Zhao, H. Kabbour and C. C. Ahn, *Journal of Physical Chemistry C*, 2008, **112**, 3164-3169.
27. S. Kato, M. Biemann, A. Borgschulte, V. Zakaznova-Herzog, A. Remhof, S. I. Orimo and A. Züttel, *Physical Chemistry Chemical Physics*, 2010, **12**, 10950.
28. Y. Yan, A. Remhof, S.-J. Hwang, H.-W. Li, P. Mauron, S.-i. Orimo and A. Züttel, *Physical Chemistry Chemical Physics*, 2012, **14**, 6514-6519.
29. P. Adelhelm and P. E. de Jongh, *Journal of Materials Chemistry*, 2011, **21**, 2417-2427.
30. P. Ngene, PhD thesis, Utrecht, 2012.
31. F. Wang, J. Graetz, M. S. Moreno, C. Ma, L. Wu, V. Volkov and Y. Zhu, *ACS Nano*, 2011, **5**, 1190-1197.