

PCCP

Accepted Manuscript



This is an *Accepted Manuscript*, which has been through the Royal Society of Chemistry peer review process and has been accepted for publication.


Accepted Manuscripts are published online shortly after acceptance, before technical editing, formatting and proof reading. Using this free service, authors can make their results available to the community, in citable form, before we publish the edited article. We will replace this *Accepted Manuscript* with the edited and formatted *Advance Article* as soon as it is available.

You can find more information about *Accepted Manuscripts* in the [Information for Authors](#).

Please note that technical editing may introduce minor changes to the text and/or graphics, which may alter content. The journal's standard [Terms & Conditions](#) and the [Ethical guidelines](#) still apply. In no event shall the Royal Society of Chemistry be held responsible for any errors or omissions in this *Accepted Manuscript* or any consequences arising from the use of any information it contains.

Table of contents:

In nonlinear optically DCNP single crystal fluorescence origins from structural traps what was evidenced by kinetics measurements at 5 K.

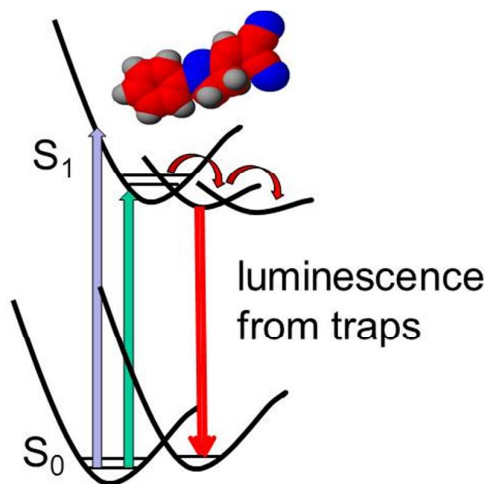

On the origin of fluorescence emission in optically non-linear DCNP crystal

O. Morawski^a, A. L. Sobolewski^a, B. Kozankiewicz^a, L. Sznitko^b, A. Miniewicz^b

Received 00th January 2012,
Accepted 00th January 2012

DOI: 10.1039/x0xx00000x

www.rsc.org/

We study absorption and emission spectra of optically nonlinear single crystal of 3-(1,1-dicyanoethenyl)-1-phenyl-4,5-dihydro-1H-pyrazole (DCNP) at 5 K. We argue that fluorescence has complex origin, it is emitted from excitonic band, with the bottom at $\sim 18115 \text{ cm}^{-1}$, and from trap states, and the two main traps have depths ~ 875 and $\sim 2465 \text{ cm}^{-1}$. The excitonic origin of the emission is confirmed by vibrational structure of fluorescence, closely resembling vibrations observed in the Raman scattering spectrum (recorded for DCNP crystal at 295 K) and by very short decay time of the excitonic emission, being consequence of excitons migration and trapping at deep traps.

1 Introduction

Pyrazoles are important heterocyclic compounds whose derivatives are used in a number of applications in medicine¹⁻³. This, so called azole family, includes also imidazoles, oxadiazoles, oxazoles and thiazoles⁴. Pyrazoles, with their ring structure composed of three carbon and two nitrogen atoms, create the π -electron conjugated systems that lead to the possibility of molecular nonlinear optical (NLO) activity. Optical and NLO properties of the number of pyrazole derivatives were already reported in the literature⁵⁻¹⁴.

The title compound 3-(1,1-dicyanoethenyl)-1-phenyl-4,5-dihydro-1H-pyrazole, abbreviated as DCNP ($\text{C}_{13}\text{H}_{10}\text{N}_4$, $M_w = 222.25 \text{ g}$) is a good example of a low-molecular mass organic dye classified as nonlinear optical chromophore due to its anisotropic “push-pull” character as described in Ref.¹². The molecular structure of this compound has been schematically shown in Fig. 1. Fluorescence properties of the single crystals of DCNP under single and two-photon excitation conditions at temperatures between room and 77 K were already reported in Ref.¹⁴. Within this temperature range the fluorescence spectrum is composed of two broad bands, one centred at about 580 and the second at 640 nm, with continuous transfer of the intensity from the higher energy band to the lower energy band following a temperature increase. Such observation raises the question about the origin of both bands. The present studies should also help in interpretation of luminescence from DCNP nanocrystals and amplified spontaneous emission and lasing¹⁵.

DCNP crystallizes in the monoclinic non-centrosymmetric space group Cc (point group m) with pseudo-orthogonal geometry where $Z = 4$ molecules of DCNP occupy a unit cell. First crystallographic structure of DCNP crystal was reported by Allen et al.¹² The more precise structural studies of this compound both by X-ray and neutron diffraction have been

done by Cole et al.¹³ at 90, 100, 200 and 290 K. The cell parameters $a = 11.8751 \text{ \AA}$, $b = 12.3735 \text{ \AA}$, $c = 7.8876 \text{ \AA}$, $\beta = 90.412^\circ$, $Z = 4$ at 290 K have been measured by XRD¹³. No phase transition was reported in this crystal down to 90 K. The densities at 290 K and 100 K as calculated from the unit cell parameters are 1.274 and 1.321 Mgm^{-3} , respectively. The molecules are well unidirectionally aligned. From neutron diffraction studies¹³ it follows that the structure is stabilized by the presence of two weak intermolecular C-H...N hydrogen bonds. Parallel and head-to-tail arrangement of the molecules in the crystallographic structure, such that the nitrile group in one molecule is adjacent to the phenyl group in the next molecule, is directly responsible for the extremely large electro-optic coefficient of DCNP crystals, represented by the dominating second order susceptibility term $\chi_{333}^{(2)}(-\omega; \omega, 0) = -2.3 \times 10^{-9} \text{ m/V}$ ¹², where the subscript 3 denotes the z-axis of the crystal that is nearly parallel to the long molecular axis.

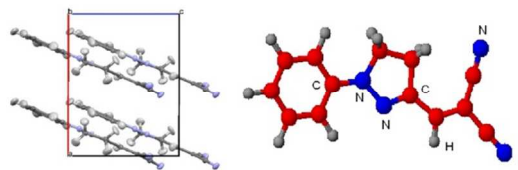


Figure 1. Projection of molecular packing in the crystal viewed along the b-axis (after Ref.¹³) and molecular structure of DCNP ($\text{C}_{13}\text{H}_{10}\text{N}_4$)

Polarization of DCNP crystal at 290 K, calculated by considering four molecules with the ground state dipole moment $\mu = 7.5 \text{ D} = 2.502 \times 10^{-29} \text{ Cm}$ placed in a unit cell of the volume $V = 1158.95 \text{ \AA}^3$ and oriented in the same direction, is equal to $|\text{P}| = 0.116 \text{ C/m}^2$. Recently, we confirmed that single

crystals of DCNP indeed show pyroelectric effect in the *z*-direction (unpublished results). Infrared (1064 nm) 5 ns pulses emitted by an Nd:YAG laser induced in a DCNP crystal an efficient fluorescence due to the two photon absorption process or the reabsorption of second order harmonic generation (SHG) light^{14,15}. Molecules of DCNP when dispersed in the polymer films of polyetherketone or PMMA, oriented by a high dc electric field, i.e. by a corona poling process, also show the efficient SHG phenomenon¹⁶⁻¹⁸.

The common property of the majority of molecular crystals, even those of the best quality, is the presence of trap states, which may be due to structural faults, vacancies, or chemical impurities. Particularly, for the DCNP we believe that the traps are of structural origin. The starting material was very carefully purified. Moreover, from the work of Black et al.¹⁹ it is known that for crystals grown from toluene solvent one deals with different growth rates along the polar axis of DCNP. Toluene appears to be selectively adsorbed at the faster growing polar end of the crystal (the cyano-rich direction) resulting in minor anisotropic misorientations being present in these crystals¹⁹. This may point out that the main source of trapping states in DCNP single crystals is related with the presence of structural and not chemical traps.

Excitonic energy migration within the crystal, especially under ambient conditions, may result in efficient population of these trap states (as well as thermal depopulation of traps) therefore optical properties of a studied crystal may be disturbed by the traps. Thus, deep understanding of the optical properties of a molecular crystal may require clarification of the traps origin.

First step into this direction is to determine trap's depths in respect to the crystal excitonic band. The purpose of the present work is to get experimental information about energy location of the excitonic band in the single crystal of DCNP, which is necessary for determination of trap's depths. This goal is realized by studying absorption and fluorescence spectra of the crystal at 5 K. In order to convince ourselves that we are investigating property of the bulk crystal we compared the vibronic structure of fluorescence (recorded at 5 K) with Raman spectra (recorded at 295 K) of a DCNP crystal. We also analysed the vibronic structure of fluorescence and fluorescence excitation spectra of isolated DCNP molecules dispersed in a Shpol'skii matrix of *n*-nonane at 5 K. The spectral analysis is supported by the kinetic study.

2 Results and discussion

2.1 Absorption and fluorescence of DCNP at 5 K

Absorption and fluorescence spectra of the single crystal of DCNP recorded at 5 K are presented in Figure 2. Sharp absorption edge, which can be identified with the bottom of an excitonic band, is observed at ~552 nm (18110 cm⁻¹). However, the absorption of nonpolarized light at this wavelength does not drop to the zero value, but to the absorbance of about 0.6 (in a ~2.5 mm thick crystal this corresponds to average absorption coefficient of $\alpha = 5.5 \text{ cm}^{-1}$). Absorbance continues its slow decrease to lower values toward longer wavelengths over the whole spectral range presented in Fig. 2. Such behaviour indicates a contribution to the absorption from a manifold of broad, continuously deeper and deeper trap states. The residual absorbance (attributed to the trap states) is strongly dependent on the light polarization (presented in Fig. S2 of Supporting Information) - with the light polarized parallel to the long axis of DCNP molecules absorbance is considerably bigger $\alpha_z(633 \text{ nm}) \approx 11 \text{ cm}^{-1}$

than that with the light of perpendicular polarization amounting to $\alpha_x(633 \text{ nm}) \approx 2 \text{ cm}^{-1}$.

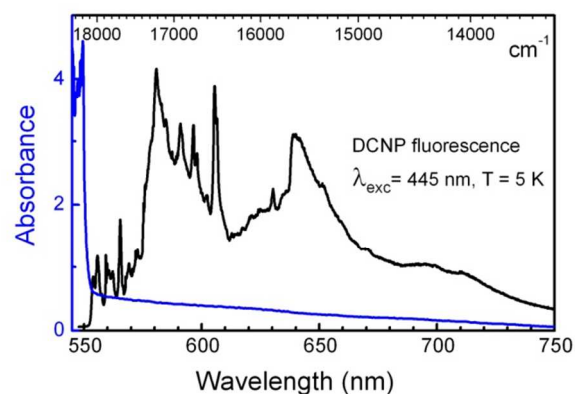


Figure 2. Absorption (blue line) and fluorescence (black line) spectra of a ~2.5 mm thick single crystal of DCNP recorded at 5 K. No correction of absorbance due to light reflection from sample surface has been applied.

This observation is a signature of the presence of small density of absorbing species whose transition dipole moment is parallel to the long axis of DCNP molecules, e.g. molecules or their clusters with reversed dipole moments with respect to majority of molecules. Typical absorption coefficients for molecular crystal above absorption edge are of the order $10^3 - 10^4 \text{ cm}^{-1}$. Our result (*cf.* Fig. 2) is consistent with absorption spectrum recorded at room temperature by Allen et al.¹². These authors observed sharp absorption edge at 580 nm at room temperature, it is about 875 cm^{-1} to lower energy as compared with our absorption edge observed at 5 K. They also observed residual absorption at longer wavelengths, polarized (like in our study) along the long axis of DCNP molecules. "Red-shift" of the absorption edge between that measured at 5 K and at room temperature may be attributed to "hot absorption", being the result of higher population of molecular vibrations in a crystal with temperature increase. Another possible mechanism, acting in the same direction, is the change of the internal crystal energy with temperature: when temperature decreases average crystal cohesive energy may increase, at the same time strengthening intermolecular interactions.

2.2 Excitonic emission and trap states

The fluorescence spectrum recorded at 5 K (*cf.* Fig. 2) is composed of several relatively narrow bands (as compared with those observed at elevated temperatures¹⁴). The onset line of fluorescence is located at about 552 nm, i.e. it exactly matches with the sharp drop of absorbance, by the same confirming that at this wavelength we should locate energy of the bottom of the excitonic S_1 band of the DCNP crystal. The spectrum, which spans between 552 and 575 nm and excited with 445 nm line composes of several narrow lines. We attribute this part of the spectrum to excitonic emission, although we cannot exclude that the emission originates from very shallow traps of the X-trap origin²⁰. Broad bands with the onsets at about 580 and 639 nm we attribute to the trap states, with the depths ~875 and ~2465 cm⁻¹, respectively. Such the conclusion is confirmed by the spectra presented in Fig. 3, which were obtained using the two different excitation wavelengths of 560 and 581 nm. Under these conditions (excitation below the excitonic band) the trap

states are excited directly. It is worth of notice that shifting of excitation wavelength by only 1 nm, i.e. from 580 nm to 581 nm results in fluorescence vanishing from the higher energy traps. Let us recall, that the fluorescence emission from these two trap states (with the maxima at 580 and 639 nm) was already reported at elevated temperatures¹⁴.

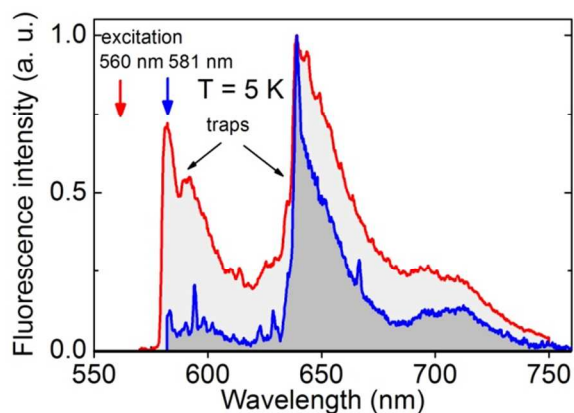


Figure 3. Fluorescence spectra of DCNP crystal at 5 K obtained with the excitation wavelengths of 560 and 581 nm, respectively.

In the forthcoming presentation and discussion we concentrate on the excitonic emission (spread in the fluorescence spectrum between 552 and 575 nm). In order to confirm excitonic origin of this emission we collected fluorescence at 5 K in two different detection configurations. We focused excitation beam of the 445 nm light (excitation to the excitonic band) on the crystal surface to a spot of diameter about 0.5 mm and collected emission light from this spot and next we shifted detection spot 1 mm apart from the excitation spot. The result of such the experiment is presented in Fig. 4. It is clearly seen that the spectrum "off-spot" is lacking excitonic component and is composed of emission from trap states only.

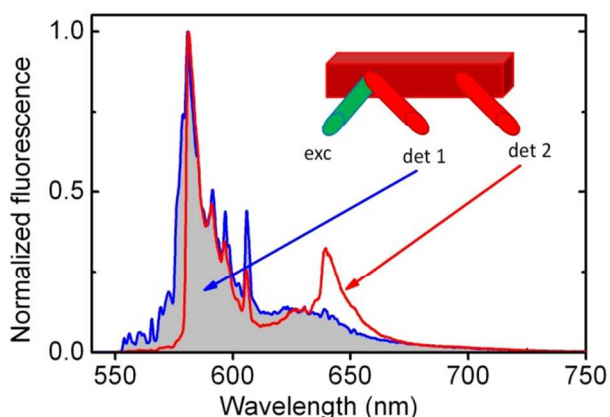


Figure 4. Fluorescence spectra of DCNP single crystal recorded at $T = 5$ K "on-spot" (blue line, det 1) and "off-spot" 1 mm aside (red line, det 2). The DCNP crystal was excited by a 445 nm laser light; both spectra were normalized at maximum.

2.3 Fluorescence decays at 5 K

The kinetic studies were performed with the 384 nm in wavelength picosecond pulses (200 ps), which excited crystal above the absorption edge, and we monitored fluorescence decays at different wavelengths. In Fig. 5 we show examples of normalized fluorescence decays measured in DCNP single crystal at $T = 5$ K and excited above absorption edge in function of emission wavelength.

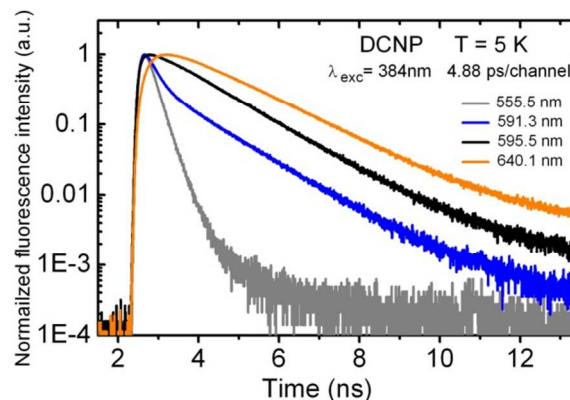


Figure 5. Fluorescence decay profiles of DCNP single crystal at temperature 5 K excited with 384 nm picosecond laser pulses and measured at 555.5 nm (excitonic emission region), 591.3, 595.5 nm (shallow trap 875 cm^{-1} emission region) and 640.1 nm (deeper trap 2465 cm^{-1} emission region).

In the "blue" part of fluorescence spectrum, corresponding to the excitonic emission, fluorescence decays were found to be very fast, in subnanosecond time scale. Fitting the decays to mono-exponential dependence by using deconvolution of the signal we found decay times equal to 210 ps for the observation at 555.5 nm and 255 ps at 564.8 nm, respectively. Considerably longer and non-exponential decays were detected at wavelengths of observation longer than 575 nm. Fitting the decay curves to bi-exponential dependence we got short-lived component of about 1.3 ns and long-lived component of about 5 ns. These two values were practically unchanged over the whole measured long wavelength spectral range 570 – 700 nm, but with lengthening of the observation wavelength the amplitude of the long-lived component was raising whereas that of the short-lived one was decreasing. Kinetics of fluorescence emission observed at 640.1 nm shows curve with maximum shifted in time with respect to excitation pulse position, this is manifestation of process of excitonic diffusion. Fluorescence decays shown in Fig. 5 point out to a complex excitation energy migration toward the trapping species. Traps strongly contribute to the emission of DCNP crystal at longer wavelengths. The most meaningful result is the very fast decay of excitonic fluorescence indicating efficient migration of excitons already at 5 K and their trapping at deep (at this temperature) trap states.

2.4 Vibrational structure of luminescence

For many organic molecules the optical spectra of several aggregates show vibrational structure principally similar to the internal vibrational modes of the monomers²¹. This phenomenon is observed also for DCNP molecule which

fluorescence spectrum of monomers in an alkane matrix has the vibronic structure similar to that in the crystal phase. Thus the comparison of Raman and fluorescence spectra can be used to check if the trapping states of the crystal are of DCNP or chemical impurity origin.

In order to confirm that the fluorescence spectrum detected within the 552–575 nm range has the excitonic (bulk) origin we compare the "blue" part of the spectrum presented already in Fig. 2 with the Raman spectrum of a single DCNP crystal (collected at 295 K). The result, where the spectra are compared and plotted in a wavenumber scale, is shown in Fig. 6a. Agreement between both spectra is quite good - several lines in the fluorescence spectrum have their partners in the Raman spectrum. A broad band, which builds up above 700 cm^{-1} (corresponding in Fig. 2 to wavelengths longer than 575 nm) is attributed to a deep trap state. Raman scattering reports on the molecular oscillation energies of bulk crystal and is not sensitive to trap states (if the concentration of traps is low, like in DCNP crystal under study). The good matching of main Raman lines with the fluorescence fine structure clearly confirms the bulk origin of fluorescence emission in the considered spectral range (552 – 575 nm).

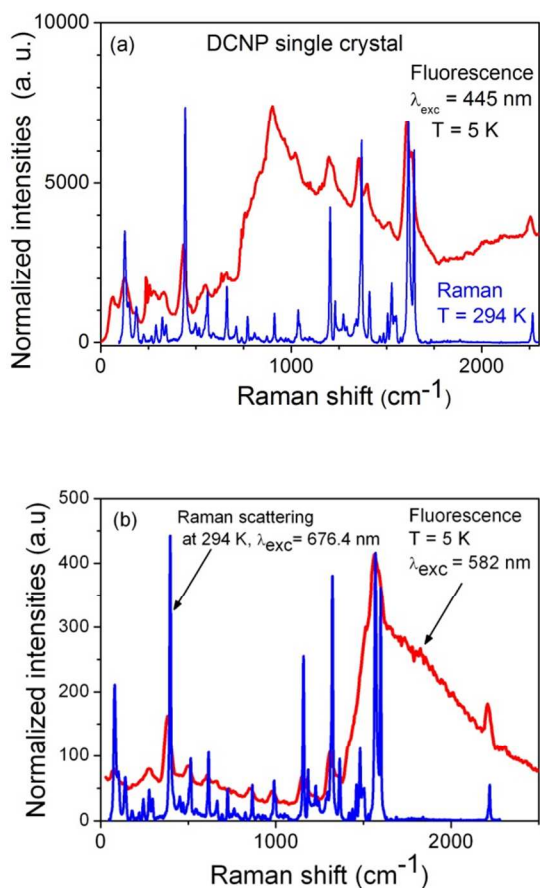


Figure 6. Raman spectrum of a DCNP single crystal measured at 295 K ($\lambda_R = 676.4$ nm, blue lines) superimposed on the low temperature, $T = 5$ K, fluorescence spectra of the crystal (red lines) excited to the excitonic band by 445 nm laser light (a) and to the trap state absorbing at 582 nm (b).

Vibrational structure of the Raman spectrum can be further used to get information about origin of a deep trap contributing to the fluorescence spectrum of DCNP crystal at wavelengths longer than 580 nm. These traps, and deeper traps, are directly populated with the 582 nm excitation wavelength, as already shown in Fig. 3. Very good matching of both, Raman and fluorescence trap spectra is presented in Fig. 6b. This result convinced us that the trap as deep as ~ 875 cm^{-1} below the excitonic band is also created on DCNP molecules, and not on chemical impurities. Fluorescence from impurities having different molecular structure than DCNP molecule should show fine structure different from that observed in Raman scattering experiment.

2.5 Shpol'skii spectra of DCNP at 5 K

Shpol'skii spectra of DCNP in *n*-nonane at 5 K provide information about the spectral characteristics of DCNP monomers. In this matrix DCNP molecules occupy two, well-defined, insertion sites, with the (0, 0) lines located at 499.6 and 502.5 nm (20012 and 19905 cm^{-1} , respectively), as presented in Fig. S1 of Supporting Information. Thus, the onset of the DCNP crystal fluorescence is shifted to lower energy, by at least, ~ 1900 cm^{-1} in respect to that of isolated DCNP molecules. Vibrational frequencies of DCNP molecules embedded in both sites are similar. Slightly different frequencies of vibrations present in the fluorescence spectrum and in the fluorescence excitation spectrum reflect geometry difference of DCNP molecules in the electronic ground and the lowest excited singlet states, respectively. Vibrations observed in the Raman spectrum of DCNP crystal superimposed on the fluorescence spectrum of DCNP molecules isolated in *n*-nonane matrix (presented for site 1) reproduce most of the molecular vibrational lines (*cf.* Fig. 7). Such the result is expected for a molecular crystal, where excitonic interactions between different molecules are considerably weaker than those forming a DCNP molecule.

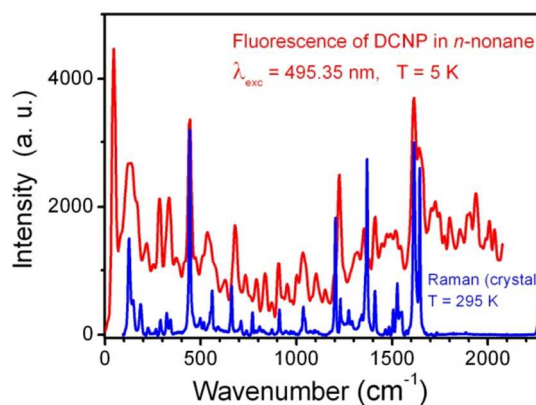


Figure 7. Raman spectrum recorded for DCNP crystal (at 295 K, $\lambda_R = 676.4$ nm) superimposed on the fluorescence spectrum of DCNP molecules in *n*-nonane matrix at 5 K excited by $\lambda_{exc} = 495.35$ nm laser light (site 1).

Fluorescence decays for DCNP in *n*-nonane matrix are mono-exponential and do not depend on the wavelength of observation (neither on temperature up to 180 K, above this temperature the *n*-nonane melts). The fluorescence decay time

for monomer is $\tau_{\text{monomer}} = 4.8$ ns, i.e. close to 3.7 and 5.6 ns, already reported for DCNP crystal at 293 K¹⁴.

Finally, let us mention that using a Parker type phosphorimeter, equipped with mechanical choppers and a sensitive EMCCD camera, we were not able to detect any long-lived (longer than 100 μs) phosphorescence emission in a DCNP crystal at 5 K. We scanned the whole spectral range between 600 and 1100 nm. Even more, our effort to enhance intersystem crossing efficiency in DCNP by dissolving this compound in iodoethane, which is known to increase population of the triplet states due to external heavy atom effect, appeared unsuccessful - we were not able to monitor any phosphorescence. We may thus conclude that intersystem crossing from excited singlet state S_1 to the triplet manifold in DCNP is not an efficient channel and excitation energy relaxation proceeds via radiative, fluorescence, and nonradiative, internal conversion, channels.

3 Experimental

3.1 Crystal preparation

The DCNP compound was synthesized and purified according to the procedure described by Allen et al. 13 who first measured the crystal NLO properties. Next, a crude material was purified by sublimation under vacuum ("instabilities at the melt temperature preclude zone refining", according to Ref. 13). Sublimed material has been extracted from the central part of a sublimation tube. Single crystals of DCNP were grown in darkness from 100 cm³ toluene DCNP solution, prepared at +40°C, and using slow cooling rate of approximately 0.1°C/day. The resulting single crystal plates were formed spontaneously at the vessel edges when the temperature of the solution approached room temperature. Some crystals have thicknesses between 0.5 and 1 mm and areas between 5 to 10 mm². The crystals used in this work for luminescence studies had form of parallelepipeds with approximate dimensions 10×5×2.5 mm³. The crystallographic b-axis is perpendicular to the plate face. The optical quality of the obtained by us crystals has been checked with a polarization microscope on (010) natural face of the single crystal showing that the principal z-axis of refractive index ellipsoid lies at angle of 26° with respect to the crystallographic c-axis. Along this z-axis long molecular axes are aligned.

3.2 Spectroscopic measurements

Spectroscopic studies of DCNP monomer molecules in a Shpol'skii, polycrystalline matrix of n-nonane were performed at 5 K. The solution of DCNP in a liquid n-nonane (concentrations 10⁻⁵ - 10⁻⁴ M) was poured into a small cylinder-shaped fused silica cuvette and quickly cooled in liquid nitrogen (77 K) to prevent aggregation. Next, a sample holder with mounted cuvette was inserted into an optical, liquid helium cryostat.

Absorption spectra of the crystal were measured in a single-beam configuration. In this case the light of a xenon lamp transmitted through the sample was dispersed with a McPherson 207 monochromator and detected with an EM196659 photomultiplier operating in a photon counting mode.

Fluorescence spectra were measured at the right angle in respect to excitation, the emission light was dispersed by a McPherson 207 monochromator and detected either by an

EM196659 photomultiplier or by an EMCCD camera (Andor, model DU420A-BR-CD) cooled to 183 K. As an excitation source we used light emitted by either a cw 532 nm (10 mW) or 445 nm (20 mW) solid state lasers. Alternatively we used a Lambda Physics FL1001 dye laser pumped by a pulsed LPX100 excimer laser ($\lambda_{\text{exc}} = 308$ nm), which when operated with Coumarin 102 dye was scanned within the spectral range between 470 and 500 nm and with Coumarin 153 between 530 and 605 nm, respectively. In the case of pulsed excitation fluorescence signals were detected by using sampling technique with a photomultiplier and a Stanford Research SR259 boxcar averager.

The Raman scattering experiment was performed at 295 K using for excitation a cw Krypton laser operating at $\lambda_R = 676.4$ nm. The Raman spectrum was taken using a Jobin Yvon T64000 spectrograph equipped with a CCD camera cooled by liquid nitrogen as a detector. The 676.4 nm light was weakly absorbed by a DCNP crystal, leading to weak fluorescence, and this fluorescence background was numerically subtracted from the detected Raman spectrum.

3.3 Emission kinetics measurements

Fluorescence kinetics studies were done with the aid of "time correlated" single photon counting technique (in the inverted time mode). Excitation pulses were provided either by the second harmonics of a mode-locked Coherent's Mira-HP picosecond laser pumped by a Verdi18 laser or by the picosecond pulses from an APE Optical Parametric Oscillator pumped by a Mira-HP/Verdi18 system. Original repetition rate of a Mira-HP laser, 80MHz, was reduced to 2 MHz with the aid of an APE Pulse Selector. The fluorescence photons were dispersed with a McPherson 207 monochromator and the fluorescence decay curves were monitored with a HMP-100-50 hybrid detector and a SPC-150 module inserted into a PC computer, both from Becker&Hickl GmbH. Fluorescence decay times were determined by using deconvolution program, which iteratively fitted theoretical curve to the experimental decay with the aid of the least-squares Levenberg-Marquardt algorithm.

4 Conclusions

We studied absorption and fluorescence spectra of a non-centrosymmetric highly polar single crystal of DCNP at temperature of 5 K. The bottom of excitonic band was assigned to lay at ~ 18115 cm⁻¹ (552 nm). We argue that the fluorescence emission which spans between 552 and 575 nm has excitonic origin. Such the conclusion is confirmed by vibrational structure of fluorescence closely resembling that observed in the Raman scattering spectrum of DCNP crystal as well as by the very short, subnanosecond decay time of fluorescence, being a fingerprint of excitons migration and trapping at deep traps. Fluorescence decay times from the trap states in a DCNP crystal and that for a DCNP monomer in a Shpol'skii matrix are much longer, approaching about 5 nanoseconds.

Important result of the work is to convince that the vibrational structure of Raman spectrum (recorded at ambient conditions) can be successfully used to reproduce vibrational structure of fluorescence spectrum recorded at cryogenic temperature (5 K). Good matching of the Raman spectrum and fluorescence spectrum of the deep (at 5 K) trap (trap with the depth ~ 875 cm⁻¹, and emission onset at 582 nm) argue that this

trap is a kind of structural defect and does not correspond to a chemical impurity.

Finally, let us add that the present contribution is dedicated to the optical study of a DCNP crystal at 5 K. The optical studies of the crystal at elevated temperatures, where the deep traps are playing dominant role, and thus their origin is of main importance, will be considered in a forthcoming elaboration.

Acknowledgements

This work was financially supported by the Polish National Science Centre, Dec-2011/03/B/ST5/01021 and the grant no. 2012/04/A/ST2/00100. We wish also thank dr T. Misiaszek from the Wrocław University of Technology for measurement of Raman spectrum in a DCNP crystal.

Notes and references

^a Address Institute of Physics, Polish Academy of Sciences PL-02668 Warsaw, Poland

^b Institute of Physical and Theoretical Chemistry, Department of Chemistry, Wrocław University of Technology, Wybrzeże Wyspiańskiego 27, PL-50370 Wrocław, Poland

†

Electronic Supplementary Information (ESI) is available: [ESI contains spectra of DCNP in n-nonane Shpol'skii matrix; Raman spectra of DCNP crystal; and table with calculated and measured frequencies of vibrations of DCNP molecules and in a crystal.] See DOI: 10.1039/b000000x/

References

- 1 A. E. Rashad, A. H. Shamroukh, M. I. Hegab and H. M. Awad, *Acta Chim. Slov.*, 2005, **52**, 429-434.
- 2 B. A. Bhat, K. L. Dhar, A. K. Saxena and M. Shanmugavel, *Bioorg. Med. Chem.*, 2005, **15**, 3177-3180.
- 3 E. M. Sharshira and N. M. Hamada, *Molecules*, 2011, **16**, 7736-7745.
- 4 C. W. Dirk, H. E. Katz, M. L. Shilling and L. A. King, *Chem. Mater.*, 1990, **2**, 700-705.
- 5 Y. Dwivedi, L. de Boni, P. J. Gonçalves, L. M. Mairink, R. Menegatti, T. L. Fonseca and S. C. Zilio, *Spectrochim. Acta Part A: Molecular and Biomolecular Spectroscopy*, 2013, **105**, 483-487.
- 6 R. D. Miller, C. R. Moylan, O. Reiser and C. A. Walsh, *Chem. Mater.*, 1993, **5**, 625-632.
- 7 S. Tabak, I. I. Grandberg and A. N. Kosrt, *Tetrahedron*, 1966, **22**, 2703-2710.
- 8 S. Chatterjee, A. Mukharjee, K. K. Mahalanabis and S. C. Bhattacharya, *J. Surface Sci. Technol.*, 2008, **24**, 195-205.
- 9 J. M. Cole, C. C. Wilson and J. A. K. Howard, *Mol. Cryst. Liq. Cryst., Science and Technology Section B: Nonlinear Optics*, 2000, **25**, 265-270.
- 10 A. Radi, S. Radi, and B. Hammouti, *J. Mater. Environ. Sci.*, 2010, **1**, 96.
- 11 K. A. Vishnumurthy, A. V. Adhikari, M. S. Sunitha and R. Philip, *AIP Conf. Proc.*, 2011, **1391**, 652.
- 12 S. Allen, T. D. McLean, P. F. Gordon, B. D. Bothwell, M.B. Hursthouse and S. A. Karaulov, *J. Appl. Phys.*, 1988, **64**, 2583-2590.
- 13 J. M. Cole, C. C. Wilson, J. A. K. Howard and F. R. Cruickshank, *Acta Cryst.*, 2000, **B56**, 1085-1093.
- 14 A. Miniewicz, K. Palewska, L. Sznitko and J. Lipinski, *J. Phys. Chem. A*, 2011, **115**, 10689-10697.
- 15 L. Sznitko, J. Mysliwiec, K. Parafiniuk, A. Szukalski, K. Palewska, S. Bartkiewicz, A. Miniewicz, *Chem. Phys. Lett.*, 2011, **512**, 247-250.; A. Miniewicz, K. Palewska, P. Karpinski, L.

- 16 W. Shi, C. Fang, Z. Xu, Q. Pan, Q. Gu, D. Xu, H. Wei and J. Yu, *Solid State Commun.*, 2000, **113**, 483-487.
- 17 W. Shi, C. Fang, Q. Pan, X. Sun, Q. Gu, D. Xu, H. Wei and J. Yu, *Chin. Phys. Lett.*, 2000, **17**, 22-24.
- 18 A-M. Manea, I. Rau, A. Tane, F. Kajzar, L. Sznitko and A. Miniewicz, *Opt. Mater.*, 2013, **36**, 69-74.
- 19 S. N. Black, R. J. Davey, P. R. Morley, P. Halfpenny, E. E. A. Shepherd and J. N. Sherwood, *J. Mater. Chem.*, 1993, **3**, 129-132.
- 20 M. Pope and C. E. Swenberg, *Electronic processes in organic crystals*, Clarendon Press, 1982.
- 21 M. R. Philpott, *J. Chem. Phys.*, 1971, **55**, 2039-2054.