

PCCP

Accepted Manuscript



This is an *Accepted Manuscript*, which has been through the Royal Society of Chemistry peer review process and has been accepted for publication.

Accepted Manuscripts are published online shortly after acceptance, before technical editing, formatting and proof reading. Using this free service, authors can make their results available to the community, in citable form, before we publish the edited article. We will replace this *Accepted Manuscript* with the edited and formatted *Advance Article* as soon as it is available.

You can find more information about *Accepted Manuscripts* in the [Information for Authors](#).

Please note that technical editing may introduce minor changes to the text and/or graphics, which may alter content. The journal's standard [Terms & Conditions](#) and the [Ethical guidelines](#) still apply. In no event shall the Royal Society of Chemistry be held responsible for any errors or omissions in this *Accepted Manuscript* or any consequences arising from the use of any information it contains.

On the crossroads of current polyelectrolyte theory and counterion-specific effects[†]

Natalie Malikova,^{*a,b} Anne-Laure Rollet,^{a,b} Sašo Čebašek,^c Matija Tomšič^c and Vojko Vlachy^c

Received Xth XXXXXXXXXXXX 20XX, Accepted Xth XXXXXXXXXXXX 20XX

First published on the web Xth XXXXXXXXXXXX 200X

DOI: 10.1039/b000000x

Aqueous solutions of polyelectrolytes are studied here by means of neutron scattering, with emphasis on backbone hydrophobicity and counter ion specific effects. Ionene polyelectrolytes with varying chain charge density and different counter ions are considered. Their neutron scattering data feature a number of aspects and trends that clearly deviate from the predictions of the existing theory. Ionenes challenge the current hydrophilic-hydrophobic classification of water-soluble polyelectrolytes. The hydrophobic character of their hydrocarbon backbone emerges only for very low chain charge densities (at 15% of charged monomers), which is significantly lower than for other polyelectrolytes with a more complex structure. Universality in the counter ion specific effect seen in ionene solutions with Br[−] or F[−] counterions is established. The polyelectrolyte peak in the scattering spectra of Br[−]-ionenes disappears beyond a specific charge concentration, which is identical across all ionene chain charge densities. In addition, scattering spectra for Br[−]-ionenes and F[−]-ionenes feature contrasting temperature trends, which are accentuated with decreasing chain charge density. Our interpretation of the F[−]-Br effect, based on the different hydration properties of the counter ions, is supported by additional NMR measurements on ionenes with mixed counter ion clouds. Overall, the study of ionene polyelectrolytes points clearly at the need of combining the scaling concepts with those of ion specificity, to obtain a theoretical framework encompassing the wealth of phenomena occurring in polyelectrolyte solutions.

1 Introduction

Recent advances have extended the already rich field of polyelectrolyte applications to the very edge of our current technology. Notable examples are polyelectrolytes as part of stimuli-responsive hydrogels,^{1–3} which lead now all the way to the development of artificial biological tissues,^{4,5} or conjugated polyelectrolytes as biosensors.⁶ Understanding the conformation and interactions of polyelectrolyte chains has far reaching consequences in biological sciences, with DNA being one of the most widely studied polyelectrolytes.⁷

In contrast to neutral polymers, the presence of charges in polyelectrolytes gives rise to a wealth of new phenomena, stemming from the interaction of charges along the polyelectrolyte chain and the total or partial counterion condensation onto the chain. Current polyelectrolyte (PE) theory originated in the scaling approach of de Gennes et al

and Pfeuty.^{8,9} The case of polyelectrolyte solutions was later broadened by Dobrynin and Rubinstein, for all the cases of different solvent quality and concentration regimes.¹⁰ The success of this theory is considerable, particularly when confronted with neutron/X-ray scattering experiments on PE solutions. It predicts correctly the scaling of the PE chain correlations probed via the universally observed maximum in scattering data, the so-called *polyelectrolyte peak*. Its position depends not only on the PE concentration and solvent quality, but also on the effective (as opposed to nominal/chemical) backbone charge, i.e. charge after possible counterion condensation. The description of counter ion condensation itself begins with the seminal work of Manning.^{11,12} Further extensions are based on the Poisson-Boltzmann approach,¹³ others attempt to account for the chain flexibility and local dielectric heterogeneities.¹⁴ The latter come the closest to describing counterion specific effects, observed by a range of techniques for electrolyte and colloidal solutions, polyelectrolyte gels etc.^{15–23} As we shall show here, a striking example of these effects is to be found when probing polyelectrolyte solutions through scattering techniques and the current accompanying theory is short of encompassing them.

Scaling theory has been tested on a number of PE solutions, and particularly on those with anionic chains built from the styrene monomer, e.g.^{13,24–27} Here, we study *ionenes*, a

[†] Electronic Supplementary Information (ESI) available: Experimental details, additional neutron and X-ray scattering data. See DOI: 10.1039/b000000x/

^a Sorbonne Universités, UPMC Univ Paris 06, UMR 8234, PHENIX, F-75005, Paris, France, Fax: +33 144 273228; Tel: +33 144 274031; E-mail: natalie.malikova@upmc.fr

^b CNRS, UMR 8234, PHENIX, F-75005, Paris, France

^c Faculty of Chemistry and Chemical Technology, University of Ljubljana, Večna pot 113, SI-1000 Ljubljana, Slovenia.

group of water soluble cationic polyelectrolytes with pH independent charge, based on quaternary ammonium charged centres linked by simple hydrocarbon chains. They have already been studied in connection to several applications, including ion exchange resins,²⁸ water treatment in oil industry,²⁹ organic templates in the synthesis of mesoporous silica,³⁰ or anti-microbial agents.³¹

The general chemical formula of ionenes is $[-(\text{CH}_3)_2\text{N}^+(\text{CH}_2)_x-(\text{CH}_3)_2\text{N}^+(\text{CH}_2)_y-]_n$ for an x,y -ionene. Values x and y represent the number of $-\text{CH}_2-$ (methylene) units between adjacent charged centres and can be varied accurately by synthesis.³²⁻³⁴ For our purposes, ionenes are considered model polyelectrolytes as they present several important advantages over other systems: (i) charged centres are part of the PE backbone instead of a side group, (ii) the distance between the charges is regular and tuneable by synthesis and (iii) the uncharged backbone is free of any bulky side groups, which are often prone to specific interactions. Of special importance is also the presence of cationic PE chains with anions as the free counter ions. This charge distribution is likely to accentuate ion specific effects. Ionenes are thus ideally suited for investigating such effects in PE solutions and testing the existing scaling theory in this respect. Figure 1 gives the schematic view of an ionene chain and a summary of structural parameters of ionenes studied so-far.

Fig. 1 *Left*: Schematic view of an ionene chain, showing the definition of a charged and uncharged monomer. *Right*: Ionene structural parameters: a is the charge separation on the chain, f_{chem} the fraction of charged monomers, ξ the Manning charge density parameter, defined as $\xi = L_B/a$, where L_B is the Bjerrum length (7.14 Å in water at room temperature). While 4,5- ionenes are at the $\xi = 1$ limit (onset of Manning-type condensation), only 3,3- ionenes have sufficient charge density to induce significant condensation ($\xi > 1$) and decrease the chemical charge (f_{chem}) to an effective charge (f_{eff}). Ionenes with Br^- and F^- counterions are referred to as Br-ionenes and F-ionenes, respectively.

ionene	a [Å]	f_{chem}	ξ
3,3-	5.00	0.50	1.43
4,5-	6.88	0.36	1.04
6,6-	8.75	0.29	0.82
6,9-	10.63	0.24	0.67
6,12-	12.50	0.20	0.57
12,12-	16.25	0.15	0.43

Within the classification of PEs into hydrophilic and hydrophobic, ionenes should fall *a priori* into the class of hydrophobic PEs, due to the very low solubility of hydrocarbon chains (uncharged ionene backbone) in water. However, re-

cent neutron scattering data as well as osmotic coefficients show that across a wide chain charge density, ionenes show surprisingly a hydrophilic character.³⁵ In addition, a striking counter ion specific effect was reported for 6,9-F and 6,9-Br ionenes.³⁵ While the former has the signature of a typical hydrophilic PE in the semi-dilute regime (a clear PE peak over almost three decades in PE monomer concentration, c_p , the peak position scaling as $c_p^{1/2}$), the latter features a disappearance of the PE peak beyond a given PE monomer concentration (1 mol dm^{-3})*.

Following upon the above observations, it is important to establish: 1) to what extent the counterion-specific effect is universal for different chain charge densities and how we interpret it and 2) at which chain charge density would we see emerge the hydrophobic character of the backbone. In order to address these questions, we have undertaken neutron scattering measurements for aqueous solutions of F-ionenes and Br-ionenes with several charge densities (from 3,3- to 12,12-), with temperature ranging between 20°C and 50°C. The effect of an addition of electrolyte (NaF and NaBr) was studied for selected systems. The scattering data is further complemented by NMR measurements.

2 Experimental Section

Br-ionenes were synthesized from the corresponding equimolar amounts of N,N,N',N' -tetramethyl-1, x -alkane and 1, y -dibromoalkane (Aldrich) by a polyaddition reaction in dimethylformamide (methanol in the case of 6,12- and 12,12-ionene) at room temperature and under argon atmosphere for a duration of 7 days^{32,34}. The crude product was washed with a large amount of acetone and dried under vacuum for 48 hours at 40 °C. The polydispersity index of ionenes thus synthesized is 1.8-2.0, as determined by size exclusion chromatography. Br-ionenes were further dialyzed against water (2 weeks) to ensure the purity of the sample. Dialysis tubes from Sigma (MWCO = 12 000 g/mol) were used. This procedure results in molecular masses of the obtained ionenes between 12 000 g/mol and 100 000 g/mol³⁶. Such ionene chains contain approximately 100 charged monomers per chain and their length is thus of the order of 100 to 1000 Å.

Ionenes with fluoride counterions were prepared from bromide salts by ion exchange during dialysis. Dialysis tubes were filled with 0.02 M solutions of the Br-ionene and first dialyzed against 0.05 M solution of NaF (3 weeks) to exchange anion and then dialyzed against water (2 weeks) to remove sodium ions. Ion conversion was checked potentiometrically using bromide selective electrode and saturated mercury sulfate electrode as the reference and the standardized solutions of AgNO_3 as the titrant reagent. The concentration of bro-

* Units of mol dm^{-3} are abbreviated as M from now on.

vide ions was under the detection limit. Sodium removal was verified with a flame test.

All ionene solutions for neutron scattering and NMR measurements were prepared gravimetrically. Deuterated water (Euriso-top, 99.9 %D) was used for neutron scattering samples, light water for NMR samples. The exact counterion concentrations were determined potentiometrically using bromide or fluoride selective electrodes and a saturated mercury sulfate electrode as the reference. Samples were titrated with standardized solutions of AgNO_3 or LaCl_3 . The pH of the solutions was close to neutral and thus we estimate the effects of any dissolved carbonic acid as very small.

Small angle neutron scattering (SANS) measurements were carried out on the PAXE and PAXY spectrometers at LLB-Orphée, Saclay, France. Using up to three different combinations of incident neutron wavelength (λ) and sample to detector distance, a wave-vector (Q) range of 0.01 to 0.45 \AA^{-1} was covered ($Q = 4\pi \sin(\theta/2)/\lambda$). The detector efficiency was taken into account by normalisation of data with flat (incoherent) signal from bulk light water. Ionene solutions were loaded into quartz cells with path length of 1 or 2 mm. Due to the isotropic nature of our samples, data were grouped in concentric rings, each corresponding to a given Q value. The measured scattered intensities were corrected for transmission, sample thickness, incoherent and solvent background to yield the coherent scattered intensity, I_{coh} . We checked the reproducibility of neutron scattering spectra, by measuring samples from different synthesis batches.

The single pulse ^{19}F NMR spectra were recorded using a Bruker Avance III 300MHz NB spectrometer, operating at 7.05 T. The lock was obtained with a sealed 2.5 mm capillary filled with D_2O inserted in the NMR tube. The chemical shift were referenced to CFCl_3 . Pulsed field gradient NMR experiments were performed using a BBFO probe equipped with 55 G/cm gradient coil. We used a NMR pulse sequence combining bipolar gradient pulses and stimulated echo.³⁷ This sequence is repeated with 16 gradients of increasing strength ($0 < g < 50$ Gauss/cm, gradient application time of 1.5 ms) and a diffusion time of 100 ms. The self-diffusion coefficients are obtained by nonlinear least-square fitting of the echo attenuation.

2.1 Polyelectrolyte peak position and scaling laws

The neutron scattering spectra of aqueous solutions of 12,12-Br and 12,12-F ionenes (least charged systems considered here) are shown in Figure 2. We see a gradual disappearance of the polyelectrolyte peak beyond a certain ionene monomer concentration in case of 12,12-Br ionenes, while the peak remains for 12,12-F ionenes across the entire concentration range studied. This is reminiscent of the behaviour of 6,9-Br and 6,9-F ionenes reported previously.³⁵ A similar trend is

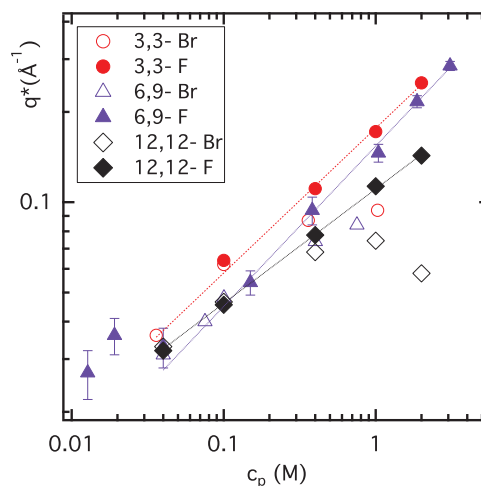


Fig. 3 Position of the polyelectrolyte peak in SANS spectra (q^*) versus ionene monomer concentration (c_p) for three ionene charge densities (3,3- and 6,9- and 12,12-) with either Br^- or F^- counter ions in each case. Error bars represented on the 6,9-F ionene data. Lines indicate a power law fit to the three data sets for F-ionenes in the range 0.04 M to 3 M: $q^* \propto c_p^\alpha$. The resulting α exponents are: 0.48 ± 0.03 for 3,3-F; 0.53 ± 0.02 for 6,9-F and 0.38 ± 0.01 for 12,12-F.

also observed for the opposite extreme in ionene charge density (3,3-Br and 3,3-F ionenes, data shown in Figure S1 of Supplementary Information).

Figure 3 features the position of the observed PE peak (q^*) as a function of ionene monomer concentration (c_p) for three different ionene charge densities (3,3- and 6,9- and 12,12-), in each case with F^- and Br^- counter ions. Up to concentrations of 0.2-0.3 M, q^* for Br^- and F^- ionenes of a given charge density are the same. Beyond this point, the behaviour is very different and is the consequence of the disappearance of the PE peak for Br^- ionenes. Interestingly, for 12,12-Br ionenes the total disappearance of the PE peak seems to be shifted towards higher monomer concentrations (at the highest concentration studied, 2 M, a clear peak is still present in the spectra of 12,12-Br, while none is seen for ionenes with higher charge densities).

Within the concentration range studied (0.04 M - 3 M), q^* for 3,3-F and 6,9-F ionenes follows a single scaling law, with an exponent close to $\frac{1}{2}$: 0.48 ± 0.03 for 3,3-F and 0.53 ± 0.02 for 6,9-F ionene. Clearly, the same power law is not obeyed for 12,12-F ionenes, for which the exponent descends to 0.38 ± 0.01 . A scaling exponent of $\frac{1}{2}$ is predicted for hydrophilic PEs in the semi-dilute regime, but also for hydrophobic PEs in the string controlled semi-diluted regime.^{8,10,38} Previously, in view of additional information from osmotic coef-

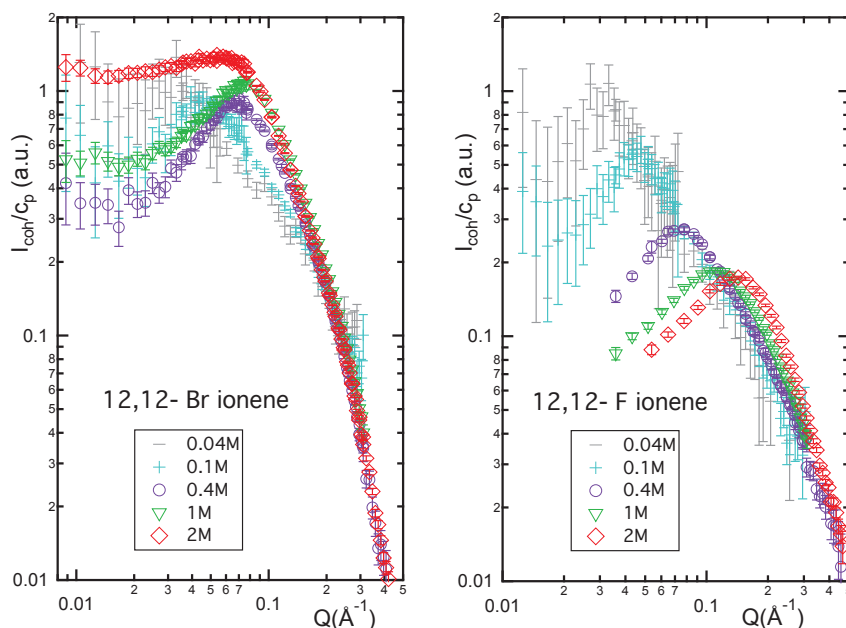


Fig. 2 Coherent neutron scattering intensity normalised by ionene monomer concentration (I_{coh}/c_p) versus scattering wave-vector (Q) for room temperature aqueous solutions of 12,12-Br and 12,12-F ionenes (in D_2O). Monomer concentrations as indicated in the legends.

ficients and the scaling of q^* with f_{chem} (fraction of charged monomers), we concluded that ionene chains at these charge densities fall rather surprisingly into the hydrophilic PE category.³⁵ In contrast to this, the significantly lower scaling exponent observed for 12,12-F ionenes is an indication of an emerging hydrophobic character of the ionene backbone. The exponent approaches the value of $\frac{1}{3}$, the prediction for the bead-controlled semi-dilute regime for hydrophobic PEs.³⁸ 12,12-ionenes correspond to $f_{chem}=0.15$, which is a surprisingly low charge density as an onset of a hydrophobic character. Indeed for partially sulfonated polystyrene sulfonate (psPSS, a reference for hydrophobic PEs), the same scaling exponent was observed already for $f_{chem}=0.40$.²⁵ This can be interpreted as a "weak" hydrophobicity of the simple methylene backbone. This is to some extent already indicated by the solubility limits of the different PEs. While psPSS is soluble in water down to $f_{chem} = 0.30$,²⁵ the solubility of ionenes is extended at least down to $f_{chem} = 0.15$, if not further. Several structural aspects stand at the origin of such behaviour. Firstly, the presence of the benzene side group in psPSS is likely to lead to specific $\pi - \pi$ interactions between the monomers³⁹ and thus accentuates the hydrophobicity of the backbone. Secondly, the *regularity* of charge distribution on ionenes, as opposed to a random distribution of charged groups in many PE systems including psPSS, might be the key to this extended solubility range. The hydration of the charged centres

of ionenes (tetralkylammonium groups) is indeed well developed up to high concentrations⁴⁰ and may mask significantly the hydrophobicity of the neutral linker between them. It remains to be seen if highly asymmetric ionenes ($x \gg y$) would show different solubility limits and an earlier emergence of backbone hydrophobicity.

2.2 F-Br counter ion specific effect and temperature dependence

The universality of the F-Br counter ion specific effect at room temperature across different ionene chain charge densities was established in the previous section. We shall consider now the temperature dependence of this effect. Figure 4 features the temperature variation of the neutron scattering spectra for the two extremes of ionene chain charge density (3,3- and 12,12-), for Br^- and F^- counter ions in each case. A wealth of contrasting trends is observed.

As seen in Figure 4 (left), the 3,3-Br system at 2 M monomer concentration is already in the regime without a PE peak. While the high- Q data superimposes very well within the experimental uncertainty at all temperatures, the intensity of the low- Q plateau is strongly temperature dependent. Note that the observed plateau extends down to the lowest Q probed (0.0125 \AA^{-1}) and thus the usual low- Q upturn in PE scattering data^{27,41} is not observed for 3,3-Br ionenes (the same is

true for 3,3-F). The 3,3-F spectra feature a broad peak with a very weak temperature dependence, within the experimental uncertainty.

Considering the 12,12- ionenes (lowest chain charge density), Figure 4 (center), a very different behaviour is observed, not only between the two counter ions but also with respect to 3,3- ionenes. At 2 M concentration, the 12,12-Br system still features a PE peak, which is strongly temperature dependent: it shifts to higher Q values and decreases in intensity as temperature is raised. The 12,12-F spectra is now also clearly temperature dependent, contrary to the 3,3-F counterpart. The peak intensity *increases* with temperature, while no shift in the peak position is observed.

A useful comparison to the 12,12- ionene data in Figure 4 (centre) is that for 3,3-Br and 3,3-F at 0.4 M ionene monomer concentration, Figure 4 (right). These two types of solutions have a very similar *charge* as opposed to *monomer* concentration, $c(N^+) = c_p f_{chem}$, 0.3 M and 0.2 M respectively. The spectra for 3,3-Br and 3,3-F at 0.4 M concentration both feature a PE peak. With increasing temperature the 3,3-Br peak shifts slowly to higher Q values while loosing intensity, the peak for 3,3-F remains temperature insensitive. Therefore, for the same charge concentration, the presence of the uncharged (hydrophobic) ionene backbone 1) accentuates the shifts in PE peak position and intensity for Br-ionenes and 2) brings about an unusual temperature dependence for F-ionenes.

Let us interpret the above data within the existing theory. The scaling theory predictions for the temperature dependence of the position of the PE peak, q^* , and of its intensity, $S(q^*)$, are summarized in Table 1. Overall, it is important to distinguish 6 different categories in the semi-dilute concentration regime itself, depending on the type of solvent, chain charge density and PE concentration regime for the case of poor solvent. While 3,3- ionenes fall into the category of good solvent, charge density above the Manning limit (denoted category A further on), 12,12- ionenes at $c_p=2$ M occupy category of poor solvent, bead-controlled regime, charge density below the Manning limit (denoted category G further on). Theory predicts rather weak temperature dependencies for q^* and $S(q^*)$ for category A ($q^* \propto T^{-0.067}$, $S(q^*) \propto T^{+0.20}$) and thus the data for 3,3-F ionenes comes as no surprise. As in the case of another PE from category A, sodium-2-acryl-amide-2-methyl propane sulfonate (AMAMPS), the temperature dependence is experimentally not resolved.²⁶ The temperature dependent spectra for 3,3-Br at 0.4 M is then unexpected. Moreover, it features trends which are in *qualitative* disagreement with the theory. According to the latter the peak should be shifting to lower Q values and increasing in intensity, as temperature increases.

The situation is more complex for 12,12- ionenes in category G, for which we cannot predict any qualitative scaling laws, as Θ , their theta temperature and thus τ , defined as

$(\Theta - T)/\Theta$, are unknown. Considering that τ decreases, while l_B increases with temperature, we may nevertheless predict that the peak position increases, while its intensity decreases, as temperature is raised. However, 12,12-F ionenes feature a PE peak with a temperature-*independent* position and an intensity *increasing* with temperature. While the peak position variation may simply not be resolved experimentally, the observed trend in peak intensity is in direct disagreement with the theoretical predictions. Referring back to Table 1, an increase in peak intensity with increasing temperature cannot be assigned to any solvent or concentration regime for PE chains with charge density below the Manning limit ($\xi < 1$). Interestingly, 12,12-Br ionenes at 2 M actually follow the theory predicted trends for category G.

Table 1 Predictions of the scaling theory^{10,26,38} regarding the temperature dependence of the position of the PE peak, q^* , and of its intensity, $S(q^*) \approx c_p(q^*)^{-3}$. We distinguish the cases of good solvent ($T \gg \Theta$) and poor solvent ($T \ll \Theta$), chain charge densities above ($\xi > 1$) and below ($\xi < 1$) the Manning condensation limit, bead- and string- controlled concentration regimes. Note that for water in the temperature range considered $l_B \propto T^{0.47}$, according to ref²⁶. The differences between $\xi > 1$ and $\xi < 1$ cases arise from considering temperature dependent f_{eff} for the former ($f_{eff} \propto l_B^{-1}$), which is substituted by temperature independent f_{chem} for the latter.

	$T \gg \Theta$	$T \ll \Theta$	
		string regime	bead regime
	$q^* \propto c_p^{1/2}$	$q^* \propto c_p^{1/2}$	$q^* \propto c_p^{1/3}$
$\xi > 1$	$q^* \propto l_B^{-1/7}$	$q^* \propto (\tau l_B)^{-1/4}$	$q^* \propto (\tau l_B)^{-1/3}$
	$S(q^*) \propto l_B^{3/7}$	$S(q^*) \propto (\tau l_B)^{3/4}$	$S(q^*) \propto \tau l_B$
$\xi < 1$	$q^* \propto l_B^{1/7}$	$q^* \propto (\tau l_B^{-1})^{-1/4}$	$q^* \propto (\tau l_B^{-1})^{-1/3}$
	$S(q^*) \propto l_B^{-3/7}$	$S(q^*) \propto (\tau l_B^{-1})^{3/4}$	$S(q^*) \propto \tau l_B^{-1}$

2.3 Polyelectrolyte peak disappearance: significance of charge concentration, master curve

In view of the unusual q^* versus c_p behaviour for Br-ionenes in Figure 3, it seems at first difficult to establish the PE concentration regime for these systems. Beyond the semi-dilute regime, more concentrated PE solutions have been shown to obey a weaker scaling law ($q^* \propto c_p^{1/4}$),^{24,41} as predicted yet again by theory.⁴² However, there is no physical reason to look for such a law in case of Br-ionenes: as F-ionenes remain in the semi-dilute regime up to $c_p=2$ M, a simple change of the counterion cannot lead to the change of PE concentration regime. The unusual behaviour of q^* versus c_p for Br-ionenes is thus a consequence of the PE peak disappearance and not of a change in PE concentration regimes. The peak disappearance in *salt-free* Br-ionene solutions is in itself an

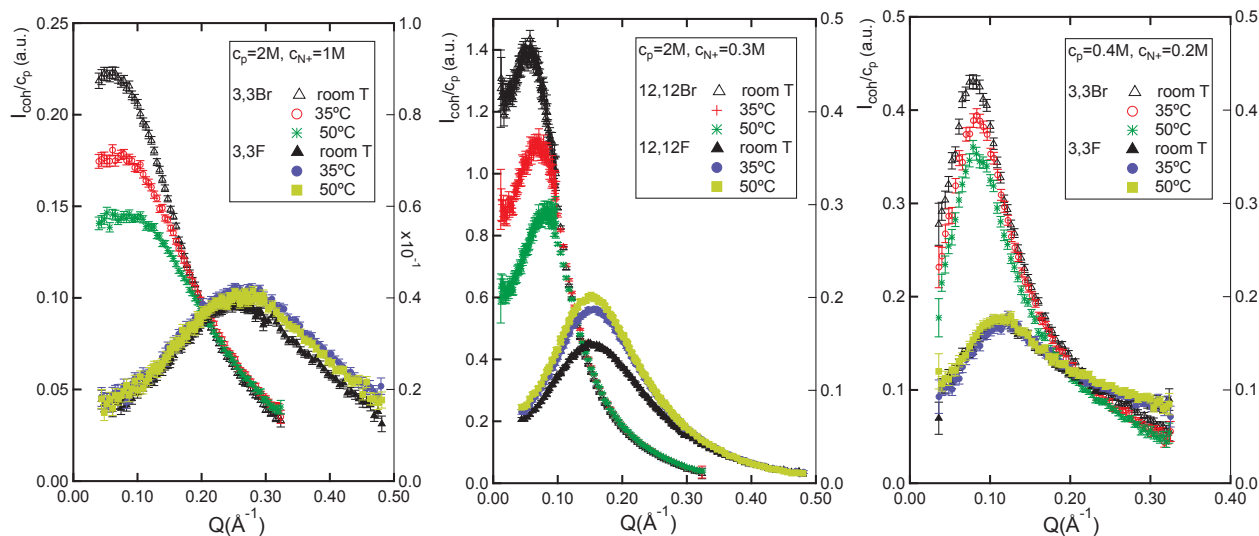


Fig. 4 Coherent neutron scattering intensity normalised by ionene monomer concentration (I_{coh}/c_p) versus scattering wave-vector (Q) for 2 M solutions of 3,3– ionenes (left), 2 M solutions of 12,12– ionenes (center) and 0.4 M solutions of 3,3– ionenes (right) at three temperatures, as indicated. LHS y-scale applies to Br-ionene, RHS y-scale to F-ionene in each case.

unusual phenomenon. It has not been reported for any other polyelectrolyte systems, with the possible exception of PSS with divalent counter ions.⁴³ On the contrary, as shown for many other PE systems, addition of simple electrolyte (salt) leads also to the peak disappearance, though with notable differences, see Figure S2 in Supplementary Information.

The disappearance of the PE peak for Br– ionenes begins at $c_p=0.2-0.3$ M (indicated by an increasingly lower q^* with respect to the F analogues), though the concentration at which the peak disappears completely is higher for more weakly charged chains. Electrostatics is a likely origin of the peak disappearance and thus the concentration of charges, $c(N^+)$, is a more relevant parameter than c_p . The position of the polyelectrolyte peak observed for both F–ionenes and Br–ionenes is replotted in Figure 5, with $c(N^+)$ as the abscissa, instead of c_p . We note that the F–ionene data now superimpose for all ionenes with different charge densities to form a master-curve (12,12–F ionene data cross the master curve hinting at a different character). The 3,3–F and 3,3–Br data is represented both with ignoring and considering Manning condensation to renormalise its charge density. Including Manning condensation brings the data closer to the master-curve. All Br–ionene data sets are now seen to deflect from the master curve at a single point, around $c(N^+)=0.05$ M. Thereafter 3,3–Br and 6,9–Br data continue towards a saturation limit, while 12,12–Br data has its own dependence, hinting again at its somewhat different character (i.e. emerging hydrophobicity of the

backbone). In any case, the total disappearance of the peak in 12,12–Br data is no longer shifted to higher concentrations in this representation. We are aware that the scaling theory does not provide a law for the type of representation in Figure 5, the appearance of a master-curve hints nevertheless at its significance.

2.4 F–Br counter ion specific effect: proposed picture

Our explanation for the F–Br counter ion specific effect in ionenes begins by considering the very different hydration properties of the two counter ions. The presence of a more weakly hydrating counter ion (with respect to F^- , the free energy of hydration is considerably lower in magnitude for Br^-)⁴⁴ results in a more compact counter ion atmosphere around each ionene backbone. It can be pictured as an effective increased affinity of Br^- for the ionene backbone. Such a scenario has been seen previously by molecular dynamics (MD) simulations on ionenes^{45,46} and is also consistent with several thermodynamic data on these systems, such as osmotic coefficients⁴⁷ and in particular enthalpies of dilution and mixing.^{48,49} In addition, we observe some correlation between the extent of the ionene counter ion atmosphere (for different halide ions) and the PE peak position, as seen by the small angle X-ray scattering (SAXS) technique (see Figure S3 in Supplementary Information). Being guided by the electronic density, SAXS is more sensitive to the correlations arising from

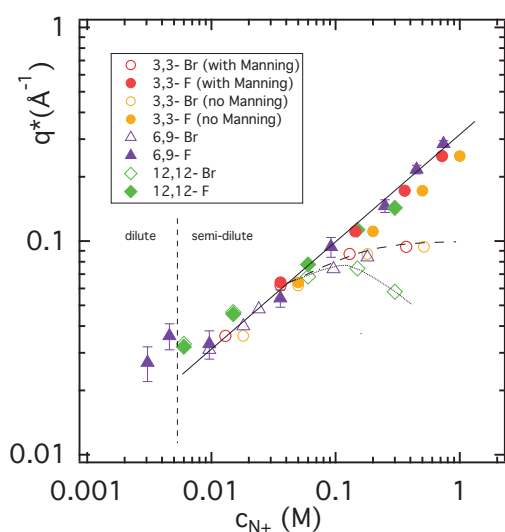


Fig. 5 Position of the polyelectrolyte peak in SANS spectra (q^*) versus charge concentration (c_{N^+}) for various ionene charge densities with either Br^- or F^- counter ions in each case. Error bars represented on the 6,9-F ionene data. Lines are guides to the eye and highlight three different trends. We indicate the transition between the dilute and semi-dilute PE concentration regime by a vertical dashed line.

counter ion clouds, as opposed to the PE backbone in the case of SANS.

Characterising the radial extent of the counter ion atmosphere in the classical way using the Debye length, $r_D = (4\pi l_B c_p f_{eff})^{1/2} = (4\pi l_B c_{N^+})^{1/2}$, this atmosphere contracts as we increase the PE concentration.¹⁰ The Debye length is approximately 43 Å at $c(N^+) = 0.01$ M and is equal to the Bjerrum length (7.14 Å in water at room temperature) already at $c(N^+) = 0.37$ M. At $c(N^+) = 0.05$ M, the onset of the PE peak disappearance, $r_D = 19$ Å, while the typical inter-chain distance, $\xi = 2\pi/q^* = 100$ Å. We see that these values satisfy the condition $r_D < \xi/2$, i.e. the counter ion atmospheres of the adjacent chains do not overlap, which should lead to the disappearance of the PE peak. However, the same condition is actually satisfied throughout the entire charge range mentioned above, so this simple reasoning cannot hold. Moreover, if it did, even the spectra for F-ionenes should not feature a peak. Now, as has been already pointed out by Dobrynin et al.^{10,50}, the electrostatic screening length in PE solutions is, in a certain concentration regime, not represented by the Debye length, rather it is of the order of the chain separation ξ , thus is in many instances *larger* than the Debye screening length. The reasoning is based on a prohibitively large entropy loss of the counter ion cloud. If it is restricted only to the Debye length distance from a PE chain, it leaves a large region between adjacent chains counter-ion free.^{10,50} Viewing the wealth of PE systems studied up to now, they all seem to fall in line with this reasoning and it is indeed the Br-ionenes that are an exception to the rule. Thus, we propose that the localisation of Br^- counter ions close to the ionene backbone due to their above-reported specific affinity (of other than direct electrostatic origin), changes the balance between the enthalpic gain and the entropic loss, in favour of the former. This is supported by the enthalpy of mixing⁴⁹ and molecular dynamics results,^{45,46} showing that only the I^- ion binds stronger to ionene than Br^- . As a result, the constriction of the counter ion atmosphere to below the chain separation indeed occurs for Br-ionenes and no PE peak is observed in this case. This occurs only above a given charge concentration and it is not a sharp transition. The narrower the counter ion atmosphere the more flexible the ionene chain until the scattering data indeed resemble that of a neutral polymer chain, as is the case for 3,3-Br ionenes at $c_p = 2$ M. For an increasingly flexible neutral chain, a less extended and a more globular or Gaussian coil overall conformation is expected, depending on the solvent quality. At the same time, Br^- counter ions in the increasingly constricted atmosphere are not necessarily condensed in the Manning sense, they could still be osmotically active. The current osmotic coefficient data (up to $c(N^+) = 0.1$ M) do not show an anomalous counter ion condensation for ionenes, in contrast to that reported for psPSS.^{35,47,51} However, it is important to extend the existing osmotic coefficients to even high

concentrations. We note that some PE systems have been reported to show a type of "incomplete condensation", retaining partially their osmotic activity in the formerly "condensed" state.⁵²

Within the proposed explanation for the disappearance of the PE peak in Br-ionenes, let us return to the observed temperature trends. It is reasonable to assume that with increasing temperature, the radial extent of the Br⁻ counter ion atmosphere increases and with it the rigidity of the backbone. Thus a more extended configuration of the chain arises and consequently, for a constant contour length, the average inter-chain distance decreases. As a result, the PE peak shifts to higher Q values, towards the q^* value of F-ionenes. The latter are likely to be in a significantly more extended conformation, due to their wide counter ion atmosphere. This is what we observe for 12,12-ionenes, in other words the 12,12-Br chain unfolds with increasing temperature. For 3,3-Br ionenes at 2 M, we observe again a decrease in the low- Q plateau (no peak observed), but we do not recover a PE peak with increasing temperature, as we could expect.

Interpreting the minimum in the low Q limit of the scattering curves in terms of the osmotic compressibility and thus in terms of the effective backbone charge, $S(Q \rightarrow 0) \sim c_p/f_{chem}$,^{10,26} we note that the effective charge on F-ionenes is consistently higher than for Br-ionenes. In direct agreement with this, the available values of osmotic coefficients also indicate higher values for F-ionenes in comparison to Br-ionenes.^{53,54} Moreover, only Br-ionenes show a strong temperature dependence of the neutron spectra, with an increasing f_{eff} as temperature increases. This is indeed consistent with the picture we develop above.

In order to test the hypothesis of an increased affinity of the ionene backbone to Br⁻ counter ions, we have undertaken NMR spectroscopy measurements on mixed counter ion ionenes. It is indeed possible to probe the difference in condensation behaviour between F⁻ and Br⁻ using NMR. The ¹⁹F chemical shift (¹⁹F δ) is sensitive to the local environment of F⁻, particularly to its average position with respect to the PE backbone. In Figure 6 we present the ¹⁹F NMR spectra for a series of 3,3-ionenes with a mixed population of F⁻/Br⁻ counterions at $c_p=2$ M. The molar fraction of Br⁻ counterions (x_{Br}) ranges from 0 to 0.8, as indicated. The ¹⁹F peak shifts towards negative values as x_{Br} increases. The chemical shift in 1 M NaF aqueous solution has also been measured as a reference and is equal to -119.798 ppm. Hence, the variation in the chemical shift indicates that F⁻ ions move towards a more bulk like environment with increasing x_{Br} , i.e. they are removed from the vicinity of PE backbone and are replaced by the Br⁻ ions. To confirm this result, we have also measured the self-diffusion coefficient of F⁻ ions, $D(^{19}F)$, using pulsed field gradient NMR. As shown in Figure 6 $D(^{19}F)$ increases with x_{Br} and comes closer to its value in NaF bulk aqueous

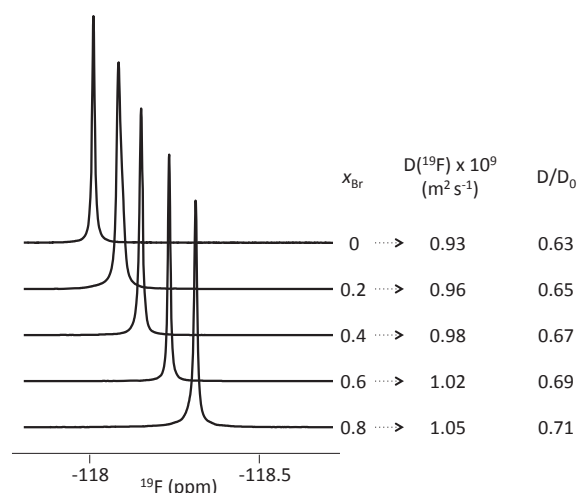


Fig. 6 Left: ¹⁹F NMR spectra for a series of 3,3-ionenes with a mixed population of F⁻/Br⁻ counter ions in aqueous solution ($c_p=2$ M). Molar fraction of Br⁻ counter ions (x_{Br}) ranges from 0 to 0.8. Right: The corresponding self-diffusion coefficient, $D(^{19}F)$, and its ratio with D_0 , the self-diffusion coefficient of F⁻ in aqueous solution at infinitely low concentration ($D_0=1.474 \times 10^{-9} m^2 s^{-1}$).

solution: $D(^{19}F) = 1.265 \times 10^{-9} m^2 s^{-1}$ in 1 M NaF(aq) and $D(^{19}F) = 1.474 \times 10^{-9} m^2 s^{-1}$ at infinite dilution.⁴⁴ This evolution confirms that F⁻ closest to the PE backbone are preferentially replaced by Br⁻, when the proportion of the latter increases.

3 Conclusion

Experimental scattering data for ionene polyelectrolytes, systems with a well defined set of structural features, present a number of aspects and trends that deviate both from previous observations on other polyelectrolyte solutions as well as from the predictions of the existing theory based on scaling concepts. Ionenes do not fall clearly into the current hydrophilic-hydrophobic classification of water soluble polyelectrolytes. In order to observe the emergence of the ionene backbone hydrophobicity, the chain charge density has to decrease to 0.15 (fraction of charged monomers), which is significantly lower than for other hydrophobic polyelectrolytes. This hints at the "weak" hydrophobicity of the hydrocarbon chain (the uncharged ionene backbone), with respect to polyelectrolyte chains with more complex structures and side groups, such as the benzene group.

The counter ion specific effect between ionenes with Br⁻

and F^- counter ions is found to be universal: it is seen for all chain charge densities studied. Interestingly, the polyelectrolyte peak in the scattering spectra of Br⁻-ionenes disappears beyond a specific charge concentration (0.5M), which is independent of the chain charge density. Our interpretation of the F⁻-Br⁻ counter ion specific effect, which is based on the different hydration energies of the two anions, is further supported at this stage by NMR measurements on mixed F/Br counter ion ionenes: F^- closest to the polyelectrolyte backbone are preferentially replaced by Br^- , when the proportion of the latter increases, thus confirming the greater affinity of Br^- ions to the ionene backbone. Due to the greater differences in hydration energies between anions, as opposed to cations, we believe the choice of ionene polyelectrolytes (cationic backbone) allowed us to highlight the counter ion specific effect. Beyond the already mentioned differences, the scattering data of ionenes with Br^- and F^- counter ions feature some contrasting temperature trends. This is most evident for the weakly charged ionenes, for which the hydrophobicity of the neutral linker begins to show its effects. 12,12 F⁻-ionenes show a surprising increase of scattered intensity with increasing temperature, which cannot be accounted for by the predictions of the current scaling theory. On the contrary, 12,12 Br⁻-ionenes feature scattered intensity decreasing with temperature, according to theory.

Overall, ionene polyelectrolytes serve as a clear example highlighting the need for combining the scaling concepts for polyelectrolyte solutions with those of ion specificity, to encompass the wealth of phenomena occurring in these systems.

4 Acknowledgements

The authors thank Mojca Seručnik at the University of Ljubljana for help with sample preparation, José Teixeira for discussions and guidance during neutron scattering experiments at the Laboratoire Léon Brillouin and Francois Ribot at the College de France for discussions and access to NMR spectrometers. M.T. is grateful to Andrej Jamnik for helpful discussions and to Otto Glatter for his most generous contribution to the instrumentation of the SAXS laboratory in Ljubljana. This research was financially supported by the CEA-MHEST (French-Slovenian) bilateral agreement.

References

- M. A. C. Stuart, W. T. S. Huck, J. Genzer, M. Müller, C. Ober, M. Stamm, G. B. Sukhorukov, I. Szleifer, V. V. Tsukruk, M. Urban, F. Winnik, S. Zauscher, I. Luzinov and S. Minko, *Nat. Mater.*, 2010, **9**, 101–113.
- E. A. Appel, J. u. del Barrio, X. J. Loh and O. A. Scherman, *Chem. Soc. Rev.*, 2012, **41**, 6195–6214.
- J. Gensel, I. Dewald, J. Erath, E. Betthausen, A. Muller and A. Fery, *Chem. Sci.*, 2013, **4**, 325–334.
- M. Leong, J. Toh, C. Du, K. Narayanan, H. Lu, T. Lim, A. Wan and J. Ying, *Nat. Commun.*, 2013, **4**, 2353.
- R. Takahashi, Z. Wu, M. Arifuzzaman, T. Nonoyama, T. Nakajima, T. Kurokawa and J. Gong, *Nat. Commun.*, 2014, **5**, 4490.
- J. H. Ortony, T. Chatterjee, L. E. Garner, A. Chworoz, A. Mikhailowsky, E. J. Kramer and G. C. Bazan, *J. Am. Chem. Soc.*, 2011, **133**, 8380–8387.
- C. K. Materese, A. Saveliev and G. A. Papoian, *J. Am. Chem. Soc.*, 2009, **131**, 15005–15013.
- P. G. de Gennes, P. Pincus, R. M. Velasco and F. Brochard, *J. de Physique*, 1976, **37**, 1461–1473.
- P. Pfeuty, *J. de Physique Colloq.*, 1978, **39**, C2–149.
- A. V. Dobrynin, R. H. Colby and M. Rubinstein, *Macromolecules*, 1995, **28**, 1859–1871.
- G. S. Manning, *J. Chem. Phys.*, 1969, **51**, 924–933.
- G. S. Manning, *J. Chem. Phys.*, 1969, **51**, 934–938.
- J. Combet, F. Isel, M. Rawiso and F. Boué, *Macromolecules*, 2005, **38**, 7456–7469.
- M. Muthukumar, *J. Chem. Phys.*, 2004, **120**, 9343–9350.
- A. Salis and B. W. Ninham, *Chem. Soc. Rev.*, 2014, **43**, 7358.
- W. Kunz and R. Neueder, *Specific Ion Effects*, World Scientific, New Jersey, 2009, pp. 3–54.
- Y. Marcus, *Chem. Rev.*, 2009, **109**, 1346–1370.
- P. Jungwirth and D. J. Tobias, *Chem. Rev.*, 2006, **106**, 1259–1281.
- K. D. Collins, *Biophys. J.*, 1997, **72**, 65–76.
- W. J. Xie and Y. Q. Gao, *J. Chem. Phys. Lett.*, 2013, **4**, 4247–4252.
- B. Liu, E. Y. Kelly and J. Liu, *Langmuir*, 2014, **30**, 13228–13234.
- O. E. Philippova, A. M. Romyantsev, E. Y. Kramarenko and A. R. Khokhlov, *Macromolecules*, 2013, **46**, 9359–9367.
- N. Yasumoto, N. Kasahara, A. Sakaki and M. Satoh, *Colloid Poly. Sci.*, 2006, **284**, 900–908.
- T. A. Waigh, R. Ober, C. E. Williams and J.-C. Galin, *Macromolecules*, 2001, **34**, 1973–1980.
- M. N. Spiteri, C. E. Williams and F. Boué, *Macromolecules*, 2007, **40**, 6679–6691.
- W. Essafi, N. Haboubi, C. Williams and F. Boué, *J. Phys. Chem. B*, 2011, **115**, 8951–8960.
- J. Combet, P. Lorchat and M. Rawiso, *Eur. Phys. Journal - Special Topics*, 2012, **213**, 243–265.
- M. P. Raskop, A. Grimm and A. Seubert, *Microchim. Acta*, 2007, **158**, 85–94.
- E. F. Lucas, C. R. E. Mansur, L. Spinelli and Y. G. C. Queiros, *Pure and Appl. Chem.*, 2009, **81**, 473–494.
- S. Berezovska, V. Yanishpolski, V. A. Tertykh, M. V. Burmistr and S. K. M., *J. Thermal Anal. and Calorimetry*, 2006, **86**, 93–96.
- E. Kiss, E. T. Heine, K. Hill, Y. C. He, N. Keusgen, C. B. Péntzes, D. Schnöller, G. Gyulai, A. Mendrek, H. Keul and M. Moeller, *Macromol. Bioscience*, 2012, **12**, 1181–1189.
- A. Rembaum and H. Noguchi, *Macromolecules*, 1972, **5**, 261–269.
- A. Rembaum and H. Noguchi, *Macromolecules*, 1972, **5**, 253–260.
- S. R. Williams and T. E. Long, *Progress in Polymer Science*, 2009, **34**, 762–782.
- N. Malikova, S. Cebasek, V. Glenisson, D. Bhowmik, G. Carrot, V. Vlachy, *Phys. Chem. Chem. Phys.*, 2012, **14**, 12898–12904.
- M. Lukšič, R. Buchner, B. Hribar-Lee and V. Vlachy, *Macromolecules*, 2009, **42**, 4337–4342.
- D. Wu, A. Chen and C. S. Johnson, Jr., *J. Magn. Reson. A*, 1995, **115**, 260–264.
- A. V. Dobrynin and M. Rubinstein, *Macromolecules*, 1999, **32**, 915–922.
- G. B. McGaughey, M. Gagne and A. K. Rappe, *J. Biol. Chem.*, 1998, **273**, 15458–15463.
- D. Bhowmik, N. Malikova, G. Mériguet, O. Bernard, J. Teixeira and P. Turq, *Phys. Chem. Chem. Phys.*, 2014, **16**, 13447–13457.

-
- 41 K. Nishida, K. Kaji and T. Kanaya, *J. Chem. Phys.*, 2001, **114**, 8671–8677.
- 42 J.-L. Barrat and J.-F. Joanny, *Adv. Chem. Phys.*, 1996, **XCIV**, 1–66.
- 43 J. Combet, M. Rawiso, C. Rochas, S. Hoffmann and F. Boué, *Macromolecules*, 2011, **44**, 3039–3052.
- 44 R. A. Robinson and R. H. Stokes, *Electrolyte solutions*, Dover publications, New York, 2002.
- 45 M. Druchok, B. Hribar Lee, H. Krienke and V. Vlachy, *Chem. Phys. Letters*, 2008, **450**, 281–285.
- 46 M. Druchok, V. Vlachy and K. A. Dill, *J. Phys. Chem. B*, 2009, **113**, 14270–14276.
- 47 K. Arh, C. Pohar and V. Vlachy, *J. Phys. Chem. B*, 2002, **106**, 9967–9973.
- 48 S. Čebašek, M. Lukšič, C. Pohar and V. Vlachy, *J. Chem. Eng. Data*, 2011, **56**, 1282–1292.
- 49 M. Seručnik, M. Bončina, M. Lukšič and V. Vlachy, *Phys. Chem. Chem. Phys.*, 2012, **14**, 6805–6811.
- 50 M. Rubinstein, H. R. Colby, A. V. Dobrynin and J.-F. Joanny, *Macromolecules*, 1996, **29**, 398–406.
- 51 W. Essafi, F. Lafuma, D. Baigl and C. E. Williams, *Europhys. Lett.*, 2005, **71**, 938–944.
- 52 D. Qu, J. S. Pedersen, S. Garnier, A. Laschewsky, H. Möhwald and R. von Klitzing, *Macromolecules*, 2006, **39**, 7364–7371.
- 53 M. Lukšič, R. Buchner, B. Hribar-Lee and V. Vlachy, *Phys. Chem. Chem. Phys.*, 2009, **11**, 10053–10058.
- 54 P. Rodič, M. Bratuša, M. Lukšič, V. Vlachy and B. Hribar-Lee, *Colloids and Surfaces A: Phys. Eng. Aspects*, 2013, **424**, 18–25.