

# Catalysis Science & Technology

Accepted Manuscript



This is an *Accepted Manuscript*, which has been through the Royal Society of Chemistry peer review process and has been accepted for publication.

*Accepted Manuscripts* are published online shortly after acceptance, before technical editing, formatting and proof reading. Using this free service, authors can make their results available to the community, in citable form, before we publish the edited article. We will replace this *Accepted Manuscript* with the edited and formatted *Advance Article* as soon as it is available.

You can find more information about *Accepted Manuscripts* in the [Information for Authors](#).


Please note that technical editing may introduce minor changes to the text and/or graphics, which may alter content. The journal's standard [Terms & Conditions](#) and the [Ethical guidelines](#) still apply. In no event shall the Royal Society of Chemistry be held responsible for any errors or omissions in this *Accepted Manuscript* or any consequences arising from the use of any information it contains.

Graphical Abstract:

## Direct Evidence for a Coordination-Insertion Mechanism in Ethylene Oligomerization Catalyzed by Neutral 2,6-Bisiminopyridine Iron Monoalkyl complexes.

M. Ángeles Cartes, Antonio Rodríguez-Delgado, Pilar Palma, Luis J. Sánchez and Juan Cámpora\*.

<sup>1</sup>H NMR studies on the ethylene oligomerization catalyzed by the neutral iron monoalkyl **3** allowed direct observation of alkyliron intermediates as well as reversible ethylene coordination to the metal center, providing for the first time direct evidence for a coordination-insertion mechanism in iron-catalyzed ethylene upgrade reactions.

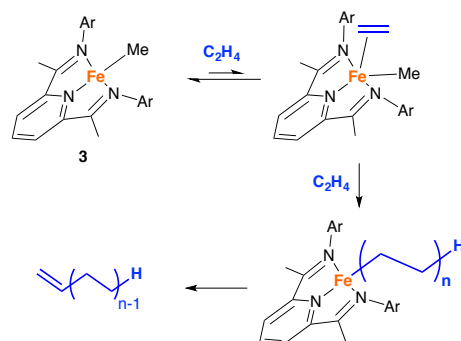

## Direct Evidence for a Coordination-Insertion Mechanism in Ethylene Oligomerization Catalysed by Neutral 2,6-Bisiminopyridine Iron Monoalkyl Complexes.

Cite this: DOI: 10.1039/x0xx00000x

Received 00th January 2012,  
Accepted 00th January 2012

M. Ángeles Cartes, Antonio Rodríguez-Delgado, Pilar Palma, Luis J. Sánchez and Juan Cámara.\*


DOI: 10.1039/x0xx00000x

[www.rsc.org/catalysis](http://www.rsc.org/catalysis)

**<sup>1</sup>H NMR studies on ethylene oligomerization catalysed by the neutral monoalkyl complex [Fe(Me)(<sup>i</sup>PrBIP)] allows direct observation of alkyliron intermediates as well as reversible ethylene coordination to the metal center, providing for the first time experimental evidences for a coordination-insertion mechanism in iron-catalysed ethylene upgrade reactions.**

Iron complexes with 2,6-bisiminopyridines (BIP) ligands continue to attract the interest of many research groups more than 15 years after the discovery of their catalytic activity in olefin polymerization.<sup>1</sup> Today, the uses of these compounds in catalysis have extended to many other important reactions.<sup>2</sup> One of the key factors for the success of BIP ligands in catalysis is their redox non-innocence, which enables reversible redox processes that are not accessible for complexes containing uniquely spectator ancillary ligands.<sup>3</sup> Even though olefin polymerization does not require redox changes during the catalytic cycle, iron catalysts benefit somehow of the special properties of BIPs since few other types of iron complexes exhibit comparable catalytic performances in such reactions.<sup>4</sup> In fact, the non-innocent behaviour of BIP ligands casts uncertainty on the identity of the catalytic species involved in typical iron polymerization systems generated from halide precursors [FeX<sub>n</sub>(BIP)] (n = 2, 3) and organoaluminum co-catalysts. It is known that reacting these iron halocomplexes with main group organometallics frequently leads to neutral or even anionic alkyl complexes [Fe(R)(BIP)]<sup>0/-</sup> that are best described as arising from the reduction of the BIP ligand rather than the metal center.<sup>5</sup> On the other hand, although Chirik demonstrated that cationic monoalkyls [Fe(R)(<sup>i</sup>PrBIP)]<sup>+</sup> containing a Fe(II) center and an innocent, electroneutral <sup>i</sup>PrBIP ligand (<sup>i</sup>PrBIP = 2,6-bis-(2,6-diisopropylphenyl)acetimidoylpyridine) are very active single-component ethylene polymerization catalysts,<sup>6</sup> this does not rule out that different alkyliron complexes species could be involved in iron-catalysed ethylene polymerization. Thus, in a series of spectroscopic studies of the activation of [FeCl<sub>2</sub>(BIP)] complexes with MAO or trialkylaluminum reagents, Bryliakov and Talsi identified the formation of two types of bimetallic Fe/Al products.<sup>7</sup> While MAO gives rise to relatively stable cationic complexes [Fe(μ-X)(μ-Me)AlMe<sub>2</sub>(BIP)]<sup>+</sup>, (X = Cl,

Me) simple aluminum alkyls (trimethyl or triisobutylaluminum) lead to isostructural but neutral species [Fe(μ-X)(μ-Alkyl)<sub>2</sub>Al(Alkyl)<sub>2</sub>(BIP)] (X = Cl, Alkyl) that are unstable at the room temperature. Based on these results, the authors suggested that, depending on the activator used, either cationic (A) or electroneutral (B) propagating species could be formed upon dissociation of the AlR<sub>3</sub> unit (Figure 1) respectively containing innocent or singly reduced BIP ligands, but sharing in common a high-spin Fe(II) ion. Intriguingly, it was suggested that, given the similar electronic configuration of the metal centre in both intermediates, they should exhibit similar catalytic behaviour.<sup>6b,7b</sup>

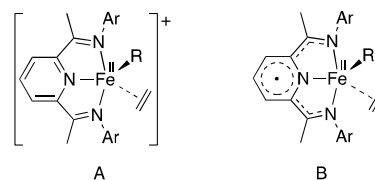


**Figure 1.** Cationic and neutral propagating species proposed for iron-catalysed ethylene polymerization

We have reported recently that the iron dialkyl complex [Fe(CH<sub>2</sub>SiMe<sub>3</sub>)<sub>2</sub>(<sup>i</sup>PrBIP)] (**1**) react with trimethylaluminum (TMA) in a stepwise manner (Scheme 1).<sup>8</sup> NMR studies showed that the first step, reduction to the monoalkyl complex [Fe(CH<sub>2</sub>SiMe<sub>3</sub>)(<sup>i</sup>PrBIP)], **2**, is accomplished with one equivalent amount of TMA per Fe atom. With a second equivalent of TMA the CH<sub>2</sub>SiMe<sub>3</sub> group is exchanged to afford the monomethyl complex [Fe(Me)(<sup>i</sup>PrBIP)], **3**. Very likely, this sequence of reactions is closely related to the activation of Fe-BIP complexes by TMA therefore the reactivity of complexes **2** and **3** towards ethylene would be highly relevant in order to understand the mechanism of the catalytic polymerization reaction.

Although **2** and **3** are paramagnetic, this type of complexes give rise to informative <sup>1</sup>H NMR spectra, and this provides a direct means for investigating their interaction with ethylene. When the latter is bubbled through solutions of complexes **2** or **3** in C<sub>6</sub>D<sub>6</sub>, at the room temperature no polyethylene is formed but GC analyses revealed the formation of mixtures of oligomers (> 95 % α-olefins), characterized by a Flory-Schulz molecular weight distribution coefficient 0.57. Once

## COMMUNICATION

ethylene is consumed, slow isomerization of the  $\alpha$ -olefins takes place as indicated by the gradual growth of new peaks in the GC of the mixtures. Precise quantification of the catalytic activities in the absence of aluminum alkyls was hampered by the sensitivity of these catalysts to impurity traces in ethylene. However,  $^1\text{H}$  NMR showed that samples containing 8  $\mu\text{mol}$  of **2** or **3** consumed 5 mL of ethylene (ca. 25 equiv) within 60 and 45 min, respectively, indicating turnover frequencies in the 20 – 40  $\text{h}^{-1}$  range. Although these activities are quite low, they demonstrate that neutral monoalkyl complexes have a distinct reactivity towards ethylene, different from ethylene polymerization observed in dual Fe/Al catalytic systems. In addition, the ability of **2** and **3** to oligomerize ethylene contrasts with the lack of catalytic activity of their cobalt analogues.<sup>9</sup>

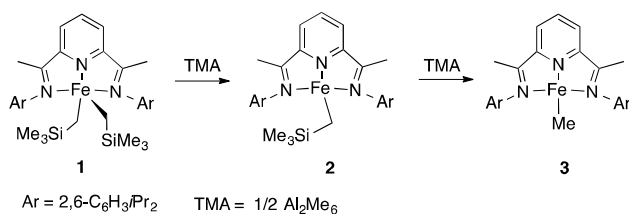

Scheme 1.


At the room temperature, ethylene has no effect on the  $^1\text{H}$  NMR spectra of **2** and **3**, *i. e.*, the oligomerization reaction proceeds while the shape and position of the signals of the complexes remain unaltered. When the oligomerization with **2** is monitored, any active intermediates remain below the detection threshold, presumably because the initial ethylene insertion into the Fe- $\text{CH}_2\text{SiMe}_3$  bond is considerably slower than the catalytic process. However, in the case of **3**, at least two sets of low intensity signals corresponding to as many different intermediates were observed during the catalytic reaction (Figure 1). The relative intensity of these signals evolves during the experiment. After 20 min, they represent up to 30 % of the original intensity of **3** but as ethylene is depleted they decay and fade away within several hours.

As shown in Figure 2, most new signals appear in regions that are close to the analogous signals of **3**. This is the kind of spectral analogy that would be expected if the new signals correspond to alkyl complexes arising from ethylene insertion reactions. Furthermore, the positions match very closely the chemical shifts reported by Chirik for the ethyl and butyl complexes  $[\text{Fe}(\text{R})(\text{iPrBIP})]$  (R = Et, *n*-Bu), marked


with dotted lines in the figure.<sup>10</sup> The slight deviations with regard the literature values are systematic and can be attributed to small differences of experimental variables such as temperature or concentration. The identification of the main intermediate signals as belonging to these two alkyl complexes is confirmed by the observation of two signals at  $\delta$  [unclear] [unclear] that have no correlates in the spectrum of **3** but match the chemical shifts reported for the  $\beta$ -hydrogen atoms of the ethyl and butyl groups. Actually, the ethyl and butyl complexes are expected to be the most abundant intermediates in an ethylene oligomerization cycle involving chain propagation by consecutive ethylene insertions and termination by chain transfer to the monomer, which suggests that this mechanism also operates in this system. These compounds are known to be thermally unstable in solution, and this is also in agreement with the disappearance of the signals once ethylene has been consumed. Note that several low-intensity paramagnetic signals are observed after 5 h. These are different from those observed in the initial stages and we tentatively assign them to branched alkyl species participating in the olefin isomerization process.

Although the accumulation of detectable amounts of intermediates indicates that **3** is more reactive than **2**, only a fraction of the former actually reacts with ethylene (in spite of this being initially in a large excess), indicating that the ethylene insertion into the Fe-C bond is still somewhat slower for the methyl complex than for higher alkyl intermediates. The origin of this effect is unclear, but could be related to the somewhat higher thermodynamic stability of transition metal-carbon bonds in methyl complexes than in ethyl or higher alkyls.<sup>11</sup>

Prior to insert into the Fe-C bond of **3**, ethylene has to coordinate to the iron centre. Although, as mentioned before, the  $^1\text{H}$  NMR spectrum of **3** is not altered by the presence of ethylene at 25  $^\circ\text{C}$ , variable temperature NMR experiments provided evidence for the reversible  $\text{Fe}\cdots\text{C}_2\text{H}_4$  interaction (Figure 3). Injecting ethylene (0.6 mL) in a toluene- $d_6$  solution of **3** (10  $\mu\text{mol}$ ; ethylene/**3** = 2.4) at  $-70$   $^\circ\text{C}$  causes the disappearance of all paramagnetic signals. The signals of **3** are observed again when the sample is warmed up to  $-50$   $^\circ\text{C}$ , although they appear broader and their intensity is ca. 25 % lower than the original. These recover their initial intensity and width as the temperature is increased. Simultaneously, the ethylene signal broadens and shifts to higher frequency. At 5  $^\circ\text{C}$ , all signals of **3** display normal intensities,

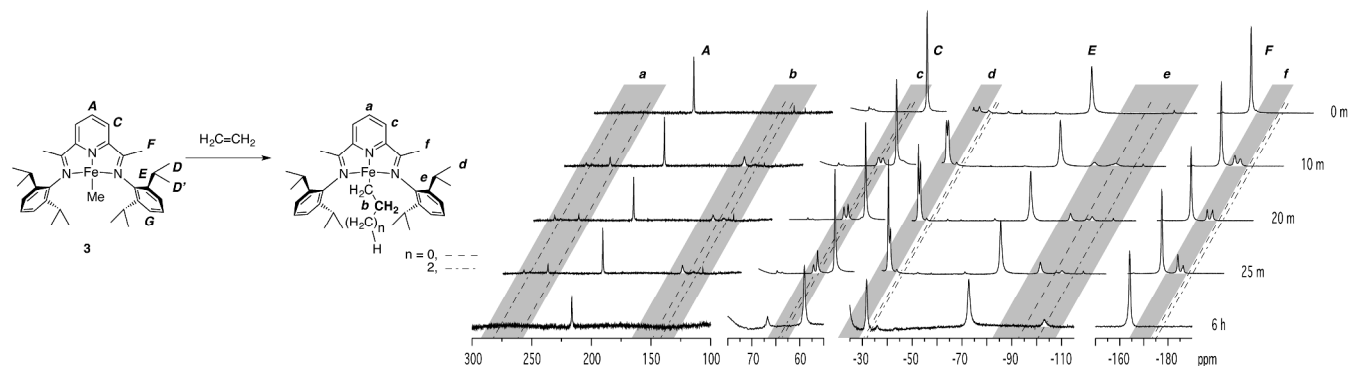

**Figure 2.**  $^1\text{H}$  NMR monitoring of the reaction of **3** with ethylene (25 Eq). Shaded regions contain signals for complexes arising from ethylene insertions into the Fe-C bonds. Dotted lines mark the position of signals of the ethyl ( $n = 0$ ) and butyl complexes ( $n = 2$ ), taken from ref. 14.

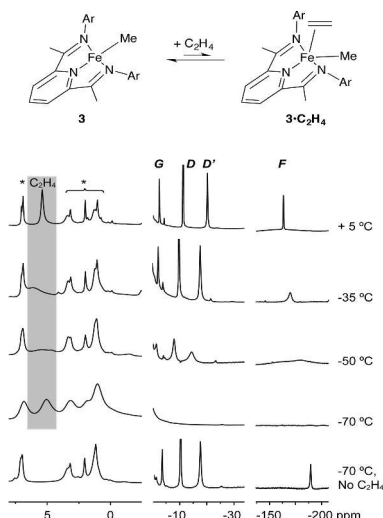

**Figure 3.** Selected regions of the  $^1\text{H}$  NMR spectrum of **3** recorded at different temperatures, in absence (bottom) and in presence of ethylene (2.4 Equiv). Signals in the diamagnetic region marked \* correspond to solvent (hexane) and residual peak of solvent (toluene- $d_6$ ). Signals D, D', F and G correspond to **3** (see Fig. 1). Vertical scales have been optimized to improve clarity.

positions and widths although that of ethylene remains broad. These observations are consistent with the formation of an NMR-silent ethylene adduct,  $3\cdot\text{C}_2\text{H}_4$ , which is thermodynamically favoured at low temperature but begins to dissociate above  $-50\text{ }^\circ\text{C}$  allowing rapid exchange between free and coordinated ethylene. The ethylene binding constant, estimated from the decrease of the intensities of the signals of **3** between  $-50$  and  $-35\text{ }^\circ\text{C}$ , is ca.  $8.5\text{ L mol}^{-1}$ , corresponding to  $\Delta G^\circ \approx -1\text{ Kcal/mol}$ , in good agreement with preliminary DFT calculations, see SI. The room temperature spectrum is consistent with essentially full dissociation of  $3\cdot\text{C}_2\text{H}_4$ , but ethylene oligomerization indicates that the complex remains thermodynamically accessible as a reaction intermediate. Although evidence for the reversible binding of ethylene to a Fe(II) alkyl complex has been reported before,<sup>12</sup> this is the first time that such interaction is observed with a catalytically active Fe-BIP complex.

Compared with their cationic analogues,<sup>6a</sup> **2** and **3** are orders of magnitude less active and produce lower molecular weight products. However, since the electronic configuration and stereochemical environment of the iron centre is very similar in both types of compounds, it is very likely that the mechanisms of chain propagation and transfer are also qualitatively similar in both cases. It is also noteworthy that, although the cobalt analogues of **2** and **3** are catalytically inactive, higher alkyls [Co(CH<sub>2</sub>CH<sub>2</sub>R)(<sup>i</sup>Pr-BIP)] readily undergo chain transfer to ethylene.<sup>13</sup> This suggests an analogy between the Fe and Co systems: in both cases going from the cationic to the neutral systems rises the ethylene insertion barrier, while chain transfer remains a competitive process.

In summary, we have shown that iron monoalkyl complexes **2** and **3** catalyse ethylene oligomerization to linear  $\alpha$ -olefins. For the first time, we detected the reversible interaction of iron alkyls with the monomer and observed the formation of alkyliron complexes arising from consecutive ethylene insertions. Although these observations support the idea that the similar electronic configuration of the iron

centre in isostructural neutral and cationic monoalkyl derivatives should lead to comparable catalytic activity,<sup>7,8</sup> the low catalytic activity of **2** and **3** and the low molecular weight of the products rule out the direct involvement of neutral iron monoalkyls in two-component ethylene polymerization catalysts.

This work was supported by the Spanish Government, Junta de Andalucía, and the European Union (Projects CTQ2012-30962, FQM5074 and FEDER funds). MAC thanks CSIC for an I3P predoctoral fellowship. We thank CESGA for granting access to computational resources (ICTS proposal No. 262).

## Notes and references

Instituto de Investigaciones Químicas. CSIC – Universidad de Sevilla. c/ Américo Vespucio, 41092, Sevilla, Spain. E-mail: [campora@iiq.csic.es](mailto:campora@iiq.csic.es); FAX: +34 954460565; Tel: +34 954489555

- 1 L. Li, and P. T. Gomes, in *Olefin Upgrading Catalysis with Nitrogen-based Metal Complexes*, eds. G. Giambastiani and J. Cámpora, Springer, Dordrecht, 2011, vol. II, pp. 77-198.
- 2 See for example: a) J. V. Obligacion, P. J. Chirik, *Org. Letters* 2013, **15**, 2680. b) K. Sylvester, P. J. Chirik, *J. Am. Chem. Soc.* 2009, **131**, 8772. c) A. B. Biernesser, J. A. Byers, *J. Am. Chem. Soc.* 2013, **135**, 16553.
- 3 a) S. Blanchard, E. Derat, M. Desage-El Murr, L. Fensterbank, M. Malacria, V. Mouríés-Mansuy, *Eur J. Inorg. Chem.*, 2012, 376. b) P. J. Chirik, K. Weighardt, *Science*, 2010, **327**, 794.
- 4 a) W. Zhang, W. H. Sun, C. Redshaw, *Chem. Soc. Rev.* 2012, **42**, 8988. b) A. Boudier, P. A. R. Breuil, L. Magna, H. Olivier-Borbigou, P. Braunstein, *Chem. Commun.* 2014, **50**, 1398.
- 5 Q. Knijnenburg, S. Gambarotta and P. H. M. Budzelaar, *Dalton Trans.*, 2006, 5442.
- 6 a) M. W. Bowkamp, E. Lobkovsky and P. J. Chirik, *J. Am. Chem. Soc.*, 2006, **127**, 9660. b) A. M. Tondreau, C. Milsman, A. D. Patrick, H. M. Hoyt, E. Lobkovsky, K. Weighardt and P. J. Chirik, *J. Am. Chem. Soc.*, 2010, **132**, 15046.
- 7 a) K. P. Bryliakov, N. V. Semikolenova, V. A. Zakharov and E. P. Talsi, *Organometallics*, 2004, **23**, 5375. b) Bryliakov, E. P. Talsi, N. V. Semikolenova and V. A. Zakharov, *Organometallics*, 2009, **28**, 3225.
- 8 M. A. Cartes, A. Rodríguez-Delgado, P. Palma, E. Álvarez, J. Cámpora. *Organometallics*, 2014, **33**, 1834.
- 9 a) T. M. Kooistra, Q. Knijnenburg, J. M. M. Smits, A. D. Horton, P. H. M. Budzelaar and A. W. Gal, *J. Am. Chem. Soc.*, 2001, **40**, 4719. b) N. Kielgrewe, W. Steffen, T. Blömker, G. Kehr, R. Fröhlich, B. Wibbling, G. Erker, J.-C. Wasilike, G. Wu and G. Bazan, *J. Am. Chem. Soc.*, 2005, **127**, 13955. c) M. J. Humphries, K. P. Tellmann, V. C. Gibson, A. J. P. White and D. J. Williams, *Organometallics*, 2005, **24**, 2309.
- 10 R. J. Trovitch, E. Lobkovsky and P. J. Chirik, *J. Am. Chem. Soc.*, 2009, **130**, 11631.
- 11 J. A. M. Simoes, J. L. Beauchamp. *Chem Rev.* 1990, **90**, 629.
- 12 Volbeda, J. Bouwkamp, M. W. *Organometallics* 2009, **28**, 209.
- 13 V. C. Gibson, K. P. Tellman, M. J. Humphreys, D. F. Wass, *Chem. Commun.* 2002, 2136.