

Dalton Transactions

Accepted Manuscript



This is an *Accepted Manuscript*, which has been through the Royal Society of Chemistry peer review process and has been accepted for publication.

Accepted Manuscripts are published online shortly after acceptance, before technical editing, formatting and proof reading. Using this free service, authors can make their results available to the community, in citable form, before we publish the edited article. We will replace this *Accepted Manuscript* with the edited and formatted *Advance Article* as soon as it is available.

You can find more information about *Accepted Manuscripts* in the [Information for Authors](#).

Please note that technical editing may introduce minor changes to the text and/or graphics, which may alter content. The journal's standard [Terms & Conditions](#) and the [Ethical guidelines](#) still apply. In no event shall the Royal Society of Chemistry be held responsible for any errors or omissions in this *Accepted Manuscript* or any consequences arising from the use of any information it contains.

Formylated Chloro-Bridged Iridium(III) Dimers as OLED Materials: Opening Up New Possibilities

*Michael.Y. Wong,^a Guohua Xie,^b Clarisse. Tourbillon,^{c,d} Martina Sandroni,^{c,e} David B. Cordes,^a
Alexandra M. Z. Slawin,^a Ifor D. W. Samuel,^b Eli Zysman-Colman^{*a}*

^a EaStCHEM School of Chemistry, University of St Andrews, St Andrews, Fife, UK, KY16 9ST, Fax: +44-1334 463808; Tel: +44-1334 463826; E-mail: eli.zysman-colman@st-andrews.ac.uk;

^b School of Physics and Astronomy, University of St. Andrews, North Haugh, St. Andrews, Fife, UK, KY16 9SS

^c Département de Chimie, Université de Sherbrooke, Sherbrooke, Québec, Canada, J1K 2R1,

^d Current address: Laboratoire PPSM - CNRS UMR 8531, ENS Cachan, 61 Av du Président Wilson, 94235 Cachan Cedex France

^e Current address: CEMCA UMR CNRS 6521, Université de Bretagne Occidentale, 6 av. Victor Le Gorgeu, Brest, France, 29200

URL: <http://www.zysman-colman.com>

Abstract.

In this study, a series of four formyl-substituted chloro-bridged iridium(III) dimers were prepared. Their absorption, photophysical and electrochemical properties were studied in dichloromethane solution. It was found that as the formyl content increased on the cyclometalating ligands, emission unexpectedly became brighter. Organic light-emitting diodes (OLEDs) were fabricated using each of these iridium dimers as the emitter. The OLED fabricated using the brightest of the series, **2b**, as the dopant afforded a decent

external quantum efficiency (EQE) of 2.6%. This suggests that chloro-bridged iridium dimers are potential candidates as solid-state emitters.

Introduction. Neutral mononuclear cyclometalated iridium complexes have received intense attention as emitters for organic light emitting diodes (OLEDs) in lighting and visual displays.¹ Their privileged use is due to the phosphorescent nature of the emission, which is mediated by the iridium metal that facilitates intersystem crossing due to spin-orbit coupling.² Thus, unlike OLED devices based on fluorescent emitters whose internal quantum efficiencies (IQE) are capped by 25% according to spin statistics, 100% of the excitons can be harvested in phosphorescent electroluminescent devices.³ Additionally, iridium(III) complexes typically exhibit bright emission at room temperature that can be tuned across the visible spectrum as a function of substitution about and combination of ligands, possess short radiative lifetimes that mitigates undesirable triplet-triplet annihilation and are thermally and chemically stable.⁴

The majority of syntheses of these mononuclear iridium complexes proceeds via the formation of a dichloro-bridged iridium intermediate of the form $[\text{Ir}(\text{C}^{\wedge}\text{N})_2\text{Cl}]_2$ where $\text{C}^{\wedge}\text{N}$ is a cyclometalating ligand such as the commonly used 2-phenylpyridinato, ppy. Despite the thousands of articles relating to the photophysical study of mononuclear iridium complexes, since the seminal work by Watts and co-workers⁵ almost thirty years ago, the study of these iridium dimers has often been overlooked.⁶ This has certainly been influenced by the fact that the parent iridium dimer, $[\text{Ir}(\text{ppy})_2\text{Cl}]_2$, and indeed most

dimers in this family, are very poorly emissive^{5b,7} in toluene solution while *fac*-Ir(ppy)₃, under similar conditions, exhibits a photoluminescence quantum yield, Φ_{PL} , ranging from 70% to near unity, depending upon the medium.⁸ Bryce, Monkman and co-workers^{6b} recently reported the first examples of dichloro-bridged iridium complexes used as emissive dopants in OLEDs. Employing complexes with substituted fluorenylpyridine C^N ligands dispersed in a PVK host polymer, they could obtain OLEDs with EQEs ranging from 0.6 to 4% and power efficiencies of 0.4-3.53 lm W⁻¹.

Monoformyl-substituted C^N ligands incorporated onto mononuclear iridium complexes have been investigated,⁹ particularly by Lo and co-workers¹⁰ as a tool for grafting on receptor units for bioimaging. To the best of our knowledge, no one has explored the optoelectronic properties of the dichloro-bridged dinuclear complexes bearing formyl-substituted ppy ligands. In this study, we synthesized and characterized a series of dichloro-bridged iridium dimers whose structures are shown in Chart 1. The optoelectronic properties of **1a-2b** were probed as a function of the regiochemistry and number of formyl units present on the cyclometalating (C^N) ligands. Unexpectedly, when the number of formyl units increased, the Φ_{PL} of the complex increased significantly, with **2a** the brightest at 15.7% in DCM. OLED devices were fabricated using these complexes as phosphorescent dopants with performances modestly reduced in comparison to those reported by Bryce, Monkman and co-workers.^{6b} This study corroborates their earlier report that dichloro-bridged dinuclear iridium complexes, even those simply functionalized as is the case here, can be used as the emissive layer in viable OLED devices.


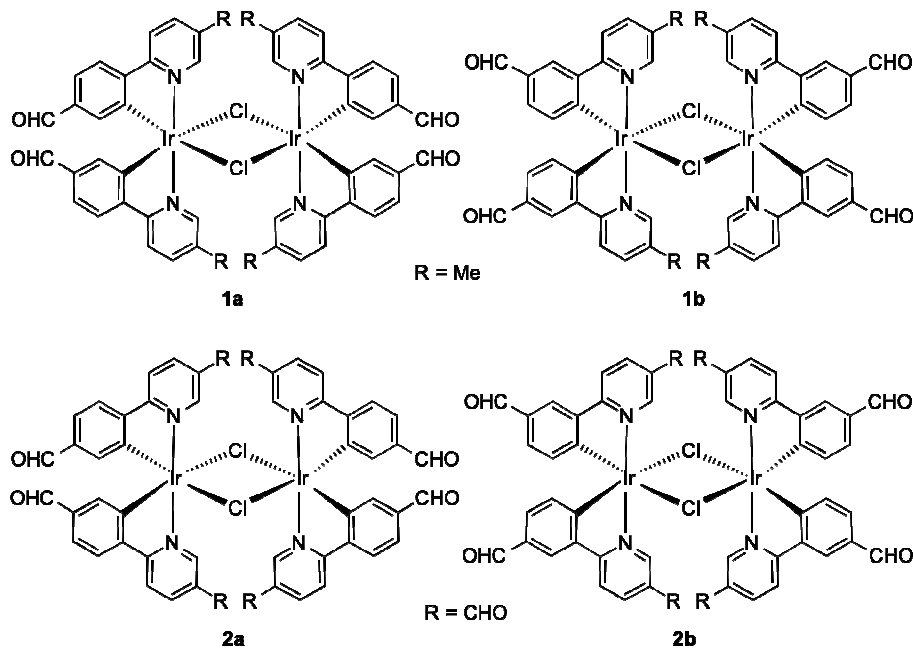


Chart 1. Chemical structures of the complexes presented in this study.

Results and Discussions:

Ligand and complex synthesis.

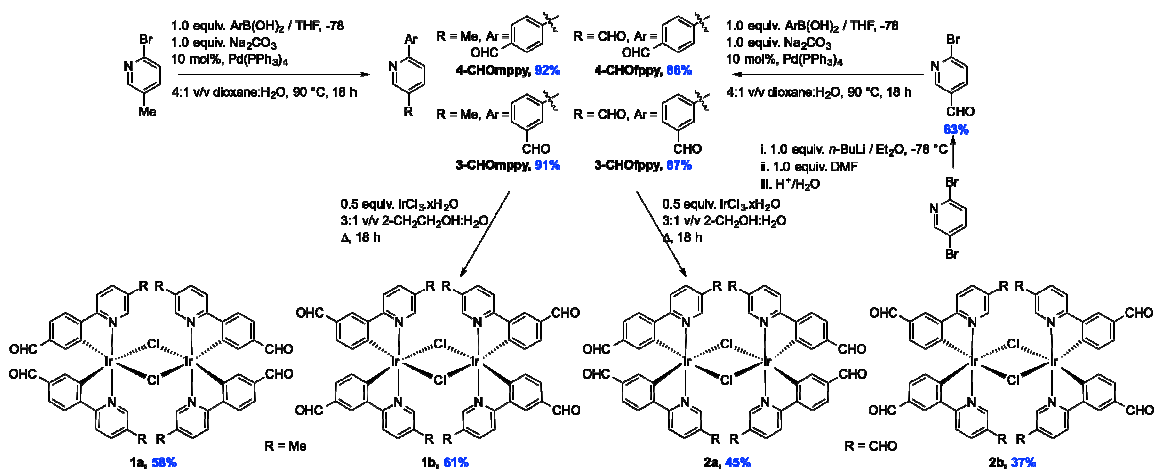

Scheme 1. Synthesis of formyl-substituted C^N ligands and iridium dimer complexes **1a-2b**.

The formyl-substituted cyclometalating (C^N) ligands were obtained in excellent yields (86-92%) following a Suzuki-Miyaura¹¹ coupling between the suitably formylated arylboronic acid and either 2-bromo-5-methylpyridine or 2-bromo-5-formylpyridine (Scheme 1). The use of Pd(PPh₃)₄ as the catalyst resulted in much cleaner conversion to product than with Pd(PPh₃)₂Cl₂, wherein significant homocoupling of the arylboronic acid was observed. The latter functionalized pyridine was itself obtained in 63% yield *via* regioselective lithium halide exchange in diethyl ether, quench with DMF and subsequent hydrolysis.¹²

The dichloro-bridged iridium(III) dimers were prepared according to the protocol first reported by Nonoyama.¹³ While **1a** and **1b** were obtained in 58 and 61%, respectively and were analytically pure following precipitation from a refluxing 3:1 v/v mixture of 2-ethoxyethanol/water, under these same conditions the synthesis of **2a** and **2b** resulted in very complicated ¹H NMR spectra. However, when the synthesis was repeated in a refluxing 3:1 v/v mixture of 2-methoxyethanol/water, **2a** and **2b** precipitated from the solution and could be obtained in more modest 45 and 37% yields, respectively. Complexes **1a-2b** were characterized by ¹H NMR, ¹³C NMR, Mp and HRMS. Additionally single crystals of sufficient quality for X-ray diffraction analyses for all four complexes were obtained (*vide infra*)

Solution state characterization

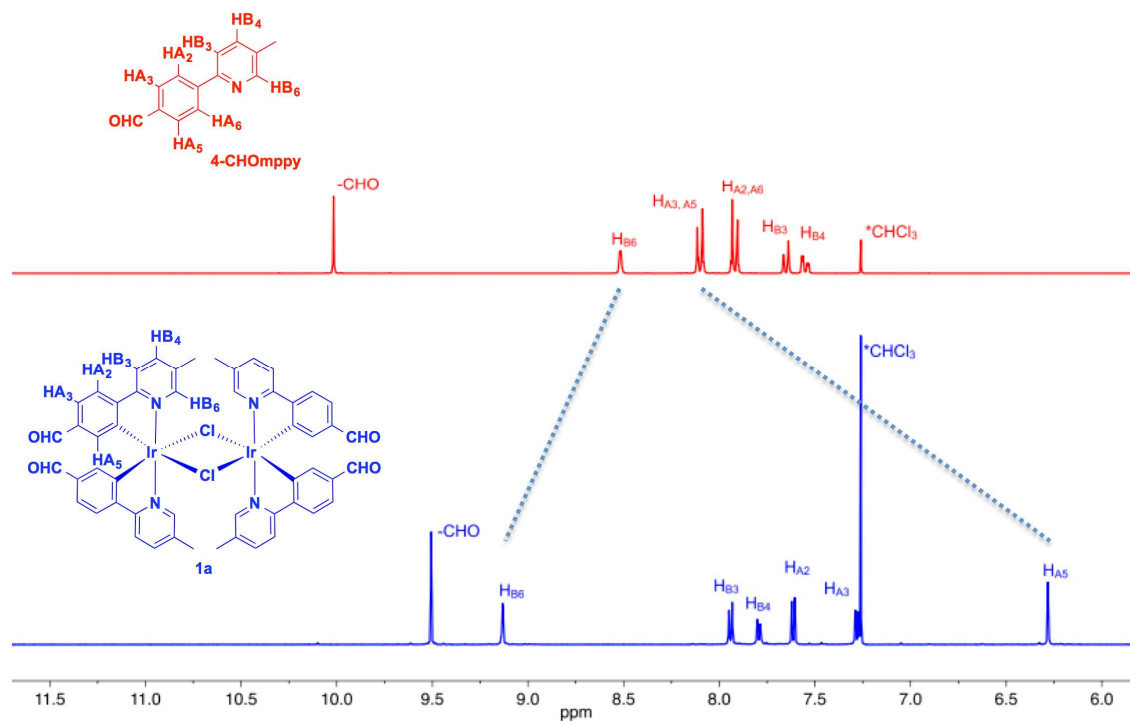


Figure 1. Stacked ^1H NMR spectra of aromatic region **4-CHOmpy** (red) and complex **1a** in CDCl_3 at 298 K.

Figure 1 shows the aromatic region of the ^1H NMR spectra for **1a** and **4-CHOmpy** (for corresponding comparison of ^1H NMR for **1b**, **2a** and **2b** with their respective C $^{\wedge}$ N ligands see Figures S19-S22, electronic supporting information, ESI). Eight well-resolved resonances are observed in the ^1H NMR of **1a** in CDCl_3 , the result of chemical non-equivalence of the $\text{H}_{3\text{A}}/\text{H}_{5\text{A}}$ protons upon cyclometalation. Structural assignments are based on 2D-COSY NMR experiments and a comparison of our 1D NMR data with those previously reported by Watts and co-workers, and more recently Schubert and co-workers.^{5c,14} The resonance for $\text{H}_{\text{A}5}$ at δ 6.16 is significantly shifted upfield due to the formal anionic charge of the cyclometalating phenyl ring.^{5a,15} By

contrast, H_{B6} is shifted downfield at δ 9.07 upon complexation.^{5c} The regiochemistry of cyclometalation in **1b** and **2b** can be simply determined from the presence of H_{A2} , which has a characteristic chemical shift at ca. δ 6 and a coupling constant of ca. 8 Hz. Thus, the formyl groups on the phenyl ring in these two complexes are located exclusively *para* to the iridium metal. The pattern of signals in the 1H NMR and the presence of only thirteen ^{13}C NMR resonances also points to a single configuration coordination mode for the four complexes, with the arrangement of the nitrogen atoms of the pyridine moieties *trans* with respect to each other, as is typical under the reaction conditions. Though the synthesis is not stereoselective and statistical mixtures of $\Delta\Delta$, $\Lambda\Lambda$ and $\Delta\Lambda$ diastereomers should exist in solution, by 1H NMR only a single set of resonances exists. Single crystal X-ray diffraction results reveal only the presence of only a racemic mixture of $\Delta\Delta$ and $\Lambda\Lambda$ isomers. (*vide infra*).

The MALDI HRMS show low intensity molecular ions for all four complexes. In all four mass spectra, a fragmentation peak with a mass-to-charge ratio (m/z) half that of the molecular ion is always observed, which resulted from homo-cleavage of the molecular ion under MS conditions. Similar observations have been reported in the literature.¹⁶

Solid-state characterization

All crystals were grown by vapour diffusion of diethyl ether into saturated DCM solution of the complexes. The connectivity of bonds provides an absolute proof of

structure. All four complexes adopt similar dinuclear structures (Figure 2) with compounds **1a**, **1b**, and **2b** crystallising in the monoclinic space group $P2_1/c$, in unit cells of broadly similar sizes, and one molecule of complex in the asymmetric unit, while compound **2a** crystallises in the space group $P2_1/n$, but with a unit cell of close to twice the size, and two molecules of complex in the asymmetric unit. The complexes adopt a slightly distorted octahedral coordination environment about the iridium(III) centres, with Ir–N *trans* to each other and Ir–C *cis*, in common with other examples of $[\text{Ir}(\text{C}^{\wedge}\text{N})_2\text{Cl}]_2$ complexes.^{5c,6,15-17} While this arrangement can be readily deduced in the cases of complexes **1a**, **1b**, and **2b**, for complex **2a**, comparison of potential Ir–C/N distances, as well as the ^1H NMR data, confirm the *trans*-N arrangement. Bond parameters about the iridium(III) are unexceptional (Figure 2), as are the Ir⋯Ir separations [3.7867(9) to 3.8068(19) Å]. In an analogous manner to related complexes, all four complexes display racemic $\Delta\Delta$ and $\Lambda\Lambda$ diastereomers, rather than the meso $\Delta\Lambda$ form. All four structures showed space open to solvent within them. In **1a** and **2a** this could be modelled as either one (disordered) or two molecules of CH_2Cl_2 per complex, respectively, with no void space remaining. In **1b** and **2b** however, no solvent molecules could be sensibly modelled, resulting in large void spaces. In **1b**, these run along the *a*-axis whereas in **2b**, channels are narrow and do not run straight along a single axis; additional thin void spaces can be seen in the *ac*-plane.

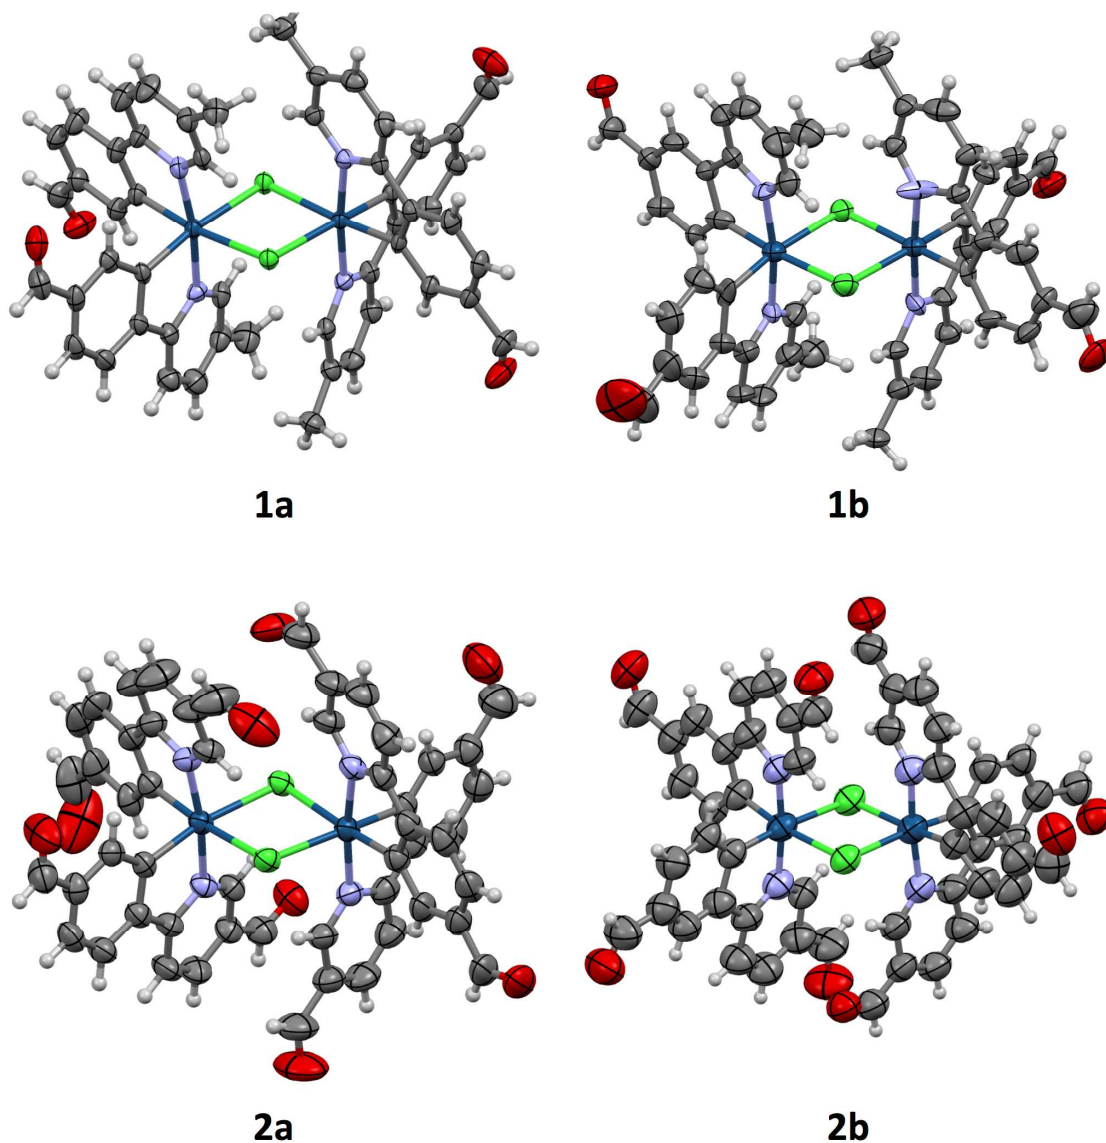


Figure 2. Crystal structures of complexes **1a-2b**, with solvent molecules omitted. Thermal ellipsoids are drawn at the 50 % probability level for **1a**, **1b**, and **2a**, and at the 30 % probability level for **2b**. Bond lengths in Å: **1a** Ir-C [1.989(9)-2.00(1)]; Ir-N [2.035(7)-2.059(7)]; Ir-Cl [2.494(2)-2.529(2)]; **1b** Ir-C [1.99(2)-2.04(2)]; Ir-N [2.01(2)-2.06(2)]; Ir-Cl [2.498(6)-2.536(6)]; **2a** Ir-C [1.988(6)-2.023(7)]; Ir-N [2.035(5)-2.058(5)]; Ir-Cl [2.510(2)-2.527(2)]; **2b** Ir-C [1.87(2)-1.92(2)]; Ir-N [1.95(2)-2.00(2)]; Ir-Cl [2.491(7)-2.542(6)]. Bond angles in degrees: **1a** N-Ir-C [80.2(3)-81.2(3)] Cl-Ir-Cl

[81.34(7)-81.43(7)]; **1b** N-Ir-C [81.5(2)-83.1(8)] Cl-Ir-Cl [81.5(2)-81.6(2)]; **2a** N-Ir-C [79.9(2)-80.8(2)] Cl-Ir-Cl [81.83(5)-82.13(5)]; **2b** N-Ir-C [80.8(9)-83.1(9)] Cl-Ir-Cl [81.4(2)-82.2(2)].

Various interactions are seen to be common to the four complexes, both intramolecular, for maintaining the molecular geometries seen, and intermolecular, for providing stabilising interactions between molecules. Intermolecular interactions can be seen as weak C-H \cdots Cl hydrogen bonds that are present between the CH(α) to the nitrogen atom of the pyridyl rings of the C^N ligands and the bridging chlorides of the complexes [H \cdots Cl distances ranging from 2.50 to 2.70 Å, with C \cdots Cl separations of 3.311(8) to 3.35(2) Å]. These hydrogen bonds are complemented, in all cases except **2b**, by C-H \cdots π interactions between a proximal CH of a phenyl ring, and the π -system of the pyridyl of an adjacent ligand; H \cdots centroid distances ranging from 2.93 to 2.94 Å, with C \cdots centroid separations of 3.72(3) to 3.725(7) Å (Figure 3).

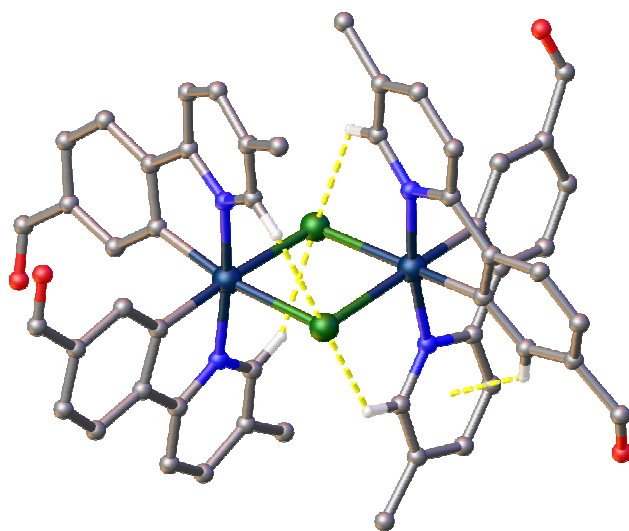


Figure 3. View of complex **1a** showing the intramolecular interactions present in the complexes. Interactions shown as dashed yellow lines, hydrogen atoms not involved in the interactions were omitted.

Common intermolecular interactions in the complexes include both interactions between the complexes and solvent, for those where the solvent could be resolved within the structure, and between adjacent complex molecules. Complex-to-solvent interactions consist of both C–H \cdots π and weak C–H \cdots Cl hydrogen bonds, the latter involving aryl hydrogens. Interactions between complexes follow a similar pattern. A few C–H \cdots π interactions are observed, although at sufficient interatomic distances [H \cdots centroid 2.73 – 2.93 Å, C \cdots centroid 3.650(7) – 3.874(10) Å] to be relatively unimportant if taken by themselves. They are reinforced, however, by sets of weak C–H \cdots O hydrogen bonds, involving both aryl and (where they exist as in **1a** and **1b**) alkyl hydrogens, at H \cdots O distances of 2.19 to 2.59 Å, and C \cdots O separations of 2.999(15) to 3.542(13) Å.

As well as these sets of conserved interactions, there are some intermolecular interactions that occur in some, but not all, of these complexes. Complexes **1a**, **1b**, and **2b** show further interaction involving their bridging chlorides. These are C–H \cdots Cl hydrogen bonds involve the formyl protons of adjacent complexes. The H \cdots Cl distances range from 2.51 to 2.82 Å, with corresponding C \cdots O separations of 3.32(4) to 3.70(3) Å. An additional feature of the interactions in these three complexes is that none of them show $\pi\cdots\pi$ interactions (no centroid \cdots centroid distances of less than 3.91 Å is present). Complex **2a**, on the other hand shows quite different interactions to these (Figure 4). The first of these is a π -stacking interaction between proximal phenyl rings of the two

molecules in the asymmetric unit. The centroid \cdots centroid distance is 3.767(4) Å, with an inclination between ring-planes of 0.2(4)°. This interaction is reinforced by one of the C–H \cdots π interactions mentioned earlier, between a hydrogen on one of the π -stacking rings, and another ring centroid on the adjacent complex. The second set of different interactions concerns weak hydrogen bonds involving the formyl protons. Unlike in the other three complexes, in **2a** these do not interact with the bridging chloride atoms, but form an extensive network of C–H \cdots O interactions with other formyl groups (Figure 4). The H \cdots O distances in these interactions vary between 2.30 and 2.52 Å, with C \cdots O separations of 3.102(14) to 3.346(13) Å. From the interatomic distances in these interactions it may be deduced that the molecules of complex in **2a** are held together more tightly in the solid state, and interact more strongly than those in the other complexes.

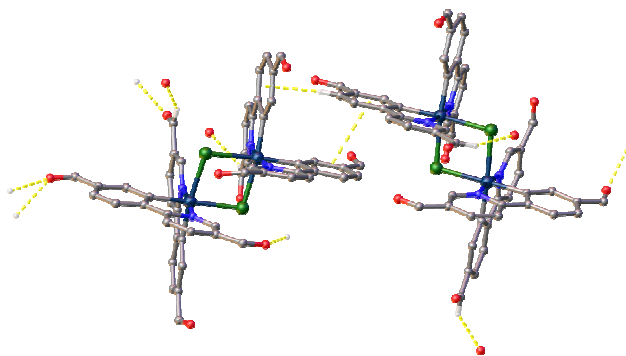


Figure 4. View of complex **2a** showing the intermolecular interactions observed in this complex but not the others. Interactions shown as dashed yellow lines, hydrogen atoms not involved in the interactions were omitted.

Electrochemical properties.

The electrochemical properties of **1a-2b** were studied in nitrogen-saturated DCM at room temperature using $n\text{NBu}_4\text{PF}_6$ as the supporting electrolyte and using Fc/Fc^+ as an internal standard. All potentials are referenced to SCE ($\text{Fc}/\text{Fc}^+ = 0.46 \text{ V}$ in DCM).¹⁸ The results are compiled in Table 1 while CV traces are shown in Figure 5. The CV behavior was reproducible across a range of scan rates ranging from 50 to 1000 $\text{mV}\cdot\text{s}^{-1}$ though at higher scan rates the redox waves broadened, rendering analysis more difficult. All complexes in this study showed essentially quasi-irreversible or irreversible electrochemistry as $i_{\text{pa}}/i_{\text{pc}} \ll 1$.

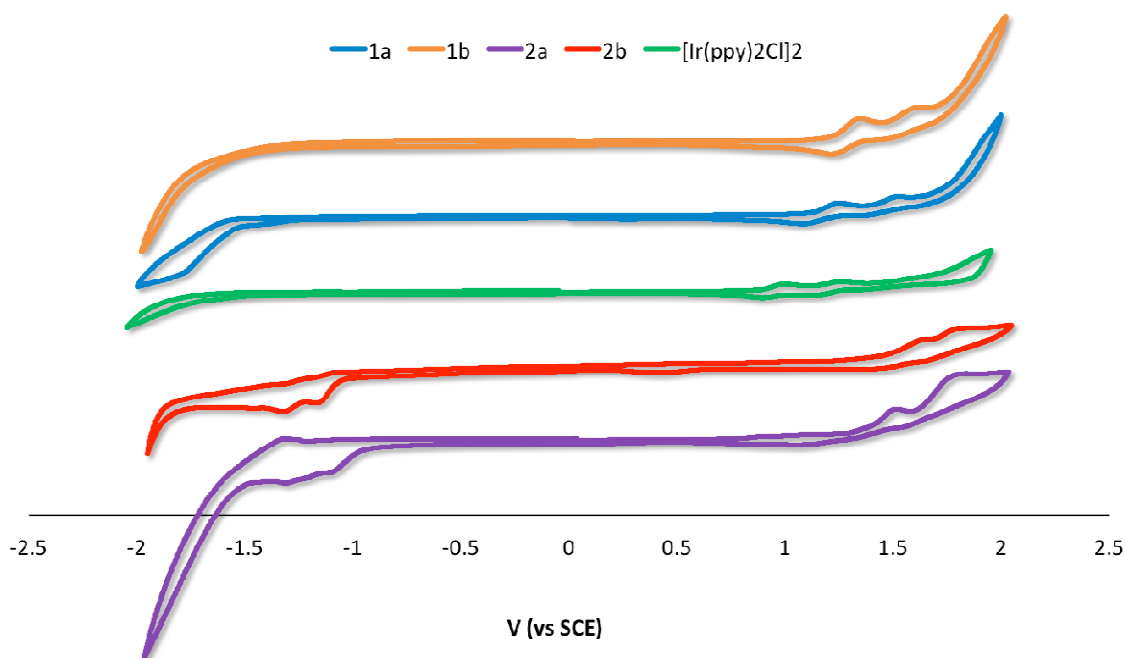


Figure 5. CV traces for **1a-2b** and $[\text{Ir}(\text{ppy})_2\text{Cl}]_2$ recorded at 298 K at $50 \text{ mV}\cdot\text{s}^{-1}$ in deaerated DCM with 0.1 M $(n\text{Bu}_4\text{N})\text{PF}_6$.

Table 1. Electrochemical data of **1a-2b** and $[\text{Ir}(\text{ppy})_2\text{Cl}]_2$.^{a,b}

Complex	$E_{\text{pa},1}^{\text{ox}}$	$E_{\text{pa},2}^{\text{ox}}$	$E_{\text{pc},1}^{\text{red}}$	$E_{\text{pc},2}^{\text{red}}$	ΔE_{redox}	E_{HOMO}	E_{LUMO}	ΔE
	V	V	V	V	V	eV	eV	eV
$[\text{Ir}(\text{ppy})_2\text{Cl}]_2$	1.00	1.26				-5.34	-2.85	2.49
1a	1.25	1.51				-5.59	-3.21 ^c	2.38
1b	1.35	1.61				-5.69	-3.11 ^c	2.58
2a	1.46	1.67	-1.10	-1.30	2.56	-5.80	-3.24	2.56
2b	1.58	1.72	-1.16	-1.31	2.74	-5.92	-3.18	2.74

^a Conditions: CV traces recorded in N_2 -saturated DCM solution with complex concentration at 10^{-4} M with 0.1 M $n\text{Bu}_4\text{NPF}_6$ at 298 K; Platinum wires were used as the working and counter electrodes, respectively while an Ag/AgCl reference electrode was employed; Scan rate: 50mVs^{-1} . Values are in V vs. SCE (Fc/Fc⁺ vs. SCE = 0.46 V).¹⁸ $\Delta E = -(E_{\text{HOMO}} - E_{\text{LUMO}})$; E_{pa} = anodic peak potential and E_{pc} = cathodic peak potential. ^b The HOMO and LUMO energies were calculated using the relation $E_{\text{HOMO/LUMO}} = -(E_{\text{pa},1}^{\text{ox}} / E_{\text{pc},1}^{\text{red}} + 4.8)$ eV, where $E_{\text{pa},1}^{\text{ox}} / E_{\text{pc},1}^{\text{red}}$ are the first oxidation or reduction peaks with respect to $E_{1/2}$ of ferrocene/ferrocenium redox couple. ^c E_{LUMO} was estimated from optical band gap, $E_{0,0}$ determined from the low energy tail at 10% intensity of the lowest energy absorption band.

The parent dimer $[\text{Ir}(\text{ppy})_2\text{Cl}]_2$ shows two one-electron oxidation waves at 1.00 and 1.26 V indicating that there is electronic communication between the two iridium centres mediated by the chloride bridges. The oxidations are assigned to the $\text{Ir}^{\text{III}}/\text{Ir}^{\text{IV}}$ redox couple with significant contribution from the aryl ring. No reduction is observed within the solvent window. This profile matches that originally reported by Watts and co-workers.^{5b} The introduction of an electron-withdrawing formyl group onto the phenyl moiety of the C[^]N ligand in **1a** and **1b** results in an expected shift to more positive potential of both oxidation waves, corresponding to a stabilization of the HOMO on each of the two iridium centers. Placement of the formyl group *para* to the Ir-C bonding

results in a 100 mV anodic shift of both oxidation waves in **1b** compared to **1a**. The additional of a second formyl group at the 5-position of the pyridine fragment of the C^N ligands make the first oxidation more difficult by 0.21 and 0.23 V for **2a** and **2b** versus **1a** and **1b**, respectively.

For **1a** and **1b** no reduction waves are observed. However, for **2a** and **2b** two irreversible reduction waves are now observed pointing to a LUMO involving the 5-formyl group. The LUMO is stabilized by a further 60 mV in **2a** compared to **2b**; the second reduction in both of these complexes occurs at ca. -1.31 V.

The band gaps ΔE for **2a** and **2b** were determined from the electrochemical data and are 2.56 and 2.74 eV, respectively. The band gaps for **1a** and **1b** at 2.38 and 2.58 eV, respectively, were extrapolated from the tailing edge at 10% intensity of the lowest energy absorption band, corresponding to the energy of the 0,0 transition. This method certainly underestimates this parameter by at least 0.65 eV as the HOMO to LUMO transition does not account for the binding energy associated with ionization.²⁰

UV-visible spectroscopy.

The UV-visible absorption spectra for **1a-2b** and $[\text{Ir}(\text{ppy})_2\text{Cl}]_2$ were recorded in aerated DCM at 298 K and are shown in Figure 6. The results are summarized in Table S1.

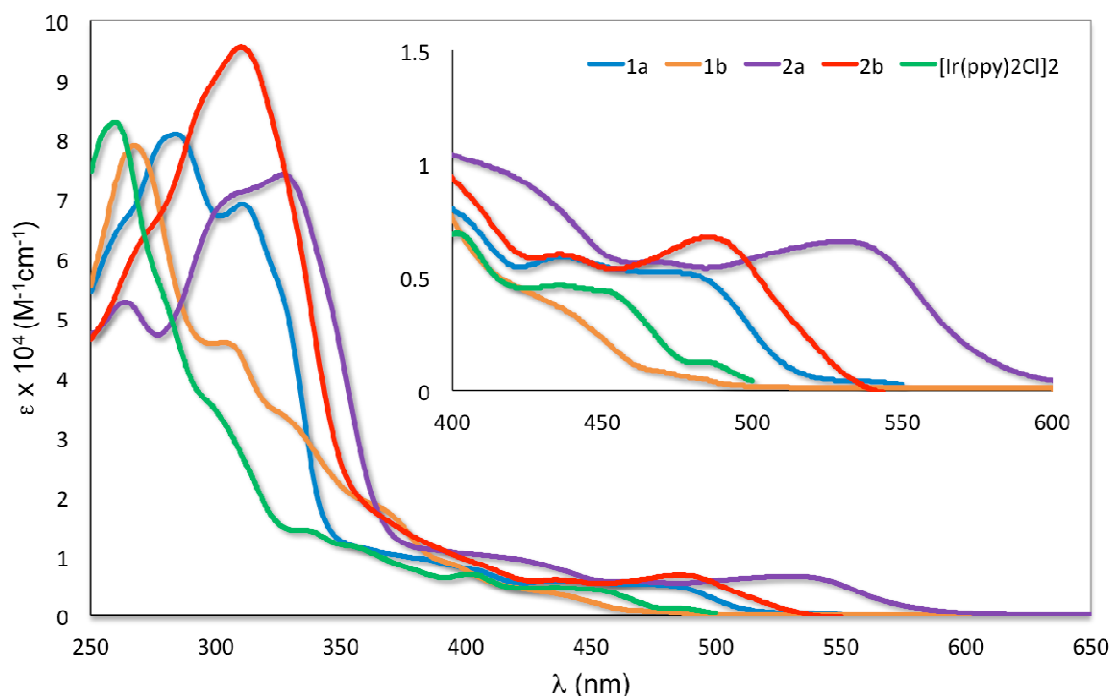


Figure 6. UV-visible absorption spectra of **1a-2b** and [Ir(ppy)₂Cl]₂ in DCM at 298 K.

Inset: zoomed UV-visible spectra for the region between 400-600 nm.

All the iridium dimers possess intense absorption bands below ca. 350 nm corresponding to spin-allowed singlet ligand-centered (¹LC) ¹ π - π^* transitions.^{6a} At lower energies, the absorption spectra are dominated by spin-allowed metal-to-ligand charge transfer (¹MLCT) and intraligand charge transfer (¹ILCT) transitions,^{5a,5b,18} spin forbidden ³MLCT transitions are certainly also present at low energies due to the large spin-orbit coupling mediated by Ir. Similar to other homodinuclear iridium complexes,²¹ the molar absorptivities of these complexes are approximately double than those of neutral mononuclear iridium complexes such as [Ir(ppy)₂(pic)] (pic = picolinate).²²

The absorption profile for **1a** and **1b** are similar, with **1a** being bathochromically shifted compared to **1b** and $[\text{Ir}(\text{ppy})_2\text{Cl}]_2$. This red-shift in **1a** is caused by the electron-withdrawing 4-formyl group, which results in a stabilisation of both the occupied π and the unoccupied π^* orbital of the C^N ligands and a smaller energy transition.²³ This red-shifting of the absorption spectrum is not observed in **1b**, with its HOMO-LUMO band blue-shifted compared to $[\text{Ir}(\text{ppy})_2\text{Cl}]_2$. The change in regiochemistry of the formyl group on the phenyl fragment results in cross-conjugation with the pyridine moiety and a reduced influence on the energies of the antibonding orbitals. Additionally, the HOMO stabilising character of the 3-formyl group is more pronounced, as it is now *para* to the Ir-C bond. Similarly, the absorption of **2a** is bathochromically shifted with respect to **2b**. The magnitude of this red-shift is unexpected, particularly given the similar ¹MLCT absorption maxima reported by Bryce, Monkman and co-workers for a series of fluorenyl-containing iridium dimer complexes bearing 5-fluoro- or 5-methoxy-substituted pyridine moieties on the C^N ligands.^{6b} The greater red-shifting of the absorption spectra for **2a** and **2b** compared to **1a** and **1b** results from the presence of the second formyl group, which further stabilises the LUMO that contains significant electron density on the pyridine ring of the ligand.

Emission spectroscopy.

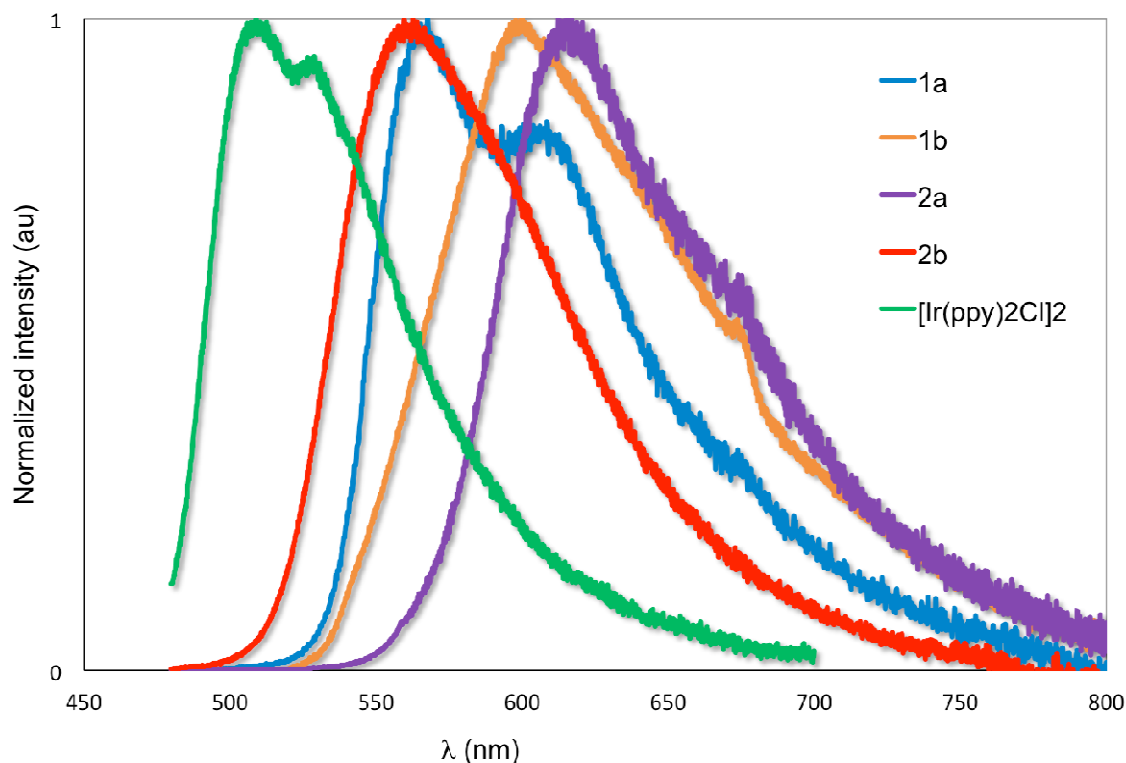


Figure 7. Normalized emission spectra of **1a-2b** and $[\text{Ir}(\text{ppy})_2\text{Cl}]_2$ in deaerated DCM at 298 K. λ_{exc} : 455 nm.

The emission properties of the five complexes were studied in degassed DCM at 298 K with the spectra shown in Figure 7 and the results summarized in Table 2. Their emission profiles are broad with the presence of either two well-defined emission bands or the presence of a low energy emission shoulder. The emission is assigned to a mixed $^3\text{MLCT}/^3\text{LC}$ transition.^{6a} The very weak emission of $[\text{Ir}(\text{ppy})_2\text{Cl}]_2$ at 520 nm reproduces that previously reported by Watts and co-workers.^{5c} The introduction of formyl groups causes a red-shift in the emission compared to the benchmark iridium dimer. The regiochemistry and quantity of the formyl groups have a dramatic impact on the photophysical properties of these complexes. Surprisingly, in **1a** the addition of the 4-formyl unit causes a red-shift of 1468 cm^{-1} and an accompanying order of magnitude

increase in Φ_{PL} to 2.5%. By contrast, incorporation of electron-withdrawing fluorine atoms onto the C^N ligands in both mononuclear neutral²⁴ and charged²⁵ complexes causes a blue-shift in the emission due to large stabilization of the HOMO. Positioning the formyl group *para* to the Ir-C in **1b** causes a further red-shift of 1095 cm⁻¹ compared to **1a**. Emission in **1b** is so weak as to preclude accurate determination of Φ_{PL} . The introduction of a second formyl group in **2b** causes a blue-shift in the emission compared to **1b**. Most striking, the emission for **2a** is not similarly blue-shifted compared to **1a** but is red-shifted by 1395 cm⁻¹ and is the brightest of the series of iridium dimers with a Φ_{PL} of 15.7%. Only recently reported fluorenyl annelated phenylpyridine C^N dichloro-bridged iridium dimers have shown brighter emission than **2a** for this class of complexes.^{6b} Its emission lifetime, τ_e , is also an order of magnitude longer than the other complexes at nearly 2 μs . The primary reason for this enhanced emission is due to the large decrease in the non-radiative rate constant, k_{nr} caused by increased rigidity conferred by the more extensive hydrogen bonding interactions (*vide supra*).

Table 2. Solution state photophysical data of **1a-2b** and $[\text{Ir}(\text{ppy})_2\text{Cl}]_2$.^a

Dimer Complex	λ_{em} (nm)	Φ_{PL} (%) ^b	τ_e (ns) ^c	k_r ($\times 10^5 \text{ s}^{-1}$) ^d	k_{nr} ($\times 10^5 \text{ s}^{-1}$) ^e
$[\text{Ir}(\text{ppy})_2\text{Cl}]_2$	520	0.1	125	0.40	79.60
1a	563, 600	2.5	206	1.21	47.33
1b ^f	600	Emission too weak			
2a	611, 670(sh)	15.7	1980	0.79	4.26
2b	556	0.9	601	0.15	16.49

^a Emission measured in N₂-saturated DCM at room temperature. ^b Relative to Ru(bpy)₃(PF₆)₂ ($\Phi_{\text{PL}} = 9.5\%$ in degassed MeCN)²⁶ ^c λ_{exc} : 470 nm. ^d Calculated from $\Phi_{\text{PL}} = \tau_e \times k_r$. ^e Calculated from $\Phi = k_r / (k_r + k_{\text{nr}})$. ^f Emission too weak to determine Φ_{PL} or τ_e .

Table 3. Solid-state photophysical data of **1a-2b**

Dimer Complex	$\lambda_{\text{PL}}(\text{nm})^a$	$\Phi_{\text{PL}}(\%)^b$	$\Phi_{\text{PL}}(\%)^c$
1a	562	1.0	10.3
1b^d	-	-	-
2a	620	1.1	14.7
2b	555	2.6	35.6

^a PL measurements of blended films of CBP:PBD:complexes (60:30:10 wt%) in a 60 nm thick film. ^b Φ_{PL} of neat films spin-coated onto a fused silica substrate from DCM solution. ^c Φ_{PL} of blended films of CBP:PBD:dimer complex (60:30:10 wt.%) on a fused silica substrate. CBP is 4,4'-N,N'-dicarbazole-biphenyl and PBD is 2-(*tert*-butylphenyl)-5-biphenyl-1,3,4-oxadiazole. ^d Data not available due to weak emission.

In order to better understand the photophysics of the materials and their potential for OLEDs, the photoluminescence quantum yield of the solid films was measured. Neat films were studied and compared with films in which the test complex was blended with charge transporting materials. The latter films are generally preferable for OLEDs because diluting the chromophore usually reduces concentration quenching, and because the host materials can facilitate charge transport. The films were prepared by spin-coating the materials from DCM solution onto fused silica substrates, and the results are shown in Table 3. As with solution-state measurements, **1b** has minimal emission in the solid state. The other materials show much higher photoluminescence quantum yield in the blend than in the neat film. Whereas **2a** was found to show the highest photoluminescence quantum yield in DCM, the brightest complex in the solid state is **2b**, with a Φ_{PL} in the doped film of 36%, more than double that of **2a**. The emission maxima found in the doped films match those observed in dilute DCM solution.

Theoretical Calculations.

The geometries and electronic structures of complexes **1a** and **2a**, as representative examples of the series, were modelled within Gaussian 09²⁷ using density functional theory (DFT) and time-dependent DFT (TDDFT).²⁸ These complexes were modelled using the B3LYP²⁹ level of theory with the SBKJC-DVZ³⁰ basis set for iridium, 6-31G* for heavy atoms directly coordinated to iridium and 3-21G* for all other atoms^{30a,31} in the presence of the solvent DCM.³² This methodology has been successfully used by us for other dinuclear iridium complexes.³³ The calculated ground-state geometries well reproduce those found in the crystal structures with the exception of the Ir-Cl bonds, is ca. 0.1 Å longer than the experimental value. The resulting Ir...Ir distance of 3.95 Å is thus also overestimated.

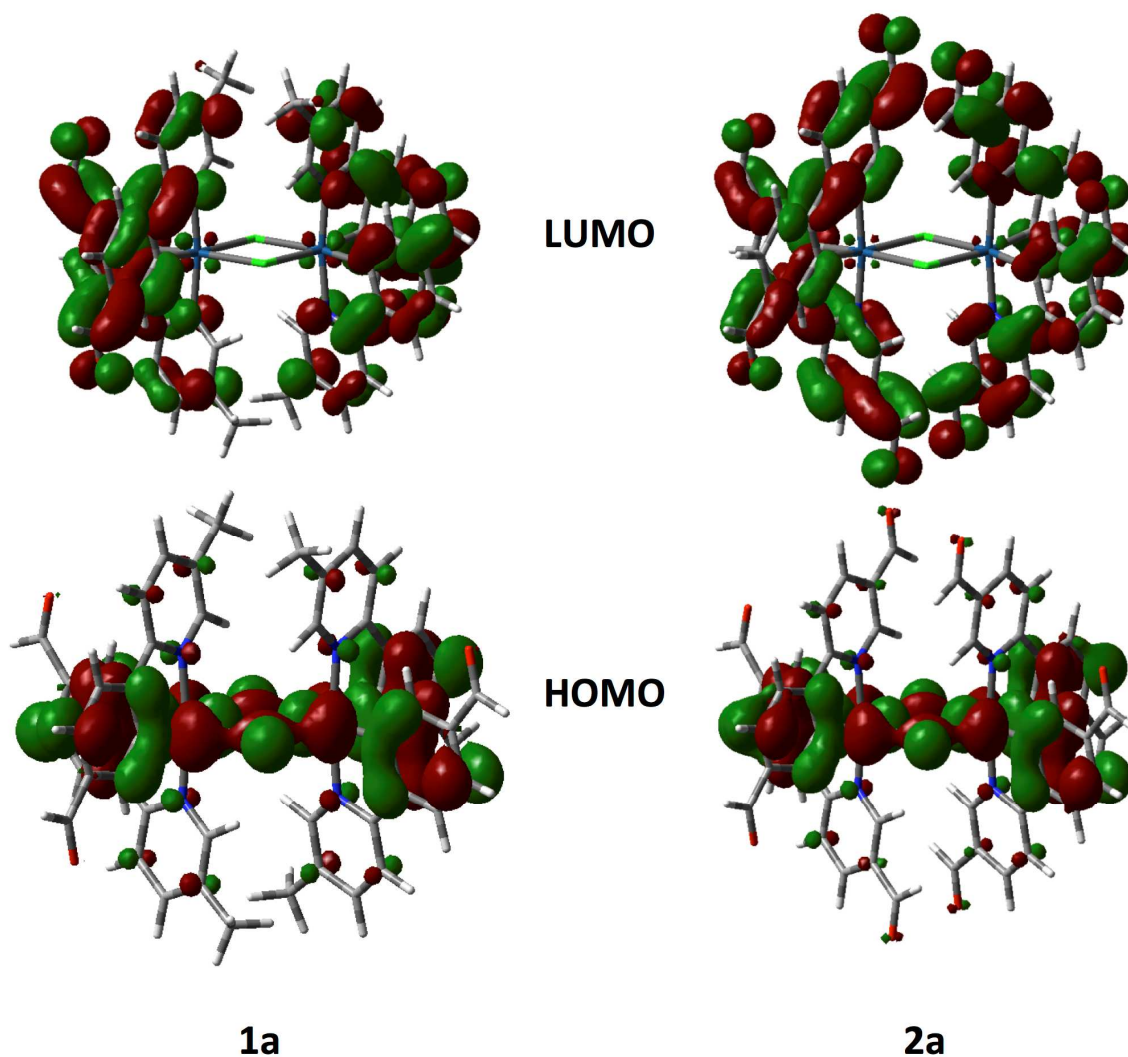


Figure 8. HOMO and LUMO orbitals of **1a** and **2a**, Electron density contour plots at $0.002 \text{ e bohr}^{-3}$.

The frontier molecular orbitals for **1a** and **2b** are shown in Figure 8. The calculated HOMO and LUMO energies for **1a** are, respectively, -5.59 and -2.20 eV while for **2a** they are -5.90 and -2.90 eV, respectively. Calculated HOMO energies agree very well with CV data in Table 1 while LUMO levels are not well reproduced. The poor prediction for **1a** is most likely a function of the underestimation based on extrapolation of the LUMO level from absorption data. In **2a**, the calculated LUMO is 0.34 eV higher

than that obtained from the electrochemical measurement. In both complexes the HOMO is distributed across the iridium dimer with electron density on the iridium metal centers, the phenyl rings of the cyclometalating ligands and the chlorine bridge. This picture, pointing to electronic communication between the two iridium atoms, agrees well with the CV traces, which show two distinct oxidation waves, one at each iridium center. The LUMO is distributed across all of the cyclometalating ligands. In **2a** electron density extends out to the formyl groups on the pyridine rings, which corroborates the assignment of the irreversible reduction in **2a** as being localized on this fragment of the complex. The topologies for HOMO-1 and LUMO+1 are nearly identical to those of HOMO and LUMO, respectively.

The predicted absorption data (Figures **S27** and **S28**) obtained by TDDFT reproduce very well the gross features of the absorption spectra, including the low energy band at 540 nm observed in **2a**. The calculated S_0 to T_1 transition obtained from TDDFT based on the S_0 optimized geometries for **1a** and **2a** are 516 and 570 nm fit well with the very weak 3CT transitions observed in the absorption spectra.

Electroluminescence Performances.

In order to investigate the electrical and optical properties of the OLEDs based on these four iridium dimer complexes, we tested each of them in a device structure which was ITO/PEDOT:PSS(30 nm)/PVK(30 nm)/CBP:PBD:dimer complex (60:30:10, 60 nm)/B3PYMPM(40 nm)/Ca(20 nm)/Al(100 nm). PEDOT:PSS, PVK and B3PYMPM

denote poly(3,4-ethylenedioxythiophene): poly(styrenesulfonate), poly(*N*-vinylcarbazole) and bis-4,6-(3,5-di-3-pyridylphenyl)-2-methylpyrimidine, respectively. PVK facilitates hole injection because its HOMO (5.6 eV)³⁴ lies between that of ITO and the co-host materials (6.0 eV). The LUMO of PVK (2.2 eV) is slightly higher than those of CBP (2.6 eV)³⁵ and PBD (2.3 eV) and its wide energy gap should confine excitons inside the emitting layer thus improving capture of opposite charges in the device.³⁴⁻³⁵ The electron-transporting layer B3PYMPM blocks the hole from penetration into the cathode due to its deep-lying HOMO (6.8 eV) and reduces the leakage current.³⁶ Hence, the multi-layer helps to confine excitons inside the emitting layer as is needed for good luminous efficacy.

Figure 9 shows the current-voltage characteristics of the devices. The devices with complexes **2a** and **2b** exhibited lower current density at high voltage (> 7V) than the devices made from **1a** and **1b**. The device based on **1b** exhibited the highest current density above 7 V. However, its luminance saturated at higher driving voltage. The devices based on complex **2b** possessed the lowest current density above 7 V. However the luminance of this device goes up very steadily once turned on. A high luminance, up to 5930 cd/m² can be achieved at a driving voltage of 14.6 V. Therefore, among the four complexes, much higher luminous efficiencies can be seen from this device, i.e. 9.1 cd/A, 2.2 lm/W and 2.6% of current efficiency (CE), power efficiency (PE) and external quantum efficiency (EQE), respectively (Figures 10a, 10b, and 10c, respectively). In contrast, the poorer efficiencies of the devices with **1a** and **1b** may be due to incomplete host to guest energy transfer (**1a**) and exciplex emission (**1b**), which can be inferred from

the EL spectra in Figure **11a** and **11c**. The EL spectra from the complexes **2a** and **2b**, were nearly independent of the current density, indicating very efficient host to guest energy transfer and nearly no exciplex contribution (Figure **11b** and **11d**). A comparison of the electrical and optical properties is listed in Table 4.

There is a correlation between the EQE of our devices and solid-state photoluminescence quantum yield (Table 3). The material with the highest Φ_{PL} (**2b**) also produces the OLED with the highest EQE. The complex with the lowest EQE (**1b**) results from its very poor emission with the lowest Φ_{PL} among the four materials. The other two materials (**1a**, **2a**) have intermediate photoluminescence and electroluminescence efficiencies. Of these two materials, **2a** has higher Φ_{PL} but lower external quantum efficiency in the OLED, suggesting that there is a difference in charge balance between the devices.³⁷ We observe EL from **1b** even though its PL is very weak. However, the spectrum of the EL (Figure **11c**), suggests it is due to the formation of an exciplex between CBP and B3PYMPM.

In the recent report by Bryce and Monkman on the use of dichloro-bridged iridium dimers as emitters in OLEDs, the devices [structure: ITO/PEDOT:PSS/PVK–PBD (40%)–complex (5%)/Ba/Al] achieved peak EQEs ranging from 0.6-4% with PE ranging from 0.40-3.53 lm/W and CE of 1.7-12 cd/A based on complexes that showed Φ_{PL} of 21-41% in chlorobenzene solution.^{6b} From Table 5, we can see that **2b** exhibits

the best performance of the series and shows comparable metrics to the best dichloro-bridged iridium complex reported by Bryce and Monkman.

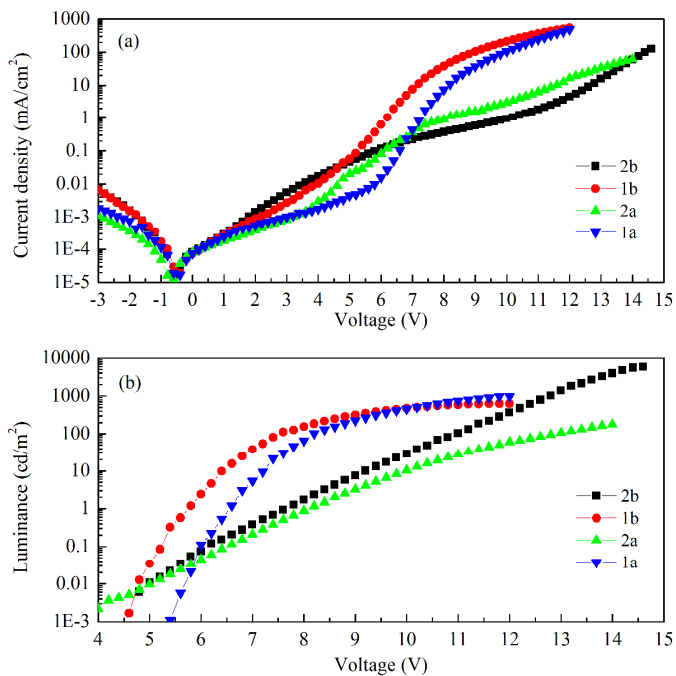


Figure 9. (a) Current density and (b) luminance vs voltage characteristics of the devices

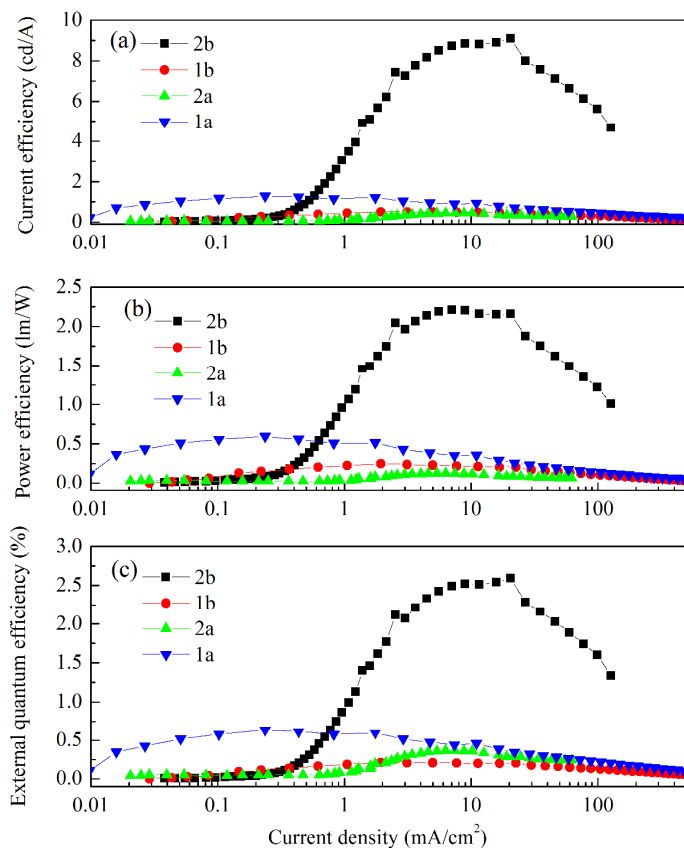


Figure 10. (a) Current efficiency, (b) power efficiency and (c) external quantum efficiency vs current density characteristics of the devices.

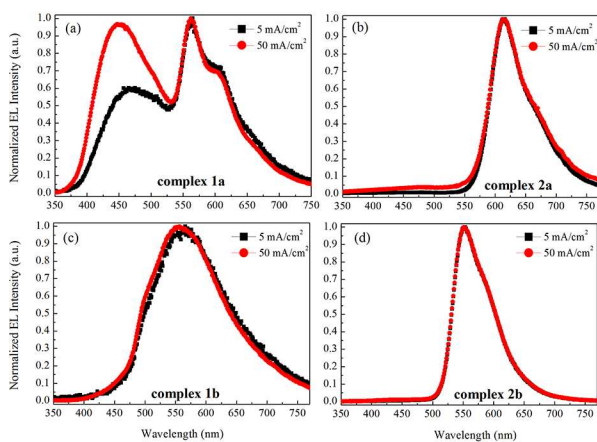


Figure 11. The normalized EL spectra of the devices with the emitters **1a** (a), **2a** (b), **1b** (c) and **2b** (d) at current densities of 5 and 50 mA/cm^2 .

Table 4. Comparison of the EL performance of the devices.^a

	Voltage at 1 cd/m ² (V)	Max. Luminance (cd/m ²)	Max. CE (cd/A)	Max. PE (lm/W)	Max. EQE (%)	λ_{em} (nm)	CIE at 50 mA/cm ²
1a	6.5	982	1.29	0.59	0.64 @ 3 cd/m ²	447, 562	(0.3074, 0.3097)
1b	5.7	630	0.51	0.25	0.21 @ 10 cd/m ²	612	(0.4073, 0.4966)
2a	8.1	178	0.44	0.13	0.37 @ 28 cd/m ²	557	(0.5991, 0.3600)
2b	7.7	>6000	9.09	2.16	2.59 @ 1860 cd/m ²	551	(0.4413, 0.5420)

^a CE = Current efficiency. PE = Power efficiency. EQE = External quantum efficiency. CIE = The Commission Internationale de l'Eclairage coordinates.

Conclusions

In this work, the systematic synthesis, structural and optoelectronic characterization, and electroluminescent device data of a series of four dichloro-bridged iridium dimers with formyl-substituted 2-phenylpyridine C^N ligands were presented. The optoelectronic properties were found to be strongly affected by the number of formyl groups and their regiochemistry. In particular, complex **2a** showed a remarkable photoluminescence quantum yield of 15.7% in DCM solution despite being the reddest emitting complex in the series. In the solid state, be it in a pristine thin film or as a dopant, complex **2b** was found to be the brightest. Of the electroluminescent devices fabricated using these iridium dimers, only the OLED employing **2b** as the emissive dopant gave reasonable device performance, with an EQE of 2.6%.

Experimental Section

General Synthetic Procedures. All the chemicals and reagent grade solvents were purchased and used as received. Pd(PPh₃)₄ was synthesized according to the literature.³⁸ All reactions were performed under a nitrogen atmosphere using Schlenk techniques. Flash column chromatography was carried out using silica gel (Silia-P from Silicycle, 60Å, 40-63µm). Analytical thin-layer-chromatography (TLC) was performed with silica plates with aluminum backings (250 µm with F-254 indicator). TLC visualization was accomplished by 254/365 nm UV lamp. ¹H and ¹³C NMR spectra were recorded on a Bruker Avance spectrometer at 500 MHz and 126 MHz, respectively. For multiplicity assignment in NMR spectra reporting, “s” stands for singlet, “d” for doublet, “t” for triplet, “m” for multiplet and “br” for broad peaks. Deuterated chloroform and methylene chloride were used for NMR spectra recording. Melting points (Mp) were measured using open-ended capillaries on an Electrothermal melting point apparatus and are uncorrected. High-resolution mass spectrometry (HRMS) was performed by EPSRC National Mass Spectrometry Service Centre (NMSSC), Swansea. Gas chromatography-mass spectrometry (GC-MS) was recorded on Hewlett Packward HP6890 series GC system tandem with 5973 Mass Selective Detector.

Ligand Syntheses.

2-bromo-5-formylpyridine: The synthesis was adapted from methods previously reported.³⁸⁻³⁹ Thus, to a suspension of 2,5-dibromopyridine (5.0 g, 21.1 mmol, 1 equiv.) in diethyl ether (50 mL) at -78 °C was added dropwise 1.6M *n*-butyllithium in hexanes (16 mL, 25.6 mmol, 1.2 equiv.). The reaction mixture was allowed to stir for 30 minutes at this temperature and a dark crimson suspension was observed. Dry DMF (6 mL, 77.8

mmol, 3.5 equiv.) was added and the reaction mixture was allowed to warm to room temperature and stirred for a further 30 minutes. The reaction mixture was then poured into 10% HCl (80 mL) and allowed to stir for 30 minutes. The mixture was then made mildly basic (ca. pH = 9.5) with sat. NaHCO₃ (aq). The mixture was extracted with DCM (3 x 50 mL). The combined organic layer was dried with anhydrous Na₂SO₄ and concentrated under reduced pressure. The crude at this stage contained largely pure product according to TLC. Recrystallization from DCM/hexanes afforded the title compound.

Light tan solid. **Yield:** 63%. **R_f:** 0.41 (EtOAc : Hexanes = 1:3 on silica). **Mp:** 100-101 °C (Lit. 100-101 °C). ⁴⁰ **¹H NMR (300 MHz, CDCl₃) δ (ppm):** 10.09 (s, 1 H), 8.82 (dd, *J* = 2.4, 0.7 Hz, 1 H), 8.02 (dd, *J* = 8.2, 2.4 Hz, 1 H), 7.68 (dt, *J* = 8.2, 0.7 Hz, 1 H). **¹³C NMR (76 MHz, CDCl₃) δ (ppm):** 189.8, 152.9, 148.7, 137.9, 131.0, 129.4. **GC-MS:** 13.2 min, *m/z*: 185 (M), 184 (M-H), 156 (M-CHO).

General procedure for Suzuki-Miyaura cross-coupling. The appropriate 2-bromopyridine (1.0 equiv.) and arylboronic acid (1.1 equiv.), sodium carbonate (3.3 equiv.) and tetrakis(triphenylphosphine)palladium(0) (5 mol%) were mixed in dioxane/water (4:1 v/v, 30mL per 1g bromopyridine). The mixture was degassed by freeze-pump-thaw for three cycles. It was then allowed to heat under N₂ at 90 °C for 8 h. The mixture was cooled to room temperature and extracted with DCM 3x. The combined organic phase was dried with anhydrous Na₂SO₄ and concentrated under reduced pressure. The residue was

purified by flash column chromatography (silica, Hexanes : EtOAc : Triethylamine = 80 :17 : 3) to offer the corresponding ligand.

2-(4-formylphenyl)-5-methylpyridine (4-CHOmpy): White solid. **Yield:** 92%. **R_f:** 0.32 (EtOAc : Hexanes = 1:3 on silica). **Mp:** 83-84 °C. **¹H NMR (300 MHz, CDCl₃) δ (ppm):** 10.02 (s, 1 H), 8.51-8.52 (m, 1 H), 8.10 (dt, *J* = 8.3, 1.6 Hz, 2 H), 7.92 (dt, *J* = 8.6, 1.7 Hz, 2 H), 7.65 (d, *J* = 7.6 Hz, 1 H), 7.55 (ddd, *J* = 8.1, 2.3, 0.7 Hz, 1 H), 2.35 (s, 3 H). **¹³C NMR (76 MHz, CDCl₃) δ (ppm):** 192.3, 153.5, 150.8, 145.3, 137.9, 136.5, 133.3, 130.5, 127.6, 121.0, 18.6. **HR-MS(ASAP): [M+H]⁺ Calculated: (C₁₃H₁₁NO) 198.0913; Found 198.0913.**

2-(4-formylphenyl)-5-formylpyridine (4-CHOfppy): White solid. **Yield:** 86%. **R_f:** 0.22 (EtOAc : Hexanes = 1:3 on silica). **Mp:** 158-159 °C. **¹H NMR (300 MHz, CDCl₃) δ (ppm):** 10.18 (s, 1 H), 10.12 (s, 1 H), 9.18 (dd, *J* = 2.2, 0.8 Hz, 1 H), 8.31-8.25 (m, 3 H), 8.05-8.02 (m, 2 H), 7.99 (dt, *J* = 8.2, 0.7 Hz, 1 H). **¹³C NMR (76 MHz, CDCl₃) δ (ppm):** 192.1, 190.6, 160.9, 152.7, 143.7, 137.7, 137.3, 130.9, 130.6, 128.6, 121.7. **HR-MS (ASAP): [M+H]⁺ Calculated: (C₁₃H₉NO₂) 212.0706; Found 212.0706.**

2-(3-formylphenyl)-5-methylpyridine (3-CHOmpy): Colorless oil. **Yield:** 91%. **R_f:** 0.35 (EtOAc : Hexanes = 1:3 on silica). **¹H NMR (300 MHz, CDCl₃) δ (ppm):** 10.10 (s, 1 H), 8.54-8.53 (m, 1 H), 8.47 (td, *J* = 1.7, 0.6 Hz, 1 H), 8.26 (ddd, *J* = 7.8, 1.9, 1.2 Hz, 1

H), 7.90 (dt, $J = 7.7, 1.4$ Hz, 1 H), 7.69 (dd, $J = 8.1, 0.9$ Hz, 1 H), 7.64-7.57 (m, 2 H), 2.38 (s, 3 H). ^{13}C NMR (76 MHz, CDCl_3) δ (ppm): 192.8, 153.6, 150.7, 140.6, 138.0, 137.3, 132.9, 129.9, 129.8, 128.6, 120.5, 18.6. HR-MS (ASAP): $[\text{M}+\text{H}]^+$ Calculated: ($\text{C}_{13}\text{H}_{11}\text{NO}$) 198.0913; Found 198.0913.

2-(3-formylphenyl)-5-formylpyridine (3-CHO f ppy): White solid. Yield: 87%. R_f : 0.23 (EtOAc : Hexanes = 1:3 on silica). Mp: 123-124 °C. ^1H NMR (300 MHz, CDCl_3) δ (ppm): 10.17 (s, 1 H), 10.14 (s, 1 H), 9.17 (dd, $J = 2.2, 0.9$ Hz, 1 H), 8.60 (td, $J = 1.9, 0.5, 1$ Hz), 8.39 (ddd, $J = 7.8, 2.0, 1.2$ Hz, 1 H), 8.29 (dd, $J = 8.3, 2.2$ Hz, 1 H), 8.03-7.98 (m, 2 H), 7.70 (t, $J = 8.4$ Hz, 1 H). ^{13}C NMR (76 MHz, CDCl_3) δ (ppm): 192.3, 190.7, 160.9, 152.8, 139.3, 137.4, 137.3, 133.6, 131.6, 130.7, 130.2, 129.2, 121.1. HR-MS (ASAP): $[\text{M}+\text{H}]^+$ Calculated: ($\text{C}_{13}\text{H}_9\text{NO}_2$) 212.0706; Found 212.0706.

General procedure for the synthesis of chloro-bridged iridium dimer complexes $[\text{Ir}(\text{C}^{\wedge}\text{N})_2\text{Cl}]_2$. Iridium trichloride trihydrate (1 equiv.) and the appropriate $\text{C}^{\wedge}\text{N}$ ligand (2.2 equiv.) were mixed in 2-alkoxyethanol/water ($v/v=3:1$, 8mL for 100mg $\text{IrCl}_3 \cdot \text{H}_2\text{O}$). 2-Ethoxyethanol was used for the *mppy* series while 2-methoxyethanol for the *fppy* series. The mixture was degassed via three freeze-pump-thaw cycles and was allowed to reflux for 18 h under N_2 . After cooling, the precipitate was filtered followed by washing with ethanol and acetone to afford the corresponding $[\text{Ir}(\text{C}^{\wedge}\text{N})_2\text{Cl}]_2$ complex.

Tetrakis[2-(4'-formylphenyl)-5-methylpyridine- C^2, N']-bis(μ -chloro)diiridium (III) $[\text{Ir}(\text{4-CHOmpy})_2\text{Cl}]_2$, 1a: Orange solid. Yield: 58%. R_f : 0.55 (DCM : EA = 1:1 on

silica). **Mp**: not observed below 400 °C. **¹H NMR (400 MHz, CD₂Cl₂) δ (ppm)**: 9.42 (s, 4 H), 9.07 (s, 4 H), 7.92 (d, *J* = 8.3 Hz, 4 H), 7.76 (dd, *J* = 8.4, 0.8 Hz, 4 H), 7.61 (d, *J* = 8.0 Hz, 4 H), 7.23 (dd, *J* = 8.0, 1.6 Hz, 4 H), 6.16 (d, *J* = 1.6 Hz, 4 H), 2.03 (s, 12 H). **¹³C NMR (100 MHz, CD₂Cl₂) δ (ppm)**: 192.2, 164.2, 151.9, 150.2, 143.7, 138.5, 135.7, 133.7, 131.6, 123.6, 122.9, 119.9, 18.5. **HR-MS (ESI): M⁺ Calculated: (C₅₂H₄₀Cl₂Ir₂N₄O₄) 1240.2; Found 1240.1.**

Tetrakis[2-(3'-formylphenyl)-5-methylpyridine-C²,N']-bis(μ-chloro)diiridium (III) [Ir(3-CHOmpy)₂Cl]₂, 1b: Yellow solid. **Yield**: 61%. **R_f**: 0.41 (DCM : EA = 1:1 on silica). **Mp**: 386 °C (decompose). **¹H NMR (400 MHz, CD₂Cl₂) δ (ppm)**: 9.81 (s, 4 H), 9.10 (dd, *J* = 1.4, 0.8 Hz, 4 H), 8.08 (d, *J* = 8.2 Hz, 4 H), 8.05 (d, *J* = 1.8 Hz, 4 H), 7.87 (ddd, *J* = 8.3, 2.0, 0.5 Hz, 4 H), 7.08 (dd, *J* = 8.0, 1.8 Hz, 4 H), 6.07 (d, *J* = 8.0 Hz, 4 H), 2.12 (s, 12 H). **¹³C NMR (100 MHz, CD₂Cl₂) δ (ppm)**: 191.2, 164.3, 156.3, 151.5, 145.2, 138.8, 133.1, 131.4, 130.8, 130.1, 123.2, 119.0, 18.5. **HR-MS (ESI): M⁺ Calculated: (C₅₂H₄₀Cl₂Ir₂N₄O₄) 1240.2; Found 1240.2.**

Tetrakis[2-(4'-formylphenyl)-5-formylpyridine-C²,N']-bis(μ-chloro)diiridium (III) [Ir(4-CHOppy)₂Cl]₂, 2a: Deep red solid. **Yield**: 45%. **R_f**: 0.32 (DCM : EA = 1:1 on silica). **Mp**: 374 °C (decompose). **¹H NMR (400 MHz, CD₂Cl₂) δ (ppm)**: 9.74 (dd, *J* = 1.9, 0.8 Hz, 4 H), 9.67 (s, 4 H), 9.58 (s, 4 H), 8.37-8.31 (m, 8 H), 7.92 (d, *J* = 8.0 Hz, 4 H), 7.44 (dd, *J* = 8.1, 1.6 Hz, 4 H), 6.35 (d, *J* = 1.5 Hz, 4 H). **¹³C NMR (100 MHz, CD₂Cl₂) δ (ppm)**: 191.7, 187.6, 172.0, 153.6, 147.9, 146.3, 137.9, 137.0, 131.6, 131.2, 126.5, 123.6, 120.7. **HR-MS (ESI): M⁺ Calculated: (C₅₂H₄₀Cl₂Ir₂N₄O₄) 1296.1; Found 1296.1.**

Tetrakis[2-(3'-formylphenyl)-5-formylpyridine- C^2,N']-bis(μ -chloro)diiridium (III) [Ir(3-CHOppy)₂Cl]₂, **2b: Orange solid. Yield: 37%. R_f : 0.25 (DCM : EA = 1:1 on silica). Mp: 337 °C (decompose). ¹H NMR (300 MHz, CD₂Cl₂) δ (ppm): 9.84 (s, 4 H), 9.64 (s, 8 H), 8.34-8.33 (m, 8 H), 8.21 (d, J = 1.8 Hz, 4 H), 7.17 (dd, J = 8.1, 1.7 Hz, 4 H), 6.13 (d, J = 8.1 Hz, 4 H). ¹³C NMR (100 MHz, CD₂Cl₂) δ (ppm): 190.7, 187.5, 172.1, 157.5, 153.4, 143.3, 137.9, 132.1, 131.7, 131.4, 131.0, 126.4, 120.0. HR-MS (ESI): M^+ Calculated: (C₅₂H₄₀Cl₂Ir₂N₄O₄) 1296.1; Found 1296.1.**

X-Ray Crystallography. Data for complexes **1a**, **1b** and **2a** were collected at 173 K by using a Rigaku FR-X Ultrahigh brilliance Microfocus RA generator/confocal optics and Rigaku XtaLAB P200 system using Mo K α radiation (λ = 0.71073 Å). Intensity data were collected using ω steps accumulating area detector images spanning at least a hemisphere of reciprocal space. Data for complex **2b** was collected at 173 K by using a Rigaku MM-007HF High brilliance RA generator/confocal optics and Rigaku XtaLAB P100 system, with Cu K α radiation (λ = 1.54187 Å). Intensity data were collected using ω and ϕ steps accumulating area detector images spanning at least a hemisphere of reciprocal space. Data for all complexes were corrected for Lorentz polarization effects. A multiscan absorption correction was applied by using CrystalClear.⁴¹ Structures were solved by Patterson methods (PATY)⁴² and refined by full-matrix least-squares against F^2 (SHELXL-2013).⁴³ Non-hydrogen atoms were refined anisotropically, and hydrogen atoms were refined using a riding model. Complex **2a** showed discrete disorder in one of the formyl groups, which was modelled over two sites. Both complexes **2a** and **2b** showed signs of unresolvable disorder in various of the formyl groups. Restraints to some

bond distances, angles and some thermal parameters were required. All calculations were performed using the CrystalStructure interface.⁴⁴ Crystallographic data for the four complexes are listed in Table 6. Data for CCDC 1026256-1026259 can be obtained free of charge from The Cambridge Crystallographic Data Centre via www.ccdc.cam.ac.uk/data_request/cif.

Table 6. Crystallographic data for **1a-2b**.

	1a	1b	2a	2b
Formula	C ₅₃ H ₄₂ Cl ₄ Ir ₂ N ₄ O ₄	C ₅₂ H ₄₀ Cl ₂ Ir ₂ N ₄ O ₄	C ₅₄ H ₃₆ Cl ₆ Ir ₂ N ₄ O ₈	C ₅₂ H ₃₂ Cl ₂ Ir ₂ N ₄ O ₈
<i>M</i> (g mol ⁻¹)	1410.12	1240.26	1466.06	1296.19
Crystal System	Monoclinic	Monoclinic	Monoclinic	Monoclinic
Space Group	<i>P</i> 2 ₁ / <i>c</i>	<i>P</i> 2 ₁ / <i>c</i>	<i>P</i> 2 ₁ / <i>n</i>	<i>P</i> 2 ₁ / <i>c</i>
<i>a</i> [Å]	11.065(2)	11.0995(19)	22.9927(11)	11.800(3)
<i>b</i> [Å]	37.753(6)	20.038(3)	11.5838(5)	24.431(6)
<i>c</i> [Å]	13.197(3)	29.679(5)	38.7370(18)	19.925(5)
β [°]	114.701(6)	99.998(4)	97.2195(13)	97.874(6)
<i>V</i> [Å ³]	5008.5(17)	6500.7(18)	10235.5(8)	5690(2)
<i>Z</i>	4	4	8	4
ρ _{calcd.} (g cm ⁻³)	1.870	1.267	1.903	1.513
μ (mm ⁻¹)	5.695	4.219	5.583	9.999
Measured refln.	51348	97749	152461	56622
Unique refln. (<i>R</i> _{int})	9097 (0.0756)	11956 (0.1210)	18712 (0.0527)	10268 (0.1622)
<i>R</i> ₁ [I > 2σ(I)]	0.0487	0.1243	0.0367	0.1313
<i>wR</i> ₂ (all)	0.1378	0.3092	0.1034	0.3816

Photophysical measurements. Optically dilute solutions of concentrations on the order of 10⁻⁵ or 10⁻⁶ M were prepared in HPLC grade DCM for absorption and emission analysis, respectively. Absorption spectra were recorded at room temperature on a Shimadzu UV-

1800 double beam spectrophotometer in a sealed quartz cuvette from Starna. Molar absorptivity values were determined from at least four solutions with concentrations varying from 3.39×10^{-6} M to 4.17×10^{-5} M followed by linear regression analysis with all results having coefficient of determination (*r*-squared values) being at least 0.998. Solutions for were degassed via three freeze-pump-thaw cycles prior to emission analysis in a home-built quartz cuvette. Steady state emission, excitation spectra and time-resolved emission spectra were recorded at 298 K using an Edinburgh Instruments F980. Samples were excited at 455nm for steady state measurements while at 470 nm for time-resolved measurements. Photoluminescence quantum yields were determined using the optically dilute method⁴⁵ in which four sample solutions with absorbance values of 0.10, 0.080, 0.060 and 0.040 at 455 nm were used. For each sample, linearity between absorption and emission intensity was verified through linear regression analysis and additional measurements were acquired until the Pearson regression factor (R^2) for the linear fit of the data set surpassed 0.9. Individual relative quantum yield values were calculated for each solution and the values reported represent the slope value. The equation $\Phi_s = \Phi_r(A_r/A_s)(I_s/I_r)(n_s/n_r)^2$ was used to calculate the relative quantum yield of each of the sample, where Φ_r is the absolute quantum yield of the reference, *n* is the refractive index of the solvent, *A* is the absorbance at the excitation wavelength, and *I* is the integrated area under the corrected emission curve. The subscripts s and r refer to the sample and reference, respectively. A solution of [Ru(bpy)₃](PF₆)₂ in ACN ($\Phi_r = 0.095$) was used as the external reference.²⁶

Electrochemistry measurements. Cyclic Voltammetry (CV) analysis was performed on an Electrochemical Analyzer potentiostat model CH600D from CH Instruments. Samples were prepared as DCM solutions, which were degassed by sparging with DCM-saturated nitrogen gas for 15 min prior to measurements. All measurements were performed in 0.1M DCM solution of $n\text{Bu}_4\text{NPF}_6$, which acted as the supporting electrolyte. An Ag/Ag^+ electrode was used as the reference electrode while a platinum electrode and a platinum wire were used as the working electrode and counter electrode, respectively. The redox potentials are reported relative to a standard calomel electrode (SCE) with a ferrocenium/ferrocene (Fc^+/Fc) redox couple as an internal reference (0.46 V vs SCE).¹⁸

Density Functional Theory (DFT) Calculations. All calculations were performed with the Gaussian 09⁴⁶ suite. The level of theory for all DFT^{28c,47} and TD-DFT^{28d-f} calculations was B3LYP; excited-state triplet geometries were calculated using the unrestricted B3LYP method (UB3LYP).^{29b,29c,48} The 6-31G* basis set⁴⁹ was used for C, H and N directly linked to Iridium while the other C, H, N and F atoms were undertaken with 3-21G* basis set,^{30a,31a-e} and the VDZ (valence double ζ) with SBKJC effective core potential basis set³⁰ was used for Iridium. The predicted phosphorescence wavelengths were obtained by energy difference between the triplet and singlet states at their respective optimized geometries.⁵⁰ The energy, oscillator strength and related MO contributions for the 100 lowest singlet-singlet and 5 lowest singlet-triplet excitations were obtained from the TD-DFT/singlets and the TD-DFT/triplets output files, respectively. The calculated absorption spectra were visualized with GaussSum 2.1 (fwhm: 1000 cm^{-1}).⁵¹

OLED fabrication and characterization. The PEDOT:PSS layer was spin-coated on pre-patterned ITO glass substrate after ultrasonic cleaning in acetone and 2-propanol consecutively and finally oxygen plasma treatment. PVK, serving as a hole transporting layer, was spin-coated directly onto PEDOT:PSS after baking at 120 °C for 10 minutes in the glove-box to remove the residual moisture. After another baking of PVK at 120 °C for 10 minutes, the emitting layer, comprising of the mixture of the iridium dimer complexes (dissolved in DCM) and hosts (dissolved in chlorobenzene), was spin-coated on PVK. An additional electron transporting layer, B3PYMPM, was thermally evaporated onto the active layer. Finally, Ca (20 nm)/Al (100 nm) as the composite cathode was thermally deposited through a shadow mask in the vacuum chamber under a pressure of 2.0×10^{-6} mbar. All the devices were encapsulated with UV epoxy resin in the glove-box. The luminance-current-voltage measurement was conducted in ambient environment by using Keithley 2400 source meter and 2000 multi-meter connected to a calibrated Si photodiode. The external quantum efficiency was calculated with the assumption of a Lambertian distribution. The electroluminescence spectrum was captured by an Andor DV420-BV CCD spectrometer. The layer thickness was measurement using a Veeco DekTak 150 surface profiler.

References

- (1) (a) Yersin, H. *Highly Efficient OLEDs with Phosphorescent Materials*; Wiley-VCH: Weinheim, **2008**; (b) Gather, M. C.; Köhnen, A.; Meerholz, K. *Adv. Mater.* **2011**, *23*, 233; (c) *WOLEDs and Organic Photovoltaics: Recent Advances and Applications*; Yam, V. W. W., Ed., **2010**; (d) Fan, C.; Yang, C. *Chem Soc Rev* **2014**, *43*, 6439; (e) Farinola, G. M.; Ragni, R. *Chem. Soc. Rev.* **2011**, *40*, 3467.

- (2) (a) Plummer, E. A.; van Dijken, A.; Hofstraat, J. W.; De Cola, L.; Brunner, K. *Adv. Funct. Mater.* **2005**, *15*, 281; (b) Adachi, C.; Baldo, M. A.; Thompson, M. E.; Forrest, S. R. *J. Appl. Phys.* **2001**, *90*, 5048; (c) Lamansky, S.; Djurovich, P.; Murphy, D.; Abdel-Razzaq, F.; Lee, H.-E.; Adachi, C.; Burrows, P. E.; Forrest, S. R.; Thompson, M. E. *J. Am. Chem. Soc.* **2001**, *123*, 4304.
- (3) (a) Baldo, M. A.; O'Brien, D. F.; You, Y.; Shoustikov, A.; Sibley, S.; Thompson, M. E.; Forrest, S. R. *Nature* **1998**, *395*, 151; (b) Yersin, H.; Rausch, A. F.; Czerwieniec, R.; Hofbeck, T.; Fischer, T. *Coord. Chem. Rev.* **2011**, *255*, 2622.
- (4) Chi, Y.; Chou, P.-T. *Chem. Soc. Rev.* **2010**, *39*, 638.
- (5) (a) Sprouse, S.; King, K. A.; Spellane, P. J.; Watts, R. J. *J. Am. Chem. Soc.* **1984**, *106*, 6647; (b) Carlson, G. A.; Djurovich, P. I.; Watts, R. J. *Inorg. Chem.* **1993**, *32*, 4483; (c) Garces, F. O.; King, K. A.; Watts, R. J. *Inorg. Chem.* **1988**, *27*, 3464.
- (6) (a) Bettington, S.; Tavasli, M.; Bryce, M. R.; Batsanov, A. S.; Thompson, A. L.; Attar, H. A. A.; Dias, F. B.; Monkman, A. P. *J. Mater. Chem.* **2006**, *16*, 1046; (b) M'Hamedi, A.; Batsanov, A. S.; Fox, M. A.; Bryce, M. R.; Abdullah, K.; Al-Attar, H. A.; Monkman, A. P. *J. Mater. Chem.* **2012**, *22*, 13529.
- (7) Lamansky, S.; Djurovich, P.; Murphy, D.; Abdel-Razzaq, F.; Kwong, R.; Tsyba, I.; Bortz, M.; Mui, B.; Bau, R.; Thompson, M. E. *Inorg. Chem.* **2001**, *40*, 1704.
- (8) (a) Hofbeck, T.; Yersin, H. *Inorg. Chem.* **2010**, *49*, 9290; (b) Sajoto, T.; Djurovich, P. I.; Tamayo, A. B.; Oxgaard, J.; Goddard, W. A.; Thompson, M. E. *J. Am. Chem. Soc.* **2009**, *131*, 9813; (c) Endo, A.; Suzuki, K.; Yoshihara, T.; Tobita, S.; Yahiro, M.; Adachi, C. *Chem. Phys. Lett.* **2008**, *460*, 155; (d) St-Pierre, G.; Ladouceur, S.; Fortin, D.; Zysman-Colman, E. *Dalton Trans.* **2011**, *40*, 11726.
- (9) (a) Holder, E.; Marin, V.; Meier, M. A. R.; Schubert, U. S. *Macromol. Rapid Commun.* **2004**, *25*, 1491; (b) Alrawashdeh, L. R.; Day, A. I.; Wallace, L. *Dalton Trans* **2013**, *42*, 16478; (c) Ma, Y.; Liu, S.; Yang, H.; Wu, Y.; Yang, C.; Liu, X.; Zhao, Q.; Wu, H.; Liang, J.; Li, F.; Huang, W. *J. Mater. Chem.* **2011**, *21*, 18974; (d) Cao, X.; Wu, Y.; Liu, K.; Yu, X.; Wu, B.; Wu, H.; Gong, Z.; Yi, T. *J. Mater. Chem.* **2012**, *22*, 2650; (e) Zaarour, M.; Guerchais, V.; Le Bozec, H.; Dragonetti, C.; Righetto, S.; Roberto, D.; De Angelis, F.; Fantacci, S.; Lobello, M. G. *Dalton Trans* **2013**, *42*, 155.
- (10) (a) Lo, K. K.-W.; Chung, C.-K.; Zhu, N. *Chem. Eur. J.* **2003**, *9*, 475; (b) Lo, K. K.-W.; Zhang, K. Y.; Leung, S.-K.; Tang, M.-C. *Angew. Chem. Int. Ed.* **2008**, *47*, 2213; (c) Leung, S. K.; Kwok, K. Y.; Zhang, K. Y.; Lo, K. K. *Inorg. Chem.* **2010**, *49*, 4984.
- (11) Miyaura, N.; Suzuki, A. *Chem. Rev.* **1995**, *95*, 2457.
- (12) Wang, X.; Rabbat, P.; O'Shea, P.; Tillyer, R.; Grabowski, E. J. J.; Reider, P. J. *Tetrahedron Lett.* **2000**, *41*, 4335.
- (13) Nonoyama, M. *Bull. Chem. Soc. Jpn.* **1974**, *47*, 767.
- (14) Holder, E.; Marin, V.; Alexeev, A.; Schubert, U. S. *J. Polym. Sci., Part A: Polym. Chem.* **2005**, *43*, 2765.
- (15) Davies, D. L.; Lowe, M. P.; Ryder, K. S.; Singh, K.; Singh, S. *Dalton Trans.* **2011**, *40*, 1028.
- (16) Bettington, S.; Thompson, A. L.; Beeby, A.; Goeta, A. E. *Acta Crystallographica Section E Structure Reports Online* **2004**, *60*, m827.
- (17) (a) Norel, L.; Rudolph, M.; Vanthuyne, N.; Williams, J. A. G.; Lescop, C.; Roussel, C.; Autschbach, J.; Crassous, J.; Réau, R. *Angew. Chem. Int. Ed.* **2010**, *49*, 99; (b) Garces, F. O.; Dedeian, K.; Keder, N. L.; Watts, R. J. *Acta Crystallogr., Sect. C: Cryst. Struct. Commun.* **1993**, *49*, 1117; (c) Chen, L.-Q.; Yang, C.-L.; Qin, J.-G. *Acta Crystallogr., Sect. C: Cryst. Struct. Commun.* **2005**, *61*, m513; (d) Mesto, E.; Scordari, F.; Lacalamita, M.; De Cola, L.; Ragni, R.; Farinola, G. M. *Acta Crystallogr C* **2013**, *69*, 480; (e) Chen, L.; Yang, C.; Li, M.; Qin, J.; Gao, J.; You, H.; Ma, D. *Crystal Growth & Design* **2006**, *7*, 39; (f) Baranoff, E.; Bolink, H. J.; Constable, E. C.; Delgado, M.; Haussinger, D.; Housecroft, C. E.; Nazeeruddin, M. K.; Neuberger, M.; Orti, E.; Schneider, G. E.; Tordera, D.; Walliser, R. M.; Zampese, J. A. *Dalton Trans.* **2013**, *42*, 1073;

- (g) Constable, E. C.; Ertl, C. D.; Housecroft, C. E.; Zampese, J. A. *Dalton Trans.* **2014**, *43*, 5343; (h) Xu, C.; Li, H. M.; Xiao, Z. Q.; Wang, Z. Q.; Tang, S. F.; Ji, B. M.; Hao, X. Q.; Song, M. P. *Dalton Trans* **2014**, *43*, 10235; (i) Wang, Z.-Q.; Xu, C.; Dong, X.-M.; Zhang, Y.-P.; Hao, X.-Q.; Gong, J.-F.; Song, M.-P.; Ji, B.-M. *Inorg. Chem. Commun.* **2011**, *14*, 316; (j) McGee, K. A.; Mann, K. R. *Inorg. Chem.* **2007**, *46*, 7800; (k) Xu, C.; Wang, Z.-Q.; Dong, X.-M.; Hao, X.-Q.; Zhao, X.-M.; Ji, B.-M.; Song, M.-P. *Inorg. Chim. Acta* **2011**, *373*, 306; (l) Chepelin, O.; Ujma, J.; Wu, X.; Slawin, A. M. Z.; Pitak, M. B.; Coles, S. J.; Michel, J.; Jones, A. C.; Barran, P. E.; Lusby, P. J. *J. Am. Chem. Soc.* **2012**, *134*, 19334; (m) Krisyuk, V.; Turgambaeva, A.; Lee, J.; Rhee, S.-W. *Transition Met. Chem.* **2005**, *30*, 786.
- (18) Connelly, N. G.; Geiger, W. E. *Chem. Rev.* **1996**, *96*, 877.
- (19) Cardona, C. M.; Li, W.; Kaifer, A. E.; Stockdale, D.; Bazan, G. C. *Adv. Mater.* **2011**, *23*, 2367.
- (20) Bredas, J.-L. *Materials Horizons* **2014**, *1*, 17.
- (21) Andreiadis, E. S.; Imbert, D.; Pécaut, J.; Calborean, A.; Ciofini, I.; Adamo, C.; Demadrille, R.; Mazzanti, M. *Inorg. Chem.* **2011**, *50*, 8197.
- (22) Beyer, B.; Ulbricht, C.; Escudero, D.; Friebe, C.; Winter, A.; González, L.; Schubert, U. S. *Organometallics* **2009**, *28*, 5478.
- (23) Welby, C. E.; Gilmartin, L.; Marriott, R. R.; Zahid, A.; Rice, C. R.; Gibson, E. A.; Elliott, P. I. *Dalton Trans* **2013**, *42*, 13527.
- (24) Tamayo, A. B.; Alleyne, B. D.; Djurovich, P. I.; Lamansky, S.; Tsyba, I.; Ho, N. N.; Bau, R.; Thompson, M. E. *J. Am. Chem. Soc.* **2003**, *125*, 7377.
- (25) Ladouceur, S.; Fortin, D.; Zysman-Colman, E. *Inorg. Chem.* **2011**, *50*, 11514.
- (26) Ishida, H.; Tobita, S.; Hasegawa, Y.; Katoh, R.; Nozaki, K. *Coord. Chem. Rev.* **2010**, *254*, 2449.
- (27) Frisch, M. J.; Trucks, G. W.; Schlegel, H. B.; Scuseria, G. E.; Robb, M. A.; Cheeseman, J. R.; Zakrzewski, V. G.; Montgomery, J. A.; Stratmann, R. E.; Burant, J. C.; Dapprich, S.; J.M., M.; Daniels, A. D.; Kudin, K. N.; Strain, M. C.; Farkas, O.; Tomasi, J.; Barone, V.; Cossi, M.; Cammi, R.; Mennucci, B.; Pomelli, C.; Adamo, C.; Clifford, S.; Ochterski, J.; Peterson, G. A.; Ayala, P. Y.; Cui, Q.; Morokuma, K.; Malik, A.; Rabuck, A. D.; Raghavachari, K.; Foresman, J. B.; Cioslowski, J.; Ortiz, J. V.; Baboul, A. G.; Stefanov, B. B.; Liu, G.; Liashenko, A.; Piskorz, P.; Komaromi, I.; Gomperts, R.; Martin, R. L.; Challacombe, M.; Gill, P. M. W.; Johnson, B. G.; Chen, W.; Wong, M. W.; Andres, J. L.; Head-Gordon, M.; Replogle, E. S.; Pople, J. A. *Gaussian 98 (Revision A.6)*; Pittsburgh, PA, **1998**
- (28) (a) Hohenberg, P.; Kohn, W. *Phys. Rev.* **1964**, *136*, B864; (b) Kohn, W.; Sham, L. J. *Phys. Rev.* **1965**, *140*, A1133; (c) In *The Challenge of d and f Electrons*; Salahub, D. R., Zerner, M. C., Eds.; ACS: Washington, DC, **1989**; (d) Stratmann, R. E.; Scuseria, G. E.; Frisch, M. J. *J. Chem. Phys.* **1998**, *109*, 8218; (e) Bauernschmitt, R.; Ahlrichs, R. *Chem. Phys. Lett.* **1996**, *256*, 454; (f) Casida, M. E.; Jamorski, C.; Casida, K. C.; Salahub, D. R. *J. Chem. Phys.* **1998**, *108*, 4439.
- (29) (a) Becke, A. D. *J. Chem. Phys.* **1993**, *98*, 5648; (b) Lee, C.; Yang, W.; Parr, R. G. *Phys. Rev. B* **1988**, *37*, 785; (c) Miehlich, B.; Savin, A.; Stoll, H.; Preuss, H. *Chem. Phys. Lett.* **1989**, *157*, 200.
- (30) (a) Binkley, J. S.; Pople, J. A.; Hehre, W. J. *J. Am. Chem. Soc.* **1980**, *102*, 939; (b) Stevens, W. J.; Basch, W. J.; Krauss, M. *J. Chem. Phys.* **1984**, *81*, 6026; (c) Stevens, W. J.; Krauss, M.; Basch, H.; Jasien, P. G. *Can. J. Chem.* **1992**, *70*, 612; (d) Cundari, T. R.; Stevens, W. J. *J. Chem. Phys.* **1993**, *98*, 5555.
- (31) (a) Gordon, M. S.; Binkley, J. S.; Pople, J. A.; Pietro, W. J.; Hehre, W. J. *J. Am. Chem. Soc.* **1982**, *104*, 2797; (b) Pietro, W. J.; Francl, M. M.; Hehre, W. J.; Defrees, D. J.; Pople, J. A.; Binkley, J. S. *J. Am. Chem. Soc.* **1982**, *104*, 5039; (c) Dobbs, K. D.; Hehre, W. J. *J. Comput. Chem.* **1986**, *7*, 359; (d) Dobbs, K. D.; Hehre, W. J. *J. Comput. Chem.* **1987**, *8*, 861; (e) Dobbs, K. D.; Hehre, W. J. *J. Comput. Chem.* **1987**, *8*, 880; (f) Ditchfield, R.; Hehre, W. J.; Pople, J. A. *J. Chem. Phys.* **1971**, *54*, 724; (g) Hehre, W. J.; Ditchfield, R.; Pople, J. A. *J. Chem. Phys.* **1972**,

- 56, 2257; (h) Hariharan, P. C.; Pople, J. A. *Theor. Chim. Acta* **1973**, 28, 213; (i) Hariharan, P. C.; Pople, J. A. *Mol. Phys.* **1974**, 27, 209; (j) Gordon, M. S. *Chem. Phys. Lett.* **1980**, 76, 163.
- (32) Tomasi, J.; Mennucci, B.; Cammi, R. *Chem. Rev.* **2005**, 105, 2999.
- (33) (a) Donato, L.; McCusker, C. E.; Castellano, F. N.; Zysman-Colman, E. *Inorg. Chem.* **2013**, 52, 8495; (b) Soliman, A. M.; Fortin, D.; Harvey, P. D.; Zysman-Colman, E. *Dalton Trans.* **2012**, 41, 9382.
- (34) Yang, X. H.; Jaiser, F.; Stiller, B.; Neher, D.; Galbrecht, F.; Scherf, U. *Adv. Funct. Mater.* **2006**, 16, 2156.
- (35) Kalinowski, J.; Cocchi, M.; Virgili, D.; Fattori, V.; Williams, J. A. G. *Adv. Mater.* **2007**, 19, 4000.
- (36) Lee, S.; Kim, K.-H.; Limbach, D.; Park, Y.-S.; Kim, J.-J. *Adv. Funct. Mater.* **2013**, 23, 4105.
- (37) Adachi, C.; Baldo, M. A.; Thompson, M. E.; Forrest, S. R. *J. Appl. Phys.* **2001**, 90, 5048.
- (38) Coulson, D. R.; Satek, L. C.; Grim, S. O. In *Inorg. Synth.*; Cotton, F. A., Ed. **2007**, 121.
- (39) Bouillon, A.; Lancelot, J.-C.; Collot, V.; Bovy, P. R.; Rault, S. *Tetrahedron* **2002**, 58, 2885.
- (40) Bernardo, P. H.; Sivaraman, T.; Wan, K. F.; Xu, J.; Krishnamoorthy, J.; Song, C. M.; Tian, L.; Chin, J. S.; Lim, D. S.; Mok, H. Y.; Yu, V. C.; Tong, J. C.; Chai, C. L. *J Med Chem* **2010**, 53, 2314.
- (41) *CrystalClear-SM Expert v. 2.1*; The Woodlands, Texas, USA, **2010-2014**
- (42) Beurskens, P. T.; Beurskens, G.; de Gelder, R.; Garcia-Granda, S.; Gould, R. O.; Israel, R.; Smits, J. M. M. *DIRDIF-99* University of Nijmegen, The Netherlands, **1999**.
- (43) Sheldrick, G. *Acta Crystallographica Section A* **2008**, 64, 112.
- (44) *CrystalStructure v4.1*; The Woodlands, Texas, USA, **2014**
- (45) (a) Crosby, G. A.; Demas, J. N. *J. Phys. Chem.* **1971**, 75, 991; (b) Fery-Forgues, S.; Lavabre, D. *J. Chem. Educ.* **1999**, 76, 1260.
- (46) Frisch, M. J.; Trucks, G. W.; Schlegel, H. B.; Scuseria, G. E.; Robb, M. A.; Cheeseman, J. R.; Scalmani, G.; Barone, V.; Mennucci, B.; Petersson, G. A.; Nakatsuji, H.; Caricato, M.; Li, X.; Hratchian, H. P.; Izmaylov, A. F.; Bloino, J.; Zheng, G.; Sonnenberg, J. L.; Hada, M.; Ehara, M.; Toyota, K.; Fukuda, R.; Hasegawa, J.; Ishida, M.; Nakajima, T.; Honda, Y.; Kitao, O.; Nakai, H.; Vreven, T.; Montgomery Jr., J. A.; Peralta, J. E.; Ogliaro, F.; Bearpark, M.; Heyd, J. J.; Brothers, E.; Kudin, K. N.; Staroverov, V. N.; Kobayashi, R.; Normand, J.; Raghavachari, K.; Rendell, A.; Burant, J. C.; Iyengar, S. S.; Tomasi, J.; Cossi, M.; Rega, N.; Millam, J. M.; Klene, M.; Knox, J. E.; Cross, J. B.; Bakken, V.; Adamo, C.; Jaramillo, J.; Gomperts, R.; Stratmann, R. E.; Yazyev, O.; Austin, A. J.; Cammi, R.; Pomelli, C.; Ochterski, J. W.; Martin, R. L.; Morokuma, K.; Zakrzewski, V. G.; Voth, G. A.; Salvador, P.; Dannenberg, J. J.; Dapprich, S.; Daniels, A. D.; Farkas, Ö.; Foresman, J. B.; Ortiz, J. V.; Cioslowski, J.; Fox, D. J., 7.0 ed.; Wallingford, CT, **2009**
- (47) (a) Hohenberg, P.; Kohn, W. *Phys. Rev.* **1964**, B136, 864; (b) Kohn, W.; Sham, L. *J. Phys. Rev.* **1965**, A140, 1133; (c) Parr, R. G.; Yang, W. *Density-functional theory of atoms and molecules*; Oxford Univ. Press: Oxford, **1989**.
- (48) Becke, A. D. *J. Chem. Phys.* **1993**, 98, 5648.
- (49) Rassolov, V. A.; Pople, J. A.; Ratner, M. A.; Windus, T. L. *J. Chem. Phys.* **1998**, 109, 1223.
- (50) (a) Ladouceur, S.; Fortin, D.; Zysman-Colman, E. *Inorg. Chem.* **2010**, 49, 5625; (b) Lowry, M. S.; Hudson, W. R.; Pascal Jr., R. A.; Bernhard, S. *J. Am. Chem. Soc.* **2004**, 126, 14129.
- (51) O'Boyle, N. M. *GaussSum 2.0* Dublin City University; Dublin Ireland, **2006**; Available at <http://gausssum.sf.net>.

TOC Graphic

