

# Dalton Transactions

Accepted Manuscript



This is an *Accepted Manuscript*, which has been through the Royal Society of Chemistry peer review process and has been accepted for publication.

*Accepted Manuscripts* are published online shortly after acceptance, before technical editing, formatting and proof reading. Using this free service, authors can make their results available to the community, in citable form, before we publish the edited article. We will replace this *Accepted Manuscript* with the edited and formatted *Advance Article* as soon as it is available.

You can find more information about *Accepted Manuscripts* in the [Information for Authors](#).

Please note that technical editing may introduce minor changes to the text and/or graphics, which may alter content. The journal's standard [Terms & Conditions](#) and the [Ethical guidelines](#) still apply. In no event shall the Royal Society of Chemistry be held responsible for any errors or omissions in this *Accepted Manuscript* or any consequences arising from the use of any information it contains.

# Long- and short-range structure studies of KBT-KBZ solid-solutions using synchrotron radiation

Samuel Liu,<sup>a</sup> Peter E. R. Blanchard,<sup>b,c</sup> Zhaoming Zhang,<sup>d</sup> Brendan J. Kennedy,<sup>a</sup> and Chris D. Ling<sup>\*a</sup>

Received Xth XXXXXXXXXXXX 20XX, Accepted Xth XXXXXXXXXXXX 20XX

First published on the web Xth XXXXXXXXXXXX 200X

DOI: 10.1039/b000000x

The relaxor ferroelectric  $K_{0.5}Bi_{0.5}TiO_3$  has been synthesised in a solid-solution series with  $K_{0.5}Bi_{0.5}ZrO_3$ , as  $K_{0.5}Bi_{0.5}Ti_{1-x}Zr_xO_3$ . High-resolution synchrotron X-ray powder diffraction and X-ray absorption near edge structure spectroscopy were used to characterise the long-range average and local structural behaviour. Rietveld refinements against diffraction data show that a pseudocubic tetragonal region exists across the whole solid-solution series, with truly cubic symmetry only observed at  $x = 1$  (pure KBZ). Variable-temperature diffraction data for  $x = 0$  (pure KBT) showed a broad ferroelectric transition from tetragonal to cubic symmetry at approximately 683 K with a coexistence of both phases close to that temperature, accompanied by a marked volume contraction. Ti K-edge data showed that Zr doping has a minimal effect on Ti off-centering, and revealed no evidence for local clustering. Metal L-edges showed that  $Ti^{4+}$  cations remain off-centered with increasing Zr content, while  $Zr^{4+}$  cations approach a higher-symmetry coordination environment, most likely due to the increased size of the Zr atoms. Although there is a minimal effect on actual Ti-offsets, an effective dilution of these environments by Zr doping leads to a reduction in polar domains and a diminished ferroelectric response.

## 1 Introduction

A thorough understanding of structure-property relationships underlies any rational search for new functional materials. In the case of ferroelectric materials, the most fundamental relationship is between the role of second-order Jahn-Teller distortions of metal cations with a  $d^0$  electronic state<sup>1</sup>, and local (or long-range) ferroelectric order. In metal oxide perovskite ( $ABO_3$ ) systems, the empty d orbitals of the B-site cation can hybridise with oxygen 2p orbitals causing a favourable offset of the B-site cation itself<sup>2</sup>. For a non-centrosymmetric crystal structure, this offset causes a net dipole<sup>3</sup>. An increase in temperature can remove the B-site cation offset, rendering the material paraelectric at the Curie temperature  $T_C$ .

Ferroelectricity is widely found in perovskites and perovskite-related materials. The most important commercially is  $Pb_{0.5}Zr_xTi_{0.5-x}O_3$  (PZT), which has a number of particular features, chief among which is the lead cation ( $Pb^{2+}$ ) which enhances the ferroelectric effect *via* additional distortions from its stereochemically active  $6s^2$  electron lone pair. It has been found that the ferroelectric properties of PZT are further enhanced near a structural transition known as the mor-

photropic phase boundary (MPB)<sup>4</sup>. A great deal of research effort has been dedicated to finding lead-free alternatives to PZT in order to minimise the use of the toxic element, and encouraging the growth of MPBs appears to be a promising route<sup>5</sup>. Bismuth-based materials have been shown to be feasible candidates, noting that  $Bi^{3+}$  is isoelectronic to  $Pb^{2+}$  and thus preserves the enhanced distortive effects. Charge balance upon replacing  $Pb^{2+}$  with  $Bi^{3+}$  can be achieved by an alkali metal cation of similar size, such as  $Na^+$  or  $K^+$ . There has been extensive research into bismuth titanates, including  $Na_{0.5}Bi_{0.5}TiO_3$  (NBT) and  $K_{0.5}Bi_{0.5}TiO_3$  (KBT), solid-solutions systems such as NBT-KBT<sup>6,7</sup>, combinations with  $SrTiO_3$ <sup>8,9</sup>,  $BaTiO_3$ <sup>10</sup>, and the multiferroic  $BiFeO_3$ <sup>11</sup>.

Relatively little research has been done into the effects of replacing the B-site cation, compared to the vast amounts of literature in A-site modifications. The  $4d^0$  cation  $Zr^{4+}$  is isoelectronic and only slightly larger than  $Ti^{4+}$ <sup>12</sup>, and complete B-site substitution is possible in ( $BaTiO_3$ <sup>13</sup> and NBT<sup>14</sup>). The present study concerns the solid-solution between KBT and  $K_{0.5}Bi_{0.5}ZrO_3$  (KBZ), first reported by Yamada *et al.*,<sup>15</sup> and more recently the subject of a physical property study by Bengagi *et al.*<sup>16</sup>. A smooth structural transition was reported on the basis of sealed-tube X-ray powder diffraction (XRD) data, from the relaxor ferroelectric tetragonal KBT (Ti end member) to the paraelectric cubic KBZ (Zr end member). A pseudocubic region was reported for  $x = 0.1$  to 0.4, in which region a dramatic decrease in the ferroelectric moment was observed<sup>16</sup>.

<sup>a</sup> School of Chemistry, University of Sydney, Sydney 2006, Australia. Fax: +61293513329; Tel: +61293514504; E-mail: [chris.ling@sydney.edu.au](mailto:chris.ling@sydney.edu.au)

<sup>b</sup> Canadian Light Source, Saskatoon, SK, S7N 2V3, Canada.

<sup>c</sup> Department of Chemistry, University of Saskatchewan, Saskatoon, SK, S7N 5C9, Canada.

<sup>d</sup> Australian Nuclear Science and Technology Organisation, Lucas Heights, New South Wales, 2234, Australia.

This work is specifically concerned with investigating chemical changes to the B-site and their effects on structural distortions in the KBT-KBZ system. Due to the presence of very heavy metals such as Bi, conventional XRD is inadequate to resolve the details of oxygen atomic displacements. Our approach is therefore to use a combination of high-resolution synchrotron XRD (SXR) to investigate long-range average structure and X-ray absorption near edge structure (XANES) spectroscopy to investigate the local coordination environment of  $\text{Ti}^{4+}$  and  $\text{Zr}^{4+}$  cations. Our recent study using these techniques on the NBT-NBZ solid-solution concluded that Zr doping had little effect on Ti-offset<sup>14</sup>; noting the slightly different sizes of  $\text{Na}^+$  and  $\text{K}^+$ , slightly different Zr doping effects can be expected in the KBT-KBZ series.

## 2 Experimental

~5 g samples of polycrystalline  $\text{K}_{0.5}\text{Bi}_{0.5}\text{Ti}_{1-x}\text{Zr}_x\text{O}_3$ , where  $x = 0$  to 1 (in 0.1 steps), were prepared by first weighing stoichiometric amounts of  $\text{Bi}_2\text{O}_3$  (Aithaca, 99.999%, dried at 1023 K for 20 h before use),  $\text{K}_2\text{CO}_3$ ,  $\text{TiO}_2$ , and  $\text{ZrO}_2$ . The reagents were finely ground with a mortar and pestle with the addition of acetone to improve homogeneity. The mixture was then reacted as a powder in alumina crucibles initially at 1023 K for 8 h, then reground and heated to 1223 K for 8 h twice. At high temperatures, significant potassium loss was noted by Bengali *et al.*<sup>16</sup>. An additional 10-15%  $\text{K}_2\text{CO}_3$  was therefore added to each sample to help minimise impurities. Long heating times improve the stability of the tetragonal phase of KBT, therefore the  $x = 0$  and 0.1 samples were additionally heated to 1223 K for 72 hrs<sup>16</sup>. Progress was monitored by X-ray powder diffraction (XRD) using a PANalytical X'pert PRO diffractometer in Bragg-Brentano geometry with a sealed-tube source of unmonochromated  $\text{Cu-K}\alpha$  radiation ( $\lambda_{\alpha 1} = 1.5405 \text{ \AA}$ ,  $\lambda_{\alpha 2} = 1.5443 \text{ \AA}$ ).

Synchrotron X-ray powder diffraction (SXR) data were obtained at the Australian Synchrotron, Melbourne, on the Powder Diffraction beamline<sup>17</sup>. Samples were ground into a very fine powder and placed in 0.3 mm quartz capillaries for high-temperature measurements of KBT, or 0.3 mm glass capillaries for room-temperature measurements. Data were collected in Debye-Scherrer geometry at 13500 eV. The corresponding refined wavelength against a  $\text{LaB}_6$  NIST standard was  $\lambda = 0.953296 (1) \text{ \AA}$ . Data collection under non-ambient conditions were achieved using a hot air blower. The temperature range was controlled between room temperature and 973 K (10 K steps, 5 K/min ramp) with  $2 \times 150 \text{ sec}$  (2 detector positions) acquisition time at each step from  $10^\circ \leq 2\theta \leq 90^\circ$ . Room-temperature samples were collected over  $2 \times 120 \text{ sec}$  acquisition times.

Initial structural models were adapted from the already reported structure of KBT<sup>18</sup>. Rietveld refinements against


diffraction data were carried out using the GSAS<sup>19</sup> program with the EXPGUI<sup>20</sup> interface and extracted atomic positions were visualised using the VESTA software package<sup>21</sup>. Cell parameters, anisotropic atomic displacement parameters (ADPs) as well as instrumental parameters and a zero offset were refined.

XANES measurements at the Ti L-edge for  $\text{K}_{0.5}\text{Bi}_{0.5}\text{Ti}_{1-x}\text{Zr}_x\text{O}_3$ , where  $x = 0$  to 0.9 were collected on the Soft X-ray beamline at the Australian Synchrotron<sup>22</sup>. Powder samples were thinly dusted on double-sided carbon tape (SPI Supplies) and inserted into the vacuum chamber via a load lock. The pressure inside the analysis chamber was maintained at better than  $10^{-9}$  Torr. All spectra were taken simultaneously with a total electron yield (TEY) signal measured from a Ti metal reference foil in the beamline. Approximately 10% of the beam intensity is removed by the reference foil. The Ti  $L_3$ -edge of metallic Ti is well known, with a distinct feature located at 453.8 eV<sup>23</sup>. This allowed for a precise energy calibration of the spectra from the various samples. The Ti K- and Zr  $L_3$ -edge XANES spectra were collected on beamline 16A1 at the National Synchrotron Radiation Research Center (NSRRC) in Hsinchu, Taiwan<sup>24</sup>. Samples were finely ground and dispersed onto Kapton tape and placed at a  $45^\circ$  angle to the incident X-ray beam. Spectra were collected in total fluorescence yield (TFY) mode using a Lytle detector with a step size of 0.2 eV near the absorption edge. The Ti K-edge spectra were calibrated against metallic Ti foil with the maximum in the first derivative of the K-edge set to 4966.4 eV. The Zr  $L_3$ -edge spectra were calibrated against elemental Zr with the maximum in the first derivative of the  $L_3$ -edge set to 2222.3 eV<sup>25</sup>. All XANES spectra were normalised using the Athena<sup>26</sup> software.

## 3 Results and Discussion

The solid-solution  $\text{K}_{0.5}\text{Bi}_{0.5}\text{Ti}_{1-x}\text{Zr}_x\text{O}_3$  ( $x = 0$  to 1 with 0.1) steps was successfully synthesised and confirmed by Rietveld refinement against laboratory XRD. Refined occupancies showed that the Ti/Zr ratio were within their nominal composition ranges and hence fixed for refinement models. Interestingly, the refinement for KBT ( $x = 0$ ) by Bengali *et al.* shows the (111) reflection to be significantly undercalculated<sup>16</sup>. A better fit to the peak profile was obtained here by refining for strain factors. The improvement is shown in Figure 1 with the relevant statistics. This suggests that closer to the Ti-rich end member of the solid-solution series, there is a significant contribution from microstrain in the material, which explains the increased synthesis time required to stabilise this phase. For  $x = 0.1 - 1$ , the strain parameter did not significantly improve the fit and was therefore not used. This suggests that the introduction of a slightly larger cation rapidly removes the microstrain by granting additional flexi-

bility to the crystal lattice. The best statistics in Rietveld refinements using laboratory XRD data were achieved using a non-centrosymmetric tetragonal  $P4mm$  (#99) model from  $x = 0 - 0.8$  and a cubic  $Pm\bar{3}m$  (#221) model for  $x = 0.9 - 1$ . This preliminary result suggested that the tetragonal pseudocubic region extends to  $x > 0.4$ , the previously reported limit<sup>16</sup>.

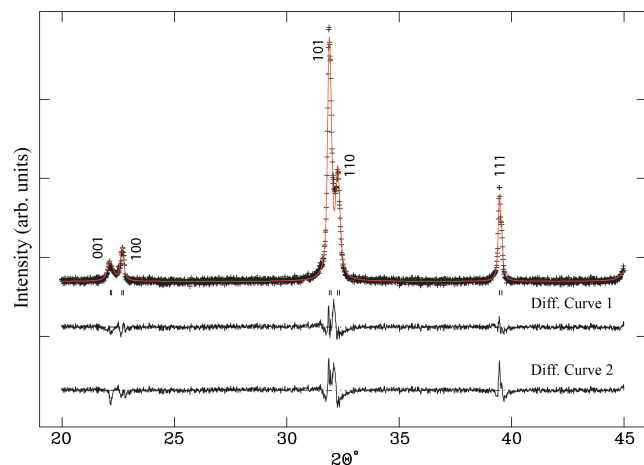


**Fig. 1** The room-temperature laboratory XRD data of KBT. Black crosses represent data points with the calculated pattern shown as a red line. Bragg reflection markers are shown in black below the observed peaks. Diff. Curve 1 refers to the difference curve of the Rietveld refinement including strain parameters shown above ( $\chi^2 = 1.673$ ,  $R_p = 0.0264$ ). Diff. Curve 2 refers to a Rietveld refinement not including strain ( $\chi^2 = 1.948$ ,  $R_p = 0.0279$ ).

### 3.1 Synchrotron XRD

Higher resolution SXR D data were used to refine models to greater precision. The room-temperature data confirmed that the samples were pure apart from a very small ( $< 2\%$ ) fraction of ( $ZrO_2$ ) in some of the samples, which could not be entirely eliminated despite the use of excess K to compensate for loss by evaporation.

In the conventional XRD data of Bengagi *et al.*<sup>16</sup>, diffraction peaks were generally observed to broaden with increasing Ti content through the pseudocubic region ( $x = 0.1 - 0.4$ ). Visually, the same behaviour was observed in our SXR D data for  $x = 0.1 - 0.4$ , with only the pure KBT compound found to possess a clear tetragonal distortion (*i.e.*, split peaks) (Figure 2). In order to test this more rigorously, Rietveld refinements were carried out against SXR D data for all samples using both the non-centrosymmetric tetragonal  $P4mm$  (#99) and cubic  $Pm\bar{3}m$  (#221) space groups. A comparison of the fits for  $x = 0.8$  is shown in Figure 3. Refining equivalent parameters, the tetragonal model provides a significantly improved fit. Refined crystal parameters also were more plausible using a tetragonal model, as shown in Table 1, where the ADPs for the

B-site cations and oxygen atoms are unreasonably large using the cubic model. Using the tetragonal model, large ADPs are only found for the K/Bi mixed occupancy A-site, as expected due to static disorder. The tetragonal model was superior for all samples except pure KBZ, where the best fit was obtained using the cubic model. The evolution of unit cell parameters across the KBT-KBZ solid-solution is shown in Figure 4. The unit cell volume is consistent with Vegard's law. The difference between the  $a$  and  $c$  parameters drops rapidly as  $x$  (Zr content) increases, but remains statistically significant until  $x = 1$ .

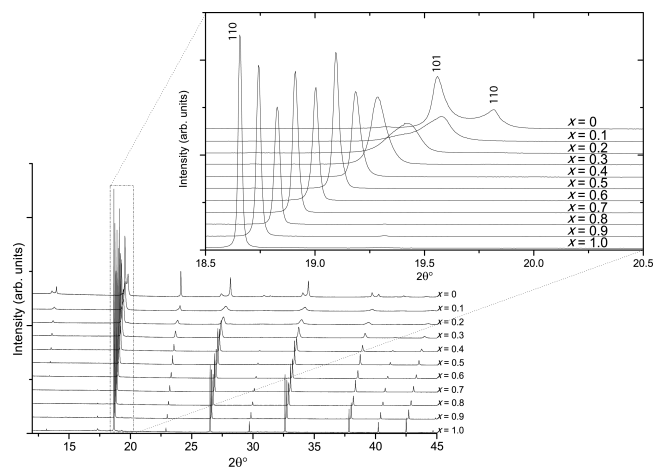

**Fig. 2** Room-temperature SXR D patterns of KBT-KBZ solid-solution.

**Table 1** Atomic Displacement Parameters for  $K_{0.5}Bi_{0.5}Ti_{0.2}Zr_{0.8}O_3$


$100 \cdot U_{iso}$	$P4mm$ (#99)	$Pm\bar{3}m$ (#221)
A-site ( $\text{\AA}^2$ )	14.47(5)	3.48(4)
B-site ( $\text{\AA}^2$ )	0.89(2)	7.74(8)
Oxygen ( $\text{\AA}^2$ )	2.91(12)	21.7(4)

The observation that the KBT-KBZ solid-solution retains tetragonal symmetry - *i.e.*, is pseudocubic rather than truly cubic - up to at least  $x = 0.9$  is consistent with its relaxor ferroelectric behaviour for  $x = 0 - 0.9$  (albeit very weak at higher  $x$ ).<sup>16</sup>

Interestingly, the sodium analogue  $Na_{0.5}Bi_{0.5}ZrO_3$  is reported to be rhombohedral/orthorhombic instead of cubic<sup>14</sup>. This structural difference between K- and Na-versions can be explained by the tolerance factor:

$$t = \frac{\sqrt{2}r_{A-O}}{2r_{B-O}} \quad (1)$$

which predicts a cubic perovskite structure when  $t = 1$ , and distortions away from that value. Pure KBZ has a tolerance factor much closer to 1.0 (0.97) than NBZ (0.93), using

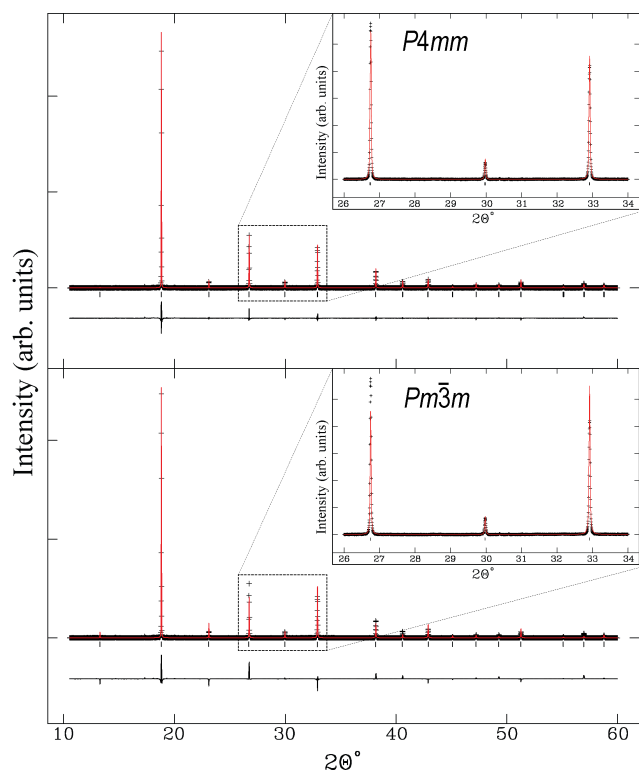


**Fig. 3**  $\text{K}_{0.5}\text{Bi}_{0.5}\text{Ti}_{0.2}\text{Zr}_{0.8}\text{O}_3$  fit to tetragonal  $P4mm$  (#99)  $R_p = 0.0347$  and  $\chi^2 = 9.294$  above and fit to cubic  $Pm\bar{3}m$  (#221)  $R_p = 0.0520$  and  $\chi^2 = 29.98$  below.

bond lengths  $r_{A-O}$  and  $r_{B-O}$  calculated from Shannon's ionic Radii<sup>12</sup>. For pure KBT, the tolerance factor is higher than the ideal value ( $t = 1.03$ ); Zr doping across the KBT-KBZ solid-solution should reduce this and lead to an increase in symmetry. Our SXRD results bear this out, in agreement with previous work<sup>15,16</sup>. This behaviour is different to the NBT-NBZ solid-solution, where the  $t < 1$  for the whole range and lower symmetry structures (rhombohedral, monoclinic and orthorhombic) are always observed<sup>14</sup>.


### 3.2 In Situ Synchrotron XRD

The temperature-dependent behaviour through the ferroelectric-paraelectric phase transition was studied by *in situ* variable-temperature SXRD. Data were collected for pure KBT in order to track the evolution of lattice parameters. This builds on previous work using conventional XRD.<sup>7,27</sup> The evolution of the diffraction patterns (Figure 5) clearly shows the transition from tetragonal to cubic symmetry at  $T_C \sim 683$  K where the lower symmetry split peaks converge to higher symmetry single peaks. Slightly below this temperature, at approximately 663 K, there is a region of phase coexistence. This was not observed in earlier

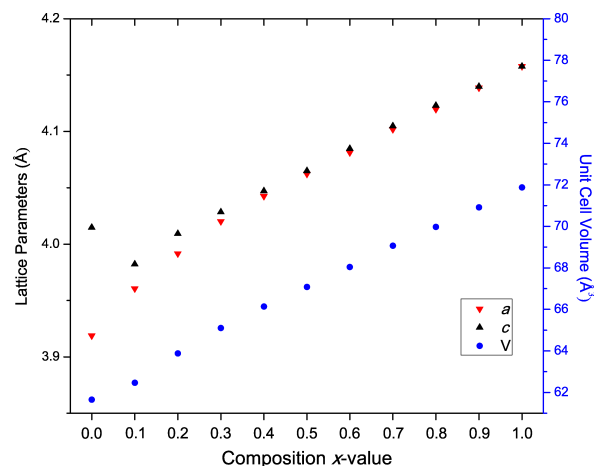

**Fig. 4** The lattice parameters extracted from Rietveld refinement across the solid-solution with  $a$  (red  $\nabla$  triangles),  $c$  (black  $\Delta$  triangles) and unit cell volume  $V$  (blue circles). For  $x = 1$  only, the data were modelled in cubic  $Pm\bar{3}m$  hence  $a$  and  $c$  are equal. Error bars are smaller than symbols.


studies, but is a known behaviour of relaxor ferroelectric compounds, in which the presence of polar nano-regions creates a distribution of ferroelectric domains and hence a range of transition temperatures<sup>27–29</sup>; and is in agreement with the broad peak in dielectric measurements reported by Bengagi *et al.*<sup>16</sup>. Around  $T_C$ , from 633 to 693 K, a two-phase model in Rietveld refinement was used to track the behaviour of the coexisting phases. This region is highlighted by the shaded area in Figure 6.

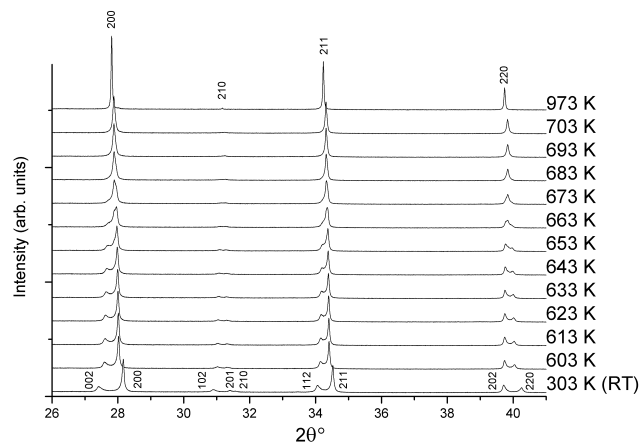

**Fig. 5** Variable-temperature SXRD patterns from  $26^\circ$  to  $41^\circ$  showing the tetragonal to cubic transition with indexed peaks.

Figure 6 shows the Rietveld-refined lattice parameters as the sample is heated from room temperature. The  $a$  and  $c$  parameters of the tetragonal phase converge to the common



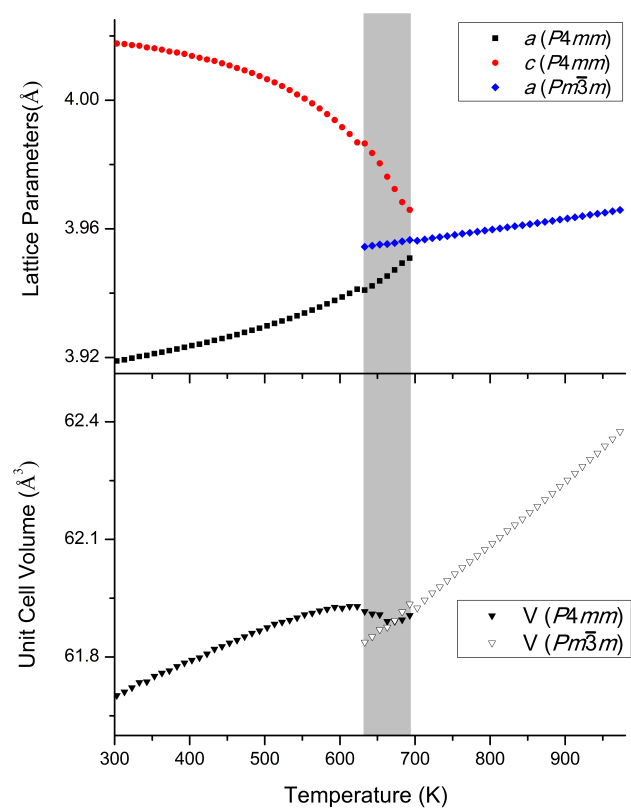

**Fig. 6** Evolution of lattice parameters for KBT obtained from Rietveld refinements against SXRD data. The grey region indicates the temperature range in which the tetragonal and cubic phases coexist.

$a$  parameter of the cubic phase in an essentially continuous second order manner, but with the unusual addition of a narrow coexistence region close to  $T_C$ , the origin of which is discussed above. Another unusual feature is the lattice volume contraction from the tetragonal to the cubic phase. We can rationalise this by considering the relationship between bond length and bond strength, which in solid-state chemistry is commonly considered in terms of effective bond valence sum (BVS) (equation 2):

$$BVS = \sum \left( \exp \left( \frac{R_0 - R_i}{b} \right) \right) \quad (2)$$

where  $R_0$  is an empirically determined constant for a particular type of bond,  $R_i$  the actual bond length, and  $b$  a constant (normally  $0.37 \text{ \AA}$ )<sup>30</sup>. In the tetragonal phase, the A-site and B-site cations are offset from the centres of their 12-fold or 6-fold coordination environments respectively, bringing them closer to some O anions and further from others. Due to the exponential nature of equation 2, this increases the total BVS compared to when those cations are at the centres of their co-


ordination environments in the cubic phase. Thus, when the structure becomes cubic above  $T_C$ , the size of those coordination environments (hence the unit cell volume) must decrease in order to maintain the same BVS. The volume drop in the tetragonal phase within the shaded region is an unrelated artefact of the two-phase refinement, due to the imperfect deconvolution of peak widths, peak separation and phase fractions.

### 3.3 XANES

Relaxor ferroelectrics have complex behaviour due to their locally mixed compositions, sizes and charges across the crystal lattice<sup>29</sup>. While diffraction provides a good measure for the average crystal structure, knowledge of the local structure is crucial to understanding the behaviour of solid-solution ferroelectrics. We have used XANES as a probe of the local coordination environment. Changes in local cation environments cause changes in orbital hybridisation, which manifest as peak shifts and intensity changes at the metal absorption edges. The Ti K-edge is particularly sensitive to the oxidation state and coordination environment of Ti in systems such as these<sup>14</sup>.

Normalised Ti K-edge spectra across the KBT-KBZ solid-solution are shown in Figure 7 (note that for  $x = 0.9$ , statistics were too poor to obtain usable data). There are two major features: the main edge feature (labelled A); and a pre-edge feature (labelled B1-B4). Feature A corresponds to the dipole-allowed transition of a 1s electron into unoccupied 4p states<sup>14</sup>. The line shape of A implies minor changes to the hybridisation of Ti 4p states with the bonding states of nearest- and next-nearest neighbouring atoms, largely due to the introduction of Zr content. Although small intensity changes are observed in the main peak A, likely due to replacing Ti 4p states with Zr 5p states, the lack of a shift in the main edge energy confirms that Ti remains tetravalent - *i.e.*, there is no evidence for oxygen vacancies<sup>14</sup>.

More subtle information about the coordination environment can be obtained by analysing the forbidden transitions in the pre-edge region. The pre-edge features arise from a dipole-forbidden transition of a 1s electron into unoccupied 3d states<sup>31</sup>. The first pre-edge feature, B1, corresponds to the dipole-forbidden transition of a 1s electron into the  $t_{2g}$  states for octahedrally coordinated Ti and remains largely the same with increasing Zr content. The higher-energy features B2 and B3 arise from a dipole-allowed transition from 1s to 3d-4p  $e_g$  states. This 3d-4p mixing occurs from the Ti off-centering inside the octahedra, breaking the octahedral crystal field symmetry into two states,  $d_{xz}$ ,  $d_{yz}$  (B2) and  $d_{xy}$  (B3), which are forbidden for centrosymmetric coordination environments (a regular octahedron)<sup>31,32</sup>. Similarly to previously reported Zr doping effects on NBT, a small increase is observed in B2 suggesting that the Ti-offset increases slightly with increasing Zr

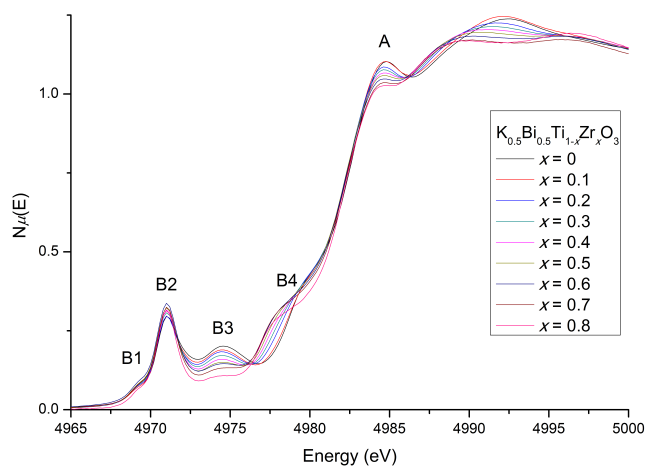


**Fig. 7** The Ti K-edge (A) including the distinct pre-edge features (B1-B4). No energy shifts are observed at the main edge, but pre-edge changes indicate an increasingly centrosymmetric environment for the B-site with increasing Zr content, while the Ti  $4^{+}$  cation distortion remains largely unchanged.

content<sup>13,14</sup>. Together, B3 and B4 are sensitive to the local ratio of Ti/Zr around the absorbing atom, and therefore to local clustering<sup>13</sup>. In the present case, B3 gradually decreases as Ti content decreases; while B4 increases as Zr content increases. These systematic trends suggest that Ti/Zr atoms are randomly distributed in the lattice<sup>13,14</sup>, with no significant clustering. The local crystal structure from  $x = 0.5$  to 0.9 (previously reported as cubic<sup>16</sup>) does not appear to ever become completely centrosymmetric, with Ti remaining off-centered. This is consistent with our high-resolution SXRD diffraction results, and the observation of weak ferroelectricity up to  $x = 0.9$  by Bengali *et al.*<sup>16</sup>.

The Ti L-edge and Zr L-edge transitions correspond to the dipole-allowed transition of a Ti or Zr 2p electron into the unoccupied d states and hence probes the B-site distortion<sup>23,33</sup>. Changes in line shape with composition for the L-edges of Ti and Zr are shown in Figures 8 and 9 respectively. In Figure 8, the four strong features correspond to the Ti L<sub>3</sub>-edge (two lower-energy transitions labelled A1 and A2) and the L<sub>2</sub>-edge (two higher-energy transitions B1 and B2). The separation between the L<sub>3</sub>- and L<sub>2</sub>-edges comes from spin-orbit splitting of Ti 2p<sub>3/2</sub> (L<sub>3</sub>) and 2p<sub>1/2</sub> (L<sub>2</sub>). In an octahedral environment, the main edge splits into the 3d subbands, corresponding to excitations to the 3d t<sub>2g</sub> (A1 and B1), and e<sub>g</sub> (A2 and B2) orbitals<sup>34</sup>. The L<sub>3</sub>-edge is usually more resolved due to the lifetime-related broadening of the L<sub>2</sub>-edge. Consequently, after normalising the data for the Ti L<sub>3</sub>-edge to A1, one can observe any line shape changes across the solid-solution series measured. Our interest lies in the A2 feature, the e<sub>g</sub> states, which consist of d<sub>z<sup>2</sup></sub> and d<sub>x<sup>2</sup>-y<sup>2</sup></sub> orbitals. These orbitals are

directed toward the ligand and are therefore sensitive to deviations in octahedral symmetry by Ti off-centering. In our normalised Ti L-edge data, peak asymmetry in A2 (less apparent in B2) is observed. This indicates a splitting of the e<sub>g</sub> states due to a deviation from octahedral symmetry (*i.e.*, off-centered Ti<sup>4+</sup>). However, no obvious line shape changes are observed across the solid-solution series. This is consistent with the observed feature B2 in our normalised Ti K-edge data, where there were minimal changes in line shape with changes in composition, suggesting that Zr doping does not affect off-centering of the Ti<sup>4+</sup> cations.

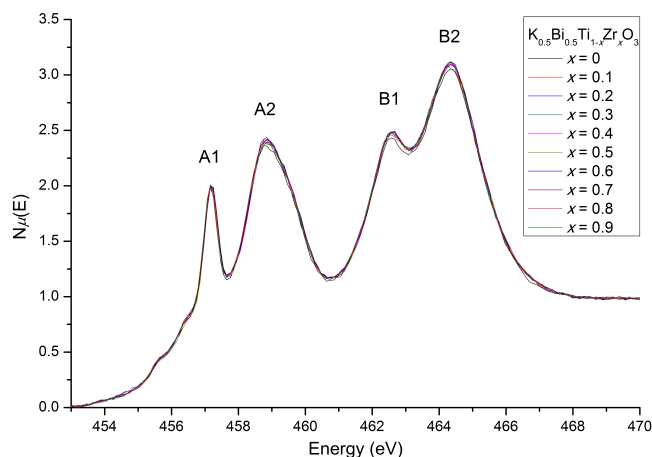


**Fig. 8** Ti L<sub>3</sub>- and L<sub>2</sub>-edges. Asymmetry is observed in peak A2, with no line shape changes across the solid-solution series.

The Zr L<sub>3</sub>-edge (Figure 9) corresponds to the transition of a 2p<sub>3/2</sub> electron into 4d states, which are split into t<sub>2g</sub> (A1) and e<sub>g</sub> (A2) states. Unlike the Ti L-edge, the Zr L<sub>3</sub>-edge line shape changes with Zr doping, particularly with respect to the e<sub>g</sub> state. In general, the asymmetry of the e<sub>g</sub> peak (A2), which is due to the splitting of the 4d e<sub>g</sub> states into 4d<sub>x<sup>2</sup>-y<sup>2</sup></sub> and 4d<sub>z<sup>2</sup></sub> states, decreases with increasing Zr content. This indicates a decrease in Zr<sup>4+</sup> cation off-centering with doping<sup>35-37</sup>. The decrease in peak splitting is more obvious in the first derivative plot of the Zr L<sub>3</sub>-edge shown in Figure 9. Such changes in the Zr environment have been observed for BaTi<sub>1-x</sub>Zr<sub>x</sub>O<sub>3</sub> (BTO-BZO)<sup>14</sup>. The similar behaviour can be explained by similarities in the effective ionic radii (IR) of Ba<sup>2+</sup> and K<sup>+</sup>/Bi<sup>3+</sup> cations. In twelve-coordinate environments, IR(Ba<sup>2+</sup>) = 1.61 Å, mean IR(K<sup>+</sup>, Bi<sup>3+</sup>) = 1.51 Å and mean IR(Na<sup>+</sup>, Bi<sup>3+</sup>) = 1.385 Å. This gives ranges for  $t(\text{BTO-BZO}) = 1.06-1.00$ ,  $t(\text{KBT-KBZ}) = 1.02-0.97$  and  $t(\text{NBT-NBZ}) = 0.98-0.93$ . However, in practice, IR(K<sup>+</sup>, Bi<sup>3+</sup>) is larger due to the asymmetry of the Bi<sup>3+</sup> cation, which brings  $t(\text{KBT-KBZ})$  closer to  $t(\text{BTO-BZO})$ , but still different to  $t(\text{NBT-NBZ})$ .

In contrast, Zr cations did not approach higher symmetry environments in the NBT-NBZ series<sup>14</sup>. This is probably due

to the fact that the end-members were already stabilised in much lower-symmetry environments (rhombohedral, monoclinic and orthorhombic) as discussed above on the basis of calculated tolerance factors. For the KBT-KBZ series under investigation here, the combined results from the normalised metal  $L_3$ -edges suggest that B-site off-centering is reduced with Zr doping. However, it appears that this is due to the  $Zr^{4+}$  cations moving to more symmetric coordination environments, rather than a reduction in Ti off-centering (as shown by the lack of line shape changes in our observed Ti  $L_3$ -edge). This can be rationalised by a cation size effect, where the larger  $Zr^{4+}$  cation environment “pushes” neighbouring  $Ti^{4+}$  environments at low Zr content compositions. At high Zr content, larger cations are more likely to remain centered in the octahedra rather than offset. The dominating presence of larger  $Zr^{4+}$  cations over fewer and smaller  $Ti^{4+}$  cations brings the average B-site closer to centrosymmetric, as shown by diffraction data. However, on a local scale,  $Ti^{4+}$  cations remain offset in the octahedra. This effect was also observed for BTO-BZO<sup>13,14</sup>.

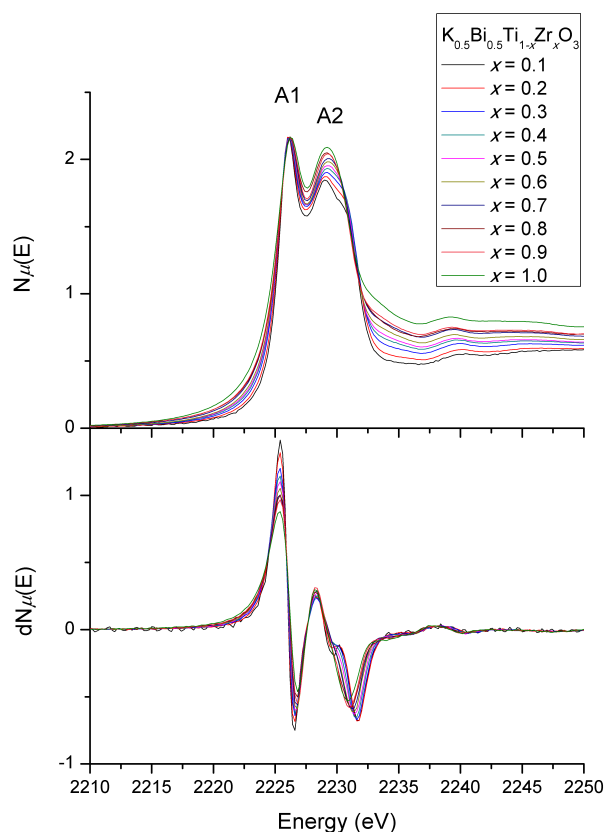

**Fig. 9** Normalised Zr  $L_3$ -edge (upper) showing distinct line shape changes in A2 across the solid-solution series, indicative of increased symmetry with Zr doping. Line shape changes are emphasised by the plot of the first derivative (lower).

In summary, analysis of XANES spectra shows that Zr doping in this series of compounds effectively dilutes the number of non-centrosymmetric environments rather than affecting the Ti-offset directly. This in turn reduces the effective number of polar nano-regions and hence weakens the ferroelectric properties in the material.

## 4 Conclusions

Synchrotron X-ray techniques have provided new insights into the evolution of long- and short-range structure across the solid-solution series  $K_{0.5}Bi_{0.5}Ti_{1-x}Zr_xO_3$ , where  $x = 0$  to 1 with 0.1 steps. Rietveld refinements against high-resolution SXRD data showed that the pseudocubic tetragonal region exists across the whole solid-solution, rather than  $0 < x < 0.4$  as previously observed. Only the pure KBT end member was clearly tetragonal, and only the pure KBZ end member was clearly cubic. On heating through the tetragonal-cubic transition at  $T_C$ , a narrow region of tetragonal and cubic phase coexistence was observed despite the overall continuous second-order nature of the transition. This was explained by the presence of polar nanoregions in these relaxor ferroelectric perovskites. A marked volume contraction from the tetragonal to the cubic phase was explained in terms of the bonding (BVS) requirements of the A-site cation as it moves from an off-centered to a centered location. A future transmission electron microscopy study, such as has been carried out on the KBT end-member,<sup>27</sup> might be able to reveal direct evidence of these polar nanoregions.

Analysis of metal L-edge XANES data across the solid-solution series revealed that  $Ti^{4+}$  cations remain off centered with increasing Zr content, while  $Zr^{4+}$  cations approach a higher symmetry coordination environment. Ti K-edge data showed a similar lack of change in the Ti off-centering. We can therefore conclude that Zr doping has a minimal effect on Ti off-centering, but rather, increases the centrosymmetry of the Zr local coordination environment with its size leading to a reduction in polar domains and hence diminished ferroelectric response.


## 5 Acknowledgements

Work at the Australian Synchrotron was performed with the assistance of Dr Helen Brand at the powder diffraction beamline, and Dr Bruce Cowie and Dr Anton Tadich at the Soft X-ray Spectroscopy beamline. Work at the National Synchrotron Radiation Research Center (NSRRC) was performed with the assistance of Dr Ling-Yun Jang and supported by the Australian Synchrotron International Access Program. CDL and BJK acknowledge the Australian Research Council and AINSE for financial support.



## References

- 1 P. Halasyamani, *Chemistry of Materials*, 2004, **16**, 3586–3592.
- 2 R. Cohen, *Nature*, 1992, **358**, 136–138.
- 3 P. S. Halasyamani and K. R. Poeppelmeier, *Chemistry of Materials*, 1998, **10**, 2753–2769.
- 4 B. Jaffe, R. Roth and S. Marzullo, *Journal of Research of the National Bureau of Standards*, 1955, **55**, 239–254.
- 5 K. S. Wallwork, B. J. Kennedy and D. Wang, Synchrotron Radiation Instrumentation, Pts 1 and 2, 2 Huntington Quadrangle, STE 1NO1, Melville, NY 11747-4501 USA, 2007, pp. 879–882.
- 6 V. Isupov, *Ferroelectrics*, 2005, **315**, 123–147.
- 7 O. Elkechai, M. Manier and J. Mercurio, *Physica Status Solidi A-Applied Research*, 1996, **157**, 499–506.
- 8 V. Bogatko, Y. Venevtsev and A. Abramova, *Inorganic Materials*, 1980, **16**, 72–74.
- 9 J. Gomah-Petry, A. Salak, P. Marchet, V. Ferreira and J. Mercurio, *Physica Status Solidi B-Basic Research*, 2004, **241**, 1949–1956.
- 10 J. Gomah-Petry, P. Marchet, A. Simon, R. Von der Muhll, M. Maglione and J. Mercurio, *Integrated Ferroelectrics*, 2004, **61**, 155–158.
- 11 V. Dorcet, P. Marchet, O. Pena and G. Trolliard, *Journal of Magnetism and Magnetic Materials*, 2009, **321**, 1762–1766.
- 12 R. Shannon, *Acta Crystallographica Section A*, 1976, **32**, 751–767.
- 13 I. Levin, E. Cockayne, V. Krayzman, J. Woicik, S. Lee and C. Randall, *Phys. Rev. B*, 2011, **83**, 094122.
- 14 P. E. R. Blanchard, S. Liu, B. J. Kennedy, C. D. Ling, Z. Zhang, M. Avdeev, L.-Y. Jang, J.-F. Lee, C.-W. Pao and J.-L. Chen, *Dalton Transactions*, 2014, **43**, 17358–17365.
- 15 Y. Yamada, T. Akutsu, H. Asada, K. Nozawa, S. Hachiga, T. Kurosaki, O. Ikagawa, H. Fujiki, K. Hozumi, T. Kawamura, T. Amakawa, K. Hirota and T. Ikeda, *Japanese Journal of Applied Physics Part 1-Regular Papers Short Notes & Review Papers*, 1995, **34**, 5462–5466.
- 16 M. Bengagi, F. Morini, M. El Maaoui and P. Marchet, *Physica Status Solidi A-Applications and Materials Science*, 2012, **209**, 2063–2072.
- 17 K. S. Wallwork, B. J. Kennedy and D. Wang, Synchrotron Radiation Instrumentation, Pts 1 and 2, 2 Huntington Quadrangle, STE 1NO1, Melville, NY 11747-4501 USA, 2007, pp. 879–882.
- 18 G. Jones, J. Kreisel and P. Thomas, *Powder Diffraction*, 2002, **17**, 301–319.
- 19 A. Larson and R. V. Dreele, *General Structure Analysis System (GSAS)*, 2000.
- 20 B. Toby, *Powder Diffraction*, 2006, **21**, 67–70.
- 21 K. Momma and F. Izumi, *Journal of Applied Crystallography*, 2008, **41**, 653–658.
- 22 B. C. C. Cowie, A. Tadich and L. Thomsen, SRI 2009: The 10th International Conference on Synchrotron Radiation Instrumentation, 2 Huntington Quadrangle, STE 1NO1, Melville, NY 11747-4501 USA, 2010, pp. 307–310.
- 23 G. Henderson, X. Liu and M. Fleet, *Physics and Chemistry of Minerals*, 2002, **29**, 32–42.
- 24 T. Dann, S. Chung, L. Huang, J. Juang, C. Chen and K. Tsang, *Journal of Synchrotron Radiation*, 1998, **5**, 664–666.
- 25 T. Schneller, H. Kohlstedt, A. Petraru, R. Waser, J. Guo, J. Denlinger, T. Learmonth, P.-A. Glans and K. E. Smith, *Journal of Sol-gel Science and Technology*, 2008, **48**, 239–252.
- 26 B. Ravel and M. Newville, *Journal of Synchrotron Radiation*, 2005, **12**, 537–541.
- 27 M. Otonicar, S. D. Skapin, B. Jancar, R. Ubic and D. Suvorov, *Journal of the American Ceramic Society*, 2010, **93**, 4168–4173.
- 28 A. Bokov and Z. Ye, *Journal of Materials Science*, 2006, **41**, 31–52.
- 29 L. Cross, *Ferroelectrics*, 1987, **76**, 241–267.
- 30 I. D. Brown and D. Altermatt, *Acta Crystallographica, Section B: Structural Science.*, 1985, **B41**, 244–247.
- 31 D. M. Pickup, E. A. Abou Neel, R. M. Moss, K. M. Wetherall, P. Guerry, M. E. Smith, J. C. Knowles and R. J. Newport, *Journal of Materials Science-Materials in Medicine*, 2008, **19**, 1681–1685.
- 32 V. R. Mastelaro, P. P. Neves, A. Michalowicz and J. A. Eiras, X-Ray Absorption Fine Structure-XAFS13, 2 Huntington Quadrangle, STE 1NO1, Melville, NY 11747-4501 USA, 2007, pp. 496–498.
- 33 P. Nachimuthu, S. Thevuthasan, E. Adams, W. Weber, B. Begg, B. Mun, D. Shuh, D. Lindle, E. Gullikson and R. Perera, *Journal of Physical Chemistry B*, 2005, **109**, 1337–1339.
- 34 V. Mastelaro, P. Neves, S. de Lazaro, E. Longo, A. Michalowicz and J. Eiras, *Journal of Applied Physics*, 2006, **99**, year.
- 35 H. Ikeno, M. Krause, T. Hoeche, C. Patzig, Y. Hu, A. Gawronski, I. Tanaka and C. Ruessel, *Journal of Physics-Condensed Matter*, 2013, **25**, year.
- 36 P. E. R. Blanchard, S. Liu, B. J. Kennedy, C. D. Ling, Z. Zhang, M. Avdeev, B. C. C. Cowie, L. Thomsen and L.-Y. Jang, *Dalton Transactions*, 2013, **42**, 14875–14882.
- 37 E. Reynolds, P. E. R. Blanchard, B. J. Kennedy, C. D. Ling, S. Liu, M. Avdeev, Z. Zhang, G. J. Cuello, A. Tadich and L.-Y. Jang, *Inorganic Chemistry*, 2013, **52**, 8409–8415.

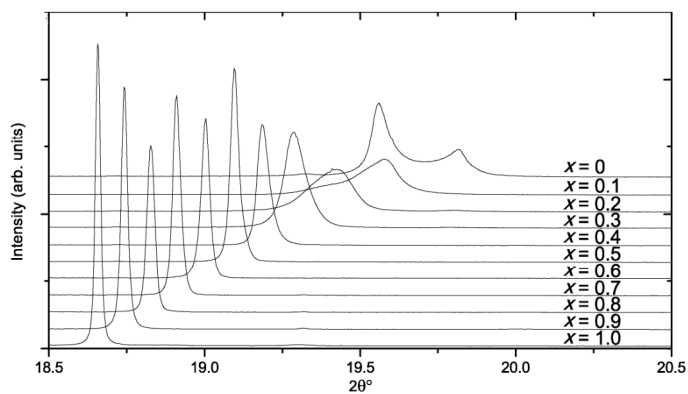

Synchrotron X-ray powder diffraction patterns of  $\text{K}_{0.5}\text{Bi}_{0.5}\text{Ti}_{1-x}\text{Zr}_x\text{O}_3$  (KBT-KBZ), showing the pseudocubic tetragonal region at all intermediate compositions in the solid-solution.