



Field and dilution effects on the magnetic relaxation behaviours of a 1D dysprosium(III)-carboxylate chain built from chiral ligands

Journal:	<i>Dalton Transactions</i>
Manuscript ID:	DT-COM-12-2014-003980.R1
Article Type:	Communication
Date Submitted by the Author:	13-Apr-2015
Complete List of Authors:	Zheng, Yan-Zhen; Xi'an Jiaotong University, Frontier Institute of Science and Technology Han, Tian; Xi'an Jiaotong University, Frontier Institute of Science and Technology Leng, Ji-Dong; Sun Yat-Sen University, School of Chemistry and Chemical Engineering, Ding, You-Song; Xi'an Jiaotong University, Frontier Institute of Science and Technology Wang, Yanyan; Jilin University, College of Chemistry Zheng, Zhiping; University of Arizona, Department of Chemistry

COMMUNICATION

Field and dilution effects on the magnetic relaxation behaviours of a 1D dysprosium(III)-carboxylate chain built from chiral ligands

Cite this: DOI: 10.1039/x0xx00000x

Received 00th January 2012,
Accepted 00th January 2012Tian Han,^a Ji-Dong Leng,^a You-Song Ding,^a Yanyan Wang,^a Zhiping Zheng^{a,b} and Yan-Zhen Zheng^{*a}

DOI: 10.1039/x0xx00000x

www.rsc.org/

A one-dimensional dysprosium(III)-carboxylate chain in which the Dy^{III} ions sit in pseudo D_{2d} -symmetry environment is synthesized and shows different slow magnetic relaxation behaviours depending on the field and dilution effects. Besides, the chiral ligand introduces the additional functions of Cotton effect and polarization for this compound.

Since the discovery of mononuclear lanthanide complexes functioning as single molecule magnets (SMMs),¹ lanthanide ions with large orbital momentum and strong magnetic anisotropy are broadly used in developing new generation molecule-based magnetic information storage materials.² Amongst these molecular materials dysprosium(III)-based complexes are particularly popular due to the inherent strong spin-orbital coupling effect and hence very high magnetic anisotropy of the $^6H_{15/2}$ state with ground Kramers doublet.³⁻⁵ The magnetic anisotropy of the Dy^{III} ions is significantly affected by the coordination geometry and the strength of ligand field, which governs the barrier height of the Dy^{III} ions for magnetization-reversal.⁶

Other than the dominated single-ion behaviour the intriguing roles of magnetic exchange-coupling and dipole-dipole interactions between the $4f$ ions are complicated. As shown by several groups, on one hand, weak magnetic interaction between the $4f$ ions allows quantum tunneling effect that mitigates the full potential of magnetic blocking,^{3i,7} while on the other hand, strong magnetic exchange enhances the slow magnetic relaxation.^{3h,8} Hitherto, understanding the nature of the magnetic relaxation in Dy^{III}-based mononuclear SMMs remains challenging, especially when the lanthanide ions are chemically linked.

For structurally one-dimensional (1D) Dy^{III}-systems, dynamic magnetic behaviour may be observed.^{4,5} However, due to the subtle magnetic exchange-coupling between the lanthanide centres, whether the relaxation is underpinning by the single-ion or single-chain magnetic origin is debatable. To thoroughly understand the magnetic dynamics of these 1D chain systems magnetic dilution is thus essential.⁹ Uniquely, magnetic dilution in molecular systems can be successfully accomplished by doping of chemically-identical diamagnetic metal ions (i.e. Y^{III}), which was highlighted in some mononuclear and polynuclear lanthanide molecular magnets.^{1,3e,3i,7} Moreover, the introduction of chirality might bring multi-

functionality to the system such as ferroelectricity and magneto-optical coupling effect.¹⁰

Pursuing these clues, we report herein the syntheses, structures and magnetic properties of a 1D dysprosium(III)-carboxylate compound $\{[\text{Dy}(\text{L})_3(\text{H}_2\text{O})]\cdot 5\text{H}_2\text{O}\}_n$ (**1**) and its 50% diluted sample $\{[\text{Dy}_{0.5}\text{Y}_{0.5}(\text{L})_3(\text{H}_2\text{O})]\cdot 5\text{H}_2\text{O}\}_n$ (**2**) (HL = D(-)-quinic acid). Slow relaxation of magnetization can be modulated as suppressing the quantum tunneling effect differently by field and/or dilution.

The reaction of D(-)-quinic acid with $\text{Dy}(\text{NO}_3)_3\cdot 6\text{H}_2\text{O}$ in water-acetonitrile, in the presence of Et_3N , affords well shaped colorless needle-like crystals. Single-crystal X-ray structural study at 150 K indicates that **1** belongs to monoclinic system with $P2_1$ space group. Crystallographic data, structure refinement, selected bonds and angles are listed in Tables S1 and S2 (ESI). The Dy^{III} ion is eight coordinated, surrounded by oxygen atoms, six of which come from three chelating ligands, one from μ_2 bridging ligand and one from coordinated water molecule (Figs. 1 and S1, ESI). In literature, the geometries of eight-coordinate Dy^{III} ions are mostly taking symmetries such as the D_{2d} -dodecahedron (DD), C_{2v} -bicapped trigonal prism (TP) and D_{4d} -square antiprism (SAP). Continuous symmetry measure (CSM) method for **1** indicates that the DD geometry is the closest one (*cacl.d.* values: D_{2d} , 0.961; D_{4d} , 1.716; C_{2v} , 2.289).¹¹ Further study using the semi-quantitative method of polytopal analysis according to the relevant dihedral angles in Table S3 (ESI) confirms the Dy^{III} ion in **1** has the distorted D_{2d} local symmetry.¹² The neighboring Dy^{III} ions are singly bridged by μ - η^1 : η^1 carboxylic groups in *syn-anti* mode to form one-dimensional infinite chain, resulting the Dy \cdots Dy distance of 6.085 Å. Adjacent chains are further expanded to a 3D supramolecular architecture *via* strong hydrogen bonds between the water molecules and the quinate ligands with the O \cdots O distances ranging from 2.608(3) to 3.231(4) Å (Fig. S2, ESI). The nearest interchain Dy \cdots Dy separation is 10.5635(4) Å.

Meanwhile, the Y^{III} doped sample $\{[\text{Dy}_{0.5}\text{Y}_{0.5}(\text{L})_3(\text{H}_2\text{O})]\cdot 5\text{H}_2\text{O}\}_n$ (**2**) is prepared to modulate the magnetic properties. Inductively coupled plasma (ICP) measurement is thus necessary to study the composition precisely. That the exact ratio for Dy^{III}:Y^{III} is 1.04:1.00 is perfectly consistent with the starting stoichiometry in the synthesis. The single-crystal structural data indicates compound **2** is isostructural to **1** with indistinguishable metal centres (Table S4, ESI). The good agreement of powder X-ray diffraction patterns

between **1** and **2** further confirms the phase purity of the bulk materials (Fig. S3, ESI).

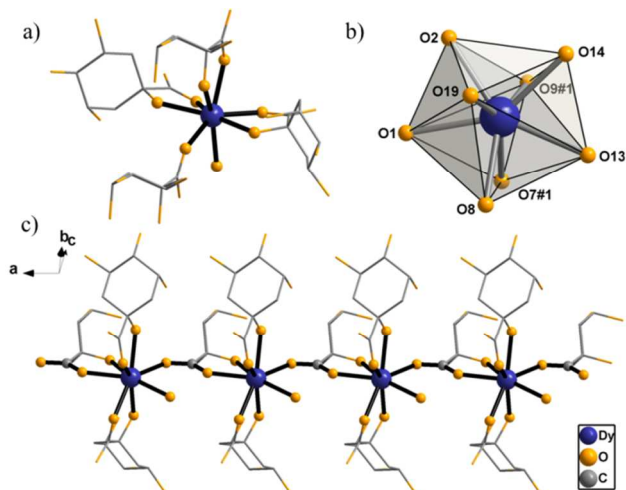


Fig. 1 a) Local structure of **1**; b) The coordination polyhedron of Dy^{III} in **1**; c) 1D chain structure of **1**. Symmetry code: #1 $x+1,y,z$.

Dc magnetic susceptibility data of **1** and **2** are measured in an applied field of 2 kOe and in the temperature range of 2–300 K (Fig. 2). At 300 K, the $\chi_M T$ product of **1** is $14.54 \text{ cm}^3 \text{ K mol}^{-1}$, close to $14.17 \text{ cm}^3 \text{ K mol}^{-1}$ expected for one Dy^{III} ion ($S = 5/2$, $L = 5$, $J = 15/2$ and $g = 4/3$). Upon cooling, the $\chi_M T$ products keep constant until 30 K, and then decrease sharply to the minimum of $10.02 \text{ cm}^3 \text{ K mol}^{-1}$ at 2 K. For **2**, the $\chi_M T$ product $14.39 \text{ cm}^3 \text{ K mol}^{-1}$ at 300 K accords well with the expected value. Upon cooling, similar behaviour of the temperature-dependent $\chi_M T$ products is observed, but the lowest value $9.35 \text{ cm}^3 \text{ K mol}^{-1}$ at 2 K is slightly smaller than the undoped sample. Because the coordination environments of the Dy^{III} ions remain unchanged, comparison of magnetic data of **2** with that of **1** could reveal that ferromagnetic interaction in the system is weakened by the dilution method.

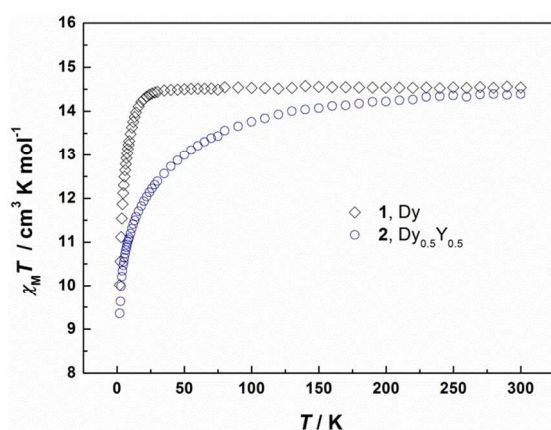


Fig. 2 $\chi_M T$ as a function of temperature in an applied field of 2 kOe for **1** and **2**. The $\chi_M T$ curve of **2** has been rescaled for one Dy^{III} ion.

The field dependences of magnetization for both compounds have been determined at low temperatures. Upon applying the magnetic field, magnetizations increase up to maximum values of 7.18 and 6.03 N β at 70 kOe and 2 K for **1** and **2**, respectively, without saturation. This may be due to the large magneto-anisotropy and/or low lying excited states of the Dy^{III} ions, as also proved by the non-superposition on $M/N\beta$ versus HT^{-1} plots at various temperatures in **1** (Fig. S4, ESI).

To further explore the dynamics of magnetization, ac magnetic susceptibilities as functions of both temperature and frequency are studied for both samples. For **1**, a significant frequency dependence of ac signals can be observed in zero dc field, indicating slow relaxation of magnetization, but unfortunately, no maximum of peak is found in both the in-phase (χ') and out-of-phase (χ'') ac signals, which is possible due to the tunneling of the magnetization (QTM) (Fig. 3a). As the application of external magnetic field can suppress the QTM effect,^{3,7,13} subsequent ac measurements were taken under various dc fields (Fig. S5, ESI).

At $H_{dc} = 500 \text{ Oe}$ obvious peaks of the χ'' data can be detected, and move to higher temperature as increasing the frequency, clearly showing frequency dependent behavior (Fig. S6, ESI). A peak tail at low temperatures is indicative of QTM often reported in lanthanide SMMs.^{1,3,6-9,14} The ac susceptibility as a function of frequency with varying temperatures reveals two independent relaxation domains. Relaxation in domain #1 shifts from low frequency to high frequency upon warming, while relaxation domain #2 involves high frequencies with temperature independent feature (Fig. S7, ESI). When the relaxation time (τ) is plotted as $\ln\tau$ vs. $1/T$ (Fig. 3b), one thermally activated regime (pathway A) and a gradual crossover to the temperature independent relaxation regime (pathway B, $\tau = 76 \text{ ms}$ at 2.0 K, indicative of a QTM process) in domain #1, and relaxation at $\tau \approx 0.3 \text{ ms}$ in domain #2 (pathway C) are obtained.¹⁵ Analysis of the data for thermally activated regime (A) using the Arrhenius law gives a pre-exponential factor of $\tau_0 = 1.6 \times 10^{-10} \text{ s}$ and an effective energy gap of $U_{eff} = 55.8 \text{ K}$. Cole–Cole plots suggest that relaxation domains #1 and #2 are both well-defined at low temperatures, and begin to merge above 3.0 K as the peak of χ'' in domain #1 shifts to high frequency (Fig. S8, ESI). At higher temperature, thermally activated pathway A is dominant.

When increasing the dc field to 1 kOe, the process in relaxation domain #2 is eliminated, leaving only one uniformed relaxation domain (Fig. S5, ESI). The ac susceptibilities as functions of both temperature and frequency at 1 kOe confirm the remaining processes in relaxation domain #1 (Figs. 3a and S9, ESI). As temperature decreases from 4.0 to 3.0 K, the maximum in χ'' moves gradually to lower frequency, falling into an Arrhenius-like behavior region (pathway A, $\tau_0 = 1.1 \times 10^{-9} \text{ s}$ and $U_{eff} = 48.2 \text{ K}$). Below 3.0 K, the relaxation is dominated by a quantum tunneling process (pathway B, $\tau = 107 \text{ ms}$ at 2.0 K) (Fig. 3b). Cole–Cole plots at different temperatures show one semicircle (Fig. S10, ESI). The ac measurements indicate that one of the relaxation processes at high frequencies with temperature independent feature can be suppressed by applying a static magnetic field.

Slow magnetic relaxation in a ferromagnetic 1D dysprosium chain through double *syn-anti* carboxylic groups originating from the single-ion behaviour of Dy^{III} has been evidenced by the group of Gao,⁹ in which the closest Dy \cdots Dy distance is 1 Å shorter than that in **1** bridged by single *syn-anti* carboxylic group. Weaker intrachain exchange coupling of **1** further clarifies the domination of single-ion anisotropy in thermal relaxation. It is well known that magnetic interactions with the neighbouring motif can greatly influence the quantum tunneling of magnetization in discrete molecules,^{3,6-8,16} but the doping effect in 1D lanthanide chain is still poorly understood.⁹

Herein we study the ac magnetic property of doped sample **2**, with 50% concentration of the dopant ion to modulate the relaxations. In the plot of χ'' data versus ν at 2 K for **2** under various dc fields, the peak with a maximum shifts from 162 Hz at 0 Oe to 0.56 Hz at 1 kOe dc field (Fig. S11, ESI). Surprisingly, when further increasing the dc field, a broad peak shows up and then separates into two sets, one of which resides at about 0.5 Hz, and the other of which displays strong field dependence with increasing frequency toward higher field.

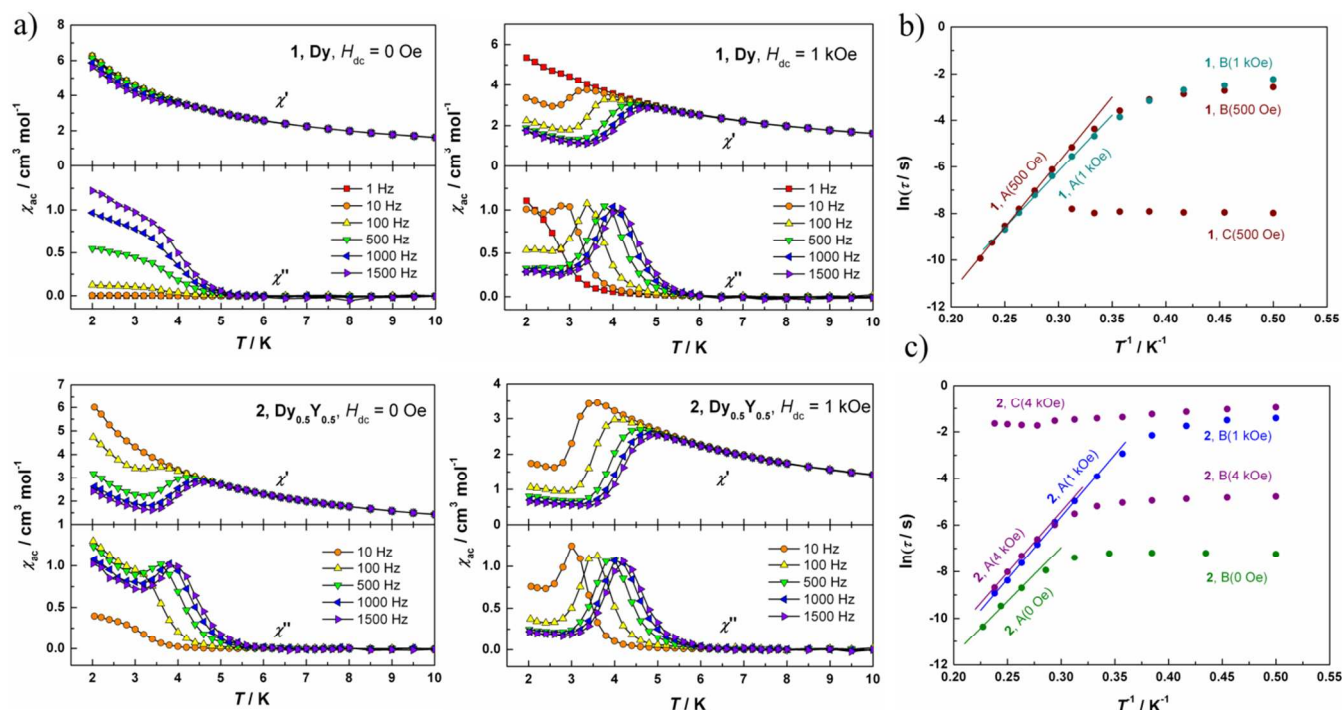


Fig. 3 a) Temperature dependence of the in-phase and out-of-phase ac susceptibility for **1** and **2** under 0 or 1 kOe dc field. b) Plots of $\ln(\tau)$ vs. $1/T$ for **1** at $H_{dc} = 500 \text{ Oe}$ and 1 kOe . c) Plots of $\ln(\tau)$ vs. $1/T$ for **2** at $H_{dc} = 0, 1 \text{ kOe}$ and 4 kOe . The solid lines represent Arrhenius fits of the frequency-dependent data.

As shown in Figs. 3a and S12 (ESI), Y(III) diluted sample **2** exhibits significant temperature and frequency dependent behaviour with a peak maximum which is absent in **1** in a zero dc field. Furthermore, the tail in $\chi''(T)$ plot below 3.0 K shows strong frequency dependence with increasing intensity toward lower frequency (except 10 Hz). This indicates that QTM effect, albeit remains, is efficiently reduced by dilution. Temperature independent peaks signaling the quantum tunneling region (pathway B) can be observed, ranging from 2.0 K to 3.2 K , with relaxation time of about 0.7 ms , which is much shorter than the one in **1** at applied dc fields. At higher temperatures, the relaxation obeys Arrhenius law (pathway A), affording $\tau_0 = 9.4 \times 10^{-10} \text{ s}$ and $U_{\text{eff}} = 46.1 \text{ K}$ (Fig. 3c). Semicircle Cole–Cole plots suggest the relaxation domain #1 is present (Fig. S13, ESI).

With an external field of 1 kOe , single peak remains, and the tail in $\chi''(T)$ plot almost disappears at low temperature, indicating a more efficient suppression of QTM (Figs. 3a and S14, ESI). The temperature dependence of the relaxation time in the range of 3.0 – 4.2 K follows an activated Arrhenius law (pathway A), giving $\tau_0 = 3.8 \times 10^{-10} \text{ s}$ and $U_{\text{eff}} = 53.5 \text{ K}$ (Fig. 3c). Deviation from linearity due to the quantum tunneling process (pathway B, $\tau = 244 \text{ ms}$ at 2.0 K) is observed below 3.0 K . The Cole–Cole plots imply a single relaxation domain (Fig. S15, ESI).

At 4 kOe , two independent relaxation domains, one at high frequencies (3 – 1500 Hz , relaxation domain #1) and the other at lower frequencies (0.1 – 3 Hz , relaxation domain #2) appear (Figs. S16 and S17, ESI).¹⁵ Relaxation domain #1 involves thermally activated process (pathway A) with $\tau_0 = 6.8 \times 10^{-10} \text{ s}$ and $U_{\text{eff}} = 52.3 \text{ K}$ and temperature independent regime (pathway B, $\tau = 8 \text{ ms}$ at 2.0 K) (Fig. 3c). Relaxation domain #2 shows relatively little temperature dependence and field dependence (pathway C). Its relaxation time (ca. 300 ms) is 3 orders of magnitude slower than that of domain #1, and no asymmetry is in Cole–Cole plots for this process (Fig. S18, ESI).

Taken together, field and dilution effects result in a various degree of reduction in the quantum tunneling (Fig. S19, ESI). Interestingly,

multiple relaxation modes are observed and accessible through the application of dc fields, as reported in mononuclear SMMs.¹⁵ However, due to the absence of peak maximum in ac measurements for $5\% \text{ Dy}$ sample, further experiments and theoretical calculation to investigate the detailed impact of dilution on the dynamic properties are necessary.

Given that **1** crystallises in a chiral space group $P2_1$ at room temperature (Table S5, ESI) while it belongs to a point group of C_2 falling into one of 10 polar point groups, its optical and ferroelectric properties were investigated at room temperature. As shown in Fig. 4, both the circular dichroism (CD) spectra for the ligand in an aqueous solution and compound **1** in the solid state exhibit strong positive Cotton effect at $\sim 240 \text{ nm}$, denoting significant dichroism associated to the homochiral ligand. Open electric field dependent polarization loop can be clearly, albeit with small remnants, observed for powder pellet sample of **1** (inset Fig. 4), showing the potential ferroelectric behavior.

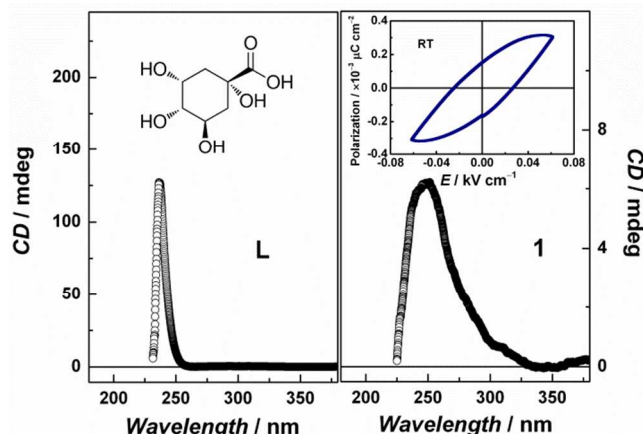


Fig. 4 Circular dichroism spectra for the D-(-)-quinic acid in an aqueous solution (left) and **1** in the solid state (right). Inset: Electric hysteresis loop of **1** at room temperature.

In summary, a novel enantiomer-pure 1D dysprosium chain has been assembled from chiral carboxylate ligand. The Dy^{III} ion in **1** sits in a distorted D_{2d} symmetry, and is bridged by single *syn-anti* carboxylic group to form an infinite chain, which shows very weak ferromagnetic interaction and slow relaxation of the magnetization. By application of a magnetic field and/or dilution, the quantum tunneling is suppressed in various degrees, thereby suggesting the dominated single-ion origin of the slow magnetic relaxation rather than the single-chain dynamics. Thus, a symbol $M^0U^0S^1$ is presumably appropriate to describe such system.¹⁷ Our comparative investigations confirm the plausible fine-tuning of QTM via dilution, which mainly alternates the magnetic interactions between individual metal centres. Moreover, the presence of small remnant in the electric-polarization measurement may bring multiferroic properties to such molecule-based materials.

This work was supported by NSFC (21201137), China Postdoctoral Science Foundation (2014M552425), "National 1000-Plan" program and the Fundamental Research Funds for the Central Universities. This work was also partially supported by the US National Science Foundation (Grant CHE-1152609).


Notes and references

^a Center for Applied Chemical Research, Frontier Institute of Science and Technology, and College of Science, Xi'an Jiaotong University, Xi'an 710054, China. Email: zheng.yanzhen@mail.xjtu.edu.cn

^b Department of Chemistry, The University of Arizona, Tucson, Arizona 85721, USA.

† Electronic Supplementary Information (ESI) available: Complete experimental detail, crystal and refinement details, supporting figures and additional magnetic data. CCDC 1027340 and 1030432. For ESI and crystallographic data in CIF or other electronic format see DOI: 10.1039/c000000x/

- N. Ishikawa, M. Sugita, T. Ishikawa, S. Y. Koshihara and Y. Kaizu, *J. Am. Chem. Soc.*, 2003, **125**, 8694.
- D. N. Woodruff, R. E. P. Winpenny and R. A. Layfield, *Chem. Rev.*, 2013, **113**, 5110.
- (a) P. Zhang, Y. N. Guo and J. K. Tang, *Coord. Chem. Rev.*, 2013, **257**, 1728; (b) Y. N. Guo, G. F. Xu, Y. Guo and J. K. Tang, *Dalton Trans.*, 2011, **40**, 9953; (c) J. K. Tang, I. Hewitt, N. T. Madhu, G. Chastanet, W. Wernsdorfer, C. E. Anson, C. Benelli, R. Sessoli and A. K. Powell, *Angew. Chem. Int. Ed.*, 2006, **45**, 1729; (d) P. H. Lin, T. J. Burchell, R. Clérac and M. Murugesu, *Angew. Chem. Int. Ed.*, 2008, **47**, 8848; (e) S. D. Jiang, B. W. Wang, G. Su, Z. M. Wang and S. Gao, *Angew. Chem. Int. Ed.*, 2010, **49**, 7448; (f) Y. N. Guo, G. F. Xu, P. Gamez, L. Zhao, S. Y. Lin, R. Deng, J. K. Tang and H. J. Zhang, *J. Am. Chem. Soc.*, 2010, **132**, 8538; (g) R. J. Blagg, C. A. Muryn, E. J. L. McInnes, F. Tuna and R. E. P. Winpenny, *Angew. Chem. Int. Ed.*, 2011, **50**, 6530; (h) J. D. Rinehart, M. Fang, W. J. Evans and J. R. Long, *Nat. Chem.*, 2011, **3**, 538; (i) R. J. Blagg, L. Ungur, F. Tuna, J. Speak, P. Comar, D. Collison, W. Wernsdorfer, E. J. L. McInnes, L. F. Chibotaru and R. E. P. Winpenny, *Nat. Chem.*, 2013, **5**, 673; (j) E. M. Fatila, M. Rouzières, M. C. Jennings, A. J. Lough, R. Clérac and K. E. Preuss, *J. Am. Chem. Soc.*, 2013, **135**, 9596; (k) J. Long, F. Habib, P. H. Lin, I. Korobkov, G. Enright, L. Ungur, W. Wernsdorfer, L. F. Chibotaru and M. Murugesu, *J. Am. Chem. Soc.*, 2011, **133**, 5319.
- (a) Y. Z. Zheng, Y. H. Lan, W. Wernsdorfer, C. E. Anson and A. K. Powell, *Chem. Eur. J.*, 2009, **15**, 12566; (b) I. Ratera and J. Veciana, *Chem. Soc. Rev.*, 2012, **41**, 303; (c) L. Bogani, C. Sangregorio, R. Sessoli and D. Gatteschi, *Angew. Chem. Int. Ed.*, 2005, **44**, 5817.
- (a) J. Jung, F. L. Natur, O. Cador, F. Pointillart, G. Calvez, C. Daiguebonne, O. Guillou, T. Guizouarn, B. L. Guennic and K. Bernot, *Chem. Commun.*, 2014, **50**, 13346; (b) Q. Chen, Y. S. Meng, Y. Q. Zhang, S. D. Jiang, H. L. Sun and S. Gao, *Chem. Commun.*, 2014, **50**, 10434; (c) E. Bartolomé, J. Bartolomé, S. Melnic, D. Prodius, S. Shova, A. Arauzo, J. Luzón, F. Luis and C. Turta, *Dalton Trans.*, 2013, **42**, 10153; (d) S. Liu, L. L. Li, H. Li, H. L. Gao, J. Z. Cui and P. Cheng, *Dalton Trans.*, 2015, **44**, 6169.
- (a) J. L. Liu, Y. C. Chen, Y. Z. Zheng, W. Q. Lin, L. Ungur, W. Wernsdorfer, L. F. Chibotaru and M. L. Tong, *Chem. Sci.*, 2013, **4**, 3310; (b) B. Na, X. J. Zhang, W. Shi, Y. Q. Zhang, B. W. Wang, C. Gao, S. Gao and P. Cheng, *Chem. Eur. J.*, 2014, **20**, 15975.
- F. Habib, P. H. Lin, J. Long, I. Korobkov, W. Wernsdorfer and M. Murugesu, *J. Am. Chem. Soc.*, 2011, **133**, 8830.
- (a) J. D. Rinehart, M. Fang, W. J. Evans and J. R. Long, *J. Am. Chem. Soc.*, 2011, **133**, 14236; (b) Y. N. Guo, G. F. Xu, W. Wernsdorfer, L. Ungur, Y. Guo, J. K. Tang, H. J. Zhang, L. F. Chibotaru and A. K. Powell, *J. Am. Chem. Soc.*, 2011, **133**, 11948.
- L. Jia, Q. Chen, Y. S. Meng, H. L. Sun and S. Gong, *Chem. Commun.*, 2014, **50**, 6052.
- (a) Y. X. Wang, W. Shi, H. Li, Y. Song, L. Fang, Y. H. Lan, A. K. Powell, W. Wernsdorfer, L. Ungur, L. F. Chibotaru, M. R. Shen and P. Cheng, *Chem. Sci.*, 2012, **3**, 3366; (b) C. Train, R. Gheorghie, V. Krstic, L. M. Chamoreau, N. S. Ovanesyan, G. L. J. A. Rikken, M. Gruselle and M. Verdagner, *Nat. Mat.*, 2008, **7**, 729.
- (a) H. Zabrodsky, S. Peleg and D. Avnir, *J. Am. Chem. Soc.*, 1992, **114**, 7843; (b) M. Pinsky and D. Avnir, *Inorg. Chem.*, 1998, **37**, 5575.
- (a) E. L. Muetterties and L. J. Guggenberger, *J. Am. Chem. Soc.*, 1974, **96**, 1748. (b) M. G. B. Drew, *Coord. Chem. Rev.*, 1977, **24**, 179.
- (a) J. Ruiz, A. J. Mota, A. Rodríguez-Diéguez, S. Titos, J. M. Herrera, E. Ruiz, E. Cremades, J. P. Costes and E. Colacio, *Chem. Commun.*, 2012, **48**, 7916; (b) Y. Zhu, F. Luo, Y. M. Song, H. X. Huang, G. M. Sun, X. Z. Tian, Z. Z. Yuan, Z. W. Liao, M. B. Luo, S. J. Liu, W. Y. Xu and X. F. Feng, *Dalton Trans.*, 2012, **41**, 6749; (c) Z. Chen, B. Zhao, P. Cheng, X. Q. Zhao, W. Shi and Y. Song, *Inorg. Chem.*, 2009, **48**, 3493.
- N. Ishikawa, M. Sugita and W. Wernsdorfer, *Angew. Chem. Int. Ed.*, 2005, **44**, 2931.
- (a) M. Jeletic, P. H. Lin, J. J. Le Roy, I. Korobkov, S. I. Gorelsky and M. Murugesu, *J. Am. Chem. Soc.*, 2011, **133**, 19286; (b) J. D. Rinehart, K. R. Meihaus, J. R. Long, *J. Am. Chem. Soc.*, 2010, **132**, 7572.
- (a) W. Wernsdorfer, N. Aliaga-Alcalde, D. N. Hendrickson and G. Christou, *Nature*, 2002, **416**, 406; (b) S. Hill, R. S. Edwards, N. Aliaga-Alcalde and G. Christou, *Science*, 2003, **302**, 1015; (c) T. N. Nguyen, W. Wernsdorfer, K. A. Abboud and G. Christou, *J. Am. Chem. Soc.*, 2011, **133**, 20688.
- Y.-Z. Zheng, Z. Zheng and X.-M. Chen, *Coord. Chem. Rev.*, 2014, **258–259**, 1.

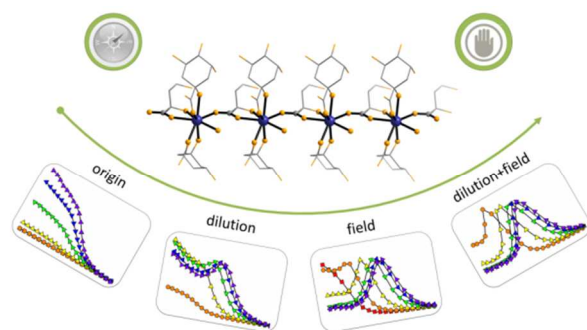

A novel enantiomer-pure dysprosium chain shows various slow magnetic relaxation behaviours depending on the field and dilution effects.