

Energy & Environmental Science

Accepted Manuscript



This is an *Accepted Manuscript*, which has been through the Royal Society of Chemistry peer review process and has been accepted for publication.

Accepted Manuscripts are published online shortly after acceptance, before technical editing, formatting and proof reading. Using this free service, authors can make their results available to the community, in citable form, before we publish the edited article. We will replace this *Accepted Manuscript* with the edited and formatted *Advance Article* as soon as it is available.

You can find more information about *Accepted Manuscripts* in the [Information for Authors](#).

Please note that technical editing may introduce minor changes to the text and/or graphics, which may alter content. The journal's standard [Terms & Conditions](#) and the [Ethical guidelines](#) still apply. In no event shall the Royal Society of Chemistry be held responsible for any errors or omissions in this *Accepted Manuscript* or any consequences arising from the use of any information it contains.

Short-range Li diffusion vs long-range ionic conduction in nanocrystalline lithium peroxide Li_2O_2 — the discharge product in lithium-air batteries

A. Dunst^{1,*}, V. Epp^{1,2,†}, I. Hanzu^{1,2}, S. A. Freunberger¹, and M. Wilkening^{1,2‡}

¹Christian Doppler Laboratory for Lithium Batteries, and Institute for Chemistry and Technology of Materials, Graz University of Technology, Stremayrgasse 9, 8010 Graz, Austria and

²DFG Research Unit 1277, Graz University of Technology, Stremayrgasse 9, 8010 Graz, Austria

(Dated: May 14, 2014)

Understanding charge carrier transport in Li_2O_2 , the storage material in the non-aqueous Li-O₂ battery, is key to the development of this high-energy battery. Here, we studied ionic transport properties and Li self-diffusion in nanocrystalline Li_2O_2 by conductivity and temperature variable ⁷Li NMR spectroscopy. Nanostructured Li_2O_2 , characterized by a mean crystallite size of less than 50 nm as estimated from X-ray diffraction peak broadening, was prepared by high-energy ball milling of microcrystalline lithium peroxide with μm -sized crystallites. At room temperature the overall conductivity σ of the microcrystalline reference sample turned out to be very low ($3.4 \times 10^{-13} \text{ S cm}^{-1}$) which is in agreement with results from temperature-variable ⁷Li NMR line shape measurements. Ball-milling, however, leads to an increase of σ by approximately two orders of magnitude ($1.1 \times 10^{-10} \text{ S cm}^{-1}$); correspondingly, the activation energy decreases from 0.89 eV to 0.82 eV. The electronic contribution σ_{con} , however, is in the order of $9 \times 10^{-12} \text{ S cm}^{-1}$ which makes less than 10% of the total one. Interestingly, ⁷Li NMR lines of nano- Li_2O_2 undergo a pronounced heterogeneous motional narrowing which manifests in a two-component line shape emerging with increasing temperatures. Most likely, the enhancement in σ can be traced back to the generation of a spin reservoir with highly mobile Li ions; these are expected to reside in the nearest neighbourhood of defects generated or near the structurally disordered and defect-rich interfacial regions formed during mechanical treatment.

PACS numbers: 66.30.-h, 76.60.-k, 82.47.Aa, 82.56.-b

Keywords: solid-state NMR, diffusive motion, lithium ion conductors, relaxation NMR, peroxides, impedance spectroscopy

I. INTRODUCTION

The development of new energy storage systems is a vital topic in materials science. In particular, the lithium-air battery causes tremendous interest not only from the part of scientific community but also from an industrial point of view.¹⁻⁵ The theoretical specific energy of the non-aqueous lithium air batteries is ca. 3500 Wh/kg _{Li_2O_2} based on the mass of active materials alone. Therefore, it significantly exceeds that of lithium-ion batteries with conventional insertion materials.⁶⁻¹⁰ Potential key applications, particularly in the long term, include electric vehicles as well as the storage of electricity from intermittent sources such as wind, solar, and tidal.

On discharge, at the positive electrode O₂ from the atmosphere enters the porous electrode, is dissolved in the non-aqueous electrolyte within the pores, and is reduced at the electrode surface forming solid lithium peroxide. Li_2O_2 can be (re-)oxidized upon charging.^{1,7,8,10} The achievable amount of Li_2O_2 that can reversibly be formed upon discharge inside the porous electrode governs the reversible capacity. While the principal possibility to electrochemically form and decompose Li_2O_2 in non-aqueous electrolytes is well established, many challenges remain towards practical application.^{1,2,6-8,11,12} These include stability issues of the electrolyte and the porous electrode that lead to side reactions and compromised cycleability.¹³⁻¹⁹ Typical side reaction products at the cathode are Li_2CO_3 , Li alkyl carbonates and Li carboxylates.^{13,17,20,21}

One other major challenge is how to form a large amount of solid, insulating Li_2O_2 by O₂ reduction in the conductive porous substrate and to effectively oxidize it on charging.²²⁻²⁶ On discharge, formation of a film of insulating Li_2O_2 limits

the film thicknesses to a few nm before electron tunnelling or bulk conduction become ineffective.^{23,24,27} This is because of the poor conductivity estimated for pure Li_2O_2 that is significantly lower than that of other battery materials. In many cases particle growth has been observed that typically leads to particles in the range of 200 to 400 nm composed of a few 10 nm large primary crystallites; this suggests additional transport mechanisms to be in place.^{5,28} On charging a two-stage process has been disclosed involving Li⁺ removal near the surface and bulk Li_2O_2 oxidation at low and high overpotentials, respectively.^{24,25,29} This requires Li motion in the surface region of the Li_2O_2 and electron transport from the Li_2O_2 to the solid electron conducting surface. Electron transport may be relatively easy for Li_2O_2 directly in contact with the surface, but becomes difficult for the majority of Li_2O_2 more remote from the surface. When we consider issues such as the reversibility of the Li peroxide accumulation and removal, it can be seen that transport in the solid state, that is, in the bulk, plays a capital role. In general, enhanced Li diffusion in the bulk may assist for the electrochemical formation as well as the resorbption and dissolution of Li peroxide. Considering recent studies, both electron and ion transport in Li_2O_2 are shown to be critical for the operation of the Li-air battery and improvements require their understanding on a microscopic level.^{5,26,30,31} In particular, it could be shown recently that finely crystalline or amorphous Li_2O_2 decomposes at lower voltages than large particles. The exact reasons, however, have not been identified yet.^{5,31}

In addition to these recent findings, there is a lively debate on charge transport properties in Li_2O_2 in general; several theoretical studies have been published up to now^{23,24,32-35} including also a very recent one on amorphous Li_2O_2 by

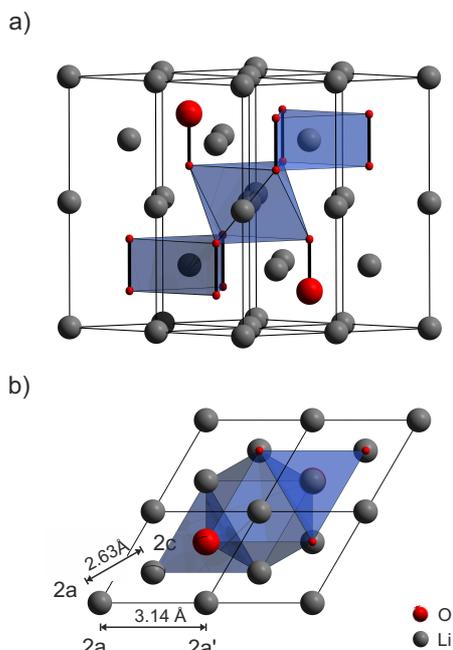


FIG. 1: Crystal structure of Li_2O_2 (hexagonal space group $P6_3/mmc$), see also Ref. 24. a) $2 \times 2 \times 1$ expansion of the unit cell. The covalently bonded O_2 dimers are arranged in an alternating ABAB stacking. There are two unique Li sites indicated by polyhedra. The trigonal prismatic Li is in the same layer as the peroxide anions. The octahedral coordinated one resides between the peroxide layers. b) view along the z-axis showing the Li-Li distances of the two crystallographically inequivalent Li sites 2a and 2c.

Siegel and co-workers.³⁶ As yet, only Maier and co-workers³⁷ have investigated electron and ion transport in microcrystalline Li_2O_2 experimentally by ac impedance spectroscopy and dc measurements; they showed that electronic conduction is governed by hole polarons, and ionic conduction is presumably mediated by negatively charged lithium vacancies; the crystal structure of Li_2O_2 (space group $P6_3/mmc$) is shown in Fig. 1. To our knowledge, there is, so far, no investigation available reporting on activation energies of the elementary hopping processes of individual Li ions. Such information can be made available by nuclear magnetic resonance (NMR) spectroscopy.

The present work is aimed at understanding both short-range and long-range Li ion transport in nanocrystalline Li_2O_2 , that is, a nanostructured sample with mean crystallites having a mean diameter of less than 50 nm which is comparable to that found in electrochemically formed Li_2O_2 . The samples investigated have been prepared *ex situ* via a top-down approach: chemically synthesised microcrystalline lithium peroxide was mechanically treated in a high-energy, planetary ball mill. The starting material was obtained in high purity by dehydration of a mixture of LiOH and H_2O_2 . Although composed of crystallites with the same mean diameter, a nanocrystalline sample prepared by ball-milling is not directly comparable with the discharge product formed in a lithium-air battery. Here, however, we considered ball milling

as an appropriate means to resemble the electrochemically formed Li_2O_2 as closely as possible with respect to both crystallite size and defects. From the point of view of structural disorder, the sample investigated might serve well to study the influence of structural disorder on ion transport properties. As has been shown also for other Li ion conductors, the transport properties of ball milled oxides may also resemble that of completely amorphous materials reflecting the upper limit of a disordered oxide or peroxide.

In the present study, long-range as well as short-range Li ion dynamics have been probed by temperature-variable conductivity spectroscopy and ^7Li NMR relaxometry. The overall conductivity σ_{dc} of the microcrystalline sample turned out to be very low which is in agreement with previous results as well as with ^7Li NMR line shape measurements presented here. Ball-milling, however, leads to an increase of σ_{dc} , being characteristic for long-range ion transport, by approximately two orders of magnitude; correspondingly, the activation energy decreases. Similarly, also short-range Li ion dynamics are influenced by high-energy ball milling. In general, a large volume fraction of interfacial regions is formed and structural disorder is introduced by mechanical treatment. The defects generated are anticipated to largely influence both ionic transport over long distances as well as the elementary steps of ion hopping to which NMR is extremely sensitive when carried out at sufficiently low temperatures.

II. EXPERIMENT

A. Preparation, structural and thermal characterization of lithium peroxide

Lithium hydroxide monohydrate (Sigma Aldrich) was dissolved in water (dest.) and an equimolar aqueous solution of hydrogen peroxide 30% (Merck) was added under Ar atmosphere. The solution was stirred under argon atmosphere at ambient conditions. The initially produced lithium hydroperoxide LiOOH was dried in vacuo and subsequently treated at 493 K for 12 h yielding microcrystalline lithium-peroxide Li_2O_2 of high purity. To prepare nanocrystalline Li_2O_2 , the source material micro- Li_2O_2 was mechanically treated in a high-energy ball mill (Fritsch Pulverisette 7 (premium line)). A grinding beaker made of stabilized ZrO_2 (45 mL) and 140 milling balls (ZrO_2 , 5 mm in diameter) were employed; the microcrystalline starting sample was milled for 180 min at a rotational speed of 600 rpm. The complete synthesis was done under Ar atmosphere.

From then on, the samples prepared were stored in an argon filled glove box. They were characterized by X-ray powder diffraction (XRD) carried out at room temperature with a Bruker D8 Advance diffractometer operating in Bragg-Brentano geometry with $\text{Cu-K}\alpha$ radiation at 40 kV. Diffractograms were analyzed by Rietveld refinement with the programs FULLPROF and X'PertHighScorePlus (Panalytical). To determine decomposition temperatures we carried out thermogravimetric (TG) and differential scanning calorimetry (DSC) measurements: for simultaneous thermal analysis a 449C Jupiter (Netzsch) was used. The heating rate was 10 K min^{-1} from 293 K to 773 K; experiments were carried out with a Helium gas stream of 50 mL min^{-1} .

B. Characterization of ion transport and Li diffusivity

1. Impedance analysis and polarization measurements

For the impedance measurements a Novocontrol Concept 80 broadband dielectric spectrometer equipped with an Alpha-A analyzer as was employed. Conductivities were measured under inert gas atmosphere produced by fresh evaporation of dry nitrogen gas (1 atm.) within a ZGS active sample cell which is capable to measure conductivities down to 10^{-14} S at frequencies ranging from 3 μ Hz to 20 MHz. A Quattro cryosystem (Novocontrol) was employed for temperature regulation with an accuracy of ca. 0.5 K. For impedance measurements the powder samples were cold-pressed. The powder samples were cold-pressed (P.O. Weber press) with an uniaxial pressure of 30 kN to cylindrical pellets (8 mm in diameter, approximately 1 mm in thickness). Electrodes were applied by plasma Au sputtering (Leica EM SCD050). Complex impedance data were recorded at temperatures ranging from 133 K to 573 K.

In order to estimate the ionic and electronic contributions to the total conductivity, potentiostatic polarization measurements were performed on the gold sputtered Li_2O_2 pellets which were pressed under protective Ar atmosphere. The pellets were placed inside air-tight Swagelok-type electrochemical cells in order to protect them during measurements from air and humidity. The polarization experiments were carried out at 293 K with a VMP3 instrument from Biologic that was equipped with a low-current option and controlled by EC-lab software. Polarization measurements were carried out with a constant voltage $U = 5$ V. The current I was recorded as a function of time t .

2. NMR spectroscopy

Temperature-variable and frequency-dependent ^7Li NMR measurements were recorded with an Avance III spectrometer (Bruker BioSpin) connected to a shimmed cryomagnet with a nominal magnetic field of 7.04 T corresponding to a resonance frequency of $\omega_0/2\pi$ of 116.5 MHz. A commercial high temperature probe (Bruker Biospin) was employed allowing $\pi/2$ pulse lengths of about 2.5 μ s.

Prior to the measurements the samples were fire sealed in evacuated glass NMR tubes of 5 mm in diameter and ca. 3 cm in length. The measurements were performed at temperatures ranging from 133 K to 604 K. Temperature regulation and monitoring was carried out with a Eurotherm temperature controller in combination with a type T thermocouple.

^7Li NMR spectra were obtained after Fourier transformation of the free induction decays (FIDs) recorded with a single pulse experiment using recycle delays of up to 60 s at the lowest accessible temperatures. ^7Li NMR spin-lattice relaxation (SLR) rates R_1 in the laboratory frame of reference were acquired by means of the classical saturation recovery pulse sequence $10 \times \pi/2 - t_d - \pi/2 - \text{acquisition}$ (acq.)³⁸⁻⁴² The initial ten $\pi/2$ pulses in rapid succession are used to destroy any longitudinal magnetization M_z . Immediately after this saturation comb, the recovery of M_z is recorded as function of delay time t_d at different temperatures. In addition, ^7Li NMR SLR rates have also been recorded in the rotating frame of ref-

erence (SLR $_{\rho}$). For this purpose, the spin-locking technique $\pi/2 \text{ p}(t_{\text{lock}}) - \text{acq.}$ ^{38,43-48} was employed. The corresponding locking frequency was chosen to be $\omega_1/2\pi = 28$ kHz with the duration of the locking pulse t_{lock} varying from 100 μ s to 100 ms. The recycle delay was set to at least $5 \times R_1^{-1} \equiv T_1$ in order to guarantee full longitudinal relaxation between each scan. Both, R_1 and $R_{1\rho}$ were obtained by parameterizing the resulting magnetic transients $M_z(t_d)$ and $M_{\rho}(t_{\text{lock}})$, respectively, by stretched exponentials: $M_z(t_d) \propto 1 - \exp(-(t/T_{1Q})^\gamma)$ and $M_{\rho}(t_{\text{lock}}) \propto \exp(-(t_{\text{lock}}/T_{1Q})^{\gamma_e})$, respectively.

In addition ^7Li NMR stimulated echoes⁴⁹⁻⁵³ have been recorded by utilizing the Jeener-Broekaert⁵⁴ pulse sequence as a function of mixing time t_m ($10 \mu\text{s} \leq t_m \leq 100$ s) at a fixed preparation time t_p : $(90^\circ)_x - t_p - (45^\circ)_y - t_m - (45^\circ) - t - \text{acquisition}$. Note that SAE NMR, that is, two-time correlation spectroscopy, takes advantage of interactions between the quadrupole moment of the nucleus and the electric field gradient (EFG) tensor at the nuclear site.⁵⁵ The technique gives access to single-particle correlation functions, so called ^7Li sin-sin hopping correlation functions. In general, the results from stimulated echo measurements are comparable to those from SLR $_{\rho}$ NMR measurements.⁵³ The difference is that Li SAE NMR, being comparable to Li exchange NMR,⁵⁶⁻⁶⁰ is sensitive to even slower Li diffusion processes.

III. RESULTS AND DISCUSSION

A. X-ray diffraction, chemical and thermal analysis

The purity of the lithium peroxide prepared was checked by X-ray powder diffraction (see Fig. 2), energy dispersive x-ray diffraction (EDX), infrared (IR) spectroscopy and inductively coupled plasma mass spectrometry (ICP-MS). The powder diffractogram obtained for microcrystalline Li_2O_2 can be fully indexed with literature 2θ values. We could not detect any significant amounts of crystalline impurity phases. Fortunately, the same is true for the ball milled material which was treated for 3 h in a planetary mill. It has also been characterized by XRD, EDX, IR spectroscopy and ICP-MS (see also the supplemental material section). As expected, the XRD peaks have broadened due to size effects and strain generated but neither any mechanochemically induced phases were formed nor any traces of crystalline impurities, such as abrasion of ZrO_2 , show up. Negligible abrasion is also corroborated by ICP-MS (see supplemental material). IR spectroscopy (see Fig. S1) reveals a negligible amount of x-ray amorphous lithium carbonate which is most likely due to post contamination. The impurity level concerning metal ions is fortunately very low as has been verified by EDX (see Fig. S2) and particularly ICP-MS (see Table 1 in the supplemental material section). Altogether, this is a perfect starting condition which helps us to interpret both results from NMR line shape measurements and relaxometry and conductivity spectroscopy.

The mean crystallite size of micro- Li_2O_2 , which is our source material, lies in the μm range as can be seen from the sharp XRD reflexes. From the extent of peak broadening we can roughly estimate a mean diameter $\langle d \rangle$ of the crystallites. The well-known equation introduced by Scherrer yields

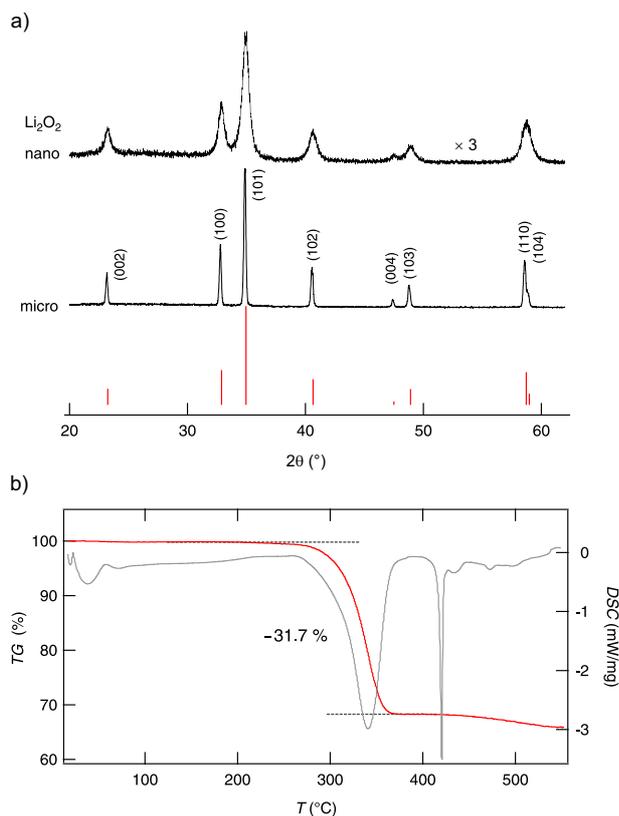


FIG. 2: a) X-ray powder diffractograms of micro- and nanocrystalline lithium peroxide. Miller indices (hkl) indicate the reflexes of Li_2O_2 . Vertical bars in the lower part of the figure illustrate peak positions and relative intensities of pure lithium peroxide. Compared to the pattern of micro- Li_2O_2 that of nano- Li_2O_2 was magnified by a factor of three. b) TG (red line) and DSC measurements (grey line) of nano- Li_2O_2 ; above ca. 500 K Li_2O_2 starts to decompose. A weight loss of ca. 32% points to the release of Oxygen leaving over Li_2O .

$\langle d \rangle \approx 25$ nm. This is in good agreement with other oxides which had been treated in high-energy ball mills to produce nanocrystalline ceramics; usually the crystallite sizes is much less than 50 nm and centres about 10 to 20 nm.⁶¹

Unfortunately, nanocrystalline Li_2O_2 decomposes at elevated temperatures. Our TG/DSC measurements (see Fig. 2) reveal that oxygen is released at temperatures significantly larger than 493 K. The TG curve is very similar to that reported in Ref. 37. Thus, NMR (and conductivity) measurements (see below) had to be restricted to this limit. Their interpretation needs careful consideration of the thermal stability of nano- Li_2O_2 also with respect to grain growth and healing of defects initially introduced.

B. Long-range transport: Conductivity measurements and potentiostatic polarization experiments

1. Conductivity spectroscopy – ionic conduction

Conductivity spectroscopy is able to probe both long-range ($\nu \rightarrow 0$) as well as short-range ion dynamics. In Fig. 3

conductivity spectra $\sigma'(\nu)$, where σ' is the real part of the complex conductivity $\hat{\sigma}$, of nanocrystalline Li_2O_2 are shown which were recorded during heating the sample from 353 K up to 533 K. They reveal distinct dc plateaus referring to $\sigma'(\nu \rightarrow 0) \equiv \sigma_{\text{dc}}$. At lower T a dispersive regime shows up which can be associated with local, *i.e.*, short-ranged, (forward-backward) jump processes. In many cases a Jonscher power law, $\sigma' \propto \nu^k$, is appropriate to account for the frequency dependence of σ' in this frequency range. The deviation from σ_{dc} in the low-frequency regime is because of polarization effects of the ion-blocking electrodes applied. σ' in the regime of electrode polarization (EP) often shows a slight change in slope in this frequency range as indicated in Fig. 3 a); the arrow points to the EP flank of the isotherm recorded at 533 K.

At lower T (Fig. 3 b)) the dispersive part starts to dominate the spectra and σ' tends to obey the relation $\sigma' \propto \nu$. This is the signature of nearly-constant-loss (NCL) behavior being typical for complex crystalline and structurally disordered ion conductors, see Ref. 62 for an overview on this topic. The behavior $\sigma' \propto \nu$ implies a negligible frequency dependence of the dielectric loss, that is the imaginary part of the complex permittivity $\epsilon''(\nu) = \sigma'(\nu)/(2\pi\nu)$ yielding $\sigma'_{\text{NCL}}(\nu) = 2\pi\nu\epsilon''_{\text{NCL}}(\nu) \approx A\nu^{1-\alpha}$ with $\alpha > 0$ but close to 0 and A being almost independent of T : $\epsilon''_{\text{NCL}}(\nu)2\pi \approx A\nu^{-\alpha}$.

NCL behavior is frequently interpreted in terms of strictly localized ion hopping which can be illustrated as caged dynamics in a double well potential, for example.⁶² The activation energy associated is anticipated to be very small. The electrical response of crystalline Li_2O_2 found at low T clearly suggests the presence of NCL-type (ion) dynamics, most probably because of the short distances of possible occupied and unoccupied (interstitial) Li sites within the crystal structure (see Fig. 1).

In contrast to such shallow activated processes, σ_{dc} is sensitive to long-range ion transport usually determined by much higher activation energies being the sum of both the migration enthalpy and the enthalpy needed to form, *e.g.*, vacant Li sites. Siegel and co-workers²⁴ nicely summarized the types of defects, their equilibrium formation energies and concentrations. As it turned out by first principle calculations the dominant positively and negatively charged defects are hole polarons and Li vacancies, respectively. In single crystalline Li_2O_2 the formation energies have been calculated to range from 0.93 to 0.95 eV with concentrations in the order of 10^7 cm^{-3} .²⁴

In general, slow Li ion transport in oxides is characterized by activation energies being much larger than 0.6 eV.^{63–65} σ_{dc} can either be read out from the distinct dc plateaus of Fig. 3 a) or by analyzing complex plane plots which can be constructed when the imaginary part Z'' of $\hat{\sigma}$ is plotted as a function of the real part, that is Z' . An ideal Debye process, governed by an exponential relaxation function, would give a semicircle whose origin coincides with the abscissa. Depressed semicircles, as found for many complex ion conductors showing structural disorder,⁶⁶ directly correlate with the presence of a dispersive part of σ' and point to a non-Debye response and so-called correlated motion.^{67,68} The single semicircles, observed for each temperature here, have to be regarded as a sum of both the response from the bulk and that from the pos-

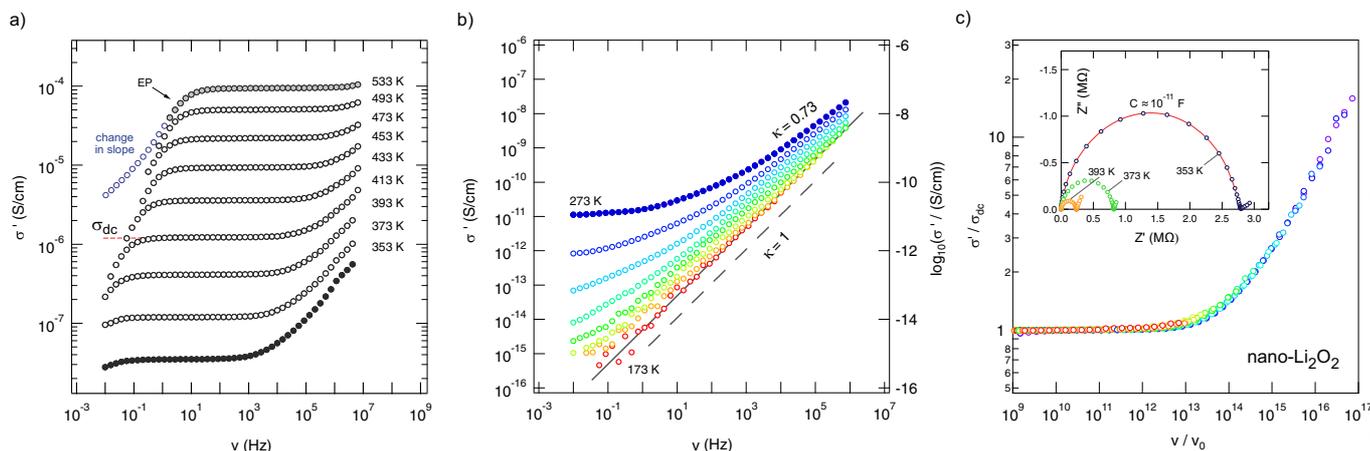


FIG. 3: a) conductivity spectra of nanocrystalline Li_2O_2 prepared by high-energy ball milling. b) conductivity spectra recorded under the same conditions as in a) but at lower T . $\kappa (= 1 - \alpha)$ is the Jonscher exponent; a value close to 1 (indicated by the dashed line) points to so-called NCL-type behaviour being frequently interpreted in terms of localized ion motions. The isotherms shown were recorded at 173 K, 183 K, 193 K, 213 K, 233 K, 253 K and 273 K. c) Scaling of the isotherms shown in a); the inset shows selected complex plane plots ($-Z''$ vs Z').

sible response of grain boundaries. Electrode effects show up as spikes or tails in the Nyquist plots presented in Fig. 3 c). Analyzing $-Z''(Z')$ with an appropriate equivalent circuit unit including a resistance and a constant phase element connected in parallel yields a (total) capacity C in the order of 10^{-11} F (inset of Fig. 3) for the main relaxation process observed. This indicates that, to a major extent, the electrical response, and thus σ_{dc} , reflects bulk ion conduction.⁶⁹

The same can be deduced from permittivity spectra $\epsilon'(\nu)$ shown in Fig. 4. While EP shows up once again at low frequencies and high temperatures, the permittivity found at higher frequencies (or lower temperatures) is well below 100 and indicates presumably bulk response. The dashed line in Fig. 4 b) illustrates the permittivity plateau leading to $\epsilon'(0) \approx 30$. This is in line with that value ($\epsilon'(0) \approx 35$) which has been reported for microcrystalline Li_2O_2 by Gerbig et al.³⁷ Moreover, experiments with different electrodes (Ti or Pt) and ac conductivity measurements as a function of oxygen partial pressure³⁷ did not show any indications that oxygen ions determine the overall conductivity. In an O_2 atmosphere the incorporation of oxygen consumes electrons leading to the formation of holes that are quite localized corresponding to a superoxide ion O_2^- on O_2^{2-} sites as electron spin resonance (EPR) spectra had indicated; moreover, the superoxide O_2^- anions seem to associate with lithium vacancies.³⁷

Interestingly to note, $\epsilon'(0)$ decreases with increasing T although the temperature was still below the decomposition point. Since this process is irreversible, it might reflect the influence of defect healing due to soft sintering of the sample or reflect the smooth onset of Li_2O release. According to Sidebottom,⁷⁰ and similarly to Roling,⁷¹ with the help of the Debye model for dipolar relaxation the change in permittivity $\Delta\epsilon = \epsilon'(0) - \epsilon'(\infty)$ (see Fig. 4) can be related to the number fraction n' of the mobile ions and the distance traversed in a single hop. Thus, a slight decrease of n' , associated with a change decrease in ion conductivity σ' (and consequently $\sigma'(\text{dc})$, as presented below), could explain the decrease ob-

served. As pointed out by Ngai and Rendell,⁷² such decrease could also be interpreted in terms of a change of the underlying motional correlation function. In a wider sense, both interpretations reflect a change in defect chemistry³⁷ in Li_2O_2 at elevated T because of oxygen loss when exposed to a reducing nitrogen atmosphere.

Despite of this slight irreversibility observed, the conductivity spectra $\sigma'(\nu)$ recorded up to 450 K (at least) can be scaled such that they collapse into a single master curve. This means that their shape does not vary significantly with increasing temperature. Here, ν_0 (see Fig. 3 c) is meant to be the 'characteristic' frequency at which $\sigma' = 2\sigma_{\text{dc}}$ holds. This scaling behavior roughly proves that a single (main) charge carrier process seems to be relevant up to 473 K.

Finally, in Fig. 5 $\sigma_{\text{dc}}T$, determined from $\sigma'(\nu)$, is plotted for micro- and nanocrystalline Li_2O_2 as a function of inverse temperature. The arrows mark the conductivities recorded during the heating run and the cooling run, respectively. Heating up to 570 K has negligible influence on σ_{dc} of the micro sample; a much larger influence, however, is observed for nanocrystalline Li_2O_2 . $\sigma_{\text{dc}}T$ of the nano sample starts to deviate from the Arrhenius line drawn if the temperature was raised to 500 K. This temperature is in good agreement with that determined via TG/DSC (see above). Note that between each data point ($\sigma_{\text{dc}}T$) the equilibration time to reach a constant temperature was about 20 min. As mentioned above this feature might be due to Li_2O release and/or a kind of sintering of the sample. Grain growth and significant sintering, however, could not be observed by XRD.

Most importantly, when comparing the initial conductivities of micro- and nanocrystalline Li_2O_2 (heating runs), that of nano- Li_2O_2 is by more than two orders of magnitude larger than that of micro- Li_2O_2 . At room temperature we have $\sigma_{\text{dc,nano}} \approx 1.35 \times 10^{-10}$ S cm^{-1} which corresponds – when the Nernst-Einstein equation is applied – to an overall solid-state diffusion coefficient in the order of 4×10^{-20} $\text{m}^2 \text{s}^{-1}$. In accordance with the increase of σ_{dc} , the corresponding activation

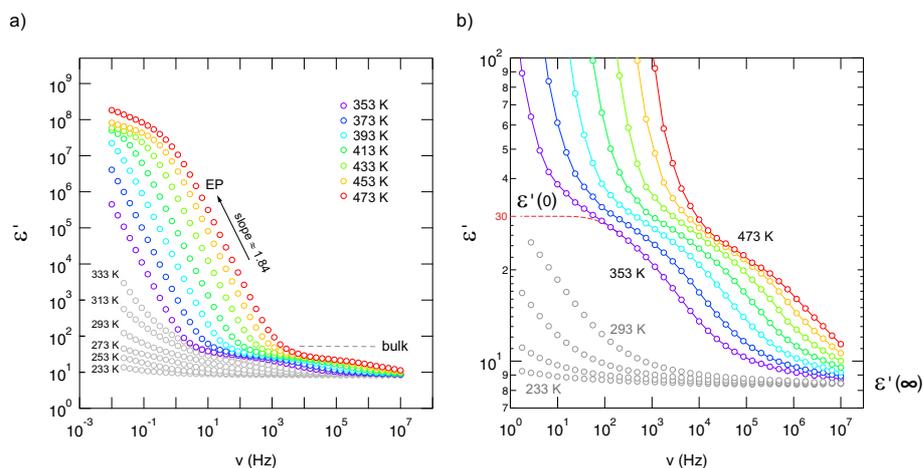


FIG. 4: a) permittivity spectra of nanocrystalline Li_2O_2 recorded at the temperatures indicated. b) magnification of the spectra shown on the left side. Spectra have been recorded in steps of 20 K. $\epsilon''(0) \approx 30$, which is in good agreement with that deduced for microcrystalline Li_2O_2 , see Ref.37, indicates bulk response rather than large contributions from grain boundaries.

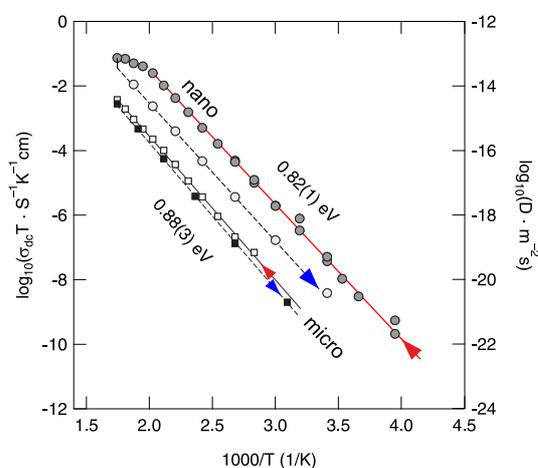


FIG. 5: Arrhenius plot of the total conductivity of nanocrystalline and microcrystalline Li_2O_2 when measured in a flow of dry nitrogen. The arrows denote the heating and cooling runs, respectively. The activation energies refer to the heating runs. During cooling we obtain 0.90(7) eV (micro) and 0.83(7) eV (nano). To obtain the right axis σ_{dc} values have been roughly converted into solid-state diffusion coefficients D via the Nernst-Einstein equation.

energy for overall (long-range) charge carrier transport is reduced from $E_a = 0.88$ eV to 0.82 eV. The result reflects the influence of crystallite size and structural disorder introduced via ball-milling on macroscopic properties such as overall conductivity, which is the sum of both the electronic and ionic contribution. For comparison, Maier and co-workers, who measured ionic (ion) and electronic (eon) conductivities of microcrystalline Li_2O_2 , found $E_{a,\text{ion}} = 0.95(5)$ eV (423 – 473 K) and $E_{a,\text{eon}} = 1.3(1)$ eV (423 – 473 K), respectively.³⁷ The bulk ion conductivity $\sigma_{\text{ion,micro}}$ of 10^{-10} to 10^{-9} S cm^{-1} recorded at 373 K is in perfect agreement with our value of 2×10^{-9} S cm^{-1} (373 K) keeping in mind that the latter represents the total conductivity.

Li_2O_2 which was treated for 1 h in a Pulverisette 5 mill, Gerbig et al. report an activation energy being reduced by $\Delta E_a = 0.14$ eV compared to that of microcrystalline Li_2O_2 . This result agrees well with our value of 0.82 eV. In order to estimate any electronic contributions to the total value of σ_{dc} we carried out preliminary potentiostatic polarization measurements at room temperature.

2. Electronic vs ionic conduction at 293 K

When an ionic conductor is polarized between blocking electrodes, a gold film in this case, the ions will start to migrate. After a while, a concentration gradient is established and the net ionic motion in the electric field stops, the electric field induced migration being counterbalanced by the chemical back-diffusion of the mobile species. When this stationary state is reached, the residual current is due to electronic conduction only.

The nanocrystalline sample exhibited a normal behavior and the current dropped exponentially (see Fig. 6). It has to be noticed that the time needed for stabilization of the current is very long, a fact that indicates a very low conductivity, and thus a very low mobility of the ionic species. Unfortunately, no clear plateau was reached during the experiment. Nevertheless, the electronic conductivity of nano- Li_2O_2 is estimated to be approximately 9×10^{-12} Scm^{-1} , that is less than 10% of the total conductivity measured at room temperature ($\approx 1.1 \times 10^{-10}$ S cm^{-1}).

In the case of our microcrystalline sample, the conductivity was so low, that it was impossible to measure any current at the same polarization voltage (0.5 V) that was used for the nanocrystalline material. Consequently, the voltage applied was increased tenfold, up 5 V. Even in this case, it was not possible to see any unequivocal exponential decrease of the current. It has to be noticed that by being submitted to such high voltages, the electrodes will no longer be blocking and there will be no accumulation at the electrode since there is an ongoing chemical reaction. Remarkably, even under such harsh

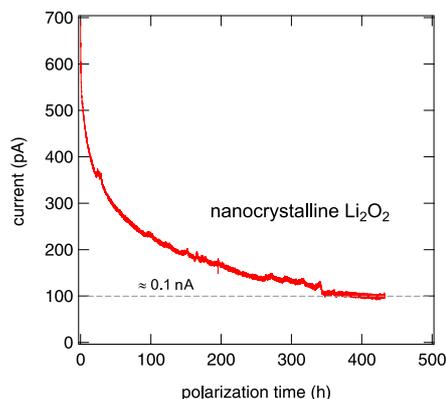


FIG. 6: Polarization curve (dc) of a nanocrystalline lithium peroxide prepared by high-energy ball milling. The electric contact to the pellet pressed was realized by plasma gold sputtering. The voltage applied across the pellet was 0.5 V. The almost constant current which is reached at long polarization time, that is the (quasi) stationary state, is slightly below 100 pA.

conditions micro- Li_2O_2 does not show any traces of damage during the 1000 hours of the experiment. The conductivity of this sample seems to be extremely low at room temperature which makes it impossible to measure it in such a direct way with our VMP3 instrument, which is so far limited to measurements at ambient temperature

Maier and co-workers performed similar measurements but at higher T ; they were able to exactly determine both σ_{ion} and σ_{eon} of microcrystalline lithium peroxide.³⁷ If we roughly extrapolate their data on micro- Li_2O_2 towards room temperature we get $\sigma_{\text{ion}}/\sigma_{\text{eon}} \approx 1000$. The same can be anticipated from our experiments. For our ball-milled sample, however, we found $\sigma_{\text{ion}}/\sigma_{\text{eon}} \approx 10$. This trend is in qualitative agreement with the result reported for nano- Li_2O_2 , which was, however, only softly milled in a Pulverisette 5 planetary mill for just 1 hour: Gerbig et al. report on an increase of σ_{ion} by half an order and σ_{eon} by one order of magnitude.³⁷ As is well known, the milling conditions, such as the type of mill, the duration of milling, the atmosphere, the ball-to-powder ratio etc., can drastically influence the structural properties and defect chemistry of the material obtained.

Irrespective of the exact influence of the milling conditions, this comparison reveals that during milling σ_{eon} increases more than σ_{ion} does, leading to a smaller ratio $\sigma_{\text{ion}}/\sigma_{\text{eon}}$. On the basis of EPR, in Ref. 37 the increase of σ_{eon} (measured in oxygen atmosphere) of a ball-milled sample has been associated with an increasing concentration of superoxide O_2^- species on peroxide sites corresponding to electron holes.

Before we look in detail on Li jump rates and activation energies deduced from NMR, we shall compare the conductivity results with other ion conductors. Taking into account the electronic contribution to the total conductivity, ion dynamics in nanocrystalline Li_2O_2 turned out to be relatively poor. Values of σ_{ion} in the order of $10^{-10} \text{ Scm}^{-1}$ and σ_{eon} in the order of $10^{-12} \text{ Scm}^{-1}$ are below those being desired for a lithium-oxygen battery. Preferably ionic conductivities should be in the order of 10^{-5} to 10^{-3} Scm^{-1} ; electronic ones even two or-

ders of magnitude higher. For comparison, the record holder in terms of extremely good ion conductivity is $\text{Li}_{10}\text{GeP}_2\text{S}_{12}$ with 10^{-3} Scm^{-1} at room temperature,⁷⁵ followed by garnet-type oxides^{42,76} (10^{-3} Scm^{-1} at approximately 300 K) or Li-bearing argyrodites.⁷⁷ Activation energies range from 0.35 to 0.25 eV. The electronic conductivity of nanocrystalline Li_2O_2 prepared by ball-milling is still lower than that of LiFePO_4 (10^{-6} S/cm , 0.6 eV^{37,78}) that may serve here as a yardstick for a mixed conductor with practical battery applications. In the case of LiFePO_4 carbon coating and nanosizing is necessary to prepare an electrode material able to work as a cathode in lithium-ion batteries. Similar conductive coating, however, cannot be realized on the forming/disappearing Li_2O_2 ; the electronic conductivity values not to be rate limiting would have to be again several orders of magnitude higher. This might be achieved by further doping of the material as well as further introduction of structural disorder.³⁶ Taking benefit from non-trivial nano-size effects would lead to the question how does ion conductivity depend on the size of the crystallites. This would require a systematic study which is beyond the scope of the present investigation focussing on the elementary steps of hopping in ball-milled Li_2O_2 .

C. Short-range motions: NMR spectra and relaxation rates

Temperature-variable ^7Li NMR spectra, when recorded under static, *i.e.*, non-rotating conditions, are sensitive to Li ion hopping processes.^{79–83} In Fig. 7 ^7Li NMR spectra of both micro- and nanocrystalline Li_2O_2 are shown. Although ^7Li is a quadrupole nucleus, due to symmetry reasons there is no electric field gradient present at the Li sites which would lead to a so-called quadrupole powder pattern.⁷³ At sufficiently low temperature the NMR line is dipolarly broadened and its shape is similar to a Gaussian. For comparison, the corresponding rigid-lattice Li NMR spectrum of Li_2O , crystallizing with cubic symmetry, looks very similar.^{74,84} At temperatures below ambient the Li hopping rate ν is low and does not affect the spectra. With increasing temperature, however, ν increases and causes line narrowing. If ν reaches the value of the NMR line width, which is 17.5 kHz at 290 K, homonuclear dipole-dipole interactions governing the line in the rigid lattice regime become increasingly averaged. In the present case, this so-called motional narrowing clearly proceeds in a heterogeneous way which means that a narrow NMR line emerges at elevated T and superimposes the broad one.^{74,84,85} The spectrum of micro- Li_2O_2 reveals that this process starts at around 482 K; it can be even better recognized when the spectrum recorded at 604 K is regarded.

Importantly, in the case of nanocrystalline Li_2O_2 the same process occurs, however, it starts at significantly lower temperatures. For comparison, at 355 K the two dynamically different spin reservoirs can be well differentiated from each other while the corresponding spectra of the microcrystalline sample still show the broad Gaussian-shaped line. Regarding previous studies on nanocrystalline Li_2O by Heitjans and co-workers,^{85,86} such two-component NMR line shapes have been interpreted in terms of (mobile) Li spins residing in or near the large volume fraction of interfacial regions gener-

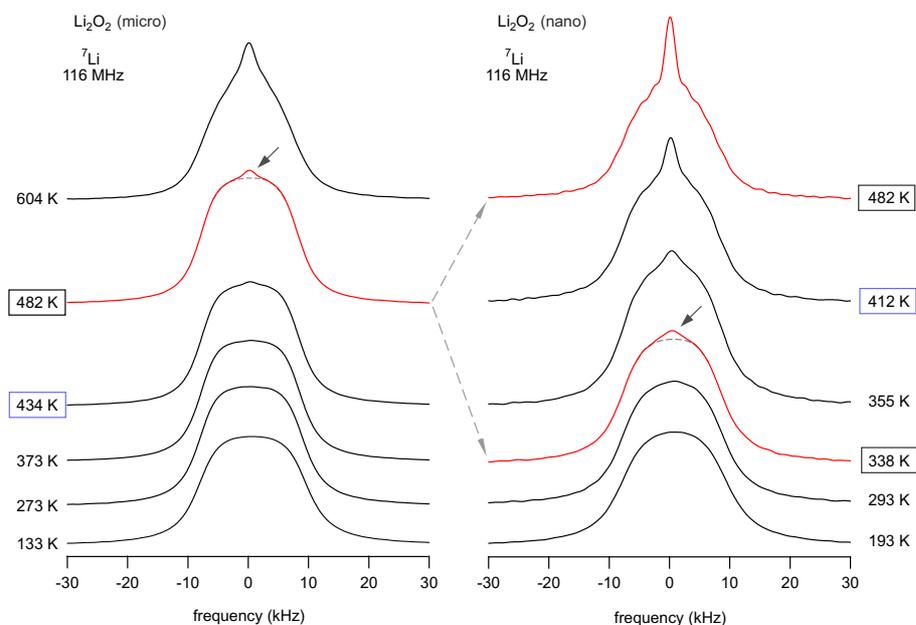


FIG. 7: Static ${}^7\text{Li}$ NMR spectra of microcrystalline (left) and nanocrystalline (right) Li_2O_2 recorded at 116 MHz and at the temperatures indicated. The arrows indicate a motionally narrowed NMR line superimposing the broad line being characteristic for Li ions in microcrystalline Li_2O_2 . Since the electric field gradient at the Li sites in Li_2O_2 vanishes due to symmetry reasons, ${}^7\text{Li}$ NMR spectra of Li_2O_2 are composed of a single line (the 'central' line) only, see also Ref. 73. The same situation is found, e.g., for Li_2O with perfect cubic symmetry.⁷⁴

ated during milling.^{74,85} This assignment can also be adapted to explain the spectra of nano- Li_2O_2 , which is anticipated to be characterized by a large number fraction of defects. Since the feature of a two-component line shape did also show up for micro- Li_2O_2 at elevated temperatures, the emergence of a narrow NMR line is either connected to thermally induced defects, forming also in micro- Li_2O_2 , or to an intrinsic heterogeneous Li^+ dynamics in the peroxide.

It is worth noting that the heterogeneous narrowing shown in Fig. 7 for nanocrystalline Li_2O_2 is fully reversible. The irreversible decomposition into Li_2O , which smoothly starts above 500 K according to TG/DSC and which could also have its microscopic (atomic-scale) infancy at 473 K, cannot be used to explain the two-component behavior observed. Here, we believe that its origin is almost completely related to the mechanically induced defect-rich structure formed. The area fraction A_f of the narrow NMR component as well as the evolution of the widths of the two NMR lines of nano- Li_2O_2 are shown in Fig. 8.

Starting from approximately 18 kHz the broad component slightly decreases. The motionally narrowed NMR line shows up at elevated T ; its widths is 1.7(1) kHz. A_f reaches 5% at 450 K, thus, indicating that only a small number fraction of Li ions is involved in the fast diffusion process. A_f corresponds to the area fraction of that component of the FIDs which after Fourier Transformation yields the narrowed NMR line. In Fig. 9 two FIDs of a spin-locking $R_{1\rho}$ experiment (28 kHz) are shown which have been recorded at quite different temperatures viz. 233 K and 455 K. While in both cases the fast decaying part corresponds to the broad Gaussian obtained after Fourier transformation, only the FID recorded at 455 K re-

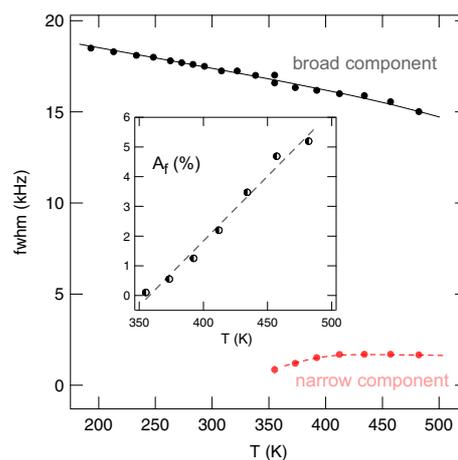


FIG. 8: Line widths (fwhm, full width at half maximum) of the two NMR components visible in the ${}^7\text{Li}$ NMR spectra shown in Fig. 7. A_f denotes the area fraction, which also equals the *number fraction*, of fast diffusing Li spins in nanocrystalline lithium peroxide prepared by high-energy ball milling.

veals an additional intensity slowly decaying with acquisition time, see also Ref.⁸⁴. Before we briefly discuss the separate analysis of this slowly decaying part in the frame of a spin-locking NMR experiment, which is certainly limited because of the low intensity of this contribution, we firstly present the rates R_1 and $R_{1\rho}$ which can be deduced from the FIDs when the *whole* area under the curve is evaluated as a function of waiting or locking time.

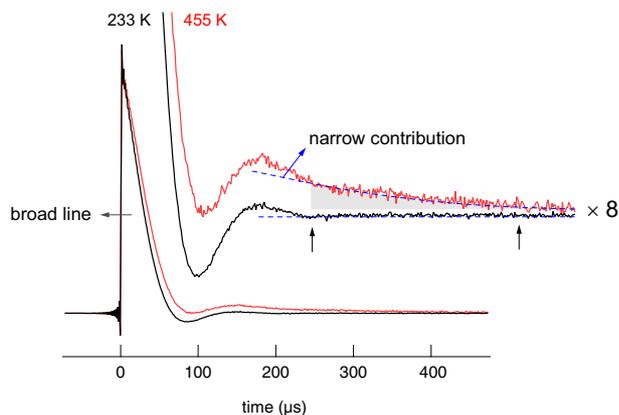


FIG. 9: ${}^7\text{Li}$ NMR (transversal) transients of nanocrystalline Li_2O_2 recorded with the spin-lock technique at 28 kHz and a Larmor frequency of 116 MHz. In contrast to the signal recorded at 233 K, the FID obtained at elevated T reveals a slowly decaying intensity which is responsible for the motionally narrowed NMR line visible in the Fourier transforms in Fig. 7.

As an example, in Fig. 10 selected magnetization transients of our spin-lock experiments are shown. They quantify the transversal decay of $M_Q(t_{\text{lock}})$ according to $M_Q(t_{\text{lock}}) \propto \exp(-(t_{\text{lock}}/T_{1Q})^\gamma)$. $\gamma_Q(T)$ is shown in Fig. 11. Over the whole temperature range the transients can be best fitted with stretched exponentials; a separation of the two spin reservoirs discussed above, *e.g.*, by the use of two single exponentials, is hardly possible because of the low number fraction of fast relaxing spins. Therefore, the rates shown in Fig. 11, which gives an overview of the NMR rates (and stretching exponents γ) of nano- Li_2O_2 measured, represent those ions which are not directly responsible for the motionally narrowed NMR line detected. The observation that the $R_{1\rho}$ -transients can only be fitted with stretched exponentials rather than with a single exponential might be connected to the fact that non-exponential curves can be expected for ${}^7\text{Li}$; this can be due to intrinsic as well as extrinsic reasons: (i) as a spin-3/2 nucleus ${}^7\text{Li}$ inter-

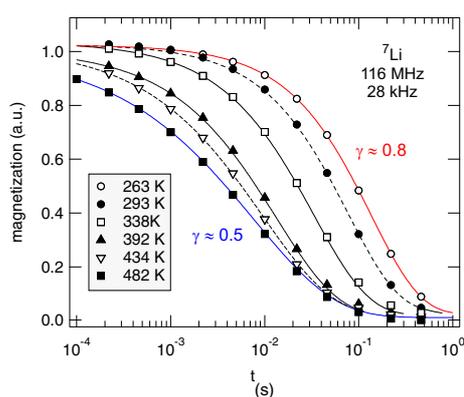


FIG. 10: Temperature-variable ${}^7\text{Li}$ NMR $R_{1\rho}$ transients recorded in the lab-frame using a spin-locking frequency of 28 kHz. Solid and dashed lines show fits with stretched exponentials. The stretching exponents γ_Q are shown as a function of T in Fig. 10.

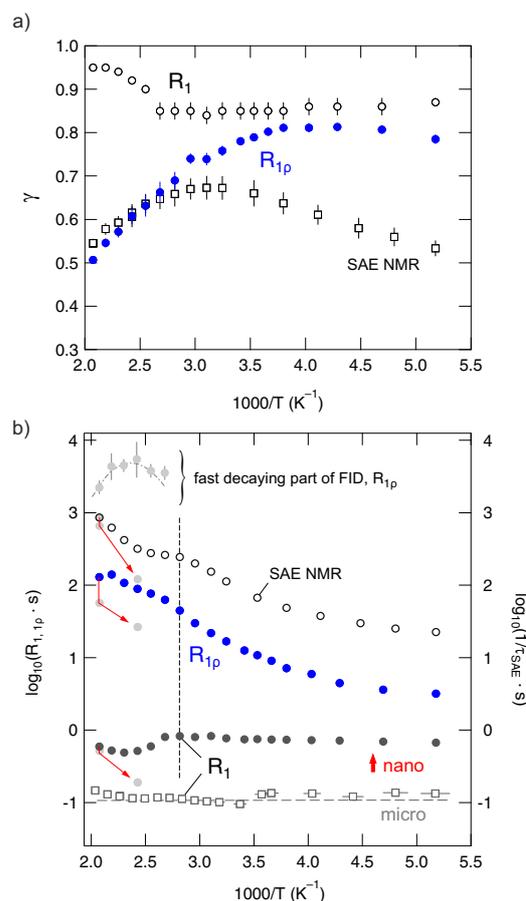


FIG. 11: a) Stretching factors $\gamma_{(\rho)}$ used to parameterize the various magnetization transients (R_1 , $R_{1\rho}$) and echo decay curves (SAE NMR) of nano- Li_2O_2 ; b) Arrhenius plot of the ${}^7\text{Li}$ NMR relaxation rates of nanocrystalline Li_2O_2 measured. The rates shown were obtained by analysing the magnetization transients and echo damping curves with stretched exponentials. The data were acquired at 116 MHz (and at a locking frequency of $\omega_1/2\pi = 28$ kHz. For comparison, the R_1 rates of microcrystalline Li_2O_2 are also shown. The arrows point to those rates which were recorded during cooling.

acts with electric field gradients being associated with defects introduced, (ii) the interaction with paramagnetic impurities may also lead to such a behavior, and/or (iii) independent of such extrinsic influences the underlying hopping correlation function could be of non-exponential shape from the outset. If not being an intrinsic feature of a single ion hopping process in nanocrystalline Li_2O_2 , the latter could also be the result of heterogeneous dynamics, *i.e.*, the overall dynamics observed is the result of a superposition of many jump processes each being describable by single exponential motional correlation functions. The latter might be corroborated by the observation that at least γ of our $R_{1\rho}$ transients varies with temperature; this points to a shift of Li dynamics in favor of an overall (non-exponential) diffusion process. Such a process increasingly may become governed by correlated motion either due to structural disorder or repulsive (Coulomb) interactions of the jumping ions.

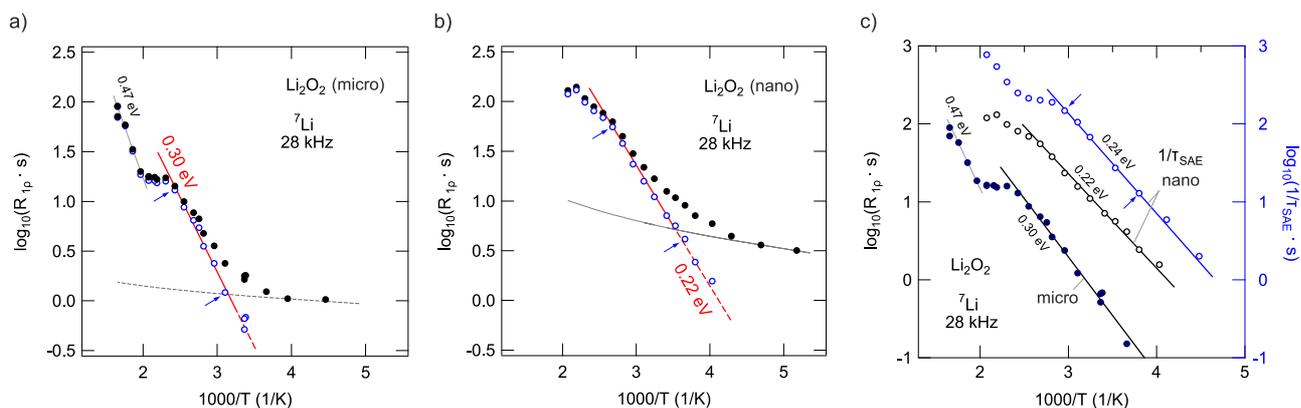


FIG. 12: a) and b) ${}^7\text{Li}$ spin-lattice relaxation rates (116 MHz, 28 kHz locking frequency) of micro- and nanocrystalline Li_2O_2 as a function of inverse temperature. The dashed lines correspond to power laws characterizing the non-diffusive background contributions to the overall rates. The correction procedure to obtain SLR rates mainly induced by diffusion is described in the text; solid lines represent Arrhenius fits, the activation energies obtained are indicated. Arrows mark the fitting ranges. c) comparison of the ${}^7\text{Li}$ SLR NMR rates recorded in the rotating frame of reference with those obtained from SAE NMR for nano- Li_2O_2 .

Compared to the corresponding γ values of microcrystalline Li_2O_2 , which vary over the temperature range covered from 0.84 to 0.72 (R_1) and from 0.64 to 0.44 ($R_{1\rho}$), the results indicate that ball-milling shifts γ of R_1 towards values closer to one rather than affecting the stretching exponents in the opposite direction. At least, this is valid for the so-called non-diffusive temperature regime which in the case of $R_{1\rho}$ becomes apparent below 200 K. For comparison, in the temperature regime covered here, the R_1 rates are clearly not induced by translational Li diffusion; even up to 500 K only a non-diffusive background rate is detected which does only weakly depend on T . This can be easily explained by the different sensitivities of the two methods to Li diffusivity.^{40,87} While $R_{1\rho}$ measurements do probe Li dynamics with jump rates in the order of the locking frequency, that is, 28 kHz in our case, R_1 is, however, sensitive to jumps with rates on the MHz time scale that is defined by the Larmor frequency itself.

It is worth mentioning that the R_1 rates apparently show a shallow local minimum around 430 K. In the same temperature regime, steps in $R_{1\rho}(1/T)$ (and $\tau_{\text{SAE}}^{-1}(1/T)$) show up (see Fig. 12). These might be related to variations in the diffusion mechanism and/or slight structural changes. The observations will be discussed in more detail below. When analyzing the low- T flanks of diffusion-induced NMR rate peaks we expect activation energies being much smaller than that probed by conductivity spectroscopy in the dc limit. This is simply due to the fact that in the low- T limit NMR relaxometry is in general sensitive to local jump processes rather than to long-range ion transport. This has been recently outlined by our group on a fluorine anion conductor.⁸⁸ Here, we use the results from NMR to make comparisons with recent theoretical predictions about local hopping barriers.

For this purpose and for further analysis of our data, it is important to emphasize that the poor ion conductivity probed expectedly manifests itself in the observation that only the rate $R_{1\rho}$ is able to probe Li dynamics below 500 K. This also holds for the SAE NMR measurements, which reveal a diffusion-induced contribution at elevated temperatures. To separate the

influence of non-diffusive and weaker-than-activated background effects on the (purely) diffusion-induced rates $R_{1\rho}$ and τ_{SAE}^{-1} , we parameterized the low-temperature background rates with appropriate power laws $R_{1\rho} \propto T^\beta$. An extrapolation to higher temperatures allowed for calculating the desired diffusion-induced $R_{1\rho,\text{diff}}$ rates (see unfilled symbols in Fig. 12 a) and b)). After this correction procedure, $R_{1\rho,\text{diff}}(1/T)$ of microcrystalline Li_2O_2 reveals a low-temperature flank pointing to a (low- T) activation energy of 0.30 eV (Fig. 12 a)). This is in good agreement with calculated hopping barriers for negatively charged Li vacancies (0.33 – 0.39 eV) by Radin et al.²⁴ and Hummelshøj et al.^{32,33} The calculations of Radin and Siegel reveal that the lowest energy pathway (0.33 eV) corresponds to migration between adjacent octahedral sites.²⁴

At elevated temperatures, that is at 430 K, the NMR rates reach a plateau value. If not associated to slight microstructural changes of the material, which are not detectable via XRD, it might be related to a shallow local rate maximum. Since no substantial NMR line narrowing shows up, this, however, can only be an indication of localized, *i.e.*, strictly short-ranged Li motions between adjacent energy minima in the structure of the peroxide. As mentioned above, such localized motions appear as $\epsilon'' \neq \nu$ (or $\sigma' \propto \nu$) in conductivity spectroscopy. With increasing temperature, the rates increase further and follow an Arrhenius line with an activation energy of 0.47 eV (Fig. 12 a)). Interestingly, this value is in agreement with that proposed for the binding or interaction energy between hole polarons and lithium vacancies (0.47 eV).³⁴ As we will see below, a somewhat smaller activation energy is found by SAE NMR in this region (0.41 eV), which is in agreement with the first-principle calculations of Radin and Siegel for nearest neighbor hole polaron hopping (0.42 eV).²⁴ Others have found 0.38 eV²⁷ and 0.37 eV.³⁴ Hence, it cannot be excluded that also polaron dynamics are indirectly seen by ${}^7\text{Li}$ NMR. When comparing these values we have to keep in mind, however, that the involvement of trigonal prismatic sites in Li dynamics leads to a barrier of 0.39 eV.²⁴

Even after a generous background correction the corresponding rates of the nanocrystalline sample are shifted towards larger values (see Fig. 12 b)) and follow an Arrhenius law being determined by a smaller activation energy of only 0.22 eV. As in the case of the microcrystalline sample a discontinuity is observed. It shows up at 400 K and is most likely of the same origin as discussed for the non-treated sample. For comparison, in the case of τ_{SAE}^{-1} of nano- Li_2O_2 (see Fig. 12 c)) it is shifted to even lower temperatures (360 K). The activation energy turned out to be slightly larger than that probed via the spin-lock NMR technique. Altogether, the shift of the relaxation and decay rates observed for the sample mechanically treated indicates enhanced local Li hopping as compared to the starting material, which has also been observed for nanocrystalline Li_2O ^{74,85} and other ion conductors prepared by milling.^{63,79,89–92} As in the case of R_1 of micro- Li_2O_2 , above 400 K the rates τ_{SAE}^{-1} increase further; the corresponding activation energy is approximately 0.42 eV (as already mentioned above).

Let us point out that the difference between $R_{1\rho}$ and τ_{SAE}^{-1} of nano- Li_2O_2 likely reflects the increased sensitivity of SAE NMR to very slow Li exchange processes.^{55,87,93–99} These might be found in the crystalline cores of the nanostructured sample. Indeed, the shape of the curve $\tau_{\text{SAE}}^{-1}(1/T)$ resembles that of $R_{1\rho}(1/T)$ of micro- Li_2O_2 . In the present case we tend to interpret the SAE decay rates as dipolar relaxation rates rather than to take them as real jump rates. The latter has been found for a variety of materials with Li migration pathways being formed by multiple electrically inequivalent Li sites. Because of both the small activation energy found by SAE NMR and the low pre-exponential factor associated, we thus suspect that dipole-dipole interactions strongly influence the spin-alignment echo damping and hence govern the decay rates obtained. Furthermore, at the lowest temperatures τ_{SAE}^{-1} seems to be increasingly influenced by spin-diffusion which hamper the detection of echo damping that is (purely) induced by particle diffusion.

Mechanical treatment has also an effect on the background rates measured by the various NMR techniques. For both R_1 and $R_{1\rho}$ we observed an increase of the non-diffusion induced rates by one order of magnitude. Several phenomena could serve as origins for this observation such as (i) strictly localized motions, as characterized by an NCL effect (vide supra), (ii) coupling of the spins to unpaired electrons, or (iii) a change of lattice vibrations. The increasing concentration of electron holes observed by Gerbig and co-workers³⁷ might be useful to explain such differences observed for ball-milled Li_2O_2 .

Taken together, enhanced long-range ion transport, as evidenced by conductivity spectroscopy, is also accompanied by increased short-range motions of all of the ^7Li NMR spins. This is reflected by decreased activation energies and increased (diffusion-induced) overall relaxation rates. Importantly, the latter shows increased Li dynamics even in the bulk of Li_2O_2 nanocrystallites. To detail the fast ^7Li spin reservoir as seen via NMR line shapes, let us reconsider the two-component line shape and the associated FIDs of nanocrystalline Li_2O_2 at elevated T in a quantitative way. If we inte-

grate only the slowly decaying part of the FID it should be possible to separate the ions being responsible for the narrowed line from those reflected by the broad one.

In Fig. 9 the two vertically drawn arrows indicate the integration range we used to construct the corresponding temperature-variable magnetization transients. For comparison, in Fig. 11 b) the SLR rates resulted are shown as grey circles in the upper part of the Arrhenius diagram. Their temperature dependence might be interpreted as a shallow maximum since the rates indeed start to decrease with increasing temperature. With the maximum condition valid for a $R_{1\rho}(1/T)$ -peak, $\omega_1\tau_c \approx 0.5$, we obtain a motional correlation rate of $\tau_c^{-1} = 3.5 \times 10^5 \text{ s}^{-1}$ at 473 K. Within a factor of two the correlation time τ_c is expected to be equal to the Li residence time between two successful jumps. Assuming a mean jump distance of only 2.5 Å, the Einstein-Smoluchowski equation for 3D uncorrelated motion¹⁰⁰ yields a self-diffusion coefficient D in the order of $D(473 \text{ K}) = 1 \times 10^{-14} \text{ m}^2 \text{ s}^{-1}$. For comparison with conductivity spectroscopy, a diffusion coefficient within this order is in good agreement with $2.1 \times 10^{-5} \text{ S cm}^{-1}$ as probed at the same temperature. This agreement points out that ion transport to which σ_{dc} is sensitive, seems to be mainly governed by the fast Li sub-ensemble detected by NMR. This Li reservoir could be a spatially local one *near* or *in* the surface-influenced interfacial regions of the nm-sized, structurally disordered Li_2O_2 crystallites.^{74,85} It might comparable to that expected for that expected for Li ion surface diffusion.

For comparison with other Li ion conductors, both active materials and solid electrolytes, a diffusion coefficient in the order of $D(473 \text{ K}) = 1 \times 10^{-14} \text{ m}^2 \text{ s}^{-1}$ reflects rather poor ion diffusivity. Considering recent examples that have been investigated by NMR, Li-bearing argyrodite, $\text{Li}_6\text{PSe}_5\text{Br}$, shows values as high as $10^{-12} \text{ m}^2 \text{ s}^{-1}$ at 263 K,⁸³ Li diffusion in the anode material LiC_6 is in the order of $10^{-15} \text{ m}^2 \text{ s}^{-1}$ at 300 K while we have $4 \times 10^{-20} \text{ m}^2 \text{ s}^{-1}$ in the case of nano- Li_2O_2 (see Fig. 5).⁸² Additionally, the well-known garnet-type electrolyte Al-doped $\text{Li}_7\text{Zr}_2\text{La}_3\text{O}_{12}$ shows a D value of $10^{-14} \text{ m}^2 \text{ s}^{-1}$ at ambient temperature rather than at 473 K; the corresponding activation energy is much lower and turned out to be 0.35 eV.⁴² Interestingly, quite recently Siegel and co-workers³⁶ calculated the ion conductivity for amorphous Li_2O_2 and found enhanced dynamics characterized by $10^{-7} \text{ S cm}^{-1}$. This is three orders of magnitude larger than that for nanocrystalline Li_2O_2 prepared by ball milling.

Considering electronic properties, quite recently Geng et al.¹⁰¹ have employed first-principles density functional theory calculations to study the properties of grain boundaries in Li_2O_2 . They report on electronic conduction channels in polycrystalline Li_2O_2 opened up by stable grain boundaries. Considering also space charge effects, which are known to influence both ionic and electronic charge carrier transport,^{102–105} it underpins the important role of interfaces being important to consider when dynamic properties shall be engineered, see also Ref. 5.

IV. SUMMARY AND CONCLUSIONS

Charge carrier transport and Li ion dynamics of nanocrystalline lithium peroxide were investigated by the complemen-

tary techniques of conductivity and NMR spectroscopy. In agreement with the recent study by Gerbig et al. translational Li ion dynamics as well as electron transport turned out to be rather poor in microcrystalline Li_2O_2 . After high-energy ball milling, however, the overall conductivity has been increased by more than two orders of magnitude and reaches $1.1 \times 10^{-10} \text{ S cm}^{-1}$ at room temperature. Potentiostatic polarization measurements reveal a discernable electronic contribution (approximately 10 %) to the total conductivity. Compared to the non-milled starting material, the activation energy decreased from 0.88 eV to 0.82 eV.

While at very low temperatures the nearly constant loss phenomenon leaves its fingerprints in the frequency dependence of the conductivity σ' , above 250 K the ^7Li NMR relaxometry measurements on nano- Li_2O_2 point to sort-range motions with an activation energy of approximately 0.22 eV. In a similar way this is also observed for microcrystalline lithium peroxide, the activation energy, however, is somewhat larger (0.30 eV). Most importantly, well below the decomposition range of nanocrystalline Li_2O_2 , the static ^7Li NMR line shapes are composed of two components. While the broad one is identical to that one observed for micro Li_2O_2 , the motionally narrowed line represents a sub-ensemble of relatively fast Li ions. Analyzing this component in the frame of a $T_{1\rho}$ NMR experiment – to our knowledge such a separation has not been reported so far for $R_{1\rho}$ rates – we were able to roughly estimate the corresponding Li jump rate at 473 K and, hence, the self-diffusion coefficient. The latter, which is in the order of $10^{-14} \text{ m}^2 \text{ s}^{-1}$, corresponds well with the dc conductivity probed at the same temperature.

In summary, enhancement of charge carrier dynamics in nanocrystalline Li_2O_2 is most likely related to the various defects and strain high-energy ball milling can introduce. Defects are introduced in both the bulk and the surface-influenced regions of the nanocrystallites. In many cases the large volume fraction of interfacial regions formed during mechanical impact show structural disorder facilitating ion transport over short and long distances. Although the enhancement is easily measurable, compared to other oxidic lithium ion conductors it turned out to be much lower. It seems that ball-milling has a larger influence on σ_{eon} than on σ_{ion} ; at room temperature we found $\sigma_{\text{ion}}/\sigma_{\text{eon}} \approx 10$, which is much larger than the ratio estimated for the microcrystalline counterpart.

Author Contributions

The authors were equally involved in experimental work, data analysis and project planning. All authors have given approval to the final version of the manuscript.

Acknowledgement. We thank our colleagues at the TU Graz for valuable discussions. Financial support by the Austrian Federal Ministry of Economy, Family and Youth, and the Austrian National Foundation for Research, Technology and Development is greatly appreciated. Furthermore, I thank the Deutsche Forschungsgemeinschaft (DFG) for financial support within the DFG Research Unit 1277, grant no. WI3600/2-1 and 4-1, and the DFG Priority Program 1415, grant no. WI3600/5-1.

* Electronic address: andreas.dunst@tugraz.at; corresponding author

† Electronic address: vikror.epp@tugraz.at

‡ Electronic address: wilkening@tugraz.at; corresponding author

¹ S. H. Oh, R. Black, E. Pomerantseva, J.-H. Lee, and L. F. Nazar, *Nature Chem.* **4**, 1004 (2012).

² K. M. Abraham and Z. Jiang, *J. Electrochem. Soc.* **1**, 143 (1996).

³ Y.-C. Lu, B. M. Gallant, D. G. Kwabi, J. R. Harding, R. R. Mitchell, M. S. Whittingham, and Y. Shao-Horn, *Energy Environ. Sci.* **6**, 750 (2013).

⁴ F. Li, H. Kitaura, and H. Zhou, *Energy Environ. Sci.* **6**, 2302 (2013).

⁵ B. D. Adams, C. Radtke, R. Black, M. L. Trudeau, K. Zaghib, and L. F. Nazar, *Energy Environ. Sci.* **6**, 1772 (2013).

⁶ B. Scrosati, J. Hassoun, and Y.-K. Sun, *Energy Environ. Sci.* **4**, 3287 (2011).

⁷ P. G. Bruce, S. A. Freunberger, L. J. Hardwick, and J.-M. Tarascon, *Nat. Mater.* **11**, 19 (2012).

⁸ M. M. Thackeray, C. Wolverton, and E. D. Isaacs, *Energy Environ. Sci.* **5**, 7854 (2012).

⁹ J. Read, *J. Electrochem. Soc.* **149**, A1190 (2002).

¹⁰ T. Ogasawara, A. Débart, M. Holzapfel, P. Novák, and P. G. Bruce, *J. Am. Chem. Soc.* **128**, 1390 (2006).

¹¹ L. Zhong, R. R. Mitchell, Y. Liu, B. M. Gallant, C. V. Thompson, J. Y. Huang, S. X. Mao, and Y. Shao-Horn, *Nano Lett.* (2013).

¹² G. Girishkumar, B. McCloskey, A. C. Luntz, S. Swanson, and W. Wilcke, *J. Phys. Chem. Lett.* **1**, 2193 (2010).

¹³ S. A. Freunberger, Y. Chen, Z. Peng, J. M. Griffin, L. J. Hardwick, F. Bardé, P. Novák, and P. G. Bruce, *Journal of the American Chemical Society* **133**, 8040 (2011).

¹⁴ F. Mizuno, S. Nakanishi, Y. Kotani, S. Yokoishi, and H. Iba, *Electrochem.* **78**, 403 (2010).

¹⁵ B. D. McCloskey, D. S. Bethune, R. M. Shelby, G. Girishkumar, and A. C. Luntz, *J. Phys. Chem. Lett.* **2**, 1161 (2011).

¹⁶ W. Xu, J. Hu, M. H. Engelhard, S. A. Towner, J. S. Hardy, J. Xiao, J. Feng, M. Y. Hu, J. Zhang, F. Ding, et al., *J. Power Sources* **215**, 240 (2012).

¹⁷ M. M. Ottakam Thotiyl, S. A. Freunberger, Z. Peng, and P. G. Bruce, *J. Am. Chem. Soc.* **135**, 494 (2013).

¹⁸ W. Xu, K. Xu, V. V. Viswanathan, S. A. Towner, J. S. Hardy, J. Xiao, Z. Nie, D. Hu, D. Wang, and J.-G. Zhang, *J. Power Sources* **196**, 9631 (2011).

¹⁹ M. M. Ottakam Thotiyl, S. A. Freunberger, Z. Peng, Y. Chen, Z. Liu, and P. G. Bruce, *Nature Mater.* **12**, 1050 (2013).

²⁰ S. A. Freunberger, Y. Chen, N. E. Drewett, L. J. Hardwick, F. Bardé, and P. G. Bruce, *Angew. Chem. Inter. Ed.* **50**, 8609 (2011).

²¹ B. D. McCloskey, A. Speidel, R. Scheffler, D. C. Miller, V. Viswanathan, J. S. Hummelshøj, J. K. Nørskov, and A. C. Luntz, *J. Phys. Chem. Lett.* **3**, 997 (2012).

²² J. S. Hummelshøj, A. C. Luntz, and J. K. Nørskov, *J. Phys. Chem.* **138**, 034703 (2013).

²³ V. Viswanathan, K. S. Thygesen, J. S. Hummelshøj, and G. G. J. K. Nørskov, *J. Chem. Phys.* **135**, 214704 (2011).

- ²⁴ M. D. Radin and D. J. Siegel, *Energy Environm. Sci.* **6**, 2370 (2013).
- ²⁵ S. Kang, Y. Mo, S. P. Ong, and G. Ceder, *Chem. Mater.* (2013).
- ²⁶ Y. Chen, S. A. Freunberger, Z. Peng, O. Fontaine, and P. G. Bruce, *Nature Chem.* **5**, 489 (2013).
- ²⁷ A. C. Luntz, V. Viswanathan, J. Voss, J. B. Varley, J. K. Nørskov, R. Scheffler, and A. Speidel, *J. Phys. Chem. Lett.* **4**, 3494 (2013).
- ²⁸ R. R. Mitchel, B. M. Gallant, Y. Shao-Horn, and C. V. Thompson, *J. Phys. Chem. Lett.* **4**, 1060 (2013).
- ²⁹ Y.-C. Lu and Y. Shao-Horn, *J. Phys. Chem. Lett.* **4**, 93 (2012).
- ³⁰ V. Timoshevskii, Z. Feng, K. H. Bevan, J. Goodenough, and K. Zaghbi, *Appl. Phys. Lett.* **103**, 073901 (2013).
- ³¹ D. Zhai, H.-H. Wang, J. Yang, K. C. Lau, K. Li, L. A. Curtiss, and K. Amine, *J. Am. Chem. Soc.* **135**, 15364 (2013).
- ³² J. S. Hummelshøj, J. Blomqvist, S. Datta, T. Vegge, J. Rossmeisl, K. S. Thygesen, A. C. Luntz, K. W. Jacobsen, and J. K. Nørskov, *J. Chem. Phys.* **132**, 071101 (2010).
- ³³ J. Chen, J. S. Hummelshøj, K. S. Thygesen, J. S. G. Myrdal, J. K. Nørskov, and T. Vegge, *Catal. Today* **165**, 2 (2011).
- ³⁴ S. P. Ong, Y. Mo, and G. Ceder, *Phys. Rev. B* **85**, 081105 (2012).
- ³⁵ M. D. Radin, J. F. Rodriguez, and D. J. S. F. Tian, *J. Am. Chem. Soc.* **134**, 1093 (2012).
- ³⁶ F. Tian, M. D. Radin, and D. J. Siegel, *Chem. Mater.* p. in press (2014).
- ³⁷ O. Gerbig, R. Merkle, and J. Maier, *Adv. Mater.* **25**, 3129 (2013).
- ³⁸ E. Fukushima and S. B. W. Roeder, *Experimental Pulse NMR: A Nuts and Bolts Approach* (Addison-Wesley Pub. Co., Advanced Book Program, Reading, Mass., 1981).
- ³⁹ P. Heitjans, A. Schirmer, and S. Indris, in *Diffusion in Condensed Matter*, edited by P. Heitjans and J. Kärger (Springer, 2005), chap. 9, p. 367.
- ⁴⁰ A. Kuhn, S. Narayanan, L. Spencer, G. R. Goward, V. Thangadurai, and M. Wilkening, *Phys. Rev. B* **83**, 94302 (2011).
- ⁴¹ A. Kuhn, J.-Y. Choi, L. Robben, F. Tietz, M. Wilkening, and P. Heitjans, *Z. Phys. Chem.* **226**, 525 (2012).
- ⁴² H. Buschmann, J. Dölle, S. Berendts, A. Kuhn, P. Bottke, M. Wilkening, P. Heitjans, A. Senyshyn, H. Ehrenberg, A. Lotnyk, et al., *Phys. Chem. Chem. Phys.* **13**, 19378 (2011).
- ⁴³ D. Ailion and C. P. Slichter, *Phys. Rev. Lett.* **12**, 168 (1964).
- ⁴⁴ C. P. Slichter and D. Ailion, *Phys. Rev.* **135**, A1099 (1964).
- ⁴⁵ D. C. Ailion and C. P. Slichter, *Phys. Rev.* **137**, A235 (1965).
- ⁴⁶ D. C. Look and I. J. Lowe, *J. Chem. Phys.* **44**, 2995 (1966).
- ⁴⁷ T. J. Rowland and F. Y. Fradin, *Phys. Rev.* **182**, 760 (1969).
- ⁴⁸ D. Wolf, *Phys. Rev. B* **10**, 2724 (1974).
- ⁴⁹ X.-P. Tang and Y. Wu, *J. Magn. Res.* **133**, 155 (1998).
- ⁵⁰ R. Böhmer, *J. Magn. Res.* **147**, 78 (2000).
- ⁵¹ F. Qi, G. Diezemann, H. Böhm, J. Lambert, and R. Böhmer, *J. Magn. Res.* **169**, 225 (2004).
- ⁵² F. Qi, T. Jörg, and R. Böhmer, *Solid State Nucl. Magn. Res.* **22**, 484 (2002).
- ⁵³ M. Wilkening and P. Heitjans, *Phys. Rev. B* **77**, 024311 (2008).
- ⁵⁴ J. Jeener and P. Broekaert, *Phys. Rev.* **157**, 232 (1967).
- ⁵⁵ R. Böhmer, K. Jeffrey, and M. Vogel, *Prog. Nucl. Magn. Reson. Spectrosc.* **50**, 87 (2007).
- ⁵⁶ P. Bottke, D. Freude, and M. Wilkening, *J. Phys. Chem. C* **117**, 8114 (2013).
- ⁵⁷ L. S. Cahill, R. Chapman, J. Britten, and G. Goward, *J. Phys. Chem. B* **110**, 7171 (2006).
- ⁵⁸ Z. Xu and J. Stebbins, *Science* **270**, 1332 (1995).
- ⁵⁹ C. Grey and N. Dupré, *Chem. Rev.* **104**, 4493 (2004).
- ⁶⁰ J. Cabana, N. Dupré, G. Rousse, C. P. Grey, and M. R. Palacin, *Solid State Ion.* **176**, 2205 (2005).
- ⁶¹ S. Indris, D. Bork, and P. Heitjans, *J. Mater. Synth. Proc.* **8**, 245 (2000).
- ⁶² K. Funke, C. Cramer, and D. Wilmer, in *Diffusion in Condensed Matter – Methods, Materials, Models*, edited by P. Heitjans and J. Kärger (Springer, Berlin, 2005), chap. 21, pp. 857–893, 2nd ed.
- ⁶³ P. Heitjans and M. Masoud and A. Feldhoff and M. Wilkening, *Faraday Discuss.* **134**, 67 (2007).
- ⁶⁴ B. Ruprecht, M. Wilkening, R. Uecker, and P. Heitjans, *Phys. Chem. Chem. Phys.* **14**, 11974 (2012).
- ⁶⁵ B. Ruprecht, H. Billetter, U. Ruschewitz, and M. Wilkening, *J. Phys.: Cond. Matter* **22**, 245901 (2010).
- ⁶⁶ D. L. Sidebottom, *Rev. Mod. Phys.* **81**, 999 (2009).
- ⁶⁷ K. Funke, *Prog. Solid State Chem.* **22**, 111 (1993).
- ⁶⁸ A. Bunde, W. Dieterich, P. Maass, and M. Meyer, in *Diffusion in Condensed Matter – Methods, Materials, Models*, edited by P. Heitjans and J. Kärger (Springer, Berlin, 2005), chap. 20, pp. 813–856, 2nd ed.
- ⁶⁹ J. T. S. Irvine, D. C. Sinclair, and A. R. West, *Adv. Mater.* **2**, 132 (1990).
- ⁷⁰ D. L. Sidebottom, *Phys. Rev. Lett.* **82**, 3653 (1999).
- ⁷¹ B. Roling, *Solid State Ion.* **105**, 185 (1998).
- ⁷² K. Ngai and R. W. Rendell, *Phys. Rev. B* **61**, 9393 (2000).
- ⁷³ M. Leskes, N. Drewett, L. Hardwick, P. Bruce, G. Goward, and C. Grey, *Angew. Chem. Int. Ed.* **51**, 8560 (2012).
- ⁷⁴ M. Wilkening, S. Indris, and P. Heitjans, *Phys. Chem. Chem. Phys.* **5**, 2225 (2003).
- ⁷⁵ N. Kamaya, K. Homma, Y. Yamakawa, M. Hirayama, R. Kanno, M. Yonemura, T. Kamiyama, Y. Kato, S. Hama, K. Kawamoto, et al., *Nat. Mater.* **10**, 682 (2011).
- ⁷⁶ R. Murugan, V. Thangadurai, and W. Weppner, *Angew. Chem. Int. Ed.* **46**, 7778 (2007).
- ⁷⁷ H.-J. Deiseroth, S.-T. Kong, H. Eckert, J. Vannahme, C. Reiner, T. Zaiss, and M. Schlosser, *Angew. Chem. Int. Ed.* **47**, 755 (2008).
- ⁷⁸ R. Amin, J. Maier, P. Balaya, D. P. Chen, and C. T. Lin, *Solid State Ion.* **179**, 1683 (2008).
- ⁷⁹ M. Wilkening, V. Epp, A. Feldhoff, and P. Heitjans, *J. Phys. Chem. C* **112**, 9291 (2008).
- ⁸⁰ M. Wilkening, W. Iwaniak, J. Heine, V. Epp, A. Kleinert, M. Behrens, G. Nusspl, W. Bensch, and P. Heitjans, *Phys. Chem. Chem. Phys.* **9**, 6199 (2007).
- ⁸¹ S. Narayanan, V. Epp, M. Wilkening, and V. Thangadurai, *RSC Adv.* **2**, 2553 (2012).
- ⁸² J. Langer, V. Epp, P. Heitjans, F. A. Mautner, and M. Wilkening, *Phys. Rev. B* **88**, 094304 (2013).
- ⁸³ V. Epp, z. Gün, H.-J. Deiseroth, and M. Wilkening, *J. Phys. Chem. Lett.* **4**, 2118 (2013).
- ⁸⁴ P. Heitjans and M. Wilkening, *Mat. Res. Bull.* **34**, 915 (2009).
- ⁸⁵ S. Indris and P. Heitjans, *J. Non-Cryst. Solids* **307**, 555 (2002).
- ⁸⁶ P. Heitjans, A. Schirmer, and S. Indris, in *Diffusion in Condensed Matter – Methods, Materials, Models*, edited by P. Heitjans and J. Kärger (Springer, Berlin, 2005), chap. 9, pp. 369–415, 2nd ed.
- ⁸⁷ M. Wilkening and P. Heitjans, *Chem. Phys. Chem.* **13**, 53 (2012).
- ⁸⁸ F. Preishuber-Pflügl, P. Bottke, B. Bitschnau, and M. Wilkening, *Phys. Chem. Chem. Phys.* p. in press (2014).
- ⁸⁹ D. Bork and P. Heitjans, *J. Phys. Chem. B* **102**, 7303 (1998).
- ⁹⁰ D. Bork and P. Heitjans, *J. Phys. Chem. B* **105**, 9162 (2001).
- ⁹¹ M. Wilkening, D. Bork, S. Indris, and P. Heitjans, *Phys. Chem. Chem. Phys.* **4**, 3246 (2002).
- ⁹² M. Masoud and P. Heitjans, *Def. Diff. Forum* **237-240**, 1016 (2005).
- ⁹³ X.-P. Tang, R. Busch, W. Johnson, and Y. Wu, *Phys. Rev. Lett.* **81**, 5358 (1998).
- ⁹⁴ X.-P. Tang, U. Geyer, R. Busch, W. Johnson, and Y. Wu, *Nature* **402**, 160 (1999).

- ⁹⁵ R. Böhmer, T. Jörg, F. Qi, and A. Titze, *Chem. Phys. Lett.* **316**, 419 (2000).
- ⁹⁶ M. Wilkening, W. Küchler, and P. Heitjans, *Phys. Rev. Lett.* **97**, 065901 (2006).
- ⁹⁷ M. Wilkening and P. Heitjans, *J. Phys.: Condens. Matter* **18**, 9849 (2006).
- ⁹⁸ M. Wilkening, C. Lyness, A. R. Armstrong, and P. G. Bruce, *J. Phys. Chem. C* **113**, 4741 (2009).
- ⁹⁹ M. Wilkening, J. Heine, C. Lyness, A. R. Armstrong, and P. G. Bruce, *Phys. Rev. B* **80**, 064302 (2009).
- ¹⁰⁰ H. Mehrer, *Diffusion in Solids*. (Springer, Berlin, 2006).
- ¹⁰¹ W. T. Geng, B. L. He, and T. Ohno, *J. Phys. Chem. C* **117**, 25222 (2013).
- ¹⁰² J. Maier, *Progr. Solid State Chem.* **23**, 171 (1995).
- ¹⁰³ J. Maier, *Nature Mater.* **4**, 805 (2005).
- ¹⁰⁴ N. Sata, K. Eberman, K. Eberl, and J. Maier, *Nature* **408**, 946 (2000).
- ¹⁰⁵ W. Puin, S. Rodewald, R. Ramlau, P. Heitjans, and Maier, *Solid State Ion.* **131**, 159 (2000).


Short-range Li diffusion vs long-range ionic conduction in nanocrystalline lithium peroxide Li_2O_2 — the discharge product in lithium-air batteries

A. Dunst *et al.*, Graz University of Technology

Broader context

Electrochemical energy storage is considered as the key technology to enable the shift from fossil to renewable energies. Among the few alternatives to Li-ion batteries that theoretically exceed significantly their specific energy, the non-aqueous Li-O₂ battery has attracted intense interest. It relies on the reversible formation of lithium peroxide in the positive electrode, $2\text{Li}^+ + \text{O}_2 + 2\text{e}^- = \text{Li}_2\text{O}_2$. Major challenges, however, face its practical realization. One is poor charge transport in Li_2O_2 that is widely recognized as a major factor limiting its achievable amount on the conductive substrate during discharge and the rate and overpotentials at which it can be formed and decomposed during cycling. So far, charge transport in Li_2O_2 is only poorly understood. To shed light on Li ion dynamics in Li_2O_2 it needs to be investigated in a complementary way by both macroscopic as well as microscopic techniques. In particular, Li NMR relaxometry offers an atomic-scale access to information on the elementary steps of ion hopping. Such results will build a first basis to understand the complex interplay of morphology, defect density and ion transport in Li_2O_2 . They may help to improve the key metrics of the Li-O₂ battery, such as capacity, rate and efficiency.

TOC graphic (8 × 4 cm)

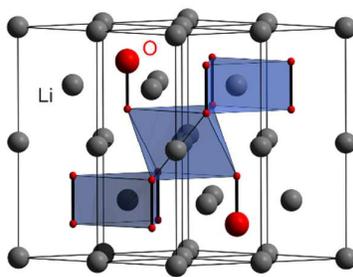

Description (1 sentence, 20 words):

Conductivity spectroscopy and ⁷Li spin-locking NMR relaxometry reveals enhanced ion dynamics in nanocrystalline Li_2O_2 prepared by high-energy ball milling