

Energy & Environmental Science

Accepted Manuscript



This is an *Accepted Manuscript*, which has been through the Royal Society of Chemistry peer review process and has been accepted for publication.

Accepted Manuscripts are published online shortly after acceptance, before technical editing, formatting and proof reading. Using this free service, authors can make their results available to the community, in citable form, before we publish the edited article. We will replace this *Accepted Manuscript* with the edited and formatted *Advance Article* as soon as it is available.

You can find more information about *Accepted Manuscripts* in the [Information for Authors](#).

Please note that technical editing may introduce minor changes to the text and/or graphics, which may alter content. The journal's standard [Terms & Conditions](#) and the [Ethical guidelines](#) still apply. In no event shall the Royal Society of Chemistry be held responsible for any errors or omissions in this *Accepted Manuscript* or any consequences arising from the use of any information it contains.

COMMUNICATION

Voltage Output of Efficient Perovskite Solar Cells with high Open-Circuit Voltage and Fill Factor

Cite this: DOI: 10.1039/x0xx00000x

Seungchan Ryu,^{a†} Jun Hong Noh,^{a†} Nam Joong Jeon,^a Young Chan Kim,^a Woon Seok Yang,^a Jangwon Seo^a and Sang Il Seok^{*,ab}

Received 00th January 2012,
Accepted 00th January 2012

DOI: 10.1039/x0xx00000x

www.rsc.org/

Besides the generated photocurrent as a key factor that impacts the efficiency of solar cells, the produced photovoltage and fill factor are also of critical importance. Therefore, understanding and optimization of the open-circuit voltage (V_{oc}) of perovskite solar cells, especially with a architecture consisting of mesoporous (mp)-TiO₂/perovskite/hole transporting materials (HTMs), are required to further improve the conversion efficiency. In this work, we study the effects of the energy level between CH₃NH₃(=MA)PbI₃ and MAPbBr₃ and a series of triarylamine polymer derivatives containing fluorene and indenofluorene, which have different highest occupied molecular orbital (HOMO) levels, in terms of the photovoltaic behaviour. The voltage output of the device is found to be dependent on the higher energy level of perovskite solar absorbers as well as the HOMO level of the HTMs. The combination of MAPbBr₃ and a deep-HOMO HTM leads to a high photovoltage of 1.40 V, with fill factor of 79% and an energy conversion efficiency of up to 6.7%, which is the highest value reported till date for MAPbBr₃ perovskite solar cells.

Efficient and inexpensive energy harvesting by solar cells is a great challenge for the 21st century in the field of renewable energy. Most recently, inorganic–organic hybrid solar cells have been demonstrated to be amongst the most promising of emerging photovoltaic devices with respect to the power conversion efficiency (PCE), use of liquid-free hole-conductors as charge carriers, abundant availability, and inexpensive fabrication.^{1–8} Mesoscopic inorganic–organic hybrid hetero-junction solar cells consisting of Sb₂S₃ or combined Sb₂S₃ and Sb₂Se₃ as light harvesters have shown a PCE of 3–7.5%.^{1–4} Inorganic light harvesters in these cells have a high potential to further improve the performance as compared to the conventional dyes, owing to benefits such as high extinction coefficients, large intrinsic dipole moments, and easily tuneable band-gaps.⁹ A breakthrough in PCE for inorganic–organic

hybrid solar cells has been achieved by the introduction of organolead trihalide perovskites as light harvesters.^{5–8} Previously, these perovskites were used for light absorption in dye-sensitized solar cells with liquid electrolytes, which exhibit a low PCE.^{10–11} However, the photovoltaic (PV) efficiency of the perovskite-based solar cells could be greatly improved by the use of a spiro-OMeTAD-based or polymeric solid hole-conductor.^{5–8} The PCE was further improved by the sequential process of PbI₂ and CH₃NH₃I (methylammonium iodide: MAI) to deposit CH₃NH₃PbI₃ (=MAPbI₃) perovskites on a mesoporous (mp)-TiO₂ electrode,¹² and planar thin layer of MAPbI_{3–x}Cl_x was deposited by the vacuum thermal evaporation method without the mp-TiO₂ electrode.¹³

In addition, the perovskite was justifiably utilized as a donor in organic photovoltaic architectures because of its large diffusion length.^{14,15} Thus, the unusual properties of the perovskites could be exploited for thin-film planar, meso-superstructured, or mesoporous architectures in perovskite-sensitized solar cells. However, we recently proposed that a bi-layer architecture consisting of the perovskite-infiltrated mp-TiO₂ and pure perovskite is crucial in fabricating efficient perovskite cells with coincident reverse and forward scans.¹⁶

Generally, high open-circuit voltage (V_{oc}) solar cells are important tools for driving electrochemical reactions or adopting new device architectures, such as the top-cell in tandem solar cell structures. Hodes and co-workers¹⁷ demonstrated a high V_{oc} of 1.5 V from a solar cell based on the organic-inorganic lead bromide and 4,4'-bis(N-carbazolyl)-1,1'-biphenyl (CBP) hybrid structure, but the efficiency was low. J. Qiu et al.¹⁸ described organolead halide perovskite cells, with CH₃NH₃PbBr₃ as the light harvester and poly[N-90-heptadecanyl-2,7-carbazole-alt-3,6-bis-(thiophen-5-yl)-2,5-dioctyl-2,5-dihydropyrrolo[3,4]pyrrole-1,4-dione] (PCBTDDP) as the hole transporting material (HTM), which showed a V_{oc} of 1.16 V and efficiency of 3.04%, which is the highest observed

for solid state MAPbBr₃ devices to date. Nevertheless, to the best of our knowledge, MAPbBr₃ perovskite solar cells that have PCEs exceeding 6% with a V_{oc} approaching 1.4 V have not yet been reported. It is necessary to determine how and where the V_{oc} is established for understanding PV performance and its optimization. In particular, the origin of V_{oc} in the bilayer cell architecture consisting of mp-TiO₂-perovskite/perovskite/HTM, which is significantly different from conventional dye-sensitized solar cells, is poorly understood. A high V_{oc} in the perovskite solar cell can be achieved by matching and judiciously selecting the perovskite lead halide-based absorber and the HTMs.

Here, we investigated the effect of lowering the highest occupied molecular orbital (HOMO) of the HTM to enhance the V_{oc} of mesoscopic perovskite solar cells. We found that a deeper HOMO results in a significantly larger V_{oc}, which enabled us to fabricate high-efficiency solar cells with a V_{oc} of up to 1.40 V and fill factor (FF) of 79% as well as PCE of 6.7 %, the highest values ever reported for MAPbBr₃perovskite solar cells.

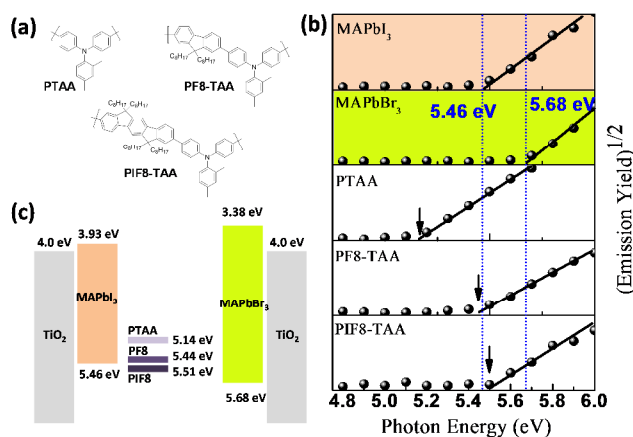


Fig. 1 (a) Molecular structure of HTMs (PTAA, PF8-TAA, and PIF8-TAA); (b) PESA spectra of perovskite films (MAPbI₃, MAPbBr₃) and HTM films on fused silica substrate; (c) energy band diagram for TiO₂, perovskite materials (MAPbI₃, MAPbBr₃), and HTMs.

Inorganic-organic hybrid solar cells were fabricated in the configuration mesoporous (mp)-TiO₂/perovskite/HTM/Au. Both the light absorber (MAPbBr₃ or MAPbI₃ perovskites) and the HTM were deposited onto mp-TiO₂ by spin coating. The homogeneous perovskite layer was deposited with full coverage on mp-TiO₂ (see Fig. S1) The HTMs used in this work are triarylamine (TAA) polymer derivatives containing fluorene and indenofluorene, named P-TAA, PF8-TAA, and PIF8-TAA; the molecular structures of these are shown in Fig. 1a.¹⁹ First, we measured the valence bands of MAPbBr₃ and MAPbI₃ perovskites, and the HOMO levels of HTMs, which are P-TAA, PF8-TAA, and PIF8-TAA, because the V_{oc} in solar cell devices can be derived from the quasi-Fermi levels of each material in the structure. Fig. 1b shows the photoelectron emission spectra for MAPbI₃, MAPbBr₃, PTAA, PF8-TAA, and PIF8-TAA obtained using a Riken Keiki AC-2 photoelectron spectrometer. Photoelectron spectroscopy (PES) measurements were successfully

performed to measure the occupied electronic states of an organic semiconductor and the valence band edges (VBEs) in solids.²⁰⁻²² The measured VBEs of MAPbI₃ and MAPbBr₃ were -5.46 eV, which is in accord with the reported values,⁶ and -5.68 eV, respectively. The HOMO levels of P-TAA, PF8-TAA, and PIF8-TAA were measured to be -5.14 eV, -5.44 eV, and -5.51 eV which are in accord with a previous report.¹⁹ The band alignment is represented in Fig. 1c, where the conduction band edge is calculated from the optical band gap of the perovskite materials. The excited state of the perovskite is higher than the TiO₂ conduction band, and the HOMO levels of PF8-TAA and PIF8-TAA are located near the valence band edges of MAPbI₃ and MAPbBr₃, respectively.

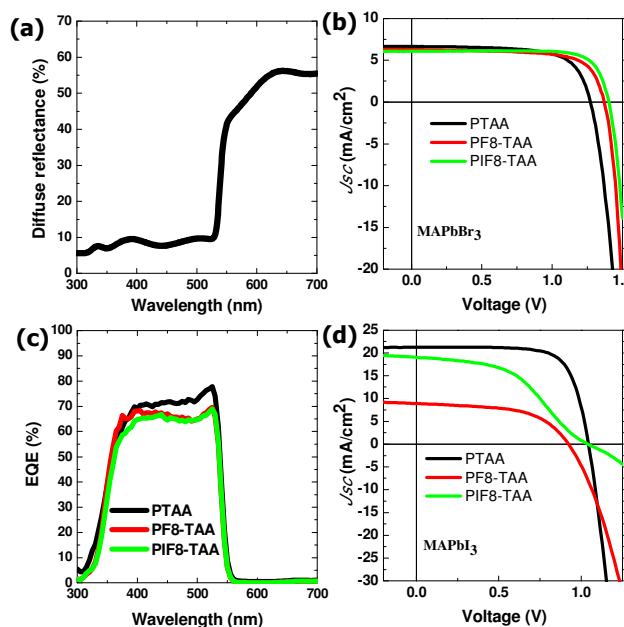


Fig. 2. (a) Diffused reflectance spectrum of FTO/bl-TiO₂/mp-TiO₂:MAPbBr₃/Au specimen; (b) *J-V* characteristics for FTO/bl-TiO₂/mp-TiO₂:MAPbBr₃/HTM/Au, where HTMs are PTAA, PF8-TAA, and PIF8-TAA; (c) EQE spectra; (d) *J-V* characteristics for FTO/bl-TiO₂/mp-TiO₂:MAPbI₃/HTM/Au with these three HTMs.

Fig. 2a shows the diffuse reflectance of MAPbBr₃ deposited on mp-TiO₂/blocking layer (bl)-TiO₂/FTO substrate, which was measured using a UV-Vis spectrometer with an integrated sphere. The optical band gap of MAPbBr₃ is calculated to be 2.3 eV from the diffuse reflectance spectra. Fig. 2b shows the *J-V* characteristics of the FTO/bl-TiO₂/mp-TiO₂:MAPbBr₃/HTM-devices with different HTMs of PTAA, PF8-TAA, and PIF8-TAA measured under AM 1.5 illumination conditions. Table 1 summarizes the extracted short-circuit current density (J_{sc}), V_{oc}, and fill factor (FF). V_{oc} increased with the deeper HOMO of the HTMs, from 1.29 V of P-TAA to 1.36 V of PF8-TAA and 1.40 V of PIF8-TAA. This reveals that the HOMO level of the HTM influences V_{oc}. The origin of V_{oc} in perovskite solar cells is typically described by the difference between the lowest unoccupied molecular orbital (LUMO) level of the perovskite and the HOMO of the HTM, or by the potential difference between the quasi-Fermi level of the electron (E_{fn}) at the electron extracting layer/anode interface and the quasi-Fermi level of

the hole (E_{h}) at the hole extracting layer/cathode interface under illumination, assuming that recombination within the device can be ignored.^{18,23} Therefore, the high V_{oc} of 1.40 V in MAPbBr₃-PIF8(TAA)-device is ascribed to the deeper HOMO level near the VBE of MAPbBr₃. The determination of V_{oc} in the perovskite cell will be further discussed later. In Fig. 2b and Table 1, we also see that the increased V_{oc} accompanies a decrease in the photocurrent (J_{sc}), while the FF increases, in the sequence P-TAA, PF8-TAA, and PIF8-TAA. The external quantum efficiency (EQE) shown in Fig. 2c for devices using PIF-TAA and PIF8-TAA as HTMs is lower than that of P-TAA over the whole range of absorption wavelengths. The relatively low EQE and decreased J_{sc} with deeper HOMO levels of the HTMs might be attributed to the lowering of the driving force for charge injection, due to the small disruption in energy levels between the VBE of MAPbBr₃ and the HOMO of the HTM, as shown in Fig. 1b. On the contrary, the remarkable FF in PIF8-TAA can be related to the charge carrier mobility ($4 \times 10^{-2} \text{ cm}^2/\text{V} \cdot \text{s}$) which is higher than that of PF8-TAA ($2 \times 10^{-2} \text{ cm}^2/\text{V} \cdot \text{s}$) and P-TAA ($4 \times 10^{-3} \text{ cm}^2/\text{V} \cdot \text{s}$).¹⁹ Much larger driving force of P-TAA may counterbalance the low charge carrier mobility, resulting in the same FF with PF8-TAA. However, FF might also be determined by other factors such as charge injection rate and recombination rate at interface contact between perovskite and HTM.²⁴ Regardless of the reduced J_{sc} , the increase in V_{oc} and FF leads to an improved PCE of 6.7%. Consequently, the V_{oc} FF, and PCE of 1.40 V, 79%, and 6.7%, respectively, are the highest among those reported for existing single-junction MAPbBr₃ perovskite solar cells. To ensure the reproducibility of the results, histogram for the efficiencies of each cell was shown in Fig. S2.

Table 1. Photovoltaic parameters for MAPbI₃ and MAPbBr₃ perovskite solar cells using PTAA, PF8-TAA, and PIF8-TAA as HTMs

Perovskite	HTMs	J_{sc} (mA/cm ²)	V_{oc} (V)	FF	PCE (%)
MAPbBr ₃	PTAA	6.6	1.29	0.70	5.9
	PF8-TAA	6.3	1.36	0.70	6.0
	PIF8-TAA	6.1	1.40	0.79	6.7
MAPbI ₃	PTAA	21.3	1.04	0.73	16.2
	PF8-TAA	8.9	0.92	0.56	4.6
	PIF8-TAA	19.0	1.04	0.46	9.1

For the perovskite solar cell, especially for the architecture consisting of the mp-TiO₂/perovskite composite and pure perovskite layers, our previous results^{7,8} suggested that the V_{oc} is not simply determined by the difference between the electron Fermi level at mp-TiO₂ and the hole Fermi level at the HTM. Under the current operation mechanism, the perovskite acts as an absorber as well as charge (either electron or hole) carrier; hence, the voltage output is expected to be high since sensitization or donor-acceptor type devices significantly reduce the expectable V_{oc} because of some charge transfer energy loss. Furthermore, perovskite has high capacitance and can accumulate charges on itself, because of which the quasi Fermi level is controlled upon illumination.²⁵

To gain more insight into the V_{oc} of the perovskite cells with HTMs having a deeper HOMO, we additionally fabricated devices using MAPbI₃ with the same HTMs used in MAPbBr₃. Fig. 2d shows the J - V characteristics for MAPbI₃ perovskite solar cells using PTAA, PIF8-TAA, and PIF8-TAA as the HTM; the photovoltaic parameters are also summarized in Table 1. One can assume that E_{fn} is constant in FTO/bl-TiO₂/mp-TiO₂:perovskite/HTM-devices, although different HOMO levels of HTMs are used. It is noted that the HOMO levels of PTAA and PF8-TAA are -5.14 eV and -5.44 eV, respectively, which are higher than the VBE (-5.46 eV) of MAPbI₃ and therefore, hole transport from MAPbI₃ to the HTMs is favoured. However, PIF8-TAA has a lower HOMO level of -5.51 eV as compared to the VBE of MAPbI₃, which may result in a hole-injection barrier between MAPbI₃ and PIF8-TAA. The J - V curve of the FTO/bl-TiO₂/mp-TiO₂:MAPbI₃/PIF8-TAA-device shows the roll-over effect, in which the current is saturated at high forward bias, while the PTAA and PF8-devices show a typical J - V response. The roll-over effect has been explained by a back contact hole-injection barrier in CdTe, PbS, and organic solar cells.²⁶ Moreover, the driving force might be not enough for hole injection from MAPbI₃ to PF8-TAA because PF8-TAA has a similar HOMO level as the VBE in MAPbI₃, as shown in Fig. 1b. Therefore, it is difficult to discuss the effect of the HOMO level in HTMs on V_{oc} for MAPbI₃-devices, because of the insufficient driving force for charge injection and the abnormality in the J - V response. Nevertheless, the significantly high J_{sc} value of 19.0 mA/cm² for FTO/bl-TiO₂/mp-TiO₂:MAPbI₃/PIF8-TAA-device in spite of the unfavourable energetic alignment between MAPbI₃ and PIF8-TAA is an interesting result. Other effects except the energy level between perovskite and the HTM may affect charge transfer, because the perovskite material is known for its very low exciton binding energy or its ability to act as a free electron-hole carrier.²⁷

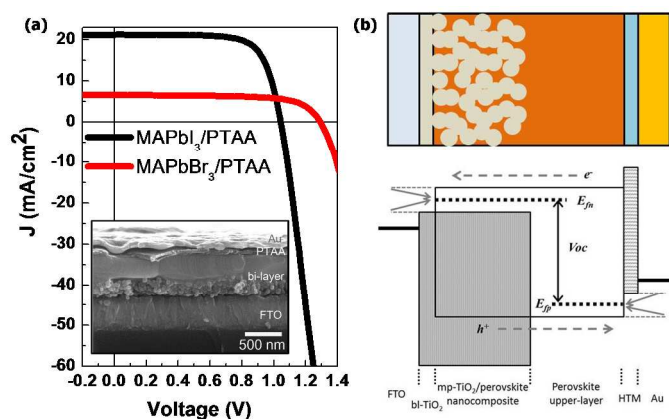


Fig 3. (a) J - V characteristics for MAPbI₃-PTAA, and MAPbBr₃-PTAA devices. Insert shows a cross-sectional SEM image of the bi-layer architecture device (FTO/bl-TiO₂/mp-TiO₂:MAPbBr₃/PTAA/Au). (b) Schematic of the bi-layered device architecture and its energy band diagram. E_{fn} and E_{fp} are the electron and hole quasi-Fermi levels, which are determined by the interaction between TiO₂ and the perovskite and between the perovskite and the HTM, respectively.

J - V characteristics and photovoltaic parameters of MAPbI₃ and MAPbBr₃ fabricated with spiro-OMeTAD [(2,2',7,7'-tetrakis(N,N -di- p -methoxyphenylamine) -9,9'-spirobifluorene)] as low-

molecular HTM were given in Fig. S3 and table S1. We see that the use of spiro-MeOTAD, which has higher HOMO level than that of PTAA, resulted in a decrease of the V_{oc} for both MAPbI₃ and MAPbBr₃. Therefore, our results further suggest that the energy level of the contact materials could have a strong impact on the deliverable energy of photoinduced charges. However, it is important to select energetically favourable contact materials with the HOMO well-aligned to the VBE of the perovskite to maximize the energy output.

Fig. 3a compares the J - V characteristics for MAPbI₃ and MAPbBr₃ perovskite solar cells using PTAA as the HTM. The cross-sectional image of a representative device is inserted in Fig. 3a. In comparison of the V_{oc} value for FTO/bl-TiO₂/mp-TiO₂:MAPbBr₃/PTAA with that of FTO/bl-TiO₂/mp-TiO₂:MAPbI₃/PTAA, the V_{oc} can be increased from 1.04 V to 1.29 V simply by changing the perovskite material from MAPbI₃ to MAPbBr₃ in the same sandwich structure between mp-TiO₂ and PTAA. This result reveals that the perovskite materials obviously contribute to E_{fn} and E_{fp} within the device. As shown in Fig. 1b, MAPbBr₃, with a wider band gap (2.3 eV) than MAPbI₃ (1.55 eV), has a lower VBE (5.68 eV) and a higher conduction band edge (CBE, 3.38 eV) as compared to MAPbI₃. Therefore, when E_{fn} and E_{fp} are built-up within the device under light illumination, MAPbBr₃ might lead to a larger difference between E_{fn} and E_{fp} as compared to MAPbI₃, in spite of using the same electron (TiO₂) and hole extracting layers (PTAA), thus resulting in higher V_{oc} . This is not expected in sensitized solar cells, because the FTO/bl-TiO₂/mp-TiO₂:MAPbBr₃/PTAA/Au device shows a higher V_{oc} of 1.29 V than the potential difference (1.16 eV) between the CBM (-4.0 eV) of TiO₂ and the HOMO level (-5.16 eV) of PTAA. Consequently, as depicted in Fig. 3b, the CBE level of the MAPbBr₃ can manipulate the voltage output of mp-TiO₂-perovskite/perovskite/HTM bilayer junction cell. Based on this reasoning, a remarkably high voltage (1.40 V) device has been realized by judicious selection of the perovskite and HTM. This also means the energy gap with charge separation significantly dominates the voltage output.

Summary

In summary, we have fabricated mp-TiO₂/MAPbI₃ and MAPbBr₃ perovskite as the light harvester, and P-TAA, PF8-TAA, PIF8-TAA as HTMs. The V_{oc} in MAPbBr₃ perovskite cells was increased from 1.29 V of P-TAA to 1.36 V of PF8-TAA and 1.40 V of PIF8-TAA with a deeper HOMO level. In addition, the V_{oc} was decreased from 1.29 V to 1.04 V by using MAPbI₃ in the place of MAPbBr₃ with the same configuration and HTM (PTAA). This result reveals that both the perovskite materials and the HOMO level of the HTM determine the high voltage output in our devices. The MAPbBr₃-based perovskite device displayed a remarkably higher V_{oc} of 1.40 V, with an FF of 79%, due to the deep HOMO level and superior hole mobility, as well as a high PCE to 6.7%, when PIF8-TAA was used as the HTM. The present study demonstrates the main roles of the HTMs and perovskite light harvester in determining the V_{oc} and

provides a suitable strategy for the design and development of perovskite-based solar cells showing a high V_{oc} , FF, and significantly improved PCE.

Acknowledgements

This work was supported by the Global Research Laboratory (GRL) Program, the Global Frontier R&D Program on Center for Multiscale Energy System funded by the National Research Foundation in Korea, and by a grant from the KRICT 2020 Program for Future Technology of the Korea Research Institute of Chemical Technology (KRICT), Republic of Korea

Notes and references

^a Division of Advanced Materials, Korea Research Institute of Chemical Technology, 141 Gajeong-Ro, Yuseong-Gu, Daejeon 305-600, Republic of Korea.

^b Department of Energy Science, Sungkyunkwan University, 2066 Seoburo, Jangan-gu, Suwon 440-746, Republic of Korea.

† Electronic Supplementary Information (ESI) available: A description on detailed experimental process, and characterization. See DOI: 10.1039/c000000x/

* To whom correspondence should be addressed. E-mail: seoksi@kRICT.re.kr or seoksi@skku.edu

‡ These two authors contributed equally to this work.

1. J. A. Chang, S. H. Im, Y. H. Lee, H.-J. Kim, C.-S. Lim, J. H. Heo and S. I. Seok, *Nano. Lett.*, 2012, **12**, 1863–1867.
2. Y. C. Choi, T. N. Mandal, W. S. Yang, Y. H. Lee, S. H. Im, J. H. Noh and S. I. Seok, *Angew. Chem. Int. Ed.*, 2014, **53**, 1329–1333.
3. Y. C. Choi, Y. H. Lee, S. H. Im, J. H. Noh, T. N. Mandal, W. S. Yang and S. I. Seok, *Adv. Energy Mater.* DOI:10.1002/aenm.201301680.
4. Y. C. Choi, D. U. Lee, J. H. Noh, E. K. Kim and S. I. Seok, *Adv. Func. Mater.* DOI: 10.1002/adfm.201304238.
5. M. M. Lee, J. Teuscher, T. Miyasaka, T. N. Murakami and H. J. Snaith, *Science* 2012, **338**, 643–647
6. H.-S. Kim, C.-R. Lee, J.-H. Im, K.-B. Lee, T. Moehl, A. Marchioro, S.-J. Moon, R. Humphry-Baker, J.-H. Yum, J. E. Moser, M. Grätzel, and N.-G. Park, *Sci. Rep.* 2012, **2**(591), 1-7.
7. J. H. Heo, S. H. Im, J. H. Noh, T. N. Mandal, C.-S. Lim, J. A. Chang, Y. H. Lee, H. Kim, A. Sarkar, M. K. Nazeeruddin, M. Grätzel and S. I. Seok, *Nat. Photon.* 2013, **7**, 486–491.
8. J. H. Noh, S. H. Im, J. H. Heo, T. N. Mandal and S. I. Seok, *Nano Lett.*, 2013, **13**, 1764–1769.
9. A. J. Nozik, *Chem. Phys. Lett.*, 2008, **457**, 3–11.
10. A. Kojima, K. Teshima, Y. Shirai and T. Miyasaka, *J. Am. Chem. Soc.*, 2009, **131**, 6050–6051.
11. J.-H. Im, C.-R. Lee, J.-W. Lee, S.-W. Park and N.-G. Park, *Nanoscale*, 2011, **3**, 4088–4093.
12. J. Burschka, N. Pellet, S.-J. Moon, R. Humphry-Baker, P. Gao, M. K. Nazeeruddin and M. Grätzel, *Nature*, 2013, **499**, 316–319.
13. M. Liu, M. B. Johnston and H. J. Snaith, *Nature*, 2013, **501**, 395–398.
14. S. D. Stranks, G. E. Eperon, G. Grancini, C. Menelaou, M. J. P. Alcocer, T. Leijtens, L. M. Herz, A. Petrozza and H. J. Snaith, *Science*, 2013, **342**, 341–344.

Journal Name

15. G. Xing, N. Mathews, S. Sun, S. S. Lim, Y. M. Lam, M. Grätzel, S. Mhaisalkar and T. C. Sum, *Science*, 2013, **342**, 344-347.
16. N. J. Jeon, J. H. Noh, Y. C. Kim, W. S. Yang, S. Ryu and S. I. Seok, submitted
17. E. Edri, S. Kirmayer, M. Kulbak, G. Hodes and D. Cahen, *J. Phys. Chem. Lett.*, 2014, **5**, 429-433.
18. B. Cai, Y. Xing, Z. Yang, W.-H. Zhang and J. Qiu, *Energy Environ. Sci.*, 2013, **6**, 1480-1485.
19. W. Zhang, J. Smith, R. Hamilton, M. Heeney, J. Kirkpatrick, K. Song, S. E. Watkins, T. Anthopoulos and I. McCulloch, *J. Am. Chem. Soc.*, 2009, **131**, 10814-10815.
20. H. Nishi, T. Nagano, S. Kuwabata and T. Torimoto, *Phys. Chem. Chem. Phys.*, 2014, **16**, 672-675.
21. B. I. MacDonald, A. Martucci, S. Rubanov, S. E. Watkins, P. Mulvaney and J. J. Jasieniak, *ACS Nano*, 2012, **6**, 5995-6004.
22. J. Hwang, E.-G. Kim, J. Liu, J.-L. Bre´das, A. Duggal and A. Kahn, *J. Phys. Chem. C* 2007, **111**, 1378-1384.
23. B. A. Gregg and M. C. Hanna, *J. Appl. Phys.*, 2003, **93**, 3605-3614.
24. E. J. Juarez-Perez, M. Wußler, F. Fabregat-Santiago, K. Lakus-Wollny, E. Mankel, T. Mayer, W. Jaegermann, and I. Mora-Sero, *J. Phys. Chem. Lett.*, 2014, **5**, 680-685.
25. H.-S. Kim, I. Mora-Sero, V. Gonzalez-Pedro, F. Fabregat-Santiago, E. J. Juarez-Perez, N.-G. Park and J. Bisquert, *Nat. Commun.*, 2013, **4**, 2242.
26. J. Gao, J. M. Luther, O. E. Semonin, R. J. Ellingson, A. J. Nojik and M. C. Beard, *Nano Lett.*, 2011, **11**, 1002-1008.
27. P. Docampo, J. M. Ball, M. Darwich, G. E. Eperon and H. J. Snaith, *Nat. Commun.*, 2013, **4**, 2761.

TOC

The voltage output of perovskite solar cells is found to be dependent on both energy level of perovskite itself as solar absorber and the hole transporting materials.

