

Energy & Environmental Science

Accepted Manuscript




This is an *Accepted Manuscript*, which has been through the Royal Society of Chemistry peer review process and has been accepted for publication.

Accepted Manuscripts are published online shortly after acceptance, before technical editing, formatting and proof reading. Using this free service, authors can make their results available to the community, in citable form, before we publish the edited article. We will replace this *Accepted Manuscript* with the edited and formatted *Advance Article* as soon as it is available.

You can find more information about *Accepted Manuscripts* in the [Information for Authors](#).

Please note that technical editing may introduce minor changes to the text and/or graphics, which may alter content. The journal's standard [Terms & Conditions](#) and the [Ethical guidelines](#) still apply. In no event shall the Royal Society of Chemistry be held responsible for any errors or omissions in this *Accepted Manuscript* or any consequences arising from the use of any information it contains.

Table of Contents

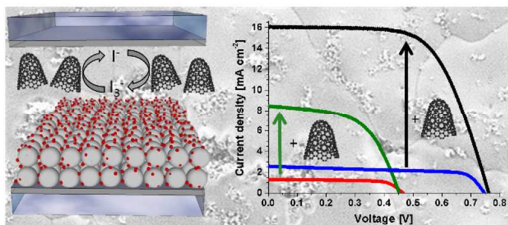

For the first time, carbon nanohorns were implemented into solid-state and quasi-solid-state electrolytes for highly efficient DSSCs yielding efficiencies of up to 7.84% at room temperature.

COMMUNICATION

Carbon Nanohorn-based electrolyte for Dye-Sensitized Solar Cells

Cite this: DOI: 10.1039/x0xx00000x

F. Loder Meyer,^a R. D. Costa,^a R. Casillas,^a F. T. U. Kohler,^b P. Wasserscheid,^b M. Prato,^c and D. M. Guldi^a

Received 00th January 2014,

Accepted 00th January 2014

DOI: 10.1039/x0xx00000x

www.rsc.org/

For the first time, carbon nanohorns were implemented into solid-state electrolytes for highly efficient solid-state and quasi-solid-state DSSCs. They feature an effective catalytic behavior towards the reduction of I_3^- and enhance the I_3^- diffusivity into the electrolyte. In a final device, solar cells with 7.84% efficiency at room temperature were achieved. As a matter of fact, this is the highest reported efficiency for nanocarbon-based electrolytes up to date.

Dye-sensitized solar cells (DSSCs) are a promising alternative to convert solar energy, especially when compared to conventional silicon-based technologies. In this context, material costs and facile fabrication processes are valuable assets.¹ Typically, in n-type DSSCs, one or several dyes are anchored to a mesoporous semiconducting electrode, for example, TiO_2 or ZnO . Upon light excitation of the dye, the latter injects electrons into the conduction band of the semiconductor electrode followed by the reduction of the oxidized dyes by the electrolyte. Under such conditions, the injected electrons perform work through an external load before they reduce the electrolyte at the platinum counter-electrode.^{2,3} Several decades of continuous optimizations resulted in state-of-the-art efficiencies in the range from 10 to 13%.^{4,5}

Under operation, the electrolyte plays a key role in terms of fully functioning DSSCs. To this date, the I^-/I_3^- redox couple is the most commonly used redox pair. Nevertheless, it suffers severe limitations including inherent corrosive nature, distinct absorption features in the visible region, and a prominent charge recombination arising from I_3^- ion pair formation at the electrode surface.⁶ Furthermore, its use in the form of liquid-based electrolytes impacts the long-term stability owing to solvent evaporation and I_3^- induced corrosion at electrode contacts. All of the aforementioned has fueled research on iodine-free

and solid-state dye-sensitized solar cells (ssDSSCs).⁷ Notably, despite all efforts, ssDSSCs feature efficiencies of around 8%,⁸ which are much inferior compared to liquid-based electrolytes.

In light of the aforementioned, novel concepts for efficient iodine-free and solid-state electrolytes are currently among the major challenges in the field of ssDSSC. To the best of our knowledge, there are several approaches to replace liquid-based electrolytes without compromising the solar cell performance. Firstly, the design of novel photoanodes to enhance the penetration of the electrolyte into the pores is considered.⁹ As a very recent example, Ahn *et al.* reported a novel honeycomb TiO_2 nanostructure for ssDSSCs yielding an efficiency of 7.4%.¹⁰ Secondly, iodine-free alternatives for ssDSSCs such as hole transport materials¹¹ and conductive polymers¹² are under investigation. Starting with the first report by Bach *et al.* in 1998,¹³ continuous improvements led to efficiencies of around 6% in, for example, spiro-OMeTAD-based ssDSSCs.¹¹ Thirdly, the replacement of conventional dyes by perovskites in combination with spiro-OMeTAD has recently boosted the efficiencies to more than 15%.¹⁴ Finally, the use of carbonaceous materials – carbon black,^{15,16} single- and multi-walled carbon nanotubes,^{17,18} and several graphene derivatives¹⁹ – as additives to iodine-free and solid-state electrolytes is emerging.^{7,20} Among them, the benefits of implementing nanocarbons stand out given i) better ionic diffusion throughout the electrolyte, ii) catalytic activity towards the reduction of I_3^- to I^- , iii) dye regeneration to reach yields that are almost unity, and iv) reduction of the internal device resistance by quasi-zero distances between oxidized dyes and the counter-electrode.^{16,21} To this end, using multi-walled carbon nanotubes based electrolytes 6.86% efficiencies evolved after continuous optimization steps.²² But, integrating nanocarbons into DSSCs by means of solution-based

techniques is still the major bottleneck of this approach due to nanocarbon bundling in solution and poor nanocarbon solubility. In the current work, we present the implementation of carbon nanohorns (CNH) into solid-state electrolytes. CNHs are conical structures with diameters between 2 and 5 nm and a length from 30 to 50 nm. In solution, they tend to associate into roundish aggregates of around 100 nm (Figure 1 and supporting information (SI) for further details).²³ Notably, the interest in CNHs has recently been intensified given their metal-free synthesis, semiconductor character, and relatively easy suspendibility in organic solvents.²⁴ CNHs have, however, never been tested inside DSSC electrolytes, despite recent reports on the benefits of CNH-based interlayers and CNH doping of TiO₂-based photoanodes.^{24,25} In the present study, we have realized an iodine-free and highly-efficient ssDSSC based on a mixture of 1-ethyl-3-methylimidazolium iodide ([EMIM]I), several additives, and CNHs. After a series of optimization steps, our ssDSSCs feature 7.84% efficiency under room temperature conditions, which exceeds that seen in current state-of-the-art nanocarbon-based ssDSSCs.²⁶

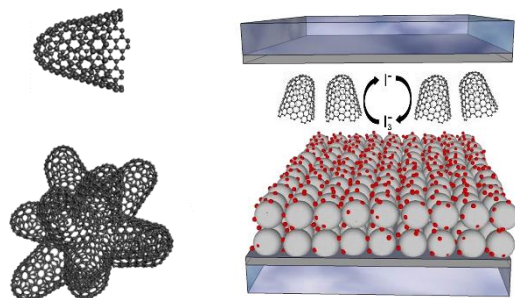


Figure 1. Left: Representation of a CNH (top), and a bundle-like CNH aggregate present in solution (bottom). Right: Schematic representation of a ssDSSC containing CNHs in the electrolyte.

First, we elucidated the optimum [EMIM]I to CNH weight ratios for their application as solid-state electrolytes. In particular, different amounts of [EMIM]I were added to acetonitrile suspensions of CNHs (37 mg/mL) and the solvent was slowly evaporated at 80 °C under vigorous stirring conditions until a viscous binary mixture was left – for more details see SI. [EMIM]I to CNH weight ratios of 10:1, 5:1, and 1:1 wt% were realized. Higher CNH amounts could not be achieved due to immiscibility. Electrolytes with 1-butyl-3-methylimidazolium tetrafluoroborate ([BMIM][BF₄]) as crystal growth inhibitor and with 4-*tert*-butylpyridine (TBP) as well as guanidinium thiocyanate (GuSCN) as additives were also prepared by the same procedure – for more details see SI. [BMIM][BF₄] was added to enhance the electrode coverage, whereas TBP and GuSCN assisted in preventing the back-electron-transfer processes and improving the dye regeneration, respectively.³

Differential scanning calorimetry (DSC) was employed to probe the effect of CNH addition on the transition temperatures, that is, from the solid to the liquid phase and *vice versa*, by heating up to 120 °C and subsequent cooling down to 0 °C (Figure S4). Upon heating, a similar solid-to-liquid transition at around 74 °C was noted for bare [EMIM]I and [EMIM]I/CNH mixtures. During cooling, [EMIM]I forms the solid phase at room temperature. In stark contrast, [EMIM]I/CNH mixtures show a liquid-to-solid phase transition, which onsets independently on the amount of CNHs at around 45 °C.

A likely rationale implies that CNHs induce crystallization. As a consequence, the hysteresis temperature shift from the liquid to the solid phases is reduced from 54 to 29 °C for pure [EMIM]I and CNH containing mixtures. Addition of [BMIM][BF₄] leads to featureless DSCs due to a melting point beyond 0 °C. Likewise, after addition of TBP and GuSCN the [EMIM]I/CNH mixtures are at room temperature best described as ionic liquids.

Information about the morphology of the [EMIM]I/CNH electrolytes came from scanning electron microscopy (SEM) measurements. Figure S5 documents the impact of CNHs onto the features of the [EMIM]I matrix. For example, the homogenous [EMIM]I crystal arrangement is disrupted upon CNH addition. Now, [EMIM]I reveal grain boundaries, into which the CNHs are integrated. In the presence of [BMIM][BF₄], TBP, or GuSCN, the low viscosity of the samples hampered a meaningful SEM analysis.

Next, the ionic diffusivity of the electrolytes was measured by means of linear sweep voltammetry (LSV). Here, the anodic and cathodic steady-state polarization diffusion current densities (J_{ss}) of the electrolyte sandwiched between two fluorine-doped tin oxide (FTO) electrodes coated with platinum are monitored – i.e., FTO-Pt/electrolyte/Pt-FTO.¹⁷ Increasing the CNH content leads to higher J_{ss} in [EMIM]I/CNH (Figure S6). The lowest J_{ss} is, indeed, observed for pure [EMIM]I (**E1**). In contrast, the highest J_{ss} evolves for the [EMIM]I/CNHs mixture with a 1:1 wt% ratio (**E2**). As a matter of fact, the same observation holds for electrolytes with [BMIM][BF₄], TBP, and GuSCN, that is, [EMIM]I/[BMIM][BF₄]/TBP/GuSCN with a weight ratio of 1:0.25:0.83:0.17 (**E3**) and with the optimized amount of CNHs [EMIM]I/CNHs/[BMIM][BF₄]:TBP:GuSCN with weight ratios of 1:1:0.25:0.83:0.17 (**E4**). Please note that **E2** and **E4** feature almost the same J_{ss} (Figure S6). From the latter we conclude that upon addition of CNHs to the electrolyte the ionic diffusivity increases. This is a crucial prerequisite for highly efficient dye regeneration under device operation conditions.

To corroborate our findings, the aforementioned FTO-Pt/electrolyte/Pt-FTO cell configuration was investigated by means of electrochemical impedance spectroscopy (EIS).²⁷ This is meant to provide insights into the charge transfer resistance across the different interfaces. Figure S7 depicts the Nyquist plots and the equivalent electrical circuits. Two semicircles are discernable each at a well distinct frequencies. Firstly, a 1000 – 10000 Hz semicircle in the Nyquist plot relates to the charge transfer resistance (R_{Pt}) and the corresponding Helmholtz capacitance (C_{Pt}) at the FTO-Pt/electrolyte interface. Secondly, the 0.1 – 100 Hz semicircle correlates with the resistance of the Warburg diffusion of the I⁻/I₃⁻ redox pair in the bulk electrolyte (R_{diff}). With this data at hand, the effective diffusion coefficient (D_{diff}) of the electrolyte can be calculated by using equation 1:²⁷

$$D_{diff} = \frac{(k_B * T)}{(m^2 * q^2 * N * [I_3^-] * R_{diff} * \delta)} \quad \text{eq. 1}$$

Here, k_B is the Boltzmann constant, T the absolute temperature, m the number of transferred electrons in the reaction, q the elementary charge, and N the Avogadro constant.

EIS analysis of the FTO-Pt/electrolyte/Pt-FTO cells confirms the two major assumptions made when implementing CNHs into the electrolyte, namely improving the catalytic reduction of I₃⁻ to I⁻ and

facilitating ionic diffusivity as noted from the LSV assays. The former is confirmed by lower R_{Pt} , which ultimately relates to the resistance to catalysis at the electrode interface. In particular, R_{Pt} gradually reduces from 190.47 to 44.84, 28.13, and to 7.38 Ω for [EMIM]I/CNH ratios of 1:0, 10:1, 5:1, and 1:1, respectively. Especially, the 26-fold reduction of R_{Pt} in **E2** relative to **E1** corroborates an improved catalytic behavior of CNHs towards the I_3^- reduction (Table S1 and Figure S7). Reassuring is the fact that the absence and the presence of CNHs in **E3** and **E4** reduces R_{Pt} from 167.33 to 41.21 Ω , respectively. Finally, we were also able to confirm the latter. As a matter of fact, CNHs in the electrolyte drastically results in increasing D_{diff} , since R_{diff} decreases from 2676.10 to 477.65, 205.63, and to 35.86 Ω for [EMIM]I/CNH ratios of 1:0, 10:1, 5:1, and 1:1, respectively (Table S1 and Figure S7) as well as from 781.04 to 31.39 Ω for **E3** and **E4**, respectively. By using equation 1, we confirm that D_{diff} increases drastically from 7.55×10^{-12} to 0.42×10^{-10} , 0.98×10^{-10} , and to $5.63 \times 10^{-10} \text{ m}^2 \text{ s}^{-1}$ for [EMIM]I/CNH ratios of 1:0, 10:1, 5:1, and 1:1, respectively. Likewise, D_{diff} increases from $0.26 \times 10^{-10} \text{ m}^2 \text{ s}^{-1}$ for **E3** to $6.44 \times 10^{-10} \text{ m}^2 \text{ s}^{-1}$ for **E4**.

To prove the effects of the implementation of CNHs into the electrolyte on the device performance, we prepared TiO_2 -based ssDSSCs with cis-diisothiocyanato-bis(2,2'-bipyridyl-4,4'-dicarboxylato) ruthenium(II) bis(tetra-butylammonium) (N719) using electrolytes without CNHs (**E1** and **E3**) and with CNHs (**E2** and **E4**). Figure 2 depicts the current-voltage (J-V) curves, while Table 1 summarizes the device performance features of ssDSSCs.

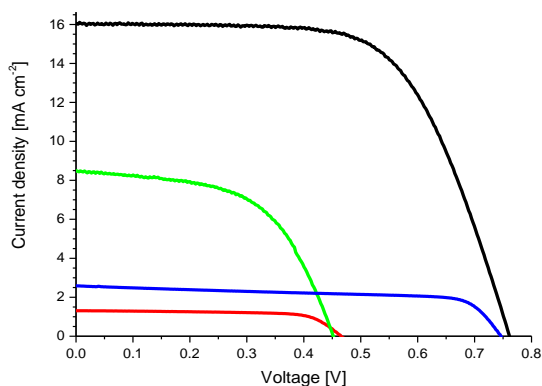


Figure 2. J-V curves of devices with **E1** (red) and **E2** (green) measured at 70 °C as well as devices with **E3** (blue) and **E4** (black) measured at room temperature.

At room temperature, the initial efficiencies (η) of ssDSSCs with **E1** and that with different CNH-amounts were all around 0.01% caused by low fill factors (FF) and low short-circuit current densities (J_{sc}) (Figure S8). This fact is expected due to the solid-state nature of the electrolytes. Upon heating, the device performance starts to improve at temperatures close to the melting point of the electrolytes, plateauing at around 70 °C in good agreement with the DSC measurements. Here, the liquid phase enables, on one hand, a better electrode coverage and, on the other hand, a better ion diffusion throughout the electrolyte. Overall, higher FF and J_{sc} evolve. Upon cooling to room temperature, the electrolytes remain in their liquid phase as seen in DSC measurements – *vide supra* – and impact the

ssDSSC performance. Figure S9 attests that at temperatures above the melting point, the efficiency is still at its maximum regardless of the number of heating-cooling cycles. Even more striking is the fact that after the first cycle, the high temperature maximum efficiency remains even at room temperature and only slowly decreases as a function of time (Figure S10).

Table 1. ssDSSC performance and EIS parameters obtained under AM1.5 conditions and 1 sun illumination

Electrolyte	J_{sc} [mA/cm ²]	V_{oc} [V]	FF	η [%]	R_{Pt} [Ω]	R_{diff} [Ω]	D_{diff} [$\times 10^{-10} \text{ m}^2 \text{ s}^{-1}$]
E1 ^a	1.27	0.47	0.71	0.42	190.47 ^c	1966.10	0.10
E2 ^a	8.29	0.45	0.56	2.09	7.57	26.54	7.61
E3 ^b	2.59	0.75	0.67	1.29	7.99	273.48	0.74
E4 ^b	16.03	0.76	0.64	7.84	1.81	7.66	26.38

^a measured at 70 °C. ^b measured at room temperature. ^c measured between two Pt electrodes.

Overall, upon increasing the CNH content inside [EMIM]I, the efficiency improves, owing to a boost in the J_{sc} (Table S2 and Figure S8). Among all of the electrolytes, devices with [EMIM]I/CNHs at a 1:1 wt% ratio (**E2**) show the best ssDSSC performance, in line with LSV and EIS measurements – *vide supra*. In details, **E2** ssDSSCs feature open-circuit voltage (V_{oc}) of 0.45 V, J_{sc} of 8.29 mA cm⁻², FF of 0.56, and η of 2.09% (Table 1 and Figure 2). On the contrary, **E1** ssDSSC show V_{oc} of 0.47 V, J_{sc} of 1.27 mA cm⁻², FF of 0.71, and η of 0.42%. Mainly responsible for the 5-fold improvement in efficiency is a higher J_{sc} with CNHs in the electrolyte.

Quite likely, the major bottleneck of the aforementioned electrolytes relates to their penetration into the mesoporous network. However, this aspect should not be applicable to **E3** and **E4** devices, in which the presence of additives such as [BMIM][BF₄] transforms them into ionic liquids at room temperature – *vide supra*. To provide a fair comparison between the performances, devices with **E1** and **E2** were measured at 70 °C, whereas those with **E3** and **E4** were measured at room temperature. As expected from our previous results with **E1** and **E2** ssDSSCs, **E3** ssDSSCs featured V_{oc} of 0.74 V, J_{sc} of 1.17 mA cm⁻², FF 0.70, and η of 0.61%, whereas **E4** ssDSSCs exhibited V_{oc} of 0.76 V, J_{sc} of 16.03 mA cm⁻², FF of 0.64, and η of 7.84% (Table 1 and Figure 2). Notably, both devices feature comparable V_{oc} and FF, only J_{sc} increases by a factor of nearly 6. This is also valid when comparing devices with **E1** and **E2** – Table 1. The increase in V_{oc} of ssDSSCs with **E3** and **E4** compared with those with **E1** and **E2** is ascribed to the use of additives.²⁸

Decisively, the latter was confirmed in EIS measurements with **E1**, **E2**, **E3**, and **E4** devices (Table 1 and Figure 3). Two findings should be highlighted. Firstly, a direct comparison between **E3** and **E4** devices demonstrates the catalytic behavior of CNHs in terms of reducing I_3^- , since R_{Pt} is lowered from 7.99 to 1.81 Ω for **E3** and **E4**, respectively (Table 1 and Figure 3). Due to the poor ionic diffusivity of **E1**, it was impossible to dissect R_{Pt} , since the interface between TiO_2 and Pt is not distinguishable and, as a consequence, the frequencies in the Bode phase of both interfaces coalesce (Figure S11). Secondly, R_{diff} drops from 1966.10 Ω for **E1** to 26.54 Ω for **E2** and similarly from 273.48 Ω for **E3** to 7.66 Ω for **E4**. This prompts to an ion diffusivity, which increases upon CNH addition (Table 1). Here, **E1** exhibits a D_{diff} of $0.10 \times 10^{-10} \text{ m}^2 \text{ s}^{-1}$, while that of **E2**

increases to $7.61 \times 10^{-10} \text{ m}^2 \text{ s}^{-1}$ due to a lower charge transport resistance (Table 1). Among all of the electrolytes, **E4** features the highest diffusion coefficient of $26.38 \times 10^{-10} \text{ m}^2 \text{ s}^{-1}$. It is safe to conclude at this point that the major impact of CNHs as an integrative part of the electrolytes is on the Warburg diffusion resistance and on the catalytic I_3^- reduction. The net result of the aforementioned is an appreciably increased dye regeneration rate, which leads to higher short-circuit current densities, and, in turn, to enhanced η . To demonstrate the lack of regeneration limits, **E4** devices were measured at different illumination intensities (Figure S12). Given the linear relationship between light intensity and the J_{SC} , on one hand, and an ordinate intercept of nearly zero, on the other hand, we postulate that the electrolyte effectively regenerates the oxidized dye even under high illumination conditions.

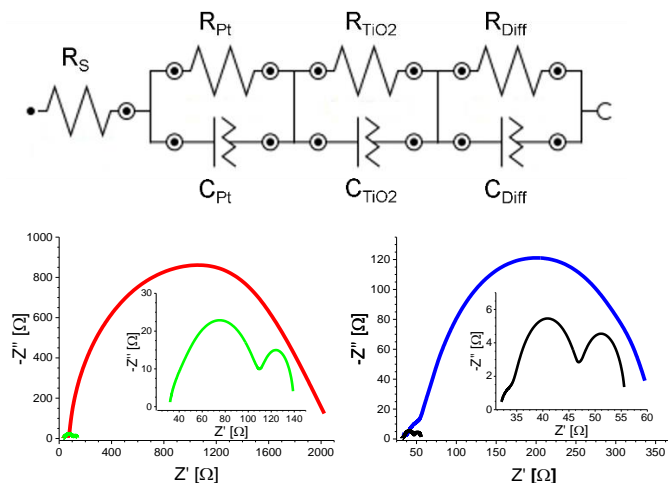


Figure 3. Upper part: Equivalent circuit for EIS analysis. Left bottom part: Nyquist plots of devices with **E1** (red) and **E2** (green) measured at 70 °C. Right bottom part: Nyquist plots of devices with **E3** (blue) and **E4** (black) measured at room temperature.

Finally, interactions between CNHs and the electrolyte were probed in time-dependent J-V and EIS measurements of DSSCs with **E3** and **E4** – Figures 4 and 5. As time progresses, ssDSSCs with **E3** and **E4** feature nearly similar V_{OC} , but J_{SC} decreases for ssDSSCs with **E3** by nearly 75%. In contrast, J_{SC} of devices with **E4** show a loss of only 9%. This is likely to relate to the dye degradation *via*, for example, substitution of the SCN^- groups by I^- when reacting with either I_3^- or polyiodide, which are formed in close proximity to the electrode surface.^{29,30} This impacts the overall dye regeneration. Negligible J_{SC} decrease for **E4** indicates, however, that CNHs support efficient electrolyte regeneration and, in turn, prevent dye degradation.

Interesting is the gradual increase of the FF in ssDSSCs with **E4**, while for ssDSSCs with **E3** the FF raises only during the first day while remaining constant afterwards – Figure 4. We rule out, however, a better electrolyte coverage of the dye-sensitized mesoporous network, owing to improved penetration as the reason for the continuous increase of the FF of ssDSSCs with **E4**.

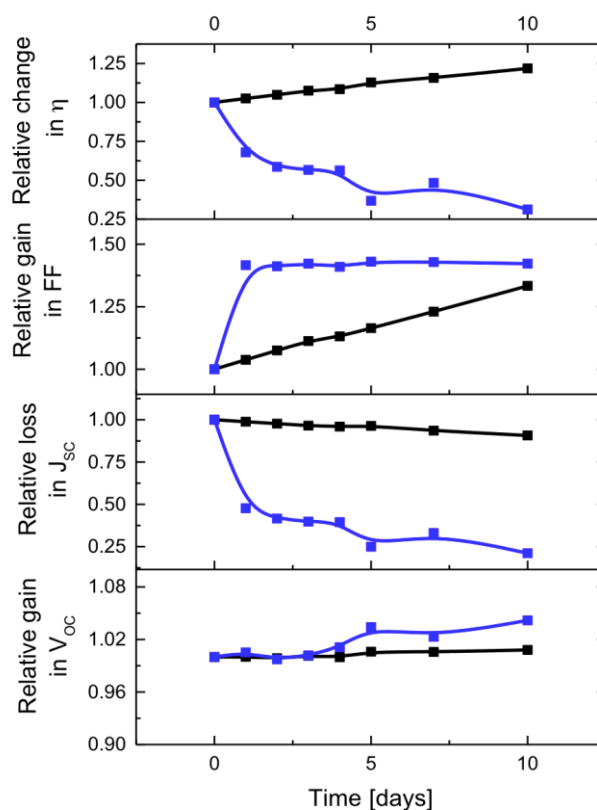


Figure 4. Time-dependent changes of the figures-of-merit for ssDSSCs with **E3** (blue) and **E4** (black).

To shed light onto this finding, we performed EIS analysis. R_{diff} of ssDSSCs with **E3** is not affected over time, while ssDSSCs with **E4** exhibit a 71% decrease in R_{diff} – Figure 5. Similarly, R_{Pt} drops considerably after the first day, but remains from there on constant. A better contact between the electrolyte and the counter electrode is likely to be responsible for this trend. After five days a considerable R_{TiO_2} increase sets in for devices with **E3**. The latter is attributed to the $\text{SCN}^- / \text{I}^-$ exchange of the dye and / or the I_3^- induced corrosion of the TiO_2 surface.²⁹ For devices with **E4**, R_{TiO_2} remains constant. Here, sufficient electrolyte regeneration and considerably reduced exposure of I_3^- to the electrode evoke long-term stability of DSSCs. Taking all of the aforementioned into account, it is not surprising that the efficiency of ssDSSCs with **E3** drops to 37%, while that of **E4** increases by 22% from its initial value after 10 days. This clearly highlights the superior performance of CNHs-based electrolytes in terms of efficiency and stability.

Finally, it is important to point out that our findings ~~this~~ leaves the question unanswered on how CNHs improve the electrolyte features over time. To rationalize the time dependence we carried out Raman experiments of **E4** extracted from different devices after 1, 2, 3, 4, and 10 days of operation – Figure S13. Raman results, namely the ratio intensification between the D and G bands from 1.08 to 1.21 for 0 and 10 days of exposure of the CNHs to the electrolyte, respectively, infer a gradual increase of defects. In other words, the trends for R_{diff} and D/G ratio go hand-in-hand – Figures 5 and S13, from which conclude that the benefits upon adding CNHs correlate with the reaction

between CNHs and I_3^-/I^- . Here, defect loaded CNHs facilitate the diffusivity of the electrolyte and / or even reduce the I_3^- and polyiodide concentrations at the electrode/dye surface. Both effects are synergetic and lead to a gain in FF, which prompts to a suppression of electron recombinations with the electrolyte,³¹ and stable J_{SC} due to the lack of both dye and electrolyte degradation. Still an open question is if the use of CNHs is self-limiting in terms of degradation or if, on the contrary, defects act as catalytic centers to further enhance the electrolyte features as our time-dependent assays suggest.

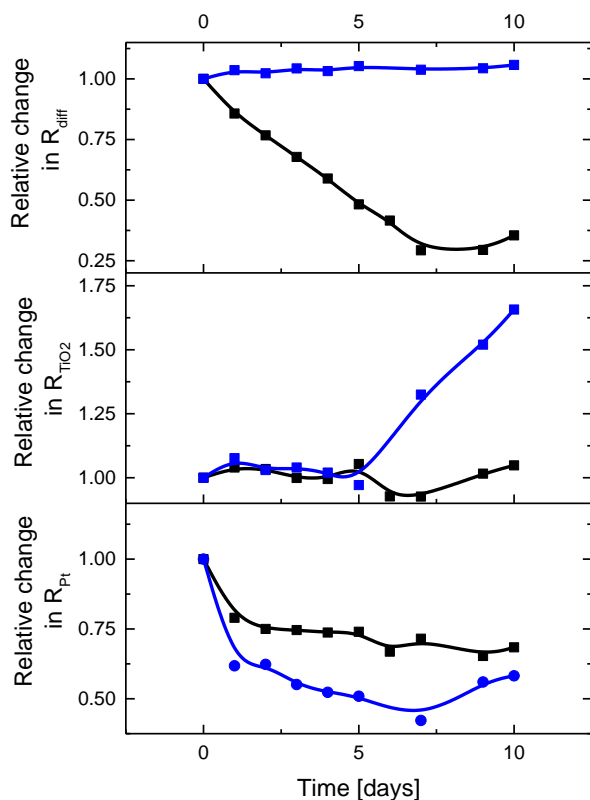


Figure 5. Time-dependent changes of the figures-of-merit from EIS measurement of ssDSSCs with E3 (blue) and E4 (black).

Conclusions

In summary, we have successfully implemented for the first time CNHs into ssDSSC electrolytes. Thereby, ssDSSCs without CNHs exhibited rather poor performance of 0.42%, which was improved up to 2.09% upon the addition of CNHs. As such, CNHs inside solid-state electrolytes impressively enhance J_{SC} , whereas V_{OC} and FF remained almost unchanged. We were able to attribute the boost in J_{SC} to a better ionic diffusivity in the electrolyte as well as to a more effective catalytic reduction of I_3^- by CNHs. This enables effective dye regeneration due to a quasi-zero distance between oxidized dyes and the counter electrode. Optimized devices with [BMIM][BF₄], TBP, and GuSCN as additives feature efficiencies of 7.84% with CNHs and only 0.61% without CNHs. Striking is the long-term stability when CNHs are used, an affect that led to better diffusivity of the electrolyte and to an effective suppression of dye degradation.

Here, a reaction between CNHs and I_3^-/I^- not only in fresh devices but also as time progresses seems to evolve as a likely rationale. This notion is supported by the correlation between CNH defects and the increase in FF and stable J_{SC} . Ongoing work focuses on transient absorption spectroscopy to pinpoint the individual steps in the regeneration processes under device operation conditions as well as to provide more insights into the reaction mechanism between the CNHs and the redox couple. Finally, it is important to point out that the application of an alternative iodide source, which exhibits a better initial performance, could lead to even higher efficiencies.

Acknowledgements

F. L. and R.D.C. acknowledge the EAM cluster in the frame of the DFG excellence programs for their support. D.M.G. acknowledges the DFG, ICMM, and the ZMP for financial and intellectual support. M.P. thanks the Italian Ministry of Education MIUR (cofin Prot. 2010N3T9M4 and Fibr RBAP11C58Y), EU (Carinhyph)

Notes and references

^a Department of Physical Chemistry I, University of Erlangen-Nürnberg, Egerlandstr. 3, 91052, Erlangen, Germany.

^b Department of Chemical and Bioengineering, Reaction Engineering, University of Erlangen-Nürnberg, Egerlandstr. 3, 91058, Erlangen, Germany.

^c Center of Excellence for Nanostructured Materials, Dipartimento di Scienze Chimiche e Farmaceutiche, Università degli Studi di Trieste, Piazzale Europa 1, 34127 Trieste, Italy.

† Footnotes should appear here. These might include comments relevant to but not central to the matter under discussion, limited experimental and spectral data, and crystallographic data.

Electronic Supplementary Information (ESI) available: [details of any supplementary information available should be included here]. See DOI: 10.1039/c000000x/

1. B. O'Regan and M. Grätzel, *Nature*, 1991, **353**, 737–740.
2. L. E. Polander, A. Yella, B. F. E. Curchod, N. Ashari Astani, J. Teuscher, R. Scopelliti, P. Gao, S. Mathew, J.-E. Moser, I. Tavernelli, U. Rothlisberger, M. Grätzel, M. K. Nazeeruddin, and J. Frey, *Angew. Chem., Int. Ed.*, 2013, **52**, 8731–8735.
3. A. Listorti, B. O'Regan, and J. R. Durrant, *Chem. Mater.*, 2011, **23**, 3381–3399.
4. A. Yella, H.-W. Lee, H. N. Tsao, C. Yi, A. K. Chandiran, M. K. Nazeeruddin, E. W.-G. Diao, C.-Y. Yeh, S. M. Zakeeruddin, and M. Grätzel, *Science*, 2011, **334**, 629–634.
5. A. El-Shafei, M. Hussain, A. Atiq, A. Islam, and L. Han, *J. Mater. Chem.*, 2012, **22**, 24048–24056.
6. H. Tian and L. Sun, *J. Mater. Chem.*, 2011, **21**, 10592–10601.
7. L. J. Brennan, M. T. Byrne, M. Bari, and Y. K. Gun'ko, *Adv. Energy Mater.*, 2011, **1**, 472–485.
8. D. K. Roh, W. S. Chi, H. Jeon, S. J. Kim, and J. H. Kim, *Adv. Funct. Mater.*, 2013, **24**, 379–386.
9. M. Grätzel, *Nature*, 2001, **414**, 338–344.
10. S. H. Ahn, W. S. Chi, D. J. Kim, S. Y. Heo, and J. H. Kim, *Adv. Funct. Mater.*, 2013, **23**, 3901–3908.

COMMUNICATION

11. J. Burschka, F. Kessler, M. K. Nazeeruddin, and M. Grätzel, *Chem. Mater.*, 2013, **25**, 2986–2990.
12. J. Kim, J. K. Koh, B. Kim, S. H. Ahn, H. Ahn, D. Y. Ryu, J. H. Kim, and E. Kim, *Adv. Funct. Mater.*, 2011, **21**, 4633–4639.
13. U. Bach, D. Lupo, P. Comte, J. E. Moser, F. Weissörtel, J. Salbeck, H. Spreitzer, and M. Grätzel, *Nature*, 1998, **395**, 583–585.
14. M. Liu, M. B. Johnston, and H. J. Snaith, *Nature*, 2013, **501**, 395–398.
15. C.-P. Lee, P.-Y. Chen, R. Vittal, and K.-C. Ho, *J. Mater. Chem.*, 2010, **20**, 2356–2361.
16. B.-X. Lei, W.-J. Fang, Y.-F. Hou, J.-Y. Liao, D.-B. Kuang, and C.-Y. Su, *J. Photochem. and Photobiol. A: Chem.*, 2010, **216**, 8–14.
17. Y.-H. Chang, P.-Y. Lin, S.-R. Huang, K.-Y. Liu, and K.-F. Lin, *J. Mater. Chem.*, 2012, **22**, 15592–15598.
18. C.-P. Lee, L.-Y. Lin, P.-Y. Chen, R. Vittal, and K.-C. Ho, *J. Mater. Chem.*, 2010, **20**, 3619–3625.
19. M. S. Akhtar, S. Kwon, F. J. Stadler, and O. B. Yang, *Nanoscale*, 2013, **5**, 5403–5411.
20. R. D. Costa, F. Lodermeier, R. Casillas, and D. M. Guldi, *Energy & Environ. Sci.*, 2014, **7**, 1281–1296.
21. V. M. Mohan, K. Murakami, A. Kono, and M. Shimomura, *J. Mater. Chem. A*, 2013, **1**, 7399–7407.
22. Y.-C. Wang, K.-C. Huang, R.-X. Dong, C.-T. Liu, C.-C. Wang, K.-C. Ho, and J.-J. Lin, *J. Mater. Chem.*, 2012, **22**, 6982–6989.
23. D. M. Guldi and N. Martín, *Carbon Nanotubes and Related Structures: Synthesis, Characterization, Functionalization, and Applications*, Wiley, 2010.
24. R. Casillas, F. Lodermeier, R. D. Costa, M. Prato, and D. M. Guldi, *Adv. Energy Mater.*, 2014, 10.1002/aenm.201301577.
25. R. D. Costa, S. Feihl, A. Kahnt, S. Gambhir, D. L. Officer, G. G. Wallace, M. I. Lucio, M. A. Herrero, E. Vázquez, Z. Syrgiannis, M. Prato, and D. M. Guldi, *Adv. Mater.*, 2013, **25**, 6513–6518.
26. R. D. Costa, F. Lodermeier, R. Casillas, and D. M. Guldi, *Energy & Environ. Sci.*, 2014, **7**, 1281–1296.
27. M. Adachi, M. Sakamoto, J. Jiu, Y. Ogata, and S. Isoda, *J. Phys. Chem. B.*, 2006, **110**, 13872–13880.
28. M. K. Nazeeruddin, A. Kay, E. Müller, P. Liska, N. Vlachopoulos, and M. Grätzel, *J. Am. Chem. Soc.*, 1993, **115**, 6382–6390.
29. H. Greijer, J. Lindgren, and A. Hagfeldt, *J. Phys. Chem. B.*, 2001, **105**, 6314–6320.
30. J. R. Jennings, Y. Liu, and Q. Wang, *J. Phys. Chem. C.*, 2011, **115**, 15109–15120.
31. S. Y. Huang, G. Schlichthörl, A. J. Nozik, M. Grätzel, and A. J. Frank, *J. Phys. Chem. B.*, 1997, **5647**, 2576–2582.