

Green Chemistry

Accepted Manuscript



This is an *Accepted Manuscript*, which has been through the Royal Society of Chemistry peer review process and has been accepted for publication.

Accepted Manuscripts are published online shortly after acceptance, before technical editing, formatting and proof reading. Using this free service, authors can make their results available to the community, in citable form, before we publish the edited article. We will replace this *Accepted Manuscript* with the edited and formatted *Advance Article* as soon as it is available.

You can find more information about *Accepted Manuscripts* in the [Information for Authors](#).

Please note that technical editing may introduce minor changes to the text and/or graphics, which may alter content. The journal's standard [Terms & Conditions](#) and the [Ethical guidelines](#) still apply. In no event shall the Royal Society of Chemistry be held responsible for any errors or omissions in this *Accepted Manuscript* or any consequences arising from the use of any information it contains.

ARTICLE

Rare-earth recycling using a functionalized ionic liquid for the selective dissolution and revalorization of $Y_2O_3:Eu^{3+}$ from lamp phosphor waste

David Dupont,^a Koen Binnemans^{a*}

Cite this: DOI: 10.1039/x0xx00000x

Received 00th January 2012,
Accepted 00th January 2012

DOI: 10.1039/x0xx00000x

www.rsc.org/

The supply risk for certain rare-earth elements (REEs) has sparked the development of recycling schemes for end-of-life products like fluorescent lamps. In this paper a new recycling process for lamp phosphor waste is proposed based on the use of the functionalized ionic liquid betainium bis(trifluoromethylsulfonyl)imide, [Hbet][Tf₂N]. This innovative method allows the selective dissolution of the valuable red phosphor $Y_2O_3:Eu^{3+}$ (YOX) without leaching the other constituents of the waste powder (other phosphors, glass particles and alumina). A selective dissolution of YOX is useful because this phosphor contains 80 wt% of the REEs although it only represents 20 wt% of the lamp phosphor waste. The proposed recycling process is a major improvement compared to currently used hydrometallurgical processes where the non-valuable halophosphate (HALO) phosphor $(Sr,Ca)_{10}(PO_4)_6(Cl,F)_2:Sb^{3+},Mn^{2+}$ is inevitably leached when attempting to dissolve YOX. Since the HALO phosphor can make up as much as 50 wt% of the lamp phosphor waste powder, this consumes significant amounts of acid and complicates the further processing steps (e.g. solvent extraction). The dissolved yttrium and europium can be recovered by a single stripping step using a stoichiometric amount of solid oxalic acid or by contacting the ionic liquid with a hydrochloric acid solution. Both approaches regenerate the ionic liquid, but precipitation stripping with oxalic acid has the additional advantage that there is no loss of ionic liquid to the water phase and that the yttrium/europium oxalate can be calcined as such to reform the red $Y_2O_3:Eu^{3+}$ phosphor (purity > 99.9 wt%), effectively closing the loop after only three process steps. The red phosphor prepared from the recycled yttrium and europium showed excellent luminescent properties. The resulting recycling process for lamp phosphor waste consumes only oxalic acid and features a selective leaching, a fast stripping and an immediate revalorization step. Combined with the mild conditions, the reusability of the ionic liquid and the fact that no additional waste water is generated, this process represents a very green and efficient alternative to traditional mineral acid leaching.

Introduction

The rare-earth elements (REEs) include the 15 lanthanides plus yttrium and scandium. They are used in many high-tech applications including wind turbines, electric vehicles, NiMH batteries, hard disk drives and fluorescent lamps.¹ The demand for these elements is expected to grow by more than 8% per year until 2020.² China dominates the REE supply from primary mining (> 90% of the global production in 2013) and the worldwide recycling rate is still very low (<1 %).² Since the tightening of the Chinese export quota for rare earths in 2010, the rare-earth elements have been labeled as critical raw materials by the European Commission and the U.S. Department of Energy.¹⁻⁴ Opening or reopening mines outside China requires time and large financial investments. Therefore

recycling of REEs from end-user products like magnets and fluorescent lamps, which together represent over 70% of the rare-earth market in terms of value (38% for magnets; 32% for lamp phosphors), could help to secure the supply of these critical elements.³ Efficient recycling of these elements could help to create a closed-loop system and to solve the balance problem which is caused by the unwanted co-production of other rare-earth elements during primary mining.^{3,5} This unwanted co-production has led to the accumulation of large stocks of certain elements (La, Ce) while facing shortages of others (Y, Eu, Tb, Nd, Dy).³⁻⁷ New recycling technologies are becoming increasingly selective, efficient and sustainable and they are opening up new possibilities for urban mining and rare-earth waste revalorization.^{1,3,6-13}

Originally, the collection of fluorescent lights was put in operation to assure the safe disposal of the mercury contained in the lamps; however, the lamp phosphors were discarded or stockpiled. It is estimated that by 2020 the stockpiled lamp phosphor waste will contain around 25,000 tons of rare earths.³ In recent years, the recovery of the REEs contained in these powders received a lot of attention due to the increasing supply risk for some of these elements.^{3,9} Lamp phosphor waste powder contains around 20 wt% of REEs including critical (Y, Eu, Tb) and less critical (La, Ce, Gd) REEs.^{3,5,14} These powders are used in fluorescent lights to convert ultraviolet radiation into visible light. They consist of fine particles (1–10 μm) coated on the inside of the glass. A blend of red Y₂O₃:Eu³⁺ (YOX), blue BaMgAl₁₀O₁₇:Eu²⁺ (BAM) and green LaPO₄:Ce³⁺, Tb³⁺ (LAP), (Ce,Tb)MgAl₁₁O₁₉ (CAT) or (Gd,Mg)B₅O₁₀: Ce³⁺, Tb³⁺ (CBT) phosphors is used to get the desired color rendering index (Table 1). Besides rare-earth phosphors, lamp phosphor waste also often contains large amounts (40–50 wt%) of non-valuable halophosphate (HALO) which emits cold white light and does not contain any REEs.³ The recycling value of the different phosphor components varies greatly. The phosphor with the highest economic value is the red Y₂O₃:Eu³⁺ (YOX) phosphor. This phosphor consists almost entirely of the two critical rare earths yttrium and europium as opposed to the other phosphors which are only doped with small amounts of critical REEs. This explains why YOX holds 80 wt% of the rare earths present in the lamp phosphor waste powder even though YOX only accounts for 20 wt% of the lamp phosphor waste (Table 1).^{3,14}


Table 1. Overview of the lamp phosphors considered in this work and the approximate content found in lamp phosphor waste.³

Name	Formula	Waste fraction (wt%) ^(a)	Value
HALO	(Sr,Ca) ₁₀ (PO ₄) ₆ (Cl,F) ₂ :Sb ³⁺ ,Mn ²⁺	40-50	Low
YOX	Y ₂ O ₃ :Eu ³⁺	20	High
BAM	BaMgAl ₁₀ O ₁₇ :Eu ²⁺	5	Low
LAP	LaPO ₄ :Ce ³⁺ ,Tb ³⁺	6-7	High

^(a) Approximate fraction found in lamp phosphor waste, the remaining consist of SiO₂ (as fine glass particles), Al₂O₃, and small quantities of other phosphors like CAT which behaves similarly to BAM, and CBT.

Many approaches have been proposed for the recycling of lamp phosphors. Physical separation methods like magnetic separation, flotation and centrifugation could allow the direct reuse of the phosphors, but so far they are not used industrially due to the high purity requirements and the deterioration of the phosphor powders during their lifetime.^{3,15-17} Chemical methods can be used to dissolve the phosphors completely or selectively based on the increasing difficulty to dissolve some of the phosphors: HALO < YOX << LAP/BAM/CAT.^{3,9,14,18-21} The halophosphate (HALO) phosphor is easily dissolved in dilute hydrochloric acid solutions at room temperature. The

dissolution of Y₂O₃:Eu³⁺ (YOX) requires more acidic conditions (e.g. 1 M HCl, 60–90 °C).^{3,22} LAP requires the use of very strong acidic conditions (e.g. 18 M H₂SO₄, 120–230 °C),^{3,22} while the aluminate phosphors BAM and CAT are best dissolved in strong alkaline conditions (35 wt% NaOH, 150 °C) in an autoclave or by molten alkali (e.g. Na₂CO₃, 1000 °C).^{3,14} Ionic liquids have been proposed for the selective extraction of previously dissolved rare earths, but so far they have not been used yet as a tool for the dissolution of phosphors.^{22,23} New recycling schemes often focus on the recovery of yttrium and europium from the red phosphor Y₂O₃:Eu³⁺ (YOX) phosphor, because of its high value and the relative ease to dissolve this phosphor compared to BAM, CAT and LAP.^{18,19,22-24} The main problem with these processes is that the halophosphate phosphor (HALO) is often ignored as they focus mostly on the so-called tri-band phosphors which all contain rare earths (YOX, BAM, LAP, CAT). However, real lamp phosphor waste contains up to 50 wt% of HALO and therefore has to be considered when trying to develop an industrially applicable recycling method.^{3,9,14,25} Unfortunately, halophosphate (Sr,Ca)₁₀(PO₄)₆(Cl,F)₂:Sb³⁺,Mn²⁺ (HALO) is very easily dissolved in dilute acids even at room temperature.³ HALO contains no rare earths and has a very low intrinsic value; therefore dissolving this phosphor leads to considerable pollution of the leachate and introduces a large amount of unwanted exogens (Sr, Ca, F, Sb, Mn, Cl) in the waste water, greatly complicating the further processing (eq 1).³



The dissolution of HALO also consumes considerable amounts of acid (18 protons per formula unit of HALO) and leads to the formation of large amounts of H₃PO₄ (6 molecules per formula unit of HALO) which forms very insoluble YPO₄ and EuPO₄ precipitates with the dissolved Y³⁺ and Eu³⁺ ions from the YOX. The design of a selective dissolution method for YOX without dissolving HALO would therefore greatly increase the efficiency and profitability of a recycling process for lamp phosphor waste, but, to the best of our knowledge, such a process has not been described yet.

At present, only one example is known of an industrially applied recycling process for lamp phosphor waste. This process was successfully implemented by Solvay in 2012 and treats more than 2000 tons of phosphor waste powder per year.⁸ According to the patent literature, multiple consecutive acidic (HCl, HNO₃) and alkaline (NaOH) attacks are required, including an alkaline fusion with Na₂CO₃ at 1000 °C, to fully disintegrate all the phosphors. The individual rare earths are then separated and recovered using solvent extraction, in order to manufacture new phosphors.¹⁴ The main drawbacks of this process are the large consumption of chemicals, the large production of waste water and the many process steps required to fully recycle the lamp phosphor waste.³

The process described in this paper aims to solve all these issues by proposing a functionalized ionic liquid as an alternative to selectively dissolve and regenerate the valuable red phosphor $Y_2O_3:Eu^{3+}$ (YOX). This three-step process (no need for solvent extraction) is very efficient, consumes only oxalic acid and generates zero additional waste (except CO_2). The ionic liquid is also automatically regenerated during the stripping step and can be reused. This type of leaching system can be described as ionometallurgy, which is the analogue of hydrometallurgy in ionic liquids and has shown interesting new behavior in various cases.²⁶⁻³⁰ Depending on the application, ionic liquids are considered to be green solvents because of their negligible vapor pressure, low-flammability and reduced toxicity compared to organic solvents and have led to several important improvements in various fields such as metallurgy, extraction, electrochemistry, organic synthesis and catalysis.^{10,12,30-35} Here, the functionalized ionic liquid betainium bis(trifluoromethylsulfonyl)imide [Hbet][Tf₂N] is proposed for the selective dissolution of $Y_2O_3:Eu^{3+}$ without dissolving the other components in the lamp phosphor waste (HALO, BAM, LAP, CAT, SiO_2 , Al_2O_3). [Hbet][Tf₂N] is a Brønsted acidic functionalized ionic liquid which has the ability to dissolve rare-earth oxides and many transition metal oxides (Figure 1).^{36,37} The dissolution of metal oxides in this ionic liquid has been studied extensively by Nockemann *et al.*³⁶⁻³⁸ Silica and alumina cannot be dissolved in [Hbet][Tf₂N] which is highly relevant to the recycling of lamp phosphor waste since these powders can contain significant amounts of silica (as fine glass particles) and alumina.^{3,9} The dissolution is driven by the reactivity of the carboxylic acid group located on the cation of the ionic liquid. In the resulting complex the rare-earth ions are coordinated by the betaine ligands, which are zwitterionic compounds when deprotonated.³⁸ The anions in [Hbet][Tf₂N] simply act as spectator anions and do not participate in the complex formation. However, the Tf₂N⁻ anion is required to obtain a hydrophobic ionic liquid ([Hbet]Cl is a water-soluble salt). The Tf₂N⁻ anion is also very stable and well-suited for high-temperature applications.³⁹

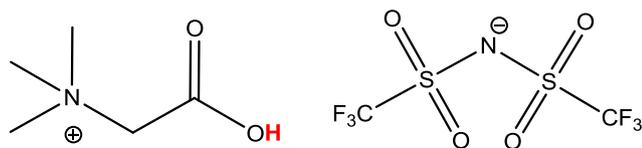


Figure 1. Structure of the ionic liquid betainium bis(trifluoromethylsulfonyl)imide [Hbet][Tf₂N]. The acidic proton of the betaine group is highlighted in red.

A blend of YOX, LAP, BAM and HALO was used to simulate the composition of the lamp phosphor waste and to study the selective dissolution of YOX in [Hbet][Tf₂N]. The dissolution of CAT was not investigated in this work because this aluminate phosphor behaves similarly to BAM, meaning that it will not dissolve in the ionic liquid and thus ends up in the same rest fraction as BAM and LAP.

Experimental

Chemicals

The phosphors $BaMgAl_{10}O_{17}:Eu^{2+}$ (BAM), $Y_2O_3:Eu^{3+}$ (YOX), $LaPO_4:Ce^{3+},Tb^{3+}$ (LAP), and $(Sr,Ca)_{10}(PO_4)_6(Cl,F)_2:Sb^{3+},Mn^{2+}$ (HALO) were purchased from Nichia (Japan) with 99% purity. Betaine chloride (HbetCl) (99%), methyl red sodium salt (pure) and 1,4-dioxane (99.9%) were obtained from Acros Organics (Geel, Belgium). Lithium bis(trifluoromethylsulfonyl)imide (LiTf₂N) (99%) was obtained from IoLiTec (Germany) and oxalic acid dihydrate (>99.5%) from J.T. Baker. Heavy water (D_2O) (99.9 atom % D) was purchased from Sigma Aldrich (Belgium). Absolute ethanol and hydrogen chloride (HCl) were obtained from VWR (Belgium). The silicone solution in isopropanol was purchased from SERVA Electrophoresis GmbH (Germany) and the gallium standard solution (1000 ppm) from Merck (Belgium). All chemicals were used as received without further purification.

Equipment and characterization

¹H NMR and ¹³C NMR spectra were recorded on a Bruker Avance 300 spectrometer, operating at a frequency of 300 MHz for ¹H and 75 MHz for ¹³C, respectively. The samples were prepared by dissolving a small amount of product in heavy water (D_2O). Elemental analysis (carbon, hydrogen, nitrogen) was performed on a CE Instruments EA-1110 element analyzer. Thermogravimetric analysis (TGA) was done on TA instruments T500 thermogravimeter (heating rate: 2 °C min⁻¹ from room temperature to 350 °C, nitrogen atmosphere). The viscosity of the ionic liquid was measured using an automatic Brookfield plate cone viscometer, Model LVDV-II CP (Brookfield Engineering Laboratories, USA). Photoluminescence spectra and luminescence lifetime measurements were recorded on an Edinburgh Instruments FS920 spectrofluorimeter. This instrument is equipped with a xenon arc lamp (450 W), a microsecond xenon flashlamp (60 W) and a red-sensitive photomultiplier (Hamamatsu R-2658). The morphology and size distribution was determined by scanning electron microscopy (SEM) using a Philips XL 30 FEG devise. Powder X-ray diffraction (XRD) was carried out on an Agilent SuperNova X-ray diffractometer, using Mo K α radiation ($\lambda = 0.71073 \text{ \AA}$) and a CCD detector. ICP-MS measurements were done on a Thermo X-Series PlasmaQuad (PQ) 2 devise. Microwave irradiation experiments were carried out in a CEM Discover monomode microwave apparatus (2.45 GHz, 100 W) with an integrated IR sensor, using 10 mL glass tube containers, sealed with snap caps. A Heraeus Megafuge 1.0 centrifuge was used to separate the undissolved phosphor particles from the ionic liquid after the leaching experiments. Total reflection X-ray fluorescence spectroscopy (TXRF) was performed with a Bruker S2 Picofox TXRF spectrometer equipped with a molybdenum source. For the sample

preparation, plastic microtubes were filled with a small amount of ionic liquid sample (200 mg), ethanol (700 μL) and 100 μL of a gallium standard solution (1000 ppm). Gallium was chosen because this element has a high sensitivity and does not interfere with the lanthanide signals. The microtubes were then vigorously shaken on a vibrating plate (IKA MS 3 basic). Finally, a 1 μL drop of this solution was put on a quartz plate, previously treated with a silicone/isopropanol solution (Serva®) to avoid spreading of the sample droplet on the quartz plate. The quartz plates were then dried for 30 min at 60 °C prior to analysis. Each sample was measured for 10 min.

Synthesis of [Hbet][Tf₂N]

The ionic liquid [Hbet][Tf₂N] was synthesized according to a literature method.³⁶ HbetCl (0.390 mol, 59.91 g) and LiTf₂N (0.390 mol, 111.97 g) were dissolved in water (50 mL) and stirred for 2 h at room temperature. The mixture was then allowed to phase-separate and the water phase containing LiCl was removed. [Hbet][Tf₂N] was then washed several times with ice water (10 mL) to remove chloride impurities until the AgNO₃ test was negative in the water phase after the washing step. The remaining water was removed using a rotary evaporator under reduced pressure. The yield was 79 % (0.310 mol, 123.47 g) with a chloride content below detection limit for TXRF analysis (0.1–0.2 ppm).⁴⁰ NMR characterization with Chemical shifts (δ) given in ppm and J values given in Hz resulted in δ_{H} (300 MHz; DMSO; Me₄Si) 3.22 (9 H, s, 3 \times Me) 4.30 (2 H, s, CH₂) and δ_{C} (75 MHz; DMSO; Me₄Si) 166.34 (s, COO) 119.45 (q, 2 \times CF₃, J = 312.75), 62.60 (s, N-CH₂), 52.88 (3 \times CH₃). CHN elemental analysis found (%): C, 21.17; H, 3.96; N, 6.76. Calc. (%) for C₇H₁₂N₂O₆F₆S₂: C, 21.11; H, 3.04; N, 7.03.

Leaching experiments

Small glass vials (4 mL) were filled with a fixed amount of [Hbet][Tf₂N] (2 g), a 10 mg sample of each of the four phosphors per g of ionic liquid (4 \times 10 mg/g) and also a small amount of water during some experiments (1 to 5 wt%). Note that all the quantities are expressed per gram of ionic liquid (mg/g). A magnetic stirring bar was then added to each of the vials and they were closed using a plastic screw cap. The dissolution experiments were carried out using a heating plate with a silicone oil bath, an integrated magnetic stirrer and a temperature sensor. The vials were placed in the silicone oil bath at the appropriate temperature and stirred for a certain amount of time. The vials were then placed in a centrifuge (5300 rpm, 20 min) to precipitate the undissolved phosphor powders and to obtain a clear ionic liquid. The metal content dissolved in the ionic liquid was determined using total reflection X-ray fluorescence spectroscopy (TXRF).

Stripping experiments

Two different stripping methods were investigated. Method 1 involved the use of an aqueous HCl phase to extract the rare-earth ions from the ionic liquid to the water phase, method 2 consisted of adding pure (solid) oxalic acid directly to the ionic liquid to precipitate the rare-earth ions as rare-earth oxalates. For every stripping experiment, Y₂O₃:Eu³⁺ (10 mg/g) was first fully dissolved in a large batch of ionic liquid (5 wt% H₂O). Small glass vials (5 mL) were then filled with a fixed amount of this REE-containing ionic liquid (1 g). For method 1, a HCl solution (1 g) was then added to the rare-earth containing ionic liquid. This lowly viscous biphasic mixture was shaken (1500 rpm) using a mechanical shaker at a set temperature (25, 70 and 80 °C). The samples were then centrifuged (1 min, 5300 rpm) to speed up phase separation, and analyzed by TXRF to determine the remaining metal content in the ionic liquid phase. For method 2, pure (solid) oxalic acid was added directly to the ionic liquid phase. These samples were more viscous and consisted of only one phase, so they were stirred using a magnetic stirring bar and a stirring plate/oil bath set-up to control the temperature (25, 50 and 70 °C). The samples were then centrifuged (5300 rpm, 20 min) to remove the oxalate precipitate and the ionic liquid phase was analyzed with TXRF to determine the remaining metal content.

Optimized full recycling process

The retained recycling process consisted of three steps. First a synthetic mixture of HALO, YOX, BAM and LAP phosphors was added to the ionic liquid [Hbet][Tf₂N] containing 5 wt% of water. The system was optimized for 10 mg of YOX per g of ionic liquid, which corresponds to approximately 40 to 50 mg of real lamp phosphor waste. A stirring bar was added and the samples were stirred for 24 to 48 h at 90 °C to obtain a selective and 100 % leaching of YOX. The remaining solid lamp phosphor waste was separated from the ionic liquid by centrifugation (5300 rpm, 20 min). A stoichiometric amount of pure oxalic acid was then added to the ionic liquid loaded with yttrium and europium to precipitate the rare-earth ions as oxalates and regenerate the ionic liquid. The samples were stirred for 10 min at 70 °C to obtain 100 % stripping. The oxalate precipitate was separated from the ionic liquid by filtration and washed with water (lowers the viscosity). The water can be removed by evaporation later on. An alternative could be to filter at 70 °C at which point the viscosity of the [Hbet][Tf₂N] (5 wt% H₂O) becomes very low. The mixed (yttrium,europium) oxalate was dried in a vacuum oven at 50 °C and then calcined at 950 °C (5 h) in an oven to obtain new Y₂O₃:Eu³⁺ (YOX) with a purity > 99.9 wt%

Results and discussion

Selective dissolution of YOX in [Hbet][Tf₂N]

The protonated functionalized ionic liquid betainium bis(trifluoromethylsulfonyl)imide [Hbet][Tf₂N] has the ability to dissolve certain metal oxides, including rare-earth oxides like

Y_2O_3 and Eu_2O_3 .^{36,37} Different parameters (water content, temperature,...) were investigated to find which leaching conditions were required to *selectively* dissolve the red $Y_2O_3:Eu^{3+}$ (YOX) phosphor within a reasonable period of time.

In the first experiment, the influence of water addition was investigated. Water-free ionic liquid was used and increasing amounts of water were then added (0, 1, 2.5 and 5 wt%). Care was taken never to exceed the solubility of water in the ionic liquid (13 wt%), because it was important to maintain one homogeneous phase during the leaching process to avoid the loss of metal ions to the water phase.⁴¹ A mix of YOX, HALO, BAM and LAP was added to the ionic liquid (4×10 mg/g) and stirred (600 rpm) at 90 °C. The water-free ionic liquid was compared with water-containing ionic liquid (1, 2.5 and 5 wt% water added). Closed vessels with screw caps were used to contain the small amounts of water at elevated temperatures. The results show that the addition of water has a positive influence on the leaching of YOX due to the lower viscosity and better ion diffusion. With a water content of 5 wt% (50 μ L/g) in the ionic liquid, full dissolution of YOX was observed after 24 h (Figure 2). More importantly, in these conditions very little dissolution of HALO was observed (< 0.05 wt%) (Figure 3) and no leaching of BAM and LAP could be detected. Higher water contents are not advisable since this will lead to increasing dissolution of HALO (Figure 3). It was also confirmed in a separate experiment, that SiO_2 and Al_2O_3 do not dissolve in the $[Hbet][Tf_2N]$ ionic liquid.^{37,42}

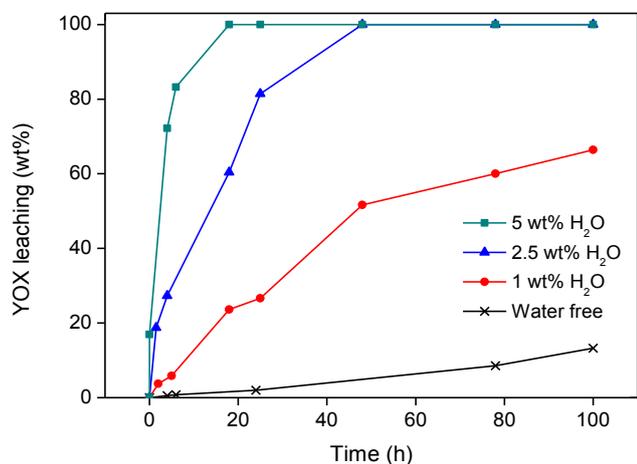


Figure 2. Dissolution of YOX (wt%) in $[Hbet][Tf_2N]$ at 90 °C with varying amounts of water in the ionic liquid (0, 1, 2.5 and 5 wt%). The solutions were stirred at 600 rpm. No dissolution of BAM and LAP was observed.


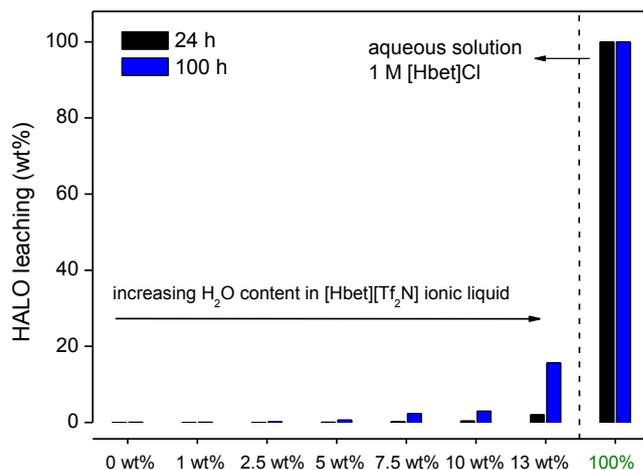


Figure 3. Leaching (wt%) of HALO by $[Hbet][Tf_2N]$ at 90 °C (600 rpm) after 24 h and 100 h, with increasing amounts of water in the ionic liquid: 0, 1, 2.5, 5, 7.5, 10 and 13 wt% (= water-saturated). Leaching is also shown in an aqueous solution containing $[Hbet]Cl$ (1 M) which has a pK_a of 1.83.⁴³

It is clear from Figure 2 and Figure 3 that in water-poor conditions (< 5 wt% H_2O in the ionic liquid) $Y_2O_3:Eu^{3+}$ dissolves much better than HALO. This is surprising considering that in dilute acidic aqueous solutions (e.g. 1 M $[Hbet]Cl$), HALO dissolves much more easily than $Y_2O_3:Eu^{3+}$. To explain this unusual behaviour a hypothesis is proposed based on the difficult solvation of anions in $[Hbet][Tf_2N]$. While metal cations (e.g. rare-earth ions) can be coordinated efficiently in $[Hbet][Tf_2N]$ by the carboxylate groups of the deprotonated betaine, this is not the case for anions.³⁶⁻³⁸ It was previously observed by Nockemann *et al.*, that the solubility of oxides in $[Hbet][Tf_2N]$ was much higher than that of chloride salts, which is in agreement with our hypothesis.³⁶ This hypothesis was supported by the observation that $NaCl$, $EuCl_3$ and YCl_3 could not be dissolved in the pure ionic liquid, while it was possible to dissolve their corresponding oxides. It was also observed that when $[Hbet][Tf_2N]$ was contacted with an aqueous YCl_3 solution some yttrium was extracted to the ionic liquid phase but no chloride was extracted. The extraction of metal ions is based on the release of protons by $[Hbet]^+$ and coordination of the metal ion by zwitterionic betaine groups, but there is no suitable mechanism for the coordination or solvation of anions in the ionic liquid. Since the dissolution of metal oxides does not create anions, they easily dissolve in this ionic liquid (eq 2) while metals salts like rare-earth chlorides (eq 3) (or even $NaCl$), do not, due to the formation of anions. This behaviour is opposite to what is found in aqueous solutions, where chlorides dissolve much easier than oxides which require the presence of acid. Only when sufficient amounts of water are added to the ionic liquid, it will dissolve (some) chloride salts because water can solvate anions (eq 3). The same is true for HALO, where many phosphate and chloride ions need to be solvated in order for HALO to dissolve (eq 1). HALO dissolves very fast in dilute acidic aqueous solutions, but very little dissolution (< 0.05 wt%) is observed in

[Hbet][Tf₂N] when less than 5 wt% of water is present. This is why such a drastic change in the dissolution behavior of HALO is observed when the water content is increased (Figure 3). The leaching of metal oxides like YOX also accelerates in the presence of water but this is mainly due to the lower viscosity and faster diffusion of protons in the ionic liquid.^{36,37} YOX forms upon dissolution only water and cations, which are efficiently solvated by the betaine groups, and it does not form anions (eq 2). The water content is therefore the most crucial parameter as the control of the water content in the ionic liquid allows the selective dissolution of YOX, without dissolving HALO.



It is important to keep the dissolution of HALO to an absolute minimum, not only from an economic point of view but also from a chemical point of view as it constitutes up to 50 wt% of the waste. The dissolution of HALO consumes a large amount of acid and releases unwanted metal ions (eq 1) which means purification methods (e.g. solvent extraction) are required to retrieve pure rare earths. The dissolution of HALO also leads to the formation of phosphate ions (eq 1) which can form very insoluble YPO₄ and EuPO₄ with the dissolved Y³⁺ and Eu³⁺ from the YOX. This hampers the further processing because rare-earth phosphates are very difficult to dissolve (like LAP and monazite). The optimal leaching system is therefore a compromise between the fast dissolution of YOX and keeping the leaching of HALO as low as possible. [Hbet][Tf₂N] with 5 wt% of H₂O (90 °C, 24h) seems to be the best compromise between speed and selectivity. In these conditions, the leaching of YOX and HALO is 100 wt% and 0.04 wt% respectively, and BAM and LAP leaching below detection limit (Figure 2 and Figure 3).

The influence of temperature on the leaching of YOX was also investigated for this optimized ionic liquid system (5 wt% H₂O) and compared with water-free ionic liquid (Figure 4). In both cases a noticeable increase in leaching speed was observed with increasing temperature (Figure 4). A temperature of 90 °C with 5 wt% (50 μL/g) of H₂O in the ionic liquid was chosen as the optimal system because of its high leaching efficiency and the fact that the water pressure is still manageable.

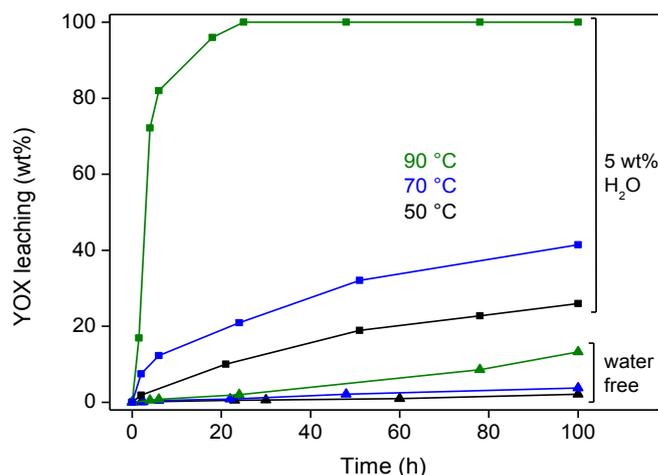


Figure 4. Dissolution (wt%) of YOX in water-free [Hbet][Tf₂N] and water-containing (5 wt% H₂O) [Hbet][Tf₂N] as function of time and temperature.

A higher temperature is favorable because it accelerates the dissolution reaction and lowers the viscosity of the ionic liquid which improves the diffusion. This is important because the leaching rate of this solid material is diffusion-controlled. The viscosity was measured as a function of the water content in the ionic liquid and the temperature (Table 2). It is clear that a higher water content and temperature drastically diminish the viscosity. The viscosity of the ionic liquid with 5 wt% water at 80 °C is only 25 cP. The viscosity at 90 °C could not be measured with our equipment but it will be even lower. Of course, the viscosity of the leaching system used in this work (ionic liquid with 5 wt% H₂O at 90 °C), is still higher than that of water (0.3 cP at 90 °C) but it is sufficiently low in order not to be an issue.

Table 2. Viscosity (cP) of [Hbet][Tf₂N] as function of the water content and temperature.

	Viscosity (cP) at 30 °C	Viscosity (cP) at 50 °C	Viscosity (cP) at 80 °C
[Hbet][Tf ₂ N] (1 wt% H ₂ O)	925	252	65
[Hbet][Tf ₂ N] (5 wt% H ₂ O)	172	67	25
[Hbet][Tf ₂ N] (water-sat.) ^(a)	22	12	6

(a) Water-saturated [Hbet][Tf₂N] contains approximately 13 wt% H₂O.⁴¹

The thermal stability of [Hbet][Tf₂N] was tested by thermogravimetric analysis (TGA) and ¹³C NMR. The thermal stability is an important characteristic since the ionic liquid will be used for leaching at temperatures up to 90 °C for prolonged amounts of time. The Tf₂N⁻ anion is known to have a high relative stability compared to other common ionic liquid anions.³⁹ For TGA, the ionic liquid was first dried under reduced pressure at 80 °C until all the remaining traces of water

were removed and the mass of the ionic liquid was stable. The ionic liquid was then heated ($2\text{ }^{\circ}\text{C min}^{-1}$) under nitrogen atmosphere, from room temperature to $350\text{ }^{\circ}\text{C}$. The results of the dynamic TGA show that the ionic liquid only starts to degrade at temperatures around $200\text{ }^{\circ}\text{C}$, which proves it is definitely stable at $90\text{ }^{\circ}\text{C}$ (Figure 5). A static measurement at $90\text{ }^{\circ}\text{C}$ for a period of 24 h, showed negligible ($< 0.01\%$) degradation of the ionic liquid. ^{13}C NMR was used to investigate the degradation of water-containing ionic liquid in experimental conditions ($90\text{ }^{\circ}\text{C}$, 5 wt% H_2O , 600 rpm, 48 h). A ^{13}C NMR spectrum was taken before and after to confirm the stability of the ionic liquid in these conditions.

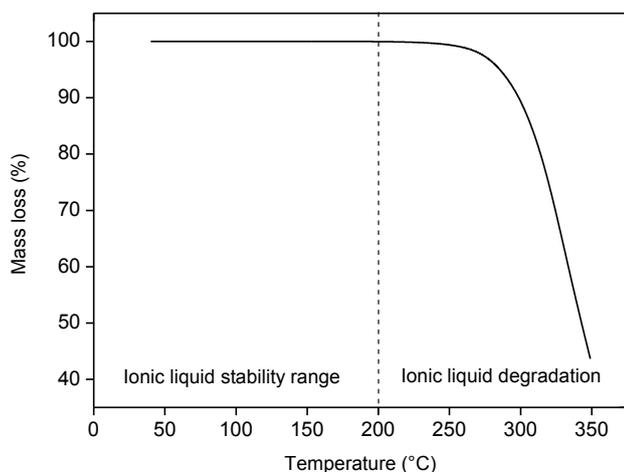


Figure 5. Thermogravimetric analysis of [Hbet][Tf₂N], measured from 40 to $350\text{ }^{\circ}\text{C}$ ($2\text{ }^{\circ}\text{C min}^{-1}$) under nitrogen atmosphere.

The loading capacity, meaning the amount of YOX that can be dissolved in the ionic liquid, was also investigated. The theoretical maximal stoichiometric solubility of Y_2O_3 in the ionic liquid would amount to 95 mg/g. However, this requires the addition of more water under reflux conditions in order to be sufficiently fast.³⁶ This would undermine the selectivity of this system since in these conditions the HALO would easily dissolve in the water phase. Higher loadings also resulted in higher viscosities due to the highly charged rare-earth ions in the ionic liquid, making the system much more difficult to handle. It was shown that in the previously mentioned optimized conditions ($90\text{ }^{\circ}\text{C}$, 5 wt% H_2O) up to 40 mg/g of YOX could be fully dissolved in the ionic liquid after 40 h (Figure 6). The parameter optimization in this work was done for a YOX loading of 10 mg/g (10,000 ppm), but it is possible to work in more concentrated conditions (solid/liquid ratio) without significant modifications. As shown in Figure 6, a dissolution of 40 mg/g of YOX in the ionic liquid would correspond to a solid/liquid ratio of 200 mg/g (200 g/kg) of waste in the ionic liquid, since fluorescent lamp waste contains around 20 wt% of YOX.

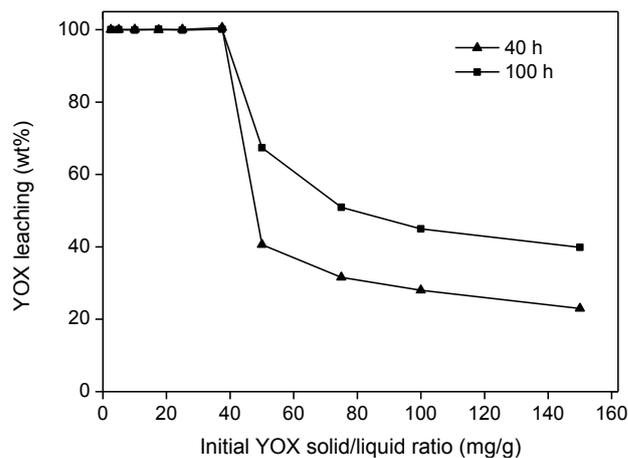


Figure 6. Dissolution (wt%) of YOX in [Hbet][Tf₂N] (5 wt% H_2O) as function of initial YOX concentration in the ionic liquid (solid/liquid ratio). The dissolutions were carried out at $90\text{ }^{\circ}\text{C}$ during 40 h and 100 h.

The dissolved Y^{3+} and Eu^{3+} (YOX) in [Hbet][Tf₂N] was recovered by a stripping step. This was achieved either by contacting the loaded ionic liquid with an acidic water phase to extract the rare-earth ions (method 1), or by directly precipitating the rare earths from the ionic liquid using pure (solid) oxalic acid (method 2). Stripping method 1 has important limitations due to the loss of ionic liquid to the water phase. Stripping with pure oxalic acid (method 2) is clearly a better alternative since no ionic liquid is lost and the YOX phosphor can be immediately regenerated from the yttrium/europium oxalate salt in a simple calcination step. However, it is still interesting to also investigate the stripping with HCl and quantify the loss of ionic liquid to the water phase even if it is not the best method. Both stripping systems are discussed separately and compared.

Stripping method 1: Recovery of yttrium and europium using an acidic aqueous phase

The first stripping system involves the use of an acidic aqueous phase, which is contacted with the loaded ionic phase. In this process the rare-earths ions (Ln) are transferred to the water phase as soluble compounds (e.g. chlorides). The acidic protons protonate the betaine ligands and regenerate the ionic liquid (eq 4).



The fact that a two-phase system is now used, means that it is necessary to look at possible losses of ionic liquid to the water phase. The loss of ionic liquid depends on the phase ratio and the amount and type of dissolved ions.⁴⁴⁻⁴⁶ Ions can be divided as salting-in (e.g. NO_3^-) and salting-out (e.g. Cl^- , SO_4^{2-}) agents as described by the Hofmeister series.^{45,47} The former class of ions tends to lead to an improved mixing of ionic liquid/water, while the latter leads to a better separation of ionic

liquid/water and therefore a smaller loss of ionic liquid to the water phase. The loss of ionic liquid to the water phase (1:1 phase ratio by mass) was quantified using ^1H NMR spectroscopy with 1,4-dioxane as an internal standard and D_2O instead of H_2O as water phase. The loss of $[\text{Hbet}][\text{Tf}_2\text{N}]$ to a (pure) water phase was determined to be 13 wt%. Lowering the pH increases the loss of ionic liquid to the water phase even more to 15.1%, 15.4% and 18.1% for 1 M H_2SO_4 , HCl and HNO_3 respectively. This is in agreement with the sequence found in the literature.⁴⁵ Although stripping with H_2SO_4 resulted in the lowest loss of ionic liquid, stripping with HCl is still the better choice because the solubility of rare-earth sulfates in water is much lower than the corresponding rare-earth chlorides. The loss of ionic liquid is very significant and it is cumbersome to recover the ionic liquid from the water phase, even though various techniques exist to recover ionic liquids at a later stage using for example strong salting-out agents, adsorbents, special membranes, electro dialysis or nanofiltration.⁴⁸⁻⁵² This is why the oxalic acid precipitation route (method 2) is the preferred method.

The different stripping parameters were then investigated for stripping with HCl , starting with the influence of acid concentration. First, 10 mg/g of YOX was dissolved in $[\text{Hbet}][\text{Tf}_2\text{N}]$ (5 wt% H_2O). Then, the loaded ionic liquid was contacted with aqueous solutions containing varying concentrations of HCl (1:1 phase ratio by mass) and shaken (1500 rpm) for 1 h at 25 °C. The remaining metal content in the ionic liquid was then analyzed using TXRF. The results showed that contacting the ionic liquid with 1 M HCl resulted in 99.6 % and 99.7 % stripping of Y^{3+} and Eu^{3+} respectively (Figure 7). A sufficient amount of HCl is needed to protonate the betaine and to form the water-soluble YCl_3 and EuCl_3 compounds. In this set-up, the stoichiometric HCl concentration is 0.3 M in the water phase, but an excess of HCl is required to obtain full stripping (1 M) (Figure 7). An interesting observation is the fact that in diluted acidic conditions with an excess of rare-earth ions compared to HCl , Y^{3+} is easier to strip than Eu^{3+} . This is in agreement with previous reports where yttrium(III) had a slightly lower affinity for betaine ligands compared to europium(III).⁴⁴ For HCl concentrations > 0.4 M no difference was observed and the stripping process became very efficient and reproducible. An HCl concentration of 1 M was retained as the optimal stripping concentration because of the fast and reliable stripping.

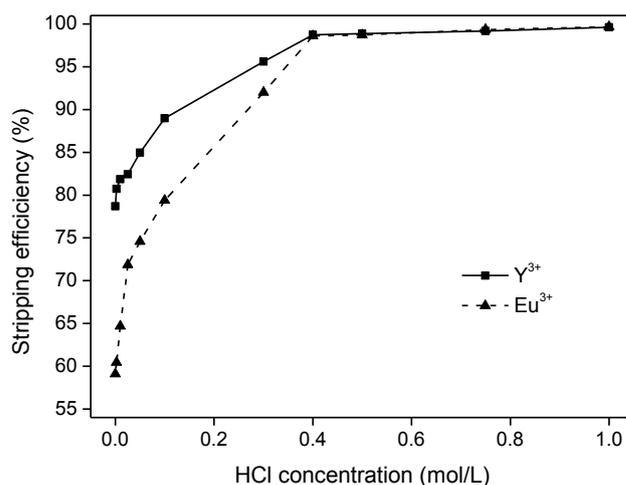


Figure 7. Stripping of Y^{3+} and Eu^{3+} from $[\text{Hbet}][\text{Tf}_2\text{N}]$, previously loaded with 10 mg/g of YOX. The influence of the HCl concentration on the stripping efficiency for Y^{3+} and Eu^{3+} is shown. The biphasic system was shaken (1500 rpm) at 25 °C for 1 h.

Secondly, the stripping kinetics was investigated. When dealing with a biphasic system, the process kinetics is controlled by the extent of the interface since the exchange of ions can only happen at this interface. The area of the interface is usually increased by intense stirring or shaking, however, a special feature of the $[\text{Hbet}][\text{Tf}_2\text{N}]/\text{H}_2\text{O}$ system is that it shows thermomorphic behavior with an upper critical solution temperature.⁴⁴ This means that the biphasic system will become one homogeneous phase above a certain temperature called the cloud point temperature. This is very interesting since the process kinetics will be much faster as they are then no longer limited by the diffusion across an interface. In order to get phase separation, the mixture has to be heated above the cloud point and shaken briefly (1 s) to overcome the metastable state, but the homogeneous state then remains stable as long as the temperature is above the cloud point. Below the cloud point, the phase separation automatically occurs again (Figure 8).

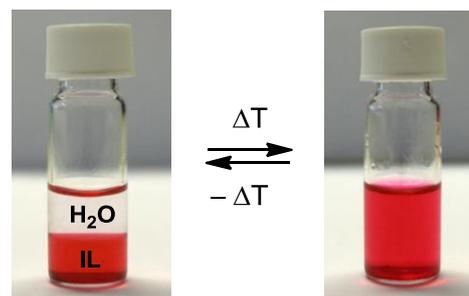


Figure 8. Reversible formation of a homogeneous phase when increasing the temperature above the cloud point (55 °C for a pure water/ionic liquid system in 1:1 ratio).⁴⁴ A coloring agent (methyl red sodium salt) was dissolved in the transparent ionic liquid phase to help the visualization. The density of $[\text{Hbet}][\text{Tf}_2\text{N}]$ liquid is higher than that of water.

The cloud point is dependent on the amount and type of ions present in the water phase, but also on the loading of the ionic liquid and the water to ionic liquid ratio.⁴¹ The cloud point was determined for this stripping system consisting of one phase with 1 g of ionic liquid in which $Y_2O_3:Eu^{3+}$ was dissolved (10 mg/g), contacted with another phase consisting of a 1 g HCl solution (1 M) in a 1:1 phase ratio. The cloud point was found to be 74 °C by heating the sample to 80 °C and then slowly cooling it down, keeping it steady at every degree for 5 min to see if it would become cloudy when gently shaken which indicates that the mixture starts to phase separate.⁵³ This cloud point is higher than for a pure $H_2O/[Hbet][Tf_2N]$ system, because of the H^+ , Cl^- , Y^{3+} and Eu^{3+} ions dissolved in it.⁴¹

The stripping kinetics was then investigated at room temperature (25 °C) and just below (70 °C) and above (80 °C) the cloud point temperature (74 °C) both with and without shaking (1500 rpm) (Figure 9).

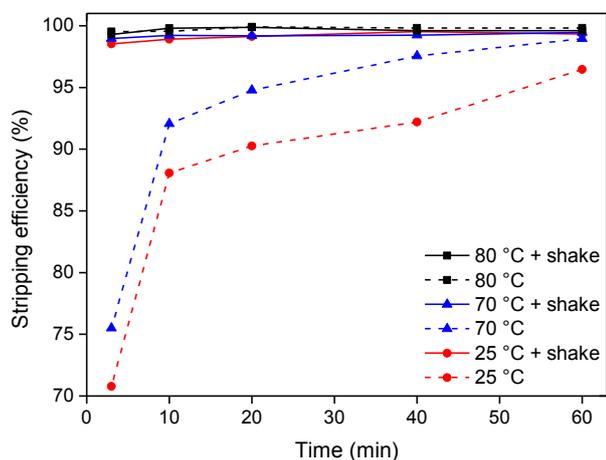


Figure 9. Stripping kinetics and the influence of shaking (1500 rpm) are shown for 25 °C, 70 °C and 80 °C with 1 M HCl. The cloud point temperature is 74 °C so at 80 °C the system is one homogeneous phase which explains the efficient stripping without shaking. For 25 °C and 70 °C it consists of two phases, a water phase and an ionic liquid phase, making shaking essential for an efficient stripping process.

Raising the temperature from 25 °C to 70 °C only slightly increases the stripping speed. However, when the temperature is raised to 80 °C, which is above the cloud point temperature, the stripping is much faster due to the disappearance of the interface between the ionic liquid and the water phase and the formation of one homogeneous phase. It is also clear that shaking has a major influence when working at temperatures below the cloud point temperature because the system is then a biphasic mixture. Shaking the samples at 80 °C (above the cloud point) has no influence since the system is then one homogeneous phase. It is clear from this experiment (Figure 9) that from an energy-saving point of view, the best choice for stripping is either to work with a biphasic mixture at 25 °C while shaking, or to work at 80 °C without shaking thanks to

the formation of a homogeneous phase. Other combinations require more energy and are less efficient.


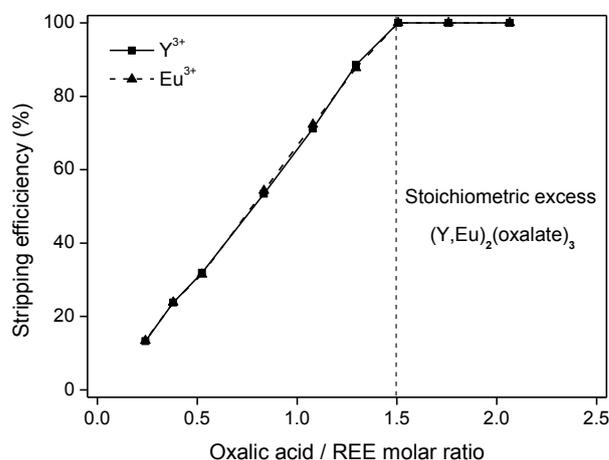


Figure 10. Stripping of yttrium and europium from $[Hbet][Tf_2N]$, using pure (solid) oxalic acid. The influence of oxalic acid concentration on the stripping efficiency is shown. A ratio of 1.5:1 is the stoichiometric amount of oxalic acid required to precipitate all rare-earth ions ($REE = Y + Eu$) in solution as $(Y,Eu)_2(C_2O_4)_3$ and results in a stripping efficiency of 100%.

Stripping method 2: Recovery of yttrium and europium using pure oxalic acid

The problem of the loss of ionic liquid to the water phase can be avoided by stripping with solid oxalic acid, directly in the ionic liquid phase. This acid forms insoluble oxalate complexes with the rare-earth ions (eq 5) and precipitates them while regenerating the ionic liquid. This stripping precipitation method is very efficient for rare-earth ions. The rare-earth oxalate precipitate can then be separated from the ionic liquid and thermally decomposed in an oven at high temperature to form the corresponding rare-earth oxides.⁵⁴ By carefully choosing the conditions it is also possible to directly resynthesize the $Y_2O_3:Eu^{3+}$ phosphor by calcination of the mixed yttrium/europium oxalate (eq 6), as described by the Solvay patent.⁵⁵ The advantage is that the yttrium and europium are already present in the right ratio to manufacture the YOX phosphor, since they have been selectively leached from used lamp phosphors in the first place. This stripping system is therefore definitely the preferred choice compared to the stripping system using an acidic water phase. The oxalic acid stripping is much more convenient and can be carried out directly in the ionic liquid, meaning there is no loss of ionic liquid to the water phase.



The different parameters of this stripping method were investigated. The results show that a stoichiometric amount (eq

5) of oxalic acid compared to the amount of rare-earth ions (3:2) is sufficient to obtain a stripping efficiency of 100% (Figure 10). Oxalic acid does not show individual selectivity for yttrium or europium in these conditions.

The influence of temperature on the stripping kinetics of this heterogeneous stripping process was investigated. The viscosity of this pure ionic liquid is obviously higher than for a biphasic water/ionic liquid mixture, but it is still very manageable especially at higher temperatures (Table 2). An ionic liquid containing 10 mg/g of YOX and 5 wt% H₂O was reused, and a stoichiometric amount of oxalic acid was added compared to the amount of rare-earth ions (3:2). The samples were then stirred (600 rpm) at different temperatures and for increasing amounts of time. The results show a drastic increase in the stripping efficiency when raising the temperature from 25 °C to 50 °C and 70 °C (Figure 11). This increase is attributed to the lower viscosity (Table 2) and the improved diffusion of the oxalic acid in the ionic liquid. At 70 °C, a stripping efficiency of 100 % was obtained after only 10 min, which is a very satisfactory result.

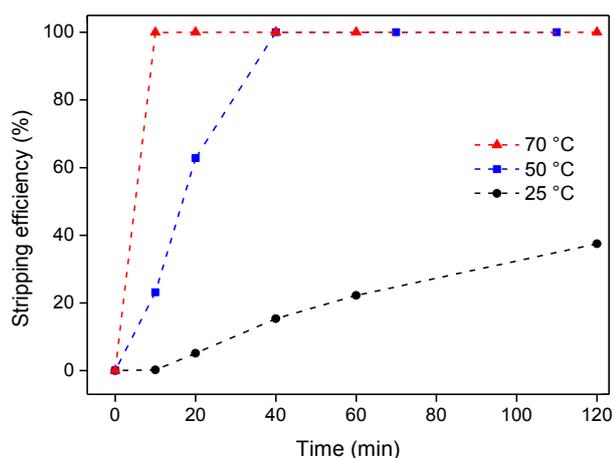


Figure 11. Stripping of yttrium and europium from [Hbet][Tf₂N] ionic liquid, using a stoichiometric amount (3:2) of pure (solid) oxalic acid. The influence of time and temperature on the total stripping efficiency (Y+Eu) is shown.

It can be concluded that this oxalate stripping process is very efficient since stoichiometric amounts of oxalic acid suffice to get full stripping of the rare-earth ions from the ionic liquid. The formation of the rare-earth oxalate precipitate is also very convenient since the oxalate salt can be transformed into new YOX phosphor Y₂O₃:Eu³⁺ by a simple calcination step. The major advantage of this stripping system compared to the biphasic system (method 1), is the fact that no ionic liquid is lost. The drawback is that this stripping system is kinetically slower and therefore requires heating at 70 °C for 10 min (Figure 11). The biphasic stripping system using HCl could be carried out efficiently by shaking at room temperature for 10

min (Figure 9). All things considered, the oxalic acid stripping method was retained for the final recycling process.

Regenerating the Y₂O₃:Eu³⁺ phosphor

The (Y,Eu)₂(C₂O₄)₃ precipitate was separated from the ionic liquid by filtration with a Büchner funnel and washed with water to lower the viscosity of the ionic liquid. Afterwards the water can be removed by evaporation. An alternative could be to filter at 70 °C at which point the viscosity of the [Hbet][Tf₂N] (5 wt% H₂O) becomes very low. The mixed oxalate was then dried in a vacuum oven at 50 °C for 12 h. The dry (Y,Eu)₂(C₂O₄)₃ was then placed in an oven at 950 °C for 5 h to obtain the Y₂O₃:Eu³⁺ phosphor. The YOX particles were characterized using ICP-MS, SEM imaging, luminescence spectroscopy and powder XRD, and compared with the purchased YOX. The purity of the recycled YOX was determined to be > 99.9 wt% by TXRF and ICP-MS with only small traces of calcium (< 0.1 wt%). The purchased YOX had a certified purity of > 99 wt%. SEM images can be found in the supplementary information (Figure S1). They showed that the particles had a size of 4.11 ± 1.41 μm which is in range with the commercial YOX phosphor (3.61 ± 1.52 μm). However, the recycled YOX phosphor had a rougher surface than the purchased phosphor (Figure S1). Powder XRD was carried out to compare the commercial YOX with the recycled YOX. The diffractograms were essentially identical, which confirmed the successful synthesis of Y₂O₃:Eu³⁺ (Figure S2). The luminescence of this material was also compared with the commercially obtained Y₂O₃:Eu³⁺ phosphor (Figure 12). When the spectra are scaled to have the same intensity of the ⁵D₀ → ⁷F₁ transition, it is interesting to compare the intensity of the ⁵D₀ → ⁷F₂ transition (around 612 nm) since this is a so-called hypersensitive transition, meaning its intensity is very dependent on its environment.⁵⁶⁻⁵⁸ It can be seen that the maximum intensity peak (⁵D₀ → ⁷F₂) has the same intensity for the recycled phosphor than for the commercial phosphor. The luminescence lifetime was also measured by studying the decay of the ⁵D₀ emitting state of Eu³⁺. The samples were excited with 254 nm light and the emission light was collected at 612 nm. The decay curves (Figure S3) were fitted as a mono-exponential decay, resulting in a luminescence lifetime of 0.989 ms (R² = 0.998) and 1.003 ms (R² = 0.997) for the recycled and purchased YOX phosphor respectively. The very good luminescence and luminescence lifetime of the recycled YOX confirms that the recycling process yields a sufficiently pure yttrium/europium oxalate product to allow direct resynthesis of the YOX phosphor (> 99.9 wt% purity). This process is only possible because of the highly selective dissolution of YOX in the ionic liquid, because any dissolution of HALO, BAM or LAP would lead to an impure product and a significant decrease in luminescence. Optimization of the calcination process (flux agents, temperature, time,...) could further improve the luminescence properties and particle morphology to obtain an optimal red phosphor, but this is outside the scope of this work and has been studied by others.^{55,59}

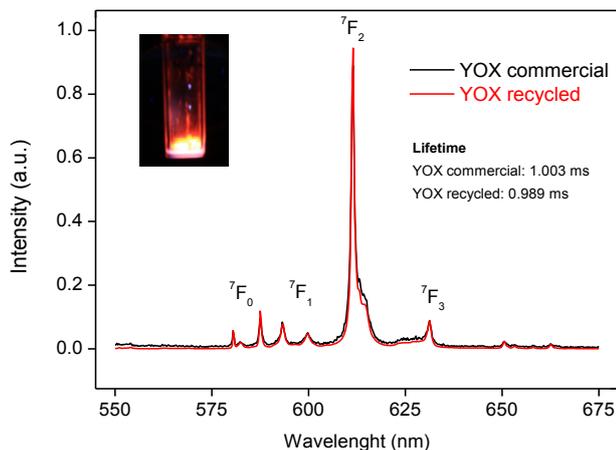


Figure 12. Luminescence spectra ($\lambda_{\text{exc}} = 254 \text{ nm}$) of the commercial red $\text{Y}_2\text{O}_3:\text{Eu}^{3+}$ (YOX) phosphor, compared with the spectrum of the recycled YOX phosphor after calcination of the $(\text{Y,Eu})_2(\text{C}_2\text{O}_4)_3$ precipitate. The spectra were scaled to have the same intensity for the ${}^5\text{D}_0 \rightarrow {}^7\text{F}_1$ transition in order to compare the intensity of hypersensitive ${}^5\text{D}_0 \rightarrow {}^7\text{F}_2$ transition. Picture: recycled YOX phosphor in a quartz container irradiated by 254 nm light. The luminescence lifetimes are also shown (Figure S3).

An overview of the proposed recycling process is shown in Figure 13. This process selectively recovers the YOX which represents 80 wt% of the critical rare-earths in the lamp phosphor waste powder and approximately 70 % of the value.¹⁴ Only oxalic acid is consumed (cheap chemical) and it creates no waste besides some CO_2 (the ionic liquid is entirely reusable). This process is a sustainable alternative compared to mineral acid leaching and could be applied on industrial scale as an on-site valorization method for recyclers since no complex solvent extraction installations are needed.

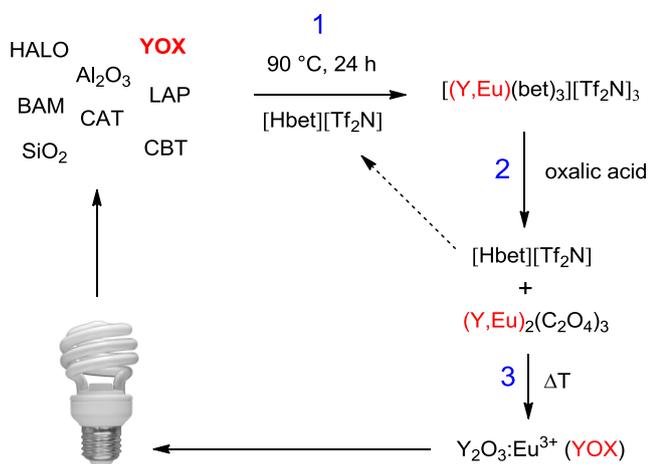


Figure 13. Overview of the proposed recycling process for lamp phosphor waste, based on the selective dissolution and revalorization of YOX with the protonated functionalized ionic liquid $[\text{Hbet}][\text{Tf}_2\text{N}]$. Step 1: selective dissolution of YOX, step 2: stripping with pure oxalic acid (regenerates the ionic liquid), step 3: direct resynthesis of YOX.

This process was optimized using a synthetic mix of phosphors (HALO, YOX, BAM, LAP). However, it is also applicable to real lamp phosphor waste because the other components (CAT, CBT, SiO_2 , Al_2O_3) do not interfere with this process as they do not dissolve in $[\text{Hbet}][\text{Tf}_2\text{N}]$.^{37,42} The influence of mercury on this process was not investigated, but many techniques exist to remove mercury from the phosphor powders.^{3,9,21,60-62} At the end of the recycling scheme, no additional waste has been created. The rest of the lamp phosphor waste (SiO_2 , Al_2O_3 , HALO, BAM, LAP, CAT, CBT) can be discarded or further processed, for example by doing a rough separation of the HALO with physical separation methods.^{3,63} This would result in a terbium concentrate ($\approx 8 \text{ wt}\%$ Tb) held in LAP, CAT and CBT. The terbium content in this concentrate is much higher than any commercially exploited ore from primary mining ($< 1.3 \text{ wt}\%$ Tb).⁴ The high demand for terbium could therefore make it worthwhile to dissolve the LAP, CAT and CBT phosphors in a final stage, but these phosphors are much more difficult to dissolve and require a lot of energy input.¹⁴

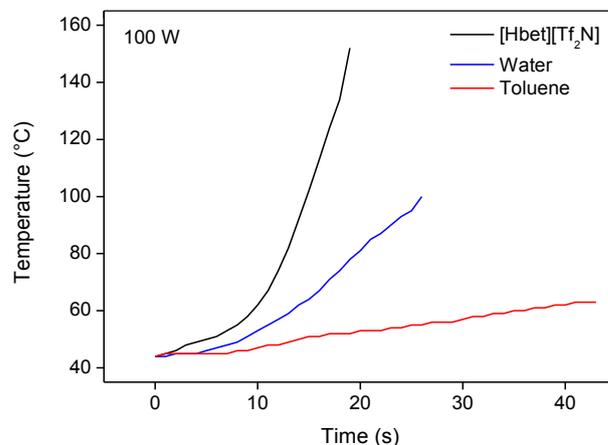


Figure 14. Heating of different solvents in a microwave oven (100 W), equipped with an infrared temperature probe.

Microwave heating

In most of our experiments, the ionic liquid was heated by a conventional heating source. However, since the leaching of YOX in the ionic liquid requires high temperatures over prolonged periods of time, it is interesting to note that ionic liquids can be heated in a very energy-efficient way by microwave irradiation. Ionic liquids consist entirely of ions as opposed to water or organic solvents which explains the high adsorption of microwave radiation.⁶⁴ Microwaves do not interfere with the dissolution process and provide a highly economical way to heat an ionic liquid in an industrial context.^{64,65} The immediate on/off behavior of microwave irradiation is also useful for process control. A programmable microwave oven with temperature and pressure control was used to test this. At 100 W, the ionic liquid $[\text{Hbet}][\text{Tf}_2\text{N}]$ was

heated to a temperature of 100 °C in less than 15 s (Figure 14). The temperature can be kept constant at a low cost.

Conclusion

The ionic liquid leaching system described in this work is a major improvement compared to mineral acid leaching, since it allows the selective dissolution of $Y_2O_3:Eu^{3+}$ (YOX) without dissolving the other phosphors (HALO, BAM, LAP). An interesting feature of the process is that the $(Sr,Ca)_{10}(PO_4)_6(Cl,F)_2:Sb^{3+},Mn^{2+}$ phosphor was not leached by the ionic liquid (< 0.05 wt%). This non-valuable broad-band white phosphor known as “halophosphate” (HALO) can make up as much as 50 wt% of the lamp phosphor waste fraction. Dissolution of HALO is unavoidable when using dilute mineral acids, especially in the conditions required for the dissolution of $Y_2O_3:Eu^{3+}$. The unusual selectivity of the ionic liquid was attributed to the fact the [Hbet][Tf₂N] is unable to solvate anions efficiently, which explains why it is only able to dissolve metal oxides efficiently and not metal salts like (LnCl₃, NaCl). The yttrium and europium dissolved in the ionic liquid [Hbet][Tf₂N] were then stripped with an HCl solution or by adding pure (solid) oxalic acid directly to the ionic liquid. The oxalic acid route precipitates the rare earths as a mixed (yttrium,europium) oxalate salt, which can be transformed into new $Y_2O_3:Eu^{3+}$ phosphor by a simple calcination step at 950 °C. The ionic liquid is automatically regenerated during the stripping step and can be reused. This innovative approach offers selectivity, mild conditions and reusability which make this a promising green technology for the targeted recovery of $Y_2O_3:Eu^{3+}$ and the valorization of lamp phosphor waste. 70 % of the value and 80 % of the critical rare earths in the lamp phosphor waste are recovered this way. Further processing of the terbium-rich rest fraction can be done but requires much harsher conditions. No additional waste is generated during this process and there is no need for additional solvent extraction steps since the YOX is dissolved selectively and immediately regenerated. This opens the way to a more simple, economic and energy-efficient industrial process for the revalorization of lamp phosphor waste.

Acknowledgements

The authors wish to thank the KU Leuven (projects GOA/13/008 and IOF-KP RARE³) and the FWO Flanders (PhD fellowship to DD) for financial support. The authors would like to thank Dorien Baeten for the help with TGA measurements, Prof. Erik van der Eycken and Geert Hooyberghs for access to microwave oven facilities and Michèle Vanroelen for the ICP-MS measurements. Jeroen Sniekers is also thanked for helping with the SEM images and Neil Brooks for powder XRD characterization.

Notes and references



^a KU Leuven, Department of Chemistry, Celestijnenlaan 200F - P.O. Box 2404, B-3001 Heverlee (Belgium); E-mail: Koen.Binnemans@chem.kuleuven.be

Electronic Supplementary Information (ESI) available: Characterization of the synthesized $Y_2O_3:Eu^{3+}$ phosphor, including SEM images, XRD diffractograms and luminescence decay curves. See DOI: 10.1039/b000000x/

1. D. Schüler, M. Buchert, R. Liu, G. S. Ditttrich and C. Merz, *Study on rare earths and their recycling*, Öko-Institut, Darmstadt, 2011.
2. *Report on Critical raw materials for the EU*, European Commission, DG Enterprise & Industry, Brussels, 2014.
3. K. Binnemans, P. T. Jones, B. Blanpain, T. Van Gerven, Y. Yang, A. Walton and M. Buchert, *J. Clean. Prod.*, 2013, 51, 1-22.
4. *Critical Materials Strategy*, U.S. Department of Energy, USA, 2010.
5. K. Binnemans, P. T. Jones, K. Acker, B. Blanpain, B. Mishra and D. Apelian, *JOM*, 2013, 65, 846-848.
6. M. Tanaka, T. Oki, K. Koyama, H. Narita and T. Oishi, in *Handbook on the Physics and Chemistry of Rare Earths*, eds. J.-C. G. Bünzli and V. K. Pecharsky, Elsevier-Amsterdam, 2013, vol. 43, ch. 255, pp. 159-212.
7. Y. Wu, X. Yin, Q. Zhang, W. Wang and X. Mu, *Resour. Conserv. Recy.*, 2014, 88, 21-31.
8. Solvay, Press release, <http://www.solvay.com>, 2012.
9. K. Binnemans and P. T. Jones, *J. Rare Earth*, 2014, 32, 195-200.
10. T. Vander Hoogerstraete, S. Wellens, K. Verachtert and K. Binnemans, *Green Chem.*, 2013, 15, 919-927.
11. S. Wellens, R. Goovaerts, C. Moller, J. Luyten, B. Thijs and K. Binnemans, *Green Chem.*, 2013, 15, 3160-3164.
12. T. Vander Hoogerstraete and K. Binnemans, *Green Chem.*, 2014, 16, 1594-1606.
13. K. Larsson, C. Ekberg and A. Ødegaard-Jensen, *Waste Manage.*, 2013, 33, 689-698.
14. J. J. Braconnier and A. Rollat, *Solvay, European Patent*, EP 2419377 A1, 2012.
15. T. Hirajima, A. Bissombolo, K. Sasaki, K. Nakayama, H. Hirai and M. Tsunekawa, *Int. J. Miner. Process.*, 2005, 77, 187-198.
16. T. Hirajima, K. Sasaki, A. Bissombolo, H. Hirai, M. Hamada and M. Tsunekawa, *Sep. Purif. Technol.*, 2005, 44, 197-204.
17. G. Mei, P. Rao, M. Mitsuaki and F. Toyohisa, *J. Wuhan. Univ. technol.*, 2009, 24, 418-423.
18. V. Innocenzi, I. De Michelis, B. Kopacek and F. Vegliò, *Waste Manage.*, 2014, 34, 1237-1250.
19. H. Liu, S. Zhang, D. Pan, J. Tian, M. Yang, M. Wu and A. A. Volinsky, *J. Hazard. Mater.*, 2014, 272, 96-101.
20. M. A. Rabah, *Waste Manage.*, 2008, 28, 318-325.
21. C. Tunsu, C. Ekberg and T. Retegan, *Hydrometallurgy*, 2014, 144-145, 91-98.
22. F. Yang, F. Kubota, Y. Baba, N. Kamiya and M. Goto, *J. Hazard. Mater.*, 2013, 254-255, 79-88.
23. H. L. Yang, W. Wang, H. M. Cui, D. L. Zhang, Y. Liu and J. Chen, *J. Chem. Technol. Biotechnol.*, 2012, 87, 198-205.
24. G. Mei, P. Rao, M. Mitsuaki and F. Toyohisa, *J. Wuhan. Univ. technol.*, 2009, 24.
25. *R. Otto and A. Wojtalewicz*, US patent 2012/0027651 A1.
26. A. P. Abbott, G. Frisch, S. J. Gurman, A. R. Hillman, J. Hartley, F. Holyoak and K. S. Ryder, *Chem. Commun.*, 2011, 47, 10031-10033.
27. S. Wellens, T. Vander Hoogerstraete, C. Möller, B. Thijs, J. Luyten and K. Binnemans, *Hydrometallurgy*, 2014, 144-145, 27-33.
28. A. Rout, S. Wellens and K. Binnemans, *RSC Adv.*, 2014, 4, 5753-5758.
29. S. Wellens, B. Thijs, C. Moller and K. Binnemans, *Phys. Chem. Chem. Phys.*, 2013, 15, 9663-9669.
30. A. P. Abbott, G. Frisch, J. Hartley and K. S. Ryder, *Green Chem.*, 2011, 13, 471-481.
31. S. Wellens, B. Thijs and K. Binnemans, *Green Chem.*, 2012, 14, 1657-1665.
32. Y. Gu, *Green Chem.*, 2012, 14, 2091-2128.
33. Q. Zhang, S. Zhang and Y. Deng, *Green Chem.*, 2011, 13, 2619-2637.

34. T. Welton, *Green Chem.*, 2011, 13, 225-225.
35. N. V. Plechkova and K. R. Seddon, *Chem. Soc. Rev.*, 2008, 37, 123-150.
36. P. Nockemann, B. Thijs, S. Pittois, J. Thoen, C. Glorieux, K. Van Hecke, L. Van Meervelt, B. Kirchner and K. Binnemans, *J. Phys. Chem. B*, 2006, 110, 20978-20992.
37. P. Nockemann, B. Thijs, T. N. Parac-Vogt, K. Van Hecke, L. Van Meervelt, B. Tinant, I. Hartenbach, T. Schleid, V. T. Ngan, M. T. Nguyen and K. Binnemans, *Inorg. Chem.*, 2008, 47, 9987-9999.
38. P. Nockemann, B. Thijs, K. Lunstroot, T. N. Parac-Vogt, C. Görrler-Walrand, K. Binnemans, K. Van Hecke, L. Van Meervelt, S. Nikitenko, J. Daniels, C. Hennig and R. Van Deun, *Chem-Eur. J.*, 2009, 15, 1449-1461.
39. R. Reddy, *J. Phase Equilib. Diffus.*, 2006, 27, 210-211.
40. T. Vander Hoogerstraete, S. Jamar, S. Wellens and K. Binnemans, *Anal. Chem.*, 2014, 86, 3931-3938.
41. T. Vander Hoogerstraete, B. Onghena and K. Binnemans, *Int. J. Mol. Sci.*, 2013, 14, 21353-21377.
42. B. Thijs, PhD thesis, KU Leuven, 2007.
43. R. M. C. Dawson, Oxford University press, New York, 3rd edn., 1986, pp. 8-9.
44. T. Vander Hoogerstraete, B. Onghena and K. Binnemans, *J. Phys. Chem. Lett.*, 2013, 4, 1659-1663.
45. M. G. Freire, P. J. Carvalho, A. M. S. Silva, L. M. N. B. F. Santos, L. P. N. Rebelo, I. M. Marrucho and J. A. P. Coutinho, *J. Phys. Chem. B*, 2008, 113, 202-211.
46. M. G. Freire, C. M. S. S. Neves, P. J. Carvalho, R. L. Gardas, A. M. Fernandes, I. M. Marrucho, L. M. N. B. F. Santos and J. A. P. Coutinho, *J. Phys. Chem. B*, 2007, 111, 13082-13089.
47. Y. Zhang and P. S. Cremer, *Curr. Opin. Chem. Biol.*, 2006, 10, 658-663.
48. L. Bai, X. Wang, Y. Nie, H. Dong, X. Zhang and S. Zhang, *Sci. China: Chem.*, 2013, 56, 1811-1816.
49. C. M. S. S. Neves, M. G. Freire and J. A. P. Coutinho, *RSC Adv.*, 2012, 2, 10882-10890.
50. C. Abels, C. Redepenning, A. Moll, T. Melin and M. Wessling, *J. Membr. Sci.*, 2012, 405-406, 1-10.
51. J. F. Fernández, D. Waterkamp and J. Thöming, *Desalination*, 2008, 224, 52-56.
52. J. Lemus, J. Palomar, F. Heras, M. A. Gilarranz and J. J. Rodríguez, *Sep. Purif. Technol.*, 2012, 97, 11-19.
53. B. Onghena, J. Jacobs, L. Van Meervelt and K. Binnemans, *Dalton Trans.*, 2014, 43, 11566-11578.
54. G. Adachi, N. Imanaka and Z. C. Kang, *Binary Rare Earth Oxides*, Kluwer Academic Publishers, Dordrecht, 2006.
55. X. Wan, *Solvay, China Patent*, EP 2176375 A1, 2010.
56. C. R. Ronda, T. Jüstel and H. Nikol, *J. Alloys Compd.*, 1998, 275-277, 669-676.
57. N. C. Chang, *J. Appl. Phys.*, 1963, 34, 3500-3504.
58. K. Binnemans and C. Gorller-Walrand, *J. Rare Earth*, 1996, 173-180.
59. T. Hirai, T. Hirano and I. Komasaawa, *J. Mater. Chem.*, 2000, 10, 2306-2310.
60. M. Jang, S. M. Hong and J. K. Park, *Waste Manage.*, 2005, 25, 5-14.
61. W. A. Durão Jr, C. A. de Castro and C. C. Windmöller, *Waste Manage.*, 2008, 28, 2311-2319.
62. C. Raposo, C. C. Windmöller and W. A. Durão Júnior, *Waste Manage.*, 2003, 23, 879-886.
63. T. Horikawa and K. Machida, *Mater. Integr.*, 2011, 24, 37-43.
64. J. Hoffmann, M. Nuchter, B. Ondruschka and P. Wasserscheid, *Green Chem.*, 2003, 5, 296-299.
65. A. Arfan and J. P. Bazureau, *Org. Process Res. Dev.*, 2005, 9, 743-748.

Table of contents entry



A recycling process for lamp phosphor waste was developed based on the selective dissolution and revalorization of the valuable red lamp phosphor $Y_2O_3:Eu^{3+}$ in the functionalized ionic liquid [Hbet][Tf₂N].
