

Organic & Biomolecular Chemistry

Accepted Manuscript



This is an *Accepted Manuscript*, which has been through the Royal Society of Chemistry peer review process and has been accepted for publication.

Accepted Manuscripts are published online shortly after acceptance, before technical editing, formatting and proof reading. Using this free service, authors can make their results available to the community, in citable form, before we publish the edited article. We will replace this *Accepted Manuscript* with the edited and formatted *Advance Article* as soon as it is available.

You can find more information about *Accepted Manuscripts* in the [Information for Authors](#).

Please note that technical editing may introduce minor changes to the text and/or graphics, which may alter content. The journal's standard [Terms & Conditions](#) and the [Ethical guidelines](#) still apply. In no event shall the Royal Society of Chemistry be held responsible for any errors or omissions in this *Accepted Manuscript* or any consequences arising from the use of any information it contains.

ARTICLE

Chiral Nanostructuring of Multivalent Macrocycles in Solution and on Surfaces

Cite this: DOI: 10.1039/x0xx00000x

Marco Caricato,^a Arnaud Deforge,^b Davide Bonifazi,^{b,c} Daniele Dondi,^a Andrea Mazzanti,^d and Dario Pasini,^{*a,e}

Received 00th January 2012,

Accepted 00th January 2012

DOI: 10.1039/x0xx00000x

www.rsc.org/

We describe the design and synthesis of a novel functionality-rich, homochiral macrocycle, possessing overall molecular D_2 symmetry, in which multivalency is introduced into the covalent framework by means of four suitably positioned pyridine moieties. The macrocycle synthesis is carried out with functionalized, enantiopure 1,1'-binaphthyl synthons as the source of chirality, by means of a room temperature esterification reaction as the cyclization procedure. Upon addition of Pd^{2+} , coordination of the pyridine moieties occur both *intra* and *intermolecularly*, to afford chiral ordered mono and dimeric macrocycles or multimeric aggregates depending on the solvents and conditions used. The metal binding event takes place in combination with a significant macrocyclic conformational rearrangement detected by circular dichroism spectroscopy. When in combination with a third component (C_{60}), the macrocycle- Pd^{2+} hybrid undergoes surface-confined nanostructuring into chiral nanofibres.

Introduction

Organic nanotubes are currently generating substantial interest: they are assembled nanospaces of suitable dimensions in which to carry out host-guest chemistry, reversible binding of smaller species for transport, storage or chemical transformation purposes; they have been utilized as biological ion channel mimics, or for addressing tailored materials properties.¹

Conformationally stable macrocycles have been used with success in the realization of organic nanotubes, by means of their assembly in the third dimension by the supramolecular organization of suitable self-recognizing functionalities embedded into the cyclic skeleton. In order to form porous nanotubes, preformed, covalent macrocycles, do possess a number of advantages over smaller building blocks. The covalent cyclic skeleton can avoid the possibility of having interpenetrated networks, often observed in metal-organic frameworks, and can lead to a cavity of predetermined, and tunable, dimensions. Some molecular building blocks successfully adopted for this strategy include cyclic oligopeptides, macrocyclic oligophenyleneethylenes, urea-containing macrocycles, aromatic oligoamides, calixarenes and cyclodextrins.² Whereas early examples of cyclic oligopeptides incorporate alternating aminoacid residues with opposed stereochemistries, resulting into achiral cyclic covalent molecules, more recent reports have explored similar cyclic systems with an overall net chirality.³

Several elegant examples of self-assembled helical chemical systems have been reported to date; the transmission of the chiral information often relies on "weak" molecular chirality (for example, aliphatic carbon chains with an asymmetric carbon atom) expressed far away from the assembly area (for example, π - π stacking of extended aromatics as the assembly mode).⁴ The introduction of a robust source of chirality into a suitable cyclic covalent skeleton can lead to innovative systems, in which helicity, and directionality, when transferred to the whole nanotube assembly, might give access to unprecedented properties at the nanoscale.⁵

We have recently reported the preparation of several chiral macrocycles incorporating Binol (1,1'-bi-2-naphthol) units, as a rigid, robust source of chirality induction. We have shown their applications for the chiroptical sensing of organic or ionic species.⁶ In this paper, we report on the design, synthesis, supramolecular and nanoscale organization of homochiral, Binol-based multivalent macrocycles, using a metal-coordination strategy as the assembly mode.

Results and Discussion

Design and Synthesis

Our design approach to chiral nanoscale constructs from monomeric macrocycles containing binaphthyl units can be summarized by the following key points:

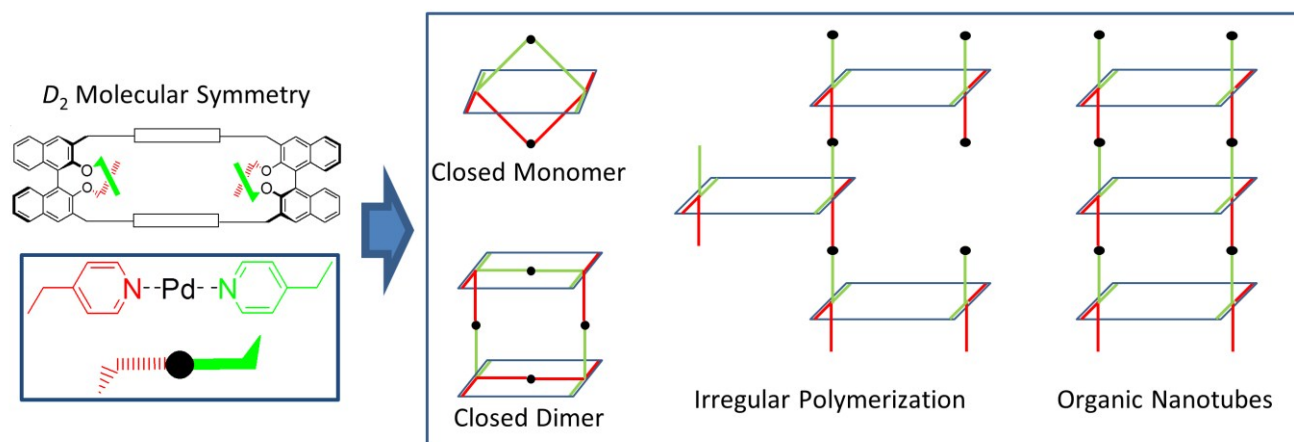


Fig 1 Pd²⁺-induced coordinative assemblies built from chiral multivalent macrocycles.


a) the use of rigid aromatic spacers joining two binaphthyl-based units, in order to define an internal, non-collapsible macrocyclic inner space, and of a minimum number of sp^3 carbon atoms, which impart a higher flexibility and conformational mobility to the covalent structure with respect to sp or sp^2 hybridized carbon atoms;

b) the use of macrocyclization reactions able to generate chemical functionalities which could ensure both configurational and chemical stability to the resulting cyclic, covalent structure. Ester functionalities can ensure supramolecular “silence”, in terms of competition/interaction with other functionalities introduced within the macrocyclic framework, for assembly purposes;

c) the coordination of the pyridine moieties to suitable PdCl₂ complexes as the 3D assembly mode; this interaction, reported to form *trans*-coordinated complexes, has been previously used for the construction of complex supramolecular architectures, and it can ensure appropriate geometries in the assembly process.^{7,8}

Figure 1 illustrates graphically the concepts expressed above. The homochiral, D_2 symmetrical macrocyclic skeleton (top left) contains four *p*-linked pyridine moieties, of which two are above (green) and two below (red) the mean plane of the macrocycle. In the presence of a suitable Pd²⁺ source, coordination of two pyridine units can form, in principle, different kinds of nanoscale structures: *i*) closed monomers and dimers, with an overall D_2 symmetry, which are feasible if the coordination can occur *intramolecularly* between pyridine moieties belonging to the two different binaphthyl units, facing each other, of the same macrocyclic molecule; *ii*) irregular assemblies, or regular helical nanotubes, in which coordination involving the pyridine moieties occurs exclusively in an *intermolecular* fashion.

The synthesis of the key macrocycle is reported in Scheme 1. We have utilized commercially-available, ether bridged dicarboxylic acid **2** as the rigid spacer, deemed suitable in order to define an internal, noncollapsible cavity, and previously utilized in the construction of rigid macrocycles for nanotube assembly.^{2f} Benzylic diol (*R*)-**1**, bearing protected methoxy functionalities in the 2,2' positions of the binaphthyl skeleton, could be cyclized with equimolar quantities of **2** to give model macrocycle (*RR*)-**3** in fair yields, after purification by column chromatography.

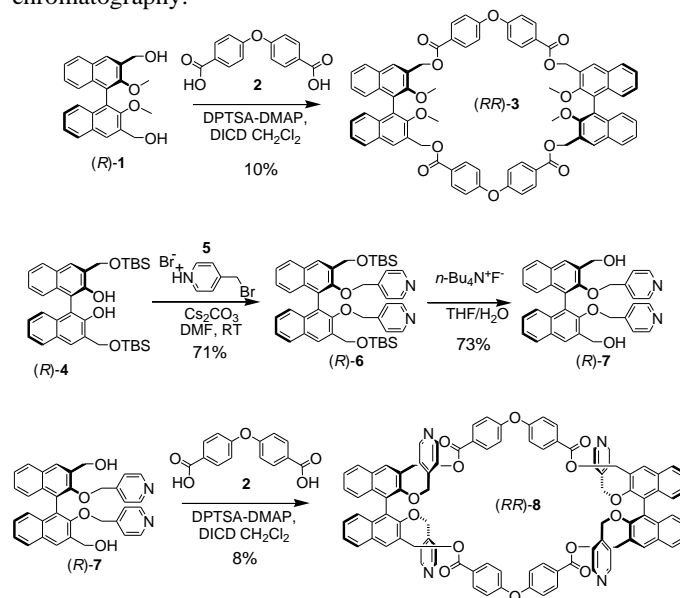

Scheme 1 Synthesis of homochiral model macrocycle (*RR*)-**3**, and of homochiral multivalent macrocycle (*RR*)-**8**.

The introduction of four pyridine functionalities within the macrocyclic framework had to be carried out convergently, since attempts to unmask the protected phenol functionalities in (*RR*)-**3**, in order to carry out postfunctionalization of the covalent structure, resulted inevitably in the degradation of the cyclic framework. The synthesis of elaborated precursor (*R*)-**7** made use of our recently reported strategy^{6c} for compound (*R*)-**4** in excellent yields; subsequent alkylation in mildly basic conditions afforded precursor (*R*)-**6**, which could be deprotected using literature conditions to give (*R*)-**7**. The cyclization of elaborated precursor (*R*)-**7**, in the esterification conditions reported above for (*R*)-**1**, afforded macrocycle (*RR*)-**8**, after purification by column chromatography using polar eluent mixtures, in reasonable yields. In the macrocyclization reactions for the synthesis of (*RR*)-**3** and (*RR*)-**8**, conversions of starting materials were complete; traces of higher macrocycles, and oligomeric-polymeric baseline material completed the compositions of the reaction mixtures. Precursors and macrocycles were fully characterized using NMR spectroscopy and mass spectrometric techniques. Macrocycle (*RR*)-**8** could be stored intact for several months as a solid at 0 °C.

Spectroscopic Characterization in Solution

NMR, UV and CD spectroscopies were all used to characterize the adducts formed upon addition of Pd(MeCN)₂Cl₂ or Pd(PhCN)₂Cl₂, used as Pd²⁺ sources, to macrocycles and model compounds. Both Pd²⁺ salts have been previously reported for the formation of complexes in which two pyridine functionalities displace the labile nitrile ligands and leave the two chlorine ligands, to form *trans*-tetracoordinated, square-planar complexes.⁷ Both salts are fully soluble in polar organic solvents (MeCN, DMSO).

¹H NMR studies of macrocycle (*RR*)-**8** in different solvents showed a complex situation which was difficult to rationalize immediately. Further complications in the interpretation of the results derived from solubility/precipitation behaviour of the adducts formed by the addition of Pd²⁺ by changing the concentration conditions of the samples.

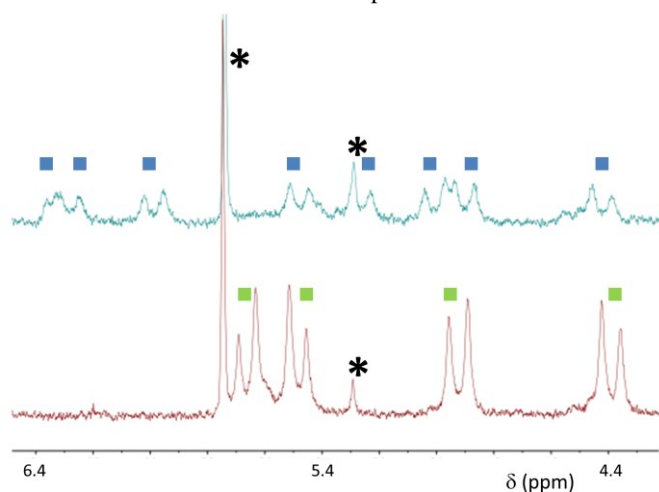


Fig 2 Partial ¹H NMR spectra of macrocycle (*RR*)-**8** (*d*₆-DMSO, 3 mM, bottom) and of (*RR*)-**8** in the presence of 2 equivalents of Pd(MeCN)₂Cl₂ (top). Residual solvent peaks are marked with asterisks.

When macrocycle (*RR*)-**8** was used at relatively high concentration (1-3 mM) in *d*₆-DMSO, by the addition of increasing amounts of Pd(MeCN)₂Cl₂ or Pd(PhCN)₂Cl₂ a completely soluble adduct was generated, and no further signal changes could be detected upon addition of more than 2 equivalents of Pd²⁺. Fig. 2 shows the two sets of resonances for the symmetry-related CH₂ groups (bottom, two double doublets for the diastereotopic protons), becoming four different sets of resonances upon reaching two equivalents of Pd²⁺ source. This splitting is in agreement with the presence of a “closed dimer” structure (Fig. 1), in which the aggregate maintains a *D*₂ overall symmetry, but the molecular fragments (red and green in the figure) are no longer equivalent through symmetry, generating different signals in the ¹H NMR spectra. To further ensure that the observed ¹H NMR signals belong to the “closed dimer” proposed structure, 2D-¹H-DOSY NMR spectra were recorded, to obtain an estimate for the size of the aggregate and compare it to the assumed structure. The measured diffusion coefficient for the free macrocycle (*D* = 1.25 × 10⁻¹⁰ m² s⁻¹) was found to be essentially twice of that of the adduct formed upon addition of two equivalents of Pd(PhCN)₂Cl₂ (*D* = 6.31 × 10⁻¹¹ m² s⁻¹) (Fig. S1, Supporting Information). The values can be translated by the Stokes–Einstein equation⁹ to a hydrodynamic radius and a dimension that is essentially double with respect to that of the macrocycle, in agreement with the calculated structures by molecular modelling (*vide infra*).

¹H NMR studies were also performed in MeCN, in order to have a direct comparison with the titration behaviour monitored by UV and CD spectroscopies (*vide infra*). When macrocycle (*RR*)-**8** was used at relatively high concentration (1 mM) in MeCN, the addition of increasing amounts of Pd(MeCN)₂Cl₂ or Pd(PhCN)₂Cl₂ resulted in the formation of an insoluble precipitate. This observation suggested the possibility of an irregular aggregation. However, a similar precipitation phenomena, at the same concentration, upon titration with Pd(MeCN)₂Cl₂, could be observed with control compound (*R*)-**6**. Since difunctional (*R*)-**6** can only form linear aggregates, the precipitation suggested the possibility that the aggregate species formed in (*RR*)-**8** could indeed be ordered, but not very soluble in the specific solvent. Even pyridine by itself in CH₃CN formed, at millimolar concentrations, insoluble precipitates when Pd(MeCN)₂Cl₂ was added to the solution.

Control studies carried out with pyridine in MeCN at lower concentration levels (< 10⁻⁴ M) showed that, upon addition of the Pd²⁺ source, the complex remained fully soluble; interestingly, and to our surprise, the displacement of the MeCN ligands on the Pd²⁺ coordinating center is not completely regiospecific. The formation of two different types of complexes, attributed to the *cis* and *trans* Pd(Py)₂Cl₂ square planar species, in a 1:3 ratio, respectively, is evident upon addition of more than 0.5 equivalent of Pd(MeCN)₂Cl₂ (Fig. S2). In the case of difunctional compound (*R*)-**6**, in more diluted conditions (2.3 × 10⁻⁵ M), fully soluble adducts upon the addition of Pd²⁺ were obtained. The broadening of all proton resonances in the ¹H NMR spectra support strongly the

formation of a coordination polymer, with no further changes in the spectra observed when more than 1 equivalent of Pd^{2+} is added with respect to the ligand (*R*)-6. The observed stoichiometry at saturation (1:1 ligand vs. Pd^{2+}) matches with the complete incorporation of the pyridine moieties (two per ligand) into the Pd^{2+} complexes (Fig. S3).

In the case of macrocycle (*RR*)-8 (Fig. 3) at low concentrations (2.8×10^{-5} M), upon addition of the Pd^{2+} source, no precipitation occurred and ^1H NMR spectroscopy revealed the assembly of soluble aggregates; these aggregates are in part polymeric in nature, as testified by the severe broadening of the baseline. A highly symmetrical adduct is also present, which possesses the same sets of proton resonances as the monomer macrocycle.

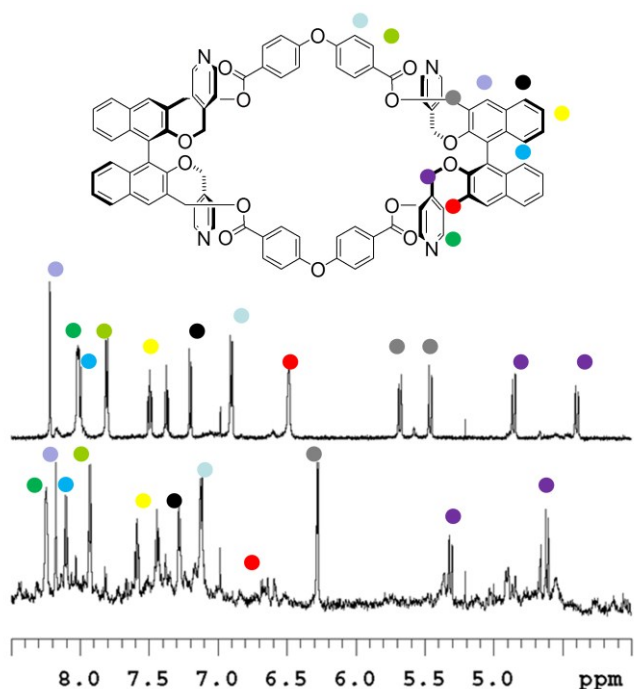


Fig. 3 ^1H NMR of in d_7 -MeCN at 25 °C top) macrocycle (*RR*)-8 (2.8×10^{-5} M, 500 MHz); bottom) same with 2 equiv. of $\text{Pd}(\text{MeCN})_2\text{Cl}_2$ added.

We have attributed this adduct to the “closed monomer” structure (Fig. 1), since in this structure “red” and “green” molecular fragments are equivalent by symmetry operations, therefore not generating any splitting in the NMR pattern. Together with the downfield shifts of the α -pyridyl protons, and the broadening of the β -pyridyl protons under the baseline, which could be expected upon Pd^{2+} coordination, substantial variations in chemical shifts could be observed for the signals attributable to the $-\text{CH}_2-$ protons, as to testify the high degree of conformational rearrangement that the macrocycle has to undertake in order to form this particular structure.

MeCN as a solvent has ideal UV cutoff properties for the study of the systems presented in this paper. In fact, three distinct chromophoric units are present, and they possess characteristic UV bands; since they are joined by sp^3 carbon atoms, they are not in conjugation with each other, so that the specific electronic transitions should persist in the UV spectra

of the precursors and macrocycles. The major absorption band (Fig. S4), centered around 230 nm can be attributed to the binaphthyl chromophore, with molar absorptivities ($\log \epsilon$ between 4 and 5) fully in line with other, non-conjugated binaphthyl synthons.^{6b-c,6e} The band centered at 270 nm, present in macrocycles (*RR*)-3 and (*RR*)-8 is assigned to the spacer chromophore unit, given the fact it is completely absent in precursor (*R*)-6, and also by comparison with published UV spectra of alkyl ester derivatives of **2**.¹⁰ The band of the pyridine chromophores is known to be low in intensity¹¹ and it is probably hidden by the broad band of the binaphthyl units. Circular dichroism spectroscopy of the same compounds show the exciton couplet typical of binaphthyl moieties (Fig. S5), corresponding to the maximum absorption band in the UV spectra. No induced CD signal could be observed in the UV bands of the other chromophores in either macrocycles (*RR*)-3 and (*RR*)-8, or the precursors.

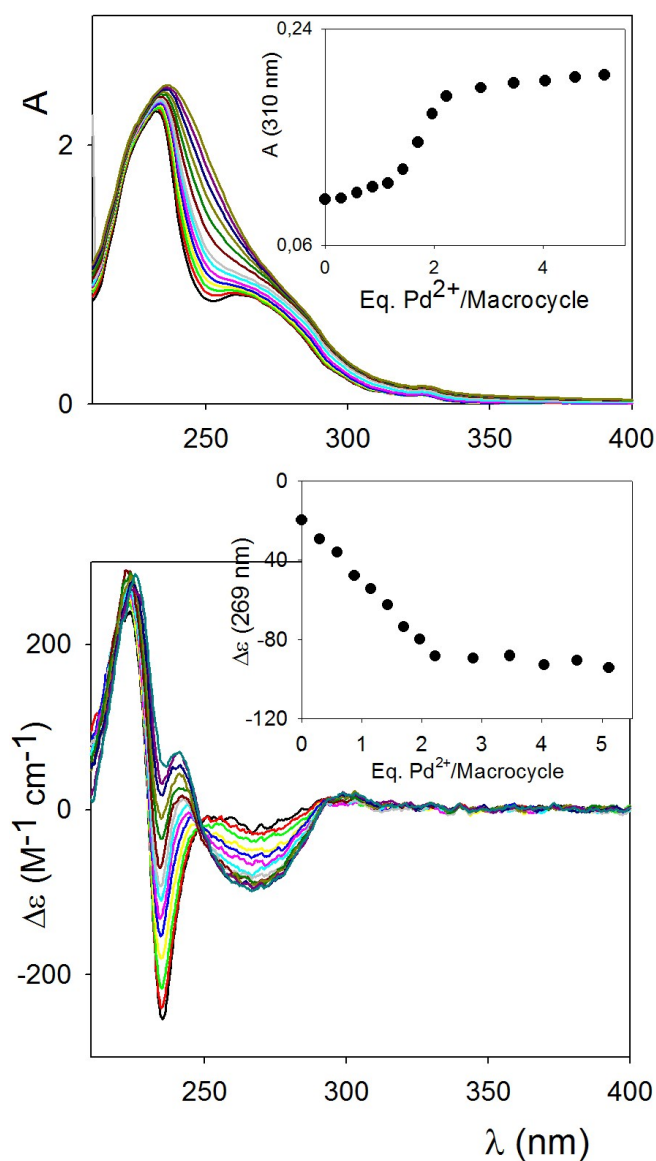


Fig. 4 Top: UV Titration of macrocycle (*RR*)-**8** (1.33×10^{-5} M) with $\text{Pd}(\text{MeCN})_2\text{Cl}_2$ in MeCN at 25 °C. Inset: titration profile vs. Pd^{2+} added equivalents at 310 nm. **Bottom:** CD Titration of macrocycle (*RR*)-**8** (1.33×10^{-6} M) with $\text{Pd}(\text{MeCN})_2\text{Cl}_2$ in MeCN at 25 °C. Inset: titration profile vs. Pd^{2+} added equivalents at 269 nm.

The UV/Vis titration was complicated by the inherent absorption of the Pd^{2+} source (Fig. S6) in the absorbance region of the chromophores belonging to the macrocycle (*RR*)-**8**. Upon addition of $\text{Pd}(\text{MeCN})_2\text{Cl}_2$ to (*RR*)-**8**, at concentrations similar to those of the ^1H NMR titration, small but substantial shifts in the silent absorbance region of the added Pd^{2+} species (310 nm), fully saturating at 2 equivalents, could be detected (Fig. 4, top).

The monitoring of the titration using CD spectroscopy was certainly more informative. An intense induced CD band appeared in correspondence to the band of the spacer chromophore unit at *ca.* 270 nm, and saturates upon the addition of two equivalents of Pd^{2+} . The exciton couplet band attributable to the binaphthyl unit shows little variation in its highest energy branch at 220 nm. Intense induced CD activity could also be detected between 230 and 250 nm, and could be attributed to the chromophore band arising from the formation of the Pd^{2+} complex with the pyridines. This band, which is partially superimposed with the lowest energy branch of the binaphthyl couplet, and with the other band centered at 270 nm, does not saturate at 2 equivalents; a continuous shift of this band is presumably signalling a shift of the equilibrium between of closed monomer/polymeric aggregates upon addition of Pd^{2+} source in solution. The induced CD signal in the bands of the chromophore spacer ester and of the Pd^{2+} complex with the pyridine moieties indicate an overall chirality of the closed monomer/polymeric aggregates as a whole, and it stresses the high degree of conformational rearrangement occurring, upon coordination, involving all moieties of the macrocycle.

Control experiments with compound (*R*)-**6** were carried out under identical conditions. The CD spectra revealed very little changes upon complexation, indicating how difunctional (*R*)-**6** does not have to change its conformation in the formation of the coordination oligomeric/polymeric adduct (Fig. S7).

Surface Assembly Studies

Atomic Force Microscopy is a powerful tool for the detection and visualization of assembled nanoscale structures.¹² To further investigate and substantiate the behavior of the systems described here, AFM experiments were performed at the air/HOPG (Highly Ordered Pyrolytic Graphite) interface. AFM samples were prepared by drop-casting appropriate solutions onto a freshly prepared surfaces. The samples were air-dried and imaged with an AFM apparatus in the tapping mode. In preliminary experiments, samples were prepared with two equivalents of $\text{PdCl}_2(\text{CH}_3\text{CN})_2$ vs macrocycle (*RR*)-**8**, in CHCl_3 at diluted ($< 10^{-5}$ M) concentrations. No interesting nanoscale aggregate could be observed under these conditions. In view of the capability of similar macrocycles to form stable complexes with C_{60} ,^{6b,6e,6f} solutions containing one equivalent of pristine C_{60} vs macrocycle (*RR*)-**8** were realized; in this case,

the solution of C_{60} with the macrocycle were first premixed, and the solution of $\text{PdCl}_2(\text{MeCN})_2$ was added several hours later. Upon deposition, nanostructured material could be observed by AFM. The images show elongated fibres together with amorphous clusters. The nanostructured materials are essentially composed by monodimensional structures with dimensions of 10-20 μm in length and 4 nm in height (Fig. S8). The last value is higher than the one measured by molecular modelling (between 1 and 2 nm, see below). In fact, by depositing the same solutions a few days after, AFM images show different fibres. They are shorter (between 0.5 and 2 μm) and the profiles indicate heights between 0.5 and 1 nm (Fig. 5), thus suggesting a time-dependent evolutive process.

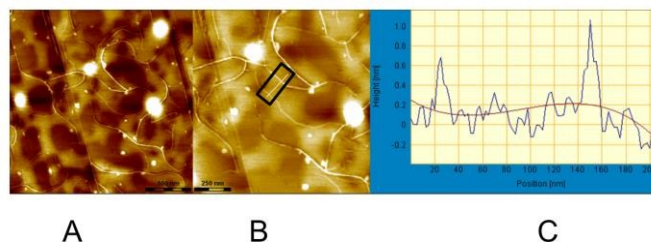


Fig. 5 AFM images of (*RR*)-**8**, C_{60} and $\text{PdCl}_2(\text{MeCN})_2$ at the HOPG interface. (A and B) Example of fibres. (C) A height profile measured along the white line (highlighted in black box) in (B).

By observing the same sample after three months, we found long fibers (Fig. 6) possessing the molecular height of the single aggregates (1-1.5 nm).

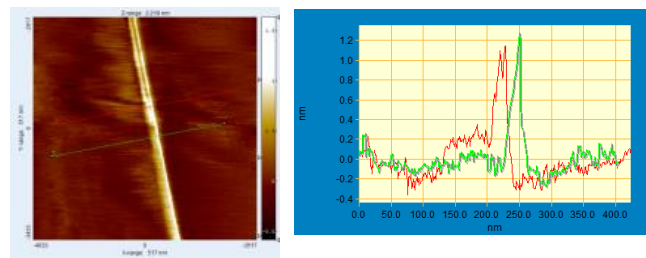


Fig. 6 AFM images of (*RR*)-**8**, C_{60} and $\text{PdCl}_2(\text{MeCN})_2$ visualized after a few months. Left: example of fibres. Right: a height profile measured along the colored lines.

Control experiments of the single components and of their binary mixtures only showed amorphous materials. We also performed control experiments with difunctional compound (*R*)-**6**, again obtaining no nanostructured fibers under the same conditions as those used for macrocycle (*RR*)-**8**.

These observations are in agreement with the formation of ordered nanostructured material, in which the nanoscale fibres are formed by single macrocyclic units piled up along a preferential dimension; the results exclude the formation of a fully crosslinked network, yet they do not support the formation of macroscopic chiral nanotubes on surfaces. Unfortunately, due to some limitations in the solubility (see above), we could not perform any studies in solution studies. On the other hand it is likely that the fullerenes spheres are being included in the macrocycle- Pd^{2+} coordination complexes, thus acting as

templates directing the growth and the assembly of the chiral monomolecular fibres on the surface.

Molecular Modelling

Calculations were initially performed on macrocycle (*RR*)-**8** with semiempirical method PM3 to locate local minima. The other calculations were performed by inserting the Pd²⁺ atoms, then the structures were preliminarily optimized with PM3, and refined with DFT B3LYP/LANL2DZ.

Initially, the *trans* coordination of the pyridine moieties and of the two chlorine atoms as ligands on the Pd²⁺ center was imposed *a priori* before further optimization. Even using the preliminary PM3 screening, it appeared evident that the *intramolecular* positioning of two pyridine moieties belonging to two different binaphthyl units of the same macrocycle afforded a plausible and relatively stable conformer. Instead, the possible complexation of Pd²⁺ by two pyridines attached to the same binaphthyl unit, either in a *cis* or a *trans* complexation mode, could be thoroughly excluded. Upon optimization with DFT, two low energy conformers could be located (A and B in Fig. 7), with the form B being more stable by about 5 kcal mol⁻¹.

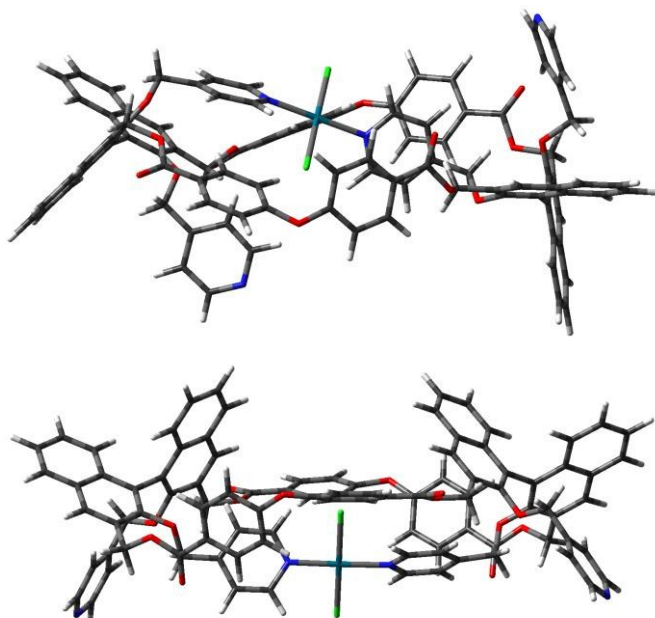


Fig. 7 Minimized conformers A (top) and B (bottom) for (*RR*)-**8**·PdCl₂.

The difference between the two resides on which pyridine attached to the naphthyl unit of the facing binaphthyls is involved in the intramolecular *trans* complexation on the Pd²⁺ center. In form A, the two pyridine involved are one above and one below the mean plane of the macrocycle (red and green in Fig. 1), whereas in form B they are both above the mean plane of the macrocycle (both green according to Fig. 1). The molecules show similar dihedral angles for the binaphthyl units (79 and 84° for A, 86 and 82° for B) and identical bond angles for the spacer oxygen atom (PhOPh angles of 122° in all cases). The overall dimensions of the minimized structures are similar

in both cases (2.6 x 1.7 nm maximum dimensions for conformer A; 2.4 x 1.3 nm maximum dimensions for conformer B). The main difference is that in form B, the two pyridine moieties not involved in the complexation are predisposed for further joining of another similar unit. In fact, conformer B can easily close to give a stable dimer (the “closed dimer” form in Fig. 1), which is shown in Fig. 8. The modelling of “closed dimer” and of conformer B was then performed independently; we did not observe any significant changes in the geometry of the intramolecularly complexed macrocycle in either monomer or dimer, as to testify that the macrocyclic structure does not have to undergo a high degree of conformational rearrangement to close to a dimeric structure.

On the other hand, it is likely that the conformer A, with two pyridine moieties pointing away from the macrocyclic structure in opposite directions, is the one involved in the formation of the nanostructured aggregates observed in solution and on surfaces.

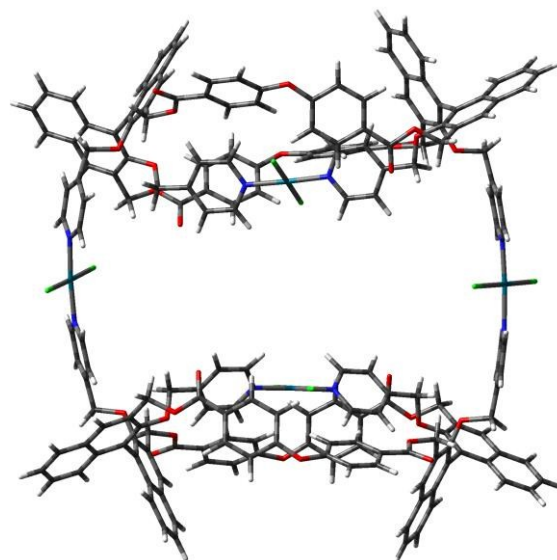


Fig. 8 Minimized conformer for the “closed dimer”.

In order to rationalize the “closed monomer” structure, which was observed in some of the conditions reported before, calculations were performed on macrocycle (*RR*)-**8** by imposing a *cis* geometry for the intramolecular Pd²⁺ complex stabilized by two pyridine moieties of facing binaphthyls. We have verified that this structure is plausible, both in terms of stability and symmetry, with the proposed structure in Fig. 1. The lowest energy conformer in this case is shown in Fig. 9.

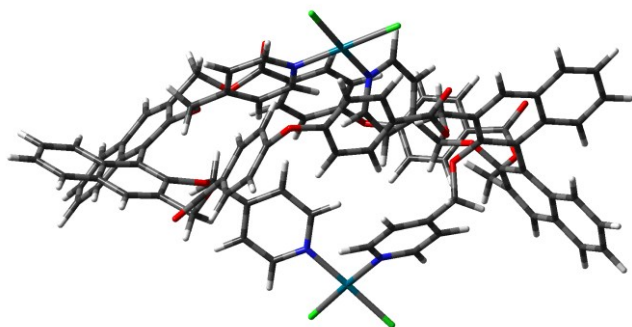


Fig. 9 Minimized conformer for the "closed monomer".

Conclusions

The realization of chiral organic nanotubes able to organize in an helical, oriented manner is of increasing scientific appeal, since properties at the nanoscale, including long range directional propagation of (chiral) information, in solution and on surfaces, can be highly rewarding. Towards this target, we have studied a new multivalent homochiral macrocycle, predisposed for assembly in 3D in which chirality is robustly expressed at the molecular level. The engineered system is capable of forming nanoscale structures with a certain level of order, both in solution and on the surfaces. We are currently working towards the design of improved macrocyclic scaffolds, to be tailored and perfected for nanoscale transport, catalysis and sensing applications.

Experimental Part

General experimental. All commercially available compounds were purchased from commercial sources and used as received. Compounds 4-dimethylaminopyridinium *p*-toluenesulfonate (DPTSA-DMAP),¹³ (*R*)-**1**,¹⁴ (*R*)-**4**^{6c} were prepared according to literature procedures. THF (Na) and CH₂Cl₂ (CaH₂) were dried before use. Analytical thin layer chromatography was performed on silica gel, chromophore loaded, commercially available plates. Flash chromatography was carried out using silica gel (pore size 60 Å, 230-400 mesh). ¹H and ¹³C NMR spectra were recorded from solutions in CDCl₃ on 200 300 MHz or 500 MHz spectrometer with the solvent residual proton signal or tetramethylsilane as a standard. The UV/Vis spectroscopic studies were recorded using commercially-available spectrophotometers. Mass spectra were recorded using an electrospray ionization instrument (ESI). Optical rotations were measured on a polarimeter in a 10 cm cell with a sodium lamp ($\lambda = 589$ nm) and are reported as follows: $[\alpha]_D^{25}$ ($c = (\text{mg/mL})^{-1}$, solvent). CD spectra were recorded at 25 °C at a scanning speed of 50 nm min⁻¹ and were background corrected. Each spectra is the instrument average of four consecutive scans.

Macrocycle (RR)-3. Compound (*R*)-**1** (150 mg, 0.401 mmol, 1 eq.) and DPTSA-DMAP (248 mg, 0.802 mmol, 2 eq.) were mixed in CH₂Cl₂ (10 mL) under N₂. A solution of diacid **2** (104 mg, 0.401 mmol, 1 eq.) in CH₂Cl₂ (10 mL) was added. After 15 min of stirring at room temperature, DICD (152 mg, 1.20 mmol, 3 eq.) was added.

The suspension became progressively clear, and the solution was stirred under N₂ overnight, after which time TLC analysis showed full conversion of compound (*R*)-**1**. The reaction mixture was quenched with H₂O (25 mL), extracted with CH₂Cl₂ (3 x 50 mL) and dried (Na₂SO₄). The crude product was purified by column chromatography (SiO₂; CH₂Cl₂/AcOEt: 100/0 to 99/1) to yield macrocycle (*RR*)-**3** (25 mg, 10%) as a white solid. $[\alpha]_D^{25} = +114$ ($c=0.0002$, CH₂Cl₂). ¹H NMR (CDCl₃, 300 MHz, 25 °C) $\delta = 8.12$ (s, 4H; binaphthyl), 8.04 (d, 8H; phenyl), 7.92 (d, 4H; binaphthyl), 7.43 (t, 4H; binaphthyl), 7.30 (d, 4H; binaphthyl), 7.19 (d, 4H; binaphthyl), 6.99 (d, 8H; phenyl), 5.62 (m, 8H; -CH₂O-), 3.33 (s, 12H; -OCH₃). ¹³C NMR (CDCl₃, 75 MHz, 25 °C) $\delta = 165.6$ (Cq), 160.2 (Cq), 155.5 (Cq-OMe), 134.5 (Cq), 132.7 (CH), 131.8 (CH), 130.2 (Cq), 129.0 (Cq), 128.1 (CH), 126.9 (CH), 125.7 (CH), 125.5 (CH), 125.0 (Cq), 124.5 (Cq), 118.6 (CH), 63.4 (CH₂), 61.4 (OMe). MS(ESI): m/z 1215.3 ($[M + Na]^+$, 100%).

Compound (R)-6. Cs₂CO₃ (794 mg, 2.44 mmol, 7 eq.) was added to a solution of compound (*R*)-**4** (200 mg, 0.35 mmol, 1 eq.) in dry DMF (8 mL). The pyridinium hydrochloride salt **5** (264 mg, 1.04 mmol, 3 eq.) was then added and the reaction mixture was stirred at room temperature overnight. The reaction mixture was then quenched with H₂O (15 mL), extracted with Et₂O (3 x 25 mL) and dried (Na₂SO₄). The crude product was purified by column chromatography (SiO₂; hexanes/AcOEt: 8/2) to yield compound (*R*)-**6** (186 mg, 71%) as a white solid. $[\alpha]_D^{25} = +65$ ($c=0.0013$, CH₂Cl₂). ¹H NMR (CDCl₃, 300 MHz, 25 °C) $\delta = 8.35$ (bs, 4H; py), 8.05 (s, 2H; binaphthyl), 7.91 (d, 2H; binaphthyl), 7.42 (t, 2H; binaphthyl), 7.25 (m, 4H; binaphthyl), 6.66 (d, 4H; py), 4.94 (s, 4H; -CH₂O-), 4.58 (dd, 4H; -CH₂O-), 1.01 (s, 18H; -C(CH₃)₃), 0.17 (s, 12H; -CH₃). ¹³C NMR (CDCl₃, 75 MHz, 25 °C) $\delta = 153.2$ (Cq), 149.0 (CH), 146.4 (Cq), 134.4 (Cq), 133.3 (Cq), 130.8 (Cq), 128.1 (CH), 127.6 (CH), 126.3 (CH), 125.4 (CH), 125.1 (CH), 124.3 (Cq), 121.0 (CH), 73.2 (CH₂), 61.1 (CH₂), 25.9 (CH₃), 18.4 (C(CH₃)₃), -5.29 (CH₃), -5.35 (CH₃). MS(ESI): m/z 779.3 ($[M + Na]^+$, 60%), 757.2 ($[M + H]^+$, 40%).

Compound (R)-7. *n*-Bu₄NF (1M in hexanes, 2 mL, 2 mmol, 6 eq.) was added to a solution of compound (*R*)-**6** (253 mg, 0.334 mmol, 1 eq.) in THF (6 mL) and H₂O (0.36 mL, 20 mmol, 60 eq.). After stirring for 15 h at room temperature, TLC analysis the full conversion of compound **6**; the reaction mixture was quenched with H₂O (15 mL), extracted with CH₂Cl₂ (1 x 20 mL) and AcOEt (2 x 20 mL) and dried (Na₂SO₄). The crude product was purified by column chromatography (SiO₂; AcOEt/*i*-PrOH/Et₃N: 85/5/10) to yield compound (*R*)-**7** as a white solid (129 mg, 73%). $[\alpha]_D^{25} = +79$ ($c=0.0016$, CH₂Cl₂). ¹H NMR (CDCl₃, 300 MHz, 25 °C) $\delta = 8.28$ (d, 4H; py), 7.98 (s, 2H; binaphthyl), 7.89 (d, 2H; binaphthyl), 7.44 (t, 2H; binaphthyl), 7.29 (m, 4H; binaphthyl), 6.64 (d, 4H; py), 4.89 (dd, 4H; -CH₂O-), 4.56 (dd, 4H; Py-CH₂O-), 2.53 (bs, 2H; -OH). ¹³C NMR (CDCl₃, 75 MHz, 25 °C) $\delta = 153.8$ (Cq), 149.0 (CH), 146.2 (Cq), 134.1 (Cq), 133.5 (Cq), 130.7 (Cq), 128.5 (CH), 128.1 (CH), 126.7 (CH), 125.4 (CH), 125.3 (CH), 124.4 (Cq), 121.0 (CH), 73.5 (CH₂), 61.4 (CH₂). MS(ESI): m/z 529.2 ($[M + H]^+$, 100%).

Macrocycle (RR)-8. Compound (*R*)-**7** (519 mg, 0.98 mmol, 1 eq.) and DPTSA-DMAP (610 mg, 1.97 mmol, 2 eq.) were dissolved in dry CH₂Cl₂ (25 mL) under N₂. A suspension of diacid **2** (254 mg,

0.98 mmol, 1 eq.) in CH₂Cl₂ (25 mL) was added. After 15 min of stirring at room temperature, DICD (372 mg, 2.95 mmol, 3 eq.) was added. The suspension became progressively clear, and the solution was stirred under N₂ overnight, after which time TLC analysis showed full conversion of compound (R)-1. The reaction mixture was quenched with H₂O (25 mL), extracted with CH₂Cl₂ (3 x 50 mL) and dried (Na₂SO₄). The crude product was purified by column chromatography (SiO₂; AcOEt/*i*-PrOH/Et₃N: 85/5/10) to yield (RR)-8a (32 mg, 8%) as a white solid. $[\alpha]_D^{25} = +20$ (c=0.021, CH₂Cl₂). ¹H NMR (CDCl₃, 300 MHz, 25 °C) δ = 8.12-7.92 (m, 24H; py, phenyl and binaphthyl), 7.47 (t, 4H; binaphthyl), 7.35 (t, 4H; binaphthyl), 7.27 (d, 4H; binaphthyl), 6.96 (d, 8H; phenyl), 6.51 (bs, 8H; Py), 5.55 (dd, 8H; -CH₂O-), 4.56 (dd, 8H; -CH₂O-). ¹³C NMR (CDCl₃, 75 MHz, 25 °C) δ = 165.5 (Cq), 160.2 (Cq), 154.5 (Cq), 149.0 (Cq), 145.5 (Cq), 134.2 (Cq), 132.5 (CH), 131.6 x 2 (CH), 130.4 (Cq), 129.0 (Cq), 128.4 (CH), 127.5 (CH), 125.6 (CH), 125.4 (CH), 125.1 (Cq), 118.7 x 2 (CH), 73.8 (CH₂), 63.3 (CH₂). MS(ESI): *m/z* 1524.5 ([M + Na]⁺, 100%).

Procedure for NMR, UV and CD titrations. The titration experiments were conducted as follows: to a stock solution of macrocycles or control compounds (solution A) were added several aliquots of the Pd²⁺ salt (solution B). Solution B is formed by the Pd²⁺ salt (at higher concentration) dissolved in solution A, in order to maintain one species always at the same, constant concentration.

Procedure for AFM studies. Samples related to Fig. 5 and 6 were prepared as follows: a solution of macrocycle (RR)-8 (0.5 mL, 10⁻⁴ M in CH₂Cl₂) and a solution of C₆₀ (0.5 mL, 10⁻⁴ M in CHCl₃) were mixed and heated at 35 °C for 40 min. Then, a solution of Pd(MeCN)₂Cl₂ (0.5 mL, 2x10⁻⁴ M in CH₂Cl₂) was added. The following day, this solution was diluted 10x and 100x with CHCl₃ to give the following concentrations: (RR)-8/Pd(MeCN)₂Cl₂/C₆₀ 0.33x10⁻⁶ M/0.66x10⁻⁶ M/0.33x10⁻⁶ M. A single drop of the solutions was added on freshly cleaved surface of HOPG to realize the sample. Experiments were realized after total evaporation of the solvent. TM-AFM measurements on the Au substrates were carried out on air at 298 K by using a Nanoscope V (model MMAFMLN, Digital Instrument Metrology Group). The tips used in all measurements were antimony-doped silicon cantilevers (*T* = 3.5–4.5 μ m, *L* = 115–135 μ m, *f_o* = 271–305 kHz, *k* = 20–80 N m⁻¹, Bruker) at a resonant frequency of ca. 280 kHz. The collected images were then analyzed with WsxM 5.0 software (Nanotec Electronica S. L.) to acquire the cross-sectional values and profiles of processed images.

Acknowledgements

Support from the University of Pavia, MIUR (Programs of National Relevant Interest PRIN grants 2004-033354 and 2009-A5Y3N9), the CINECA Supercomputer Center (ISCRA NANOCHIR project HP10CKIGGH), and, in part, from CARIPLO Foundation (2007–2009) and INSTM-Regione Lombardia (2010–2012 and 2013–2015) is gratefully acknowledged. D.B. gratefully acknowledges the EU through the ERC Starting Grant “COLORLANDS” project, the FRS-FNRS (FRFC contract n° 2.4.550.09), the Science Policy Office

of the Belgian Federal Government (BELSPO-IAP 7/05 project), the “TINTIN” ARC project (09/14-023). D.P. wishes to thank Prof. Linda Shimizu and Dr. Kinkini Roy at the University of South Carolina, USA, for performing the DOSY experiments.

Notes and references

^a Department of Chemistry, University of Pavia, Viale Taramelli, 10 - 27100 - Pavia - Italy. E-mail: dario.pasini@unipv.it. Homepage: www.unipv.it/labt

^b Department of Chemistry and Namur Research College (NARC), University of Namur (UNamur), Rue de Bruxelles 61, Namur, 5000, Belgium.

^c Department of Chemical and Pharmaceutical Sciences and INSTM UdR Trieste, University of Trieste, Piazzale Europa 1, Trieste, 34127, Italy.

^d Department of Industrial Chemistry “Toso Montanari”, School of Science, University of Bologna, V. Risorgimento 4, 40136, Bologna, Italy.

^e INSTM Research Unit, University of Pavia, Italy.

† Electronic Supplementary Information (ESI) available: additional UV, CD and NMR spectra, and copies of NMR and mass spectra for all newly synthesized compounds. See DOI: 10.1039/b000000x/

- M. R. Ghadiri, J. R. Granja and L. K. Buehler, *Nature* 1994, **369**, 301–304.
 - D. T. Bong, T. D. Clark, J. R. Granja and M. R. Ghadiri, *Angew. Chem. Int. Ed.* 2001, **40**, 988–1011.
 - D. Pasini and M. Ricci, *Curr. Org. Synth.* 2007, **4**, 59–80.
 - R. J. Brea, C. Reiriz and J. R. Granja, *Chem. Soc. Rev.* 2010, **39**, 1448–1456.
 - S. Leclair, P. Baillargeon, R. Skouta, D. Gauthier, Y. Zhao and Y. L. Dory, *Angew. Chem. Int. Ed.* 2004, **43**, 349–353.
 - G. Dan Pantos, P. Pengo and J. K. M. Sanders, *Angew. Chem. Int. Ed.* 2007, **46**, 194–197.
 - Y. Baudry, G. Bollot, V. Gorteau, S. Litvinchuk, J. Mareda, M. Nishihara, D. Pasini, F. Perret, D. Ronan, N. Sakai, M. R. Shah, A. Som, N. Sorde, P. Talukdar, D.-H. Tran and S. Matile, *Adv. Funct. Mat.* 2006, **16**, 169–179.
 - K. Sakaguchi, T. Kamimura, H. Uno, S. Mori, S. Ozako, H. Nobukuni, M. Ishida and F. Tani, *J. Org. Chem.* 2014, **79**, 2980–2992.
- C. Grave and A. D. Schlüter, *Eur. J. Org. Chem.* 2002, 3075–3098.
 - Y. Yamaguchi and Z.-I. Yoshida, *Chem. Eur. J.* 2003, **9**, 5430–5440.
 - S. Höger, *Chem. Eur. J.* 2004, **10**, 1320–1329.
 - D. Zhao and J. S. Moore, *Chem. Commun.* 2003, 807–818.
 - Y. Xu, M. D. Smith, M. F. Geer, P. J. Pellechia, J. C. Brown, A. C. Wibowo and L. S. Shimizu, *J. Am. Chem. Soc.* 2010, **132**, 5334–5335.
 - L. S. Shimizu, A. D. Hughes, M. D. Smith, M. J. Davis, B. P. Zhang, H.-C. zur Loye and K. D. Shimizu, *J. Am. Chem. Soc.* 2003, **125**, 14972–14973.
 - A. J. Hesel, A. L. Brown, K. Yamato, W. Feng, L. Yuan, A. J. Clements, S. V. Harding, G. Szabo, Z. Shao and B. Gong, *J. Am. Chem. Soc.* 2008, **130**, 15784–15785.
 - B. Gong and Z. Shao, *Acc. Chem. Res.* 2013, **46**, 2856–2866.
 - L. S. Shimizu, S. R. Salpage and A. A. Korous, *Acc. Chem. Res.* 2014, **47**, 2116–2127.
 - A. Ikeda and S. Shinkai, *J. Chem. Soc., Chem. Commun.* 1994, 2375–2376.
 - G. Gattuso, S. Menzer, S. A. Nepogodiev, J. F. Stoddart and D. J. Williams, *Angew. Chem. Int. Ed. Engl.* 1997, **36**, 1451–1454.
 - B. H. Hong, S. C. Bae, C.-W. Lee, S. Jeong and K. S. Kim, *Science* 2001, **294**, 348–351.
 - V. G. Organo, A. V. Leontiev, V. Sgarlata, H. V. R. Dias and D. R. Rudkevich, *Angew. Chem. Int. Ed.* 2005, **44**, 3043–3047.
 - M. Boccalon, E. Iengo and P. Tecilla, *J. Am. Chem. Soc.* 2012, **134**, 20310–20313.
 - P. J. Stang, D. H. Cao, S. Saito and A. M. Arif, *J. Am. Chem. Soc.* 1995, **117**, 6273–6283.

- 3 a) L. Fischer, M. Decossas, J. P. Briand, C. Didierjean and G. Guichard, *Angew. Chem. Int. Ed.* 2009, **48**, 1625–1628. b) A. Hennig, L. Fischer, G. Guichard and S. Matile, *J. Am. Chem. Soc.* 2009, **131**, 16889–16895.
- 4 a) J. J. L. M. Cornelissen, A. E. Rowan, R. J. M. Nolte and N. A. J. M. Sommerdijk, *Chem. Rev.* 2001, **101**, 4039–4070. b) F. J. M. Hoeben, P. Jonkheijm, E. W. Meijer and A. P. H. J. Schenning, *Chem. Rev.* 2005, **105**, 1491–1546. c) D. K. Smith, *Chem. Soc. Rev.* 2009, **38**, 684–694. d) J. Kumaki, S. Sakurai and E. Yashima, *Chem. Soc. Rev.*, 2009, **38**, 737–746. e) J. Clayden, *Chem. Soc. Rev.*, 2009, **38**, 817–829. f) P. Jonkheijm, P. van der Schoot, A. P. H. J. Schenning and E. W. Meijer, *Science* 2006; **313**, 80–83. g) M.-Q. Zhao, Q. Zhang, G.-L. Tian and F. Wei, *Nanoscale* 2014, **6**, 9339–9354.
- 5 a) L. Pu, *Chem. Rev.* 1998, **98**, 2405–2494. b) Y. Chen, S. Yekta and A. K. Yudin, *Chem. Rev.* 2003, **103**, 3155–3211. c) P. Kocovsky, S. Vyskocyl and M. Smrcina, *Chem. Rev.* 2003, **103**, 3213–3245. d) J. M. Brunel, *Chem. Rev.* 2005, **105**, 857–898. e) A. Shockravi, A. Javadi and E. Abouzari-Lotf, *RSC Advances* 2013, **3**, 6717–6746. f) M. Caricato, A. K. Sharma, C. Coluccini and D. Pasini, *Nanoscale*, 2014, **6**, 7165–7174.
- 6 a) A. Bencini, C. Coluccini, A. Garau, C. Giorgi, V. Lippolis, L. Messori, D. Pasini and S. Puccioni, *Chem. Commun.* 2012, **48**, 10428–10430. b) C. Coluccini, D. Dondi, M. Caricato, A. Taglietti, M. Boiocchi and D. Pasini, *Org. Biomol. Chem.* 2010, **8**, 1640–1649. c) M. Caricato, N. J. Leza, K. Roy, D. Dondi, G. Gattuso, L. S. Shimizu, D. A. Vander Griend and D. Pasini, *Eur. J. Org. Chem.* 2013, 6078–6083. d) M. Caricato, A. Olmo, C. Gargiulli, G. Gattuso and D. Pasini, *Tetrahedron*, 2012, **68**, 7861–7866. e) M. Caricato, C. Coluccini, D. Dondi, D. A. VanderGriend and D. Pasini, *Org. Biomol. Chem.*, 2010, **8**, 3272–3280. f) A. Moletti, C. Coluccini, D. Pasini and A. Taglietti, *Dalton Trans.*, 2007, **16**, 1588–1592. g) C. Coluccini, A. Mazzanti and D. Pasini, *Org. Biomol. Chem.*, 2010, **8**, 1807–1815. h) C. Coluccini, A. Castelluccio and D. Pasini, *J. Org. Chem.* 2008, **73**, 4237–4240. S. i) S. Colombo, C. Coluccini, M. Caricato, C. Gargiulli, G. Gattuso and D. Pasini, *Tetrahedron* 2010, **66**, 4206–4211. j) A. Pacini, M. Caricato, S. Ferrari, D. Capsoni, A. Martínez de Ilduya, S. Muñoz-Guerra and D. Pasini, *J. Polym. Sci. A. Polym. Chem.* 2012, **50**, 4790–4799. m) M. Caricato, S. Díez González, I. Arandia Ariño and D. Pasini, *Beilstein J. Org. Chem.* 2014, **10**, 1308–1316. n) M. Caricato, N. J. Leza, C. Gargiulli, G. Gattuso, D. Dondi and D. Pasini, *Beilstein J. Org. Chem.* 2012, **8**, 967–976. o) M. Agnes, A. Sorrenti, D. Pasini, K. Wurst and D. B. Amabilino, *CrystEngComm* 2014, **16**, 10131–10138. p) M. Crespo Alonso, M. Arca, F. Isaia, R. Lai, V. Lippolis, S. K. Callear, M. Caricato, D. Pasini, S. J. Coles and M. C. Aragoni, *CrystEngComm* 2014, **16**, 8582–8590.
- 7 For examples of pyridine moieties forming *trans* PdCl₂ coordination complexes, see: a) Z. Qin, M. C. Jennings and R. J. Puddephatt, *Inorg. Chem.* 2001, **40**, 6220–6228. b) D. Y. K. Lee, M. H. W. Lam and W.-Y. Wong, *New J. Chem.* 2002, **26**, 330–335. c) R. E. Marsh, *Acta Crystallogr., Sect. B: Struct. Sci.* 2005, **61**, 359. d) J. Rajput, J. R. Moss, A. T. Hutton, D. T. Hendricks, C. E. Arendse and C. Imrie, *J. Organomet. Chem.* 2004, **689**, 1553–1568. e) Y. M. Na, T. H. Noh, I. S. Chun, Y.-A. Lee, J. Hong and O.-S. Jung, *Inorg. Chem.* 2008, **47**, 1391–1396. f) A. Bacchi, M. Carcelli, T. Chiodo and F. Mezzadri, *CrystEngComm* 2008, **10**, 1916–1927. g) T. J. Burchell, D. J. Eisler and R. J. Puddephatt, *Dalton Trans.* 2005, 268–272. h) R. Wang, L. Xu, J. Ji, Q. Shi, Y. Li, Z. Zhou, M. Hong and A.S.C. Chan, *Eur. J. Inorg. Chem.* 2005, 751–758. i) H. M. Lee and C.-Y. Liao, *Acta Crystallogr. Sect. E-Struct. Rep. Online* 2008, **64**, M1447–U932. l) C. Coluccini, P. Metrangolo, M. Parachini, D. Pasini, G. Resnati and P. Righetti, *J. Polym. Sci. A. Polym. Chem.* 2008, **46**, 5202–5213. m) L. Pirondini, D. Bonifazi, E. Menozzi, E. Wegelius, K. Rissanen, C. Massera and E. Dalcanale, *Eur. J. Org. Chem.* 2001, 2311–2320. n) Y. S. Chong, M. D. Smith and K. D. Shimizu, *J. Am. Chem. Soc.* 2001, **123**, 7463–7464. o) M. T. Stone and J. S. Moore, *J. Am. Chem. Soc.* 2005, **127**, 5928–5935. p) G. Giachi, M. Frediani, W. Oberhauser and E. Passaglia, *J. Polym. Sci. Pol. Chem.* 2011, **49**, 4708–4713.
- 8 For the use of Pd²⁺ sources in the construction of nanoscale architectures, see: a) S. Hiraoka, Y. Sakata and M. Shionoya, *J. Am. Chem. Soc.* 2008, **130**, 10058–10059. b) B. A. Blight, J. A. Wisner and M. C. Jennings, *Angew. Chem. Int. Ed.* 2007, **46**, 2835–2838. c) C. Gütz, R. Hovorka, G. Schnakenburg and A. Lützen, *Chem. Eur. J.* 2013, **19**, 10890–10894. d) B. J. Holliday and C. A. Mirkin, *Angew. Chem, Int. Ed.* 2001, **40**, 2022–2043. e) N. L. S. Yue, D. J. Eisler, M. C. Jennings and R. J. Puddephatt, *Inorg. Chem.* 2004, **43**, 7671–7681. f) K. Suzuki, K. Takao, S. Sato and M. Fujita, *M. J. Am. Chem. Soc.* 2010, **132**, 2544–2546. g) S. Leininger, B. Olenyuk and P. J. Stang, *Chem Rev.* 2000, **100**, 853–907. h) B. Olenyuk and P. J. Stang, *Acc. Chem. Res.* 1997, **30**, 502–518.
- 9 A. Macchioni, G. Ciancaleoni, C. Zuccaccia and D. Zuccaccia, *Chem. Soc. Rev.* 2008, **37**, 479–489.
- 10 A. Ulubelen, G. Topcu and N. Tan, *Phytochemistry* 1995, **40**, 1473–1475.
- 11 4-Alkylpyridines feature absorption signals centered at 254 nm, with low molar absorptivities (ca. 2500): G. Viscardi, P. Savarino, P. Quagliotto, E. Barni and M. Botta, *J. Heterocyclic Chem.* 1996, **33**, 1195–1200.
- 12 a) A. Llanes-Pallas, K. Yoosaf, H. Traboulsi, J. Mohanraj, T. Seldrum, J. Dumont, A. Minoia, R. Lazzaroni, N. Armadori, and D. Bonifazi, *J. Am. Chem. Soc.* 2011, **133**, 15412–15424. b) J. Kumaki, E. Yashima, G. Bollot, J. Mareda, S. Litvinchuk and S. Matile, *Angew. Chem. Int. Ed.* 2005, **44**, 6154–6157.
- 13 J. S. Moore and S. I. Stupp, *Macromolecules* 1990, **23**, 65–70.
- 14 H. T. Stock and R. M. Kellogg, *J. Org. Chem.* 1996, **61**, 3093–3105.