

RSC Advances



This is an *Accepted Manuscript*, which has been through the Royal Society of Chemistry peer review process and has been accepted for publication.

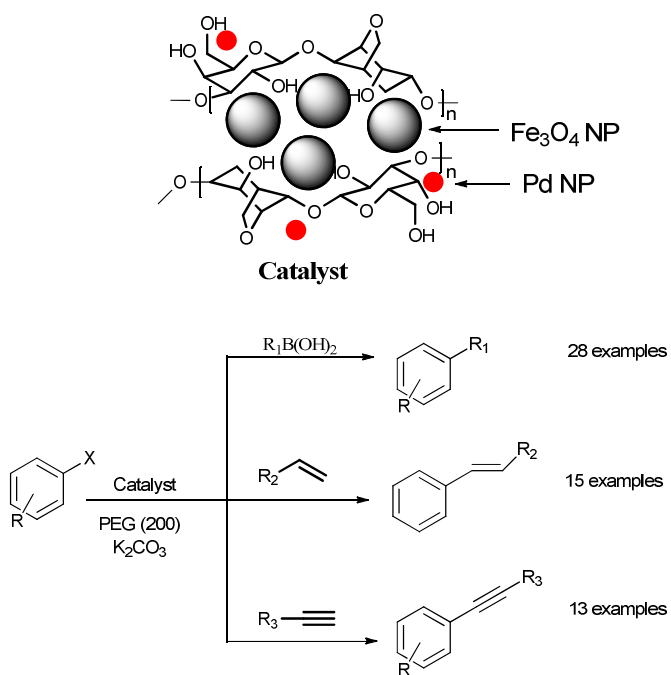
Accepted Manuscripts are published online shortly after acceptance, before technical editing, formatting and proof reading. Using this free service, authors can make their results available to the community, in citable form, before we publish the edited article. This *Accepted Manuscript* will be replaced by the edited, formatted and paginated article as soon as this is available.

You can find more information about *Accepted Manuscripts* in the [Information for Authors](#).

Please note that technical editing may introduce minor changes to the text and/or graphics, which may alter content. The journal's standard [Terms & Conditions](#) and the [Ethical guidelines](#) still apply. In no event shall the Royal Society of Chemistry be held responsible for any errors or omissions in this *Accepted Manuscript* or any consequences arising from the use of any information it contains.

Table of contents

Palladium nanoparticles supported on agarose functionalized Fe_3O_4 , catalyzed C-C bond formation reactions.



ARTICLE

Palladium nanoparticles supported on agarose functionalized magnetic nanoparticles of Fe₃O₄ as a recyclable catalyst for C-C bond formation via Suzuki-Miyaura, Heck-Mizoroki and Sonogashira-Hagihara coupling reactions†

Cite this: DOI: 10.1039/x0xx00000x

Received 00th January 2012,
Accepted 00th January 2012

DOI: 10.1039/x0xx00000x

www.rsc.org/

Habib Firouzabadi*^a, Nasser Iranpoor*^a, Mohammad Gholinejad^b, Samira Akbari^a, Nedda Jeddi^b

In this paper, palladium nanoparticles supported on agarose functionalized magnetic nanoparticles of Fe₃O₄ has been introduced. The new material was characterized by EDX, TEM, TGA, FT-IR, VSM, AAS, and solid Uv-visible analysis. This magnetic material has been successfully applied as a highly efficient, magnetically recoverable and air-stable catalyst for the Suzuki-Miyaura, Heck-Mizoroki and Sonogashira-Hagihara coupling reactions. Using this material as a catalyst, a wide range of substrates was employed for carbon-carbon bond formation in wet PEG200.

Introduction

Transition metals playing an important role in organic reactions as catalysts.¹ Among different types of transition metal catalysts, palladium has gained significant catalytic function due to important carbon-carbon and carbon-hetero atom bond formation reactions. Palladium catalyzed Suzuki-Miyaura,² Heck-Mizoroki³ and Sonogashira-Hagihara⁴ are important and powerful strategies for the formation of carbon-carbon bonds. In recent years, both homogeneous and heterogeneous palladium catalysts have been employed for the above mentioned coupling reactions.⁵ However, since palladium metal and its compounds are expensive, homogeneous palladium catalysis suffers from the problem associated to its separation from the reaction mixture. In addition, using homogeneous palladium catalysts might result contamination of the coupling products with palladium species, especially when they are used for biologically active natural products and pharmaceuticals. Using heterogeneous catalysts can overcome the mentioned troubles. However, despite the simple handling of heterogeneous catalysts, they are typically less effective than their homogeneous counterparts. Moreover, many of the heterogeneous catalysts encounter difficulties for their separation from the reaction mixture by filtration and centrifugation. This problem could be solved by preparation of magnetic catalysts which can be separated by an external magnet from the reaction system.⁶ In recent years, extensive attention has been paid to the use of Fe₃O₄ nanoparticles as a magnetically recoverable solid supports for transition metals

such as palladium⁷, copper⁸, nickel⁹, and gold¹⁰. The advantages of magnetic nanocatalytic systems are their easy separation by an external magnet, high reactivity, and enormous surface area to volume ratio and morphology of catalysts. In addition, the magnetic property of catalysts causes their flocculation or dispersion being reversibly controlled by a static magnetic field. Consequently, magnetic nanoparticles can be well-dispersed in the reaction medium for their reuse in the absence of an external magnetic field.

Nowadays, most efforts on development of magnetic nanoparticles supported catalysts are focused on the synthesis of size-controlled and monodispersed magnetic nanoparticles (MNPs)¹¹ as well as in their surface stabilization by simple organic compounds, such as silanes,¹² carboxylic acids,¹³ and phosphonic acids.¹⁴ This surface modification is often performed through a process that involves the exchange of stabilizing ligands or the coating of the magnetic core with an organic/inorganic polymer shell.¹⁵ Also, apart from the surface modification of MNPs, several researchers have combined magnetic nanoparticles with activated carbon fiber,¹⁶ carbon nanotubes¹⁷, and graphene.¹⁸

Very recently we have introduced agarose as a cheap and bioorganic ligand and support for palladium nanoparticles and its application in different carbon-carbon bond formation reactions.¹⁹ Also, preparation of magnetically recoverable heteropolyacids/chitosan/Fe₃O₄ (HSiW-CS-Fe₃O₄) and its successful application in acetalization reaction of benzaldehyde with ethylene glycol has been reported.²⁰ Now in

this report, we present a newly developed material which is composed of magnetic Fe_3O_4 nanoparticles modified with agarose supported palladium nanoparticles which is presented as $\text{Pd@agarose-Fe}_3\text{O}_4$ through the whole text of this article. Characterization of this material was performed by SEM, EDX, TEM, TGA, FT-IR, VSM, AAS, and solid UV-visible spectrum. This new material has been applied as a magnetically separable and recyclable catalyst for C-C bond formation with success *via* Suzuki-Miyaura, Heck-Mizoroki and Sonogashira-Hagihara reactions.

Results and discussion

Fe_3O_4 nanoparticles were prepared without using any capping agent or surfactant *via* conventional co-precipitation of iron (II) chloride and iron (III) chloride according to the reported procedure.²¹ After sonication, Fe_3O_4 nanoparticles were treated with agarose in the presence of $\text{Pd}(\text{OAc})_2$ and citric acid as a reducing agent in aqueous media. After drying the resulting material, the initial investigation was focused on the characterization of the resulting new solid material.

Based on the atomic absorption spectroscopy (AAS) analysis the amounts of Pd in $\text{Pd@agarose-Fe}_3\text{O}_4$ was found to be (0.0075 mmolPd/g).

Solid UV-Vis spectrum of the obtained material shows complete conversion of Pd(II) to Pd(0) by the absence of the peak at 420 nm which belongs to Pd(II) species (Figure 1). In addition, increase of the absorption in the visible region for the catalyst, indicate that the Pd(0) nanoparticles are formed.²²

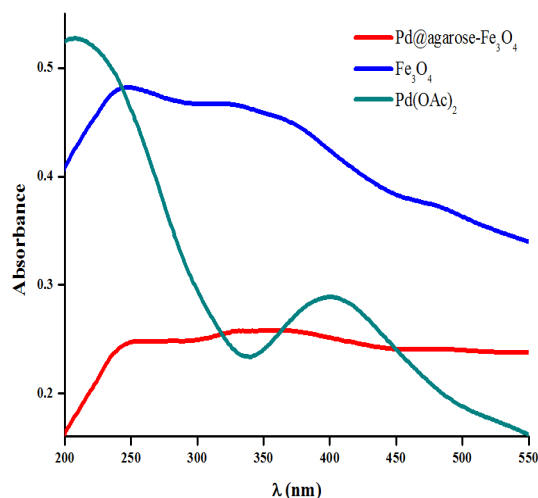


Figure 1. , Solid UV-Vis spectrum of $\text{Pd}(\text{OAc})_2$, Fe_3O_4 and $\text{Pd@agarose-Fe}_3\text{O}_4$

FT-IR spectrum of $\text{Pd@agarose-Fe}_3\text{O}_4$ did not show carbonyl group absorption band which confirms that the $-\text{OAc}$ anion has been removed after the process of reduction of Pd(II) to Pd(0). The characteristic absorption bands of Fe_3O_4 nanoparticles at 630, 578 and 442 cm^{-1} are attributed to the presence of $\text{Fe}-\text{O}$ bonds.²³ These results certainly approve the existence of magnetic Fe_3O_4 nanoparticles in the new solid material (see supporting information).

In order to get information about the size of metal particles distributed in agarose mass, the TEM image of the material (Figure 2) was studied. The image shows that the particles are

mostly spherical and have an average diameter of about 10-15 nm. However, the amount of palladium NP on the surface of the of the material is very low and therefore, differentiation of Pd NP from Fe_3O_4 NP is not so easy.

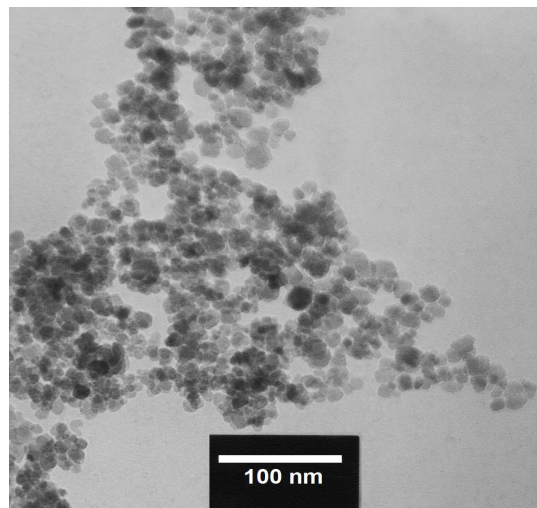


Figure 2: TEM image of $\text{Pd@agarose-Fe}_3\text{O}_4$ with the average spherical particle size 10-15 nm

The EDX study of $\text{Pd@agarose-Fe}_3\text{O}_4$ (see supporting information) confirms the presence of palladium and iron nanoparticles in the structure of the material.

The thermo-gravimetric analysis (TGA) of $\text{Pd@agarose-Fe}_3\text{O}_4$ shows that the prepared composite have high thermal stability and negligible agarose leaching up to 200 °C (Figure 3).

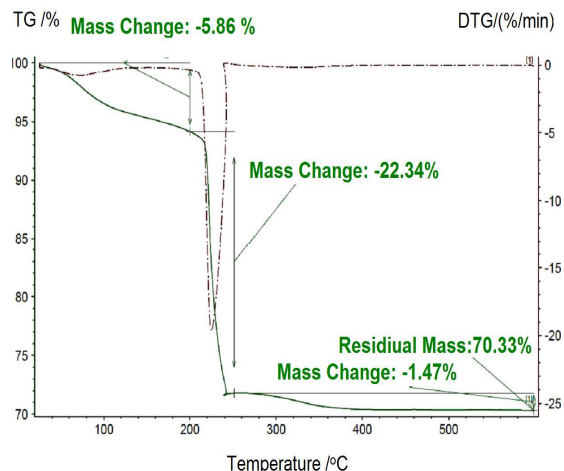


Figure 3: Thermo-gravimetric diagram of $\text{Pd@agarose-Fe}_3\text{O}_4$

The superparamagnetic²⁴ behavior of $\text{Pd@agarose-Fe}_3\text{O}_4$ was confirmed using magnetization curves of Fe_3O_4 NPs and $\text{Pd@agarose-Fe}_3\text{O}_4$ at room temperature (Figure 4). The two samples show zero coercivity and remanence on the magnetization loop. The absence of hysteresis loop shows superparamagnetic property and the ability of the material to be separated from the reaction mixture by an external magnet

(Figure 5). In addition, the decrease of magnetization value of the composite (65.8 emug⁻¹) in comparison with Fe₃O₄ NP (48.7 emug⁻¹) confirms that the surface of Fe₃O₄ NP is covered by the attachment of agarose molecules through their bond formation *via* their hydroxyl functional groups.

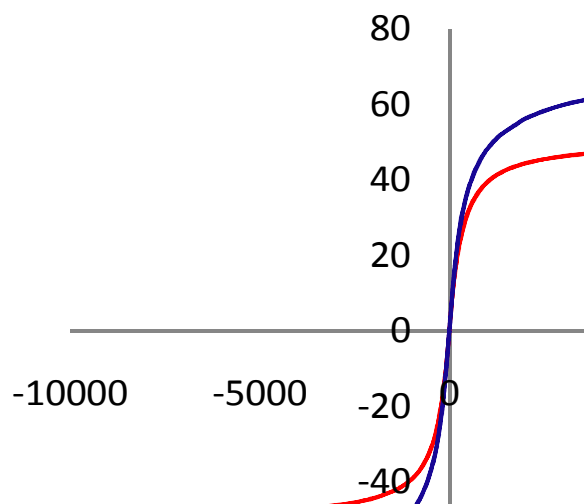
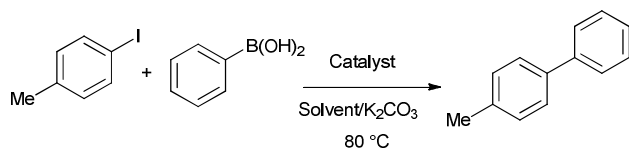


Figure 4: The magnetization curves of nanoparticles of Fe₃O₄ NP and Pd@agarose-Fe₃O₄

After characterization of Pd@agarose-Fe₃O₄, we have investigated the catalytic properties of Pd@agarose-Fe₃O₄ for C-C bond formation *via* a Suzuki-Miyaura coupling reaction. For this purpose, reaction of 4-iodotoluene (1.0 mmol) with phenylboronic acid (1.5 mmol) as a model reaction in the presence of K₂CO₃ (1.5 mmol) and 20 mg of Pd@agarose-Fe₃O₄ (this optimized amount of the catalyst has been found through a study as shown in Table 3 which contains 1.5 × 10⁻⁴ mmol of Pd as determined by ICP analysis) in different solvents at 80 °C was studied (Table 1). The results of this study showed that wet PEG 200 was the most suitable solvent for this reaction.

Table 1. Screening of different solvents for the reaction of 4-iodotoluene with phenylboronic acid catalyzed by Pd@agarose-Fe₃O₄.

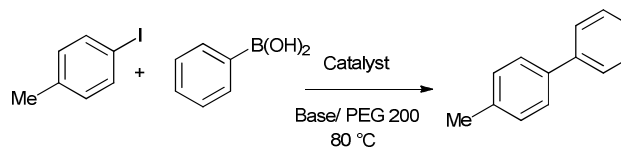


Entry	solvent	Base	Yield
1	Toluene	0.5	N.R
2	Water	0.5	52
3	EtOH	0.5	60

4	PEG 200	0.5	94
5	DMF	0.5	40

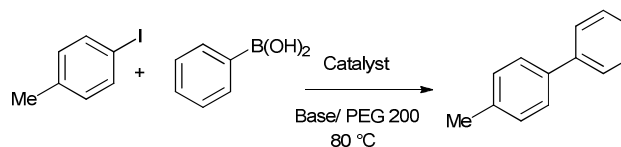
The effect of different bases was also studied upon the reaction of 4-iodotoluene with phenylboronic acid. Among the studied bases, NaOH and K₂CO₃ were found to be suitable, however, K₂CO₃ was selected as the most efficient base for the reaction as shown in Table 2.

Table 2. Screening of different bases for the reaction of iodotoluene with phenylboronic acid in the presence of Pd@agarose-Fe₃O₄



Entry	Solvent	Base	Yield(%)
1	NaOH	0.5	90
2	K ₂ CO ₃	0.5	94
3	Morpholine	0.5	20
4	Et ₃ N	0.5	45
5	None	0.5	17

Table 3. Effect of different amounts of Pd@agarose-Fe₃O₄ for the reaction of 4-iodotoluene with phenylboronic acid



























































Entry	Solvent	Base	Yield(%)
1	0	0.05	N.R
2	0.005	0.05	50
3	0.01	0.05	80
4	0.02	0.05	94

Then the optimized reaction condition was applied to the reaction of varieties of aryl halides with arylboronic acids. Aryl iodides were reacted efficiently with phenylboronic acid, 4-fluorophenylboronic acid and pinacol vinylboronate. The reactions proceeded smoothly to produce the desired biphenyl products in excellent yields. Also, the reaction of aryl bromides under the optimized conditions were performed well to give the desired biphenyl products in high to excellent yields. However, under the optimized reaction conditions, the reactions of aryl chlorides proceeded sluggishly. Therefore, the temperature of the reaction was raised to 130 °C in which the aryl chlorides were reacted more efficiently and afforded the corresponding biphenyl products in 67-89% isolated yields (Table 4).

Table 4. Reaction of different aryl halides (I, Br, Cl) with organoborons catalyzed by Pd@agarose-Fe₃O₄

$$\text{Ar-X} + \text{RBZ} \xrightarrow[\text{K}_2\text{CO}_3 (1.5 \text{ mmol}), \text{PEG 200 (2 mL)}, 80-130 \text{ }^\circ\text{C}]{\text{catalyst (20mg), } 1.57 \times 10^{-4} \text{ mmol of Pd}} \text{Ar-R}$$

Entry	Aryl Halide	RBZ	Time (h)	Product	Isolated Yield%
1		PhB(OH) ₂	0.5		97
2		PhB(OH) ₂	0.5		95
3		PhB(OH) ₂	0.5		94
4		PhB(OH) ₂	0.5		90
5		PhB(OH) ₂	0.5		90
6		PhB(OH) ₂	6		93
7		PhB(OH) ₂	4		92
8		PhB(OH) ₂	3.5		87
9		PhB(OH) ₂	0.5		93
10		PhB(OH) ₂	0.75		92
11		PhB(OH) ₂	0.5		90
12		Pinacol vinylboronate	2		85
13		Pinacol vinylboronate	2		80
14		Pinacol vinylboronate	1.5		90
15		Pinacol vinylboronate	6		80
16		4-Fluorophenylboronic acid	0.5		95
17		4-Fluorophenylboronic acid	0.5		93




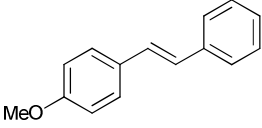

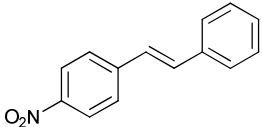



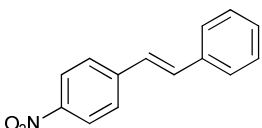

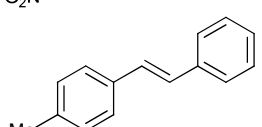

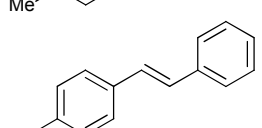







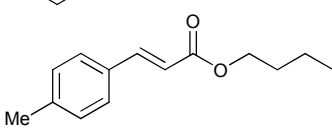

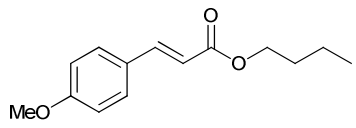
18		4-Fluorophenylboronic acid	0.5		93
19		4-Fluorophenylboronic acid	0.5		92
20		4-Fluorophenylboronic acid	6.5		90
21		PhB(OH) ₂	24		73
22		PhB(OH) ₂	24		86
23		PhB(OH) ₂	24		75
24		PhB(OH) ₂	24		89
25		4-Fluorophenylboronic acid	24		70
26		4-Fluorophenylboronic acid	24		72
27		Pinacol vinylboronate	24		67
28		Pinacol vinylboronate	24		70







Along the expansion of the application of the catalyst, Heck-Mizoroki reaction was also studied under similar optimized reaction conditions as mentioned above. For this purpose, reaction of a variety of aryl halides with styrene, butyl acrylate and 1-octene in the presence of 20 mg of the catalyst and K₂CO₃ in PEG200 at 80 °C were studied. However, the reaction of aryl bromides and chlorides with alkenes were found to be

inefficient at 80 °C. Therefore, the reaction temperature was increased to 120 °C for arylbromides and to 130 °C for aryl chlorides. The results show that the catalyst was suitable and efficient for Heck-Mizoroki reaction using structurally different aryl halides and alkenes to give the desired alkene compounds in good to excellent isolated yields (Table 5).

Table 5: Reaction of different aryl halides (I, Br, Cl) with styrene, butyl acrylate and 1-octene in the presence of the catalyst

$$\text{ArX} + \text{R}-\text{CH}=\text{CH}_2 \xrightarrow[\text{K}_2\text{CO}_3 (1.5 \text{ mmol}), \text{PEG 200 (2 mL)}, 80-130 \text{ }^\circ\text{C}]{\text{catalyst (20mg), } 1.57 \times 10^{-4} \text{ mmol of Pd}} \text{Ar}-\text{CH}=\text{CH}-\text{R}$$

Entry	ArX	Alkene	T (°C)	Time (h)	Product	Yield%
1		Styrene	80	1(1) ^a		94(89)
2		Styrene	80	4		92
3		Styrene	80	1		94
4		Styrene	80	18		67
5		Styrene	120	20		20
6		Styrene	120	14		93
7		Styrene	120	16		87
8		Styrene	120	20		85
9		Styrene	130	24		87
10		butyl acrylate	80	1		94
11		butyl acrylate	80	1		94
12		butyl acrylate	80	1		92

13		butyl acrylate	120	14		60
14		butyl acrylate	120	10		88
15		butyl acrylate	130	24		76

^a In parenthesis, time and the isolated yield of the large-scale reaction is indicated using 10 mmol of iodobenzene and 20 mmol of styrene.

^b Yield of *cis* and *trans* product

The application of the catalyst was also extended to C-C bond formation *via* Sonogashira-Hagihara reaction by studying the reaction of structurally different aryl iodides, bromides and chlorides with phenylacetylene. First, optimization of the reaction conditions with respect to solvents, bases, temperature, and the amounts of the catalyst for the reaction of 4-iodotoluene (1.0 mmol) with phenylacetylene (1.5 mmol) using 10 mg of the catalyst in the presence of K_2CO_3 (2 mmol) in different solvents at 100 °C was thoroughly studied. The results showed that PEG 200 and K_2CO_3 were the most suitable solvent and the base for the reaction. Under these conditions, the yield of the product was found to be only 60%, even though the reaction was completed with respect to the

reactants in the appropriate reaction time (Table 6, Entry 1). This observation directed us to study the effect of the amounts of the catalyst upon the reaction. By increasing the amount of the catalyst from 10 to 30 mg, an increase in the by-product formation was observed (Table 7, Entry 10, 11). Thus the amount of the catalyst was kept at 10 mg. Then the effect of increasing the temperature was investigated. The results showed that increasing the temperature from 100 °C to 120 °C was accompanied with the decrease of the reaction time but the amount of unwanted products were increased (Table 6, Entry 13, 14). Finally, we decided to increase the amount of K_2CO_3 from 2 mmol to 3 mmol in the presence of 10 mg of the catalyst in wet PEG 200. By this change, the desired product was obtained in 94% isolated yield (entry 17, Table 6).

Table 6. Optimization conditions for Sonogashira-Hagihara reaction for the reaction of 4-iodotoluene and phenylacetylene using Pd@agarose-Fe₃O₄

Me-C₆H₄-I + Ph-C≡C-H $\xrightarrow[\text{base, solvent, heat}]{\text{catalyst}}$ Ph-C≡C-C₆H₄-Me

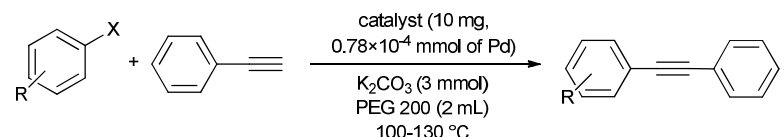
Entry	Catalyst(gr)	Solvent	Base	Temp. (°C)	Time (h)	Isolated Yields (%)
1	0.02	PEG 200	K ₂ CO ₃	100	1	60 ^a
2	0.02	PEG 200	KOAc	100	1	40
3	0.02	PEG 200	<i>n</i> -Pr ₃ N	100	1	10
4	0.02	PEG 200	None	100	1.5	N.R
5	0.02	DMSO	K ₂ CO ₃	100	1	44
6	0.02	EtOH	K ₂ CO ₃	100	1	25
7	0.02	NMP	K ₂ CO ₃	100	1	50
8	0.02	DMF	K ₂ CO ₃	100	1	30
9	0.02	EG	K ₂ CO ₃	100	1	10
10	0.03	PEG 200	K ₂ CO ₃	100	0.5	50
11	0.01	PEG 200	K ₂ CO ₃	100	3	73
12	None	PEG 200	K ₂ CO ₃	100	5	10
13	0.01	PEG 200	K ₂ CO ₃	110	1.5	65
14	0.01	PEG 200	K ₂ CO ₃	120	1	60
15	0.01	PEG 200	K ₂ CO ₃ / TBAB	100	3	70
16	0.01	None	K ₂ CO ₃ / TBAB	100	1.5	N.R
17	0.01	PEG200	K₂CO₃	100	1.5	94^b

























^a Conversion was 100% under the defined condition. ^b Reaction proceeded in the presence of 3 mmol of K₂CO₃

Then the optimized reaction condition was applied for the reaction of structurally different halides with phenyl acetylene. The reaction of aryl iodides and bromides was smoothly performed and the desired aryl alkynes were obtained in 60-95% isolated yields (Entries 1-11, Table 7). In the case of aryl

chlorides, the reaction needed harsher conditions therefore, the reaction temperature was raised to 130 °C. At this temperature, aryl chlorides were reacted and the corresponding aryl alkynes were obtained in 53-62 % isolated yields (Entries 12, 13, Table 7).

Table 7. Sonogashira-Hagihara reaction of aryl halides with phenylacetylene catalyzed by Pd@agarose-Fe₃O₄



Entry	Aryl halide	Product	Time (h)	Isolated Yield (%)
1			1	95
2			6	84
3			1.5	94
4			3	85
5			3.5	68
6			2.5	94
7			3	89
8			1	60
9			10	78
11			5	90
12			24	53 ^a
13			24	62 ^a

^a reaction temperature is 130 °C

Finally, recycling of the catalyst was tested upon the reaction of 4-iodotoluene with *n*-butyl acrylate employing 20 mg of the catalyst in the presence of K₂CO₃/PEG 200 at 80 °C. After completion of the reaction, the reaction mixture was diluted with ethyl acetate. The catalyst was separated by an external magnet (Figure 5), washed with ethyl acetate, water and dried under vacuum. The resulting solid catalyst was used directly for the next run. The yield of the desired product was dropped from 94 after the first run to 86% after the sixth run, which shows a negligible loss in catalytic activity of the catalyst (Table 8).

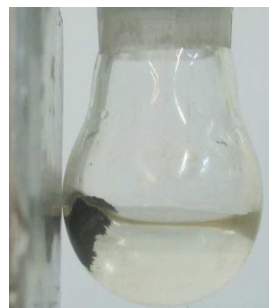
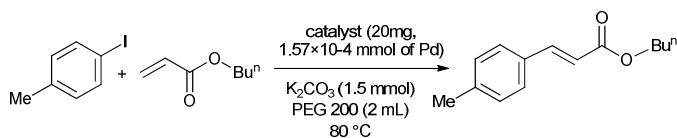


Figure 5: Photograph showing the magnetic separation of Pd@agarose-Fe₃O₄ catalyst from PEG phase by an external magnet

Table 8. Recycling of Pd@agarose-Fe₃O₄ for the reaction of 4-iodotoluene with n-butyl acrylate



Entry	solvent	Base
1	1	94
2	1	94
3	1	92
4	1	90
5	1	87
6	1	86

As shown in Table 8, no considerable change in the reaction yield has been observed during the six consecutive runs. This observation indicates that, the amounts of leaching of Pd into the reaction mixture must not be so significant, which has been also quantitatively approved by ICP analysis. The analysis showed that after the six recycling runs of the catalyst, only 7% of leaching of Pd has been occurred.

The TEM image of the recycled catalyst shows that the catalyst preserves its structure with little aggregation of the nanoparticles after the second run (Figure 6).

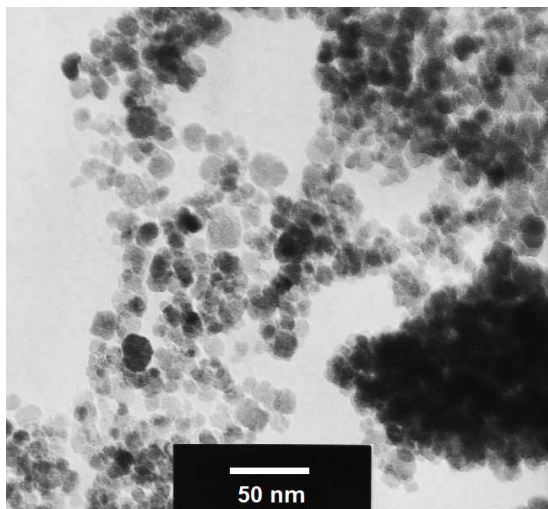


Figure 6: TEM image of the catalyst after the 2nd run of recycling

Conclusion

In conclusion, in this study we have introduced a new magnetically separable material; Pd@agarose-Fe₃O₄. In this composite, palladium nanoparticles are supported on agarose hydrogel which is attached to magnetic Fe₃O₄ nanoparticles. This new compound was characterized by different techniques such as EDX, TEM, TGA, FT-IR, VSM, AAS, and solid UV-visible analysis. Pd@agarose-Fe₃O₄ which shows good magnetic property has been successfully applied as a catalyst for Suzuki-Miyaura, Heck-Mizoroki and Sonogashira-Hagihara reactions of structurally different aryl halides in wet PEG 200. The recycling of the catalyst was successfully tested in Heck-Mizoroki reaction for six consecutive runs. The TEM picture of the recycled catalyst shows that agglomeration of the nanoparticles in the catalyst has been negligible and the size of

the particles has been reasonably preserved during the reaction. The ICP analysis of the reaction mixture shows that the amounts of the leached Pd species into the reaction mixture has not been so significant and after six consecutive runs in a Heck reaction, only 7% of Pd leaching has been occurred into the reaction media.

Experimental

All reactants were purchased from Acros, Merck and Sigma Aldrich and were used without further purification. ¹H NMR spectra were recorded at 250 and 400 MHz and ¹³C NMR were recorded at 62.9 and 100 MHz in CDCl₃ using TMS as internal standard. Thin layer chromatography was carried out on silica gel 254 analytical sheets obtained from Fluka. Column chromatography was carried out on silica gel 60 Merck (230-240 mesh) in glass columns (2 or 3 cm diameter) using 15-30 grams of silica gel per one gram of the crude mixture. Thermogravimetric analysis was conducted from room temperature to 800 °C in an oxygen flow using a NETZSCH STA 409 PC/PG instrument. The structures of the prepared materials were observed by transmission electron microscopy (Philips CM-120). FT-IR spectra were run on a Shimadzu FTIR-8300 spectrophotometer. UV-Vis spectra were recorded on Perkin Elmer, Lambda 25, UV/Vis spectrometer.

Gram-scale preparation of Pd@agarose-Fe₃O₄:

Agarose (1.00 g) was dissolved in water (100 mL) and heated to 80 °C for 15 min. To this solution, the synthesized Fe₃O₄ nanoparticles (4.00 g) which was sonicated in H₂O (25 mL) for 15 min were added. The resulting mixture was stirred for 4 h at 80 °C. Then an acidic solution of Pd(OAc)₂ (0.022 g, 1.0 mM) was added. After that, a solution of citric acid (20 mL, 4.0 mM) was added and stirred for 12 h at 80 °C. Upon stirring of the mixture, a black gel mass of the hydrogel was formed which was separated from the mixture by an external magnet. The resulting solid Pd@agarose-Fe₃O₄ was washed with cold water (3 × 15 mL), ethanol (3 × 15 mL) and dried under vacuum to give Pd@agarose-Fe₃O₄ composite.

General procedure for Suzuki-Miyaura reaction of aryl halides catalyzed by Pd@agarose-Fe₃O₄ in PEG 200:

To a flask containing the catalyst (20 mg contains 1.57 × 10⁻⁴ mmol of Pd species as determined by ICP analysis in PEG 200 (2 mL), were added aryl halide (1.0 mmol), the organoborane (1.5 mmol) and K₂CO₃ (2.0 mmol, 0.276 g) and stirred at 80 °C for the appropriate reaction time. After completion of the reaction (monitored by GC or TLC), the catalyst was separated from the reaction mixture by an external magnet. Then H₂O (10 mL) was added to the mixture and the product was extracted with ethyl acetate (3 × 10 mL). The organic extracts were combined together and dried over anhydrous MgSO₄. Evaporation of the solvent afforded the crude desired product which was purified by column chromatography on silica gel using n-hexane or different mixtures of n-hexane/ethyl acetate as the eluents to afford the highly pure products in 80-97% yields (Table 4).

General procedure for the Heck-Mizoroki reaction of aryl halides and styrene in the presence of Pd@agarose-Fe₃O₄ in PEG 200:

Aryl halide (1.0 mmol) and alkene (2.0 mmol) were added to a flask containing the catalyst (20 mg contains 1.57×10^{-4} mmol of Pd) and K_2CO_3 (2.0 mmol) in PEG 200 (2 mL). The mixture was stirred at the appropriate reaction time and the temperature (Table 5). Progress of the reaction was monitored by GC or TLC. After completion of the reaction, the catalyst was separated by an external magnet. Then, H_2O (10 mL) was added to the mixture and extracted with ethyl acetate (3×10 mL). The organic portions were combined together and dried over anhydrous $MgSO_4$ and filtered. The resulting solution was evaporated under vacuum to give the crude product. The column chromatography of the crude product on silica gel using n-hexane or different mixtures of n-hexane/ethyl acetate as the eluents afforded the highly pure product (Table 5).

General procedure for Sonogashira-Hagihara reaction of aryl halides in the presence of Pd@agarose- Fe_3O_4 in PEG 200:

A round-bottom flask was charged with phenylacetylene (1.5 mmol, 0.153 g), K_2CO_3 (3.0 mmol, 0.414 g), PEG 200 (2 mL), and aryl halide (1.0 mmol). To this mixture, the catalyst (10 mg, contains 0.78×10^{-4} mmol of Pd) was added. The mixture was stirred at 100 °C under argon atmosphere and the progress of the reaction was monitored by GC or TLC. After completion of the reaction, the catalyst was removed by an external magnet. To the resulting mixture H_2O (10 mL) was added followed by extraction with ethyl acetate (3×10 mL). The combined organic phases were dried over anhydrous $MgSO_4$ and filtered. The organic solvent was evaporated under diminished pressure to give the desired crude product. Purification of the crude product was performed by column chromatography on silica using n-hexane or different mixtures of n-hexane/ethyl acetate as the eluents to afford the product in a high purity in 53-95% isolated yields (Table 7).

Acknowledgements

The authors are thankful for the support of this work by grant number BN048 from the National Elite Foundation of Iran, Iran National Science Foundation (INSF-Grant number of 90007432), Institute for Advanced Studies in Basic Sciences (IASBS) Research Council and Shiraz University Research Council. M.G. is also thankful to Dr. S. H. Kazemi and H. R. Shahsavari for SEM/EDX and solid UV-visible analysis.

Notes and references

^aThe Late Professor Ali Akbar Moshfegh Laboratory, Chemistry Department, College of Sciences, Shiraz University, Shiraz 71454, Iran
Email: firouzabadi@chem.susc.ac.ir; iranpoor@chem.susc.ac.ir

^bDepartment of Chemistry, Institute for Advanced Studies in Basic Sciences (IASBS), P. O. Box 45195-1159, Gava zang, Zanjan 45137-6731, Iran.

† Electronic Supplementary Information (ESI) available. See DOI:10.1039/b000000x/

1. B. C. G. Soderberg, *Coord. Chem. Rev.* 2003, **241**, 147–247.
2. (a) F. Alonso, I. P. Beletskaya, M. Yus, *Tetrahedron* 2008, **64**, 3047–3101; (b) F.-S. Han, *Chem. Soc. Rev.*, 2013, **42**, 5270; (c) V. Polshettiwar, A. Decottignies, C. Len, A. Fihri, *ChemSusChem*

- 2010, **3**, 502; (c) S. Kotha, K. Lahiri, D. Kashinath, *Tetrahedron*, 2002, **58**, 9633.
3. (a) A. M. Trzeciak, J. J. Ziołkowski, *Coord. Chem. Rev.* 2007, **251**, 1281; (b) V. Polshettiwar, A. Molnar, *Tetrahedron* 2007, **63**, 6949; (c) V. Farina, *Adv. Synth. Catal.* 2004, **346**, 1553.
4. (a) K. Sonogashira, in: F. Diederich, A. de Meijera (Eds.), *Metal Catalyzed Cross-Coupling Reactions*, Wiley-VCH, Weinheim, 2004; (b) R.R. Tykwinski, *Angew. Chem. Int. Ed.* 2003, **42**, 1566; (c) E. Negishi, L. Anastasia, *Chem. Rev.* 2003, **103**, 1979; (d) K. Sonogashira, in: E. Negishi, A. de Meijere (Eds.), *Handbook of Organopalladium Chemistry for Organic Synthesis*, Wiley-Interscience, New York, 2002; (e) K. Sonogashira, *J. Organomet. Chem.* 2002, **653**, 46; (f) R. Rossi, A. Carpita, F. Bellina, *Org. Prep. Proced. Int.* 1995, **27**, 127; (g) K. Sonogashira, in: B.M. Trost, I. Fleming (Eds.), *Comprehensive Organic Synthesis*, Pergamon, Oxford, 1991, pp. 521–561. h) R. Chinchilla, C. Najera, *Chem. Rev.* 2007, **107**, 874.
5. (a) M. Lamblin, L. N.-Hardy, J.-C. Hierso, E. Fouquet, F.-X. Felpin, *Adv. Synth. Catal.* 2010, **352**, 33; (b) N. T. S. Phan, M. Van Der Sluys, C. W. Jones, *Adv. Synth. Catal.* 2006, **348**, 609.
6. (a) C. W. Lim, I. S. Lee, *Nano Today* 2010, **5**, 412 ; R. B. Nasir Baig, R. S. Varma, *Green Chem.*, 2013, **15**, 398; (b) S. Shylesh, V. Schnemann, W. R. Thiel, *Angew. Chem. Int. Ed.* 2010, **49**, 3428.
7. (a) B. Baruwati, D. Guin, S. V. Manorama, *Org. Lett.* 2007, **9**, 5377; (b) Z. Yinghuai, S. C. Peng, A. Emi, S. Zhenshun, Monalisa, R. A. Kemp, *Adv. Synth. Catal.* 2007, **349**, 1917; (c) J. Hu, Y. Wang, M. Han, Y. Zhou, X. Jiang, P. Sun, *Catal. Sci. Technol.*, 2012, **2**, 2332; (d) Z. Wang, B. Shen, Z. Aihua, N. He, *Chem. Eng. J.* 2005, **113**, 27; (e) P. D. Stevens, G. Li, J. Fan, M. Yen, Y. Gao, *Chem. Commun.*, 2005, 4435; (f) J. Liu, X. Peng, W. Sun, Y. Zhao, C. Xia, *Org. Lett.*, 2008, **10**, 3933; (g) D. Rosario-Amorin, M. Gaboyard, R. Clerac, L. Vellutini, S. Nlate, K. Heuze, *Chem. Eur. J.* 2012, **18**, 3305; (h) Q. Zhang, H. Su, J. Luo, Y. Wei, *Catal. Sci. Technol.*, 2013, **3**, 235; (i) H. Yang, G. Li, Z. Ma, *J. Mater. Chem.*, 2012, **22**, 6639–6648; (j) J. Wang, B. Xu, H. Sun, G. Song, *Tetrahedron Lett.* 2013, **54**, 238; (k) P. Li, L. Wang, L. Zhang, G.-W. Wang, *Adv. Synth. Catal.* 2012, **354**, 1307; (l) J.-R. Niu, X. Huo, F.-W. Zhang, H.-B. Wang, P. Zhao, W.-Q. Hu, J. Ma, R. Li, *ChemCatChem* 2013, **5**, 349.
8. (a) M. J. Aliaga, D. J. Ramon, M. Yus, *Org. Biomol. Chem.* 2010, **8**, 43; (b) F. Nador, M. A. Volpe, F. Alonso, A. Feldhoff, A. Kirschning, G. Radivoy, *Appl. Catal., A* 2013, **455**, 39; (c) T. Zeng, L. Yang, R. Hudson, G. Song, A. R. Moores, C. J. Li, *Org. Lett.* 2011, **13**, 442.
9. H.-J. Yoon, J.-W. Choi, H. Kang, T. Kang, S.-M. Lee, B.-H. Jun, Y.-S. Lee, *Synlett* 2010, 2518.
10. (a) Y.-M. Zhou, H.-B. Wang, M. Gong, Z.-Y. Sun, K. Cheng, X.-k. Kong, Z. Guo, Q.-W. Chen, *Dalton Trans.*, 2013, **42**, 9906; (b) J. Hu, Y.-l. Dong, X.-j. Chen, H.-j. Zhang, J.-m. Zheng, Q. Wang, X.-g. Chen, *Chem. Eng. J.* 2014, **236**, 1; (c) F. G. de Rivera, I. Angurell, M. D. Rossell, R. Erni, J. Llorca, N. J. Divins, G. Muller, M. Seco, O. Rossell, *Chem. Eur. J.* 2013, **19**, 11963.
11. (a) J. Liu, X. Peng, W. Sun, Y. Zhao, C. Xia, *Org. Lett.* 2008, **10**, 3933; (b) M. S. Kwon, I. S. Park, J. S. Jang, J. S. Lee, J. Park, *Org. Lett.* 2007, **9**, 3417; (c) H. Yoon, S. Ko, J. Jang, *Chem. Commun.* 2007, 1468; (d) K. Mori, S. Kanai, T. Hara, T. Mizugaki,

- K. Ebitani, K. Jitsukawa, K. Kaneda, *Chem. Mater.* 2007, **19**, 1249; (e) X. Teng, D. Black, N. J. Watkins, Y. Gao, H. Yang, *Nano Lett.* 2003, **3**, 261; (f) M. Shokouhimehr, Y. Piao, J. Kim, Y. Jang, T. Hyeon, *Angew. Chem.* 2007, **119**, 7169; *Angew. Chem. Int. Ed.* 2007, **46**, 7039; (g) T. Zeng, W.-W. Chen, C. M. Cirtiu, A. Moores, G. Song, C.-J. Li, *Green Chem.* 2010, **12**, 570.
12. (a) S. Luo, X. Zheng, H. Xu, X. Mi, L. Zhang, J.-P. Cheng, *Adv. Synth. Catal.* 2007, **349**, 2431; (b) R. Abu-Reziq, D. Wang, M. Post, H. Alper, *Adv. Synth. Catal.* 2007, **349**, 2145; (c) M. Kawamura, K. Sato, *Chem. Commun.* 2006, 4718; (d) S. Ding, Y. Xing, M. Radosz, Y. Shen, *Macromolecules* 2006, **39**, 6399; (e) N. T. S. Phan, C. W. Jones, *J. Mol. Catal. A* 2006, **253**, 123; (f) P. D. Stevens, G. Li, J. Fan, M. Yen, Y. Gao, *Chem. Commun.* 2005, 4435; (g) R. De Palma, S. Peeters, M. J. Van Bael, H. Van den Rul, K. Bonroy, W. Laureyn, J. Mullens, G. Borghs, G. Maes, *Chem. Mater.* 2007, **19**, 1821; (h) S. Luo, X. Zheng, J.-P. Cheng, *Chem. Commun.* 2008, 5719.
13. (a) L. M. Rossi, L. L. R. Vono, F. P. Silva, P. K. Kiyohara, E. L. Duarte, J. R. Matos, *Appl. Catal. A* 2007, **330**, 139; (b) T. J. Yoon, W. Lee, Y.-S. Oh, J.-K. Lee, *New J. Chem.* 2003, **27**, 227; (c) T. J. Yoon, J. I. Kim, J.-K. Lee, *Inorg. Chim. Acta* 2003, **345**, 228.
14. (a) A. Hu, G. T. Yee, W. Lin, *J. Am. Chem. Soc.* 2005, **127**, 12486; (b) G. Chouhan, D. Wang, H. Alper, *Chem. Commun.* 2007, 4809; (c) Y. Zheng, C. Duanmu, Y. Gao, *Org. Lett.* 2006, **8**, 3215; (d) Z. Yinghui, S. C. Peng, A. Emi, S. Zhenshun, Monalisa, R. A. Kemp, *Adv. Synth. Catal.* 2007, **349**, 1917.
15. (a) C. R. Vestal, J. Zhang, *J. Am. Chem. Soc.* 2002, **124**, 14312 – 14313; (b) S. Yu, M. Chow, *J. Mater. Chem.* 2004, **14**, 2781; (c) C. Mangeney, M. Fertani, S. Bousalem, M. Zhicai, S. Ammar, F. Herbst, P. Beaunier, A. Elaissari, M. M. Chehimi, *Langmuir* 2007, **23**, 10940; (d) K. M. Ho, P. Li, *Langmuir* 2008, **24**, 1801; (e) A. Schaetz, M. Zeltner, T. D. Michl, M. Rossier, R. Fuhrer, W. J. Stark, *Chem. Eur. J.* 2011, **17**, 10566; (f) F. Caruso, M. Spasova, A. Susha, M. Giersig, R. A. Caruso, *Chem. Mater.* 2001, **13**, 109; (g) A. P. Philipse, M. P. B. van Bruggen, C. Pathmamanoharan, *Langmuir* 1994, **10**, 92.
16. S. J. Zhang, X. Y. Li, J. P. Chen, *Carbon*, 2010, **48**, 60.
17. D. Yang, F. Yang, J. H. Hu, J. Long, C. C. Wang, D. L. Fu and Q. X. Ni, *Chem. Commun.*, 2009, 4447–4449.
18. (a) X. Y. Yang, X. Y. Zhang, Y. F. Ma, Y. Huang, Y. S. Wang and Y. S. Chen, *J. Mater. Chem.*, 2009, **19**, 2710; (b) H. P. Cong, J. J. He, Y. Lu and S. H. Yu, *Small*, 2009, **6**, 169.
19. (a) H. Firouzabadi, N. Iranpoor, F. Kazemi, *J. Mol. Catal. A: Chem.* 2011, **348**, 94; (b) H. Firouzabadi, N. Iranpoor, M. Gholinejad, F. Kazemi, *RSC Advances*, 2011, **1**, 1013; (c) H. Firouzabadi, N. Iranpoor, F. Kazemi, M. Gholinejad, *J. Mol. Catal. A: Chem.* 2012, **357**, 154.
20. A. Kong, P. Wang, H. Zhang, F. Yang, S. P. Huang, Y. Shan, *Appl. Catal. A: General* 2012, **417–418**, 183.
21. H. Firouzabadi, N. Iranpoor, M. Gholinejad, J. Hoseini, *Adv. Synth. Catal.* 2010, **352**, 119.
22. (a) Y. Li, X. M. Hong, D. M. Collard, M. A. El-Sayed, *Org. Lett.* 2000, **2**, 2385; (b) B. M. Choudary, S. Madhi, N. S. Chowdari, M. L. Kantam, B. Sreedhar, *J. Am. Chem. Soc.* 2002, **124**, 14127–14136.
23. J. Zhang, S. Rana, R.S. Srivastava, R.D.K. Misra, *Acta Biomaterialia*. 2008, **4**, 40.
24. H. Mahmoudi, A. A. Jafari, *ChemCatChem* 2013, **5**, 3743