

RSC Advances



This is an *Accepted Manuscript*, which has been through the Royal Society of Chemistry peer review process and has been accepted for publication.

Accepted Manuscripts are published online shortly after acceptance, before technical editing, formatting and proof reading. Using this free service, authors can make their results available to the community, in citable form, before we publish the edited article. This *Accepted Manuscript* will be replaced by the edited, formatted and paginated article as soon as this is available.

You can find more information about *Accepted Manuscripts* in the [Information for Authors](#).

Please note that technical editing may introduce minor changes to the text and/or graphics, which may alter content. The journal's standard [Terms & Conditions](#) and the [Ethical guidelines](#) still apply. In no event shall the Royal Society of Chemistry be held responsible for any errors or omissions in this *Accepted Manuscript* or any consequences arising from the use of any information it contains.

Engineering Diketopyrrolopyrrole Sensitizers for Highly Efficient Dye-Sensitized Solar Cells: Enhanced Light Harvesting and Intramolecular Charge Transfer

Cite this: DOI: 10.1039/x0xx00000x

Jin-Hua Huang,^{a,b} Ke-Jian Jiang,^{a,b,*} Fang Zhang,^{a,b} Wei Wu,^{a,b} Shao-Gang Li,^{a,b} Lian-Ming Yang,^{a,b} and Yan-Lin Song^{a,b,*}

Received 00th January 2012,
Accepted 00th January 2012

DOI: 10.1039/x0xx00000x

www.rsc.org/

Two asymmetric DPP dyes with a D- π -A structure are reported, where DPP is used as a bridge to connect triphenylamine donor and cyanoacetic acid acceptor, respectively. The compact dyes exhibit high light absorption ability covering the whole visible spectral region. The most efficient cell exhibited a short-circuit current density of 17.72 mA cm⁻², an open-circuit voltage of 725 mV, and a fill factor of 74%, yielding a power conversion efficiency of 9.51% under standard test conditions (irradiation of 1000 W m⁻², air mass=1.5 G), which is the highest value reported for DPP-based DSCs employing a I⁻/I₃⁻ redox couple. Furthermore, the DPP dyes show remarkable stability under long-term irradiation over 1000 h. Considering the facile synthesis and excellent stability, the DPP sensitizer would be a promising option for high efficient DSCs. The results show that judicious molecular engineering is crucial for constructing highly efficient charge transfer sensitizers in DSCs.

Introduction

As one of the key components in dye-sensitized solar cells (DSCs), the sensitizer exerts a significant influence on the device power conversion and stability.^[1] With ruthenium complexes^[2a-d] and zinc porphyrin dyes,^[2e-g] high power conversion efficiencies of up to 8-12% have been reported. On the other hand, metal-free organic dyes, usually with an electron donor- π bridge-electron acceptor (D- π -A) configuration, have been actively pursued due to their molecular tailoring flexibility and raw material abundance, and comparable efficiencies have been achieved.^[3] In the D- π -A organic dyes, triarylamine and cyanoacrylic acid were widely used as donor and acceptor, respectively, and various π -conjugated linkers were employed to bridge the donor and acceptor units to create a large number of D- π -A dyes for DSCs. It is well known that a linker is of paramount importance in tuning the molecular energy gap, and the electronic and steric structures, strongly affecting device performances.^[4]

Diketopyrrolopyrrole (DPP) chromophore has a uniquely planar conjugated bicyclic structure with electron-withdrawing property, and its derivatives are extensively used as high-performance pigments due to its exceptional photochemical, mechanical and thermal stability.^[5] Following its successful investigations in a series of optical electronic devices,^[6] it was also employed as a linker in development of sensitizers for DSCs in recent years.^[7] Following the first report in 2010,^[7a] Han's group introduced a strong electron donor indoline in a DPP dye, giving efficiency of 7.4%.^[7d] Recently, asymmetric DPP sensitizer **DPP07** with intense absorption in the red/near-

IR region were prepared with efficiencies of ~8.6% using a I⁻/I₃⁻ based electrolyte.^[8] In our previous report, a compact DPP dye **ICD-1**, was designed, where diphenylamine unit was directly connected to Phenyl-DPP unit with D- π -A structure, giving a power conversion efficiency of 8.61%. The result demonstrated that the electron communication in **ICD-1** is more favourable as compare with that in the similar structured sensitizer **ICD-2** with a triphenylamine donor.^[9] Encouraged by the result, we focused on the further structural optimization of DPP-based dyes for improving light harvesting ability. Here, two compact asymmetric DPP dyes (**ICD-8** and **ICD-9**), were designed, and an efficiency up to 9.51% was achieved in a DSC with an I⁻/I₃⁻ based electrolyte under standard AM 1.5 conditions. The chemical structures of the dyes are shown in Fig. 1.

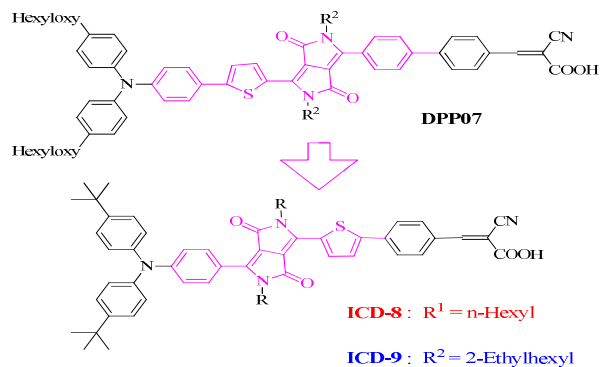


Fig. 1 Molecular structures of **DPP07**, **ICD-8** and **ICD-9**.

Results and discussion

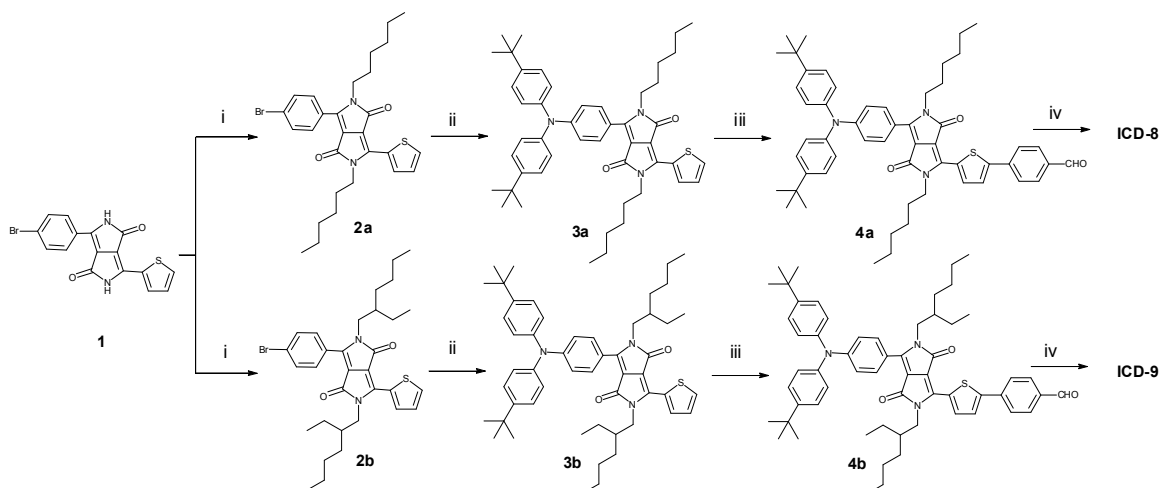


Fig. 2 Synthetic routes of dye **ICD-8** and **ICD-9**. i) KOtBu , NMP; ii) $\text{Pd}(\text{OAc})_2$, $\text{P}(\text{Bu})_3$, $t\text{-BuONa}$, PhMe, Ar, 90°C ; iii) $n\text{-BuLi}$, $(n\text{-Bu})_3\text{SnCl}$, -78°C ; $\text{PdCl}_2(\text{PPh}_3)_2$, Ar, 65°C ; iv) cyanoacetic acid, piperidine, THF, Ar, reflux.

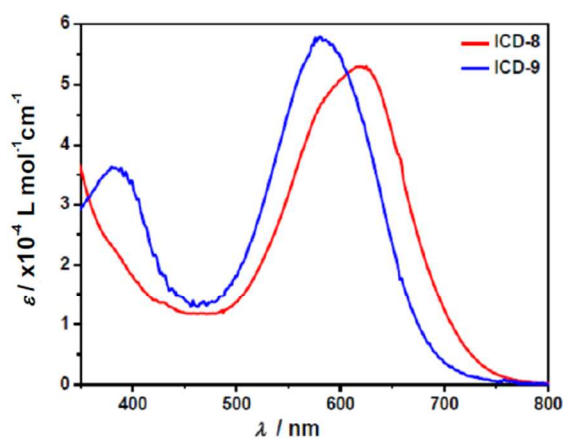


Fig. 3 Absorption spectra of **ICD-8** and **ICD-9** measured in dichloromethane solution.

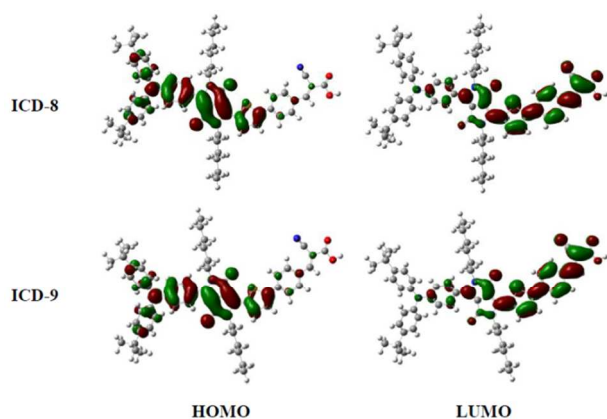


Fig. 4 Frontier Molecular Orbitals of the HOMO and LUMO for **ICD-8** and **ICD-9**, calculated with DFT on a B3LYP/6-31+G(d) Level (isodensity = 0.03 au).

The synthetic route of **ICD-8** and **ICD-9** is described in **Fig. 2**. Their UV-Vis absorption spectra examined in dichloromethane solutions were displayed in **Fig. 3**, and the relevant parameters are collected in **Table 1**. Both the dyes

show broader absorption spectra with two absorption bands covering a wide range in the visible region. The maximum absorption peak of **ICD-9** is at 581 nm, which is 21 nm red shift compared to that (560 nm) of the similar dye **DPP07** where an additional phenyl unit is included.^[8a] More importantly, the absorption spectrum of **ICD-9** covers the whole visible range, while the latter lacks absorption between 360-450 nm.^[8a] The result indicates that **ICD-9** dye is compact in structure, and possesses highly potential light harvesting ability as sensitizer in DSCs. In the case of **ICD-8**, the maximum absorption peak (λ_{max} , 620 nm) was significantly red shifted by 39 nm as compared with that in **ICD-9**. The large difference can be explained by the increased dihedral twist at the Ph-DPP-Th bonds in the presence of two large ethylhexyl units in **ICD-9**. The bulky units can attenuate the tendency of dye aggregation on TiO_2 surface, and improve the device performance.

In order to gain insight into the geometrical configuration and electron distribution of the frontier orbitals of the two dyes, density functional theory (DFT) calculations were made on a B3LYP/6-31G level as shown in **Fig. 4**. As shown in **Fig. 4**, the frontier HOMOs of both the dyes are homogeneously delocalized over the whole triphenylamine and DPP units, while their LUMOs are on the cyanoacrylic acid group and part of the DPP macrocycle. Thus electron communication may be favourable between the donor and the acceptor in both the dyes, allowing an efficient electron transfer from dye to TiO_2 electrode under light irradiation. The larger twist angles are expected to localize the triphenylamine radical cation away from the acceptor, and might be beneficial for retarding the back electron transfer from TiO_2 to the oxidized dye and improving the device open-circuit voltage.^[8a]

To further investigate the molecular energy levels, cyclic voltammetry measurements were performed in a 0.1 M dichloromethane solution of tetrabutylammonium hexafluorophosphate with ferrocene as internal standard at 0.63 V vs. NHE. The first oxidation potentials ($E_{\text{s}+/0}$) of **ICD-8** and **ICD-9** were observed to be 0.92 and 0.93 V vs. NHE, respectively, which are assigned to the oxidation of triphenylamine units. Both the potential values are substantially more positive than the iodide/tri-iodide couple redox (0.4 V vs. NHE), indicating that the ground-state sensitizer regeneration

Table 1 Photoelectrochemical Properties of **ICD-8** and **ICD-9**, and Their Solar Cell Performance.

| Dye | λ_{max} ^[a] [nm] | ϵ [L mol ⁻¹ cm ⁻¹] | E_{0-0} ^[b] [eV] | E_{S+0} ^[c] [V] | $E_{S+/*}$ ^[d] [V] | J_{sc} [mA cm ⁻²] | V_{oc} [mV] | FF | η ^[e] [%] |
|--------------|--|--|------------------------------------|-----------------------------------|------------------------------------|-------------------------------------|--------------------|------------|--------------------------------|
| ICD-8 | 620 | 53000 | 1.81 | 0.92 | -0.89 | 16.76 | 683 | 0.66 | 7.56 |
| | 339 | 39800 | | | | ± 0.20 | ± 10 | ± 0.02 | |
| ICD-9 | 581 | 57800 | 1.89 | 0.93 | -0.96 | 17.72 | 725 | 0.74 | 9.51 |
| | 393 | 35400 | | | | ± 0.20 | ± 10 | ± 0.02 | |

[a] Absorption in CH₂Cl₂ solutions (1 × 10⁻⁵ M) at rt; [b] E_{0-0} values were estimated from the intersection of the absorption and emission spectra; [c] The oxidation potentials of the dyes were measured in CH₂Cl₂ solutions with tetrabutylammoniumhexafluorophosphate (TBAPF₆, 0.1 M) as electrolyte, Pt wires as working and counter electrode, Ag/Ag⁺ as reference electrode; calibrated with ferrocene/ferrocenium (Fc/Fc⁺) as an internal reference and converted to NHE by addition of 630 mV; [d] The estimation was determined by subtracting E_{0-0} from E_{S+0} ; [e] The data were recorded under AM 1.5 G simulated solar light at a light intensity of 100 mW cm⁻², and represents the average of three devices, where TiO₂ films with 11 μm thick nanocrystalline layer and 6 μm thick scattering layer were used with an electrolyte containing 0.68 M dimethyl imidazolium iodide, 0.05 M iodine, 0.10 M LiI, 0.05 M guanidinium thiocyanate, and 0.40 M *tert*-butylpyridine in a mixture of acetonitrile and valeronitrile (85/15, v/v), and each data was averaged by three parallel samples.

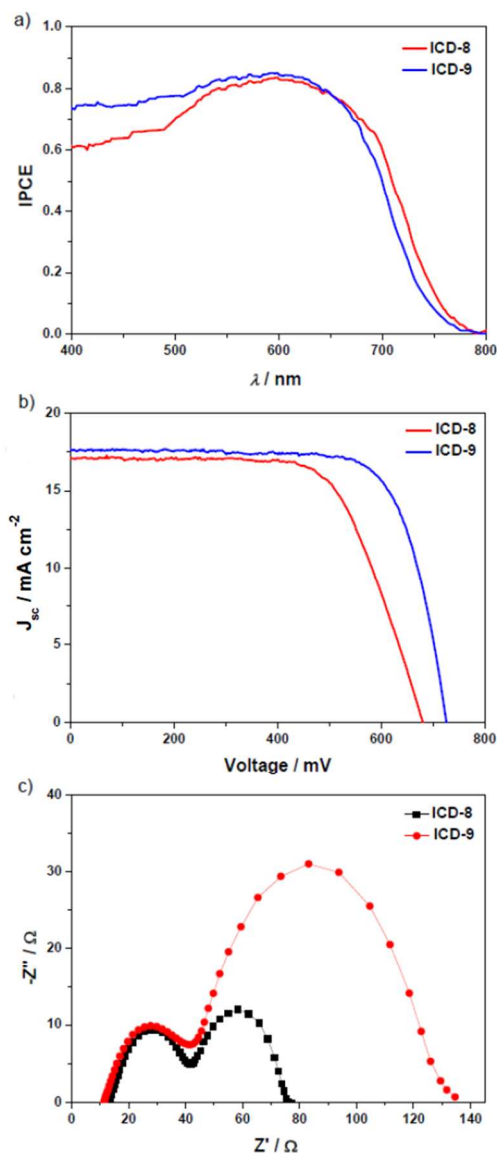


Fig. 5 a) Incident photon-to-electron conversion efficiency (IPCE) action; b) I - V characteristics measured under AM 1.5 conditions; c) electrochemical impedance spectra measured in the dark at a forward bias of 0.6 V for the DSCs employing **ICD-8** and **ICD-9**.

is energetically favorable in DSC^[10].

The optical transition energies (E_{0-0}) were 1.81 eV for **ICD-8** and 1.89 eV for **ICD-9**, estimated from the intersection of their absorption and emission spectra. excited-state redox potential, $E_{S+/*}$, determined by subtracting E_{0-0} from E_{S+0} , were -0.89 V for **ICD-8** and -0.96 eV for **ICD-9**. Both the values are negative enough to allow their excited state electron transfer into the TiO₂ conduction band (-0.5 V vs. NHE).^[11]

For preparation of the DSCs, a double TiO₂ electrode containing an 11 μm transparent layer and a 6 μm scattering layer was employed. The electrodes were prepared by screen printing method, and sintered at 500 °C in air for 30 min, followed with treatment by 0.05 M titanium tetrachloride solution and subsequent heat treatment at 500 °C for 30 min.^[12] The prepared TiO₂ electrodes were stained in the dye solution of 0.2 mM **ICD-8** or **ICD-9** in a mixture of acetonitrile, *tert*-butylalcohol and tetrahydrofuran (1:1:0.2, v/v/v). In the solution, 20 mM 3 α ,7 α -dihydroxy-5 β -cholic acid (che nodeoxycholic acid) was added as co-adsorbent to prevent dye aggregation on TiO₂ surface. The final device was prepared in a sandwich-type, where the dyed TiO₂ electrode and a Pt-counter electrode was sealed with a hot-melt film, and filled with an I⁻/I₃⁻ electrolyte between them. The electrolyte contains 0.68 M dimethyl imidazolium iodide, 0.05 M iodine, 0.10 M LiI, 0.05 M guanidinium thiocyanate, and 0.40 M *tert*-butylpyridine in the mixture of acetonitrile and valeronitrile (85:15, v/v).

Fig. 5a shows action spectra in the form of monochromatic incident photon-to-current conversion efficiencies (IPCEs). Both the dye-based DSCs exhibited a strong and broad response in the entire visible spectral region with the highest value of 85% and 83% at 593 nm for **ICD-9** and **ICD-8**, respectively. In the spectra, **ICD-8** showed slightly higher response in the long wavelengths 660-800 nm but much lower IPCE values at the other spectral regions, compared to **ICD-9**, which is in good agreement with absorption spectra. Both the dyes are rare examples having panchromatic spectral response, because most organic dyes show narrow absorption bands, could not absorb efficiently over the entire visible in DSCs with a single sensitizer.^[13] The compact **ICD-9** exhibits a broader spectral response, as compared to the dye **DPP07** mentioned above, where the device lacks efficient response between 400-500 nm.^[8a]

Fig. 5b shows the photocurrent density-voltage characteristics for DSCs with **ICD-8** and **ICD-9** measured under AM 1.5 G simulated solar light at a light intensity of 100 mW cm⁻². **ICD-9** based-device gave a short circuit photocurrent density (J_{sc}) of 17.72 \pm 0.20 mA/cm², an open circuit voltage (V_{oc}) of 725 \pm 10 mV, and a fill factor (FF) of 0.74 \pm 0.02,

corresponding to an overall conversion efficiency (η), derived from the equation $\eta = J_{sc} \times V_{oc} \times FF / \text{light intensity}$, of 9.51%, while **ICD-8** based device gave J_{sc} of 16.76 ± 0.20 mA/cm², V_{oc} of 683 ± 10 mV, FF of 0.66 ± 0.02 , and η of 7.56% under the same conditions. The large differences in the efficiencies come mainly from the differences in the V_{oc} and FF between them. In the given systems with different dyes, generally, the V_{oc} is strongly affected by the charge recombination at the dyed TiO₂ interface due to the dye aggregation. Considering their structural difference, the higher V_{oc} can be assigned to the effective aggregation suppression from branched 2-ethyl-hexyl chains in **ICD-9**.^[14]

For further elucidating the large difference in V_{oc} s for **ICD-8** and **ICD-9**, electrochemical impedance spectroscopy (EIS) was performed to investigate the FTO/TiO₂/dye interfaces. The Nyquist plots of DSCs were recorded in the dark with a forward bias of 0.6 V, as shown in **Fig. 5c**. Two semicircles from left to right in the Nyquist plot were assigned to the resistances of charge transfer (R_{Pt}) on the Pt counterelectrode and charge recombination (R_r) at the interface of the TiO₂/electrolyte.^[15] Clearly, the semicircle for R_r is larger in **ICD-9** than that in **ICD-8**, indicating the effective suppression of charge recombination at the interface of the TiO₂/electrolyte in **ICD-9** based device, which is consistent with the observed high V_{oc} value.

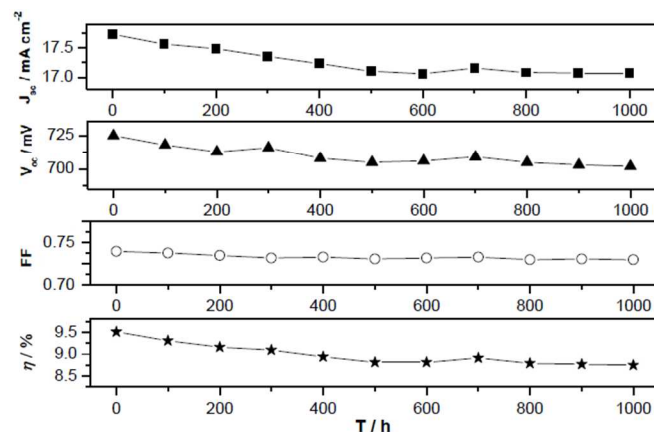


Fig. 6 Variations of the photovoltaic parameters (J_{sc} , V_{oc} , FF , and η) with aging time for the DSSC device based on RD-II under one-sun light soaking.

For testing long-term stability, photovoltaic performance of **ICD-9** based devices was recorded discontinuously over the entire 1000 h testing period at room temperature under one-sun light soaking. As shown in **Fig. 6**, the photovoltaic parameters J_{sc} , V_{oc} and FF of the **ICD-9** based cell changed slightly with the time, and the final conversion efficiency retained 92% of its initial value. The high stability may come from strong adsorption ability of the compact dye on TiO₂ surface, and will be favourable for the practical application.

Conclusions

In conclusion, two new asymmetric DPP dyes with a D- π -A structure were designed with high light absorption ability covering the whole visible spectral region. The panchromatic dye **ICD-9** exhibits high power conversion efficiency of 9.51% under standard AM 1.5 conditions, which is the highest values reported for DPP dye-based DSCs employing a I^-/I_3^- redox couple. Furthermore, the DPP dyes show remarkable stability under long-term irradiation over 1000 h. Considering the facile

synthesis and excellent stability, the DPP sensitizer would be a promising option for high efficient DSCs. Further improvement of the performance could be expected for DPP sensitizers through further extending spectral response for high short circuit photocurrent, and employing Co^{2+}/Co^{3+} redox couple for high open circuit voltage.^[16] More importantly, judicious molecular engineering is crucial for constructing highly efficient charge transfer sensitizers in DSCs. The results would provide valuable, basic guidelines for rational designs of D- π -A molecules for high-performance DSCs and other optoelectronic devices.

Experimental

General information:

Unless otherwise noted, all solvents were treated by standard methods before use. All reagents were commercially available and used without further purification unless indicated otherwise. Thin lay all chemicals were analytical grade and used as received. NMR spectra were recorded on a BRUKER AVANCE 400 MHz instruments. The residual solvent protons (¹H) were used as internal standards. ¹H-NMR data are presented as follows: chemical shift in ppm (δ) downfield from tetramethylsilane (multiplicity, coupling constant (Hz), integration). The following abbreviations are used in reporting NMR data: s, singlet; br.s, broad singlet; d, doublet; t, triplet; q, quartet; dd, doublet of doublets; m, multiplet. Mass spectra were taken on a Bruker Daltonics Inc. APEXII FT-ICR spectrometer. The material 3-(4-bromophenyl)-6-(thiophen-2-yl)-2,5-dihydro-pyrrolo [3,4-c]pyrrole-1,4-dione(DPP) were prepared according to the literature procedures^[17].

Synthesis of 2a:

In an oven-dried 250 mL three-necked flask, 8g (18 mmol) **DPP** (**1**) and 4.03 g (36 mmol) potassium tert-butoxide were dissolved in 150mL of dry NMP, the solution was vigorously stirred at 60 °C for 30 min, after which time 20.8 g (108 mmol) of 1-bromohexane was dropwise over a period of 90 min. The reaction was maintained for another 20 hours. After cooling to room temperature, toluene was added and the organic phase was filtered through a silica-gel pad. The filtrate was washed with water (3*50 mL) and brine (3*50 mL). The combined organic phases were evaporated under reduced pressure and the residue purified by silica-gel column chromatography to give the desired product. 2.5 g (22%) of bright orange needles were obtained.

Synthesis of 3a:

An oven-dried 100 mL three-necked flask was charged with compound **2a** (0.6 g, 1.0 mmol), Pd(OAc)₂ (22 mg, 0.1 mmol), P^tBu₃ (20 mg, 0.1 mmol), bis(*tert*-butylphenyl)amine (0.48 g, 1.30 mmol), ^tBuONa (0.48 g, 5.0 mmol). The flask was evacuated and backfilled with nitrogen, with the operation being repeated twice. Then 20 mL toluene was added and the mixture was heated at 90 °C for 16 h. After cooling to room temperature, dichloromethane were added and the organic phase was filtered through a silica-gel pad. The filtrate was with water (3*20 mL) and brine (3*20 mL). The combined organic phases was dried on MgSO₄, filtered and evaporated under reduced pressure and the residue purified by silica-gel column chromatography to give a purple solid(0.61 g, 62%). ¹H-NMR(CDCl₃, 400 MHz) δ (ppm): 0.80-0.86(m, 6H), 1.26-1.31 (m, 25H), 1.54(s, 5H), 1.71 (s, 4H), 3.83 (t, $J = 8.0$ Hz, 2H), 4.00 (t, $J = 8.0$ Hz, 2H), 7.03 (d, $J = 4.8$ Hz, 3H), 7.12 (d, $J = 8.8$ Hz, 4H), 7.33 (d, $J = 8.4$ Hz, 4H), 7.60 (d, $J = 5.2$ Hz, 1H), 7.75(d, $J = 8.8$ Hz, 2H), 8.84 (d, $J = 3.2$ Hz, 1H).

Synthesis of 4a:

In an oven-dried 250 mL three-necked flask, compound (**3a**) (0.8 g, 1 mmol) and dried THF (50 mL) were added under N₂ atmosphere. *n*-Butyl lithium (0.42 mL, 2.4 M in hexane, 1 mmol), was added dropwise at -78 °C stirred for 1 h with the temperature maintained -78 °C. then the mixture was warmed up to -40 °C for 3 h and cooled to -78 °C again, tributyltin chloride (0.27 mL, 1 mmol) was added one portion. The mixture was warmed to room temperature slowly and stirred for another 24 h. then 4-Bromobenzaldehyde (0.28 g, 1.5 mmol) and PdCl₂(PPh₃)₂ (120 mg, 0.171 mmol) were added, the solution was stirred at 65 °C for another 15 h, cooled and concentrated on the rotary evaporator. The residue was subjected to column chromatography to afford a dark solid (812 mg, 90%). ¹H-NMR(CDCl₃, 400 MHz) δ(ppm): 0.86-0.90(m, 6H), 1.27-1.31(m, 30H), 1.75 (4H), 3.86 (d, *J* = 7.6 Hz, 2H), 4.04 (t, *J* = 7.6 Hz, 2H), 7.03 (d, *J* = 8.8 Hz, 2H), 7.13 (d, *J* = 6.8 Hz, 4H), 7.34 (d, *J* = 8.8 Hz, 4H), 7.59 (d, *J* = 4.0 Hz, 1H), 7.77 (d, *J* = 8.8 Hz, 2H), 7.83 (d, *J* = 8.4 Hz, 2H), 7.93 (d, *J* = 8.4 Hz, 2H), 8.86 (d, *J* = 4.4 Hz, 1H), 10.02 (s, 1H).

Synthesis of ICD-8:

An oven-dried 100 mL one-necked flask was charged with compound **4** (4.2 × 10⁻⁴ mol), cyanoacetic acid (8 × 10⁻³ mol), 10 mL of dry THF and 0.5 ml piperidine. The solution was heated to reflux for 15 h and the colour turned to deep red. After cooling to room temperature, dichloromethane and a diluted solution of hydrochloric acid were added and the organic phase was washed with water (3*20 mL) and brine (3*20 mL). The combined organic phase was dried on MgSO₄, filtered and evaporated under reduced pressure and the residue purified by silica-gel column chromatography to give a dark-purple solid (78%). ¹H-NMR(DMSO, 400 MHz) δ(ppm) : 0.79-0.85(m, 6H), 1.19-1.34 (m, 30H), 1.54-1.60(m, 4H), 3.78 (2H), 3.93 (2H), 6.83 (d, *J* = 8.0 Hz, 4H), 7.10 (d, *J* = 8.0 Hz, 4H), 7.42 (d, *J* = 8.0 Hz, 4H), 7.76(d, *J* = 4.4 Hz, 2H), 7.76-7.98 (m, 8H), 8.83 (d, *J* = 4 Hz, 1H); MS (MALDI-TOF): *m/z* found: 912.7 (M+).

Synthesis of 2b:

In an oven-dried 250 mL three-necked flask, 8g (18 mmol) DPP (**1**) and 4.03 g (36 mmol) potassium *tert*-butoxide were dissolved in 150 mL of dry NMP, the solution was vigorously stirred at 60 °C for 30 min, after which time 20.8 g (108 mmol) of 1-bromo-2-ethylhexane was dropwisely over a period of 90 min. The reaction was maintained for another 20 hours. After cooling to room temperature, toluene was added and the organic phase was filtered through a silica-gel pad. The filtrate was washed with water (3*50 mL) and brine (3*50 mL). The combined organic phases were evaporated under reduced pressure and the residue purified by silica-gel column chromatography to give the desired product. 2.5 g (22%) of bright orange needles were obtained.

Synthesis of 3b:

An oven-dried 100 mL three-necked flask was charged with compound **2b** (0.6 g, 1.0 mmol), Pd(OAc)₂ (22 mg, 0.1 mmol), P^tBu₃ (20 mg, 0.1 mmol), bis(*tert*-butyl phenyl)amine (0.48 g, 1.30 mmol), ^tBuONa (0.48 g, 5.0 mmol). The flask was evacuated and backfilled with nitrogen, with the operation being repeated twice. Then 20 mL toluene was added and the mixture was heated at 90 °C for 16 h. After cooling to room temperature, dichloromethane were added and the organic phase was filtered through a silica-gel pad. The filtrate was with water (3*20 mL) and brine (3*20 mL). The combined organic phases was dried on MgSO₄, filtered and evaporated under reduced pressure and the residue purified by silica-gel column chromatography to give a purple solid(0.61 g, 62%). ¹H-NMR(CDCl₃, 400 MHz) δ(ppm): 0.80-0.94(m, 12H), 1.28-1.38 (m, 28H), 1.61-1.68(m, 6H), 1.68 (s, 2H), 3.83 (t, *J* = 7.6 Hz, 2H), 3.99 (t, *J* = 7.6 Hz, 2H), 7.03 (d, *J* = 4.8 Hz, 3H), 7.12

(d, *J* = 8.8 Hz, 4H), 7.33 (d, *J* = 8.4 Hz, 4H), 7.60 (d, *J* = 5.2 Hz, 1H), 7.75(d, *J* = 8.8 Hz, 2H), 8.84 (d, *J* = 3.2 Hz, 1H).

Synthesis of 4b:

In an oven-dried 250 mL three-necked flask, compound (**3b**) (0.8 g, 1 mmol) and dried THF (50 mL) were added under N₂ atmosphere. *n*-Butyl lithium (0.42 mL, 2.4 M in hexane, 1 mmol), was added dropwise at -78 °C stirred for 1 h with the temperature maintained -78 °C. then the mixture was warmed up to -40 °C for 3 h and cooled to -78 °C again, tributyltin chloride (0.27 mL, 1 mmol) was added one portion. The mixture was warmed to room temperature slowly and stirred for another 24 h. then 4-Bromobenzaldehyde (0.28 g, 1.5 mmol) and PdCl₂(PPh₃)₂ (120 mg, 0.171 mmol) were added, the solution was stirred at 65 °C for another 15 h, cooled and concentrated on the rotary evaporator. The residue was subjected to column chromatography to afford a dark solid (812 mg, 90%). ¹H-NMR(CDCl₃, 400 MHz) δ(ppm): 0.76-0.94(m, 12H), 1.27-1.38 (m, 29H), 1.60-1.66(m, 6H), 1.68 (s, 1H), 3.86 (d, *J* = 7.6 Hz, 2H), 4.0 (d, *J* = 7.6 Hz, 2H), 7.03 (d, *J* = 8.8 Hz, 2H), 7.11 (d, *J* = 8.8 Hz, 4H), 7.32 (d, *J* = 8.4 Hz, 4H), 7.58 (d, *J* = 4 Hz, 1H), 7.72 (d, *J* = 8.8 Hz, 2H), 7.82 (d, *J* = 8.4 Hz, 2H), 7.93 (d, *J* = 8 Hz, 2H), 8.85 (d, *J* = 4 Hz, 1H), 10.03 (s, 1H).

Synthesis of ICD-9:

An oven-dried 100 mL one-necked flask was charged with compound **4b** (4.2 × 10⁻⁴ mol), cyanoacetic acid (8 × 10⁻³ mol), 10 mL of dry THF and 0.5ml piperidine. The solution was heated to reflux for 15 h and the colour turned to deep red. After cooling to room temperature, dichloromethane and a diluted solution of hydrochloric acid were added and the organic phase was washed with water (3*20 mL) and brine (3*20 mL). The combined organic phase was dried on MgSO₄, filtered and evaporated under reduced pressure and the residue purified by silica-gel column chromatography to give a dark-purple solid (78%). ¹H-NMR(DMSO, 400 MHz) δ(ppm) : 0.78-0.88(m, 12H), 1.16-1.38 (m, 29H), 1.55-1.62(m, 6H), 1.74 (s, 1H), 3.80 (s, 2H), 3.87 (d, *J* = 6.8 Hz, 2H), 6.84 (d, *J* = 8.4 Hz, 4H), 7.10 (d, *J* = 8.4 Hz, 4H), 7.41 (d, *J* = 8.4 Hz, 4H), 7.76(d, *J* = 4.4 Hz, 2H), 7.86-7.99 (m, 6H), 8.80 (d, *J* = 4 Hz, 1H); MS (MALDI-TOF): *m/z* found: 968.5 (M+).

DSC fabrication:

The nanocrystalline TiO₂ pastes (particle size, 20 nm) were prepared using a previously reported procedure.^[18] Fluorine doped thin oxide (FTO, 4 mm thickness, 10 ohms/sq, Nippon Sheet Glass, Japan) conducting electrodes were washed with soap and water, followed by sonication for 10 min in acetone and isopropanol, respectively. Following a drying period, the electrodes were then submerged in a 40 mM aqueous solution of TiCl₄ for 30 min at 75 °C, and then washed by water and ethanol. On the electrodes, an 11 μm thick nanocrystalline TiO₂ layer and 6 μm thick TiO₂ light scattering layer (particle size, 400 nm, PST-400C) were prepared by screen-printing method. The TiO₂ electrodes were heated at 500 °C for 30 min, followed by treating with a 40 mM aqueous solution of TiCl₄ for 30 min at 75 °C and subsequent sintering at 500 °C for 30 min. The thickness of TiO₂ films was measured by a profiler, Sloan, Dektak3. The electrodes were immersed in a dye bath containing 0.2 mM ICD-8 or ICD-9 and 20 mM 3 α ,7 α -dihydroxy-5 β -cholic acid (chenodeoxycholic acid) in 4-*tert*-butanol/acetonitrile mixture/tetrahydrofuran (1:1:0.2, v/v) and kept for 24 h at room temperature. The dyed electrodes were then rinsed with the mixed solvent to remove excess dye. A platinum-coated counter electrode was prepared according to the reporter,^[19] and two holes were drilled on its opposite sides. The two electrodes were sealed together with a 25 μm thick thermoplastic Surlyn frame. An electrolyte solution was then introduced through one of the two holes in the counter electrode,

and the holes were sealed with the thermoplastic Surlyn. The electrolyte contains 0.68 M dimethyl imidazolium iodide, 0.05 M iodine, 0.10 M LiI, 0.05 M guanidinium thiocyanate, and 0.40 M *tert*-butylpyridine in the mixture of acetonitrile and valeronitrile (85:15, v/v). All the devices were prepared with a photoactive area of about 0.3 cm², and a metal mask of 0.165 cm² was covered on the device for photovoltaic property measurements.

Characterization:

The photocurrent-voltage (*I*-*V*) characteristics were recorded at room temperature using a computer-controlled Keithley 2400 source meter under air mass (AM) 1.5 simulated illumination (100 mW cm⁻², Oriol, 67005), and each data was averaged by three parallel samples. The action spectra of monochromatic incident photo-to-current conversion efficiency (IPCE) for solar cells were performed using a commercial setup (PV-25 DYE, JASCO). A 300 W Xenon lamp was employed as light source for generation of a monochromatic beam. Calibrations were performed with a standard silicon photodiode. IPCE is defined by $IPCE(\lambda) = hcJ_{sc}/e\phi\lambda$, where *h* is Planck's constant, *c* is the speed of light in a vacuum, *e* is the electronic charge, λ is the wavelength in meters (m), *J*_{sc} is the short-circuit photocurrent density (A m⁻²), and ϕ is the incident radiation flux (W m⁻²).

Acknowledgements

This work is supported by the National Nature Science Foundation (Grant Nos. 21174149, 51173190, 21073203, and 21121001), the National 863 Program (No. 2011AA050521), and the 973 Program (2009CB930404, 2011CB932303, and 2011CB808400).

Notes and references

^a Beijing National Laboratory for Molecular Sciences (BNLMS).

^b Key Laboratory of Green Printing, Institute of Chemistry, Chinese Academy of Sciences, Beijing 100190, P. R. China.

- B. O'regan, M. Grätzel, *Nature*, 1991, **353**, 737.
- a) M. K. Nazeeruddin, F. De Angelis, S. Fantacci, A. Selloni, G. Viscardi, P. Liska, S. Ito, B. Takeru, M. Grätzel, *J. Am. Chem. Soc.*, 2005, **127**, 16835; b) Y. Chiba, A. Islam, Y. Watanabe, R. Komiya, N. Koide, L. Jpn. Han, *J. Appl. Phys.*, 2006, **45**, L638; c) F. Gao, Y. Wang, D. Shi, J. Zhang, M. Wang, X. Jing, R. Humphry-Baker, P. Wang, S. M. Zakeeruddin, M. Grätzel, *J. Am. Chem. Soc.*, 2008, **130**, 10720; d) K.-J. Jiang, N. Masaki, J. Xia, S. Noda, S. Yanagida, *Chem. Commun.*, 2006, **23**, 2460; e) A. Yella, H. W. Lee, H. N. Tsao, C. Y. Yi, A. K. Chandiran, M. K. Nazeeruddin, E. W. G. Diau, C. Y. Yeh, S. M. Zakeeruddin, M. Grätzel, *Science*, 2011, **334**, 629; f) Y.-C. Chang, C.-L. Wang, T.-Y. Pan, S.-H. Hong, C.-M. Lan, H.-H. Kuo, C.-F. Lo, H.-Y. Hsu, C.-Y. Lin, E. W.-G. Diau, *Chem. Commun.*, 2011, **47**, 8910; g) A. Yella, C.-L. Mai, S. M. Zakeeruddin, S.-N. Chang, C.-H. Hsieh, C.-Y. Yeh, M. Grätzel, *Angew. Chem. Int. Ed.*, 2014, **53**, 1.
- a) K. Hara, K. Sayama, Y. Ohga, A. Shinpo, S. Suga, H. Arakawa, *Chem. Commun.*, 2001, **6**, 569; (b) S. Kim, J. K. Lee, S. O. Kang, J. Ko, J. H. Yum, A. Fantacci, F. D. Angelis, D. Di Censo, M. K. Nazeeruddin, M. Grätzel, *J. Am. Chem. Soc.*, 2006, **128**, 16701; c) Y. Bai, J. Zhang, D. Zhou, Y. Wang, M. Zhang, P. Wang, *J. Am. Chem. Soc.*, 2011, **133**, 11442; d) S. Li, K.-J. Jiang, K. Shao, L. Yang, *Chem. Commun.*, 2006, **26**, 2792; e) T. Horiuchi, H. Miura, K. Sumioka, S. Uchida, *J. Am. Chem. Soc.*, 2004, **126**, 12218; f) D. P. Hagberg, T. Edvinsson, T. Marinado, G. Boschloo, A. Hagfeldt, L. Sun, *Chem. Commun.*, 2006, **21**, 2245; (g) S. Ito, H. Miura, S. Uchida, M. Takata, K. Sumioka, P. Liska, P. Comte, P. Pechy, M. Grätzel, *Chem. Commun.*, 2008, **41**, 5194; (h) T. Bessho, S.M. Zakeeruddin, C.-Y. Yeh, E.W.-G. Diau, M. Graetzel, *Angew. Chem. Int. Ed.*, 2010, **49**, 6646; (i) W. Zeng, Y. Cao, Y. Bai, Y. Wang, Y. Shi, M. Zhang, F. Wang, C. Pan, P. Wang, *Chem. Mater.*, 2010, **22**, 1915; (j) N. Koumura, Z.-S. Wang, S. Mori, M. Miyashita, E. Suzuki, K. Hara, *J. Am. Chem. Soc.*, 2006, **128**, 14256.
- a) G.L. Zhang, Y. Bai, R.Z. Li, D. Shi, S. Wenger, S. M. Zakeeruddin, M. Grätzel, P. Wang, *Energy Environ. Sci.*, 2009, **2**, 92; b) G.L. Zhang, H. Bala, Y.M. Cheng, D. Shi, X.J. Lv, Q.J. Yu, P. Wang, *Chem. Commun.*, 2009, **16**, 2198; c) J.Y. Liu, D.F. Zhou, M.F. Xu, X.Y. Jing, P. Wang, *Energy Environ. Sci.*, 2011, **4**, 3545; d) S. Haid, M. Marszalek, A. Mishra, M. Wielopolski, J. Teuscher, J.-E. Moser, R. Humphry-Baker, S. M. Zakeeruddin, M. Grätzel, P. Bäuerle, *Adv. Funct. Mater.*, 2012, **22**, 1291; e) M.F. Xu, M. Zhang, M. Pastore, R.Z. Li, F. D. Angelis, P. Wang, *Chem. Sci.*, 2012, **3**, 976; f) N. Cai, R. Z. Li, Y. L. Wang, M. Zhang, P. Wang, *Energy Environ. Sci.*, 2013, **6**, 139; g) M. Zhang, Y.L. Wang, M.F. Xu, W.T. Ma, R.Z. Li, P. Wang, *Energy Environ. Sci.*, 2013, **6**, 2944.
- S.Y. Qu, H. Tian, *Chem. Commun.*, 2012, **48**, 30391
- a) M. Fukuda, K. Kodama, H. Yamamoto, K. Mito, *Dyes Pigm.*, 2004, **63**, 115; b) Z. Qiao, Y. Xu, S. Lin, J. Peng, D. Cao, *Synth. Met.*, 2010, **160**, 1544; c) M. Tantiwiwat, A. Tamayo, N. Luu, X.-D. Dang, T.-Q. Nguyen, *J. Phys. Chem. C.*, 2008, **112**, 17402; d) H. Bronstein, Z. Chen, R. S. Ashraf, W. Zhang, J. Du, J. R. Durrant, P. S. Tuladhar, K. Song, S. E. Watkins, Y. Geerts, M. M. Wienk, R. A. J. Janssen, P. S. T. Anthopoulos, H. Sirringhaus, M. Heeney, I. McCulloch, *J. Am. Chem. Soc.*, 2011, **133**, 3272; e) J. C. Bijleveld, A. P. Zoombelt, S. G. J. Mathijssen, M. M. Wienk, M. Turbiez, D. M. Leeuw, R. A. J. Janssen, *J. Am. Chem. Soc.*, 2009, **131**, 16616.
- a) S. Y. Qu, W. J. Wu, J. L. Hua, C. Kong, Y. T. Long, H. Tian, *J. Phys. Chem. C.*, 2010, **114**, 1343; b) C. Kanimozhi, P. Balraju, G. D. Sharma, S. Patil, *J. Phys. Chem. C.*, 2010, **114**, 3287; c) J. Warnan, L. Favereau, Y. Pellegrin, E. Blart, D. Jacquemin, F. Odobel, *J. Photochem. Photobiol. A.*, 2011, **226**, 9; d) S. Y. Qu, C. J. Qin, A. Islam, Y. Z. Wu, W. H. Zhu, J. L. Hua, H. Tian, L. Y. Han, *Chem. Commun.*, 2012, **48**, 6972; e) S. Y. Qu, B. Wang, F. L. Guo, J. Li, W. J. Wu, C. Kong, Y. T. Long, Hua, J. L. *Dyes Pigm.*, 2012, **92**, 1384; f) T. W. Holcombe, J.-H. Yum, J. Yoon, P. Gao, M. Marszalek, D. Di Censo, K. Rakstys, M. K. Nazeeruddin, M. Grätzel, *Chem. Commun.*, 2012, **48**, 10724;
- a) J.-H. Yum, W. H. Thomas, Y. Kim, J. Yoon, K. Rakstys, M. K. Nazeeruddin, M. Grätzel, *Chem. Commun.*, 2012, **48**, 10727. b) J.-H. Yum, T. W. Holcombe, Y. Kim, K. Rakstys, T. Moehl, J. Teuscher, J. H. Delcamp, M. K. Nazeeruddin, M. Grätzel, *Sci. Rep.*, 2013, **3**, 2446.
- F. Zhang, K.-J. Jiang, J.-H. Huang, C.-C. Yu, S.-G. Li, M.-G. Chen, L.-M. Yang, Y.-L. Song, *J. Mater. Chem. A*, 2013, **1**, 4858.
- M. Grätzel, *Nature*, 2001, **414**, 338.
- A. Hagfeldt, G. Boschloo, L. Sun, L. Kloo, H. Pettersson, *Chem. Rev.*, 2010, **110**, 6595.
- S. Ito, P. Chen, P. Comte, M. K. Nazeeruddin, P. Liska, P. Pechy, M. Grätzel, *Prog. Photovolt: Res. Appl.*, 2007, **15**, 603.
- a) J.-H. Yum, E. Baranoff, S. Wenger, M. K. Nazeeruddin, M. Grätzel, *Energy Environ. Sci.*, 2011, **4**, 842; b) C.-M. Lan, H.-P. Wu,

- T.-Y. Pan, C.-W. Chang, W.-S. Chao, C.-T. Chen, C.-L. Wang, C.-Y. Lin, E. W.-G. Diau, *Energy Environ. Sci.*, 2012, **5**, 6460; c) M. Cheng, X. Yang, F. Zhang, J. Zhao, L. Sun, *J. Phys. Chem. C*, 2013, **117**, 9076; d) L. Yu, K. Fan, T. Duan, X. Chen, R. Li, T. Peng, *ACS Sustainable Chem. Eng.*, 2014, dx.doi.org/10.1021/sc400532g; e) C.-L. Wang, J.-Y. Hu, C.-H. Wu, H.-H. Kuo, Y.-C. Chang, Z.-J. Lan, H.-P. Wu, E. W.-G. Diau, C.-Y. Lin, *Energy Environ. Sci.*, DOI: 10.1039/C3EE44168G.
- 14 a) C. Kim, J. Liu, J. Lin, A. B. Tamayo, B. Walker, G. Wu, T.-Q. Nguyen, *Chem. Mater.*, 2012, **24**, 1699; b) L. Dou, J. Gao, E. Richard, J. You, C.-C. Chen, K. C. Cha, Y. He, G. Li, Y. J. Yang, *J. Am. Chem. Soc.*, 2012, **134**, 10071.
- 15 F. Fabregat-Santiago, J. Bisquert, G. Garcia-Belmonte, G. Boschloo, A. Hagfeldt, *Sol. Energy Mater. Sol. Cells*, 2005, **87**, 117.
- 16 J. Luo, M. Xu, R. Li, K.-W. Huang, C. Jiang, Q. Qi, W. Zeng, J. Zhang, C. Chi, P. Wang, J. Wu, *J. Am. Chem. Soc.*, 2013, **136**, 265.
- 17 Y.b. Xu, Y. Jin, W.h. Lin, J.b. Peng, H.f. Jiang, D. Cao, *Synthetic Metals*, 2010, **160**, 2135.
- 18 P. Wang, S. M. Zakeeruddin, P. Comte, R. Charvet, R. Humphry-Baker and M. Grätzel, *J. Phys. Chem. B*, 2003, **107**, 14336.
- 19 S. Ito, T. N. Murakami, P. Comte, P. Liska, C. Grätzel, M. K. Nazeeruddin, M. Grätzel, *Thin Solid Films*, 2008, **516**, 4613.