

# RSC Advances



This is an *Accepted Manuscript*, which has been through the Royal Society of Chemistry peer review process and has been accepted for publication.

*Accepted Manuscripts* are published online shortly after acceptance, before technical editing, formatting and proof reading. Using this free service, authors can make their results available to the community, in citable form, before we publish the edited article. This *Accepted Manuscript* will be replaced by the edited, formatted and paginated article as soon as this is available.

You can find more information about *Accepted Manuscripts* in the [Information for Authors](#).

Please note that technical editing may introduce minor changes to the text and/or graphics, which may alter content. The journal's standard [Terms & Conditions](#) and the [Ethical guidelines](#) still apply. In no event shall the Royal Society of Chemistry be held responsible for any errors or omissions in this *Accepted Manuscript* or any consequences arising from the use of any information it contains.

Cite this: DOI: 10.1039/c0xx00000x

[www.rsc.org/xxxxxx](http://www.rsc.org/xxxxxx)

ARTICLE TYPE

## Synthesis of poly(butylene succinate) through oligomerization – cyclization – ROP route

Céline Labruyère,<sup>a</sup> Olivier Talon,<sup>b</sup> Nathalie Berezina,<sup>b\*</sup> Eric Khouzakoun<sup>b</sup> and Christine Jérôme<sup>a</sup>*Received (in XXX, XXX) Xth XXXXXXXXX 20XX, Accepted Xth XXXXXXXXX 20XX*

DOI: 10.1039/b000000x

The preparation of cyclic butylene succinate lactone *via* catalytic depolymerization of poly(butylene succinate) oligomers (OPBS) and conversion to high-molecular weight poly(butylene succinate) (PBS) *via* ring-opening polymerization (ROP) is described. OPBS was first synthesized by two-stage melt polycondensation, purified and characterized by size exclusion chromatography (SEC). Then, it was  
10 depolymerized under reduce pressure in a glass oven and the volatile fraction (VF) was collected and characterized. The butylene succinate lactones obtained by intramolecular transesterification were characterized by nuclear magnetic resonance (<sup>1</sup>H NMR) and mass spectrometry (MS). Their further successful ROP polymerization within 24 hours afforded the desired PBS with  $M_w$  of 65 000 g/mol and  $\bar{D}$  of 2.2.

Cite this: DOI: 10.1039/c0xx00000x

www.rsc.org/xxxxxx

## ARTICLE TYPE

## Introduction

Nowadays, aliphatic polyesters are among the most promising materials to replace conventional plastics for several reasons. In addition to their high performance, they can be processed on conventional equipment at conventional temperature. Those polyesters exhibit controllable biodegradability and their monomers are more and more produced from renewable feedstock. One of these, poly(butylene succinate) (PBS) is a white crystalline thermoplastic exhibiting melting point and toughness similar to low-density poly(ethylene) (LDPE), glass transition temperature and tensile strength between poly(ethylene) (PE) and poly(propylene) (PP) and stiffness between LDPE and high-density polyethylene (HDPE)[1, 2]. PBS is synthesized through a two-stage melt polycondensation process (esterification and polycondensation) of 1,4-butanediol and succinic acid. As these step-growth polymerizations usually reach oligomers, chain extenders, *e.g.* hexamethylene diisocyanate, are required to reach processable polymers with  $\overline{M}_n$  and  $\overline{M}_w$  respectively of about 40 000 and 100 000 g/mol [2-4].

An alternative to the condensation polymerization followed by extension step is the chain-growth polymerization from lactone monomer: ring-opening polymerization (ROP). This polymerization procedure is known to give both higher controlled molecular weights and higher monomer conversions without byproducts. The synthesis of cyclic mono- or multi-mer of aliphatic polyester (PLA, PET, PBT...) were reported using different chemical reactions such as condensation or thermal catalytic depolymerization [5-7] and are daily used in industry to produce high molecular weight polymer PLA [8, 9]. The cyclic oligomers production from the thermal depolymerization of polyesters could also be a way to recycle them [10]. In the special case of PBS, mono- and multi-mer lactones were already observed in literature. Indeed, they have been known for some time, being formed in the parent condensed polymers at concentrations of 1-3% [11-13] and they were observed as byproduct of (thermal, thermo or photo-oxidative) degradation of PBS [4, 14-20]. Nevertheless, they were not much isolated and their potential for polymerization was not studied. To date, and as far as we know, only Matsumura's laboratory [20-23] has investigated the synthesis of butylene succinate cycles with the aim of polymerizing them. Matsumura obtained oligomeric lactones with different size by lipase-catalyzed degradation of oligo-PBS and re-polymerized them by ROP with the same enzyme.

In this study, for the first time PBS lactone monomers were successfully chemically synthesized and further polymerized by ROP in bulk.

## Keywords

Poly(ester); ring-opening polymerization; thermal depolymerization; cyclic oligomers; chemical recycling, PBS.

## Materials and methods

## Chemicals

Succinic acid (99%, Merck), 1,4-butanediol (p.s., Merck), ZnO (99.9%, Sigma-Aldrich), acetone (p.a., Merck), toluene (technical grade, VWR), chloroform (technical grade, VWR), tin(II) 2-ethylhexanoate ( $\text{Sn}(\text{Oct})_2$ ) (96 %, Alfa Aesar), titanium (IV) tetraisopropoxide (97%, Sigma-Aldrich), GC derivatization agent (BSTFA + TMCS, 99:1; Supelco, Aldrich) were used as received without further purification.

## Synthesis of poly(butylene succinate) oligomers (OPBS)

Synthesis of aliphatic oligomeric polyesters was performed following the two-stage melt polycondensation method (esterification and polycondensation) in a steel batch reactor. Succinic acid (SA) and 1,4-butanediol (BDO) in a molar ratio 1/1.12 and the catalyst titanium (IV) tetraisopropoxide ( $5.2 \cdot 10^{-3}$  mol /mol SA) were charged into the stainless steel vessel equipped with a condenser. After three vacuum-argon cycles to remove oxygen, the reaction mixture was heated at 185 °C under argon and stirring at a constant speed (50 rpm) was applied. This first step (esterification by condensation of monomers) is considered to be complete after the collection of theoretical amount of  $\text{H}_2\text{O}$  (2 h), which was removed from the reaction mixture by distillation and collected in a graduated cylinder. In the second step of polycondensation, a vacuum was applied slowly over a time period of about 3 h at 220 °C. After the end of the polycondensation reaction, the OPBS (solubilized in  $\text{CHCl}_3$ ) was purified by extraction with HCl solution (1 M) and precipitated in THF and finally characterized by SEC.

## Synthesis of butyl succinate lactone (BSL)

OPBS was depolymerized in a Glass Oven B-585 Kugelrohr (bulb to bulb distillatory) supplied by Büchi at 290 °C under controlled reduced pressure (10 mbar) during 1 h. Typically, 8 g of polymer and ZnO (1 wt%), both previously dried 16 h at 60 °C under reduced pressure, were introduced in the 20 mL end-bulb placed in the oven and the volatile fractions (VF) were collected in 20 mL mid-bulb placed outside. The compositions of the volatile fractions were evaluated by GC-(FID or MS) (on BSTFA derivatized samples), MS, and proton nuclear magnetic resonance ( $^1\text{H}$  NMR). The butylene succinate lactone monomers were purified from the other by-products of VF by solubilization in toluene.

The spectral data of butyl succinate cyclic dimer (DBSL) cyclic butylene succinate ester are shown to be representative.  $^1\text{H}$  NMR ( $\text{CDCl}_3$ ,  $\delta$  in ppm): 4.05 (triplet, 4H,  $-\text{CH}_2\text{OCO}$ ), 2.64 (triplet, 4H,  $-\text{CH}_2-\text{COO}-$ ), 1.71 (quintuplet, 4H,  $-\text{OCH}_2-\text{CH}_2-\text{CH}_2-\text{CH}_2-\text{O}-$ ).

## Polymerization of BSL by ROP

Typically, 0.15 g of BSL dimer ( $0.4 \cdot 10^{-3}$  mol), previously dried 16 h at 80 °C under reduced pressure,  $\text{Sn}(\text{Oct})_2$  (10  $\mu\text{L}$  of a 0.015

M toluene solution,) octanol (0.1 mL of a 0.3 M toluene solution) and toluene (2 mL) were introduced in a two-necked flask equipped with a three-way stopcock and a magnetic stirring bar in a glove box. The mixture was then heated at 115 °C (the temperature was kept at rather low level to avoid the transesterification issues) under stirring to homogenize the medium then the solvent was evaporated. After 24 hours, the polymerization mixture was cooled down to room temperature and dissolved in chloroform, then the solution was precipitated in excessive acetone. The obtained polymer was characterized by SEC and <sup>1</sup>H NMR.

### Analyses

Size-exclusion chromatography (SEC) was performed in CHCl<sub>3</sub> at 30 °C using an Agilent liquid chromatograph equipped with an Agilent degasser, an isocratic HPLC pump (flow rate = 1 mL min<sup>-1</sup>), an Agilent autosampler (loop volume = 200 μL, solution conc. = 2.5 mg mL<sup>-1</sup>), an Agilent-DRI refractive index detector and three columns: a PL gel 10 μm guard column and two PL gel Mixed-D 10 μm columns (linear columns for separation of  $M_w$  PS ranging from 500 to 10<sup>6</sup> g mol<sup>-1</sup>). Polystyrene standards were used for calibration.

<sup>1</sup>H-NMR spectrum were recorded on solutions prepared in CDCl<sub>3</sub> using a Bruker AMX-500 apparatus at a frequency of 500 MHz.

Gas chromatography system (Shimadzu, GC-2010) equipped with a flame ionization detector (GC-FID) and a fused silica capillary separation column (Macherey Nagel, Optima 5; 30 m long x 0.25 mm). The identification of the peaks on the chromatograms was carried out using a gas chromatography–mass spectrometry (GC–MS) system (Shimadzu, QP2010) with an electron impact ionization (EI) at 70 eV and separation column (Macherey Nagel, Optima 5 MS; 30 m long x 0.25 mm). Carrier gas is Helium. The temperature program on both GC was inspired from literature [14]: temperature of the injector set at 340 °C, of the column set at 50 °C for 5 min, then programmed up to 340 °C at a rate of 5 °C/min, and held at 340 °C for 25 min.

The MS experiments were performed on a Waters QToF2 mass spectrometer at the University of Mons – Mass Spectrometry Research Group. The sample solutions were delivered to the ESI source by a Harvard Apparatus syringe pump at a flow rate of 5 μL/min. Typical ESI conditions were: positive ion mode; capillary voltage, 3.1 kV; cone voltage, 40 V; source temperature, 80 °C; desolvation temperature, 120 °C. Dry nitrogen was used as the ESI gas. The quadrupole was set to pass ions from m/z 100 to 1500 and all ions were transmitted into the pusher region of the time-of-flight (TOF) analyzer for mass-analysis with 1 s integration time. Data were acquired in continuum mode until acceptable average data were obtained (typically 20 scans). The sample solutions were prepared as follow: 1 mg of solid sample was dissolved in 1 mL of acetonitrile (HPLC grade) and 5 μL of a NaI solution (1 mg/mL) in acetonitrile were added to the acetonitrile solution before direct infusion.


## Results and discussion

### Synthesis and characterization of polyesters

The OPBS used in this study was prepared by a two steps melt polycondensation process. In the first stage (esterification), succinic acid reacted with 1,4-butanediol (DBO) catalyzed by

titanium (IV) tetraisopropoxide to form oligomers and water was eliminated as byproduct. As DBO is rather volatile, it was used in a small excess in order to produce alcohol/acid  $\alpha,\omega$ -terminated PBS.


In the second stage (polycondensation), the prepared oligomers condensed at a higher temperature with the application of vacuum. To prevent the risk of overestimating the yield in volatile fraction (VF) in the following degradation reaction, the OPBS was successfully purified through extraction with acid and precipitation in THF. The crude oligomer was light yellow and became white after purification. Characterization by size-exclusion chromatography (SEC) of the OPBS shows that it contains less small molecules as succinic acid and 1,4-butanediol (Fig. 1) after purification. ( $M_n = 6\ 600$  g/mol and  $D = 1.62$ ).

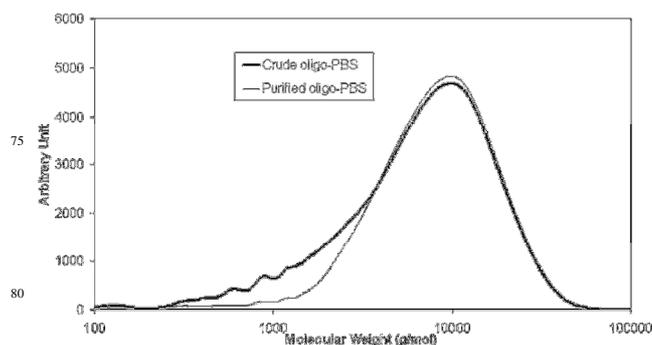


**Figure 1:** Chromatogram of crude and purified oligo-PBS

### Synthesis and characterization of BSL

The oligo-PBS was decomposed in a bulb to bulb distillatory with ZnO (1 wt%) at 290 °C and 10 mbar. This bulb tube oven really suits for this kind of reaction: the polymer is decomposed in the end-bulb placed in the oven and the vapor phases are collected in the mid-bulb placed outside the oven and cooled down by the air (Fig. 2). The VF is a white crystalline solid and the weight yield is around 14 wt%.

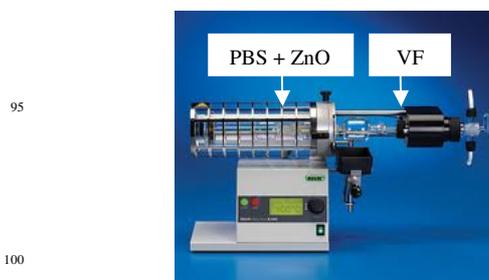


**Figure 2:** Glass Oven B-585 Kugelrohr and localization of reagents and products

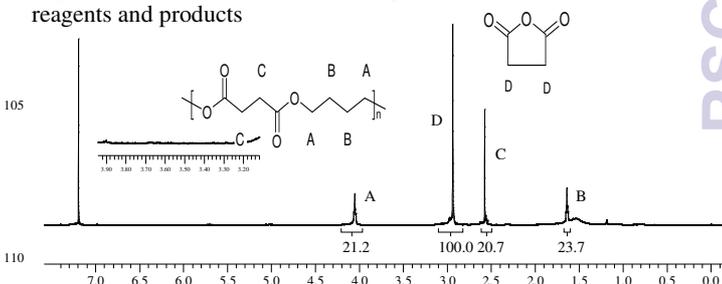

**Figure 3:** <sup>1</sup>H NMR spectrum of VF of depolymerization of OPBS (CDCl<sub>3</sub>)

The composition of the VF was obtained by  $^1\text{H}$  NMR spectrum (Fig. 3). It contains an important quantity of succinic anhydride (SAN) (2.9 ppm) (4.7 mol/mol of BS unit) and products including butylene succinate groups (4.1; 2.6 and 1.6 ppm). The SAN could be the result of the direct dehydration of the succinic acid formed as byproduct of degradation. The analysis supports the cyclic structure of butylene succinate molecules. Indeed, linear molecules should show a peak at 3.6 ppm for terminal hydroxyl methylene proton ( $\text{CH}_2\text{-OH}$ ) or an integration value of peak at 2.6 superior to those of peaks at 4.1 and 1.6 ppm for terminal succinic acid proton ( $\text{CH}_2\text{-COOH}$ ) but none of those observations can be made at the above mentioned spectrum. However, NMR spectroscopy provides structural information only on functional groups or segments of molecules and not on the full molecule. It is so inappropriate to detect the different lactones as a function of their size. Mass spectrometry (MS) is more adapted to identify these molecules including butylene succinate functions. Indeed, it reveals (Fig. 4) that the VF is composed of several products listed in Tab. 1: SAN and butylene succinate lactones with 1 to 3 butylene succinate groups. In the present publication, we call them MBSL, DBSL, TriBSL and TetraBSL for mono-; di-; tri- or tetra- butylene succinate lactone (IUPAC nomenclature would be 1,6,11,16-tetraoxacycloeicosane-2,5,12,15-tetraone [13] for DBSL). Because of the principle of analysis and of the sensibility of MS, the proportion of components of the VF observed by MS is different from these observed in  $^1\text{H}$  NMR spectrum.

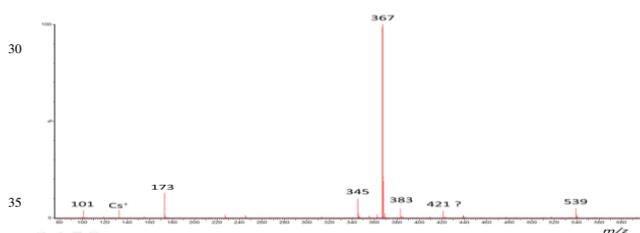


**Figure 4:** ESI-ToF analyses of VF of depolymerization of oligo-PBS

**Table 1:** Identification of ions observed in ESI-ToF analyses of VF


m/z	Identification	Chemical structure
101	Succinic anhydride / $\text{H}^+$	
173	MBSL / $\text{H}^+$	
345	DBSL / $\text{H}^+$	
367	DBSL / $\text{Na}^+$	
383	DBSL / $\text{K}^+$	
539	TriBSL / $\text{Na}^+$	

These lactones are obtained by intramolecular transesterification (Fig. 5) of the oligo(butylene succinate) chains (several mechanisms can be involved concomitantly, including alcoholysis or acidolysis by chain ends, as well as ester-ester exchange reactions, all leading to the same products; Fig. 5 only illustrates the latter). They are produced in different proportion due to their ease of formation and to their stability; in the present case the dimer is predominant. Spanagel and Carothers [24] already observed this phenomenon and concluded that for repeat unit lengths of 8, 9, 10 or 11 chain atoms the dimeric esters tended to predominate in oligomer mixtures obtained. Stoll and Stoll-Comte [25] have suggested that this is due to a steric hindrance caused by mutual repulsions of peripheral hydrogens which are crowded against one another.

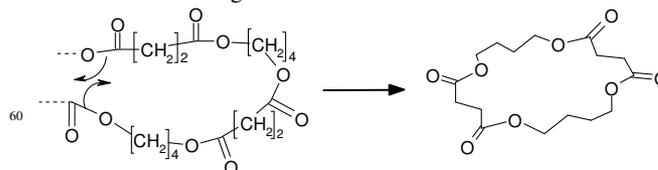

**Figure 5:** intramolecular transesterification leading to dibutylsuccinate lactone DBSL

The crude VF was also analyzed by gas chromatography (GC) because this technique is more adapted to individually quantify the components of the VF. GC-MS was first used to attribute molecules to elution peaks then GC-FID was done to improve quantification (Fig. 6). All the peaks up to 12 minutes are attributed to the solvent and the derivatization agent. The product observed at 22 minutes is succinic acid (obtain by reaction of succinic anhydride with the derivatization agent) and the DBSL appears at 46 minutes. The other cycles are not observed because of their small quantities.

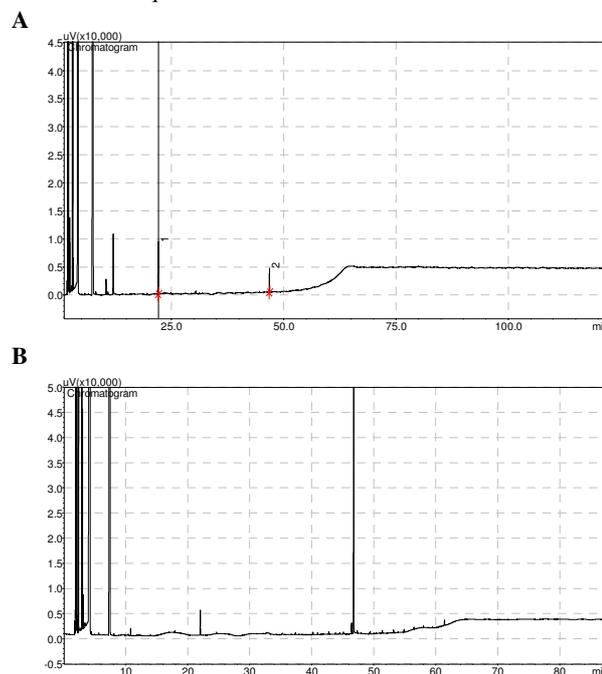

**Figure 6:** GC-FID chromatograms of crude VF (A) and purified lactone (B).




## Notes and references

<sup>a</sup> Center for Education and Research on Macromolecules (CERM), University of Liege, Sart-Tilman, B-4000 Liège, Belgium

<sup>b</sup> Materia Nova, Ghislenghien, 1 Rue des Foudriers, 7822 Ghislenghien, Belgium. Tel. +32 68 27 47 74; E-mail: nathalie.berezina@materianova.be

- 1 Y. F. Shih, and Y.-C. Chieh, *Macromol. Th. Simul.*, 2007, **16**, 101
- 2 J. Xu, J. and B.-H. Guo, *Biotechnol. J.*, 2010, **5**, 1149
- 3 N. Jacquel, N., et al., *J. Polym. Sci. A: Polym. Chem.*, 2011, **49**, 5301
- 4 P. Rizzarelli and S. Carroccio, *Polym. Degrad. Stability*, 2009, **94**, 1825
- 5 F.D. Kopinke, et al., *Polym. Degrad. Stability*, 1996, **53**, 329
- 6 D.J. Brunelle, et al., *Macromolecules*, 1998, **31**, 4782
- 7 N. González-Vidal, et al., *Macromolecules*, 2008, **41**, 4136
- 8 P. Coszach, and P.A. Mariage, *Method for obtaining lactide*. US 2011/0155557 A1, 2011, Futero S.A.
- 9 T.P. Coupin, P. Coszach, and D. Hottos, *Isotactic polylactic acid and method for producing same*. JP2012515245, 2010, Futero S.A.
- 10 N. Berezina, N. Landercy, P.A. Mariage and B. Moreau, *World J. Org. Chem.*, 2013, **1**, 20
- 11 T. Yashiro, H.R. Kricheldorf, and S. Huijser, *Macromol. Chem. Physics*, 2009, **210**, 1607
- 12 A.C. Davis, *Polymer*, 1977, **18**, 305
- 13 K. Noguchi, H. Kondo, Y. Ichikawa, J. Washiyama and K. Okuyama, *Acta Crystallographica C Crystal Structure Commun.*, 2006, **62**, 528
- 14 H. Sato, et al., *Polym. Degrad. Stability*, 2001, **73**, 327
- 15 D.N. Bikiaris, et al., *Polym. Degrad. Stability*, 2007, **92**, 525
- 16 K. Chrissafis, K.M. Paraskevopoulos, and D.N. Bikiaris, *Polym. Degrad. Stability*, 2006, **91**, 60
- 17 S. Carroccio, et al., *Macromolecules*, 2004, **37**, 6576
- 18 S. Carroccio, P. Rizzarelli, and C. Puglisi., *Rapid Commun. Mass Spectrometry*, 2000, **14**, 1513
- 19 K. Chrissafis, K.M. Paraskevopoulos, and D.N. Bikiaris, *Thermochimica Acta*, 2005, **435**, 142
- 20 Y. Tsuneizumi, Y., et al., *Polym. Degrad. Stability*, 2010, **95**, 1387
- 21 A. Kondo, et al., *Macromol. Biosci.*, 2008, **8**, 533
- 22 S. Okajima, et al., *Biomacromolecules*, 2003, **4**, 1514
- 23 S. Sugihara, K. Toshima, and S. Matsumura, *Macromol. Rapid Commun.*, 2006, **27**, 203
- 24 E.W. Spanagel, and W.H. Carothers, *J. Am. Chem. Soc.*, 1935, **57**, 929
- 25 M. Stoll, and G. Stoll-Comte, *Helvetica Chimica Acta*, 1930, **13**, 1185
- 26 J.F. Carpentier, *Macromol. Rapid Commun.*, 2010, **31**, 1696
- 27 S. Ren, J. Ling, and Z. Shen, *Europ. Polym. J.*, 2004, **40**, 647
- 28 K.S. Bisht et al., *Macromolecules*, 1997, **30**, 7735
- 29 C. Jerome, and P. Lecomte, *Adv. Drug Deliv. Rev.*, 2008, **60**, 1056
- 30 S. Kobayashi, *Macromol. Symp.*, 2006, **240**, 178

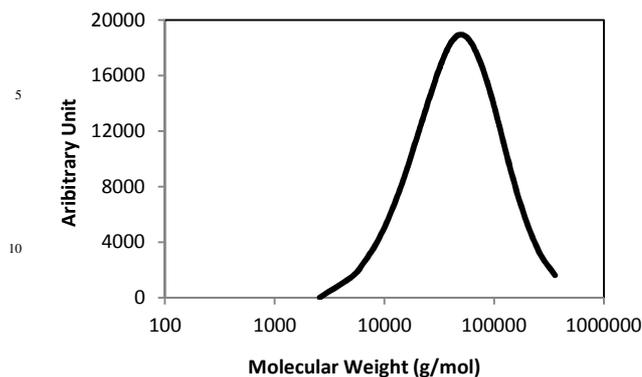

15 **Figure 8:** Chromatogram of PBS obtained by ROP

Several kinds of cyclic monomers, such as lactones [26], anhydrides [27], or carbonates [28] can be used for ROP. Several kinds of catalysts were also already reported, e.g. metallic complexes [29] and enzymes [30]. The size of the ring of the cyclic monomer used is another important parameter to consider, it should be both, stable and reactive, enough to allow successful polymerization. Thus, the 6-membered lactide for the synthesis of PLA or the 7-membered  $\epsilon$ -caprolactone for the synthesis of PCL are nice examples of suitable cyclic monomers. In our case, the 20-membered DBSL was found to be the major product of the depolymerization process. This macrocycle is less easy to handle for both its production and purification; however the results obtained for its first ROP polymerization show that it worth the effort.

## Conclusions


The development of valuable routes for the synthesis of high molecular weight PBS is crucial to reach desired properties of this bioplastic. In this study, and for the first time, PBS was obtained by chemically catalyzed ROP from previously prepared, through oligomers depolymerization, cyclic precursors. This first attempt of ROP polymerization for the preparation of PBS reached the  $\overline{M}_w$  of 65 000 g/mol, which is comparable to the best results obtained after chain extension for the polycondensation route [2].

The elucidation of the depolymerization process of oligomers and the identification of the cyclic precursors represent the main pavement on the road to the widespread usage of the ROP technique for the preparation of higher molecular weight PBS in the near future.

## Acknowledgements

Financial support from Wallonia and European Commission (SINOPLISS) is gratefully acknowledged. The authors wish to thank Dr P. Gerbaux from CISMa and Dr. R. Mincheva from LPCM of UMons (Belgium) for respectively the MS and <sup>1</sup>H-NMR measurements. Many thanks are due to Dr. Ing. C. Frederix and Dr. C. Cateto Borges for supporting the preliminary researches and to Dr. B. Grignard for constructive discussions. Technical support of N. Landercy and J. Mariage was also greatly appreciated.

## Table of content entry

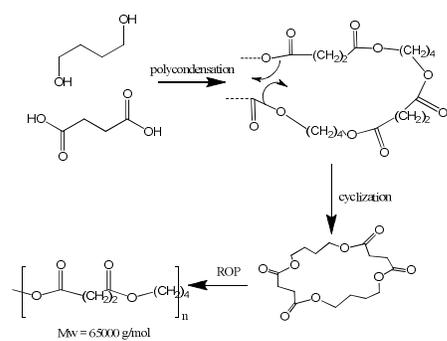

First chemical ROP for the production of PBS with high  $\overline{M}_w$ .