



**Factors controlling the photoresponse of copper(I) diimine dyes containing hole-transporting dendrons in dye-sensitized solar cells: substituent and solvent effects**

Journal:	<i>RSC Advances</i>
Manuscript ID:	RA-ART-04-2014-003700.R1
Article Type:	Paper
Date Submitted by the Author:	23-Apr-2014
Complete List of Authors:	Housecroft, Catherine; University of Basel, Department of Chemistry Constable, Edwin; University of Basel, Departement Chemie Bozic-Weber, Biljana; University of Basel, Department of Chemistry Brauchli, Sven; University of Basel, Chemistry Hostettler, Nik; University of Basel, Department of Chemistry Zampese, J.; University of Basel, Chemistry

## ARTICLE

# Factors controlling the photoresponse of copper(I) diimine dyes containing hole-transporting dendrons in dye-sensitized solar cells: substituent and solvent effects

Cite this: DOI: 10.1039/x0xx00000x

Received 00th January 2012,  
Accepted 00th January 2012

DOI: 10.1039/x0xx00000x

www.rsc.org/

Sven Y. Brauchli,<sup>a</sup> Biljana Bozic-Weber,<sup>a</sup> Edwin C. Constable,<sup>\*a</sup> Nik Hostettler,<sup>a</sup> Catherine E. Housecroft,<sup>\*a</sup> Jennifer A. Zampese

Two series of 2,2'-bipyridine (bpy) ligands bearing different 6,6'-substituents (Me, <sup>n</sup>Bu, <sup>iso</sup>Bu, neryl, Ph and 2-naphthyl) and carrying first-generation (ligands **1–6**) or second-generation (ligands **7–12**) hole transporting dendrons in the 4,4'-positions are reported. They have been incorporated into homoleptic copper(I) complexes [CuL<sub>2</sub>][PF<sub>6</sub>]. FTO/TiO<sub>2</sub> electrodes functionalized with the anchoring ligand ((6,6'-dimethyl-[2,2'-bipyridine]-4,4'-diyl)bis(4,1-phenylene))bis(phosphonic acid), **13**, were dipped in either CH<sub>2</sub>Cl<sub>2</sub> or acetone solutions of [CuL<sub>2</sub>][PF<sub>6</sub>] to produce two series of surface-bound heteroleptic dyes. Their performances in dye-sensitized solar cells (DSCs) are assessed. Solid-state absorption spectra of dye-functionalized electrodes show that dye uptake is greater if acetone is used in the dye-dipping cycle rather than CH<sub>2</sub>Cl<sub>2</sub>, and the DSCs made using acetone generally perform better than analogous DSCs made using CH<sub>2</sub>Cl<sub>2</sub>. Using acetone-dipping solutions, the best DSC efficiencies are obtained with the second-generation dyes [Cu(**13**)(L)]<sup>+</sup> (L = **7–11** with Me, <sup>n</sup>Bu, <sup>iso</sup>Bu, hexyl, Ph groups); [Cu(**13**)(**12**)]<sup>+</sup> (**12** contains 2-naphthyl groups in the 6,6'-positions) and its first-generation analogue [Cu(**13**)(**6**)]<sup>+</sup> perform poorly. When CH<sub>2</sub>Cl<sub>2</sub> is used in the dipping cycle, DSCs with dyes [Cu(**13**)(**1**)]<sup>+</sup> and [Cu(**13**)(**7**)]<sup>+</sup> (6,6'-Me<sub>2</sub>-substituted) show the highest V<sub>oc</sub>, J<sub>sc</sub> and η values, and EQE spectra confirm electron injection over wider energy range than for other dyes. For CH<sub>2</sub>Cl<sub>2</sub> in the dipping cycle (but not for acetone), [Cu(**13**)(**5**)]<sup>+</sup> (6,6'-Ph<sub>2</sub>-substituted) performs as well as [Cu(**13**)(**1**)]<sup>+</sup>. The overall results of the study indicate that a combination of small 6,6'-substituents and acetone in the dye-dipping cycle lead to the best performing dyes.


## Introduction

Conventional Grätzel dye-sensitized solar cells (DSCs) incorporate ruthenium(II) complexes as photosensitizers.<sup>1</sup> Our ongoing focus on DSCs containing copper(I) complexes as sensitizers is predicated both upon their possessing similar photophysical properties to ruthenium(II) complexes,<sup>2,3</sup> and upon the greater abundance of copper than ruthenium in the Earth. Sauvage and co-workers pioneered the introduction of copper(I) complexes in DSCs,<sup>4</sup> and more recent uses of copper(I) in dyes in DSCs have been surveyed by Robertson<sup>5</sup> and by us.<sup>6</sup> The recent report of an remarkable photoconversion efficiency of 4.66% for a DSC with a heteroleptic copper(I) dye containing 6,6'-dimesityl-2,2'-bipyridine-4,4'-dicarboxylic acid as the anchoring ligand and a 2,2'-bipyridine ancillary ligand with triphenylamino domains underlines the potential of

copper(I) sensitizers.<sup>7</sup> In the latter case, the efficiency was enhanced by using the co-adsorbant chenodeoxycholic acid.

We recently described the syntheses and characterization of the two copper(I) diimine complexes incorporating ligands containing first- and second-generation hole-transport dendrons (Scheme 1). For both ligands, semi-empirical MO calculations at the PM3 level showed that the HOMOs (degenerate set) and LUMO are localized on the dendron and 2,2'-bipyridine (bpy) metal-binding unit, respectively.<sup>8</sup> By applying a ligand exchange strategy,<sup>9</sup> we assembled dye-sensitized solar cells (DSCs) containing dyes [Cu(L<sub>ancillary</sub>)(L<sub>anchor</sub>)]<sup>+</sup> anchored on mesoporous TiO<sub>2</sub>. The combination of the hole-transport substituents in the ancillary ligands with the anchoring ligand 6,6'-dimethyl-2,2'-bipyridine-4,4'-bis(phosphonic acid) resulted in power-to-current conversion efficiencies of 20.7% relative to 100% for N719 measured under the same conditions in fully

masked DSCs.<sup>8</sup> We have also established that the photoresponse of a  $[\text{Cu}(\text{L}_{\text{ancillary}})(\text{L}_{\text{anchor}})]^{\dagger}$  dye can be significantly improved by introducing an aromatic linker between the bpy and phosphonate domains of the anchoring ligand, and by replacing the 6- and 6'-methyl substituents in the ancillary ligand by isobutyl or phenyl groups.<sup>10</sup> We now describe a systematic extension of these studies in which the ancillary bpy ligands (**1–12** in Scheme 2) contain (i) first- or second-generation hole-transport dendrons and (ii) alkyl or aromatic substituents of varying steric bulk in the 6,6'-positions. The anchoring ligand in the  $[\text{Cu}(\text{L}_{\text{ancillary}})(\text{L}_{\text{anchor}})]^{\dagger}$  dyes is **13** (Scheme 3) which has shown the greatest potential in recent studies. The heteroleptic complex is assembled using ligand exchange between surface-anchored ligand  $\text{L}_{\text{anchor}}$  and a homoleptic complex  $[\text{Cu}(\text{L}_{\text{ancillary}})_2]^{\dagger}$ . This approach circumvents the need to isolate the heteroleptic species (which is often not possible because of the rapid establishment of statistical solution equilibria between homo- and heteroleptic species). Characterisation of related surface species has previously been carried out.<sup>9</sup>

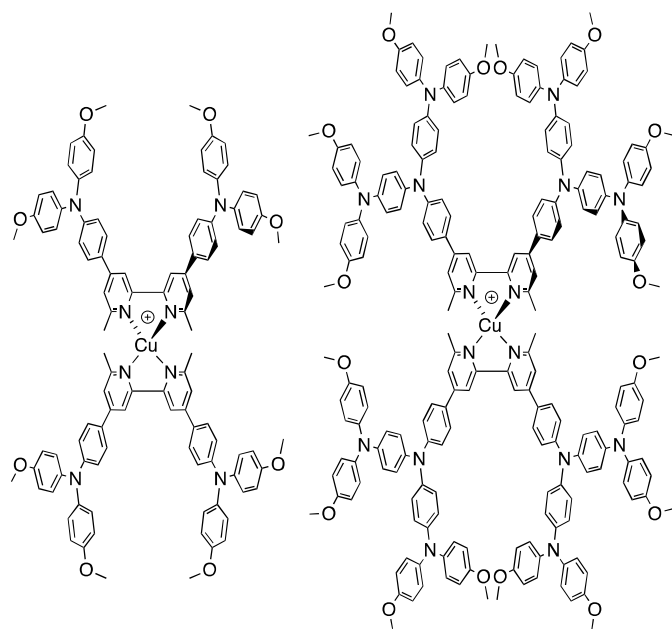

Scheme 1. Homoleptic copper(I) diimine complexes with ligands containing first- and second-generation hole-transport dendrons.<sup>8</sup>

## Experimental

### General

A Bruker Avance III-500 NMR spectrometer was used to record  $^1\text{H}$  and  $^{13}\text{C}$  NMR spectra, and chemical shifts were referenced to residual solvent peaks with respect to  $\delta(\text{TMS}) = 0$  ppm. Solution absorption spectra were recorded with a Cary 5000 spectrophotometer and FT-IR spectra of solid samples on a Perkin Elmer UATR Two spectrometer. MALDI-TOF and electrospray ionization (ESI) mass spectra were recorded on

Bruker Daltonics microflex and Bruker esquire 3000<sup>plus</sup> instruments, respectively. Electrochemical measurements were made using a CH Instruments 900B potentiostat with glassy carbon, platinum wire and silver wire as the working, counter, and reference electrodes, respectively. Substrates were dissolved in HPLC grade  $\text{CH}_2\text{Cl}_2$  (ca.  $10^{-4}$  to  $10^{-5}$  mol  $\text{dm}^{-3}$ ) containing 0.1 mol  $\text{dm}^{-3}$   $[\text{nBu}_4\text{N}][\text{PF}_6]$  as the supporting electrolyte; all solutions were degassed with argon.  $\text{Cp}_2\text{Fe}$  was used as internal reference.

The external quantum efficiency (EQE) measurements were made using a Spe-Quest quantum efficiency instrument from Rera Systems (Netherlands) equipped with a 100 W halogen lamp (QTH) and a lambda 300 grating monochromator (Lot Oriol). The monochromatic light was modulated to 3Hz using a chopper wheel (ThorLabs). The cell response was amplified with a large dynamic range IV converter (CVI Melles Griot) and then measured with a SR830 DSP Lock-In amplifier (Stanford Research).

Compounds **1** and **7**,<sup>8</sup> anchoring ligand **13**,<sup>10</sup>  $[\text{Cu}(\text{MeCN})_4][\text{PF}_6]$ ,<sup>11</sup>  $[\text{Cu}(\mathbf{1})_2][\text{PF}_6]$ <sup>8</sup> and  $[\text{Cu}(\mathbf{7})_2][\text{PF}_6]$ <sup>8</sup> were prepared as previously reported. The syntheses and characterization data of the ligands and the numbering scheme for the NMR assignments are given in the ESI.†

### $[\text{Cu}(\mathbf{2})_2][\text{PF}_6]$

$[\text{Cu}(\text{MeCN})_4][\text{PF}_6]$  (35.2 mg, 0.094 mmol) was reacted with **2** (165 mg, 0.189 mmol) in a mixture of MeCN (15 mL) and  $\text{CH}_2\text{Cl}_2$  (15 mL). The solution turned red immediately and was stirred overnight at room temperature. Then, the volume of the solvent was reduced *in vacuo* and the product was precipitated by addition of  $\text{Et}_2\text{O}$ . The solid was separated by filtration, was washed with  $\text{Et}_2\text{O}$  and was dried in a stream of air.  $[\text{Cu}(\mathbf{2})_2][\text{PF}_6]$  was isolated as a red solid (145 mg, 0.074 mmol, 78%).  $^1\text{H}$  NMR (500 MHz,  $\text{CDCl}_3$ )  $\delta/\text{ppm}$ : 8.27 (d,  $J = 1.2$  Hz, 4H,  $\text{H}^{\text{A3}}$ ), 7.59 (d,  $J = 8.8$  Hz, 8H,  $\text{H}^{\text{B2}}$ ), 7.57 (d,  $J = 1.2$  Hz, 4H,  $\text{H}^{\text{A5}}$ ), 7.14 (d,  $J = 9.0$  Hz, 16H,  $\text{H}^{\text{C2}}$ ), 7.02 (d,  $J = 8.8$  Hz, 8H,  $\text{H}^{\text{B3}}$ ), 6.89 (d,  $J = 9.0$  Hz, 16H,  $\text{H}^{\text{C3}}$ ), 3.83 (s, 24H, OMe), 2.62 (t,  $J = 8.2$  Hz, 8H,  $\text{H}^{\text{a}}$ ), 1.44 – 1.32 (m, 8H,  $\text{H}^{\text{b}}$ ), 0.90 (tq,  $J = 7.4$  Hz, 8H,  $\text{H}^{\text{c}}$ ), 0.48 (t,  $J = 7.4$  Hz, 12H,  $\text{H}^{\text{d}}$ ).  $^{13}\text{C}$  NMR (126 MHz,  $\text{CDCl}_3$ )  $\delta/\text{ppm}$ : 161.5 ( $\text{C}^{\text{A6}}$ ), 156.8 ( $\text{C}^{\text{C4}}$ ), 152.6 ( $\text{C}^{\text{A2}}$ ), 150.8 ( $\text{C}^{\text{B4}}$ ), 150.2 ( $\text{C}^{\text{B1}}$ ), 139.8 ( $\text{C}^{\text{C1}}$ ), 127.8 ( $\text{C}^{\text{B2}}$ ), 127.5 ( $\text{C}^{\text{C2}}$ ), 127.3 ( $\text{C}^{\text{A4}}$ ), 121.8 ( $\text{C}^{\text{A5}}$ ), 119.4 ( $\text{C}^{\text{B3}}$ ), 116.3 ( $\text{C}^{\text{A3}}$ ), 115.1 ( $\text{C}^{\text{C3}}$ ), 55.7 ( $\text{O}^{\text{Me}}$ ), 39.8 ( $\text{C}^{\text{a}}$ ), 31.9 ( $\text{C}^{\text{b}}$ ), 22.7 ( $\text{C}^{\text{c}}$ ), 13.6 ( $\text{C}^{\text{d}}$ ). IR ( $\tilde{\nu}/\text{cm}^{-1}$ ): 3187 (w), 3036 (w), 2997 (w), 2952 (w), 2924 (w), 2866 (w), 2853 (w), 2832 (w), 1595 (s), 1501 (s), 1462 (m), 1440 (m), 1321 (m), 1237 (s), 1195 (m), 1179 (m), 1102 (m), 1031 (m), 838 (s), 824 (s), 728 (m), 574 (m), 557 (m), 527 (m). ESI MS ( $m/z$ ): 1813.8  $[\text{M}-\text{PF}_6]^+$ , (calc. 1813.8). UV-VIS ( $\text{CH}_2\text{Cl}_2$ ,  $1.0 \times 10^{-5}$  mol  $\text{dm}^{-3}$ ):  $\lambda_{\text{max}}/\text{nm}$  306 ( $\epsilon/\text{dm}^3 \text{mol}^{-1} \text{cm}^{-1}$  67500), 386 (60400), 480 sh (27500). Found: C, 71.69; H, 6.32; N, 5.52;  $\text{C}_{116}\text{H}_{116}\text{N}_8\text{O}_8\text{CuPF}_6$  requires C, 71.13; H, 5.97; N, 5.72.

### $[\text{Cu}(\mathbf{3})_2][\text{PF}_6]$

The method was as for  $[\text{Cu}(\mathbf{2})_2][\text{PF}_6]$  starting with  $[\text{Cu}(\text{MeCN})_4][\text{PF}_6]$  (47.9 mg, 0.128 mmol) and **3** (225 mg,

0.257 mmol) was isolated as red solid (105 mg, 0.054 mmol, 42%). <sup>1</sup>H NMR (500 MHz, CDCl<sub>3</sub>) δ/ppm: 8.27 (s, 4H, H<sup>A3</sup>), 7.60 (d, *J* = 8.5 Hz, 8H, H<sup>B2</sup>), 7.52 (s, 4H, H<sup>A5</sup>), 7.14 (d, *J* = 8.7 Hz, 16H, H<sup>C2</sup>), 7.02 (d, *J* = 8.6 Hz, 8H, H<sup>B3</sup>), 6.89 (d, *J* = 8.4 Hz, 16H, H<sup>C3</sup>), 3.83 (s, 24H, H<sup>OMe</sup>), 2.47 (d, *J* = 7.4 Hz, 8H, H<sup>a</sup>), 1.69 (m, 4H, H<sup>b</sup>), 0.54 (d, *J* = 6.7 Hz, 24H, H<sup>c</sup>). <sup>13</sup>C NMR (126 MHz, CDCl<sub>3</sub>) δ/ppm: 160.5 (C<sup>A6</sup>), 156.9 (C<sup>C4</sup>), 153.1 (C<sup>A2</sup>), 149.9 (C<sup>B1</sup>, C<sup>B4</sup>), 139.9 (C<sup>C1</sup>), 127.9 (C<sup>B2</sup>), 127.6 (C<sup>A4</sup>, C<sup>C2</sup>), 122.8 (C<sup>A5</sup>), 119.5 (C<sup>B3</sup>), 116.5 (C<sup>A3</sup>), 115.1 (C<sup>C3</sup>), 55.7 (C<sup>OMe</sup>), 48.8 (C<sup>a</sup>), 28.5 (C<sup>b</sup>), 22.2 (C<sup>c</sup>). IR (ν̄/cm<sup>-1</sup>): 3190 (w), 3033 (w), 2997 (w), 2953 (w), 2929 (w), 2866 (w), 2834 (w), 1594 (s), 1504 (s), 1463 (m), 1440 (m), 1322 (m), 1289 (m), 1239 (s), 1196 (m), 1179 (m), 1102 (m), 1032 (m), 825 (s), 597 (m), 574 (m), 557 (m), 531 (m). ESI MS (*m/z*): 1814.8 [M-PF<sub>6</sub>]<sup>+</sup> (calc. 1813.8), 875.6 [3+H]<sup>+</sup> (base peak, calc. 875.5). UV-VIS (CH<sub>2</sub>Cl<sub>2</sub>, 1.0 × 10<sup>-5</sup> mol dm<sup>-3</sup>): λ<sub>max</sub>/nm 305 (ε/dm<sup>3</sup> mol<sup>-1</sup> cm<sup>-1</sup> 63000), 393 (58700), 480 sh (28200). Found: C, 70.14; H, 6.30; N, 5.48; C<sub>116</sub>H<sub>116</sub>N<sub>8</sub>O<sub>8</sub>CuPF<sub>6</sub>·H<sub>2</sub>O requires C, 70.48; H, 6.02; N, 5.67.

#### [Cu(4)<sub>2</sub>][PF<sub>6</sub>]

The method was as for [Cu(2)<sub>2</sub>][PF<sub>6</sub>] starting with [Cu(MeCN)<sub>4</sub>][PF<sub>6</sub>] (31.7 mg, 0.085 mmol) and **4** (158 mg, 0.17 mmol). [Cu(4)<sub>2</sub>][PF<sub>6</sub>] was isolated as a red solid (153 mg, 0.074 mmol, 86%). <sup>1</sup>H NMR (500 MHz, CDCl<sub>3</sub>) δ/ppm: 8.26 (d, *J* = 1.4 Hz, 4H, H<sup>A3</sup>), 7.58 (d, *J* = 8.9 Hz, 8H, H<sup>B2</sup>), 7.56 (d, *J* = 1.4 Hz, 4H, H<sup>A5</sup>), 7.13 (d, *J* = 9.0 Hz, 16H, H<sup>C2</sup>), 7.02 (d, *J* = 8.9 Hz, 8H, H<sup>B3</sup>), 6.89 (d, *J* = 9.0 Hz, 16H, H<sup>C3</sup>), 3.83 (s, 24H, H<sup>OMe</sup>), 2.61 (t, *J* = 8.2 Hz, 8H, H<sup>a</sup>), 1.38 (m, 8H, H<sup>b</sup>), 0.95 (m, 8H, H<sup>d</sup>), 0.86 (m, 8H, H<sup>c</sup>), 0.77 (m, 8H, H<sup>e</sup>), 0.62 (t, *J* = 7.3 Hz, 12H, H<sup>f</sup>). <sup>13</sup>C NMR (126 MHz, CDCl<sub>3</sub>) δ/ppm: 161.6 (C<sup>A6</sup>), 156.8 (C<sup>C4</sup>), 152.6 (C<sup>A2</sup>), 150.8 (C<sup>B4</sup>), 150.2 (C<sup>B1</sup>), 139.8 (C<sup>C1</sup>), 127.8 (C<sup>B2</sup>), 127.5 (C<sup>C2</sup>), 127.2 (C<sup>A4</sup>), 121.8 (C<sup>A5</sup>), 119.4 (C<sup>B3</sup>), 116.2 (C<sup>A3</sup>), 115.1 (C<sup>C3</sup>), 55.7 (C<sup>OMe</sup>), 40.1 (C<sup>a</sup>), 31.5 (C<sup>c</sup>), 30.0 (C<sup>b</sup>), 29.5 (C<sup>e</sup>), 22.6 (C<sup>d</sup>), 14.1 (C<sup>f</sup>). IR (ν̄/cm<sup>-1</sup>): 3187 (w), 3036 (w), 2997 (w), 2947 (w), 2924 (w), 2853 (w), 2835 (w), 1594 (s), 1504 (s), 1461 (m), 1327 (m), 1294 (m), 1239 (s), 1200 (m), 1179 (m), 1102 (m), 1031 (m), 838 (s), 825 (s), 729 (m), 663 (m), 573 (m), 557 (m), 535 (m). ESI MS (*m/z*): 1926.0 [M-PF<sub>6</sub>]<sup>+</sup> (base peak, calc. 1924.5), 932.2 [4+H]<sup>+</sup> (calc. 931.5). UV-VIS (CH<sub>2</sub>Cl<sub>2</sub>, 1.0 × 10<sup>-5</sup> mol dm<sup>-3</sup>): λ<sub>max</sub>/nm 306 (ε/dm<sup>3</sup> mol<sup>-1</sup> cm<sup>-1</sup> 65700), 388 (60000), 480 sh (28000). Found: C, 68.93; H, 6.12; N, 5.46; C<sub>124</sub>H<sub>132</sub>N<sub>8</sub>O<sub>8</sub>CuPF<sub>6</sub>·4H<sub>2</sub>O requires C, 69.50; H, 6.58; N, 5.23.

#### [Cu(5)<sub>2</sub>][PF<sub>6</sub>]

The method was as for [Cu(2)<sub>2</sub>][PF<sub>6</sub>] starting with [Cu(MeCN)<sub>4</sub>][PF<sub>6</sub>] (45.9 mg, 0.123 mmol) and **5** (225 mg, 0.246 mmol) in CH<sub>2</sub>Cl<sub>2</sub> (40 mL), and the reaction mixture turned green-black. [Cu(5)<sub>2</sub>][PF<sub>6</sub>] was isolated as a green-black solid (225 mg, 0.11 mmol, 90%). <sup>1</sup>H NMR (500 MHz, CDCl<sub>3</sub>) δ/ppm: 7.95 (d, *J* = 1.2 Hz, 4H, H<sup>A3</sup>), 7.61 (d, *J* = 1.2 Hz, 4H, H<sup>A5</sup>), 7.58 (m, 8H, H<sup>D2</sup>), 7.56 (d, *J* = 8.8 Hz, 8H, H<sup>B2</sup>), 7.17 (d, *J* = 9.0 Hz, 16H, H<sup>C2</sup>), 7.05 (d, *J* = 8.8 Hz, 8H, H<sup>B3</sup>), 7.03 (m, 4H, H<sup>D4</sup>), 6.92 (d, *J* = 9.0 Hz, 16H, H<sup>C3</sup>), 7.03 (m, 8H, H<sup>D3</sup>), 3.84 (s, 24H, H<sup>OMe</sup>). <sup>13</sup>C NMR (126 MHz, CDCl<sub>3</sub>) δ/ppm: 157.0

(C<sup>A6</sup>), 156.9 (C<sup>C4</sup>), 153.6 (C<sup>A2</sup>), 150.9 (C<sup>B4</sup>), 149.9 (C<sup>B1</sup>), 139.8 (C<sup>C1</sup>), 138.7 (C<sup>D1</sup>), 129.2 (C<sup>D4</sup>), 127.8 (C<sup>B2</sup>), 127.7 (C<sup>D2</sup>, C<sup>D3</sup>), 127.6 (C<sup>C2</sup>), 127.2 (C<sup>A4</sup>), 121.5 (C<sup>A5</sup>), 119.4 (C<sup>B3</sup>), 117.8 (C<sup>A3</sup>), 115.1 (C<sup>C3</sup>), 55.7 (C<sup>OMe</sup>). IR (ν̄/cm<sup>-1</sup>): 3036 (w), 2999 (w), 2950 (w), 2931 (w), 2903 (w), 2832 (w), 1593 (s), 1504 (s), 1321 (m), 1238 (s), 1196 (m), 1179 (m), 1104 (m), 1030 (m), 824 (s), 773 (m), 741 (m), 729 (m), 696 (m), 576 (m), 557 (m), 527 (m). ESI MS (*m/z*): 1894.4 [M-PF<sub>6</sub>]<sup>+</sup> (calc. 1893.7), 915.9 [5+H]<sup>+</sup> (base peak, calc. 915.4). UV-VIS (CH<sub>2</sub>Cl<sub>2</sub>, 1.0 × 10<sup>-5</sup> mol dm<sup>-3</sup>): λ<sub>max</sub>/nm 286 (ε/dm<sup>3</sup> mol<sup>-1</sup> cm<sup>-1</sup> 79300), 331 (51600), 401 (55600), 560 sh (7000). Found: C, 73.04; H, 5.39; N, 5.30; C<sub>124</sub>H<sub>100</sub>N<sub>8</sub>O<sub>8</sub>CuPF<sub>6</sub> requires C, 73.05; H, 4.94; N, 5.50.

#### [Cu(6)<sub>2</sub>][PF<sub>6</sub>]

The method was as for [Cu(2)<sub>2</sub>][PF<sub>6</sub>] starting with [Cu(MeCN)<sub>4</sub>][PF<sub>6</sub>] (27.6 mg, 0.074 mmol) and **6** (150 mg, 0.148 mmol) in CH<sub>2</sub>Cl<sub>2</sub> (40 mL). The reaction mixture was green-black, and [Cu(6)<sub>2</sub>][PF<sub>6</sub>] was isolated as a green-black solid (153 mg, 0.068 mmol, 92%). <sup>1</sup>H NMR (500 MHz, CDCl<sub>3</sub>) δ/ppm: 8.22 (s, 4H, H<sup>D1</sup>), 7.62 (m, 4H, H<sup>D3</sup>), 7.57 (m, 8H, H<sup>A5+D5/D8</sup>), 7.43 (d, *J* = 8.6 Hz, 4H, H<sup>D4</sup>), 7.32 (m, 16H, H<sup>A3+B2+D6/D7</sup>), 7.20 (d, *J* = 8.9 Hz, 16H, H<sup>C2</sup>), 7.14 (m, 8H, H<sup>D5/D8+D6/D7</sup>), 7.03 (d, *J* = 8.7 Hz, 8H, H<sup>B3</sup>), 6.95 (d, *J* = 9.0 Hz, 16H, H<sup>C3</sup>), 3.86 (s, 24H, H<sup>OMe</sup>). <sup>13</sup>C NMR (126 MHz, CDCl<sub>3</sub>) δ/ppm: 156.9 (C<sup>C4</sup>), 156.5 (C<sup>A6</sup>), 153.5 (C<sup>A2</sup>), 150.8 (C<sup>B4</sup>), 149.8 (C<sup>B1</sup>), 139.9 (C<sup>C1</sup>), 136.0 (C<sup>D2</sup>), 133.3 (C<sup>D4a/D8a</sup>), 132.2 (C<sup>D4a/D8a</sup>), 128.1 (C<sup>D5/D6/D7/D8</sup>), 127.9 (C<sup>B2</sup>), 127.6 (C<sup>C2</sup>), 127.5 (C<sup>D1+D4+D5/D8</sup>), 127.2 (C<sup>A4</sup>), 127.1 (C<sup>D6/D7</sup>), 126.4 (C<sup>D5/D6/D7/D8</sup>), 125.1 (C<sup>D3</sup>), 121.2 (C<sup>A5</sup>), 119.2 (C<sup>B3</sup>), 117.4 (C<sup>A3</sup>), 115.2 (C<sup>C3</sup>), 55.7 (C<sup>OMe</sup>). IR (ν̄/cm<sup>-1</sup>): 3038 (w), 2999 (w), 2950 (w), 2929 (w), 2905 (w), 2832 (w), 1592 (s), 1504 (s), 1320 (m), 1239 (m), 1196 (m), 1179 (m), 1102 (m), 1032 (m), 824 (s), 781 (m), 755 (m), 741 (m), 576 (m), 557 (m), 533 (m), 477 (m). ESI MS (*m/z*): 2094.8 [M-PF<sub>6</sub>]<sup>+</sup> (base peak, calc. 2093.8), 1016.1 [6+H]<sup>+</sup> (calc. 1015.4). UV-VIS (CH<sub>2</sub>Cl<sub>2</sub>, 1.0 × 10<sup>-5</sup> mol dm<sup>-3</sup>): λ<sub>max</sub>/nm 290 (ε/dm<sup>3</sup> mol<sup>-1</sup> cm<sup>-1</sup> 103100), 340 sh (55400), 408 (58000), 576 (5900). Found: C, 73.11; H, 5.18; N, 4.98; C<sub>140</sub>H<sub>108</sub>N<sub>8</sub>O<sub>8</sub>CuPF<sub>6</sub>·3H<sub>2</sub>O requires C, 73.33; H, 5.01; N, 4.89.

#### [Cu(8)<sub>2</sub>][PF<sub>6</sub>]

The method was as for [Cu(2)<sub>2</sub>][PF<sub>6</sub>] starting with [Cu(MeCN)<sub>4</sub>][PF<sub>6</sub>] (27.6 mg, 73.9 μmol) and **8** (246 mg, 0.148 mmol) in MeCN (18 mL) and CH<sub>2</sub>Cl<sub>2</sub> (18 mL). [Cu(8)<sub>2</sub>][PF<sub>6</sub>] was isolated as a red solid (202 mg, 57.2 μmol, 77%). <sup>1</sup>H NMR (500 MHz, CD<sub>2</sub>Cl<sub>2</sub>) δ/ppm: 8.34 (d, *J* = 1.0 Hz, 4H, H<sup>A3</sup>), 7.65 (d, *J* = 8.8 Hz, 8H, H<sup>B2</sup>), 7.60 (d, *J* = 1.0 Hz, 4H, H<sup>A5</sup>), 7.11 (d, *J* = 8.8 Hz, 8H, H<sup>B3</sup>), 7.07 (d, *J* = 9.0 Hz, 32H, H<sup>D2</sup>), 7.02 (d, *J* = 8.9 Hz, 16H, H<sup>C2</sup>), 6.90 (d, *J* = 8.9 Hz, 16H, H<sup>C3</sup>), 6.84 (d, *J* = 9.0 Hz, 32H, H<sup>D3</sup>), 3.77 (s, 48H, H<sup>OMe</sup>), 2.64 (t, *J* = 8.1 Hz, 8H, H<sup>a</sup>), 1.39 (m, 8H, H<sup>b</sup>), 0.90 (m, 8H, H<sup>c</sup>), 0.48 (t, *J* = 7.3 Hz, 12H, H<sup>d</sup>). <sup>13</sup>C NMR (126 MHz, CD<sub>2</sub>Cl<sub>2</sub>) δ/ppm: 162.0 (C<sup>A6</sup>), 156.5 (C<sup>D4</sup>), 153.1 (C<sup>A2</sup>), 151.0 (C<sup>B4</sup>), 150.5 (C<sup>A4</sup>), 146.2 (C<sup>C4</sup>), 141.4 (C<sup>D1</sup>), 139.9 (C<sup>C1</sup>), 128.2 (C<sup>B2</sup>), 128.0 (C<sup>B1</sup>), 127.2 (C<sup>C2</sup>), 126.9 (C<sup>D2</sup>), 122.1 (C<sup>A5+C3</sup>), 120.1 (C<sup>B3</sup>), 116.8 (C<sup>A3</sup>), 115.2 (C<sup>D3</sup>), 56.0 (C<sup>OMe</sup>), 40.2 (C<sup>a</sup>), 32.4 (C<sup>b</sup>), 23.1 (C<sup>c</sup>), 13.8 (C<sup>d</sup>). IR

( $\tilde{\nu}/\text{cm}^{-1}$ ): 3036 (w), 2997 (w), 2954 (w), 2929 (w), 2905 (w), 2834 (w), 1595 (m), 1497 (s), 1313 (m), 1237 (s), 1033 (m), 824 (s), 576 (m), 539 (m). MALDI-TOF MS ( $m/z$ ): 1728.2 [Cu(8)]<sup>+</sup> (calc. 1726.7), 1664.8 [8+H]<sup>+</sup> (calc. 1664.8). UV-VIS (CH<sub>2</sub>Cl<sub>2</sub>,  $1.0 \times 10^{-5}$  mol dm<sup>-3</sup>):  $\lambda_{\text{max}}/\text{nm}$  225 ( $\epsilon/\text{dm}^3 \text{ mol}^{-1} \text{ cm}^{-1}$  170200), 309 (159600), 340 sh (134200), 480 sh (39600). Found: C, 73.53; H, 6.33; N, 6.03; C<sub>220</sub>H<sub>204</sub>CuF<sub>6</sub>N<sub>16</sub>O<sub>16</sub>P<sub>3</sub>H<sub>2</sub>O requires C, 73.59; H, 5.89; N, 6.24.

#### [Cu(9)<sub>2</sub>][PF<sub>6</sub>]

The method was as for [Cu(2)<sub>2</sub>][PF<sub>6</sub>] starting with [Cu(MeCN)<sub>4</sub>][PF<sub>6</sub>] (31.9 mg, 85.7  $\mu\text{mol}$ ) and **9** (285 mg, 171  $\mu\text{mol}$ ) in a mixture of MeCN (10 mL) and CH<sub>2</sub>Cl<sub>2</sub> (20 mL). [Cu(9)<sub>2</sub>][PF<sub>6</sub>] was isolated as red solid (251 mg, 70.9  $\mu\text{mol}$ , 83%). <sup>1</sup>H NMR (500 MHz, CD<sub>2</sub>Cl<sub>2</sub>)  $\delta/\text{ppm}$ : 8.35 (d,  $J = 1.3$  Hz, 4H, H<sup>A3</sup>), 7.66 (d,  $J = 8.9$  Hz, 8H, H<sup>B2</sup>), 7.56 (d,  $J = 1.3$  Hz, 4H, H<sup>A5</sup>), 7.11 (d,  $J = 8.8$  Hz, 8H, H<sup>B3</sup>), 7.07 (d,  $J = 9.0$  Hz, 32H, H<sup>D2</sup>), 7.02 (d,  $J = 9.0$  Hz, 16H, H<sup>C2</sup>), 6.89 (d,  $J = 9.0$  Hz, 16H, H<sup>C3</sup>), 6.84 (d,  $J = 9.0$  Hz, 32H, H<sup>D3</sup>), 3.77 (s, 48H, H<sup>OMe</sup>), 2.49 (d,  $J = 7.2$  Hz, 8H, H<sup>a</sup>), 1.72 (m, 4H, H<sup>b</sup>), 0.54 (d,  $J = 6.6$  Hz, 24H, H<sup>c</sup>). <sup>13</sup>C NMR (126 MHz, CD<sub>2</sub>Cl<sub>2</sub>)  $\delta/\text{ppm}$ : 160.9 (C<sup>A6</sup>), 156.5 (C<sup>D4</sup>), 153.6 (C<sup>A2</sup>), 151.1 (C<sup>B4</sup>), 150.2 (C<sup>A4</sup>), 146.2 (C<sup>C4</sup>), 141.5 (C<sup>D1</sup>), 139.9 (C<sup>C1</sup>), 128.2 (C<sup>B2</sup>), 127.8 (C<sup>B1</sup>), 127.2 (C<sup>C2</sup>), 126.9 (C<sup>D2</sup>), 123.2 (C<sup>A5</sup>), 122.1 (C<sup>C3</sup>), 120.2 (C<sup>B3</sup>), 117.0 (C<sup>A3</sup>), 115.2 (C<sup>D3</sup>), 56.0 (C<sup>OMe</sup>), 49.2 (C<sup>a</sup>), 28.8 (C<sup>b</sup>), 22.4 (C<sup>c</sup>). IR ( $\tilde{\nu}/\text{cm}^{-1}$ ): 3030 (w), 2997 (w), 2970 (w), 2952 (w), 2926 (w), 2903 (w), 2866 (w), 2834 (w), 1595 (m), 1497 (s), 1312 (m), 1236 (s), 1034 (m), 824 (s), 576 (m), 528 (m). MALDI-TOF MS ( $m/z$ ): 3397.1 [M-PF<sub>6</sub>]<sup>+</sup> (calc. 3391.5), 1729.1 [Cu(9)]<sup>+</sup> (calc. 1726.7), 1666.0 [9+H]<sup>+</sup> (calc. 1664.8). UV-VIS (CH<sub>2</sub>Cl<sub>2</sub>,  $1.0 \times 10^{-5}$  mol dm<sup>-3</sup>):  $\lambda_{\text{max}}/\text{nm}$  225 ( $\epsilon/\text{dm}^3 \text{ mol}^{-1} \text{ cm}^{-1}$  164000), 309 (159900), 340 sh (134000), 480 sh (41400). Found: C, 74.30; H, 6.03; N, 6.49; C<sub>220</sub>H<sub>204</sub>N<sub>16</sub>O<sub>16</sub>CuPF<sub>6</sub> requires C, 74.71; H, 5.81; N, 6.34.

#### [Cu(10)<sub>2</sub>][PF<sub>6</sub>]

The method was as for [Cu(2)<sub>2</sub>][PF<sub>6</sub>] starting with [Cu(MeCN)<sub>4</sub>][PF<sub>6</sub>] (29.5 mg, 79.1  $\mu\text{mol}$ ) and **10** (272 mg, 158  $\mu\text{mol}$ ) in a mixture of MeCN (20 mL) and CH<sub>2</sub>Cl<sub>2</sub> (20 mL). [Cu(10)<sub>2</sub>][PF<sub>6</sub>] was isolated as red solid (242 mg, 66.2  $\mu\text{mol}$ , 84%). <sup>1</sup>H NMR (500 MHz, CD<sub>2</sub>Cl<sub>2</sub>)  $\delta/\text{ppm}$ : 8.34 (d,  $J = 1.2$  Hz, 4H, H<sup>A3</sup>), 7.65 (d,  $J = 8.9$  Hz, 8H, H<sup>B2</sup>), 7.61 (d,  $J = 1.2$  Hz, 4H, H<sup>A5</sup>), 7.11 (d,  $J = 8.8$  Hz, 8H, H<sup>B3</sup>), 7.07 (d,  $J = 9.0$  Hz, 32H, H<sup>D2</sup>), 7.02 (d,  $J = 9.0$  Hz, 16H, H<sup>C2</sup>), 6.90 (d,  $J = 9.0$  Hz, 16H, H<sup>C3</sup>), 6.84 (d,  $J = 9.0$  Hz, 32H, H<sup>D3</sup>), 3.77 (s, 48H, H<sup>OMe</sup>), 2.63 (t,  $J = 8.2$  Hz, 8H, H<sup>a</sup>), 1.40 (m, 4H, H<sup>b</sup>), 0.95 (m, 8H, H<sup>c</sup>), 0.87 (m, 8H, H<sup>c</sup>), 0.79 (m, 8H, H<sup>d</sup>), 0.61 (t,  $J = 7.3$  Hz, 12H, H<sup>f</sup>). <sup>13</sup>C NMR (126 MHz, CD<sub>2</sub>Cl<sub>2</sub>)  $\delta/\text{ppm}$ : 162.1 (C<sup>A6</sup>), 156.5 (C<sup>D4</sup>), 153.1 (C<sup>A2</sup>), 151.0 (C<sup>B4</sup>), 150.5 (C<sup>A4</sup>), 146.2 (C<sup>C4</sup>), 141.4 (C<sup>D1</sup>), 139.9 (C<sup>C1</sup>), 128.2 (C<sup>B2</sup>), 127.9 (C<sup>B1</sup>), 127.1 (C<sup>C2</sup>), 126.9 (C<sup>D2</sup>), 122.2 (C<sup>A5</sup>), 122.1 (C<sup>C3</sup>), 120.2 (C<sup>B3</sup>), 116.6 (C<sup>A3</sup>), 115.2 (C<sup>D3</sup>), 56.0 (C<sup>OMe</sup>), 40.6 (C<sup>a</sup>), 32.0 (C<sup>d</sup>), 30.5 (C<sup>b</sup>), 29.9 (C<sup>c</sup>), 23.0 (C<sup>e</sup>), 14.3 (C<sup>f</sup>). IR ( $\tilde{\nu}/\text{cm}^{-1}$ ): 3037 (w), 2997 (w), 2950 (w), 2928 (w), 2853 (w), 2834 (w), 1594 (m), 1495 (s), 1312 (m), 1235 (s), 1032 (m), 822 (s), 575 (m), 536 (m). MALDI-TOF MS ( $m/z$ ): 1784.7 [Cu(10)]<sup>+</sup> (calc. 1782.8), 1720.9 [10+H]<sup>+</sup> (calc.


1720.9). UV-VIS (CH<sub>2</sub>Cl<sub>2</sub>,  $1.0 \times 10^{-5}$  mol dm<sup>-3</sup>):  $\lambda_{\text{max}}/\text{nm}$  225 ( $\epsilon/\text{dm}^3 \text{ mol}^{-1} \text{ cm}^{-1}$  164100), 309 (155400), 340 sh (131200), 480 sh (42200). Found: C, 73.54; H, 6.25; N, 6.14; C<sub>228</sub>H<sub>220</sub>N<sub>16</sub>O<sub>16</sub>CuPF<sub>6</sub>·4H<sub>2</sub>O requires C, 73.60; H, 6.18; N, 6.02.

#### [Cu(11)<sub>2</sub>][PF<sub>6</sub>]

The method was as for [Cu(2)<sub>2</sub>][PF<sub>6</sub>] starting with [Cu(MeCN)<sub>4</sub>][PF<sub>6</sub>] (27.8 mg, 74.5  $\mu\text{mol}$ ) and **11** (254 mg, 149  $\mu\text{mol}$ ) in CH<sub>2</sub>Cl<sub>2</sub> (40 mL); the reaction mixture turned green-black. [Cu(11)<sub>2</sub>][PF<sub>6</sub>] was isolated as a green-black solid (233 mg, 64.3  $\mu\text{mol}$ , 86%). <sup>1</sup>H NMR (500 MHz, CD<sub>2</sub>Cl<sub>2</sub>)  $\delta/\text{ppm}$ : 8.02 (d,  $J = 1.7$  Hz, 4H, H<sup>A3</sup>), 7.66 (d,  $J = 1.7$  Hz, 4H, H<sup>A5</sup>), 7.63 (m, 16H, H<sup>B2+E2</sup>), 7.14 (d,  $J = 8.5$  Hz, 8H, H<sup>B3</sup>), 7.09 (d,  $J = 9.0$  Hz, 32H, H<sup>D2</sup>), 7.05 (m, 20H, H<sup>C2+E4</sup>), 6.92 (m, 24H, H<sup>C3+E3</sup>), 6.86 (d,  $J = 9.0$  Hz, 32H, H<sup>D3</sup>), 3.78 (s, 48H, H<sup>OMe</sup>). <sup>13</sup>C NMR (126 MHz, CD<sub>2</sub>Cl<sub>2</sub>)  $\delta/\text{ppm}$ : 157.4 (C<sup>A6</sup>), 156.5 (C<sup>D4</sup>), 154.2 (C<sup>A2</sup>), 151.1 (C<sup>B4</sup>), 150.2 (C<sup>A4</sup>), 146.6 (C<sup>C4</sup>), 141.5 (C<sup>D1</sup>), 139.8 (C<sup>C1</sup>), 139.2 (C<sup>E1</sup>), 129.5 (C<sup>E4</sup>), 128.2 (C<sup>E2</sup>), 128.0 (C<sup>E3</sup>), 127.9 (C<sup>B1</sup>), 127.2 (C<sup>C1</sup>), 126.9 (C<sup>D2</sup>), 122.1 (C<sup>C3</sup>), 121.9 (C<sup>A5</sup>), 120.1 (C<sup>B3</sup>), 118.4 (C<sup>A3</sup>), 115.2 (C<sup>D3</sup>), 55.9 (C<sup>OMe</sup>). IR ( $\tilde{\nu}/\text{cm}^{-1}$ ): 3033 (w), 3004 (w), 2989 (w), 2952 (w), 2929 (w), 2903 (w), 2834 (w), 1593 (m), 1497 (s), 1314 (m), 1238 (s), 1032 (m), 824 (s), 765 (m), 750 (m), 576 (m), 538 (m). MALDI-TOF MS ( $m/z$ ): 3478.9 [M-PF<sub>6</sub>]<sup>+</sup> (calc. 3471.4), 1769.1 [Cu(11)]<sup>+</sup> (calc. 1766.7), 1705.7 [11+H]<sup>+</sup> (calc. 1704.7). UV-VIS (CH<sub>2</sub>Cl<sub>2</sub>,  $1.0 \times 10^{-5}$  mol dm<sup>-3</sup>):  $\lambda_{\text{max}}/\text{nm}$  226 ( $\epsilon/\text{dm}^3 \text{ mol}^{-1} \text{ cm}^{-1}$  225900), 308 (190100), 340 sh (166000), 435 sh (57000), 580 sh (11500). Found: C, 73.04; H, 5.16; N, 6.16; C<sub>228</sub>H<sub>188</sub>N<sub>16</sub>O<sub>16</sub>CuPF<sub>6</sub>·2CH<sub>2</sub>Cl<sub>2</sub> requires C, 72.96; H, 5.11; N, 5.92.

#### [Cu(12)<sub>2</sub>][PF<sub>6</sub>]

The method was as for [Cu(2)<sub>2</sub>][PF<sub>6</sub>] starting with [Cu(MeCN)<sub>4</sub>][PF<sub>6</sub>] (25.3 mg, 67.8  $\mu\text{mol}$ ) and **12** (245 mg, 136  $\mu\text{mol}$ ) in CH<sub>2</sub>Cl<sub>2</sub> (100 mL); the reaction mixture was green-black. [Cu(12)<sub>2</sub>][PF<sub>6</sub>] was isolated as green-black solid (231 mg, 60.6  $\mu\text{mol}$ , 89%). <sup>1</sup>H NMR (500 MHz, CD<sub>2</sub>Cl<sub>2</sub>)  $\delta/\text{ppm}$ : 8.29 (d,  $J = 1.4$  Hz, 4H, H<sup>E1</sup>), 7.69 (dd,  $J = 8.5, 1.6$  Hz, 4H, H<sup>E3</sup>), 7.60 (d,  $J = 1.3$  Hz, 4H, H<sup>A5</sup>), 7.58 (d,  $J = 8.2$  Hz, 4H, H<sup>E5/E8</sup>), 7.45 (d,  $J = 8.5$  Hz, 4H, H<sup>E4</sup>), 7.43 (d,  $J = 1.3$  Hz, 4H, H<sup>A3</sup>), 7.36 (d,  $J = 8.7$  Hz, 8H, H<sup>B2</sup>), 7.33 (m, 4H, H<sup>E6/E7</sup>), 7.21 (m, 8H, H<sup>E5/E8+E6/E7</sup>), 7.11 (m, 56H, H<sup>B3+C2+D2</sup>), 6.95 (d,  $J = 8.9$  Hz, 16H, H<sup>C3</sup>), 6.87 (d,  $J = 9.0$  Hz, 32H, H<sup>D3</sup>), 3.79 (s, 48H, H<sup>OMe</sup>). <sup>13</sup>C NMR (126 MHz, CD<sub>2</sub>Cl<sub>2</sub>)  $\delta/\text{ppm}$ : 156.8 (C<sup>A6</sup>), 156.6 (C<sup>D4</sup>), 154.1 (C<sup>A2</sup>), 151.0 (C<sup>B4</sup>), 150.1 (C<sup>A4</sup>), 146.2 (C<sup>C4</sup>), 141.5 (C<sup>D1</sup>), 139.9 (C<sup>C1</sup>), 136.4 (C<sup>E4a/E8a</sup>), 133.7 (C<sup>E2</sup>), 132.6 (C<sup>E4a/E8a</sup>), 128.5 (C<sup>E5/E8/E6/E7</sup>), 128.2 (C<sup>B2</sup>), 128.0 (C<sup>E1</sup>), 127.8 (C<sup>E5/E8</sup>), 127.7 (C<sup>E4+E6/E7</sup>), 127.5 (C<sup>B1</sup>), 127.2 (C<sup>C2</sup>), 127.0 (C<sup>D2+E6/E7/E5/E8</sup>), 125.6 (C<sup>E3</sup>), 122.1 (C<sup>C3</sup>), 121.5 (C<sup>A5</sup>), 120.0 (C<sup>B3</sup>), 118.0 (C<sup>A3</sup>), 115.2 (C<sup>D3</sup>), 56.0 (C<sup>OMe</sup>). IR ( $\tilde{\nu}/\text{cm}^{-1}$ ): 3036 (w), 3002 (w), 2991 (w), 2950 (w), 2926 (w), 2903 (w), 2833 (w), 1592 (m), 1496 (s), 1314 (m), 1275 (m), 1261 (m), 1237 (s), 1033 (m), 823 (s), 765 (s), 751 (s), 575 (m), 525 (m), 477 (m). MALDI-TOF MS ( $m/z$ ): 3676.2 [M-PF<sub>6</sub>]<sup>+</sup> (calc. 3671.4), 1869.9 [Cu(12)]<sup>+</sup> (calc. 1867.7), 1805.9 [12+H]<sup>+</sup> (calc. 1804.8).

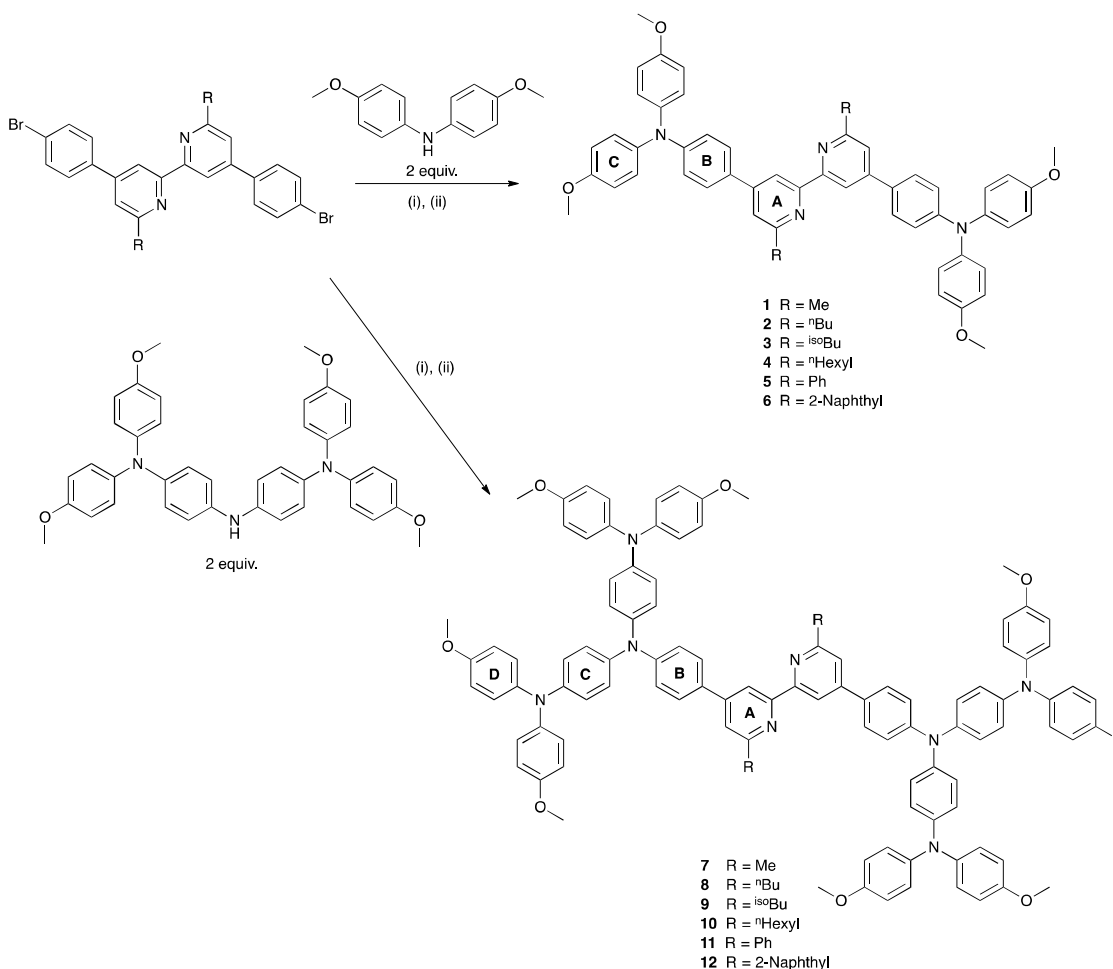

Scheme 2. Synthetic route to compounds 1-12. Conditions: (i) NaO<sup>t</sup>Bu; (ii) Pd(bda)<sub>2</sub>, P<sup>t</sup>Bu<sub>3</sub>, toluene, 100 °C, 16 h. Pd(bda)<sub>2</sub> = bis(dibenzylideneacetone)palladium(0).

UV-VIS (CH<sub>2</sub>Cl<sub>2</sub>, 1.0 × 10<sup>-5</sup> mol dm<sup>-3</sup>): λ<sub>max</sub>/nm: 226 (ε/dm<sup>3</sup> mol<sup>-1</sup> cm<sup>-1</sup> 276400), 240 *sh.* (237300), 306 (194300), 340 *sh.* (170200), 448 (56000), 580 *sh.* (10700). Found: C, 75.83; H, 5.42; N, 5.81; C<sub>244</sub>H<sub>196</sub>N<sub>16</sub>O<sub>16</sub>CuPF<sub>6</sub>·2H<sub>2</sub>O requires C, 76.06; H, 5.23; N, 5.82.

### Crystallography

Single crystal data were collected on a Bruker APEX-II diffractometer with data reduction, solution and refinement using the programs APEX<sup>12</sup> and SHELX-13.<sup>13</sup> The ORTEP-type diagram and structure analysis used Mercury v. 3.0.<sup>14,15</sup>

### Compound 3

C<sub>58</sub>H<sub>58</sub>N<sub>4</sub>O<sub>4</sub>, *M* = 875.08, yellow block, triclinic, space group *P*-1, *a* = 9.9980(4), *b* = 11.2625(4), *c* = 11.6848(5) Å, α = 64.9850(10), β = 80.227(2), γ = 89.948(2)°, *U* = 1171.31(8) Å<sup>3</sup>, *Z* = 1, *D*<sub>c</sub> = 1.241 Mg m<sup>-3</sup>, μ(Cu-Kα) = 0.611 mm<sup>-1</sup>, *T* = 123 K. Total 23653 reflections, 4153 unique, *R*<sub>int</sub> = 0.0258. Refinement of 3800 reflections (302 parameters) with *I* > 2σ(*I*) converged at final *R*1 = 0.0343 (*R*1 all data = 0.0376), *wR*2 = 0.0910 (*wR*2 all data = 0.0942), *gof* = 1.040. CCDC 987649.

### DSC fabrication and measurements


DSCs were prepared adapting the method of Grätzel and coworkers.<sup>16,17</sup> Solaronix Test Cell Titania Electrodes made from TCO22-7 FTO coated glass, prepared by screen-printing for a homogenous surface using Ti-Nanoxide pastes, active layer from Ti-Nanoxide T/SP covered by a reflective layer of Ti-Nanoxide R/SP, active area: 6 × 6 mm, thickness: titania layer 9 μm plus scattering layer 3 μm (Fig. S1†) were used. The electrodes were rinsed with EtOH and sintered at 450 °C for 30 min, then cooled to ca. 80 °C and immersed in a 1 mM DMSO solution of the anchoring ligand **13** for 24 h. The colourless electrode was removed from the solution, washed with DMSO and EtOH and dried at 60 °C. The functionalized electrode was immersed in either a 0.1 mM CH<sub>2</sub>Cl<sub>2</sub> or a 0.1 mM acetone solution of each homoleptic copper(I) complex for ≈68 h. Reference cells were prepared by dipping a commercial electrode into an EtOH solution (0.3 mM) of N719 (Solaronix) for ≈68 h. The electrodes were finally washed with the same solvent as used for dye-assembly and dried at 60 °C. Solaronix Test Cell Platinum Electrodes were used for the counter-electrodes, and residual organic impurities were removed by heating at 450 °C for 30 min.

The dye-covered TiO<sub>2</sub> electrode and Pt counter-electrode were assembled using thermoplast hot-melt sealing foil (Solaronix Test Cell Gaskets) by heating while pressing them

together. The electrolyte ( $\text{LiI}$  ( $0.1 \text{ mol dm}^{-3}$ ),  $\text{I}_2$  ( $0.05 \text{ mol dm}^{-3}$ ), 1-methylbenzimidazole ( $0.5 \text{ mol dm}^{-3}$ ) and 1-butyl-3-methylimidazolium iodide ( $0.6 \text{ mol dm}^{-3}$ ) in 3-methoxypropionitrile) was introduced into the DSC by vacuum backfilling. The hole in the counter electrode was sealed using hot-melt sealing foil (Solaronix Test Cell Sealings) and a cover glass (Solaronix Test Cell Caps). Measurements were made by irradiating from behind using a light source SolarSim 150 ( $100 \text{ mW cm}^{-2} = 1 \text{ sun}$ ). The power of the simulated light was calibrated by using a reference Si cell.

### Scanning electron microscopy

Secondary electron SEM micrograph images were recorded under vacuum ( $\sim 1 \times 10^{-6} \text{ mbar}$ ) using an FEI Nova Nano SEM 230 at an accelerating voltage of 5 keV and magnification of  $\sim 9000\times$ . The sample was prepared by scoring and fracturing the glass electrode in order to image the cross section of the different layers.

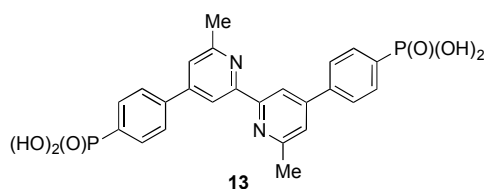

Scheme 3. Structure of anchoring ligand **13**.


## Results and discussion

### Ligand synthesis and characterization

We have previously described the syntheses of the first- and second-generation ligands **1** and **7** by treatment of 4,4'-bis(4-bromophenyl)-6,6'-dimethyl-2,2'-bipyridine with either bis(4-methoxyphenyl)amine or 4,4'-bis(*N,N*-bis(4-methoxyphenyl)amino)diphenylamine.<sup>8</sup> An analogous strategy was adopted for the preparation of first-generation ligands **2–6** and second-generation ligands **8–12**. The appropriate 4,4'-bis(4-bromophenyl)-6,6'-dialkyl-2,2'-bipyridine or 4,4'-bis(4-bromophenyl)-6,6'-diaryl-2,2'-bipyridine precursors have previously been reported<sup>10</sup> with the exception of 4,4'-bis(4-bromophenyl)-6,6'-di(naphthalen-2-yl)-2,2'-bipyridine (**6a**, Scheme 4). This was prepared by Kröhnke methodology<sup>18</sup> starting from (1*E*,5*E*)-1,6-bis(4-bromophenyl)hexa-1,5-diene-3,4-dione as shown in Scheme 4. The product is poorly soluble in most common organic solvents and NMR spectra† were recorded in TFA- $\text{d}_1$  and thus represent data for the protonated ligand  $[\text{H}(\mathbf{6a})]^+$ . The  $^1\text{H}$  and  $^{13}\text{C}$  NMR spectra were assigned using COSY, NOESY, HMQC and HMBC methods. The resonance for  $\text{H}^{\text{A}3}$  is a sensitive probe for the conformation of the bpy domain. Neutral bpy adopts a *trans*-configuration which switches to a *cis*-conformation in the monoprotonated ligand, and the resonance for proton  $\text{H}^{\text{A}5}$  (see Scheme 2 and ESI† for atom numbering) is particularly sensitive to the protonation state of the bpy unit.<sup>19</sup> A NOESY cross peak from  $\text{H}^{\text{C}1}$  to  $\text{H}^{\text{A}5}$  distinguishes the signals for  $\text{H}^{\text{A}5}$  ( $\delta$  8.66 ppm) and

$\text{H}^{\text{A}3}$  ( $\delta$  8.68 ppm). The close chemical shifts of these signals contrasts with their significant separation in 4,4'-bis(4-bromophenyl)-6,6'-dialkyl-2,2'-bipyridines ( $\text{H}^{\text{A}3}$  and  $\text{H}^{\text{A}5}$  appear at  $\delta$  8.48 and  $7.34 \pm 0.03 \text{ ppm}$ , respectively for alkyl = Me,  $^n\text{Bu}$ ,  $^{iso}\text{Bu}$ ,  $^n\text{Hexyl}$ ) and in 4,4'-bis(4-bromophenyl)-6,6'-diphenyl-2,2'-bipyridine ( $\delta$  8.91 and 8.04 ppm).<sup>8,10</sup>

The reactions shown in Scheme 2 proceeded smoothly to give, after purification, the first-generation ligands **2–5** in  $>85\%$  and **6** in 60%. Yields for the second-generation compounds **8–12** ranged from 65 to 81%. All the ligands are readily soluble in  $\text{CHCl}_3$  and  $\text{CH}_2\text{Cl}_2$ . The electrospray mass spectrum of each of **2–6** exhibited a base peak assigned to  $[\text{M}+\text{H}]^+$ . For the second-generation ligands, peaks were observed for  $[\text{M}+2\text{H}]^{2+}$  and, for **9** and **12**, an additional peak arising from  $[\text{M}+\text{H}]^+$ .† The  $^1\text{H}$  and  $^{13}\text{C}$  NMR spectra of  $\text{CDCl}_3$  solutions of the compounds were assigned by 2D techniques. The spectra† indicate a symmetrical bpy domain and signal integrals are consistent with the bis-functionalized structures shown in Scheme 2. Representative spectra for a pair of first- and second-generation ligands are shown in Fig. 1.

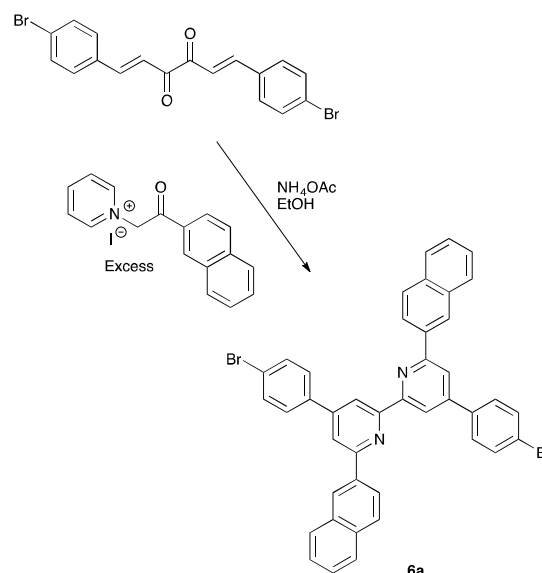

Scheme 4. Synthesis of the precursor 4,4'-bis(4-bromophenyl)-6,6'-di(naphthalen-2-yl)-2,2'-bipyridine, **6a**, by Kröhnke methodology.

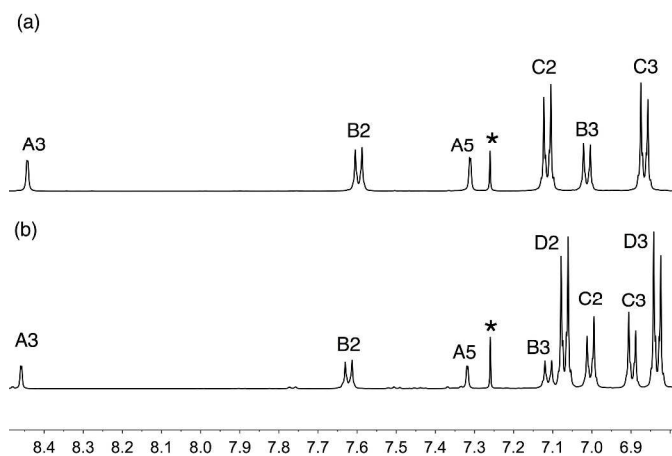


Fig. 1. Aromatic region of the 500 MHz  $^1\text{H}$  NMR spectra ( $\text{CDCl}_3$ , 295 K) of (a) first-generation **4** and (b) second-generation **10**. See Scheme 2 and ESI† for ring labelling. \* = residual  $\text{CHCl}_3$ .

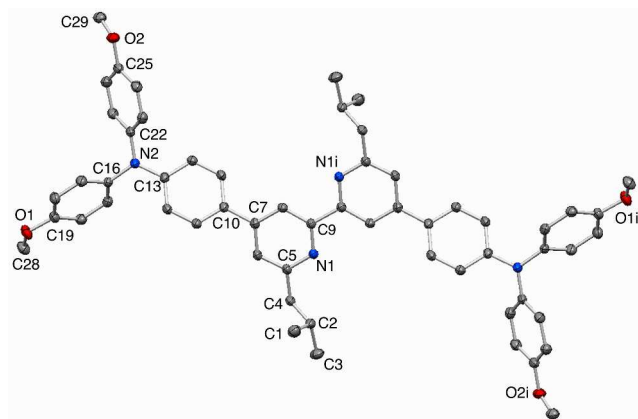


Fig. 2. Structure of compound **3** with ellipsoids plotted at 50% probability; H atoms omitted for clarity. Symmetry code  $i = 1-x, 2-y, 2-z$ . Selected bond parameters: N1–C5 = 1.3451(14), N1–C9 = 1.3453(14), N2–C13 = 1.4006(14), N2–C22 = 1.4262(14), N2–C16 = 1.4302(14), C19–O1 = 1.3649(14), C25–O2 = 1.3697(14), O1–C28 = 1.4225(16), O2–C29 = 1.4274(15) Å; C13–N2–C22 = 121.22(9), C13–N2–C16 = 120.38(9), C22–N2–C16 = 118.16(9), C19–O1–C28 = 117.40(10), C25–O2–C29 = 116.05(9)°.

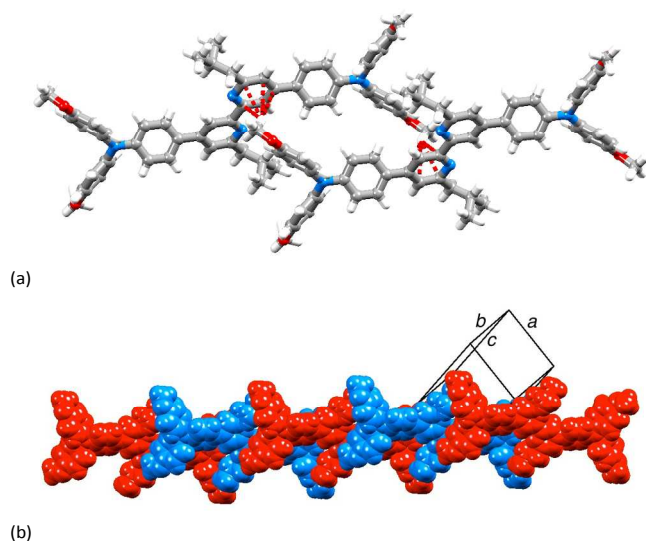


Fig. 3. (a) Centrosymmetric pair of molecules of **3** embrace through  $\text{CH}_{\text{OMe}} \cdots \pi_{\text{pyridine}}$  contacts. (b) The interactions extend between molecules to generate hydrogen bonded chains.

X-Ray quality single crystals of **3** were grown by  $\text{Et}_2\text{O}$  diffusion into an acetone/chloroform solution of the compound. The structure of **3** is shown in Fig. 2. Selected bond parameters are given in the figure caption. The compound crystallizes in the space group  $P\bar{1}$  with half of the molecule in the asymmetric unit; the second half is generated through an inversion centre and the bpy unit necessarily adopts a *trans*-conformation and is planar. The phenylene unit is twisted  $36.7^\circ$  with respect to the pyridine ring to which it is bonded, thereby minimizing inter-ring H...H interactions. Atom N2 is in a planar environment, consistent with delocalization of the lone pair into the arene  $\pi$ -systems. The twisted arrangement of the three arene rings bonded to N2 is expected on steric grounds. The presence of the isobutyl groups prevents face-to-face interactions between bpy domains of neighbouring molecules. Dominant packing interactions involve methoxy  $\text{CH} \cdots \pi_{\text{pyridine}}$  contacts ( $\text{CH} \cdots \text{centroid} = 2.39$  Å) which lead to a centrosymmetric embrace between adjacent molecules (Fig. 3a). These interactions lead to the assembly of hydrogen-bonded chains which slice obliquely through the unit cell (Fig. 3b).

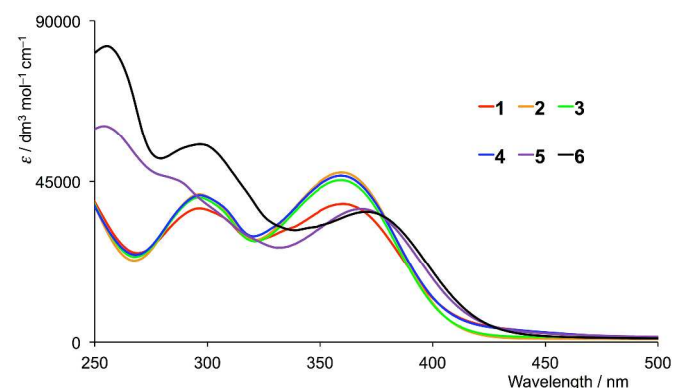


Fig. 4. Solution absorption spectra of the first-generation ligands **1–6** in  $\text{CH}_2\text{Cl}_2$  ( $1 \times 10^{-5}$  mol  $\text{dm}^{-3}$ ).

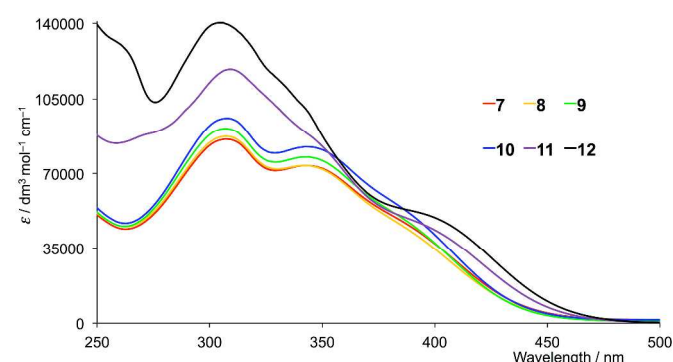


Fig. 5. Solution absorption spectra of the second-generation ligands **7–12** in  $\text{CH}_2\text{Cl}_2$  ( $1 \times 10^{-5}$  mol  $\text{dm}^{-3}$ ).

The solution absorption spectra of the first- and second-generation ligands are displayed in Figs. 4 and 5, respectively.



The spectra are all broad with intense bands which tail into the visible region. The observed absorptions originate from  $\pi^* \leftarrow \pi$  and  $\pi^* \leftarrow n$  transitions, and the spectra of **1–4** (which contain 6- and 6'-alkyl substituents) are similar, as are those of the second-generation ligands **7–10**. Extension of the aromatic domains on going from **1** to **7** (both with methyl substituents) leads to the anticipated increase in extinction coefficient (red curves in Figs. 4 and 5). Similar trends are observed upon comparing the spectra of **2** and **8**, **3** and **9**, or **4** and **10**. As expected, the intensities of the highest energy bands in the spectra of **5** and **11** (phenyl substituents, purple curves in Figs. 4 and 5) and **6** and **12** (naphthyl substituents, black curves in Figs. 4 and 5) are substantially larger than those of the alkyl-substituted ligands.

### Synthesis and characterization of homoleptic copper(I) complexes

We have previously reported the syntheses and properties of  $[\text{Cu}(\mathbf{1})_2][\text{PF}_6]$  and  $[\text{Cu}(\mathbf{7})_2][\text{PF}_6]$ .<sup>8</sup> Homoleptic copper(I) complexes containing ligands **2–6** and **8–12** were prepared by treatment of  $[\text{Cu}(\text{NCMe})_4][\text{PF}_6]$  with two equivalents of the appropriate ligand. Yields of  $[\text{CuL}_2][\text{PF}_6]$  were typically high. The electropray mass spectra of the complexes containing the first-generation ligands **2–6** each exhibited a peak envelope corresponding to  $[\text{M-PF}_6]^+$  with the correct isotopic pattern. In addition, peaks assigned to  $[\mathbf{3}+\text{H}]^+$ ,  $[\mathbf{4}+\text{H}]^+$ ,  $[\mathbf{5}+\text{H}]^+$  or  $[\mathbf{6}+\text{H}]^+$  were observed in the spectra of the respective complexes. Ligand loss was observed in the mass spectra of the complexes with the second-generation ligands and the spectra exhibited peaks for  $[\text{CuL}]^+$  and  $[\text{L}+\text{H}]^+$  for  $\text{L} = \mathbf{8}, \mathbf{9}, \mathbf{10}, \mathbf{11}$  or **12**. For  $\text{L} = \mathbf{9}, \mathbf{11}$  and **12**, a peak envelope arising from  $[\text{M-PF}_6]^+$  was also observed.

The  $^1\text{H}$  and  $^{13}\text{C}$  NMR spectra of  $[\text{CuL}_2][\text{PF}_6]$  with  $\text{L} = \mathbf{2–6}$  were recorded in  $\text{CDCl}_3$ , making the spectra directly comparable with those of the free ligands. Although the complexes containing the second-generation ligands are soluble in  $\text{CDCl}_3$ , signals in the  $^1\text{H}$  NMR spectra were broadened, necessitating a solvent change to  $\text{CD}_2\text{Cl}_2$  to obtain well-resolved spectra. Fig. 6 compares the aromatic regions of the  $^1\text{H}$  NMR spectra of **2** and  $[\text{Cu}(\mathbf{2})_2][\text{PF}_6]$ . Shifts in the signals for  $\text{H}^{\text{A3}}$  and  $\text{H}^{\text{A5}}$  are consistent with the change in conformation of the bpy unit upon coordination. Resonances for the peripheral dendron protons are essentially unaffected; the signal for the OMe protons appears at  $\delta$  3.82 ppm in **2** and at  $\delta$  3.83 ppm in  $[\text{Cu}(\mathbf{2})_2][\text{PF}_6]$ . The trends are typical of the spectra of all ligand-complex pairs in which the ligand bears 6- and 6'-alkyl substituents (Table 1). The shift to lower frequency for  $\text{H}^{\text{A3}}$  on comparing ligand with complex (Table 1) is more pronounced for ligands **5** and **11** (phenyl substituents) than for the pairs of alkyl-substituted ligands, and is even more so for **6** and **12** (2-naphthyl substituents). The structure of  $[\text{Cu}(\mathbf{6})_2]^+$  modelled using Spartan 14 (v. 1.1.3, MMFF level) is shown in Fig. 7. The  $\text{H}^{\text{A3}}$  protons on one bpy ligand are located within a cleft between the two naphthyl domains of the second ligand and thus lie in the shielding region of their ring currents. The same effect is observed for both first- and second-generation ligands and their complexes (Table 1).

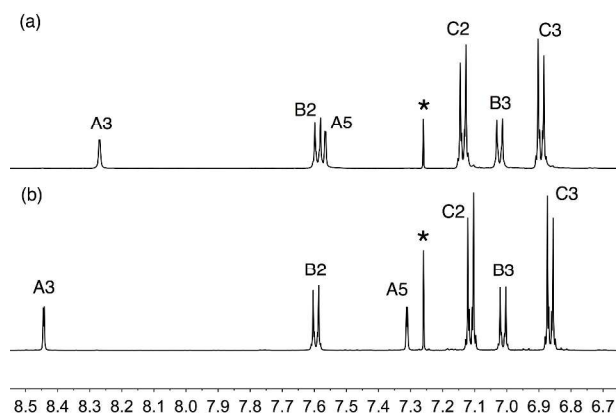


Fig. 6. Aromatic region of the 500 MHz  $^1\text{H}$  NMR spectra ( $\text{CDCl}_3$ , 295 K) of (a)  $[\text{Cu}(\mathbf{2})_2][\text{PF}_6]$  and (b) free ligand **2**. See Scheme 2 and ESI† for ring labelling. \* = residual  $\text{CHCl}_3$ .

Table 1. Comparison of chemical shifts of bpy protons  $\text{H}^{\text{A3}}$  and  $\text{H}^{\text{A5}}$  in free ligand, L, in  $\text{CDCl}_3$  and  $[\text{CuL}_2][\text{PF}_6]$  complexes in  $\text{CDCl}_3$  for  $\text{L} = \mathbf{1–6}$  and  $\text{CD}_2\text{Cl}_2$  for  $\text{L} = \mathbf{7–12}$ .

L	$\text{H}^{\text{A3}}$ in L	$\text{H}^{\text{A5}}$ in L	$\text{H}^{\text{A3}}$ in $[\text{CuL}_2]^+$	$\text{H}^{\text{A5}}$ in $[\text{CuL}_2]^+$
First-generation				
<b>1</b>	8.39	7.33	8.25	7.59
<b>2</b>	8.44	7.31	8.27	7.57
<b>3</b>	8.46	7.28	8.27	7.52
<b>4</b>	8.44	7.31	8.26	7.56
<b>5</b>	8.82	7.95	7.95	7.61
<b>6</b>	8.89	8.11	7.32	7.57
Second-generation				
<b>7</b>	8.40	7.33	8.26	7.57
<b>8</b>	8.46	7.32	8.34	7.60
<b>9</b>	8.46	7.28	8.35	7.56
<b>10</b>	8.46	7.32	8.34	7.61
<b>11</b>	8.83	7.96	8.02	7.66
<b>12</b>	8.93	8.12	7.43	7.60

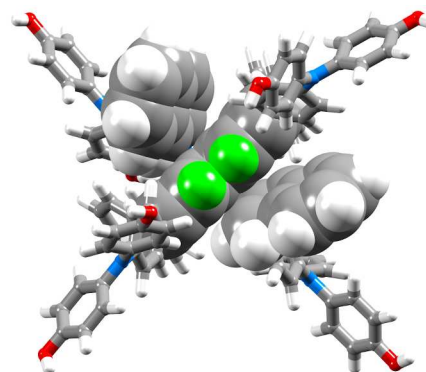


Fig. 7. Modelled structure of  $[\text{Cu}(\mathbf{6})_2]^+$ . The  $\text{H}^{\text{A3}}$  protons (in green) and bpy domain of one ligand and the two 2-naphthyl groups of the second ligand are shown in space-filling representation.

The absorption spectra of  $\text{CH}_2\text{Cl}_2$  solutions of the copper(I) complexes are shown in Fig. 8 (first-generation ligands) and Fig. 9 (second-generation). The broad absorption bands extend significantly further to longer wavelength than for the free ligands. The approximate doubling of the extinction

**Table 1** Cyclic voltammetric data for  $[\text{CuL}_2][\text{PF}_6]$  with L = 1–12 with respect to  $\text{Fc}/\text{Fc}^+$ ;  $\text{CH}_2\text{Cl}_2$  solutions with  $[\text{Bu}_4\text{N}][\text{PF}_6]$  as supporting electrolyte and scan rate of  $0.1 \text{ V s}^{-1}$ . Processes are reversible unless otherwise stated (qr = quasi-reversible; ir = irreversible).

Complex	$E_{1/2}^{\text{ox}} / \text{V}$ ( $E_{\text{pc}} - E_{\text{pa}} / \text{mV}$ )	$E_{1/2}^{\text{ox}} / \text{V}$ ( $E_{\text{pc}} - E_{\text{pa}} / \text{mV}$ )	$E_{1/2}^{\text{ox}} / \text{V}$ ( $E_{\text{pc}} - E_{\text{pa}} / \text{mV}$ )	$E_{1/2}^{\text{ox}} / \text{V}$ ( $E_{\text{pc}} - E_{\text{pa}} / \text{mV}$ )	$E_{1/2}^{\text{ox}} / \text{V}$ ( $E_{\text{pc}} - E_{\text{pa}} / \text{mV}$ )	$E_{1/2}^{\text{red}} / \text{V}$ ( $E_{\text{pc}} - E_{\text{pa}} / \text{mV}$ )
$[\text{Cu}(1)_2][\text{PF}_6]$		+0.29 (96)	+0.44 (87)		+1.00 <sup>ir</sup>	-2.04 <sup>ir</sup>
$[\text{Cu}(2)_2][\text{PF}_6]$		+0.29 (79)	+0.57 (65)		+0.98 (94) <sup>qr</sup>	-2.07 <sup>ir</sup>
$[\text{Cu}(3)_2][\text{PF}_6]$		+0.29 (86)	+0.58 (66)		+0.99 (102) <sup>qr</sup>	-2.08 <sup>ir</sup>
$[\text{Cu}(4)_2][\text{PF}_6]$		+0.29 (89)	+0.57 (74)		+0.96 (106) <sup>qr</sup>	-2.05 <sup>ir</sup>
$[\text{Cu}(5)_2][\text{PF}_6]$		+0.32 <sup>a</sup>	+0.40 <sup>a</sup>		+0.99 (83) <sup>qr</sup>	-2.25 <sup>ir</sup>
$[\text{Cu}(6)_2][\text{PF}_6]$		+0.31 <sup>a</sup>	+0.40 <sup>a</sup>		+0.97 (96) <sup>qr</sup>	-2.07 <sup>ir</sup>
$[\text{Cu}(7)_2][\text{PF}_6]$	-0.07 (78)	+0.20 (75)	+0.47 (129)	+0.69 (168)	+1.03 <sup>ir</sup>	-2.03 <sup>ir</sup>
$[\text{Cu}(8)_2][\text{PF}_6]$	-0.07 (83)	+0.19 (83)	+0.54 (99)	+0.69 (155)	+1.01 (111) <sup>qr</sup>	-2.07 <sup>ir</sup>
$[\text{Cu}(9)_2][\text{PF}_6]$	-0.08 (65)	+0.18 (88)	+0.55 (90)	+0.68 (157)	+1.02 (85) <sup>qr</sup>	-2.06 <sup>ir</sup>
$[\text{Cu}(10)_2][\text{PF}_6]$	-0.07 (79)	+0.18 (89)	+0.55 (84)	+0.69 (150)	+1.03 (86) <sup>qr</sup>	-2.06 <sup>ir</sup>
$[\text{Cu}(11)_2][\text{PF}_6]$	-0.07 (81)	+0.19 (103)	+0.39(81)	+0.69 (170)	+1.03 (69) <sup>qr</sup>	-2.19 <sup>ir</sup>
$[\text{Cu}(12)_2][\text{PF}_6]$	-0.08 (63)	+0.19 (85)	+0.39 (67)	+0.68 (168)	+1.02 <sup>ir</sup>	-2.08 <sup>ir</sup>

<sup>a</sup> 1st and 2nd oxidation processes overlap.

coefficients on comparing the spectra of ligands with complexes is consistent with the homoleptic complexes  $[\text{CuL}_2]^+$ . At high energies ( $\lambda < 450 \text{ nm}$ ), the absorption spectra of  $[\text{CuL}_2]^+$  for L = 1–6 possess similar bands-shapes to those of the first-generation ligands 1–6 (compare Fig. 8 with Fig. 4). The ligand-centred band at  $\approx 360 \text{ nm}$  undergoes a red-shift of 10–30 nm on going from ligand to complex. The shoulder at around 480 nm in the spectra of  $[\text{CuL}_2]^+$  for L = 1–4 is absent in the spectra of the ligands and is assigned to the MLCT band. The energy is consistent with the band at 483 nm observed in  $[\text{Cu}(6,6\text{-Me}_2\text{bpy})_2]^+$ , the MLCT character of which has been confirmed from TD-DFT calculations.<sup>20</sup> For  $[\text{Cu}(5)_2][\text{PF}_6]$  and  $[\text{Cu}(6)_2][\text{PF}_6]$ , a low intensity band at 560 and 576 nm, respectively, (Fig. 8) is assumed to arise from the MLCT. The absorption spectra of  $[\text{CuL}_2]^+$  for second-generation ligands 7–12 are dominated by high energy bands originating from ligand-based  $\pi^* \leftarrow \pi$  and  $\pi^* \leftarrow n$  transitions (Fig. 9). Broad shoulders in the spectra of  $\text{CH}_2\text{Cl}_2$  solutions of  $[\text{Cu}(7)_2][\text{PF}_6]$ ,  $[\text{Cu}(8)_2][\text{PF}_6]$ ,  $[\text{Cu}(9)_2][\text{PF}_6]$  and  $[\text{Cu}(10)_2][\text{PF}_6]$  centred around 480 nm are assigned to MLCT transitions. (Note that the previously reported spectrum for  $[\text{Cu}(7)_2][\text{PF}_6]$  with  $\lambda_{\text{max}} = 505 \text{ nm}$  was recorded in MeCN.)<sup>8</sup> The MLCT bands for  $[\text{Cu}(11)_2][\text{PF}_6]$  and  $[\text{Cu}(12)_2][\text{PF}_6]$  are assigned to the low intensity absorption maxima at 580 nm (Fig. 9), consistent with the first-generation analogues (Fig. 8). The broad and intense spectral responses of all the complexes, especially those containing ligands 7–12, suggest that they should be good candidates as precursors to dyes in DSCs.

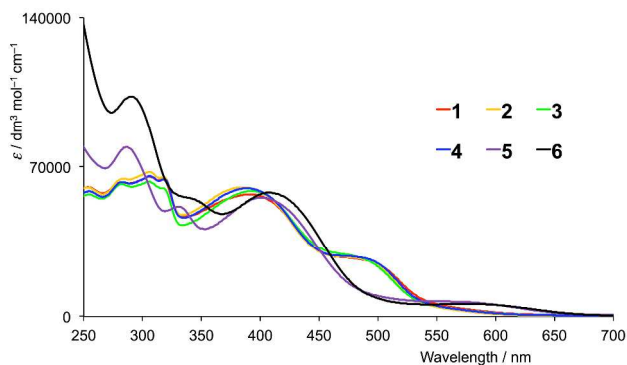


Fig. 8. Solution absorption spectra of in  $\text{CH}_2\text{Cl}_2$  solutions of  $(1 \times 10^{-5} \text{ mol dm}^{-3})$   $[\text{CuL}_2][\text{PF}_6]$  where L = 1–6 (first-generation ligands).

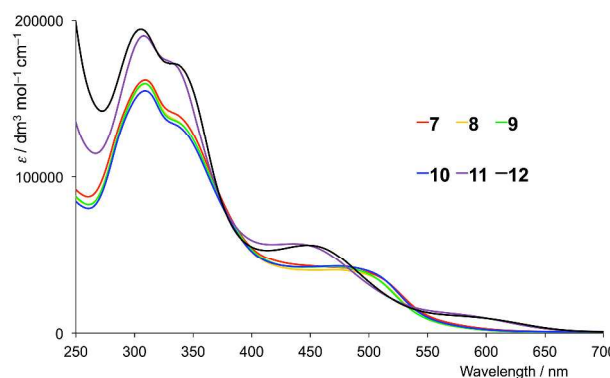


Fig. 9. Solution absorption spectra of in  $\text{CH}_2\text{Cl}_2$  solutions of  $(1 \times 10^{-5} \text{ mol dm}^{-3})$   $[\text{CuL}_2][\text{PF}_6]$  where L = 7–12 (second-generation ligands).

## Electrochemistry

Cyclic voltammetric data for the homoleptic copper(I) complexes are presented in Table 1. Cyclic voltammograms were recorded  $\text{CH}_2\text{Cl}_2$  to preclude association of the metal ion with coordinating solvents,<sup>21</sup> and are always referenced to internal ferrocene. For the first- or second-generation complexes, three or five oxidation processes are observed, respectively. A representative pair of CVs for first-generation  $[\text{Cu}(3)_2][\text{PF}_6]$  and second-generation  $[\text{Cu}(9)_2][\text{PF}_6]$  is shown in Fig. 10. By comparison with related systems, the oxidation process in the range 0.40–0.58 V is assigned to the  $\text{Cu}^+/\text{Cu}^{2+}$  couple. In copper(I) diimine complexes, incorporation of substituents *ortho* to the *N*-donor sites (e.g. 6,6'-positions in bpy) stabilizes tetrahedral  $\text{Cu}^+$  with respect to square-planar copper(II) by sterically encumbering the flattening of the coordination environment. The potentials for the  $\text{Cu}^+/\text{Cu}^{2+}$  couple in  $[\text{CuL}_2][\text{PF}_6]$  with L = 1–6 follow the same trend as in the series  $[\text{CuL}_2][\text{PF}_6]$  with L = 7–12. The complexes containing the phenyl or 2-naphthyl substituents (ligands 5, 6, 11 and 12) exhibit the lowest metal oxidation potentials, followed by the complexes containing the methyl substituents (ligands 1 and 7). The metal-centred oxidation in  $[\text{Cu}(2)_2][\text{PF}_6]$ ,  $[\text{Cu}(3)_2][\text{PF}_6]$ ,  $[\text{Cu}(4)_2][\text{PF}_6]$ ,  $[\text{Cu}(8)_2][\text{PF}_6]$ ,  $[\text{Cu}(9)_2][\text{PF}_6]$  and



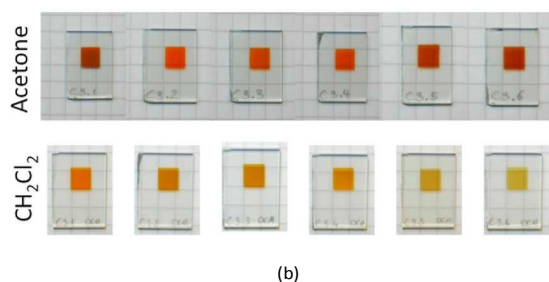


Fig. 11. Cells after dipping in acetone or  $\text{CH}_2\text{Cl}_2$  solutions of the homoleptic complexes: (a) first-generation ligands 1–6 (left to right), (b) second-generation ligands 7–12 (left to right).

FTO/ $\text{TiO}_2$  electrodes (without a scattering layer) with adsorbed dye were prepared and their solid-state absorption spectra recorded, each spectrum being corrected for the background spectrum of a blank electrode. Absorption spectra for electrodes with first-generation dyes made using  $\text{CH}_2\text{Cl}_2$  or acetone solutions of the homoleptic complexes  $[\text{CuL}_2][\text{PF}_6]$  with  $L = 1-6$  are shown in Figs. 12a and 12b, respectively. For a given ancillary ligand, the general trend is for enhanced absorptivity when acetone is used in the dipping solution during cell fabrication. A similar trend is observed for complexes containing the second-generation ligands 7–12. The enhancement of absorption observed on changing from  $\text{CH}_2\text{Cl}_2$  to acetone coupled with that on going from first- to second-generation ligand in the surface-immobilized heteroleptic complex, is exemplified in Fig. 13 with  $[\text{Cu}(\mathbf{13})(\mathbf{4})]^+$  and  $[\text{Cu}(\mathbf{13})(\mathbf{10})]^+$ .


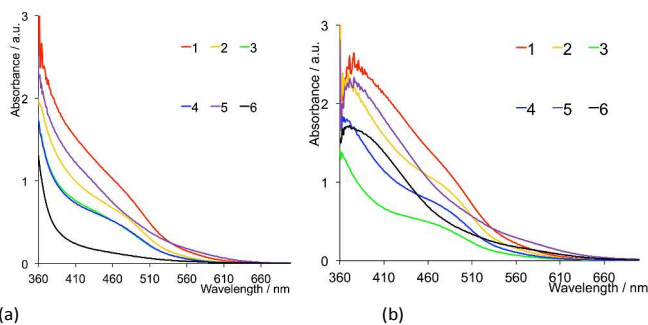


Fig. 12. Solid-state absorption spectra of electrodes with anchored dyes  $[\text{Cu}(\mathbf{13})(L)]^+$  where  $L = 1-6$ . The electrodes were made using (a)  $\text{CH}_2\text{Cl}_2$ , or (b) acetone solutions of  $[\text{CuL}_2][\text{PF}_6]$ .

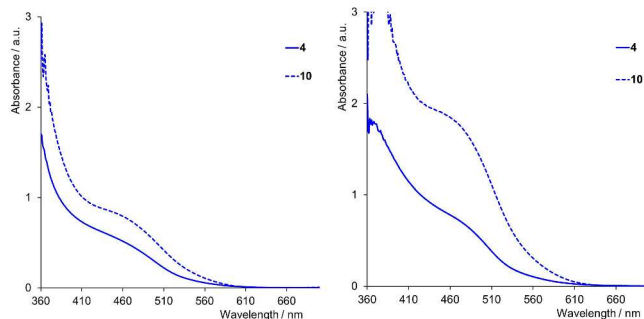

(a) (b)  
Fig. 13. Solid-state absorption spectra of electrodes with the anchored first- and second-generation dyes  $[\text{Cu}(\mathbf{13})(\mathbf{4})]^+$  and  $[\text{Cu}(\mathbf{13})(\mathbf{10})]^+$ . The electrodes with anchored dye were prepared using (a)  $\text{CH}_2\text{Cl}_2$ , or (b) acetone solutions of  $[\text{CuL}_2][\text{PF}_6]$  ( $L = 4$  or  $10$ ).

### DSC performances: first- versus second-generation ancillary ligands

The enhanced absorption observed using acetone in the dye dipping cycle leads us to initially focus on the performances of these DSCs. All DSCs were masked to avoid overestimation of efficiencies.<sup>26</sup> In order to ensure that DSC parameters were reproducible, measurements were made using duplicate cells for each dye-solvent combination. A complete set of DSC parameters is presented in Table S1†, and Table 2 summarizes representative DSC characteristics using anchoring ligand **13**, first-generation ancillary ligands and acetone in the dye dipping cycle, measured over a period of three weeks and with respect to the standard dye N719. The final column in the table shows relative efficiencies with respect to N719 set to 100%. Performance data for the dyes containing the second-generation ligands 7–12 are given in Tables 3 and S2†.

Table 2. DSC performance data for sealed and masked cells using anchoring ligand **13** and first-generation ancillary ligands, and acetone in the  $[\text{CuL}_2][\text{PF}_6]$  dipping cycle. Relative efficiencies (last column) are with respect to 100% for standard dye N719 measured under the same conditions. See also Table S1.

Anchored dye	On the day of sealing the cell				□□□□□□ □ η / %□
	$J_{\text{SC}} / \text{mA cm}^{-2}$	$V_{\text{OC}} / \text{mV}$	$ff$	η / %	
$[\text{Cu}(\mathbf{13})(\mathbf{1})]^+$	6.00	510	70.3	2.15	29.4
$[\text{Cu}(\mathbf{13})(\mathbf{2})]^+$	4.41	482	69.4	1.48	20.2
$[\text{Cu}(\mathbf{13})(\mathbf{3})]^+$	4.22	475	69.6	1.39	19.0
$[\text{Cu}(\mathbf{13})(\mathbf{4})]^+$	5.60	542	71.8	2.18	29.8
$[\text{Cu}(\mathbf{13})(\mathbf{5})]^+$	3.22	468	68.6	1.03	14.1
$[\text{Cu}(\mathbf{13})(\mathbf{6})]^+$	4.29	508	67.0	1.46	19.9
N719	16.72	641	68.4	7.32	100
Anchored dye	22 <sup>a</sup> days after sealing the cell				□□□□□□ □ η / %
	$J_{\text{SC}} / \text{mA cm}^{-2}$	$V_{\text{OC}} / \text{mV}$	$ff$	η / %	
$[\text{Cu}(\mathbf{13})(\mathbf{1})]^+$	5.27	520	71.1	1.94	24.4
$[\text{Cu}(\mathbf{13})(\mathbf{2})]^+$	4.42	516	70.7	1.61	20.3
$[\text{Cu}(\mathbf{13})(\mathbf{3})]^+$	4.18	487	69.6	1.42	17.9
$[\text{Cu}(\mathbf{13})(\mathbf{4})]^+$	5.05	532	70.8	1.90	23.9
$[\text{Cu}(\mathbf{13})(\mathbf{5})]^+$	4.00	485	69.9	1.36	17.1
$[\text{Cu}(\mathbf{13})(\mathbf{6})]^+$	4.10	504	68.0	1.41	17.7
N719	16.65	671	71.2	7.95	100

<sup>a</sup>For  $[\text{Cu}(\mathbf{13})(\mathbf{1})]^+$ , the second measurements were made after 18 days.

A comparison of Tables 2 and 3 reveals that, with the exception of  $[\text{Cu}(\mathbf{13})(\mathbf{6})]^+$  and  $[\text{Cu}(\mathbf{13})(\mathbf{12})]^+$  (**6** and **12** = 6,6'-bis(2-naphthyl) substituted ligands), the dyes containing the second-generation ancillary ligands give higher global efficiencies. This corresponds to an increase in the solid-state absorbance of the DSCs as illustrated in Fig. 12. After three weeks, the DSCs with the ancillary ligands 7–9 and **11** exhibit higher  $J_{\text{SC}}$  values than those with 1–3 and **5** (Figs. 14, 15, S1†, S2†), while  $J_{\text{SC}}$  for dyes containing the *n*-hexyl substituents (**4** and **10**) are

similar (Fig. S3†). For [Cu(13)(9)]<sup>+</sup> (isobutyl substituents, second-generation), there is also a significant gain in  $V_{OC}$  over the three week period (Fig. 14). The dyes with the methyl (Fig. 15) or n-butyl (Fig. S1†) substituents perform the best, with enhancement on going from first- to second-generation ancillary ligands. [Cu(13)(1)]<sup>+</sup> and [Cu(13)(7)]<sup>+</sup> (methyl substituted ancillary ligands) suffer from reduced  $J_{SC}$  as the DSCs age, but benefit from increased  $V_{OC}$ . This latter enhancement is also observed in [Cu(13)(2)]<sup>+</sup> and [Cu(13)(8)]<sup>+</sup> (n-butyl groups).

The dyes which incorporate the sterically hindering 2-naphthyl groups exhibit poorer device performances than the other dyes, and this is associated with lower  $J_{SC}$  values (Fig. 16). As the DSCs age, the efficiencies decrease, with this trend observed for both generations of ligands; these observations are confirmed for the duplicate DSCs (Tables S1 and S2†). The data also suggest that extending the dendron on going from 6 to 12 is detrimental to overall dye performance (Fig. 16).

Table 3. DSC performance data for masked cells using anchoring ligand 13 and second-generation ancillary ligands, and acetone in the [CuL<sub>2</sub>][PF<sub>6</sub>] dipping cycle. Relative efficiencies (last column) are with respect to 100% for standard dye N719 measured under the same conditions. See also Table S2.

Anchored dye	On the day of sealing the cell				
	$J_{SC}$ / mA cm <sup>-2</sup>	$V_{OC}$ / mV	$ff$	$\eta$ / %	□□□□□□ □ $\eta$ / %
[Cu(13)(7)] <sup>+</sup>	6.46	515	67.9	2.26	32.8
[Cu(13)(8)] <sup>+</sup>	6.08	506	70.8	2.18	31.6
[Cu(13)(9)] <sup>+</sup>	5.48	475	69.9	1.82	26.4
[Cu(13)(10)] <sup>+</sup>	5.25	488	70.9	1.81	26.2
[Cu(13)(11)] <sup>+</sup>	4.01	459	70.2	1.29	18.7
[Cu(13)(12)] <sup>+</sup>	3.04	444	69.2	0.93	13.5
N719	16.52	608	68.8	6.90	100
Anchored dye	22 <sup>a</sup> days after sealing the cell				
	$J_{SC}$ / mA cm <sup>-2</sup>	$V_{OC}$ / mV	$ff$	$\eta$ / %	□□□□□□ □ $\eta$ / %
[Cu(13)(7)] <sup>+</sup>	5.94	536	70.3	2.23	27.5
[Cu(13)(8)] <sup>+</sup>	5.97	532	71.6	2.27	28.0
[Cu(13)(9)] <sup>+</sup>	6.31	541	71.0	2.42	29.8
[Cu(13)(10)] <sup>+</sup>	5.47	522	70.6	2.02	24.9
[Cu(13)(11)] <sup>+</sup>	4.99	487	71.3	1.73	21.3
[Cu(13)(12)] <sup>+</sup>	2.77	466	70.2	0.91	11.2
N719	16.98	674	70.9	8.11	100

<sup>a</sup>For N719, the second measurement was made after 15 days.

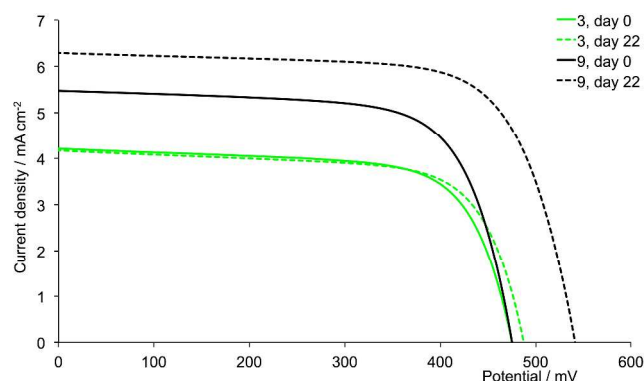


Fig. 14  $J$ - $V$  curves for dyes [Cu(13)(3)]<sup>+</sup> and [Cu(13)(9)]<sup>+</sup> (isobutyl substituents, acetone used in the dye-dipping cycle) on day of sealing the DSC (day 0) and after 18 or 22 days showing enhancement of  $J_{SC}$  with second-generation ligand.

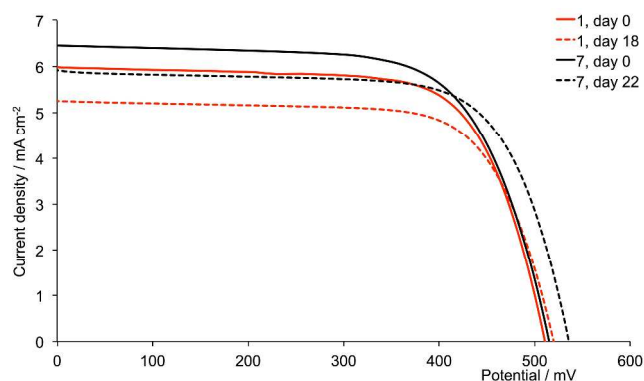


Fig. 15  $J$ - $V$  curves for dyes [Cu(13)(1)]<sup>+</sup> and [Cu(13)(7)]<sup>+</sup> (methyl substituents, acetone used in the [CuL<sub>2</sub>][PF<sub>6</sub>] dipping cycle) on day of sealing the DSC (day 0) and after 18 or 22 days.

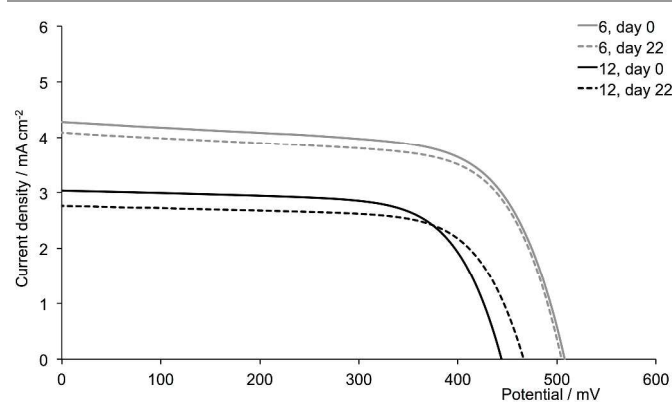


Fig. 16  $J$ - $V$  curves for dyes [Cu(13)(6)]<sup>+</sup> and [Cu(13)(12)]<sup>+</sup> (naphthyl substituents, acetone used in the [CuL<sub>2</sub>][PF<sub>6</sub>] dipping cycle) on day of sealing the DSC (day 0) and after 22 days.

Fig. 17 shows the EQE spectra of freshly sealed DSCs for all the dyes; the spectra were also recorded after 22 days (Fig. S4 and S5†). Only small changes in EQE parameters (Tables 4 and 5) are observed for a given DSC over a 22 day period. Except for 2-naphthyl-containing dyes, on going from the first- to second-generation ligand in each pair (e.g. [Cu(13)(1)]<sup>+</sup> to [Cu(13)(7)]<sup>+</sup>), values of EQE<sub>max</sub> typically increase. Irrespective of the ancillary ligand, the dyes exhibit values of  $\lambda_{max}$  in the range 470–490 nm. For the dye containing 1 (methyl groups), Fig. 17a shows a pronounced low energy shoulder at 590 nm, confirming improved photoresponse and electron injection consistent with the relatively high conversion efficiency observed for anchored dye [Cu(13)(1)]<sup>+</sup> (Table 3). The dyes with the second-generation alkyl-functionalized ancillary ligands all exhibit enhanced EQE to lower energies than the first-generation analogues (Fig. 17b versus 17a). This observation appears not to carry through to dyes 5 and 11 with phenyl substituents where there is little gain in EQE at higher wavelength upon extending the hole transport domain.

Consistent with the earlier discussion, EQE data confirm poorer electron injection on going from **6** to **12** (naphthyl-groups).

Table 4. EQE maxima for DSCs containing first-generation dyes.

Anchored dye	Day 0		Day 22	
	$\lambda_{\max}$ / nm	EQE <sub>max</sub> / %	$\lambda_{\max}$ / nm	EQE <sub>max</sub> / %
[Cu( <b>13</b> )( <b>1</b> )] <sup>+</sup>	470	35.2	470	31.3
[Cu( <b>13</b> )( <b>2</b> )] <sup>+</sup>	470	34.4	470	32.8
[Cu( <b>13</b> )( <b>3</b> )] <sup>+</sup>	470	34.2	470	32.0
[Cu( <b>13</b> )( <b>4</b> )] <sup>+</sup>	470	40.6	470	37.2
[Cu( <b>13</b> )( <b>5</b> )] <sup>+</sup>	470	29.0	470	32.7
[Cu( <b>13</b> )( <b>6</b> )] <sup>+</sup>	470	35.0	470	31.2

Table 5. EQE maxima for DSCs containing second-generation dyes.

Anchored dye	Day 0		Day 22	
	$\lambda_{\max}$ / nm	EQE <sub>max</sub> / %	$\lambda_{\max}$ / nm	EQE <sub>max</sub> / %
[Cu( <b>13</b> )( <b>7</b> )] <sup>+</sup>	470-490	42.2	480	41.8
[Cu( <b>13</b> )( <b>8</b> )] <sup>+</sup>	470	41.3	470	41.7
[Cu( <b>13</b> )( <b>9</b> )] <sup>+</sup>	470	40.3	470	46.5
[Cu( <b>13</b> )( <b>10</b> )] <sup>+</sup>	470	38.6	480	41.3
[Cu( <b>13</b> )( <b>11</b> )] <sup>+</sup>	470	36.1	480	41.4
[Cu( <b>13</b> )( <b>12</b> )] <sup>+</sup>	460-470	27.6	470	24.3

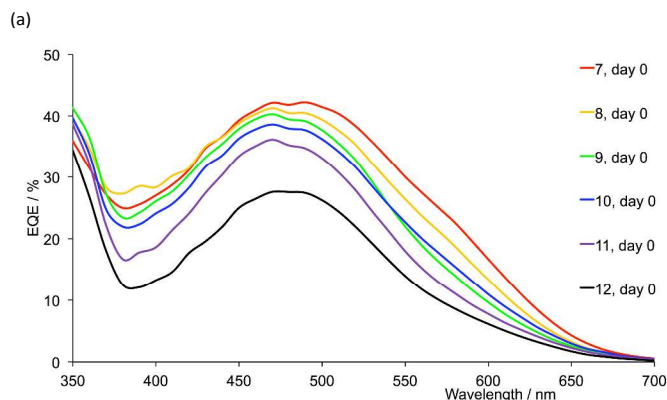
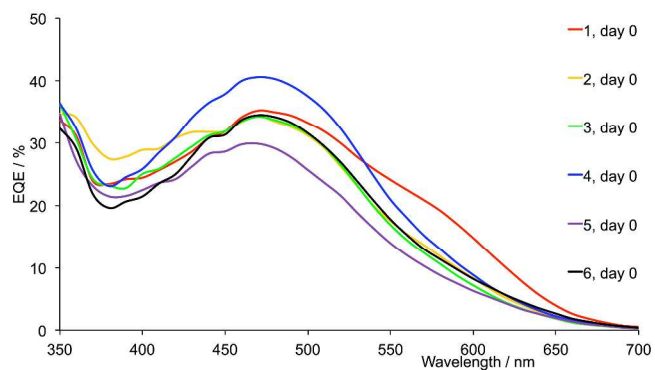


Fig. 17 EQE spectra (on the day of sealing) of DSCs with dyes containing ancillary ligands (a) **1–6** and (b) **7–12**. Acetone was used in the [CuL<sub>2</sub>][PF<sub>6</sub>]<sub>2</sub> dipping cycle.

Table 6. DSC performance data for masked cells using anchoring ligand **13** and first or second-generation ancillary ligands, and CH<sub>2</sub>Cl<sub>2</sub> in the [CuL<sub>2</sub>][PF<sub>6</sub>]<sub>2</sub> dipping cycle. Relative efficiencies (last column) are with respect to 100% for standard dye N719 measured under the same conditions. See also Tables S3 and S4.

First-generation ligands; on the day of sealing the cell					
Anchored dye	$J_{SC}$ / mA cm <sup>-2</sup>	$V_{OC}$ / mV	$ff$	$\eta$ / %	□□□□□□□□ □ $\eta$ / %□
[Cu( <b>13</b> )( <b>1</b> )] <sup>+</sup>	5.47	490	69.4	1.86	25.1
[Cu( <b>13</b> )( <b>2</b> )] <sup>+</sup>	4.65	475	69.8	1.54	20.8
[Cu( <b>13</b> )( <b>3</b> )] <sup>+</sup>	3.94	479	69.6	1.31	17.7
[Cu( <b>13</b> )( <b>4</b> )] <sup>+</sup>	4.07	491	71.8	1.43	19.3
[Cu( <b>13</b> )( <b>5</b> )] <sup>+</sup>	5.35	492	70.4	1.85	25.0
[Cu( <b>13</b> )( <b>6</b> )] <sup>+</sup>	2.94	485	68.3	0.97	13.1
N719	16.31	637	71.3	7.41	100.0

Second-generation ligands; on the day of sealing the cell					
Anchored dye	$J_{SC}$ / mA cm <sup>-2</sup>	$V_{OC}$ / mV	$ff$	$\eta$ / %	□□□□□□□□ □ $\eta$ / %
[Cu( <b>13</b> )( <b>7</b> )] <sup>+</sup>	4.32	509	68.1	1.50	20.3
[Cu( <b>13</b> )( <b>8</b> )] <sup>+</sup>	4.08	469	67.9	1.30	17.6
[Cu( <b>13</b> )( <b>9</b> )] <sup>+</sup>	2.60	428	65.3	0.73	9.9
[Cu( <b>13</b> )( <b>10</b> )] <sup>+</sup>	2.73	459	68.5	0.86	11.6
[Cu( <b>13</b> )( <b>11</b> )] <sup>+</sup>	1.78	418	67.2	0.50	6.8
[Cu( <b>13</b> )( <b>12</b> )] <sup>+</sup>	1.63	411	61.1	0.41	5.5
N719	16.44	647	69.5	7.40	100.0

### DSC performances: influence of solvent in the dye dipping cycles

We now return to the influence of the solvent during the dye dipping cycle when making the solar cells. Tables S3 and S4<sup>†</sup> give DSC parameters for cells (including duplicates) which were fabricated using CH<sub>2</sub>Cl<sub>2</sub> solutions of the homoleptic dyes. Measurements were made over a three week period and Figs. S6 and S7<sup>†</sup> summarize the  $J$ - $V$  characteristics. Data for the best performing cells on the day of sealing are presented in Table 6, and Figs. 18 and 19 show  $J$ - $V$  curves for the first- and second-generation dyes, respectively. A comparison of the data in Table 6 with those in Tables 2 and 3 indicates that, in general, the conversion efficiencies are higher when acetone is used during cell fabrication. It is difficult to see unambiguous trends between the DSC performances and the 6,6'-substituents in the ancillary ligand. However, in all cases, the dyes containing the methyl substituents perform well. The worst performing dyes contain the bulky 2-naphthyl groups, irrespective of solvent, and the EQE spectra in Figs. 17 and 20 confirm the poorest electron injection as a function of wavelength for dyes with ligands **6** and **12**.

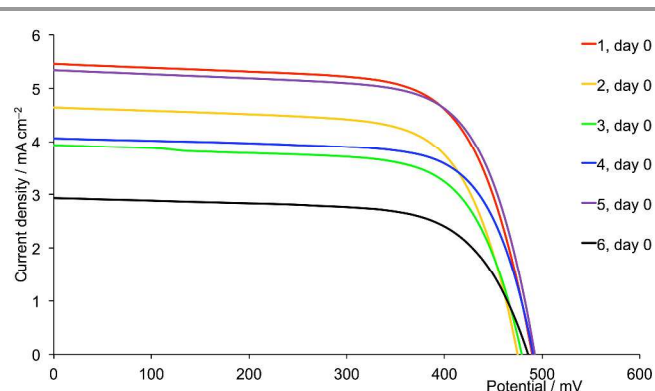


Fig. 18 J-V curves for dyes  $[\text{Cu}(\mathbf{13})(\text{L})]^+$  with  $\text{L} = \mathbf{1-6}$  on day of sealing the DSCs (day 0).  $\text{CH}_2\text{Cl}_2$  was used in the  $[\text{CuL}_2][\text{PF}_6]$  dipping cycle.

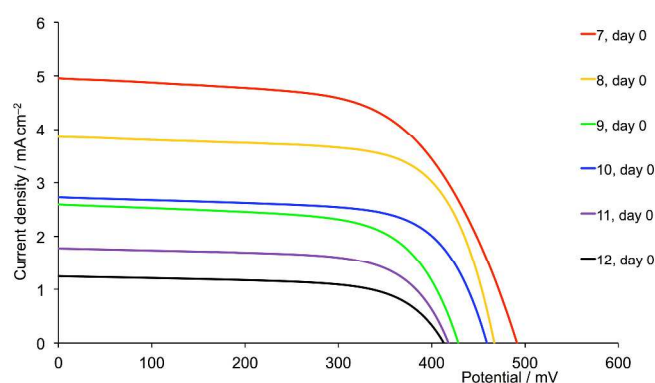


Fig. 19 J-V curves for dyes  $[\text{Cu}(\mathbf{13})(\text{L})]^+$  with  $\text{L} = \mathbf{7-12}$  on day of sealing the DSCs (day 0).  $\text{CH}_2\text{Cl}_2$  was used in the  $[\text{CuL}_2][\text{PF}_6]$  dipping cycle.

For the second-generation dyes (Fig. 19), the DSC performance corresponds quite well to the steric demands of the 6,6'-substituents, the best  $V_{\text{OC}}$ ,  $J_{\text{SC}}$  and  $\eta$  values being observed when methyl groups are used. The EQE spectra for these dyes (Fig. 20b) are also consistent with this performance ordering, and we again (compare red curves in Figs. 17b and 20b) observe extension of the EQE spectrum of the dye containing **7** to lower energy compared to the remaining dyes.

One of the most dramatic differences between performances of DSCs assembled using acetone or  $\text{CH}_2\text{Cl}_2$  copper(I) complex solutions is seen with the 6,6'-diphenyl substituted ancillary ligands. The performance of DSCs containing  $[\text{Cu}(\mathbf{13})(\mathbf{5})]^+$  (first-generation, phenyl) improves when  $\text{CH}_2\text{Cl}_2$  is used instead of acetone. For the  $\text{CH}_2\text{Cl}_2$ -derived dyes, a ripening effect is observed (Table S3<sup>†</sup>) with  $\eta$  increasing from 1.85 to 2.06% (25.0 to 26.0% relative to N719), mainly due to an increase in  $V_{\text{OC}}$  from 492 to 537 mV (Fig. S6<sup>†</sup>). For the  $\text{CH}_2\text{Cl}_2$  dye solutions,  $[\text{Cu}(\mathbf{13})(\mathbf{5})]^+$  is the optimum dye. However, extending the hole transporting domain appears to be unfavourable with losses in both  $V_{\text{OC}}$  and  $J_{\text{SC}}$  (Fig. 18 versus 19, purple curves). The values of  $\text{EQE}_{\text{max}}$  are 42.2% (at  $\lambda_{\text{max}} = 470$  nm) for  $[\text{Cu}(\mathbf{13})(\mathbf{5})]^+$  and 18.0% (at  $\lambda_{\text{max}} = 480$  nm) for  $[\text{Cu}(\mathbf{13})(\mathbf{11})]^+$ . DSCs with  $[\text{Cu}(\mathbf{13})(\mathbf{5})]^+$  (first-generation, phenyl) show similar values of  $V_{\text{OC}}$ ,  $J_{\text{SC}}$  and  $\eta$  to those with  $[\text{Cu}(\mathbf{13})(\mathbf{1})]^+$  (first-generation, methyl). We attribute the loss in performance on going from  $[\text{Cu}(\mathbf{13})(\mathbf{5})]^+$  to  $[\text{Cu}(\mathbf{13})(\mathbf{11})]^+$  to

dye aggregation arising from intermolecular interactions involving the phenyl substituents and dendron in the second-generation **11**.

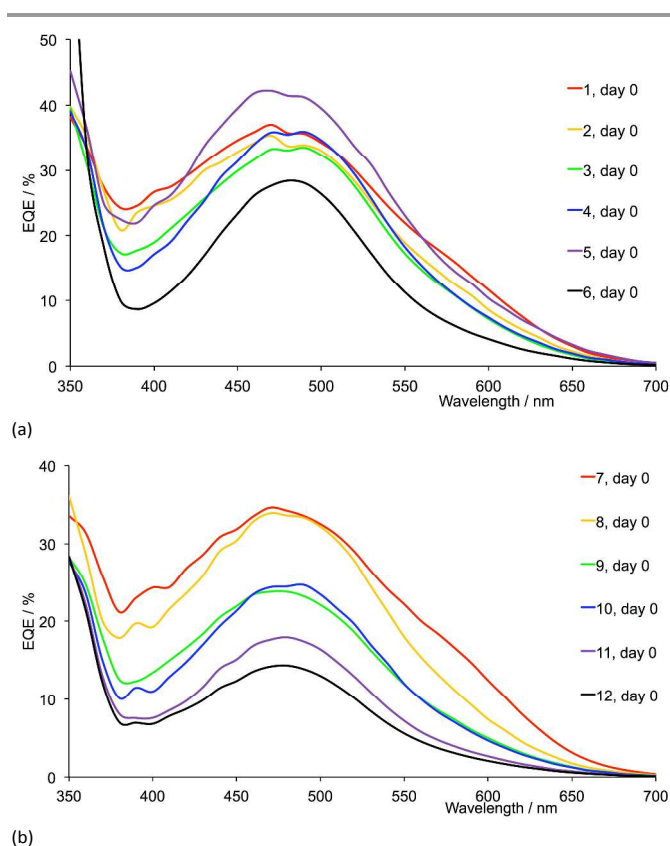


Fig. 20 EQE spectra (on the day of sealing) of DSCs with dyes containing ligands (a) **1-6** and (b) **7-12**.  $\text{CH}_2\text{Cl}_2$  was used in the  $[\text{CuL}_2][\text{PF}_6]$  dipping cycle.

## Conclusions

We have prepared and characterized two series of homoleptic  $[\text{CuL}_2]^+$  complexes containing bpy-derived ligands with different 6,6'-substituents, and either first-generation (ligands **1-6**) or second-generation (ligands **7-12**) hole transporting dendrons. FTO/TiO<sub>2</sub> electrodes were functionalized with the phosphonic acid **13**. Ligand exchange using either  $\text{CH}_2\text{Cl}_2$  or acetone solutions of  $[\text{CuL}_2]^+$  gave two series of surface-bound heteroleptic dyes. Solid-state absorption spectra of dye-covered electrodes show that uptake of the dye is improved if acetone rather than  $\text{CH}_2\text{Cl}_2$  is used in the dye-dipping cycle.

When acetone is used in the dye-soaking process, the best DSC efficiencies are obtained using the second generation dyes except for those with 2-naphthyl groups where low  $J_{\text{SC}}$  values contribute to a poor performance. The enhancement on going from first- to second-generation dendron is consistent with increased absorbance in the solid-state absorption spectra. The dyes that perform most efficiently, both for first and generation-ancillary ligands, are those with the methyl or *n*-butyl substituents. The EQE spectra of the DSCs containing the

methyl-containing ancillary ligands show extension of the band to lower energy, consistent with electron injection over a wider range of wavelengths compared to the other dyes.

Overall, the DSC performances for cells made using acetone in the dye-dipping cycle are better than those made using CH<sub>2</sub>Cl<sub>2</sub> solutions. For dyes assembled in CH<sub>2</sub>Cl<sub>2</sub>, those with ancillary ligands **1** and **7** (methyl groups) perform well, and exhibit the highest  $V_{OC}$ ,  $J_{SC}$  and  $\eta$  values as well as EQE spectra that extend further towards higher wavelengths than the other dyes. The EQE spectra indicate that dyes containing the 2-naphthyl groups in L<sub>ancillary</sub> show the poorest electron injection, consistent with low  $J_{SC}$  values. We conclude that incorporation of these large aromatic substituents is detrimental to DSC performance. In contrast, the first-generation 6,6'-diphenyl-substituted ancillary ligand, **5**, gives a dye that performs as well as that containing **1** (methyl groups), and for CH<sub>2</sub>Cl<sub>2</sub>-derived dyes, [Cu(**13**)(**5**)]<sup>+</sup> is the optimum dye. However, the performance dramatically falls on going to the second-generation analogue **11**.

Our overall conclusions are among the [Cu(**13**)(L<sub>ancillary</sub>)]<sup>+</sup> dyes studied, the most promising L<sub>ancillary</sub> ligands are **1** and **5** (methyl or phenyl substituents) if CH<sub>2</sub>Cl<sub>2</sub> is used in the dye-dipping cycle. Generally, acetone is favoured over CH<sub>2</sub>Cl<sub>2</sub> in the dye-assembly process, and gives adsorbed dyes that exhibit higher absorbances in the solid-state absorption spectra and enhanced conversion efficiencies. Use of the bulky 2-naphthyl substituents militates against good DSC performance. We will report on the effects of adding the co-adsorbant chenodeoxycholate to these DSC systems in the near future.

## Acknowledgements

The European Research Council (Advanced Grant 267816 LiLo), Swiss National Science Foundation and University of Basel are acknowledged for financial support. Cathrin Ertl, Roché Walliser and Dr Colin Martin are thanked for recording 500 NMR spectra, and Dr Collin Morris is acknowledged for recording the SEM image at the ZMB (University of Basel).

## Notes and references

Department of Chemistry, University of Basel, Spitalstrasse 51, CH4056 Basel, Switzerland. Tel: +41 61 267 1008; E-mail: edwin.constable@unibas.ch; catherine.housecroft@unibas.ch.

† Electronic Supplementary Information (ESI) available: Syntheses and characterization of 4,4'-bis(4-bromophenyl)-6,6'-di(naphthalen-2-yl)-2,2'-bipyridine and ligands **2–6**, **8–12**; Fig. S1. SEM image of commercial electrode. Figs. S2–S6: Additional  $J-V$  curves and EQE spectra; Tables S1–S4: DSC parameters for all cells including duplicate data sets. See DOI: 10.1039/b000000x/

- G. C. Vougioukalakis, A. I. Philippopoulos, T. Stergiopoulos and P. Falaras, *Coord. Chem. Rev.*, 2011, **255**, 2602 and references therein.
- N. Armaroli, *Chem. Soc. Rev.*, 2001, **30**, 113.
- N. Armaroli, *Top. Curr. Chem.*, 2007, **280**, 69.
- N. Alonso-Vante, J-F. Nierengarten, J.-P. Sauvage, *J. Chem. Soc. Dalton Trans.*, 1994, 1650.
- N. Robertson, *ChemSusChem*, 2008, **1**, 977.
- B. Bozic-Weber, E. C. Constable and C. E. Housecroft, *Chem. Soc. Rev.*, 2013, **257**, 3089.
- M. Sandroni, L. Favereau, A. Planchat, H. Akdas-Kilig, N. Szuwarski, Y. Pellegrin, E. Blart, H. Le Bozec, M. Boujtita, F. Odobel, *J. Mater. Chem. A*, 2014, **2**, 9944.
- B. Bozic-Weber, S. Brauchli, E. C. Constable, S. O. Furer, C. E. Housecroft and I. A. Wright, *Phys. Chem. Chem. Phys.*, 2013, **15**, 4500
- B. Bozic-Weber, E. C. Constable, C. E. Housecroft, P. Kopecky, M. Neuburger and J. A. Zampese, *Dalton Trans.*, 2011, **40**, 12584
- B. Bozic-Weber, S. Y. Brauchli, E. C. Constable, S. O. Furer, C. E. Housecroft, F. J. Malzner, I. A. Wright and J. A. Zampese, *Dalton Trans.*, 2013, **42**, 12293.
- G. J. Kubas, *Inorg. Synth.*, 1990, **28**, 68.
- Bruker Analytical X-ray Systems, Inc., 2006, APEX2, version 2 User Manual, M86-E01078, Madison, WI.
- G. M. Sheldrick, *Acta Crystallogr., Sect. A*, 2008, **64**, 112.
- I. J. Bruno, J. C. Cole, P. R. Edgington, M. K. Kessler, C. F. Macrae, P. McCabe, J. Pearson and R. Taylor, *Acta Crystallogr., Sect. B* 2002, **58**, 389.
- C. F. Macrae, I. J. Bruno, J. A. Chisholm, P. R. Edgington, P. McCabe, E. Pidcock, L. Rodriguez-Monge, R. Taylor, J. van de Streek and P. A. Wood, *J. Appl. Cryst.*, 2008, **41**, 466.
- S. Ito, P. Chen, P. Comte, M. K. Nazeeruddin, P. Liska, P. Péchy and M. Grätzel, *Prog. Photovoltaics: Res. Appl.*, 2007, **15**, 603.
- S. Ito, T. N. Murakami, P. Comte, P. Liska, C. Grätzel, M. K. Nazeeruddin and M. Grätzel, *Thin Solid Films*, 2008, 516, 4613.
- F. Kröhnke, *Synthesis*, 1976, 1.
- See for example: P. V. James, K. Yoosaf, J. Kumar, K. G. Thomas, A. Listorti, G. Accorsi and N. Armaroli, *Photochem. Photobiol. Sci.*, 2009, **8**, 1432.
- B. Bozic-Weber, V. Chaurin, E. C. Constable, C. E. Housecroft, M. Meuwly, M. Neuburger, J. A. Rudd, E. Schönhofer and L. Siegfried, *Dalton Trans.*, 2012, **41**, 14157.
- M. K. Eggleston, D. R. McMillin, K. S. Koenig and A. J. Pallenberg, *Inorg. Chem.*, 1997, **36**, 172
- R. J. P. Williams, *Eur. J. Biochem.*, 1995, **234**, 363.



- 23 Y. Jahng, J. Hazelrigg, D. Kimball, E. Riesgo, R. Wu and R. P. Thummel, *Inorg. Chem.*, 1997, **36**, 5390.
- 24 D. V. Scaltrito, D. W. Thompson, J. A. O'Callaghan and G. J. Meyer, *Coord. Chem. Rev.*, 2000, **208**, 243.
- 25 T. E. Hewat, L. J. Yellowlees and N. Robertson, *Dalton Trans.*, 2014, **43**, 4127.
- 26 H. J. Snaith, *Energy Environ. Sci.*, 2012, **5**, 6513.

TOC to accompany

**Influential factors controlling the photoresponse of copper(I) diimine dyes containing hole-transporting dendrons in dye-sensitized solar cells: substituent and solvent effects**

S. Y. Brauchli, B. Bozic-Weber, E. C. Constable, N. Hostettler, C. E. Housecroft and J. A. Zampese

A detailed study of how two factors (substituents on ancillary ligands and solvents during dye assembly) affect performances of copper(I) diimine dyes in DSCs with phosphonic acid anchoring groups is presented.

