

# RSC Advances




This is an *Accepted Manuscript*, which has been through the Royal Society of Chemistry peer review process and has been accepted for publication.

*Accepted Manuscripts* are published online shortly after acceptance, before technical editing, formatting and proof reading. Using this free service, authors can make their results available to the community, in citable form, before we publish the edited article. This *Accepted Manuscript* will be replaced by the edited, formatted and paginated article as soon as this is available.

You can find more information about *Accepted Manuscripts* in the [Information for Authors](#).

Please note that technical editing may introduce minor changes to the text and/or graphics, which may alter content. The journal's standard [Terms & Conditions](#) and the [Ethical guidelines](#) still apply. In no event shall the Royal Society of Chemistry be held responsible for any errors or omissions in this *Accepted Manuscript* or any consequences arising from the use of any information it contains.

## Graphical Abstract

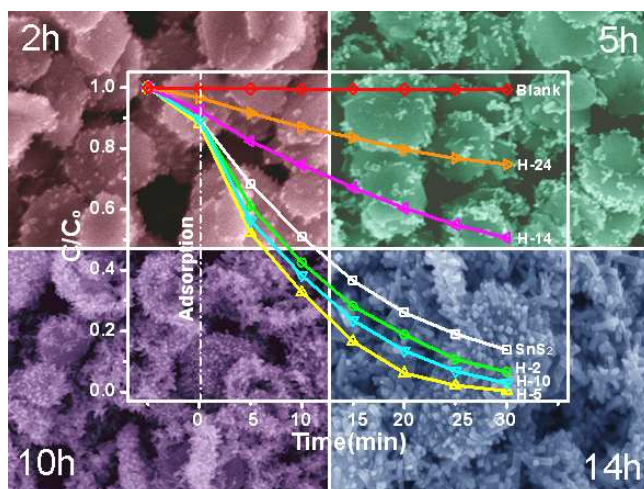

A novel and facile hydrothermal-assisted self-hydrolysis route has been proposed for the controllable preparation of SnS<sub>2</sub>/SnO<sub>2</sub> heterostructured nanoplates (HNPs), which only employ pregrown SnS<sub>2</sub> nanoplates as the precursors without using any additional surfactant. Very interestingly, the size, morphology and content of SnO<sub>2</sub> in the SnS<sub>2</sub>/SnO<sub>2</sub> HNPs can be conveniently tuned by just varying the reaction duration in the self-hydrolysis process.

Cite this: DOI: 10.1039/c0xx00000x

www.rsc.org/xxxxxx

ARTICLE TYPE

# Controllable growth of SnS<sub>2</sub>/SnO<sub>2</sub> heterostructured nanoplates via a hydrothermal-assisted self-hydrolysis process and their visible-light-driven photocatalytic reduction of Cr(VI)

Liyuan Mao,<sup>‡</sup> Jingjing Li,<sup>‡</sup> Yunlong Xie, Yijun Zhong, and Yong Hu\*

Received (in XXX, XXX) Xth XXXXXXXXXX 20XX, Accepted Xth XXXXXXXXXX 20XX

DOI: 10.1039/b000000x


A novel and facile hydrothermal-assisted self-hydrolysis route has been proposed for the controllable preparation of SnS<sub>2</sub>/SnO<sub>2</sub> heterostructured nanoplates (HNPs). Benefiting from the unique structural features, the as-prepared SnS<sub>2</sub>/SnO<sub>2</sub> HNPs exhibit significantly enhanced visible-light-driven photocatalytic activity in the reduction of aqueous Cr(VI).

Semiconductor hetero-nanostructures, composed of chemically distinct components, possess unique and enhanced properties in contrast with individual component materials, arising from strong interfacial interactions at the nanoscale, which have led to revolutionary new applications in various areas, such as catalysis, optical, magnetic, electrical, sensors, and so on.<sup>1-9</sup> As a kind of CdI<sub>2</sub>-type layered semiconductor, SnS<sub>2</sub> displays a wide photoelectrochemical response in the visible light region with a narrow band gap of about 2.2eV.<sup>10, 11</sup> Compared with other metal sulfides, such as CdS, SnS<sub>2</sub> is low toxicity and good chemical stability makes it becomes a promising visible-light-driven photocatalyst.<sup>12-14</sup> SnO<sub>2</sub> is a stable oxide semiconductor with a wide band gap of about 3.5-3.8 eV, which can couple to SnS<sub>2</sub> to form a heterostructure for various potential applications, such as photocatalysis, gas-sensing, and lithium-ion batteries, etc.<sup>15-17</sup> Especially, SnS<sub>2</sub>/SnO<sub>2</sub> hetero-nanostructures have demonstrated enhanced photocatalytic activity because of enhanced charge separation of photogenerated carriers through interfacial charge transfer.<sup>15, 16</sup> Lots of research efforts have been devoted to the fabrication of this kind advantageous heterostructure.<sup>17-19</sup> However, to the best of our knowledge, there is no report on solution fabrication of SnS<sub>2</sub>/SnO<sub>2</sub> heterostructures via an in-situ hydrolysis process without employing any additional metal salt.

In this work, we have developed a controllable hydrothermal-assisted self-hydrolysis route to prepare SnS<sub>2</sub>/SnO<sub>2</sub> heterostructured nanoplates (HNPs), which only use the pregrown SnS<sub>2</sub> nanoplates (NPs) as precursors without employing any additional surfactant. This is a facile and novel method, and a series of SnS<sub>2</sub>/SnO<sub>2</sub> HNPs with the different SnO<sub>2</sub> contents have been successfully obtained by self-hydrolysis of SnO<sub>2</sub> NPs in the presence of citric acid at 180 °C for different time. A series of samples prepared with the different reaction time (0, 2, 5, 10, 14, and 24h) in the hydrothermal process were denoted as pure SnS<sub>2</sub>, H-2, H-5, H-10, H-14 and H-24, respectively. It has been


discovered that the reaction duration plays a very important role in determining the size, morphology and composition of the final products. Benefiting from the unique structural features, the as-prepared SnS<sub>2</sub>/SnO<sub>2</sub> HNPs exhibit significantly enhanced visible-light-driven photocatalytic activity in the reduction of aqueous Cr(VI). Furthermore, the mechanisms of the optimal SnO<sub>2</sub> content to reach the maximum photocatalytic activity in the SnS<sub>2</sub>/SnO<sub>2</sub> HNPs are proposed and discussed.

The phase composition and structure of the as-prepared pure SnS<sub>2</sub> NPs and SnS<sub>2</sub>/SnO<sub>2</sub> HNPs obtained with the different reaction times were first examined by powder X-ray diffraction (XRD) analysis, as shown in Fig. 1. For pure SnS<sub>2</sub> NPs, all the diffraction peaks can be well indexed to the pure hexagonal phase SnS<sub>2</sub> (JCPDS card no. 23-0677) with lattice constants of a = 3.648 Å and c = 5.899 Å. No impurity peaks are detected which shows that the products are of pure phase. For SnS<sub>2</sub>/SnO<sub>2</sub> HNPs, in addition to the obvious SnS<sub>2</sub> patterns, broadened diffraction peaks at 2θ values of 26.6°, 33.9°, 37.9°, 51.8°, 54.8°, 57.8°, 61.9°, 64.7° and 65.9° match well with the (110), (101), (200), (211), (220), (002), (310), (112) and (301) crystal planes of tetragonal phase SnO<sub>2</sub> (JCPDS card no. 41-1445, a = 4.738 Å), respectively. In particular, the peak intensity of the SnO<sub>2</sub> component gets stronger with the increase of the hydrolysis time, indicating the amount of SnO<sub>2</sub> in the hybrid system is increased gradually. The energy dispersive X-ray spectroscopy (EDS) analysis was also performed to confirm the existence of Sn, O, and S elements in the hetero-nanostructures (Fig. S1, see ESI<sup>†</sup>). The SnS<sub>2</sub>/SnO<sub>2</sub> molar ratio in the nanocomposites (Table S1, see ESI<sup>†</sup>) decreases with the increase of reaction time in the hydrothermal process, consistent with the XRD analysis.

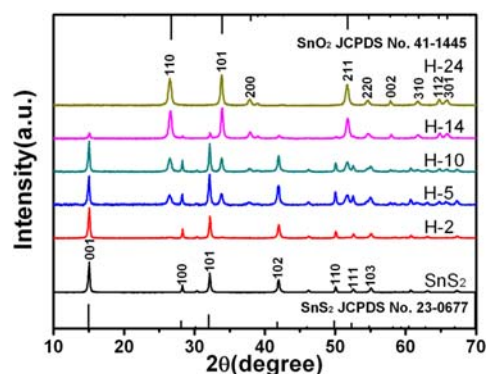


**Fig. 1** XRD patterns of as-prepared pure SnS<sub>2</sub> NPs and SnS<sub>2</sub>/SnO<sub>2</sub> HNPs obtained with different reaction durations.

The typical scanning electron microscopy (SEM) images of the as-obtained pure SnS<sub>2</sub> NPs and SnS<sub>2</sub>/SnO<sub>2</sub> HNPs are shown in Fig. 2. A panoramic view of the SEM image (Fig. 2a) of pure SnS<sub>2</sub> shows that the product is completely composed of monodispersed hexagonal plates with an average size of around 500 nm in diameter. The high-magnification image (inset in Fig. 2a) reveals the surface of SnS<sub>2</sub> NP is relatively smooth, without the presence of any secondary nanostructures. Time-dependent experiments are carried out to understand the formation process of HNPs, Fig. 2b-f shows the SEM images of five samples obtained with different reaction durations in the self-hydrolysis process. As can be seen in Fig. 2b, at the early stage of the reaction (2h), some particle subunits are formed on the surface of SnS<sub>2</sub> NPs. When the reaction duration is increased to 5-14h (Fig. 2c, d and e), the product obviously contains a large portion of irregular particles deposited on the surface of NPs. And, the nanoparticles gradually grow into short nanorods with the increasing of reaction time. When the reaction duration is further prolonged, the SnS<sub>2</sub> NPs can hardly be observed due to the more Sn<sup>4+</sup> ions released from SnS<sub>2</sub> (Fig. 2f).

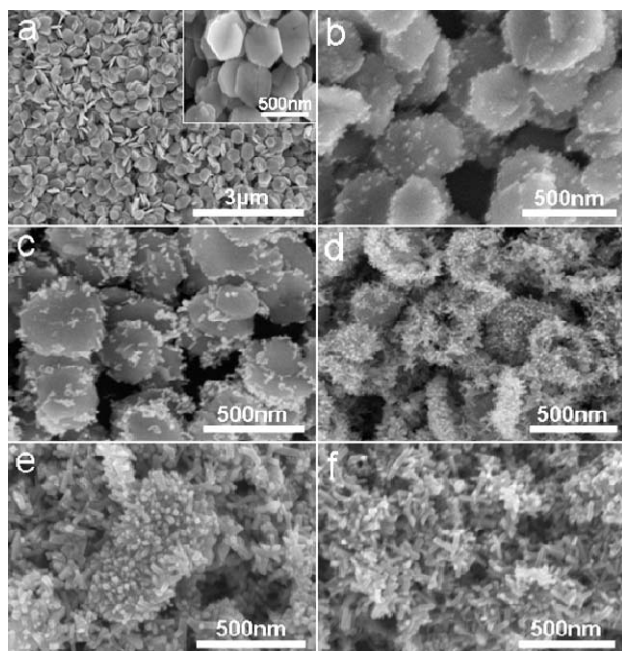



**Fig. 2** SEM images of the as-obtained samples with the different reaction times: (a) pure SnS<sub>2</sub>, (b) H-2, (c) H-5, (d) H-10, (e) H-14, and (f) H-24.

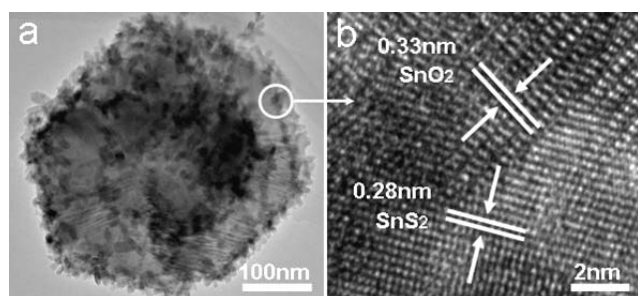


**Fig. 3** (a) TEM and (b) HRTEM images of the as-obtained sample H-5.

Transmission electron microscopy (TEM) and high-resolution (HR)TEM measurements provide further information about the microstructure of the products. Fig. 3a shows typical TEM image of the as-prepared H-5 sample, where we can clearly see that monodispersed SnO<sub>2</sub> nanoparticles are tightly grown on the surface of the SnS<sub>2</sub> NP. The interface of SnS<sub>2</sub>/SnO<sub>2</sub> hetero-nanostructure is further confirmed by the HRTEM image (Fig. 3b), the fringe interval of 0.28 nm corresponds to the interplanar spacing of the (101) planes of hexagonal phase SnS<sub>2</sub>, while the 0.33 nm interval is in agreement with the (110) interplanar spacing of tetragonal phase SnO<sub>2</sub>.

Based on all the above experimental results, the growth process of the SnS<sub>2</sub>/SnO<sub>2</sub> HNPs is illustrated in Scheme 1. In an acidic solution, Sn<sup>4+</sup> ions hydrolyze first and then further dehydrate to produce SnO<sub>2</sub> according to reactions 1 (eqn (1)) and 2 (eqn (2)) at 180 °C under hydrothermal treatment.<sup>20, 21</sup>



When the reaction time is prolonged, the successively released Sn<sup>4+</sup> from the dissociation reactions of SnS<sub>2</sub> will further hydrolyze and nucleate to form SnO<sub>2</sub> nanoparticles on the surface of SnS<sub>2</sub> NPs. However, the-obtained SnO<sub>2</sub> nanoparticles with high-energy sites will further grow according to crystallographic-oriented direction to form short nanorods with the increasing of reaction duration.<sup>5</sup> Meanwhile, SnS<sub>2</sub> NPs are gradually dissolved to provide continuous Sn<sup>4+</sup> ions for the growth of SnO<sub>2</sub> so that SnO<sub>2</sub> short nanorods are finally obtained while very little SnS<sub>2</sub> are left after 24 h in the hydrothermal treatment.

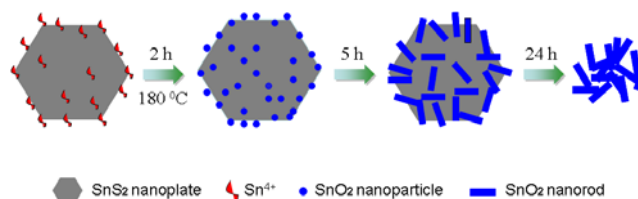

**Scheme 1** Schematic illustration of the conversion processes from SnS<sub>2</sub> NP to SnS<sub>2</sub>/SnO<sub>2</sub> HNP via a hydrothermal-assisted self-hydrolysis process.

The UV-vis diffuse reflectance spectra of the as-prepared pure SnS<sub>2</sub> NPs and SnS<sub>2</sub>/SnO<sub>2</sub> HNPs are investigated (Fig. S2a, see ESI†). The pure SnS<sub>2</sub> NPs display optical absorption edge at around 550 nm, which may be assigned to the intrinsic bandgap absorption of SnS<sub>2</sub>.<sup>22</sup> The absorption curves of the as-obtained sample H-2, H-5 and H-10 are similar to SnS<sub>2</sub> NPs, but the absorption intensity decreases with the less content SnS<sub>2</sub>. For sample H-24, the sharp absorption onset at around 350 nm, corresponding to the big energy band gap of SnO<sub>2</sub> (3.5 eV),<sup>23</sup> which indicates that SnS<sub>2</sub> NPs are almost converted into SnO<sub>2</sub>. The band gaps (E<sub>g</sub>) of the samples are derived based on the theory of optical absorption using the relation (eqn (3)).<sup>24</sup>

$$(\alpha h\nu)^n = k(h\nu - E_g) \quad (3)$$

Where  $h\nu$  is the photon energy,  $\alpha$  is the absorption coefficient,  $k$  is a constant relative to the material, and  $n$  is either 2 for a direct transition or 1/2 for an indirect transition. The E<sub>g</sub> of the as-prepared pure SnS<sub>2</sub>, H-2, H-5, H-10, H-14 and H-24 are estimated to be 2.23, 2.21, 2.21, 2.24, 2.24 and 3.51, respectively, which indicates that SnS<sub>2</sub>/SnO<sub>2</sub> have the potential to be efficient visible light-driven photocatalysts (Fig. S2b, see ESI†). To further



investigate the heterojunction interface is beneficial to photogenerated charge separation, the photocurrent transient response measurement of pure SnO<sub>2</sub> and SnS<sub>2</sub>/SnO<sub>2</sub> heterostructure (sample H-5) is performed. Fig. S3 (see ESI†) shows the rapid and consistent photocurrent responses for each switch-on and -off event in multiple 100s on-off cycles under visible-light illumination. It is worth to note that the photocurrent density of the SnS<sub>2</sub>/SnO<sub>2</sub> heterostructure is about 40 μA·cm<sup>-2</sup>, almost 4 times higher than that of pure SnS<sub>2</sub>, which is about 10 μA·cm<sup>-2</sup>. The enhanced photocurrent response of the as-prepared SnS<sub>2</sub>/SnO<sub>2</sub> heterostructure indicates higher separation efficiency of the photoinduced carriers and a lower recombination rate in such hybrid structures under visible-light illumination. This can be explained by the favorable transfer of electrons from SnS<sub>2</sub> to SnO<sub>2</sub> that reduces the recombination of electron-hole pairs. Therefore, the SnS<sub>2</sub>/SnO<sub>2</sub> HNPs exhibit the enhanced photoreduction of Cr(VI).

The photocatalytic reduction tests of Cr(VI) species in an aqueous solution under visible-light irradiation using the as-prepared SnS<sub>2</sub>/SnO<sub>2</sub> HNPs as photocatalysts were further carried out. As can be seen in Fig. 4a, where *C* is the concentration of Cr(VI) after light irradiation and *C*<sub>0</sub> is the initial concentration of Cr(VI) before dark adsorption. After irradiated for 30 min, there is no obvious change in the Cr(VI) concentration after visible-light irradiation in the absence of the catalysts, whereas nearly 86.2%, 93.4%, 99.7%, 97.2%, 49.4% and 25.3% of Cr(VI) is degraded by samples pure SnS<sub>2</sub>, H-2, H-5, H-10, H-14 and H-24, respectively. The sample H-5 exhibits the highest photocatalytic activity among all of the samples, which indicates that there is an optimal loading amount of SnO<sub>2</sub> nanoparticles on the SnS<sub>2</sub> NPs. We have further studied the stability and reusability of sample H-5, as shown in Fig. 4b. After six cycles of photocatalytic reduction of Cr(VI), there is still 79.1% of Cr(VI) can be reduced. This loss might be mainly caused by the deposited Cr(III) species on the surface of SnS<sub>2</sub>/SnO<sub>2</sub> HNPs,<sup>12, 25</sup> and partly caused by the loss of the photocatalysts during each collection and rinsing cycle. The superior photocatalytic reduction activity of these hetero-nanostructures may be ascribed as follows. A schematic diagram representing charge transfer process in the SnS<sub>2</sub>/SnO<sub>2</sub> HNPs is illustrated in Scheme S1 (see ESI†). The conduction band of SnS<sub>2</sub> is more negative than that of SnO<sub>2</sub>, the electrons quickly transfer to the conduction band of SnO<sub>2</sub> when SnS<sub>2</sub> is excited under visible-light illumination, whereas the generated holes accumulate in the valence band of SnS<sub>2</sub>. The efficient separation of the electron-hole pairs and reduction of charge recombination in the electron transfer process increases both the yield and the lifetime of the photogenerated carriers, and consequently enhances the photocatalytic performance. However, the excessive SnO<sub>2</sub> may reduce the inherent optical absorption of SnS<sub>2</sub> and result in a rapid decrease in photogenerated charges, ultimately reducing the photocatalytic activity. Therefore, the sample H-5 should have the ideal hetero-nanostructure, which possess the optimal balancing of charge separation and transport and hence demonstrate most favorable photocatalytic reduction activity in this particular case. The surface area of the as-prepared pure SnO<sub>2</sub> and SnS<sub>2</sub>/SnO<sub>2</sub> HNPs (sample H-5 and H-24) is measured by the Brunauer-Emmett-Teller (BET) method using an ASAP2020 sorptometer. The as-prepared pure SnS<sub>2</sub>, H-5, and H-24 have a

specific surface area of 12.16, 15.93 and 27.94 m<sup>2</sup>g<sup>-1</sup>, respectively. This result indicates that the surface areas of the as-obtained products gradually increase when the self-hydrolysis reaction time is prolonged. Thus, the specific surface area is not the determining factor in the photocatalytic efficiency.

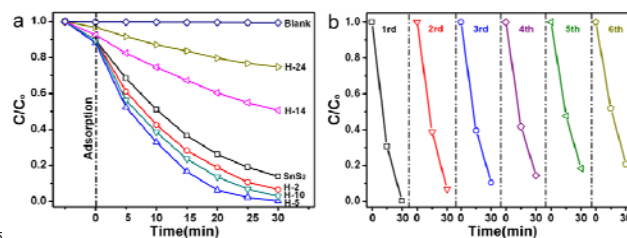


Fig. 5 (a) Photocatalytic reduction of Cr(VI) in the presence of different photocatalysts under visible-light irradiation. (b) Recycling test of photoreduction of Cr(VI) using sample H-5 as the photocatalyst under visible-light irradiation for 30 min.

In summary, we have developed a facile hydrothermal-assisted self-hydrolysis route to form SnS<sub>2</sub>/SnO<sub>2</sub> HNPs, which only use the as-obtained SnS<sub>2</sub> NPs as precursors in the presence of citric acid. It has been found that the size, morphology and content of SnO<sub>2</sub> in the SnS<sub>2</sub>/SnO<sub>2</sub> HNPs can be conveniently tuned by just varying the reaction duration in the hydrothermal treatment. As expected, the as-prepared SnS<sub>2</sub>/SnO<sub>2</sub> HNPs exhibit enhanced visible-light-driven photocatalytic activity in the reduction of aqueous Cr(VI), because the interfacial electron can transfer from SnS<sub>2</sub> to SnO<sub>2</sub> in the SnS<sub>2</sub>/SnO<sub>2</sub> hybrid system. The synthetic method presented here is very simple and cost-effective, and can be extended to prepare other metal sulfide/oxide hetero-nanostructures for a wide range of applications.

#### Acknowledgements

Y. Hu acknowledges financial support from the Natural Science Foundation of China (21171146, 21371152) and Zhejiang Provincial Natural Science Foundation of China (LR14B010001).

#### Notes and references

- Key Laboratory of the Ministry of Education for Advanced Catalysis Materials, Institute of Physical Chemistry, Zhejiang Normal University, Jinhua, 321004, P. R. China. E-mail: yonghu@zjnu.edu.cn
- † These authors contributed equally to this work.
- † Electronic Supplementary Information (ESI) available: [Detailed experimental procedures, additional EDS pattern, UV-vis diffuse reflectance spectra. See DOI: 10.1039/b000000x/]
- Y. R. Wang, W. L. Yang, L. Zhang, Y. Hu and X. W. Lou, *Nanoscale*, 2013, **5**, 10864-10867.
  - H. Y. Zheng, Y. J. Li, H. B. Liu, X. D. Yin and Y. L. Li, *Chem. Soc. Rev.*, 2011, **40**, 4506-4524.
  - W. L. Yang, L. Zhang, Y. Hu, Y. J. Zhong, H. B. Wu and X. W. Lou, *Angew. Chem. Int. Ed.*, 2012, **51**, 11501-11504.
  - X. H. Zhao, P. Wang and B. J. Li, *Chem. Commun.*, 2010, **46**, 6768-6770.
  - Z. Lou, F. Li, J. N. Deng, L. L. Wang and T. Zhang, *ACS Appl. Mater. Interfaces*, 2013, **5**, 12310-12316.
  - L. Y. Mao, Y. R. Wang, Y. J. Zhong, J. Q. Ning and Y. Hu, *J. Mater. Chem. A*, 2013, **1**, 8101-8104.
  - D. Sarkar, G. G. Khan, A. K. Singh and K. Mandal, *J. Phys. Chem. C*, 2012, **116**, 23540-23546.
  - Y. Hu, H. H. Qian, Y. Liu, G. H. Du, F. M. Zhang, L. B. Wang and X. Hu, *CrystEngComm*, 2011, **13**, 3438-3443.
  - B. Mukherjee, A. Peterson and V. Subramanian, *Chem. Commun.*, 2012,

- 48, 2415-2417.
- 10 Y. F. Sun, H. Cheng, S. Gao, Z. H. Sun, Q. H. Liu, Q. Liu, F. C. Lei, T. Yao, J. F. He, S. Q. Wei and Y. Xie, *Angew. Chem. Int. Ed.*, 2012, **51**, 8727-8731.
- 5 11 P. Chen, Y. Su, H. Liu and Y. Wang, *ACS Appl. Mater. Interfaces*, 2013, **5**, 12073-12082.
- 12 Y. C. Zhang, J. Li, M. Zhang and D. D. Dionysiou, *Environ. Sci. Technol.*, 2011, **45**, 9324-9331.
- 13 X. Li, J. Zhu and H. X. Li, *Appl. Catal. B: Environ.*, 2012, **123-124**, 174-181.
- 10 14 Z. Y. Zhang, C. L. Shao, X. H. Li, Y. Y. Sun, M. Y. Zhang, J. B. Mu, P. Zhang, Z. C. Guo and Y. C. Liu, *Nanoscale*, 2013, **5**, 606-618.
- 15 X. L. Zhou, T. F. Zhou, J. C. Hu and J. L. Li, *CrystEngComm*, 2012, **14**, 5627-5633.
- 15 16 Y. C. Zhang, Z. N. Du, K. W. Li, M. Zhang and D. D. Dionysiou, *ACS Appl. Mater. Interfaces*, 2011, **3**, 1528-1537.
- 17 K. Chang, W. X. Chen, H. Li and H. Li, *Electrochim. Acta*, 2011, **56**, 2856-2861.
- 18 Y. C. Zhang, L. Yao, G. Zhang, D. D. Dionysiou, J. Li and X. Du, *Appl. Catal. B: Environ.*, 2014, **144**, 730-738.
- 20 19 Y. C. Zhang, Z. N. Du and M. Zhang, *Mater. Lett.*, 2011, **65**, 2891-2894.
- 20 Z. Y. Wang, Z. C. Wang, S. Madhavi and X. W. Lou, *Chem. Eur. J.*, 2012, **18**, 7561-7567.
- 25 21 Z. H. Wen, G. Wang, W. Lu, Q. Wang, Q. Zhang and J. H. Li, *Cryst. Growth Des.*, 2007, **7**, 1722-1725.
- 22 R. Lucena, F. Fresno and J. C. Conesa, *Appl. Catal. A: Gen.*, 2012, **415-416**, 111-117.
- 23 C. H. Wang, C. L. Shao, X. T. Zhang and Y. C. Liu, *Inorg. Chem.*, 2009, **48**, 7261-7268.
- 30 24 C. Y. Yu, Y. R. Wang, Y. Liu, C. F. Guo and Y. Hu, *Mater. Lett.*, 2013, **100**, 278-281.
- 25 N. Wang, Y. Z. Xu, L. H. Zhu, X. T. Shen and H. Q. Tang, *J. Photochem. Photobiol. A: Chem.*, 2009, **201**, 121-127.
- 35