

# RSC Advances




This is an *Accepted Manuscript*, which has been through the Royal Society of Chemistry peer review process and has been accepted for publication.

*Accepted Manuscripts* are published online shortly after acceptance, before technical editing, formatting and proof reading. Using this free service, authors can make their results available to the community, in citable form, before we publish the edited article. This *Accepted Manuscript* will be replaced by the edited, formatted and paginated article as soon as this is available.

You can find more information about *Accepted Manuscripts* in the [Information for Authors](#).

Please note that technical editing may introduce minor changes to the text and/or graphics, which may alter content. The journal's standard [Terms & Conditions](#) and the [Ethical guidelines](#) still apply. In no event shall the Royal Society of Chemistry be held responsible for any errors or omissions in this *Accepted Manuscript* or any consequences arising from the use of any information it contains.

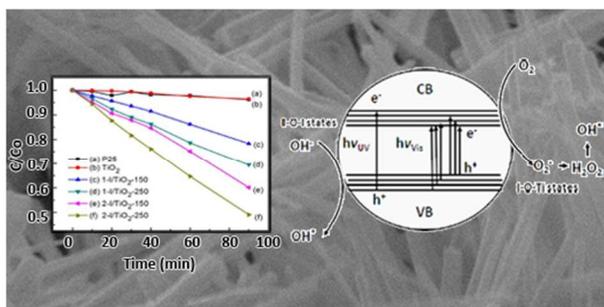

Oxygen vacancies induced by multi-valences of iodine in two-step hydrothermal synthesized I/TiO<sub>2</sub> with enhanced visible photoactivity

## Generation of oxygen vacancies in visible light activated one-dimensional iodine TiO<sub>2</sub> photocatalysts

Wenjuan Li <sup>a,b</sup>, Robert Liang <sup>b,c</sup>, Anming Hu <sup>b,d</sup>, Zhaohui Huang <sup>a</sup> and Y. Norman Zhou <sup>b,c,\*</sup>

<sup>a</sup> School of Materials Science and Engineering, China University of Geosciences, Beijing 100083, P.R. China

<sup>b</sup> Department of Mechanical and Mechatronics, University of Waterloo, Waterloo N2L 3G1, Ontario, Canada

<sup>c</sup> Waterloo Institute for Nanotechnology, University of Waterloo, Waterloo, ON, N2L 3G1, Ontario, Canada

<sup>d</sup> Mechanical, Aerospace, & Biomedical Engineering Department, University of Tennessee – Knoxville, Knoxville, TN, 37996-2210, USA

\* Corresponding author:

Tel. +1-519-888-4567 ext.36095

Email: nzhou@uwaterloo.ca

**Abstract:** A facile and efficient way of generating oxygen vacancies in visible light activated one-dimensional iodine doped TiO<sub>2</sub> photocatalysts was first reported in this work. A two-step hydrothermal synthesis was used to synthesize TiO<sub>2</sub> nanomaterials modified by iodic acid (HIO<sub>3</sub>) as a dopant. Detailed analysis was conducted to illustrate the intrinsic doping/reaction mechanisms of iodic acid on the modification of the TiO<sub>2</sub> matrix. The phase and structure evolution were deduced from x-ray diffraction (XRD), Raman, and scanning electron microscopy (SEM). X-ray photoelectron spectroscopy (XPS) was conducted to analyze the generation of oxygen vacancies and the formation of I-O-Ti bonds in the TiO<sub>2</sub> lattice. Multi-valences of iodine, due to the reduction of iodic acid, facilitated the generation of oxygen vacancies and 3d state Ti<sup>3+</sup> species in the TiO<sub>2</sub> lattice. The visible light absorption and enhanced photocatalytic activity of the TiO<sub>2</sub> nanomaterials were attributed to existing oxygen vacancies, iodine multi-valences in I-O-Ti bonds, and 3d state Ti<sup>3+</sup> sites in TiO<sub>2</sub> lattice. The photocatalytic degradation efficiency under visible light ( $\lambda > 400$  nm) followed a pseudo first-order kinetic model. Rutile nanowires using a two-step synthesis method produced the highest methylene blue (10 mg L<sup>-1</sup>) degradation rate constant, K<sub>ap</sub>, of 7.92×10<sup>-3</sup> min<sup>-1</sup> compared to other synthesized nanomaterials. The K<sub>ap</sub> value obtained was an order of magnitude greater than commercial P25 (3.87×10<sup>-4</sup> min<sup>-1</sup>) and pristine TiO<sub>2</sub> nanowires (4.18×10<sup>-4</sup> min<sup>-1</sup>). The iodine doped TiO<sub>2</sub> photocatalysts can be used in TiO<sub>2</sub>/light irradiation advanced oxidation processes (AOPs) in water treatment using sunlight or a visible light source, rather than an ultraviolet irradiation source.

Keywords: Iodine; hydrothermal; oxygen vacancies; visible light; photocatalysis

## 1. INTRODUCTION

Since the discovery of photoelectrochemical splitting of water on n-TiO<sub>2</sub> electrodes,<sup>1</sup> semiconductor-based TiO<sub>2</sub> materials have been investigated extensively as photo-catalysts for solar energy conversion,<sup>2-4</sup> photoelectrochemical processes,<sup>5,6</sup> and environmental applications.<sup>7,8</sup> TiO<sub>2</sub> nanomaterials are regarded as good photo-catalysts because of their chemical and thermal stability, availability, nontoxicity, and biocompatibility.<sup>1-3</sup> TiO<sub>2</sub> photocatalysts are able to degrade environmental pollutants in the ultraviolet wavelength range effectively. However, the energy efficiency of these photocatalysts is low using solar light because only 3 % - 5% of solar energy exists in the ultraviolet range. Another drawback of TiO<sub>2</sub> photocatalysts are the high recombination rates of photo-induced electron-hole pairs that further reduce their efficiency. In order to completely utilize solar energy, it is of great importance to develop photocatalysts that are able to generate electron-hole pairs via visible light excitation.

Over the past few decades, research work has been done aiming at expanding photoabsorption to the visible light region and enhancing the photocatalytic activities of TiO<sub>2</sub> by doping either non-metal (N,<sup>9-11</sup> C,<sup>12-14</sup> S,<sup>15</sup> I,<sup>16-19</sup> or metal atoms (Fe,<sup>20</sup> Ag,<sup>21</sup> Mo,<sup>22</sup> Cu,<sup>23</sup> Au<sup>24</sup>). Among these modifications, non-metal doped TiO<sub>2</sub> materials exhibit promising visible driven photo-catalytic activities compared to pristine or other metal doped TiO<sub>2</sub> materials. The band gap modification using non-metals does not create recombination centers that occur with metal doping.<sup>11</sup>

Iodine has also been extensively used for visible light activated TiO<sub>2</sub> photocatalysts with multiple chemical states of iodine. The different chemical states of iodine in TiO<sub>2</sub> dramatically affect their photocatalytic activity.<sup>16-19</sup> Iodine doping and surface modification may also induce oxygen vacancies and oxygen sub-stoichiometry, which lowers the bandgap of photocatalysts.<sup>25-27</sup> Oxygen defects, which lie close to the conduction band (CB) of titania, can act as active electron traps. They can be promoted to the surface by visible light absorption where they are involved in degradation of pollutant.<sup>26</sup> TiO<sub>2</sub> with a high oxygen deficiency may possess visible-light absorption and photocatalytic activities under the irradiation of light wavelengths longer than 400 nm, and the overlap between the oxygen defect states and titania CB states leads to a band gap decrease.<sup>27</sup>

A facile and effective way of generating oxygen vacancies in one-dimensional TiO<sub>2</sub> photocatalysts through iodine modification was first reported in this work. The enhanced visible activated iodine modified TiO<sub>2</sub> nanomaterials were obtained via simple two-step hydrothermal synthesis. The products were characterized by X-ray diffraction (XRD), Raman spectroscopy, Scanning electron microscopy (SEM) characterization, X-ray photoelectron spectroscopy (XPS) and UV-Vis diffuse

reflectance spectra (UV-DRS). The nature of the extended absorption edge, visible light driven photocatalytic activity, and microstructures in iodine modified  $\text{TiO}_2$  were investigated in terms of both phase evolution and surface/bulk oxygen defects. The chemical reactions of iodine ( $\text{HIO}_3$ ) and its doping mechanisms along with detailed XPS analysis on the generation of  $\text{Ti}^{3+}$  sites as I-O-Ti bonds and oxygen vacancies were revealed. The formation of I-O-Ti bonds substitution via  $\text{I}^{5+}$  substitution with  $\text{Ti}^{4+}$  was also discussed.

## 2 EXPERIMENTAL METHODS

### 2.1 Material Synthesis

#### 2.1.1 One-step synthesis of iodine modified $\text{TiO}_2$

A modified hydrothermal synthesis using Aeroxide™ P25 (Evoniks Industries) and iodic acid ( $\text{HIO}_3$ , 99.99% Sigma-Aldrich Chemicals) was employed followed by calcination for the samples in this work.<sup>17</sup> In a typical experiment, 2 g of P25 was dissolved in a 10 M NaOH alkaline solution by adding  $\text{HIO}_3$  (molar ratio of Ti: I = 1: 0.5) into the solution; then the fully mixed solution was transferred into a Teflon-lined stainless steel autoclave. The autoclave was placed in a furnace where the temperature was set to 150 °C or 250 °C for 24 hours. The resultant white precipitate was washed multiple times with MilliQ water (resistivity: 18.2  $\Omega$  cm) to remove excess ions. The wet powder was then filtered and dried in an oven at 80 °C overnight. The dried powder was calcined at 450 °C for 2 h in a furnace to obtain iodine modified  $\text{TiO}_2$ . The prepared samples were labelled as 1-I/ $\text{TiO}_2$ -150 and 1-I/ $\text{TiO}_2$ -250 denoting the temperatures that the nanomaterials were synthesized. For comparison, a reference sample of pristine  $\text{TiO}_2$  nanowires (NWs) were hydrothermally synthesized following the same procedure at 260 °C except without the addition of iodic acid. The dried products were calcined at a temperature of 700 °C to improve the crystallinity of anatase.<sup>8</sup>

#### 2.1.2 Two-step synthesis of iodine modified $\text{TiO}_2$

To understand the mechanisms of visible light induced photocatalytic activity of the iodine modified  $\text{TiO}_2$  nanomaterials, samples were synthesized via a two-step process. In the first step, pristine  $\text{TiO}_2$  NWs was prepared following the same procedure for our reference  $\text{TiO}_2$  NWs. In the second-step,  $\text{HIO}_3$  (molar ratio of Ti: I = 1: 0.5) was added into a solution containing 10 M NaOH alkaline solution and pristine  $\text{TiO}_2$  NWs produced in the first step. The mixed solution was transferred to an autoclave and

heated at 150 °C or 250 °C. The samples were dried at 80 °C overnight and a post-calcination was employed at 450 °C to obtain samples of 2-I/TiO<sub>2</sub>-150, 2-I/TiO<sub>2</sub>-250, respectively.

## 2.2 Microstructure, phase and photocatalytic characterizations

The phase and microstructure of fabricated specimens were examined using X-ray diffraction (XRD, Bruker D8 FOCUS, US) and field emission scanning electron microscopy (SEM, LEO-Ultra, GEMINI, Germany). X-ray photoelectron spectrum (XPS) measurements were carried out using a multi-technique ultra-high vacuum imaging XPS microprobe spectrometer (Thermo VG Scientific ESCALab 250) equipped with a hemispherical analyzer (of 150 mm mean radius) and non-monochromatic Al K $\alpha$  from a twin anode X-ray source. The spectrometer was calibrated using a carbon source at C 1s (Binding energy of 284.6 eV) with respect to the Fermi level. The chamber vacuum level was maintained at  $5 \times 10^{-9}$  mbar. An emission current of 0.2 mA were used for charge compensation during the analysis. The elemental composition was calculated from XPS spectra using CasaXPS software. Raman spectroscopy was conducted using a Renishaw micro-Raman spectrometer with a He-Ne ion laser at an excitation wavelength of 633 nm. The spectral resolution of the Raman shift is 0.5 cm<sup>-1</sup>. The absorption edge and band gap energy of the products were determined through the diffuse reflectance spectra which was measured using a UV-Vis-NIR spectrophotometer with an integrated spherical detector (UV-2501PC, Shimadzu, Japan) in the range of 200 nm to 800 nm. BaTiO<sub>3</sub> was used as a reference material to obtain reflectance data.

The visible light photocatalytic activity of the prepared samples was studied by the photodegradation of methylene blue (MB) in aqueous solution. In a typical experiment, 20 mg of prepared TiO<sub>2</sub> photocatalysts were dispersed into 50 mL of MB solution (0.03 mM). Before illumination, the suspension was kept in the dark at room temperature by magnetic stirring for 60 min. Photocatalytic degradation was assessed in the presence or absence of simulated visible light irradiation provided by a 150 W Xenon lamp (Newport, USA) equipped with a 400 nm cut-off filter (Thorlabs, USA). The irradiance was 4.4 W m<sup>-2</sup> at 0.2 m from the end of the collimating column. During the photoreaction process, aliquots of 5 ml were collected at specific time points. The collected aliquots were centrifuged at 3000 rpm to remove remaining photocatalysts and the concentration of MB was determined by UV-Vis spectroscopy at 663 nm using a standardized calibration curve.

## 3. RESULTS AND DISCUSSION

### 3.1 Characterization of Crystal Structure and Morphology

X-ray diffraction (XRD) patterns of as-prepared one-step iodine modified samples and pristine TiO<sub>2</sub> nanowires are shown in Figure 1. Anatase (JCPDS Card No. 21-1272) peaks are found at 2 $\theta$  values of 24.8° , 37.3° , 47.6° , 53.5° , 55.1° and 62.2° ; these correspond to (101), (004), (200), (105), (211) and (204) crystal planes.<sup>8</sup> Rutile (JCPDS Card No. 21-1276) peaks are found at 2 $\theta$  values of 27.0° , 35.6° , 40.8° , 54.0° , 53.9° , 56.1° , and 61.0° ; these correspond to crystal planes of (110), (101), (200), (111), (210), (211), (220), (002) and (310).<sup>8</sup> The anatase phase is obtained in our reference sample. For the one-step iodine modified TiO<sub>2</sub> samples, the anatase phase is maintained under a low processing temperature of 150 °C, while the rutile phase is prevalent at a higher processing temperature of 250 °C. Rutile TiO<sub>2</sub> is usually obtained via high temperature (more than 800 °C) calcination of anatase or in an acidic hydrothermal process.<sup>28-33</sup> In our research, the coexistence of acidic component (HIO<sub>3</sub>) and basic component (NaOH) can facilitate the formation of anatase and rutile at 150 °C and 250 °C, respectively. The XRD diffraction peaks in the one-step process are similar to that of the two-step process (Figure S1 in Supporting Information).

Raman analysis (Figure 2) was also conducted to further verify the phase of the one-step samples. The peaks observed match well with the characteristic peaks of anatase<sup>12,13</sup> at Raman shifts of 143 (E<sub>1g</sub>), 196 (E<sub>2g</sub>), 395 (B<sub>1g</sub>), 514 (A<sub>1g</sub>), 638 (E<sub>3g</sub>) cm<sup>-1</sup>, with respect to the reference sample and the iodine modified sample at 150 °C. For modified samples at 250 °C, the other observed Raman peaks at around 142 (B<sub>1g</sub>), 445 (E<sub>g</sub>) and 609 (A<sub>1g</sub>) cm<sup>-1</sup> are all characteristic peaks of rutile.<sup>8,28</sup> Additionally, second-order scattering features of rutile can also be observed, with prominent shifts at 235 cm<sup>-1</sup> and 252 cm<sup>-1</sup> as multi-photon vibration modes.<sup>8,34</sup> This observation is in agreement with those obtained from the X-ray diffraction data (Figure 1). The Raman characteristic peaks for the one-step process are similar to the two-step process (Figure S2 in Supporting Information).

Scanning electron microscopy (SEM) morphologies of TiO<sub>2</sub> NWs and iodine modified TiO<sub>2</sub> are given in Figure 3. Figures 3a -3d depict TiO<sub>2</sub> nanomaterial structures synthesized under a one-step process, whereas Figures e and f show TiO<sub>2</sub> nanomaterial structures synthesized under a two-step process. Figure 3a and 3b represent pristine TiO<sub>2</sub> NWs that have a width of 50 - 200 nm and lengths in the micron-scale. These results are similar with previous literature in which the same hydrothermal procedure was adopted.<sup>31,32</sup> The iodine modified samples at 150 °C have a fine particle-like (Figure 3c - one-step) and a sheet-like (Figure 3e - two-step) morphology consisting of aggregated particles having poor crystal growth, which is shown in the XRD results. Additionally, Figure 3d (one-step) and Figure 3f (two-step) depict evenly distributed TiO<sub>2</sub> rutile nanowires processed at 250 °C. These TiO<sub>2</sub> nanowires are hundreds

of nm in width and several microns in length and are bundled together. The inset image of Figure 3d shows the rutile TiO<sub>2</sub> nanowires at a higher magnification.

### 3.2 Measurement of UV-Vis Diffuse Reflectance Spectra

The UV-Vis diffusion reflectance spectra (DRS) of pristine TiO<sub>2</sub> NWs (Figure 4a) and iodine modified samples (Figure 4b and 4c). The DRS spectra indicates a red shift from 380 nm to values between 410 nm - 480 nm at the two synthesis temperatures (150 °C and 250 °C). The indirect band gap energies ( $E_g$ ) of the samples were calculated by plotting  $[F(R_{\infty})hv]^{1/2}$  vs. Band Energy (inset of Figure 4) using the Kubelka-Munk theory, which usually applies to high-scattering materials including impurity-doped solids.<sup>35</sup> The bandgap energy of pristine TiO<sub>2</sub> nanowires and anatase nanowires synthesized at 150 °C is about 3.16 eV; this value is red shifted to 2.92 eV for rutile nanowires synthesized at 250 °C. The absorption tails in the spectra of 1-I/TiO<sub>2</sub>-150 (Figure 4b) reflects the low energy electron density states on the bottom of the conduction band, while the slope reflects an increase of high energy electron density states.<sup>22</sup> The absorption edge of 1-I/TiO<sub>2</sub>-250 (Figure 4c) shows a stronger red shift compared to 1-I/TiO<sub>2</sub>-150 due to the presence of the rutile phase.

### 3.3 X-ray Photoelectron Spectroscopy

The surface chemical states of as-prepared samples were analyzed by XPS. The XPS survey shown in Figure 5a reveals that the samples mainly contains Ti, O, C, from which, no obvious I 3d binding peaks were observed at 619 eV (I 3d 5/2) and 632 eV (I 3d 3/2), in accordance to the XPS database from the National Institute of Standards and Technology (NIST). Compared with the relatively high contents of oxygen and titanium, it was difficult to detect the XPS spectra of iodine from survey spectra because of the low content of iodine dopant. The C 1s at 284.6 eV is adopted as the reference peak for the calibration of all the binding energies. Figure 5b shows the high-resolution C1s XPS spectra of as-prepared samples. A broad energy range from 282 eV to 292 eV can be observed. By deconvoluting these peaks, the binding energy at 283.4 eV can be ascribed to carbon substituting for oxygen atom in the lattice of TiO<sub>2</sub>, forming the O-Ti-C bond, while the peaks around 286.4 eV and 288.7 eV correspond to C-O bonds and C=O bonds, respectively.<sup>12,13</sup> Using a high resolution spectra, chemical states of I 3d peaks are shown in Figure 5c, in which evidence for the doped iodine is observed. The shift of I 3d 5/3 from 622 eV for HIO<sub>3</sub> to 620 eV may arise from the energetically favorable substitution from Ti<sup>4+</sup> (with radius of 0.64 nm) to I<sup>5+</sup> (with radius of 0.62 nm).<sup>16</sup> These iodine peaks only appear in samples at 150 °C as revealed by the XPS analysis. In terms of samples prepared at 250 °C, no high resolution iodine spectrum could be




observed, which could be explained by the fact of promoted decomposition of iodine oxides to vaporized  $I_2$ , which followed by the desorption of produced  $I_2$ .

The oxygen (O 1s) and titanium (Ti 2p) binding regions are shown in Figure 6. It is worth noting that the peaks of the oxygen show different chemical states with different integrated areas in different samples. The two main O 1s peaks are attributed to  $O^{2-}$  (528.2 eV -529.5 eV) and oxygen vacancies  $O^*$  (531.1 eV - 533.5 eV).<sup>36</sup> Deconvolution of the peaks reveals that the number of oxygen vacancies ( $O^*$  in  $TiO_{2-x}$  around 531.1 eV -533.5 eV) increases as the hydrothermal temperature increases (Table 1).

The residual iodine was present at samples synthesized at lower temperatures (Figure 6a and 6c) and show iodine oxide deconvoluted peaks at 530 eV ( $O^{2-}$  in  $I_2O_5$ ) and 533 eV ( $O^*$  in  $I_2O_{5-x}$ ); no such peaks appear in Figure 6b and 6d. In addition, the  $O^*$  in  $I_2O_{5-x}$  has a binding energy ranging from 532.8 eV to 533.6 eV. This indicates the formation of I-O-Ti bonds in the  $TiO_2$  matrix from the substitution of  $I^{5+}$  with  $Ti^{4+}$ .<sup>18</sup> In the inset figures of Ti 2p XPS spectrum, the two peaks at 455.6 eV and 462.8 eV correspond to the different oxidation states of Ti, which are attributed to  $Ti^{3+}$  (458.1 eV) and  $Ti^{4+}$  (463.4 eV) sites. These  $Ti^{3+}$  species exist from the reduction of  $Ti^{4+}$  by the free electrons that are left from oxygen vacancies.<sup>11,37</sup> Table 1 illustrates the detailed atomic percentage for each chemical state. By comparing the relative contents of both  $Ti^{3+}$  species and  $Ti^{4+}$  species under both synthesis processes (one-step and two-step),  $Ti^{3+}$  species shows higher contents at 150 °C than that at 250 °C.

### 3.4 Iodine modified $TiO_2$ : a chemical reaction mechanistic view



With the existence of iodic acid in the reaction system, an oxidative environment is created due to the existence of  $I^{5+}$ , which has a high reactivity and tendency to form iodine oxides with multivalences of iodine (i.e.  $I_2O_4$ ,  $I_4O_9$  as  $I_2O_{5-x}$ ), which accept oxygen atoms from the  $TiO_2$  lattice. Consequently, the substitution of  $I^{5+}$  for  $Ti^{4+}$  in the form of an I-O-Ti bond creates oxygen vacancies in  $TiO_2$  matrix.<sup>16,17</sup> The reversible equilibrium reactions for  $Ti^{4+}$  and  $O^{2-}$  are given:<sup>36</sup>





where O stands for the charge balanced oxygen atoms in titania,  $V_O^{2+}$  stands for the oxygen vacancies.

The decomposition of iodic acid ( $HIO_3$ ) leads to the formation of  $I_2O_5$ . The amorphous phase in the samples contributes to surface oxygen defects or the adsorption of iodine oxides on the surface of  $TiO_2$

crystals.<sup>33</sup> Oxygen vacancies were generated in the lattice of TiO<sub>2</sub>, which is mainly caused by the reduction of I<sup>5+</sup> to lower multi-valance states. During the reduction reaction of I<sup>5+</sup>, free electrons were released and oxygen vacancies were generated in the lattice of TiO<sub>2</sub>; at the same time, the free electrons are also participating in the reduction of Ti<sup>4+</sup> to Ti<sup>3+</sup> (Equation 3). At 250 °C, the decomposition and reduction process of I<sub>2</sub>O<sub>5</sub> consumes more free electrons from oxygen atoms, which produce more oxygen vacancies in TiO<sub>2</sub> (Equation 2); this leads to less electrons being available that contribute to the generation of Ti<sup>3+</sup> being restricted (Equation 3). The following reactions occur to iodine acid (HIO<sub>3</sub>):<sup>16</sup>



where  $\Delta$  stands for energy in the form of heat. I<sub>2</sub>O<sub>5-x</sub> (I<sup>5+</sup>) is reduced to lower valence states (I<sup>3+</sup> or I<sub>2</sub>) :



The I<sup>5+</sup> ions can act as electron acceptors when reducing to lower multi-valance states. The efficient electron scavenging by these multi-valance iodine ions contributes to the efficient separation of electron-hole pairs.<sup>19</sup> Additionally, increased oxygen vacancies are generated (*via* Eq.2) through the reducing reaction with the accompaniment of increased substitution of I<sup>5+</sup> for Ti<sup>4+</sup> in I-O-Ti bonds. The equilibrium reaction between Ti<sup>4+</sup> and O<sup>2-</sup> is restricted at high temperatures of 250 °C, and less Ti<sup>3+</sup> sites are generated; however, more oxygen vacancies (by releasing electrons for the reduction of I<sub>2</sub>O<sub>5-x</sub>) are produced inside the TiO<sub>2</sub> lattice than the relative contents produced at 150 °C.

### 3.5 Evaluation of Visible Light Photocatalytic Activity

The visible light photocatalytic degradation of all samples was studied using methylene blue (MB) in aqueous solution. The MB concentration was determined using a calibration curve generated by spectrophotometry of premade standards. To indicate the decomposition efficiency, the photocatalytic activity of the catalysts can be quantitatively evaluated by obtaining the apparent reaction rate constant ( $K_{ap}$ ) from a pseudo-first-order kinetic reaction. The kinetic equation is expressed as:<sup>22</sup>

$$\ln(C_0/C) = K_{ap}t \quad (8),$$

where,  $C_0$  and  $C$  are the initial and final concentration and  $t$  is the irradiation time, respectively. The photocatalytic degradation of MB under visible light irradiation is shown Figure 7a and 7b. P25 is used as a performance benchmark to compare the synthesized  $\text{TiO}_2$  photocatalysts. Theoretically, the pristine anatase  $\text{TiO}_2$  NWs or commercial P25 do not show a visible light photocatalytic activity due to the large band gap of anatase. As shown in Figure 7a, neither P25 nor  $\text{TiO}_2$  NWs shows significant photodegradation under visible light irradiation, in which the degradation rate is limited to 3.6 % and 3.8 %, respectively, within experimental error range. The modified samples in our research show an increased photodegradation under visible light irradiation.

The surface area of each sample was characterized by the BET method (Table 2), since it is one of the important factors that influence the photocatalytic activity. According to literature, without considering other factors such as the choice of irradiation source, electronic properties, and optical absorption, large surface area nanomaterials tend to have increased degradation efficiency because of increased adsorption capacity and higher chemical reactivity. The change in surface area affects the photoactivity of the anatase samples because of the nanoparticle nature of as-prepared anatase. The anatase nanoparticle clusters (two-step) have larger surface areas compared to the anatase nanoparticles (one-step) and the rutile nanowires.

Visible light absorbance and a narrower bandgap in the  $\text{TiO}_2$  matrix are important factors in determining the visible light photoactivity as well as other electronic properties of the material, such as photoconductance.<sup>38</sup> From Table 2, the iodine modified  $\text{TiO}_2$  have their bandgaps narrowed from 3.16 eV to up to 2.92 eV when compared to pristine  $\text{TiO}_2$ . The bandgap narrowing improves the visible light degradation efficiency of MB. The 2-I/ $\text{TiO}_2$ -250 sample had the highest degradation rate in which the MB degradation rate reaches 50.9 % after 90 minutes ( $K_{\text{ap}}=7.92\times 10^{-3} \text{ min}^{-1}$ ) under visible light irradiation. One of the reasons rutile presents better visible light photodegradation of MB, compared to similarly prepared anatase is the lower bandgap of rutile nanowire than that of the anatase nanoparticle cluster. The rutile nanowire product (2-I/ $\text{TiO}_2$ -250), in particular, is capable of generating more electron-hole pairs under visible light due to the creation of both the  $\text{Ti}^{3+}$  sites, I-O-Ti and oxygen vacancies. With the bandgap further decreased by oxygen vacancies, better visible activated catalytic performance could be expected from rutile phase. The other reason lies in that rutile phase has higher photoconductance (photoconductance is related to the photoactivity) in the visible light region within the photon energy level of the bandgap, so there is a more  $e^-$  and  $h^+$  generation compared to anatase, even though the photoconductance is higher in anatase over the entire UV-Vis spectrum.<sup>38</sup>

The presence of excess  $Ti^{3+}$  sites contributes to the visible light absorption because of the formation of the 3d orbital of the  $Ti^{3+}$  ions in the bandgap just below the bottom of the CB.<sup>6,10</sup> The existence of  $Ti^{3+}$  can form a defect that promotes charge transfer and suppress electron-hole recombination.<sup>6,38</sup> The 3d states of  $Ti^{3+}$  below CB are due to the presence of oxygen vacancies in the  $TiO_2$  lattice. Additionally, the created oxygen vacancies also act as charge carriers of holes (positive effect) and benefit the separation of electron-hole pairs.<sup>39</sup> Oxygen vacancies can efficiently transfer photo-induced electrons to reduce the recombination of electron-hole pairs and thus benefit the visible light photocatalytic activity. The creation of oxygen vacancies induce additional acceptor states above the valence band (VB) edge of  $TiO_2$ , resulting in narrowing of the bandgap.<sup>35</sup> However, according to previous studies,<sup>11,40</sup> high concentrations of the 3d state  $Ti^{3+}$  sites associated with oxygen vacancies are considered as the electron-hole recombination centers (negative effect), which can also be verified in our case of low temperature (150 °C) samples. In the case of specimens at 250 °C, there are relatively low concentrations of 3d state  $Ti^{3+}$  sites and high content of oxygen vacancies that act as the charge carriers or electron donors, which decrease the recombination rate of photo-induced electron-hole pairs.<sup>40</sup> The generation of a low concentrations of 3d  $Ti^{3+}$  sites is controllable and high oxygen vacancies is the key to the enhanced photocatalytic performance of visible sensitized  $TiO_2$  nanomaterials.

From the above deductions and in conjunction with XPS analysis, we can conclude that the chemical reaction causes the reduction of high valence iodine ions to a lower valence by consuming oxygen atoms from pristine  $TiO_2$ . Oxygen vacancies can be created with the increased formation of I-O-Ti bonds by the modification of iodine. The formation of 3d  $Ti^{3+}$  sites and oxygen vacancies narrows the absorption bandgap of  $TiO_2$ . This bandgap narrowing allows  $TiO_2$  photocatalysts to be excited under visible light irradiation and generate electron-hole pairs, most of which are trapped or react in aqueous solutions producing reactive species such as  $O_2^-$ ,  $\cdot OH$  radicals, and  $H_2O_2$ .<sup>11</sup> Photo-generated electrons transfer directly into the CB with the existence of oxygen vacancies and I-O-Ti bonding in the titania matrix. Interactions of these activity species account for the efficient degradation property of MB under visible light irradiation. These nanomaterial photocatalysts can be applied to the organic degradation of pollutants for water treatment using cheap solar irradiation, instead of an ultraviolet irradiation source.

#### 4 CONCLUSIONS

Iodine modified  $TiO_2$  photocatalysts with enhanced photocatalytic activities under visible light were successfully prepared by a hydrothermal process using P25 and iodic acid ( $HIO_3$ ) as the precursor and the intrinsic reaction mechanism of these photocatalysts were studied. The results show that using a

low temperature at 150 °C generates fine particle-like structures of anatase phase, whereas at a higher temperature of 250 °C, the products generated were dominated by nanowire structures of rutile phase. Both phases of TiO<sub>2</sub> photocatalysts show enhancements in photoabsorption and photodegradation under visible light irradiation. Rutile nanowires, in particular, demonstrates a higher photodegradation rate than anatase nanoparticle clusters when compared with similarly prepared materials (one-step and two-step hydrothermal methods). The multi-valences of iodine can be used as the oxidant of oxygen atoms for the synthesis of iodine modified TiO<sub>2</sub> with oxygen vacancies. Oxygen vacancies are produced with the increasing formation of I-O-Ti bonds and result in the optical response in the visible light region. Elevating the temperature from 150 °C to 250 °C, increases oxygen vacancies and decreases 3d Ti<sup>3+</sup> sites by the reducing reactions of iodine ions, resulting in enhanced visible photocatalytic activity.

## ACKNOWLEDGEMENTS

This work has been financially supported by the Natural Sciences and Engineering Research Council of Canada through a strategic project grant, the Canadian Water Network Innovative Technologies for Water Treatment Program, and the Canada Research Chairs Program. Technical support from Trojan UV, the City of Guelph Wastewater Services, Deep Blue NRG, and GE Water & Process Technologies are highly appreciated. W.J. Li acknowledges the China Scholarship Council (CSC) for providing a Doctoral Scholarship.

## REFERENCES

1. A. Fujishima and K. Honda, *Nature*, 1972, **238**, 37-38.
2. J. Zhang, W. Q. Peng, Z. H. Chen, H. Chen and L. Y. Han, *J Phys. Chem. C*, 2012, **116**, 19182-19190.
3. D. H. Chen, F. Z. Huang, Y. B. Cheng and R. A. Caruso, *Adv. Mater.*, 2009, **21**, 2206-2210.
4. G. F. Ortiz, I. Hanzu, P. Lavela, J. L. Tirado, P. Knauthac and T. Djenizian, *J. Mater. Chem.*, 2010, **20**, 4041-4046.
5. T. Morikawa, T. Ohwaki, K. Suzuki, S. moribe and S. Tero-kubota, *Appl. Catal. B: Environ.*, 2008, **83**, 56-62.
6. S. Hoang, S. W. Guo, N. T. Hahn, A. J. Bard and C. B. Mullins, *Nano letters*, 2012, **12**, 26-32.
7. D. Rimeh, D. Patrick and R. Didier, *Ind. Eng. Chem. Res.*, 2013, **52**, 3581-3599.

8. A. Hu, X. Zhang, D. Luong, K. D. Oakes, M. R. Servos, R. Liang, S. Kurdi, P. Peng and Y. Zhou, *Waste Biomass Valor*, 2012, **3**, 443-449.
9. Y. Wang, C. X. Feng, M. Zhang, J. J. Yang and Z. J. Zhang, *Appl. Catal. B: Environ.*, 2010, **100**, 84-90.
10. G. D. Yang, Z. Jiang, H. H. Shi, T. C. Xiao and Z. F. Yan, *J. Mater. Chem.*, 2010, **20**, 5301-5309.
11. C. Burda, Y. B. Lou, X. B. Chen, A. C. S. Samia, H. Stout and J. L. Gole. *Nano letters*, 2003, **3**, 1049-1051.
12. D. H. Wang, L. Jia, X. L. Wu, L. Q. Lu and A. W. Xu, *Nanoscale*, 2012, **4**, 576-584.
13. F. Dong, S. Guo, H. Q. Wang, X. F. Li and Z. B. Wu, *J. Phys. Chem. C*, 2011, **115**, 13285-13292.
14. J. G. Yu, G. P. Dai, Q. J. Xiang and M. Jaroniec, *J. Mater. Chem.*, 2011, **21**, 1049-1057.
15. T. Umebayashi, T. Yamaki, S. Yamamoto, A. Miyashita, S. Tanaka, T. Sumita and K. Asai, *J. Appl. Phys.*, 2003, **93**, 5156-5160.
16. X. T. Hong, Z. P. Wang, W. M. Cai, F. Lu, J. Zhang, Y. Z. Yang, N. Ma and Y. J. Liu, *Chem. Mater.*, 2005, **17**, 1548-1552.
17. S. Song, J. J. Tu, Z. Q. He, F. Y. Hong, W. P. Liu and J. M. Chen, *Appl. Catal. A: General*, 2010, **378**, 169-174.
18. G. Liu, C. H. Sun, X. X. Yan, L. N. Cheng, Z. G. Chen, X. W. Wang, L. Z. Wang, S. C. Smith, M. Lu, and H.M. Cheng, *J. Mater. Chem.*, 2009, **19**, 2822-2829.
19. W. Y. Su, Y. F. Zhang, Z. H. Li, L. Wu, X. X. Wang, J. Q. Li and X. Z. Fu, *Langmuir*, 2008, **24**, 3422-3428.
20. K. B. Jaimy, V.P. Safeena, S. Ghosh, H.Y. Hebalkar and K. G. K. Warriar, *Dalton Trans.*, 2012, **41**, 4824-4832.
21. N. Sobana, M. Muruganadham and M. Swaminathan, *J. Mol. Catal. A: Chem.*, 2006, **258**, 124-132.
22. J. Zhang, J. H. Xi and Z. G. Ji, *J. Mater. Chem.*, 2012, **22**, 17700-17708.
23. G. Colón, M. Maicu, M.C. Hidalgo and J.A. Navío, *Appl. Catal. B: Environ.*, 2006, **67**, 41-51.
24. S. Y. Zhu, S. J. Liang, Q. Gu, L. Y. Xie, J. X. Wang, Z. X. Ding and P. Liu, *Appl. Catal. B: Environ.*, 2012, **119-120**, 146-155.
25. T. Ihara, M. Miyoshi, Y. Iriyama, O. Matsumoto and S. Sugihara, *Appl. Catal. B: Environ.*, 2003, **42**, 403-409.
26. I. Nakamura, N. Negishi, S. Kutsuna, T. Ihara, S. Sugihara and K. Takeuchi, *J. Mol. Catal. A: Chem.*, 2000, **161**, 205-212.
27. I. Justicia, P. Ordejon, G. Canto, J. L. Mozos, J. Fraxedas, G. A. Battiston, R. Gerbasi and A. Figueras, *Adv. Mater.*, 2002, **14**, 1399-1402.

28. X. W. Zhao, W. Z. Jin, J. G. Cai, J. F. Ye, Z. H. Li, Y. R. Ma, J. L. Xie and L. M. Qi, *Adv. Funct. Mater.*, 2011, **21**, 3554-3563.
29. J. Jitputti, S. Pavasupree, Y. Suzuki and S. Yoshikawa, *Japan. J. Appl. Phys.*, 2008, **47**, 751-756.
30. W. J. Zhou, X. Y. Liu, J. J. Cui, D. Liu, J. Li, H. D. Jiang, J. Y. Wang and H. Liu, *Cryst. Eng. Comm.*, 2011, **13**, 4557-4563.
31. A. M. Hu, X. Zhang, K. D. Oakes, P. Peng, Y. N. Zhou and M. R. Servos, *J. Hazard. Mater.*, 2011, **189**, 278-285.
32. A. Hu, R. Liang, X. Zhang, S. Kurdi, D. Luong, H. Huang, P. Peng, E. Marzbanrad, K.D. Oakes, Y. Zhou and M.R. Servos, *J. Photochem. Photobiol. A: Chem.*, 2013, **256**, 7-15.
33. D. L. Shieh, Y. S. Lin, J. H. Yeh, S. C. Chen, B. C. Lin and J. L. Lin, *Chem. Commun.*, 2012, **48**, 2528-2530.
34. M. Y. Xin, J. L. Zhang and F. Chen, *Appl. Catal. B: Environ.*, 2009, **89**, 563-569.
35. P. Kubelka and F. Munk, *Z. Tech. Phys.* 1931, **12**, 593-601.
36. N. H. Yang, C. C. Tseng, J. L. Wu, C. C. Juan, S. J. Lin and S. Y. Chang, *RSC Adv.*, 2013, **3**, 7093-7099.
37. R. H. Li, H. Kobayashi, J. F. Guo and J. Fan, *Chem. Commun.*, 2011, **47**, 8584-8586.
38. Y. Yamada and Y. Kanemitsu, *Appl. Phys. Lett.* 2012, **101**, 133907.
39. P. Xu, L. Lu, T. Xu, S. M. Gao, B. B. Huang and Y. Dai, *J. Phys. Chem. C*, 2010, **114**, 9510-9517.
40. S. Ikeda, N. Sugiyama, S. Murakami, H. Kominami, Y. Kera, H. Noguchi, K. Uosaki, T. Torimoto and B. Ohtani, *Phys. Chem. Chem. Phys.*, 2003, **5**, 778-783 .

**TABLE CAPTIONS**

**Table 1** Oxygen states and titanium states in iodine modified samples under various synthesis conditions

**Table 2** Properties of synthesized TiO<sub>2</sub> samples and their visible-light efficiencies

**FIGURE CAPTIONS**

**Figure 1** X-ray diffraction spectra of as prepared (a) Pristine TiO<sub>2</sub> NWs, (b) 1-I/TiO<sub>2</sub>-150, and (c) 1-I/TiO<sub>2</sub>-250.

**Figure 2** Raman spectra of as prepared (a) Pristine TiO<sub>2</sub> NWs, (b) 1-I/TiO<sub>2</sub>-150, and (c) 1-I/TiO<sub>2</sub>-250.

**Figure 3** SEM images of as prepared (a) pure anatase TiO<sub>2</sub> NWs; (b) specific magnification (Black area in Figure 3a) of TiO<sub>2</sub> NWs; (c) anatase fine-particles in 1-I/TiO<sub>2</sub>-150; (d) rutile phase NW in 1-I/TiO<sub>2</sub>-250, the inset shows the magnification image of specific area in figure 3d; (e) anatase sheet structure in 2-I/TiO<sub>2</sub>-250; and (f) rutile phase NW in 2-I/TiO<sub>2</sub>-250.

**Figure 4** Diffuse reflectance spectra of as prepared (a) TiO<sub>2</sub> NWs, (b) 1-I/TiO<sub>2</sub>-150, and (c) 1-I/TiO<sub>2</sub>-250. The inset presents the plot of  $[F(R_{\infty})h\nu]^{1/2}$  vs. photo energy of as prepared (a) TiO<sub>2</sub> NWs, (b) 1-I/TiO<sub>2</sub>-150, and (c) 1-I/TiO<sub>2</sub>-250.

**Figure 5** XPS spectra of (a) survey spectrum, (b) C 1s calibration curve, and (c) I 3d spectra in 1-I/TiO<sub>2</sub>-150.

**Figure 6** XPS spectra of O 1s spectrum in different samples: (a) 1-I/TiO<sub>2</sub>-150, (b) 1-I/TiO<sub>2</sub>-250, (c) 2-I/TiO<sub>2</sub>-150, and (d) 2-I/TiO<sub>2</sub>-250. The inset figure corresponds to the Ti 2p spectra of each sample.

**Figure 7** Degradation of 0.03mM methylene blue (MB) using various catalysts at concentrations of 0.4 g L<sup>-1</sup> for 90 min under visible irradiation ( $\lambda > 400$  nm). (a) Normalized concentration ( $C/C_0$ ) as a function of irradiation time; (b)  $\ln(C_0/C)$  as a function of irradiation time.


**Table 1**


Samples	O 1s (%)				Ti 2p (%)		
	O* (TiO <sub>2-x</sub> )	O <sup>2-</sup> (TiO <sub>2</sub> )	O* (I <sub>2</sub> O <sub>5-x</sub> )	O <sup>2-</sup> (I <sub>2</sub> O <sub>5</sub> )	Ti <sup>3+</sup> (TiO <sub>2-x</sub> )	Ti <sup>4+</sup> (TiO <sub>2</sub> )	Ti <sup>3+</sup> (I-O-Ti)
1-I/TiO <sub>2</sub> -150	20.90	30.05	32.21	16.83	56.35	11.62	32.03
2-I/TiO <sub>2</sub> -150	41.70	21.33	23.94	13.03	33.29	19.13	47.58
1-I/TiO <sub>2</sub> -250	55.58	41.88	-----	2.54	28.02	71.98	-----
2-I/TiO <sub>2</sub> -250	64.08	35.92	-----	-----	39.61	60.39	-----

Table 2

Samples	Phase	Morphology	Specific Surface Area (m <sup>2</sup> /g)	Band Gap (eV)	Degradation Rate <sup>d</sup> (%)	K <sub>ap</sub> <sup>c</sup> (10 <sup>-3</sup> min <sup>-1</sup> )
P25	A <sup>a</sup> + R <sup>b</sup>	Nanoparticle	52	3.05	3.6	0.387
Pristine TiO <sub>2</sub>	A	Nanowire	21.52	3.16	3.8	0.418
1-I/TiO <sub>2</sub> -150	A	Nanoparticle cluster	189.37	3.08	21.7	2.71
1-I/TiO <sub>2</sub> -250	R	Nanowire	76.53	2.92	30.6	4.07
2-I/TiO <sub>2</sub> -150	A	Nano sheet cluster	321.44	3.16	39.9	5.50
2-I/TiO <sub>2</sub> -250	R	Nanowire	55.52	2.92	50.9	7.92

<sup>a</sup>A=anatase;<sup>b</sup>R=rutile;<sup>c</sup>K<sub>ap</sub>=apparent constant value<sup>d</sup>Degradation of 0.03mM methylene blue(MB) with catalysts dosage of 0.4 g/L for 1.5 h under visible irradiation ( $\lambda > 400$  nm).

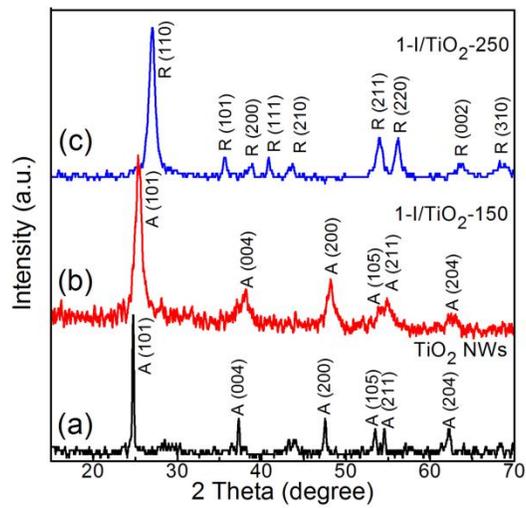**Figure 1**

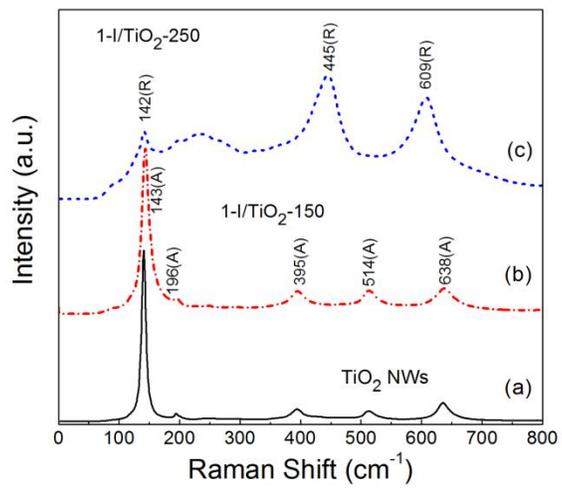**Figure 2**

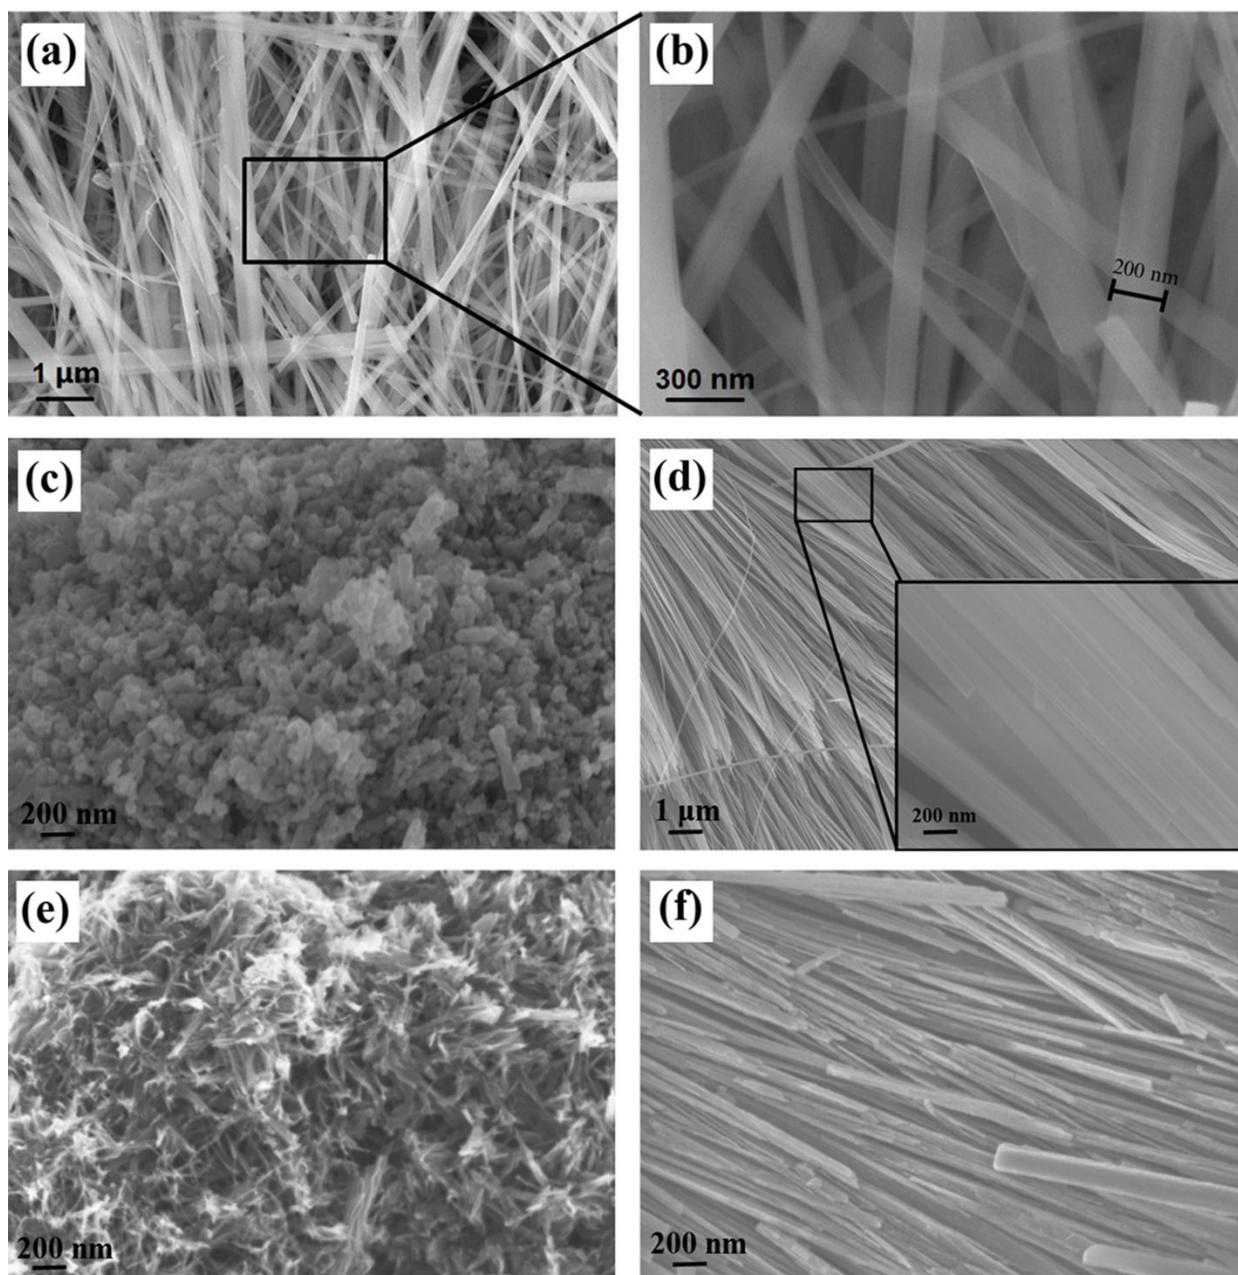


Figure 3

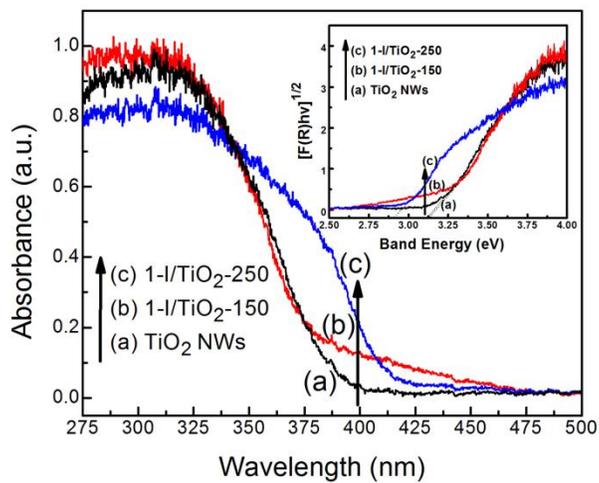


Figure 4

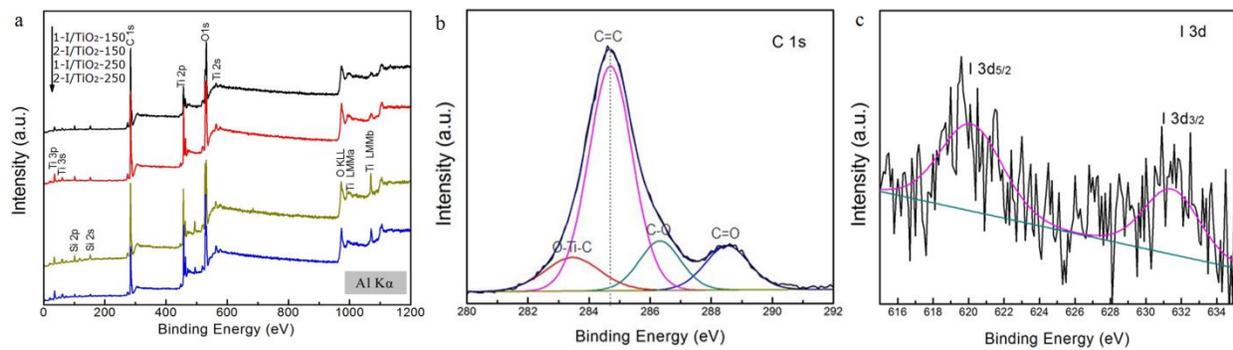


Figure 5

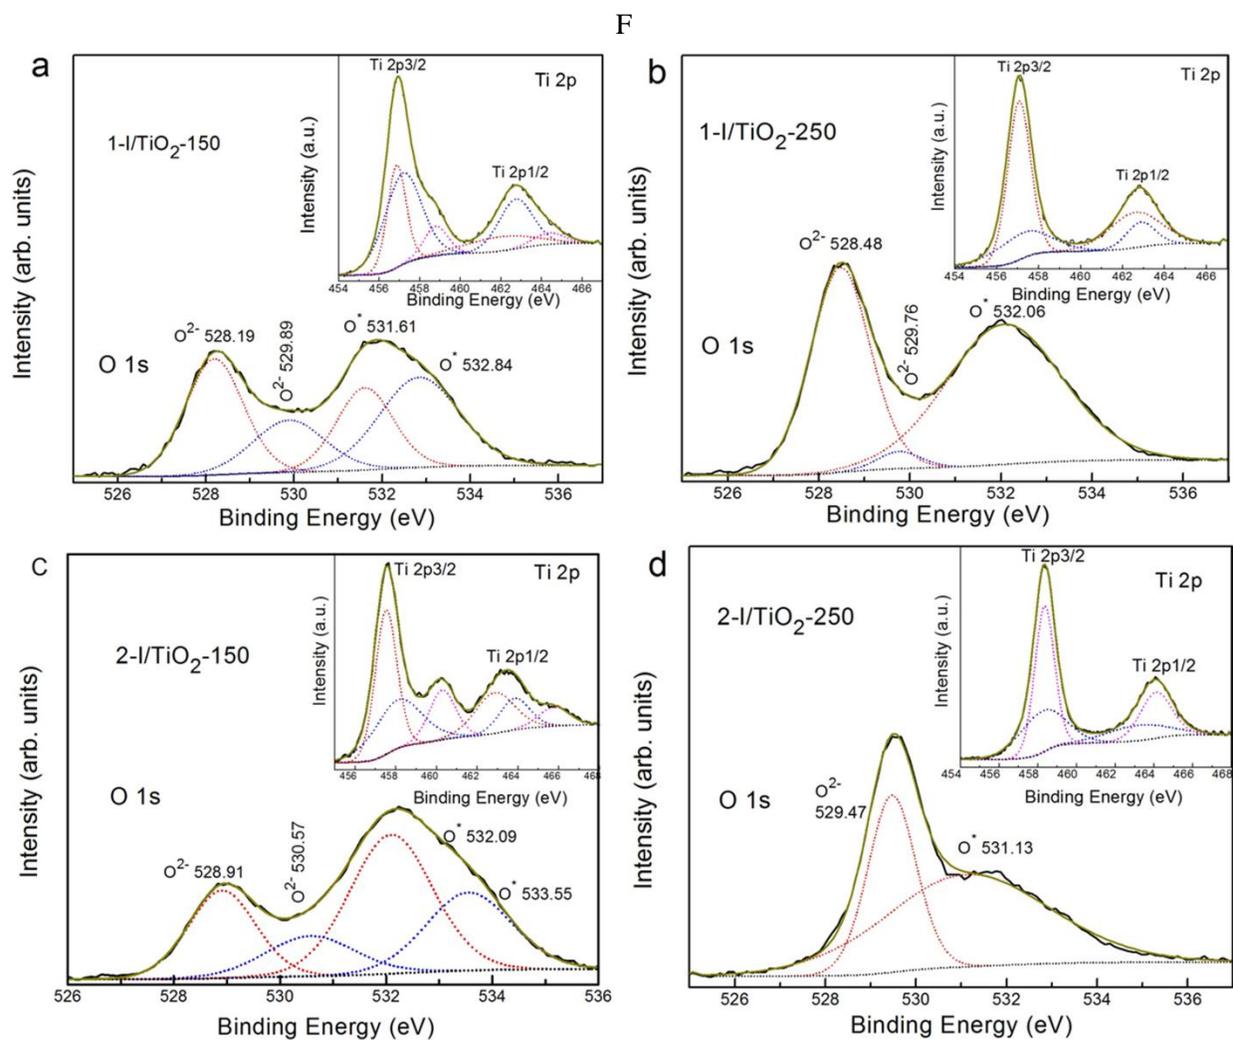


Figure 6

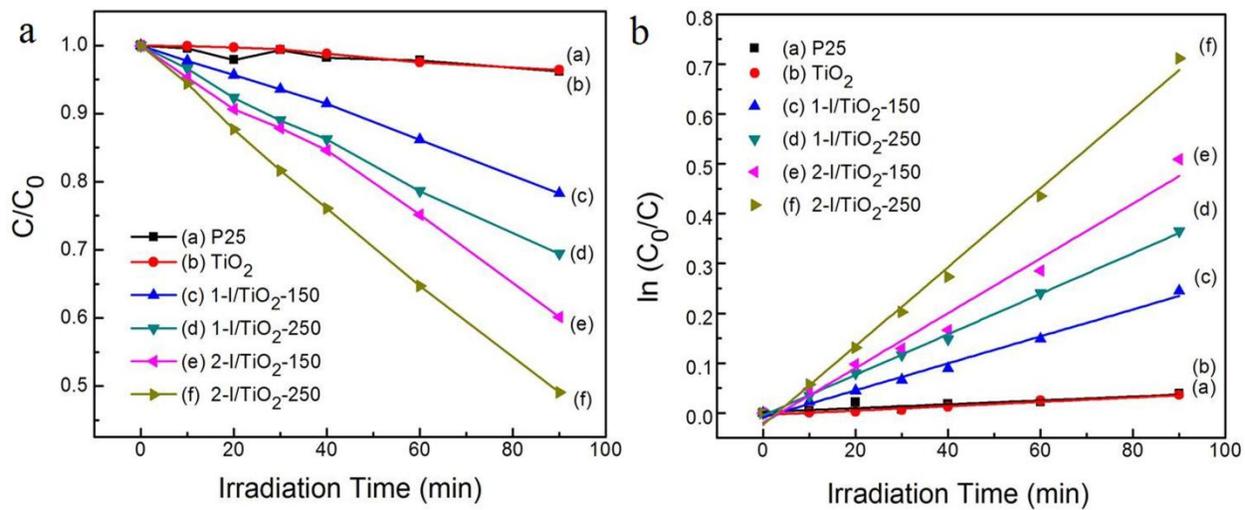


Figure 7