

# RSC Advances




This is an *Accepted Manuscript*, which has been through the Royal Society of Chemistry peer review process and has been accepted for publication.

*Accepted Manuscripts* are published online shortly after acceptance, before technical editing, formatting and proof reading. Using this free service, authors can make their results available to the community, in citable form, before we publish the edited article. This *Accepted Manuscript* will be replaced by the edited, formatted and paginated article as soon as this is available.

You can find more information about *Accepted Manuscripts* in the [Information for Authors](#).

Please note that technical editing may introduce minor changes to the text and/or graphics, which may alter content. The journal's standard [Terms & Conditions](#) and the [Ethical guidelines](#) still apply. In no event shall the Royal Society of Chemistry be held responsible for any errors or omissions in this *Accepted Manuscript* or any consequences arising from the use of any information it contains.

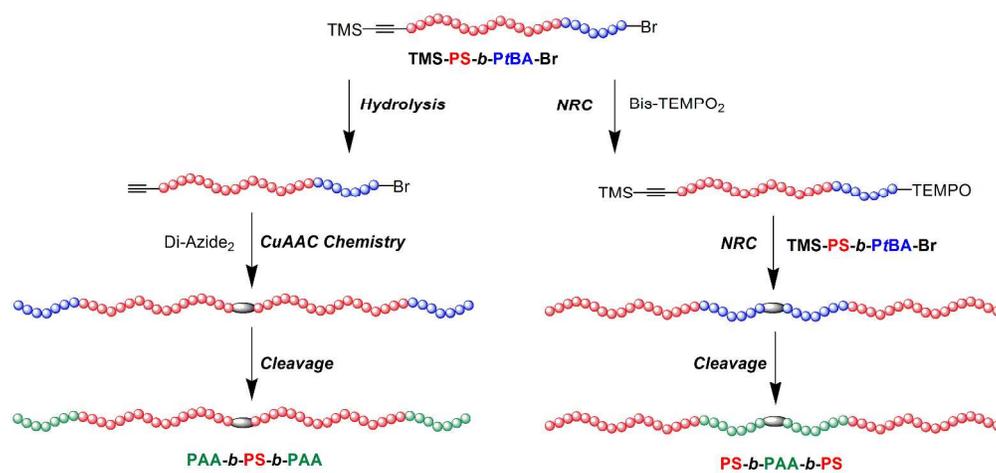

375x174mm (300 x 300 DPI)

## ARTICLE

# Synthesis and Characterization of Amphiphilic Triblock Copolymers with Identical Compositions but Different Block Sequences

Cite this: DOI: 10.1039/x0xx00000x

Chengjiao Lu, Lingdi Chen, Kun Huang, Guowei Wang\*

Received 00th January 2012,  
Accepted 00th January 2012

DOI: 10.1039/x0xx00000x

www.rsc.org/

The amphiphilic triblock copolymers poly(acrylic acid)-*b*-poly(styrene)-*b*-poly(acrylic acid) (PAA-*b*-PS-*b*-PAA) and PS-*b*-PAA-*b*-PS with identical compositions but different block sequences were synthesized by combination of atom transfer radical polymerization (ATRP) mechanism and nitroxide radical coupling (NRC) reaction or copper-catalyzed azide / alkyne click (CuAAC) chemistry. Firstly, the diblock copolymers TMS≡PS-*b*-PtBA-Br were prepared by sequential ATRP of styrene (St) and *tert*-butyl acrylate (*t*BA) monomers from trimethylsilyl propargyl 2-bromoisobutyrate (TMS-PgBiB) initiator. Then, the triblock copolymers PS-*b*-PtBA-*b*-PS were prepared by NRC reaction between TMS≡PS-*b*-PtBA-Br and coupling agent bis[4-(2,2,6,6-tetramethylpiperidine-1-oxyl)] succinate (Bis-TEMPO<sub>2</sub>). And the triblock copolymers PtBA-*b*-PS-*b*-PtBA were obtained by CuAAC chemistry between Alkynyl-PS-*b*-PtBA-Br and a coupling agent 1,4-diazidobutane (Di-Azide<sub>2</sub>). The target triblock copolymers PAA-*b*-PS-*b*-PAA and PS-*b*-PAA-*b*-PS were finally derived from the cleavage of corresponding PS-*b*-PtBA-*b*-PS and PtBA-*b*-PS-*b*-PtBA. The self-assembly behaviour was preliminarily studied by FLS, FESEM and DLS instruments, and the results showed that the PS-*b*-PAA-*b*-PS and PAA-*b*-PS-*b*-PAA could give distinct critical micelle concentration (*cmc*) values and different sizes of micelles in water.

## INTRODUCTION

The rapid development of “living”/controlled polymerization mechanisms and efficient coupling techniques in polymer chemistry have greatly accelerated the synthesis of polymers with complicated architectures,<sup>1-7</sup> which further makes it possible to explore the structure-property relationship of polymers. For example, as an important research area, the research on self-assembly behaviour of amphiphilic polymers with complicated architectures has been largely beneficial from the progresses in polymer chemistry and especially focused by numerous scientists, and appreciable improvement has been achieved.

Originally, Eisenberg et al. reported that the diblock copolymers, for example of poly(styrene)-*b*-poly(acrylic acid) (PS-*b*-PAA), could form a variety of interesting morphologies like spheres,<sup>8-10</sup> rods,<sup>11,12</sup> lamellas,<sup>13-15</sup> vesicles<sup>8,16,17</sup> and hexagonally packed hollow hoops<sup>18</sup> when the medium was deliberately selected. As the simplest topology of diblock copolymers in various complicated polymers, the effect of topology on self-assembly behaviour of polymers might not be reflected in such system. The research model with somewhat complicated topology might be a better choice, for example of PAA-*b*-PS-*b*-PAA, different toroid-shaped and spherical morphologies could be observed in selective solvents.<sup>19</sup> Followed with the pioneer work of Eisenberg's, considerable research progresses have also been made by other researchers. However, most researches were focused on the effect of solvents, compositions, topologies on self-assembly behaviour with multiple independent variables changing at the same time,<sup>14,20-23</sup> and limited works were concentrated on the comparative study of polymers changing a single variable at once (for example, the same compositions but different topologies or conversely the same


topologies but different compositions, etc.). In our previous work, we had tried to synthesize some triblock copolymer poly(styrene)-poly(ethylene oxide)-poly(acrylic acid) (PS-*b*-PEO-*b*-PAA) and PEO-*b*-PS-*b*-PAA with different block sequences to investigate and compare their self-assembly behaviours.<sup>20</sup> Although the polymeric segments could be regulated in the different sequences by a certain synthetic procedure, however, limited in the synthetic methods, the molecular weight of each segment was difficult to control and the obtained results could not be compared in a parallel level. Thus, one could find that the synthesis of polymers with precise compositions and topologies is still a key point and a challenging work.

Typically, for the copolymer with certain compositions and topologies, the “living”/controlled polymerization mechanisms and efficient coupling techniques must be elaborately combined, rather than a random procedure. Especially, a certain efficient coupling technique always plays an important role in the synthesis of polymers. Copper-catalyzed azide / alkyne click (CuAAC) chemistry, because of its tolerance to solvents and various functional groups, as well as its high efficiency (close to 100 %),<sup>24</sup> has been widely applied to the synthesis of multi-block, star-like, hyperbranched, dendrimer-like polymers, etc.<sup>25-28</sup> Another coupling reaction developed by our group, nitroxide radical coupling (NRC) reaction, has also been proved to be a rather robust and orthogonal technique with almost 100 % efficiency.<sup>29-34</sup> Because of the easily available functional halogen groups from atom transfer radical polymerization (ATRP) mechanism, and nitroxide radicals (such as the 2,2,6,6-tetramethylpiperidine-1-oxyl (TEMPO) group or its derivatives) from anionic polymerization mechanism or further modification, the NRC reaction has become an important candidate of coupling technique in polymer chemistry. By means of this NRC

reaction, a library of polymers with complicated architectures has also been smoothly realized.<sup>30-32</sup>

Considering the above researches in self-assembly and the synthetic strategies to complicated polymers, in this contribution, by combination of ATRP mechanism and efficient NRC reaction or CuAAC chemistry, an innovative synthetic process to triblock copolymers PS-*b*-PAA-*b*-PS and PAA-*b*-PS-*b*-PAA with identical compositions but different block sequences was explored. The key precursor of diblock copolymer (TMS-PS-*b*-PtBA-Br) with

bromide group and a trimethylsilyl (TMS) protected alkynyl groups was firstly obtained by sequential ATRP mechanism. Then, the NRC reaction and CuAAC chemistry were selectively used to synthesize triblock copolymer PS-*b*-PtBA-*b*-PS and PtBA-*b*-PS-*b*-PtBA, respectively, and PS-*b*-PAA-*b*-PS and PAA-*b*-PS-*b*-PAA were further obtained by cleavage (Scheme 1). In order to study the difference between PS-*b*-PAA-*b*-PS and PAA-*b*-PS-*b*-PAA, the critical micelle concentration (*cmc*) and the morphologies of copolymers in water were preliminarily investigated and compared.

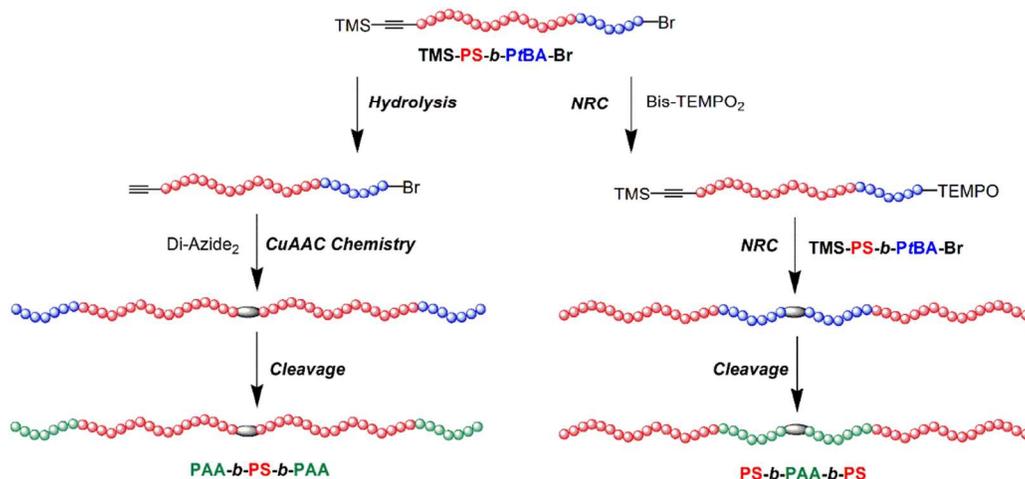

SCHEME 1 The synthetic procedure of triblock copolymers PS-*b*-PAA-*b*-PS and PAA-*b*-PS-*b*-PAA.

## EXPERIMENTAL

### Materials

Styrene [St, 99%, Sinopharm Chemical Reagent Co. (SCR)] was washed with 10% NaOH aqueous solution followed by water three times, dried over anhydrous MgSO<sub>4</sub>, further dried over CaH<sub>2</sub>, and distilled under reduced pressure. *Tert*-butyl acrylate (*t*BA, 99%, SCR) was dried by CaH<sub>2</sub> for 24 h and distilled under reduced pressure before use. Tetrahydrofuran (THF, >99%, SCR) was refluxed and distilled from sodium naphthalene solution. Copper(I) bromide [Cu(I)Br, 95%, SCR] was stirred overnight in acetic acid, filtered, washed with ethanol and ethyl ether successively, and dried in vacuum. *N*-Phenyl-1-naphthylamine (PNA, 97%, Alfa Aesar) was purified by recrystallization in ethanol for three times. Trimethylsilyl propargyl alcohol (99%), 2-bromoisobutyl bromide (99%), 1,4-dibromobutane (98%), *N,N,N',N',N'*-pentamethyldiethylenetriamine (PMDETA, 99%) and Tetrabutylammonium fluoride hydrate (TBAF, 98%) were purchased from Aldrich and used as received. Tris(*N,N*-dimethylamino)ethylamine (Me<sub>6</sub>TREN, 99%) was purchased from Alfa Aesar and used as received. Dimethyl sulfoxide (DMSO, 99%), dimethyl formamide (DMF, 99.5%) and sodium azide (NaN<sub>3</sub>, 98%) were purchased from SCR and used as received. Trimethylsilyl propargyl-2-bromoisobutyrate (TMS-PgBiB) was synthesized according to literature.<sup>35</sup> 4-Hydroxyl-2,2,6,6-tetramethylpiperidine-1-oxyl (HO-TEMPO) was synthesized according to literature.<sup>36</sup> Bis[4-(2,2,6,6-tetramethylpiperidine-1-oxyl)] succinate (Bis-TEMPO<sub>2</sub>) was synthesized according to literature from HO-TEMPO and succinyl dichloride.<sup>37</sup> 1,4-diazidobutane (Di-Azide<sub>2</sub>) was synthesized according to literature<sup>38</sup> from 1,4-dibromobutane and NaN<sub>3</sub>. All other reagents were all purchased from SCR and used as received except for declaration.


### Measurements

Gel permeation chromatographic (GPC) was performed in THF at 35 °C with an elution rate of 1.0 mL/min on an Agilent 1100 equipped with a G1310A pump, a G1362A refractive index detector, and a G1314A variable wavelength detector. One 5- $\mu$ m LP gel column (500 Å, molecular range 500–2  $\times$  10<sup>4</sup> g/mol) and two 5-lm LP gel mixed bed column (molecular range 200–3  $\times$  10<sup>6</sup> g/mol) were calibrated by PS standard samples. <sup>1</sup>H NMR spectra were recorded on a DMX 500-MHz spectrometer in CDCl<sub>3</sub> with tetramethylsilane (TMS) as the internal reference, except for the products PS-*b*-PAA-*b*-PS and PAA-*b*-PS-*b*-PAA, which were measured in DMF-*d*<sub>7</sub> solvent. Steady-state fluorescent spectra of PNA were measured on a FLS920 spectrometer operating at 25 °C. The size of the micelles was measured by dynamic light scattering (DLS) using a Malvern Zetasizer Nano ZS. The emission intensity at 418 nm was recorded to determine the *cmc* and the  $\lambda_{ex}$  was 340 nm. Field emission scanning electron microscopy (FESEM) images were obtained by an Ultra 55 field-emission scanning electron microscope operated at 5 kV.


### Synthesis of Heterofunctional PS with Bromide and a Trimethylsilyl Protected Alkynyl End Groups (TMS- $\equiv$ -PS-Br)

The heterofunctional TMS- $\equiv$ -PS-Br was obtained by ATRP of St monomers from TMS-PgBiB initiator (Scheme 2). Typically, TMS-PgBiB (0.4610 g, 1.66 mmol), CuBr (0.2450 g, 1.71 mmol), PMDETA (0.35 mL, 1.68 mmol) and St (40 mL, 348 mmol) were introduced into a 100-mL ampule successively. The reaction mixture was degassed by three freeze-pump-thaw cycles and purged with nitrogen, and then immersed into oil bath at 90 °C for 5.0 h. After the polymerization was stopped by dipping into liquid nitrogen, the crude product was diluted with THF and passed through a column chromatograph filled with neutral alumina to remove the copper complex, and finally precipitated into methanol. The precipitate was collected and dried at 45 °C in vacuum to a constant weight. GPC:  $M_{n,GPC}$  = 7,500 g/mol, PDI = 1.06. <sup>1</sup>H NMR (CDCl<sub>3</sub>,  $\delta$ , ppm, TMS): 0.12-0.22 ((CH<sub>3</sub>)<sub>3</sub>Si-), 0.78-0.98 (-

$C(CH_3)_2$ -), 1.17-2.51 (3H, aliphatic main chain  $-CH_2CH-$  on PS chain), 3.95-4.20 ( $-C\equiv C-CH_2O-$ ), 4.35-4.55 ( $BrCHCO_2H_5-$ ), 6.30-7.30 (5H, aromatic  $-C_6H_5$  on PS chain).  $M_{n,NMR} = 7,400$  g/mol.

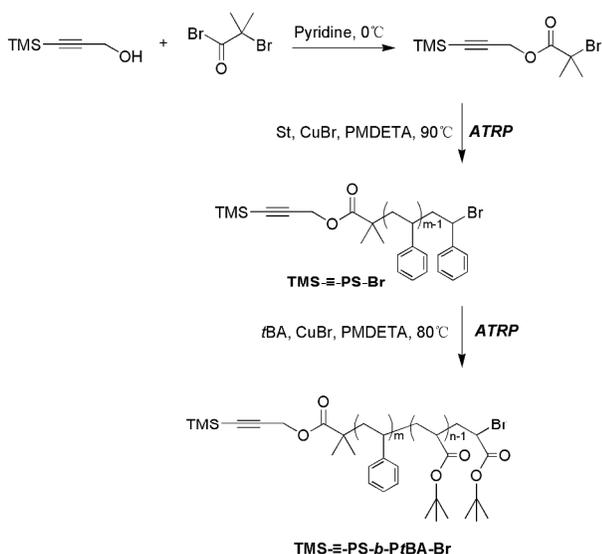

**SCHEME 2** The synthetic procedure of diblock copolymer TMS- $\equiv$ -PS-*b*-PtBA-Br.

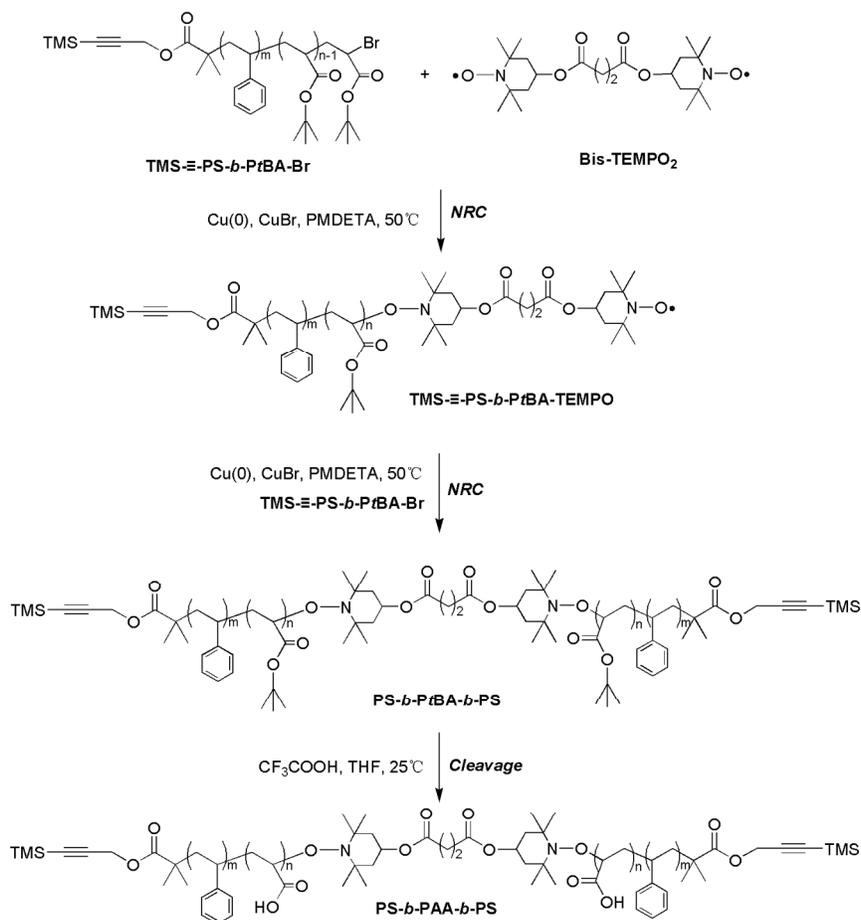

**SCHEME 3** The synthetic procedure of ABA type triblock copolymer PS-*b*-PAA-*b*-PS

### Synthesis of Diblock Copolymer with Bromide and a Trimethylsilyl Protected Alkynyl End Groups (TMS- $\equiv$ -PS-*b*-PtBA-Br)


The diblock copolymer TMS- $\equiv$ -PS-*b*-PtBA-Br was obtained by ATRP of *t*BA monomers initiated from TMS-PS-Br macro-initiator (**Scheme 2**). First, TMS- $\equiv$ -PS-Br (3.00 g, 0.40 mmol), CuBr (0.0630 g, 0.44 mmol), PMDETA (0.10 mL, 0.48 mmol), *t*BA (20 mL, 138 mmol) and toluene (12 mL) were sequentially introduced into a 100-mL ampule. The reaction mixture was degassed by three freeze-pump-thaw cycles and purged with nitrogen, and immersed into oil bath at 80 °C for 5.0 h. After the polymerization was stopped by dipping into liquid nitrogen, the crude product was diluted with THF and passed through a column chromatograph filled with neutral alumina to remove the copper complex, and precipitated into the mixed solvents of methanol and water ( $V_{\text{methanol}}/V_{\text{water}}=1:1$ ). The precipitate was collected and dried at 45 °C in vacuum to a constant weight. GPC:  $M_{n,GPC} = 9,000$  g/mol, PDI = 1.10.  $^1H$  NMR ( $CDCl_3$ ,  $\delta$ , ppm, TMS): 0.12-0.22 ( $(CH_3)_3Si-$ ), 0.78-0.98 ( $-C(CH_3)_2-$ ), 1.13-2.48 (15H, aliphatic main chain  $-CH_2CH-$  on PS chain, aliphatic main chain  $-CH_2CH-$  on PtBA chain and *tert*-butyl group protons  $-C(CH_3)_3$ ), 3.70-3.90 ( $BrCHCOO-$ ), 3.95-4.20 ( $-C\equiv C-CH_2O-$ ), 6.30-7.30 (5H, aromatic  $-C_6H_5$  on PS chain).  $M_{n,NMR} = 10,300$  g/mol.

### Synthesis of Triblock Copolymer PS-*b*-PtBA-*b*-PS

Firstly, the diblock copolymer with a TEMPO and a trimethylsilyl protected alkynyl end groups (TMS≡-PS-*b*-PtBA-TEMPO) was achieved by NRC reaction between TMS≡-PS-*b*-PtBA-Br and Bis-TEMPO<sub>2</sub> (Scheme 3). Into a 100-mL ampule, the TMS-PS-*b*-PtBA-Br (0.1540 g, 0.017 mmol), Bis-TEMPO<sub>2</sub> (0.5090 g, 0.8 mmol), Cu (0.0480 g, 0.75 mmol), CuBr (0.0881 g, 0.60 mmol), Me<sub>6</sub>TREN (0.2740 g, 1.19 mmol), DMSO (1.5 mL) and toluene (1.5 mL) were introduced successively. The reaction mixture was degassed by three freeze-pump-thaw cycles and purged with nitrogen, and then immersed into oil bath at 50 °C for 36 h. After the copper powder was removed by centrifugation, the product was purified according to that of TMS≡-PS-*b*-PtBA-Br, and dried at 45 °C in vacuum to a constant weight.

Then, the triblock copolymer PS-*b*-PtBA-*b*-PS was obtained by a second NRC reaction between TMS≡-PS-*b*-PtBA-

TEMPO and TMS≡-PS-*b*-PtBA-Br. The samples TMS≡-PS-*b*-PtBA-TEMPO (0.1511 g, 0.017 mmol), TMS≡-PS-*b*-PtBA (0.1870 g, 0.02 mmol), Cu(0) (0.0100 g, 0.16 mmol), CuBr (0.0321 g, 0.22 mmol), Me<sub>6</sub>TREN (0.079 g, 0.34 mmol), DMSO (1.0 mL) and toluene (1.0 mL) were introduced into a 100-mL ampule successively. The reaction mixture was degassed by three freeze-pump-thaw cycles and purged with nitrogen, and then immersed into oil bath at 50 °C for 36 h. The subsequent purification procedure was also similar to that of TMS≡-PS-*b*-PtBA-Br. In order to remove the uncoupled diblock copolymers, the product was further purified by fractional precipitation from THF/H<sub>2</sub>O system, and the obtained product was dried at 45 °C in vacuum to a constant weight. GPC:  $M_{n,GPC} = 19,800$  g/mol, PDI = 1.13. <sup>1</sup>H NMR (CDCl<sub>3</sub>, δ, ppm, TMS): 2.10-2.48 (-CH<sub>2</sub>CH- on PtBA chain), 6.30-7.30 (5H, aromatic -C<sub>6</sub>H<sub>5</sub> on PS chain).

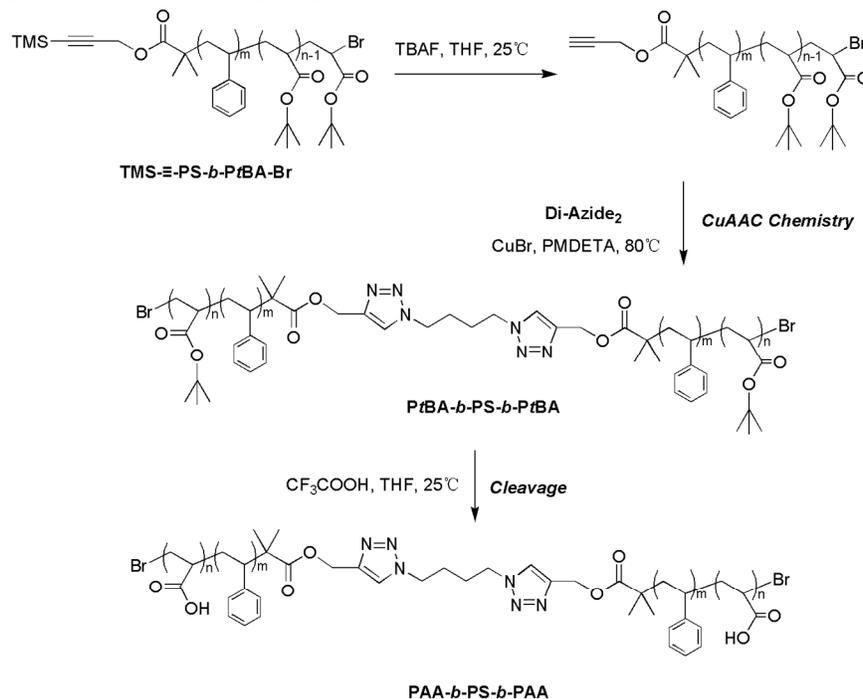

**SCHEME 4** The synthetic procedure of BAB type triblock copolymer PAA-*b*-PS-*b*-PAA.

### Synthesis of Triblock Copolymer PtBA-*b*-PS-*b*-PtBA

Firstly, the Alkynyl-PS-*b*-PtBA-Br was obtained by removal of TMS group from diblock copolymer TMS≡-PS-*b*-PtBA-Br (Scheme 4). Typically, the sample TMS≡-PS-*b*-PtBA-Br (0.7801 g, 0.060 mmol) was dissolved in THF (30 mL) and TBAF (0.29 g, 0.92 mmol) was introduced. After the mixture was immersed into an oil bath at 25 °C for 24 h, the product was precipitated into a mixed solvent of methanol and water ( $V_{\text{methanol}}/V_{\text{water}}=1:1$ ). The precipitate was collected and dried at 45 °C in vacuum to a constant weight.

Subsequently, the triblock copolymer PtBA-*b*-PS-*b*-PtBA was obtained by CuAAC chemistry between Di-Azide<sub>2</sub> and Alkynyl-PS-*b*-PtBA (0.2900 g, 0.023 mmol), CuBr (0.0851 g, 0.060 mmol), PMDETA (1.2 mL, 5.76 mmol) and DMF (1.5 mL) were introduced into a 100-mL ampule successively. After the reaction mixture was

degassed by three freeze-pump-thaw cycles and purged with nitrogen, the ampule was immersed into an oil bath at 80 °C and Di-Azide<sub>2</sub> (0.0231 g, 0.118 mmol) was added into the ampule dropwise by syringe in 12 h. After another 24 h, the crude polymers were recovered by the similar procedure for TMS≡-PS-*b*-PtBA-Br. The uncoupled diblock copolymers were also removed by fractional precipitation from THF/H<sub>2</sub>O system, and the obtained product was dried at 45 °C in vacuum to a constant weight. GPC:  $M_{n,GPC} = 20,000$  g/mol, PDI = 1.10. <sup>1</sup>H NMR (CDCl<sub>3</sub>, δ, ppm, TMS): 2.10-2.48 (-CH<sub>2</sub>CH- on PtBA chain), 6.30-7.30 (5H, aromatic -C<sub>6</sub>H<sub>5</sub> on PS chain).

### Synthesis of ABA Type PS-*b*-PAA-*b*-PS and BAB Type PAA-*b*-PS-*b*-PAA Triblock Copolymer

The triblock copolymers PS-*b*-PAA-*b*-PS and PAA-*b*-PS-*b*-PAA were prepared by cleavage of corresponding triblock

copolymer PS-*b*-PtBA-*b*-PS and PtBA-*b*-PS-*b*-PtBA. Taking the cleavage of PS-*b*-PtBA-*b*-PS as example, PS-*b*-PtBA-*b*-PS (0.0201 g,  $8 \times 10^{-4}$  mmol), THF (5.0 mL) and CF<sub>3</sub>COOH (1.0 mL) were introduced into a 50-mL round-bottom flask. After 24 h, the reaction mixture was evaporated by a rotary evaporator to remove the solvent. The crude product was dissolved by DMF and precipitated into water. The solvent was removed by centrifugation and the achieved product was dried at 45 °C in vacuum to a constant weight. <sup>1</sup>H NMR (CDCl<sub>3</sub>, δ, ppm, TMS): 2.10-2.48 (-CH<sub>2</sub>CH- on PAA chain), 6.30-7.30 (5H, aromatic -C<sub>6</sub>H<sub>5</sub> on PS chain). Similarly, the PAA-*b*-PS-*b*-PAA was obtained by cleavage of triblock copolymer PtBA-*b*-PS-*b*-PtBA.

#### Determination of Critical Micelle Concentration (*cmc*) of Amphiphilic ABA Type PS-*b*-PAA-*b*-PS and BAB Type PAA-*b*-PS-*b*-PAA Triblock Copolymers

According to literature,<sup>39</sup> the PNA was used as fluorescence probe to measure the *cmc* values of triblock copolymer PS-*b*-PAA-*b*-PS or PAA-*b*-PS-*b*-PAA in water. First, the acetone solution of PNA (0.001 mol/L) was added into a large amount of water to give the concentration of PNA of  $2 \times 10^{-9}$  mol/mL. Then, different amounts of micellar solution of PS-*b*-PAA-*b*-PS or PAA-*b*-PS-*b*-PAA were added into water containing PNA ([PNA] =  $2 \times 10^{-9}$  mol/mL), and the concentration of triblock copolymer PS-*b*-PAA-*b*-PS or PAA-*b*-PS-*b*-PAA were modulated from  $2.0 \times 10^{-8}$  to 0.1 g/mL for FLS measurement.

#### Self-assembly Behaviour of Amphiphilic ABA Type PS-*b*-PAA-*b*-PS and BAB Type PAA-*b*-PS-*b*-PAA Triblock Copolymers

Typically, the triblock copolymer PS-*b*-PAA-*b*-PS or PAA-*b*-PS-*b*-PAA (6.0 mg) was dissolved in DMF (2.0 mL), and the deionized water (8 mL) was added dropwise using syringe pump under vigorous stirring within 3.0 h. After stirring for another 24 h, the suspension system was dialyzed against deionized water for three days using a dialysis bag with a 3kDa cutoff molecular weight. The obtained micelle solution was diluted to  $5 \times 10^{-4}$  g/mL and characterized by FESEM instrument. The samples were freeze in liquid nitrogen and dried in a freeze drier before observation.

## RESULTS AND DISCUSSION

#### Synthesis and Characterization of Diblock Copolymer TMS≡PS-*b*-PtBA-Br

The diblock copolymer TMS≡PS-*b*-PtBA-Br with a functional bromide and a protected alkynyl end groups was prepared by ATRP of *t*BA monomers from TMS≡PS-Br macro-initiator, which was synthesized by ATRP of St monomers from TMS-PgBiB initiator. Fig. 1 (A) and (B) showed the GPC traces of TMS≡PS-Br and TMS≡PS-*b*-PtBA-Br, respectively, the monomodal peaks, low PDIs and the clear shift from TMS≡PS-Br curve to TMS≡PS-*b*-PtBA-Br curve confirmed that both ATRP procedures were successful.

In Fig. 2 (A) for the <sup>1</sup>H NMR of TMS≡PS-Br, except for the characteristic resonance signals for aromatic protons (-C<sub>6</sub>H<sub>5</sub>) on PS chain at 6.30-7.30 ppm (e), the <sup>1</sup>H NMR spectrum also exhibited the characteristic resonance signals due to methine group proton (BrCHC<sub>6</sub>H<sub>5</sub>-) at 4.35-4.55 ppm

(d'), propargyl group protons (-C≡C-CH<sub>2</sub>O-) at 3.95-4.20 ppm (a) and methyl group protons (-C(CH<sub>3</sub>)<sub>2</sub>-) at 0.78-0.98 ppm (b), which further proved the successful preparation of TMS≡PS-Br. According to <sup>1</sup>H NMR spectrum, the  $M_{n,NMR}$  of TMS≡PS-Br was calculated by Formula 1:

$$M_{n,NMR} = \frac{A_{6.30-6.90}/2}{A_{3.95-4.20}/2} \times 104 + 277 \quad (1)$$

where  $A_{6.30-6.90}$  was the integral area of partial aromatic protons on PS chain, and  $A_{3.94-4.20}$  was the integral area of propargyl group protons (-C≡C-CH<sub>2</sub>O-) at 3.95-4.20 ppm. The values of 104 and 277 were the molecular weight of St unit and that of initiator residue, respectively. The obtained  $M_{n,NMR}$  was 7,400 g/mol, which approximated to that obtained from above GPC measurement (7,500 g/mol). The amount of St unit on each macromolecule was also estimated as 68, and the detailed data was listed in Table 1.

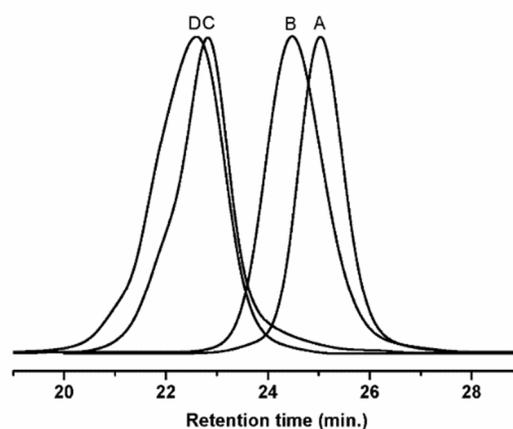


FIGURE 1 The GPC traces of TMS≡PS-Br (A) ( $M_n = 7,500$  g/mol, PDI = 1.06), TMS≡PS-*b*-PtBA-Br (B) ( $M_n = 9,000$  g/mol, PDI = 1.10), PS-*b*-PtBA-*b*-PS (C) ( $M_n = 19,800$  g/mol, PDI = 1.13), PtBA-*b*-PS-*b*-PtBA (D) ( $M_n = 20,000$  g/mol, PDI = 1.10).

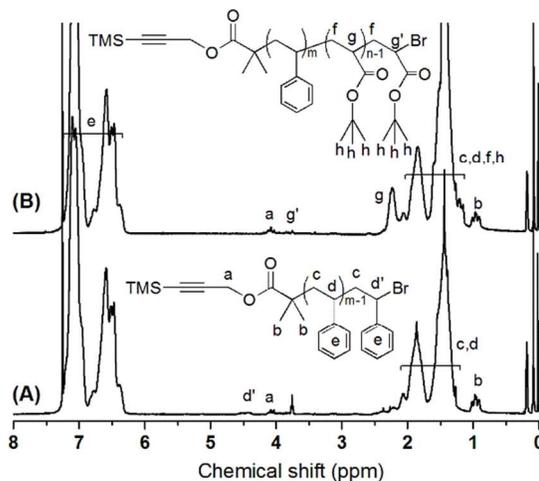


FIGURE 2 The <sup>1</sup>H NMR spectra of TMS≡PS-Br (A), TMS≡PS-*b*-PtBA-Br (B) (in CDCl<sub>3</sub> solvent).

Also, the  $^1\text{H}$  NMR spectrum of TMS- $\equiv$ -PS-*b*-P*t*BA-Br was shown in Fig. 2 (B), compared with that of TMS- $\equiv$ -PS-Br, the new resonance signal at 3.70-3.90 ppm (g') for methine group proton (BrCHCOO-) and the resonance signal at 2.10-2.48 ppm (g) for methine group proton (-CH<sub>2</sub>CH) confirmed the successful ATRP of *t*BA monomers from TMS- $\equiv$ -PS-Br macro-initiator. According to  $^1\text{H}$  NMR spectrum, the  $M_{n,\text{NMR}}$  of TMS- $\equiv$ -PS-*b*-P*t*BA-Br could be derived from Formula 2:

$$M_{n,\text{NMR}} = \left( \frac{A_{2.10-2.48}}{A_{6.30-6.90}/2} \times \frac{128}{104} + 1 \right) \times M_{n,\text{NMR},(\text{TMS-}\equiv\text{-PS-Br)} \quad (2)$$

where  $A_{2.10-2.48}$  was the integral area of the methine group proton (-CH<sub>2</sub>CH) at 2.10-2.48 ppm. The value of 128 was the molecular weight of *t*BA units. And others were the same as defined before. The obtained  $M_{n,\text{NMR}}$  was 10,300 g/mol, and the amount of P*t*BA units introduced on each macromolecule was calculated as 23.

**TABLE 1** The data of the target copolymers and the intermediates.

Entry	$M_{n,\text{GPC}}$ (g/mol) <sup>a</sup>	PDI <sup>a</sup>	$M_{n,\text{NMR}}$ (g/mol)	$N_{\text{St}}^{\text{d}}$	$N_{\text{tBA}}^{\text{e}}$
TMS- $\equiv$ -PS-Br	7,500	1.06	7,400 <sup>b</sup>	68	
TMS- $\equiv$ -PS- <i>b</i> -P <i>t</i> BA-Br	9,000	1.10	10,300 <sup>c</sup>	68	32
PS- <i>b</i> -P <i>t</i> BA- <i>b</i> -PS	19,800	1.13	20,600	136	64
P <i>t</i> BA- <i>b</i> -PS- <i>b</i> -P <i>t</i> BA	2,0000	1.10	20,600	136	64


<sup>a</sup> Determined by GPC performed in THF solvent using PS as standard. <sup>b</sup> The molecular weight was calculated according to Formula 1. <sup>c</sup> The molecular weight was calculated according to Formula 2. <sup>d</sup> The number of St units was calculated using Formula:  $N_{\text{St}} = M_{n,\text{NMR},(\text{TMS-}\equiv\text{-PS-Br})}/104$ , where the value of 104 corresponded to the molecular weights of St unit. <sup>e</sup> The number of *t*BA units was calculated using Formula:  $N_{\text{tBA}} = (M_{n,\text{NMR},(\text{TMS-}\equiv\text{-PS-}b\text{-P}t\text{BA-Br})} - M_{n,\text{NMR},(\text{TMS-}\equiv\text{-PS-Br})})/128$ , where the value of 128 corresponded to the molecular weights of *t*BA unit.

### Synthesis and Characterization of ABA Type Triblock Copolymer PS-*b*-PAA-*b*-PS

For the target ABA type triblock copolymer PS-*b*-PAA-*b*-PS, the atom transfer radical coupling (ATRC)<sup>40</sup> was initially adopted to synthesize PS-*b*-P*t*BA-*b*-PS. However, almost no coupling product was discriminated from GPC measurement, which can be ascribed to the disproportionation termination on terminal P*t*BA-Br.<sup>41-43</sup> Especially, the higher molecular weight of precursor would bring a larger hindrance, and further led to a lower coupling efficiency. Alternatively, the NRC reaction was considered to synthesize PS-*b*-PAA-*b*-PS. Firstly, its precursor PS-*b*-P*t*BA-*b*-PS was obtained by NRC reaction between TMS- $\equiv$ -PS-*b*-P*t*BA-Br and TMS- $\equiv$ -PS-*b*-P*t*BA-TEMPO, and the latter was first prepared by NRC reaction between TMS- $\equiv$ -PS-*b*-P*t*BA-Br and the coupling agent Bis-TEMPO<sub>2</sub>.

In order to obtain a high coupling efficiency, the feed procedure was well analyzed and balanced. In the first case, an attempt was made to couple the TMS- $\equiv$ -PS-*b*-P*t*BA-Br and Bis-TEMPO<sub>2</sub> directly to get the target PS-*b*-P*t*BA-*b*-PS. That was, the TMS- $\equiv$ -PS-*b*-P*t*BA-Br and Bis-TEMPO<sub>2</sub> were simultaneously added and sealed in the system. However, the inevitable equivalent deviation between the macromolecule TMS- $\equiv$ -PS-*b*-P*t*BA-Br and small molecular weight compound Bis-TEMPO<sub>2</sub> always produced amount of uncoupled precursors. Alternatively, the equivalent deviation between macromolecules and Bis-TEMPO<sub>2</sub> might be solved by a dropwise addition procedure. Thus, in the second case, the macromolecule TMS- $\equiv$ -PS-*b*-P*t*BA-Br was first added and the compound Bis-TEMPO<sub>2</sub> was added dropwise by syringe. However, the trace oxygen might be introduced by syringe, which would have a vital effect on the NRC reaction. Also, the instantaneous low concentration of TEMPO groups in system would not guarantee the sufficient NRC reaction and the side reaction (such as the disproportionation termination) of generated carbon radicals might be enhanced. Conversely, in the third case, the compound Bis-TEMPO<sub>2</sub> was first added and the macromolecule TMS- $\equiv$ -PS-*b*-P*t*BA-Br in toluene was then added dropwise. Similarly, except for

the introduction of trace oxygen, the viscous TMS- $\equiv$ -PS-*b*-P*t*BA-Br solution also increased the trouble of feeding procedure. Thus, in order to avoid the equivalent deviation from calculation and the introduction of trace oxygen, as well as reduce the side reaction of formed carbon radical in system and simplify the operation, a fourth route in this work was designed and adopted. That was, the precursor TMS- $\equiv$ -PS-*b*-P*t*BA-TEMPO was first formed by NRC reaction between TMS- $\equiv$ -PS-*b*-P*t*BA-Br and excess coupling agent Bis-TEMPO<sub>2</sub>, and the purified TMS- $\equiv$ -PS-*b*-P*t*BA-TEMPO (see Fig. S1 in Supporting Information) could then couple with the precursor TMS- $\equiv$ -PS-*b*-P*t*BA-Br.

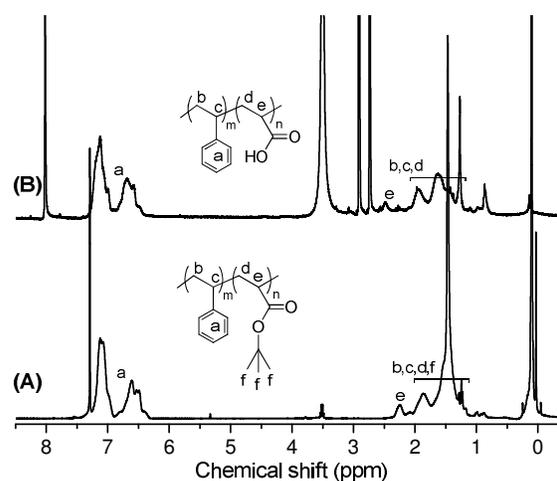

**FIGURE 3** The  $^1\text{H}$  NMR spectra of PS-*b*-P*t*BA-*b*-PS (A) (in CDCl<sub>3</sub> solvent) and PS-*b*-PAA-*b*-PS (B) (in DMF-*d*<sub>7</sub> solvent).

After the purification of crude product, Fig. 1 (C) showed the GPC trace of PS-*b*-P*t*BA-*b*-PS. The monomodal peak, low PDI (1.13) and the significantly increased  $M_{n,\text{GPC}}$  (19,800 g/mol) compared with that of TMS- $\equiv$ -PS-*b*-P*t*BA-Br

confirmed that the NRC was successful. In **Fig. 3 (A)**, except for the characteristic resonance signals for aromatic protons ( $-C_6H_5$ ) on PS chain at 6.30-7.30 ppm (a), the  $^1H$  NMR spectrum of PS-*b*-PtBA-*b*-PS also exhibited the characteristic resonance signals due to methine group proton ( $-CH_2CH-$ ) at 2.10-2.48 ppm (e). Finally, the ABA type triblock copolymers PS-*b*-PAA-*b*-PS was further prepared by **cleavage** of PS-*b*-PtBA-*b*-PS in THF solvent in the presence of  $CF_3COOH$ . **Fig. 3 (B)** showed the  $^1H$  NMR spectrum of PS-*b*-PAA-*b*-PS in  $DMF-d_7$ . Compared with the spectrum of PS-*b*-PtBA-*b*-PS, the resonance signal at 1.13-2.48 ppm in the spectrum of PS-*b*-PAA-*b*-PS was obviously weakened, which showed that the *tert*-butyl groups on PtBA segment were removed. Thus, all the above information clearly confirmed that the ABA type triblock copolymer PS-*b*-PAA-*b*-PS was obtained.

### Synthesis and Characterization of BAB Type Triblock Copolymer PAA-*b*-PS-*b*-PAA


Also, in order to get the target BAB type triblock copolymer PAA-*b*-PS-*b*-PAA, its precursor PtBA-*b*-PS-*b*-PtBA was prepared by CuAAC chemistry between Alkynyl-PS-*b*-PtBA-Br (see **Fig. S2** in Supporting Information) and the coupling agent Di-Azide<sub>2</sub>, and the former was derived from the **cleavage** of  $TMS\equiv PS-*b*-PtBA-Br$  in the presence of TBAF. Unlike the NRC reaction, because the CuAAC chemistry tolerates a certain content of oxygen, the dropwise addition procedure could be considered in this system. That was, the Alkynyl-PS-*b*-PtBA-Br was **firstly** added and Di-Azide<sub>2</sub> was then added dropwise, which could largely exclude the equivalent deviation between macromolecules Alkynyl-PS-*b*-PtBA-Br and small molecular weight compound Di-Azide<sub>2</sub> and further ensure the high coupling efficiency. As mentioned in the above section, the terminal PtBA-Br tended to the disproportionation termination<sup>43</sup> and the products formed from ATRC reaction can be neglected. Thus, under this CuAAC chemistry condition, the interruption of ATRC reaction can be excluded and the aimed product PtBA-*b*-PS-*b*-PtBA was achieved.

**Fig. 1(D)** showed the GPC trace of purified PtBA-*b*-PS-*b*-PtBA. The monomodal peak, low PDI (1.10), as well as the increased  $M_{n,GPC}$  (20,000 g/mol) confirmed that the CuAAC chemistry was successful. The  $^1H$  NMR spectra of PtBA-*b*-PS-*b*-PtBA and PAA-*b*-PS-*b*-PAA showed similar results to those of the above PS-*b*-PtBA-*b*-PS and PS-*b*-PAA-*b*-PS (see **Fig. S3** in Supporting Information), which further meant that **these** two series of triblock copolymers actually had the identical compositions but different block sequences.

### Self-assembly Behaviour of Amphiphilic ABA Type PS-*b*-PAA-*b*-PS and BAB Type PAA-*b*-PS-*b*-PAA Triblock Copolymer

The amphiphilic nature of triblock copolymer PS-*b*-PAA-*b*-PS or PAA-*b*-PS-*b*-PAA, consisting of hydrophobic PS chain and hydrophilic PAA chain, provided an opportunity to form micelles in a selective solvent (such as water). The *cmc* of triblock copolymer in water was determined by fluorescence technique using PNA as probe, which is a more suitable fluorescent probe than pyrene in terms of reproducibility because it displays higher fluorescence activity in nonpolar environments and can also be very easily quenched by polar solvents (such as water).<sup>39</sup> The relationship of the

fluorescence intensity ratio ( $I/I_0$ ) of PNA as a function of the concentration of PS-*b*-PAA-*b*-PS was plotted in **Fig. 4 (A)**. It was found that  $I/I_0$  increased sharply when the concentration exceeded a certain value, which demonstrated that the PNA probe began to be incorporated into the hydrophobic region of micelles. Thus, the intersection of two straight lines with a value of  $8.44 \times 10^{-3}$  g/L was determined as the *cmc* of PS-*b*-PAA-*b*-PS. Similarly, the *cmc* of PAA-*b*-PS-*b*-PAA was also determined as  $2.62 \times 10^{-2}$  g/L according to **Fig. 4 (B)**. Obviously, the *cmc* value of PS-*b*-PAA-*b*-PS was about 32 times higher than that of PAA-*b*-PS-*b*-PAA. In a parallel level, with the identical compositions but different block sequences, these two copolymers show distinct *cmc* values. This result could give the information that the block sequence (connection style of segment) actually has effect on the self-assembly behaviour of amphiphilic triblock copolymers.

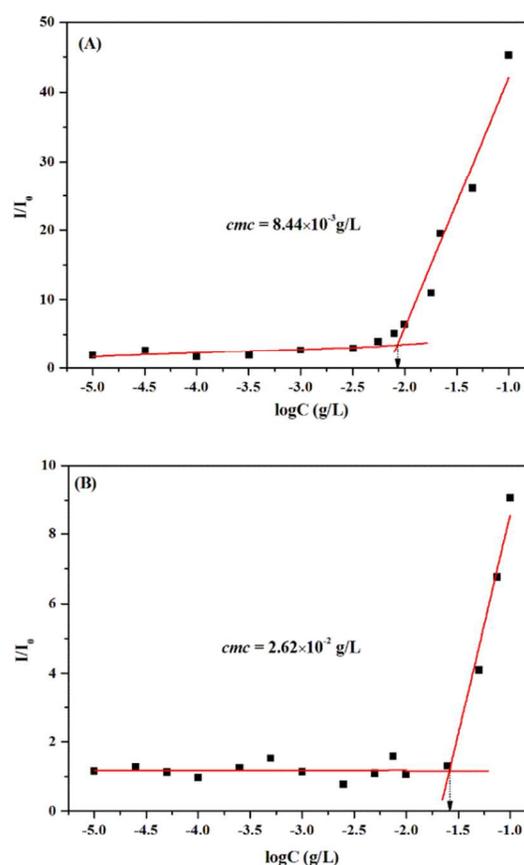

**FIGURE 4** Dependence of fluorescence intensity ratio  $I/I_0$  of PNA fluorescence emission spectra on the concentration of PS-*b*-PAA-*b*-PS (A) or PAA-*b*-PS-*b*-PAA (B) triblock copolymer ( $\lambda_{ex}=340$ nm).


To further investigate the differences of solution behaviour between the triblock copolymer PS-*b*-PAA-*b*-PS and PAA-*b*-PS-*b*-PAA, the micelle morphology was observed by FESEM instrument. As a reference, the micelle morphology of PS-*b*-PAA was also observed simultaneously. The diblock copolymer PS-*b*-PAA was obtained by the typical **cleavage** of  $TMS\equiv PS-*b*-PtBA-Br$  by  $CF_3COOH$ . **Fig. 5 (A, B, C)**

showed the micelle morphologies of PS-*b*-PAA, PS-*b*-PAA-*b*-PS and PAA-*b*-PS-*b*-PAA in water. Small particles could be found scattered in all the three FESEM images, which meant that the micelles were formed by all the three copolymers. Differently, it was found that the size of micelles from triblock copolymer PS-*b*-PAA-*b*-PS was similar to that of micelles from diblock copolymer PS-*b*-PAA, while the size of micelles from triblock copolymer PAA-*b*-PS-*b*-PAA were somewhat larger. That was, the average diameter of PS-*b*-PAA micelles or PS-*b*-PAA-*b*-PS micelles was around 30 nm, and the average diameter of PAA-*b*-PS-*b*-PAA micelles was around 47 nm. Also, by DLS measurement, the sizes of micelles formed by PS-*b*-PAA, PS-*b*-PAA-*b*-PS and PAA-*b*-PS-*b*-PAA copolymers were obtained as 17nm, 18nm and 44nm, respectively (Fig. S4), which were well agreed with those by SEM instrument.


From Fig. 5 (A, B, C), all these amphiphilic copolymers showed the classical spherical morphologies in water. As has been well investigated, the spherical morphologies were the simplest morphologies of micelles, in which the hydrophobic segments tend to form a core inside the micelle particle while the hydrophilic segments tend to form a shell outside the micelle (Scheme 4).<sup>44</sup> Based on the result that the size of PS-*b*-PAA-*b*-PS micelles was similar to PS-*b*-PAA micelles, while the PAA-*b*-PS-*b*-PAA micelles were somewhat larger, we might figure that the block sequence of the copolymers played a very important role in the formation of micelles. For triblock copolymer PS-*b*-PAA-*b*-PS, because both ends of PAA segment were seriously restricted by PS segments, the outer PAA shell in micelle could not be well solubilized in water. Differently, for triblock copolymer PAA-*b*-PS-*b*-PAA, only one end of PAA segment was connected on PS segment, and the outer PAA segments in micelle could wind into water freely. This fact could also explain why the PAA-*b*-PS-*b*-PAA micelles were larger than PS-*b*-PAA-*b*-PS micelles.

As described in INTRODUCTION section, although plenty of works had focused on the self-assembly behaviour of

amphiphilic polymers, rare of them had aimed to study the effect of solvents, compositions, topologies on their properties changing a single variable at once. In this contribution, based on the precisely designed synthetic route, the ABA type triblock copolymer PS-*b*-PAA-*b*-PS and BAB type triblock copolymer PAA-*b*-PS-*b*-PAA were both synthesized from the same precursor of TMS≡-PS-*b*-PrBA-Br, which made the two triblock copolymers share the identical compositions but different block sequences. The different self-assembly behaviour of these copolymers in water might be an important result to enrich the structure-property relationship. Also, this difference might be evidence that the triblock copolymers with identical compositions but different block sequences were actually synthesized.

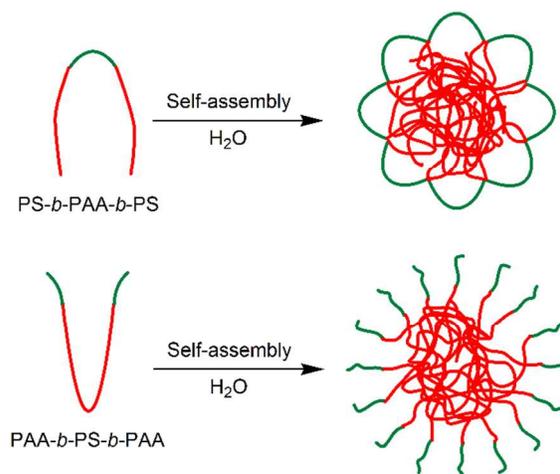

**SCHEME 5** The proposed mechanism for the formation of micelles of triblock copolymer PS-*b*-PAA-*b*-PS and PAA-*b*-PS-*b*-PAA with identical compositions but different block sequences in selective solvent.

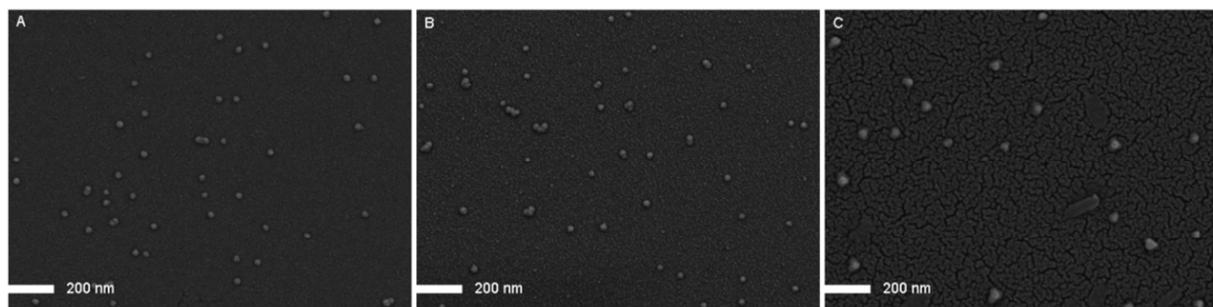

**FIGURE 5** FESEM images of micelles formed by PS-*b*-PAA (A), PS-*b*-PAA-*b*-PS (B) and PAA-*b*-PS-*b*-PAA (C) in water.

## ARTICLE

## CONCLUSIONS

In conclusion, the amphiphilic ABA type PS-*b*-PAA-*b*-PS and BAB type PAA-*b*-PS-*b*-PAA triblock copolymers with identical compositions but different block sequences were successfully synthesized by combination of ATRP mechanism and NRC or CuAAC chemistry. This versatile synthetic route might be used to derive series of copolymers with varied compositions. The self-assembly behaviour of copolymers was preliminarily studied and compared, and the results showed that the PS-*b*-PAA-*b*-PS and PAA-*b*-PS-*b*-PAA could give distinct *cmc* values and different sizes of micelles in selective solvents, which further enriches the related theory of structure-property relationship.

## SUPPORTING INFORMATION

More information of <sup>1</sup>H NMR spectra for intermediates and target copolymers and DLS results.

## ACKNOWLEDGEMENTS

We appreciate the financial support of this research by the Natural Science Foundation of China (21274024).

## NOTES AND REFERENCES

Department of Macromolecular Science, State Key Laboratory of Molecular Engineering of Polymers, Fudan University, Shanghai 200433, China

Correspondence to: Guowei Wang (E-mail: gwwang@fudan.edu.cn)

- Lin, W. J.; Chen, W. C.; Wu, W. C.; Niu, Y. H.; Jen, A. K. Y. *Macromolecules* **2004**, *37*, 2335-2341.
- Yoshida, R.; Uchida, K.; Kaneko, Y.; Sakai, K.; Kikuchi, A.; Sakurai, Y.; Okano, T. *Nature* **1995**, *374*, 240-242.
- Liu, B. L.; Kazlaucinas, A.; Guthrie, J. T.; Perrier, S. *Macromolecules* **2005**, *38*, 2131-2136.
- Jikei, M.; Kakimoto, M. *Progress in Polymer Science* **2001**, *26*, 1233-1285.
- Zhang, Y.; Wang, G.; Huang, J. *Macromolecules* **2010**, *43*, 10343-10347.
- Jia, Z.; Fu, Q.; Huang, J. *Macromolecules* **2006**, *39*, 5190-5193.
- Yagci, Y.; Tasdelen, M. A. *Progress in Polymer Science* **2006**, *31*, 1133-1170.
- Zhang, L. F.; Eisenberg, A. *Journal of the American Chemical Society* **1996**, *118*, 3168-3181.
- Zhang, L. F.; Eisenberg, A. *Science* **1995**, *268*, 1728-1731.
- Gao, Z. S.; Varshney, S. K.; Wong, S.; Eisenberg, A. *Macromolecules* **1994**, *27*, 7923-7927.
- Zhang, L. F.; Yu, K.; Eisenberg, A. *Science* **1996**, *272*, 1777-1779.
- Zhang, L. F.; Eisenberg, A. *Polymers for Advanced Technologies* **1998**, *9*, 677-699.
- Zhang, L. F.; Eisenberg, A. *Macromolecules* **1999**, *32*, 2239-2249.
- Shen, H. W.; Eisenberg, A. *Macromolecules* **2000**, *33*, 2561-2572.
- Liang, H.; Favis, B. D.; Yu, Y. S.; Eisenberg, A. *Macromolecules* **1999**, *32*, 1637-1642.
- Zhang, L. F.; Eisenberg, A. *Macromolecules* **1996**, *29*, 8805-8815.
- Shen, H. W.; Eisenberg, A. *Angewandte Chemie-International Edition* **2000**, *39*, 3310-+.
- Zhang, L. F.; Bartels, C.; Yu, Y. S.; Shen, H. W.; Eisenberg, A. *Physical Review Letters* **1997**, *79*, 5034-5037.
- Ruehl, J.; Nilsen, A.; Born, S.; Thoniyot, P.; Xu, L.-P.; Chen, S.; Braslau, R. *Polymer* **2007**, *48*, 2564-2571.
- Zhang, Y.; Lin, W.; Jing, R.; Huang, J. *Journal of Physical Chemistry B* **2008**, *112*, 16455-16460.
- Hückstädt, H.; Göpfert, A.; Abetz, V. *Polymer* **2000**, *41*, 9089-9094.
- Chen, Z.; Cui, H.; Hales, K.; Li, Z.; Qi, K.; Pochan, D. J.; Wooley, K. L. *Journal of the American Chemical Society* **2005**, *127*, 8592-8593.
- Azzam, T.; Eisenberg, A. *Angewandte Chemie International Edition* **2006**, *45*, 7443-7447.
- El-Sagheer, A. H.; Brown, T. *Chemical Society Reviews* **2010**, *39*, 1388-1405.
- Vogtle, F.; Gestermann, S.; Hesse, R.; Schwierz, H.; Windisch, B. *Progress in Polymer Science* **2000**, *25*, 987-1041.
- Murat, M.; Grest, G. S. *Macromolecules* **1996**, *29*, 1278-1285.
- Matthews, O. A.; Shipway, A. N.; Stoddart, J. F. *Progress in Polymer Science* **1998**, *23*, 1-56.
- Binder, W. H.; Sachsenhofer, R. *Macromolecular Rapid Communications* **2007**, *28*, 15-54.
- Fu, Q.; Lin, W.; Huang, J. *Macromolecules* **2008**, *41*, 2381-2387.
- Fu, Q.; Zhang, Z.; Lin, W.; Huang, J. *Macromolecules* **2009**, *42*, 4381-4383.
- Kulis, J.; Bell, C. A.; Micallef, A. S.; Jia, Z.; Monteiro, M. J. *Macromolecules* **2009**, *42*, 8218-8227.
- Zhang, K.; Zhuang, P.; Wang, Z.; Li, Y.; Jiang, Z.; Hu, Q.; Liu, M.; Zhao, Q. *Carbohydrate Polymers* **2012**, *90*, 1515-1521.
- Lin, W.; Fu, Q.; Zhang, Y.; Huang, J. *Macromolecules* **2008**, *41*, 4127-4135.
- Li, Y.; Zhang, Y.; Yang, D.; Li, Y.; Hu, J.; Feng, C.; Zhai, S.; Lu, G.; Huang, X. *Macromolecules* **2010**, *43*, 262-270.
- Opsteen, J. A.; van Hest, J. C. M. *Chemical Communications* **2005**, 57-59.
- Kurosaki, T.; Wanlee, K.; Okawara, M. *Journal of Polymer Science Part a-Polymer Chemistry* **1972**, *10*, 3295-3310.
- Nicolay, R.; Marx, L.; Hemery, P.; Matyjaszewski, K. *Macromolecules* **2007**, *40*, 9217-9223.
- Fan, X.; Huang, B.; Wang, G.; Huang, J. *Macromolecules* **2012**, *45*, 3779-3786.
- You, L. C.; Lu, F. Z.; Li, Z. C.; Zhang, W.; Li, F. M. *Macromolecules* **2003**, *36*, 1-4.
- Yoshikawa, C.; Goto, A.; Fukuda, T. *e-Polymers* **2002**, *2*, 172-183.
- Wrue, M. H.; McUmber, A. C.; Anthamatten, M. *Macromolecules* **2009**, *42*, 9255-9262.
- GAN, B. A.; GCI, Y. Y. *Turk J Chem* **2007**, *31*, 1-10.
- Wang, G.; Huang, J. *Polymer Chemistry* **2014**, *5*, 277-308.
- Halperin, A.; Tirrell, M.; Lodge, T. P. *Advances in Polymer Science* **1992**, *100*, 31-71.