

RSC Advances



This is an *Accepted Manuscript*, which has been through the Royal Society of Chemistry peer review process and has been accepted for publication.

Accepted Manuscripts are published online shortly after acceptance, before technical editing, formatting and proof reading. Using this free service, authors can make their results available to the community, in citable form, before we publish the edited article. This *Accepted Manuscript* will be replaced by the edited, formatted and paginated article as soon as this is available.

You can find more information about *Accepted Manuscripts* in the [Information for Authors](#).

Please note that technical editing may introduce minor changes to the text and/or graphics, which may alter content. The journal's standard [Terms & Conditions](#) and the [Ethical guidelines](#) still apply. In no event shall the Royal Society of Chemistry be held responsible for any errors or omissions in this *Accepted Manuscript* or any consequences arising from the use of any information it contains.

COMMUNICATION

Cite this: DOI: 10.1039/x0xx00000x

Phthalocyanine Blue in Aqueous Solutions

Mark Staniford,^a Marina M. Lezhnina,^{a,b} Ulrich H. Kynast^{a*}

Received 00th January 2012, Accepted 00th January 2012

DOI: 10.1039/x0xx00000x

www.rsc.org/

Using laponite nano-clay carriers, a facile method for the solubilisation of natively insoluble phthalocyanines into aqueous solution is described. Copper(II) phthalocyanine, technologically a most relevant pigment (C.I. Pigment Blue 15), thus yields hitherto unknown clear and stable aqueous dispersions of either colloidal α -CuPc or monomeric CuPc, depending on details of the preparation.

Copper(II) phthalocyanine (CuPc) is one of the most frequently used pigments in painting and coating industries, with an annual production of approximately 60 000 t/yr. The blue colorant possesses a very high extinction coefficient due to the intense π - π^* transitions within the ligand electronic system. Its insolubility in common solvents is obviously of advantage, if the CuPc is intended for pigment use in coatings. However, for applications requiring solubility, substantial effort has been devoted to the synthesis of substituted phthalocyanines to grant solubility,¹ in aqueous ambience in particular, e.g. the widely used examples phthalocyanine-3,4',4'',4'''-tetrasulfonic acid or Alcian Blue ("Ingrain blue 1"). Obviously, the preparative effort involved will go to the price of elevated costs. Readily soluble phthalocyanines (also including other ions than Cu(II)) hold the potential to impact mere coating applications just as much as more filigrane uses in homogeneous (photo-) catalysis,² solar cells,³ LEDs (both as hole injection aids⁴ and emitters⁵), or even photodynamic therapies (PDT).^{6,7}

As an illustrative example for phthalocyanine solubilisation, we




Figure 1. Phthalocyanines. In the present investigation M = Cu, R = H.

here report on a straight forward method to solubilize CuPc into water in concentrations, this far only known for organic solvents, by the aid of the nano-clay shuttles. The commercial clay used most successfully for this purpose, "LAPONITE RD"[†], $\text{Na}_{0.7}(\text{H}_2\text{O})_n\{(\text{Li}_{0.3}\text{Mg}_{5.5})[\text{Si}_8\text{O}_{20}(\text{OH})_4]\}$, can be viewed as a nano-scaled hectorite derivative⁸ or a charged offspring of talcum, primarily consisting of disk-shaped platelets of 25 nm in diameter and 1 nm height, which completely exfoliate to form clear dispersions in water (see also Figure 2 and the corresponding caption).⁹

The resulting negatively charged platelets have been shown to adsorb numerous cationic dye species, among them Methylene

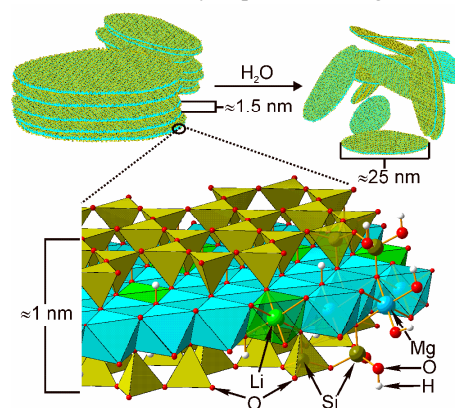


Figure 2. Nano-Clay ("Laponite") used in this investigation. Like the parent mineral talcum, structurally each individual disk or platelet consists of a tetrahedral-octahedral-tetrahedral arrangement ("TOT"). Chemically, ionisable Si-O-H and Mg-O-H groups protrude from the rims of the platelets and contribute to the laponite's unusual rheological properties; if Li^+ (green) is introduced to replace Mg^{2+} cations (blue) within the octahedra, additional cations (e.g. Na^+ , not shown, but see Figure 4) are accommodated between the aligned disks as indicated in the top left of the sketch. As opposed to talcum, these very charges now enable complete exfoliation on exposure to aqueous media, leaving individual platelets with negatively charged faces behind.

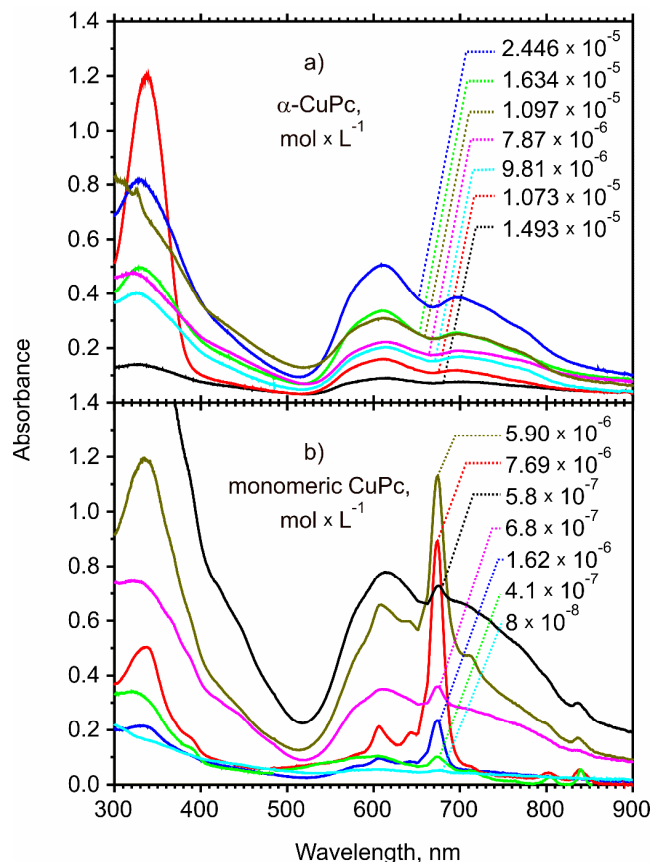


Figure 3. Absorption spectra of laponite hybrids with α -CuPc (a) in saturated $\text{CH}_3\text{CN}/\text{H}_2\text{O}$ solutions (solutions (1), a) and of monomeric CuPc species in water (solutions (2), b) at a concentration of 1 wt % of laponite. The data reproduced in the plots were recalculated from the extinction coefficient of monomeric CuPc from the sample containing $7.68 \times 10^{-6} \text{ mol L}^{-1}$ (b, red curve). Original concentrations, extinction coefficients and corresponding amounts of CuPc-molecules per disk (“mpd”, see ESI) are also listed in Table S1.

Blue¹⁰ or luminescent Rhodamine dyes,¹¹ which can be attracted via polar and coulomb forces. However, very recently, the neutral and nonpolar dyes Indigo¹² and Nile Red,¹³ both completely insoluble in water, have also been found to interact strong enough with nano-clays to be solubilised, the luminescent Nile Red surprisingly even retaining its emissive character in water. While the capability of laponite to mobilise these dyes may be ascribed to polar interactions and hydrogen bonding, the precise nature of the bonding in laponite-CuPc hybrids remains yet to be clarified. Despite considerable analytical adversities encountered in their analysis, we find their solution behavior so unique that it seems worth to be reported on: not only can the CuPc be solubilised, but the presence of monomeric species in aqueous solutions and the corresponding impact for other Pc materials, such as singlet oxygen generators, struck us as especially remarkable.

Among the approaches to establish an efficient adsorption pathway for CuPc on the laponite surface, refluxing the laponite and CuPc materials for 48 hrs in water/solvent mixtures (acetonitrile, methanol) in a 1:1 ratio at 1 wt % laponite-dispersion yielded the best samples with respect to homogeneity and (re-)dispersability; no noteworthy difference was found between the use of $\text{CH}_3\text{CN}/\text{H}_2\text{O}$ and $\text{CH}_3\text{OH}/\text{H}_2\text{O}$ as dispersants. The Pc adsorption could further be enhanced by mortaring the materials very thoroughly prior to loading. Other pathways (reactions via

the gas phase, i. e. sublimation of the Pc, in situ formation of the CuPc from Cu^{2+} /phthalocyanine mixtures in various solvents) proved to be less suited due to non-re-dispersability of the powders. The preparation in water proved to be possible also, but necessitated several steps of filtration and centrifugation, respectively, in order to obtain transparent solutions and was only used in efforts to obtain extinction coefficients (see below). After filtration of the $\text{CH}_3\text{CN}/\text{H}_2\text{O}$ dispersion to separate non-dispersible or insoluble residues, absorption spectra of the mother liquors, referred to as solutions (1), were recorded (Figure 3a). The spectra were taken from dispersions at a constant 1 wt % with respect to laponite, which, using data of the supplier ($\rho=2.53 \text{ g/cm}^3$, disk diameter of 25 nm)¹⁴ and a value of 1.5 nm for the disk thickness accounting for the inclusion of interlayer water¹³, can be recalculated to correspond to 5.2×10^{18} disks L^{-1} .

The volume of the first filtrates (solutions (1)), containing only α -CuPc, was subsequently reduced with a rotary evaporator to a thick gel and dried in a vacuum drying chamber for 24 h at 60 °C. The resulting, blue colored powders, showed diffraction peaks of the laponite only and no signs of CuPc crystallinity in XRD (see Electronic Supplementary Information (ESI), Figure S2; Figure S4 additionally shows the FTIR spectra of a hybrid in comparison to pure α -CuPc), although a trend towards an increased order of the platelets with increasing CuPc contents may be depicted, as indicated by the [001] and [003] reflexes at $2\theta = 6.6^\circ$ and 28.1° . The α -CuPc aggregates could be re-dispersed completely in pure H_2O to obtain 1 wt % - laponite dispersions (solutions (2)).

Absorption spectra of the first filtrates (solutions (1), Figure 3a) closely resemble the spectra obtained from α -CuPc,^{15,16} and unambiguously suggest the exclusive presence of dimers or higher associates, of the CuPc in the aqueous solution as well, as evident from the split Q-bands at 616 and 697 nm,^{15,17-19} also known as Davydov splitting,^{15,20} i.e. the broadening due to a variety of interactions with neighboring molecules. Accounts on the electronic structure of α -CuPc have been elaborated using absorption spectroscopy, electron microscopies, AFM, XRD^{21,22} and UPS,¹⁶ a recent review exhaustively discusses the nature of the electronic transitions in monomeric CuPc as well.²³

The true concentrations of α -CuPc in the first filtrate (solution (1), $\text{CH}_3\text{CN}/\text{H}_2\text{O}$, Figure 3a and Figure 4), could not be analyzed with sufficient precision: carbon analyses of the samples carried out after evaporation of the solvent, revealed amounts well above the expected values for pure CuPc-laponites, as all samples still contained co-adsorbed CH_3CN in appreciable and, unfortunately, non-reproducible amounts (up to a fivefold excess in carbon over the theory for the pure CuPc-laponites). Despite appreciable effort (e.g. vacuum drying at various elevated temperatures of up to 250 °C, freeze drying), we were not able to completely remove the organic solvent without carbonisation. Carbon determinations are feasible for the laponite systems in principle, as we found from vacuum-sublimed hybrids, where we found a very good fit between the experimental data and theoretical values, however, as mentioned, such samples could not be re-dispersed. Therefore all elemental analyses of samples prepared from solutions containing organic matter, including copper and nitrogen determinations contained too large an error to be useful, a situation, which is yet more complicated by the relatively small theoretical overall carbon content (e.g. 0.5 wt % at 10 molecules per disk, “mpd” see also eq. S1, and lower, taking the true loading efficiencies into account) and a continuous release of water extending into a range of 700 °C (see DTG, Figure S3). An estimate of the extinction coefficient $\epsilon_{\alpha\text{-CuPc}}$ (approximately $2.1 \times 10^4 \text{ L x mol}^{-1} \times \text{cm}^{-1}$) was thus possible only indirectly via solutions containing monomeric CuPc, as described below.

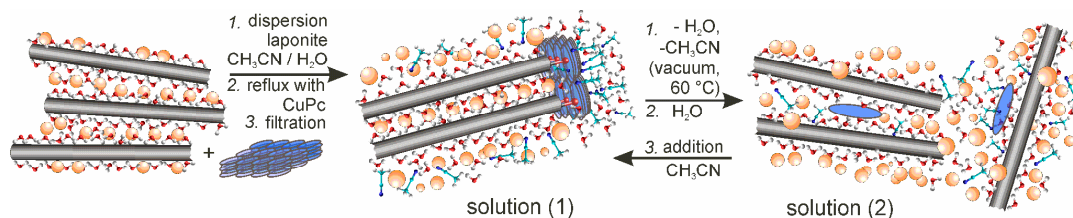


Figure 4. Formation of laponite mobilised CuPc species in aqueous media. Micelle-like colloids of α -CuPc are formed in $\text{H}_2\text{O}/\text{CH}_3\text{CN}$ (middle), adhering and solubilised by the laponite. After careful removal of CH_3CN and H_2O , at low CuPc concentrations, monomeric CuPc on laponite can be obtained after re-dispersion in water (right). Higher loads and readdition of CH_3CN reverses the situation again. Grey bars represent a sectional view of a laponite disks from the side, red and white balls and blue and white balls hinting H_2O and CH_3CN , respectively, while orange balls symbolise Na^+ in the vicinity. Blue disks represent CuPc.

Absorption spectra of the water - re-dispersed samples (solution (2), reproduced in Figure 3a, now clearly demonstrate the presence of monomeric species as evidenced by the emergence of the Q-band at 673 nm, which is very close to the 671 and 678 nm observed for CuPc in solution (THF and 1-chloronaphthalene, respectively^{24, 25}), while the absorption in the vapor phase is reported to be blue-shifted to 656 nm.^{26,27} For loadings below a threshold of approximately $7.69 \times 10^{-6} \text{ mol} \times \text{L}^{-1}$ (see also below), corresponding to 0.89 mpd, the monomer is by far the dominating guest species, above that level, dimers or higher associates are formed. For samples of lower CuPc contents, the absorption spectra suggest monomeric CuPc to be the dominating species by far in the re-dispersed aqueous solution (see the blue and red curves in Figure 3b for example). At this stage, we also need to mention that in water, monomeric CuPc is slightly prone to protonation via Brønsted acid sites characteristic of the laponite clay, if exposed to temperatures higher than approximately 60°C . Minute absorptions at 810 nm and above are indicative of this protonation.

As pointed out above, we encountered substantial difficulties in the determination of the laponite loading with CuPc. We have therefore chosen to estimate the apparent concentrations of the monomeric CuPc on laponite from the absorption spectra. Due to its very low solubility, data on the absorption coefficient of CuPc are sparse,¹⁹ although data have been obtained from solutions of 1-chloronaphthalene^{25,28,29} and THF,³⁰ in the gas phase,²⁶ in thin films,³¹ glasses and polymers. Obviously, the low solubility of CuPc causes large uncertainties in the reported extinction coefficients. However, a recent diligent treatise²⁴ suggests an extinction coefficient ϵ_{673} for protonated CuPc of $(1.4 \pm 0.7) \times 10^5 \text{ L} \times \text{mol}^{-1} \times \text{cm}^{-1}$ in trifluoroacetic acid and $(1.6 \pm 0.16) \times 10^5 \text{ L} \times \text{mol}^{-1} \times \text{cm}^{-1}$ in concentrated sulfuric acid. Thus, we prepared a calibration curve of pure CuPc in H_2SO_4 (see Figure S1), from which an extinction coefficient of $157762 \text{ L} \times \text{mol}^{-1} \times \text{cm}^{-1}$ in close proximity to the above value could be extracted, which served as the basis of our subsequent concentration estimates in H_2SO_4 . We preferred the use of H_2SO_4 due to the additional presence of the clay, for which weaker acids required a prolonged dissolution time.

Samples used to obtain the extinction coefficient of monomeric CuPc were prepared in pure water, in order to avoid obscuring side reactions of organic residues on the laponite, additionally, to avoid protonation, during all drying, re-dispersion and filtration steps, temperatures below 60°C were maintained. The absorbances of clear monomeric CuPc solutions, free of α -CuPc, were measured, evaporated to almost dryness, and redissolved in H_2SO_4 . Using the calibration curve, the CuPc content could be determined. As this content corresponds to the amount of CuPc in the preceding solution, an extinction coefficient $\epsilon_{\text{mono},673}$ of $102777 \text{ L} \times \text{mol}^{-1} \times \text{cm}^{-1}$ ($\pm 23\%$) for monomeric CuPc in aqueous solution could be calculated (for further details to the procedures and experimental errors refer to the ESI).

This derived extinction coefficient $\epsilon_{\text{mono},673}$ in turn enabled us to re-estimate the true concentrations of the CuPc monomers at various loadings, and in a reverse manner, to recalculate the concentration and extinction coefficient of the (aggregated) α -CuPc solutions of the first $\text{CH}_3\text{CN}/\text{H}_2\text{O}$ filtrate (solution (1)). The detailed procedure for these estimates is reported in the supplement to this paper. An extinction coefficient for α -CuPc in aqueous solution has not previously been reported for its obvious insolubility. Inspecting Figure 3b of samples that were prepared and recorded in $\text{CH}_3\text{CN}/\text{H}_2\text{O}$ after filtration (solutions (1)), the spectral position of the Q-band related absorptions at 616 and 679 nm is not affected by the nano-clay loading level. Also evident is the absence of any monomeric species, which would give rise to a strong absorption at 673 nm. The absorption spectra furthermore reveal an increasing shoulder of the Soret-band just above 400 nm, which is due to the increasing formation of scattering agglomerates; only for loadings below approximately $8 \times 10^{-6} \text{ mol} \times \text{L}^{-1}$, agglomeration appears to be negligible. While we realise that the integrated absorption coefficient is a better value for the broad band absorptions of α -CuPc, we here use the extinction coefficient $\epsilon_{\alpha,616}$ of $2.1 \times 10^4 \text{ L} \times \text{mol}^{-1} \times \text{cm}^{-1}$ for the purpose of comparison with monomeric CuPc.

The content of eventually found in the hybrids was in our series restricted to approximately $2.5 \times 10^{-5} \text{ mol} \times \text{L}^{-1}$, corresponding to roughly 2.8 α -CuPc molecules per clay platelet (mpd). As opposed to that, the highest amount of monomeric CuPc (Figure 3b), after careful removal of the CH_3CN under the moderate conditions described above (vacuum drying chamber for 24 h at 60°C) and re-dispersion in water, was found as $7.68 \times 10^{-6} \text{ mol} \times \text{L}^{-1}$ only, i.e., 0.89 mpd of monomeric CuPc - now less than one molecule per platelet. Significantly, the loading efficiency with regard to the actual amounts of CuPc weighed out amounts to some 5 % only, and drops dramatically to less than 1 %, if concentrations in excess of $6 \times 10^{-4} \text{ mol} \times \text{L}^{-1}$ CuPc are applied (see Figure S5 and Table S1).

The colloidal α -CuPc particles adhering to laponites are preferentially located at the rims rather than at the faces of the clay (see Fig. 4), since the intergallery distance between the platelets does not change, as evident from the unaltered basal reflex [001] ($2\theta = 6.6^\circ$) in the XRDs of the solids (Figure S2). The formation of small colloidal particles is obviously promoted by the presence of stabilizing CH_3CN . Consequently, on addition of CH_3CN to aqueous dispersions containing only monomeric CuPc-laponite, the monomer band vanishes again to the cost of the two broad α -CuPc bands (Figure S6).

Conclusions

While the mobilization of unsubstituted CuPc into aqueous media, additionally accompanied by the formation of monomers, is a surprising observation in its own right, efforts to increase the

pigment's solubility further are desirable for e.g. coating applications. Beyond the use as colorants, monomeric phthalocyanines are currently being investigated with regard to their (photo-) catalytic activity. As preliminary results indicate, Si(OH)₂Pc and Al(OH)Pc are promising candidates for singlet oxygen generation in aqueous solution. Furthermore, established nano-clay functionalisation schemes via siloxane reagents readily enable the coupling to relevant bioassays, and pathways to targeted photodynamic therapy and anti-microbial uses of the Pc-laponite hybrids seem feasible.

Notes and references


^a Muenster University of Applied Sciences, Institute for Optical Technologies, Münster/Steinfurt, Stegerwald-Str. 39, 48565 Steinfurt, Germany. E-mail: uk@fh-muenster.de

^b On Leave from Volga State University of Technology, Department of Physics, Lenin-pl.3, Yoshkar-Ola 424000, Russia.

† LAPONITE, is a former trademark of Rockwood Additives Limited, now distributed by Altana/Byck. The term "laponite" is used synonymously in this text for Laponite RD.

Electronic Supplementary Information (ESI) available: Experimental details and methods; Figures S1-S6; Table S1. See DOI: 10.1039/c000000x/

- 1 F. Dumoulin, M. Durmuş, V. Ahsen and T. Nyokong, *Coord. Chem. Rev.*, 2010, **254**, 2792.
- 2 B. Sorokin, *Chem. Rev.*, 2013, **113**, 8152.
- 3 M. Ince, A. Medina, J.-H. Yum, A. Yella, C. G. Claessens, M. V. Martínez-Díaz, M. Grätzel, M. K. Nazeeruddin and T. Torres, *Chemistry – A European Journal*, 2014, **20**, 2016.
- 4 D. Hohnholz, S. Steinbrecher and M. Hanack, *J. Mol. Struct.*, 2000, **521**, 231.
- 5 Barker, X. Zeng, S. Bettington, A. S. Batsanov, M. R. Bryce and A. Beeby, *Chemistry – A European Journal*, 2007, **13**, 6710.
- 6 J. F. Lovell, T. W. B. Liu, J. Chen and G. Zheng, *Chem. Rev.*, 2010, **110**, 2839.
- 7 T. Nyokong, *Pure Appl. Chem.*, 2011, **833**, 1763.
- 8 J. Breu, W. Seidl and A. Stoll, *Z. Anorg. Allg. Chem.*, 2003, **629**, 503.
- 9 W. Thompson and J. T. Butterworth, *J. Colloid Interface Sci.*, 1992, **151**, 236.
- 10 J. C. a. R. A. Schoonheydt, *Clays Clay Miner.*, 1988, **26**, 214.
- 11 F. Lopez Arbeloa and V. Martínez Martínez, *Chem. Mater.*, 2006, **18**, 1407.
- 12 M. M. Lezhnina, T. Grewe, H. Stoehr and U. Kynast, *Angew. Chem., Int. Ed.*, 2012, **51**, 10652.
- 13 T. Felbeck, T. Behnke, K. Hoffmann, M. Grabolle, M. M. Lezhnina, U. H. Kynast and U. Resch-Genger, *Langmuir*, 2013, **29**, 11489.
- 14 www.byk.com/fileadmin/byk/additives/product_groups/rheology/former_rockwood_additives/technical_brochures/BYK_B-RI21_LAPONITE_EN.pdf. (19.03.2014).
- 15 Lucia and F. D. Verderame, *The Journal of Chemical Physics*, 1968, **48**, 2674.
- 16 L. Lozzi, S. Santucci, S. La Rosa, B. Delley and S. Picozzi, *The Journal of Chemical Physics*, 2004, **121**, 1883.
- 17 V. Plyashkevich, T. Basova, P. Semyannikov and A. Hassan, *Thermochim. Acta*, 2010, **501**, 108.
- 18 M. J. Stillman and A. J. Thomson, *Journal of the Chemical Society, Faraday Transactions 2: Molecular and Chemical Physics*, 1974, **70**, 805.
- 19 Y. A. Mikheev, L. N. Guseva and Y. A. Ershov, *Russian Journal of Physical Chemistry A*, 2007, **81**, 617.
- 20 A. S. Davidov, *J. Exp. Theor. Phys.*, 1948, **18**, 210.
- 21 S. Karan and B. Mallik, *The Journal of Physical Chemistry C*, 2007, **111**, 7352.
- 22 S. Karan, D. Basak and B. Mallik, *Chem. Phys. Lett.*, 2007, **434**, 265.
- 23 K. Ishii, *Coord. Chem. Rev.*, 2012, **256**, 1556.
- 24 Ghani, J. Kristen and H. Riegler, *J. Chem. Eng. Data*, 2012, **57**, 439.
- 25 H. F. H. Moser and A. L. A. L. Thomas, *Phthalocyanine compounds / [by] Frank H. Moser and Arthur L. Thomas*, Reinhold ; London : Chapman & Hall, 1963.
- 26 D. Eastwood, L. Edwards, M. Gouterman and J. Steinfeld, *J. Mol. Spectrosc.*, 1966, **20**, 381.
- 27 L. Edwards and M. Gouterman, *J. Mol. Spectrosc.*, 1970, **33**, 292.
- 28 J. S. Anderson, E. F. Bradbrook, A. H. Cook and R. P. Linstead, *Journal of the Chemical Society (Resumed)*, 1938, 1151.
- 29 E. Ficken and R. P. Linstead, *Journal of the Chemical Society (Resumed)*, 1952, 4846.
- 30 J. Gardener, J. H. G. Owen, K. Miki and S. Heutz, *Surf. Sci.*, 2008, **602**, 843.
- 31 M. Farag, *Optics & Laser Technology*, 2007, **39**, 728.

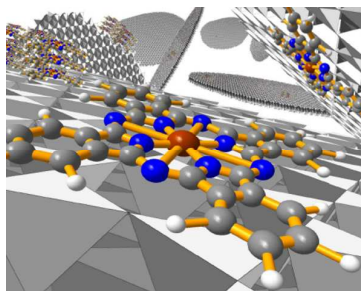

Natively insoluble, unsubstituted Cu(II) phthalocyanines can be solubilised in water by the aid of nano-clays as colloidal α -CuPc and monomeric CuPc.