

RSC Advances




This is an *Accepted Manuscript*, which has been through the Royal Society of Chemistry peer review process and has been accepted for publication.

Accepted Manuscripts are published online shortly after acceptance, before technical editing, formatting and proof reading. Using this free service, authors can make their results available to the community, in citable form, before we publish the edited article. This *Accepted Manuscript* will be replaced by the edited, formatted and paginated article as soon as this is available.

You can find more information about *Accepted Manuscripts* in the [Information for Authors](#).

Please note that technical editing may introduce minor changes to the text and/or graphics, which may alter content. The journal's standard [Terms & Conditions](#) and the [Ethical guidelines](#) still apply. In no event shall the Royal Society of Chemistry be held responsible for any errors or omissions in this *Accepted Manuscript* or any consequences arising from the use of any information it contains.

TOC figure:

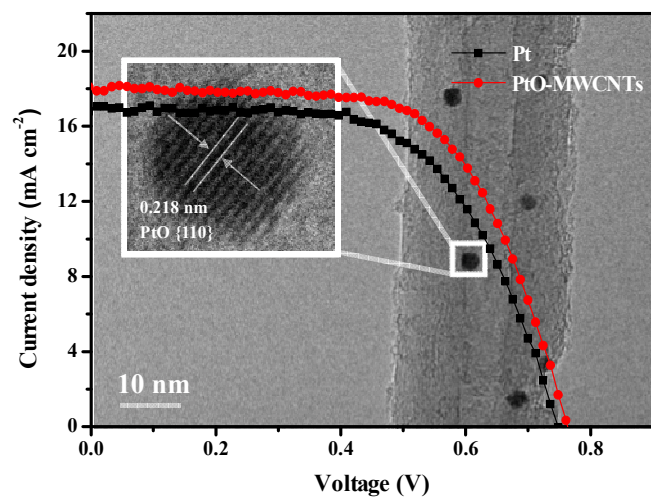

PtO-MWCNTs nanocomposites were prepared by a trithiol-terminated poly(methacrylic acid) (PMAA-PTTM) polymer ligands assisted strategy and were applied as counter electrode (CE) in dye-sensitized solar cells (DSCs) for the first time. PtO-MWCNTs nanocomposites CE based DSCs showed an energy conversion efficiency (η_{DSC}) of 8.67%, higher than that of Pt CE (7.69%), indicating that the PtO-MWCNTs nanocomposite was a promising electrocatalyst for DSCs.

Cite this: DOI: 10.1039/c0xx00000x

www.rsc.org/xxxxxx

ARTICLE TYPE

Novel PtO decorated MWCNTs as Highly Efficient Counter Electrode for Dye-Sensitized Solar Cells †

Xiao Chen^{a†}, Jian Wei Guo^{a†}, Yu Hou^a, Yu Hang Li^a, Shuang Yang^a, Li Rong Zheng^c, Bo Zhang^a, Xiao Hua Yang^{*a} and Hua Gui Yang^{a,b}

Received (in XXX, XXX) Xth XXXXXXXXXX 20XX, Accepted Xth XXXXXXXXXX 20XX

DOI: 10.1039/b000000x

PtO decorated multi-walled carbon nanotubes (MWCNTs) were prepared by a polymer ligands assisted strategy and applied as the counter electrode (CE) in dye-sensitized solar cells (DSCs) for the first time. Compared with the energy conversion efficiency (E_{ff}) of Pt CE based DSCs, the DSCs with PtO-MWCNTs CE showed an overall E_{ff} of 8.67%, giving an improvement of 12.7%. Better electrocatalytic activity towards I_3^-/I^- redox pairs than Pt CE indicated that the PtO-MWCNTs was a promising electrocatalyst for DSCs.

The dye-sensitized solar cells (DSCs) were firstly reported by O'Regan and Grätzel in 1991 and have become the focus of attention for its low consumption, easy fabrication and powerful harvesting efficiency.¹ As one of the most important components in the DSCs, counter electrode (CE) collects the electron from the external circuit, and catalyzes the reduction of triiodide ions.² It is well-known that platinum is a superior CE material due to its excellent catalytic activity for I_3^- reduction and high electrical conductivity. However, the high price and low reserve of Pt severely restrict the large-scale application of the DSCs.³ Therefore, many efforts have been devoted to exploring low-cost and high performance materials as replacements for Pt, such as different forms of carbon materials⁴, conducting polymers⁵, metal sulphides⁶, metal carbides⁷, metal nitrides⁸, metal phosphides⁹ and metal oxides¹⁰. Among these developed substitutes, Pt decorated multi-walled carbon nanotubes (MWCNTs) are well researched and demonstrate better electrocatalytic activity for I_3^-/I^- redox reaction than that of Pt.¹¹ Recently, the PtO was reported to be an excellent catalyst for photocatalytic hydrogen evolution.¹² To the best of our knowledge, there is no report about the PtO decorated MWCNTs as CE in DSCs.

Here, we utilize a trithiol-terminated poly(methacrylic acid) to synthesize PtO-MWCNTs nanocomposite, and apply it as CE materials in DSCs. The chemical state of Pt species on the surface of MWCNTs was confirmed to be Pt²⁺ by extended X-ray absorption fine structure (EXAFS) and X-ray photoelectron spectroscopy (XPS) measurements. Moreover, the PtO-MWCNTs CE based solar cells yield an energy conversion efficiency of 8.67%, giving an improvement of 12.7% than that of Pt CE. Better electrocatalytic activity of PtO-MWCNTs indicates that the PtO-MWCNTs

nanocomposite is a promising catalyst in DSCs.

The overall morphology of PtO-MWCNTs nanocomposites was analyzed using the transmission electron microscopy (TEM). As shown in Fig. 1A, the PtO nanoparticles were dispersed homogeneously on the surface of MWCNTs with ultra-small particle size. The size distribution image in Fig. 1D confirms that PtO nanoparticles with mainly a size range of 0.8-1.0 nm are dispersedly loaded on the surface of the MWCNTs. The elemental analysis of the PtO-MWCNTs nanocomposites, employing energy dispersive spectroscopy (EDS) (Fig. 1C), reveals that elements of Pt, O and C coexisted in the sample, which demonstrates that the composite prepared by our strategy is composed of oxidized Pt and MWCNTs. Fig. 1B shows the enlarged HR-TEM image of the PtO loaded on the MWCNTs surface. The lattice distance in the enlarged view was measured to be 0.218 nm, corresponding to the {110} surface of PtO. The scanning electron microscopy (SEM) images of prepared PtO-MWCNTs CE and Pt CE on FTO are shown in Fig. S3.

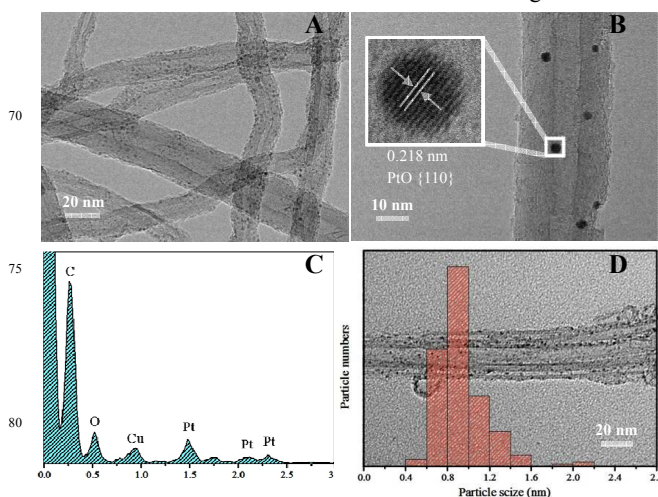


Fig. 1 (A) HR-TEM image of PtO-MWCNTs nanocomposites, (B) the enlarged view of the HR-TEM image of the PtO loaded on the MWCNTs surface, (C) EDS spectrum of the synthesized PtO-MWCNTs nanocomposites, (D) size distribution of PtO nanoparticles loaded on the MWCNTs (based on a count of 197 nanocrystallites).

In order to further examine the chemical state of Pt species

on the surface of MWCNTs, the PtO-MWCNTs nanocomposites were then studied by EXAFS and XPS measurements. Fig. 2A shows that only one apparent peak at 1.0-2.0 Å is displayed in Fourier-transformed spectrum of EXAFS for the PtO-MWCNTs. To identify the nature of the backscatter, EXAFS spectra of Pt and PtO₂ samples were measured as reference. The peak at 1.0-2.0 Å in PtO₂ is due to scattering from the nearest oxygen atoms, whereas the peak at 2.0-3.3 Å in Pt foil is related to scattering from the neighbouring Pt. Thus, the only peak at 1.0-2.0 Å in PtO-MWCNTs is believed to be the contribution from Pt-O binding. Fig. 2B shows the normalized X-ray absorption near-edge structure spectrum of PtO-MWCNTs, and the reference spectra of Pt foil and PtO₂. The intensities in the spectra reflect the oxidation state of Pt in different samples. Thus, the intensity of the PtO-MWCNTs, which is between that of Pt and PtO₂, further suggests that the Pt in the materials exists as oxidized Pt.¹³ The X-ray photoelectron spectroscopy (XPS; Fig. S1) was further studied to examine the chemical state of Pt species in obtained materials. The main peaks in PtO-MWCNTs centre at 72.8 and 76.0 eV, which can be assigned to Pt²⁺ bonded to oxygen.¹⁴

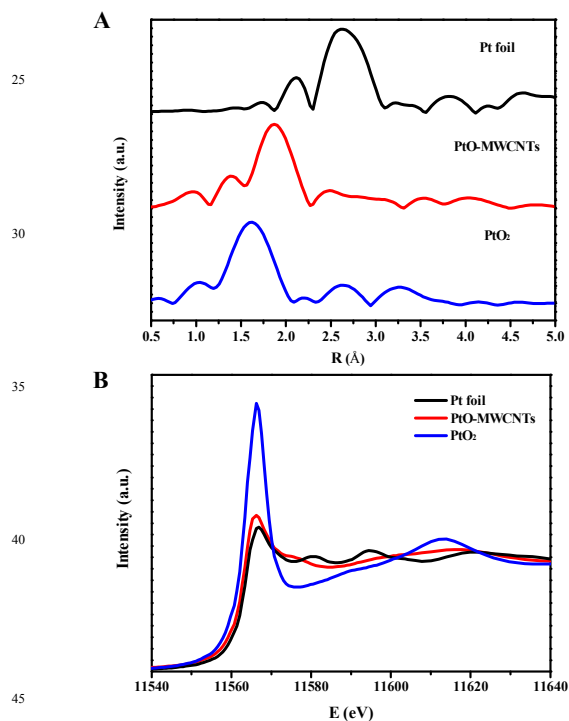


Fig. 2 (A) The k^3 -weighted Fourier transform spectra from EXAFS, $\times 1/3$ represents signal magnification, (B) The normalized X-ray absorption near-edge structure spectra at the Pt L_3 -edge of the Pt foil, PtO₂ and initial PtO-MWCNTs.

Fig. 3 shows the photocurrent-voltage (J-V) curves of the DSCs with different CEs measured under illumination at 100 mW cm⁻² and the detailed photovoltaic parameters are summarized in Table 1. As shown in Fig. 3, higher J_{sc} (17.93 mA cm⁻²) of PtO-MWCNTs CE based DSCs indicates that PtO-MWCNTs CE demonstrates better electrocatalytic activity for I₃⁻ reduction than that of Pt CE.¹⁵ Moreover, the V_{oc} (763.6 mV) of PtO-MWCNTs CE based DSC is higher than that of Pt

CE (746.2 mV), which means there are more interfacial active sites in PtO-MWCNTs CE.¹⁶ Compared with the E_{ff} (7.69%) of Pt CE based solar cells, the DSCs with PtO-MWCNTs CE show an overall E_{ff} of 8.67%, giving an improvement of 12.7%.

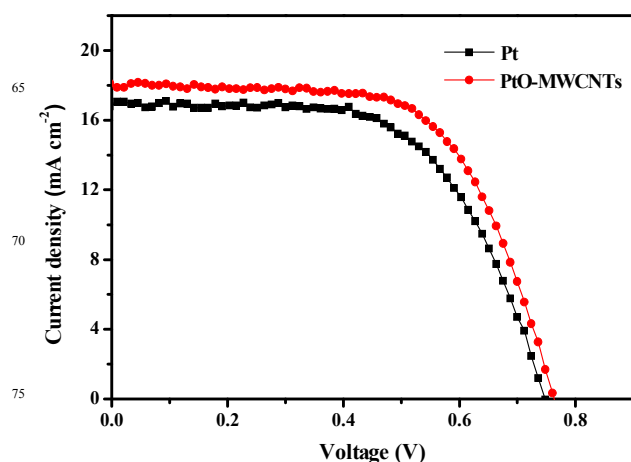


Fig. 3 J-V characteristics of the DSCs with Pt CE and PtO-MWCNTs CE measured at 100 mW cm⁻².

Table 1 Photovoltaic parameters of DSCs with different counter electrodes, measured at 100 mW cm⁻² illumination.

CE Sample	J_{sc} mA cm ⁻²	V_{oc} mV	FF %	η %	R_s Ω	R_{ct} Ω	C μF
Pt	16.95	746.2	60.8	7.69	11.42	2.66	2.42
PtO-MWCNTs	17.93	763.6	63.3	8.67	9.41	0.78	109.6

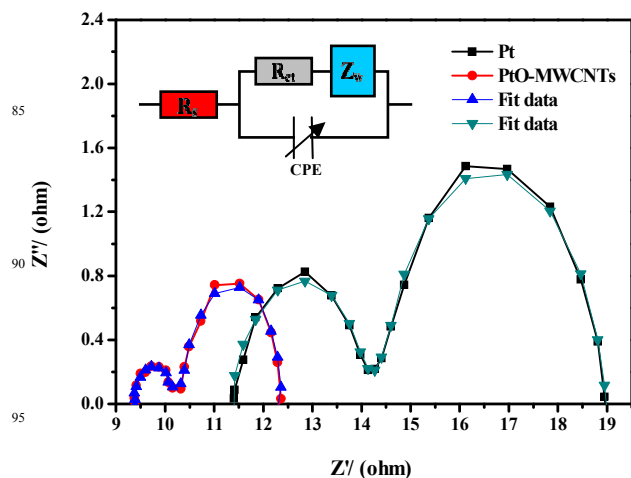


Fig. 4 EIS curves of the DSCs with Pt CE and PtO-MWCNTs CE, measured at 100 mW cm⁻² light intensity.

In order to further investigate the different catalytic activity for triiodide reduction between the PtO-MWCNTs CEs and Pt CEs, the electrochemical impedance spectroscopy (EIS) measurement was employed and the Nyquist plots of the symmetrical cells were shown in Fig. 4. The values of the series resistance (R_s), the charge-transfer resistance (R_{ct}) and constant phase element (CPE) are obtained by fitting the

spectra with an EIS spectrum analyzer, and summarized in Table 1. The equivalent circuit used to fit the experimental EIS data is shown in the inset of Fig. 4. The R_s is mainly composed of the bulk resistance of CE materials, resistance of FTO glass substrate and contact resistance, *etc.* The R_s of PtO-MWCNTs CE is 9.41 Ω , while this value of Pt CE is 11.42 Ω . A relatively faster electron transfer kinetics and better electrical conductivity are responsible for the decrease in R_s of the PtO-MWCNTs CE.^{10(a)} The R_{ct} is a measure of the ease of electron exchange between the counter electrode and the electrolyte and thus varies inversely with the triiodide reduction activity of the CEs. The lower R_{ct} of PtO-MWCNTs leads to a better catalytic activity, explaining the better performance than that of Pt CE based cells.¹⁷ Moreover, a much larger capacitance (C) of PtO-MWCNTs CE indicates a higher surface area than that of Pt CE, which is responsible for higher E_{fr} and in agreement with previous report.¹⁶ In conclusion, low R_s , low R_{ct} and high C result in the high power-conversion efficiency of DSCs with PtO-MWCNTs CE and agree well with the photovoltaic experiments.

To further examine the interfacial charge-transfer properties of the triiodide/iodide couple in the electrode surface, Tafel polarization measurement was carried out with dummy cells fabricated with two identical electrodes (CE//electrolyte//CE). The Tafel curves in Fig. S2 show that the current density (J) is a logarithmic function of the voltage (U). In Tafel zone (at middle overpotential), the anodic and cathodic branches of the PtO-MWCNTs CE show a larger slope than the conventional Pt CE, indicating the presence of a large exchange current density on the electrode surfaces, which means that PtO-MWCNTs CE has a higher catalytic activity than the Pt CE. Moreover, the current densities of PtO-MWCNTs CE obtained in all three zones are higher, which is consistent with the results of photovoltaic and EIS measurements.¹⁷


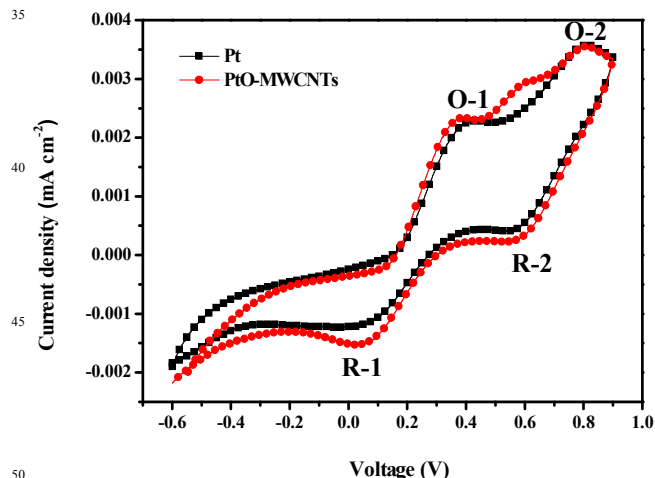


Fig. 5 Cyclic voltammograms of iodide species for PtO-MWCNTs and Pt electrodes.

The cyclic voltammetry (CV) measurement was further carried out in a three-electrode system to evaluate the electrocatalytic properties of the PtO-MWCNTs CE (Fig. 5). Typical curves with two pairs of oxidation and reduction peaks (O-1/R-1, O-2/R-2) are obtained for PtO-MWCNTs CE. The left

peak is corresponding to the redox reaction of eqn (1), while the right one is corresponding to the reaction of eqn (2).



As shown in Fig. 5, the CEs based on the PtO-MWCNTs and Pt show very similar shapes in terms of redox peak positions. Comparing the current densities of two CEs, PtO-MWCNTs nanocomposites exhibit higher values than that of Pt, suggesting a higher intrinsic catalytic activity for redox reaction of iodide ions.¹⁸ Moreover, the peak-to-peak splitting (E_{pp}) of PtO-MWCNTs CE is slightly smaller than that of bare Pt CE, further conforming that the electrocatalytic activity and reversibility of I_3^-/I^- redox reaction on PtO-MWCNTs CE are better.⁶

In summary, we demonstrate a PMAA-PTTM polymer ligands assisted method to synthesize PtO-MWCNTs nanocomposites. The chemical state of Pt species in the PtO-MWCNTs nanocomposite is confirmed to be Pt^{2+} by EXAFS and XPS measurements. Furthermore, PtO-MWCNTs CE exhibits better photovoltaic performance than the conventional Pt electrode, which indicates PtO-MWCNTs is a high-efficient CE material for DSCs.

This work was financially supported by National Natural Science Foundation of China (21373083, 21203061), Fundamental Research Funds for the Central Universities (WD1313009, WD1214036, WM1314018), Shanghai Municipal Natural Science Foundation (14ZR1410200) and China Postdoctoral Science Foundation (2013T60425).

Notes and references

- ^a Key Laboratory for Ultrafine Materials of Ministry of Education, School of Materials Science and Engineering, East China University of Science and Technology, 130 Meilong Road, Shanghai, 200237 (China). Fax: (+86)21-6425-2127; Tel: (+86)21-6425-2127; E-mail: yangxiaohuayou@163.com
- ^b Centre for Clean Environment and Energy, Gold Coast Campus, Griffith University, Queensland 4222 (Australia).
- ^c Beijing Synchrotron Radiation Facility, Institute of High Energy Physics, Chinese Academy of Sciences, Beijing 100049, (China).
- † These authors contributed equally to this work.

- (a) B. O'Regan and M. Grätzel, *Nature*, 1991, **353**, 737-740. (b) M. Grätzel, *Nature*, 2001, **414**, 338-344.
- (a) G. R. Li, F. Wang, Q. W. Jiang, X. P. Gao and P. W. Shen, *Angew. Chem. Int. Ed.*, 2010, **49**, 3653-3656. (b) H. Zhang, Y. Wang, D. Yang, Y. Li, H. Liu, P. Liu, B. J. Wood and H. Zhao, *Adv. Mater.*, 2012, **24**, 1598-1603.
- K. C. Huang, Y. C. Wang, R. X. Dong, W. C. Tsai, K. W. Tsai, C. C. Wang, Y. H. Chen, R. Vittal, J. J. Lin and K. C. Ho, *J. Mater. Chem.*, 2010, **20**, 4067-4073.
- (a) P. Joshi, Y. Xie, M. Ropp, D. Galipeau, S. Bailey and Q. Q. Qiao, *Energy Environ. Sci.*, 2009, **2**, 426-429. (b) L. Kavan, J. H. Yum and M. Grätzel, *ACS Nano*, 2011, **5**, 165-172.
- S. Ahmad, J. H. Yum, H. J. Butt, M. K. Nazeeruddin and M. Grätzel, *ChemPhysChem*, 2010, **11**, 2814-2819.
- (a) M. Wang, A. M. Anghel, B. T. Marsan, N. L. Cevy Ha, N. Pootrakulchote, S. M. Zakeeruddin and M. Grätzel, *J. Am. Chem. Soc.*, 2009, **131**, 15976-15977. (b) X. Chen, Y. Hou, B. Zhang, X. H. Yang and H. G. Yang, *Chem. Commun.*, 2013, **49**, 5793-5795.
- M. Wu, X. Lin, A. Hagfeldt and T. Ma, *Angew. Chem. Int. Ed.*, 2011, **50**, 3520-3524.

8. A. M. Hung, N. A. Konopliv and J. N. Cha, *Langmuir*, 2011, **27**, 12322-12328.
9. M. Wu, J. Bai, Y. Wang, A. Wang, X. Lin, L. Wang, Y. Shen, Z. Wang, A. Hagfeldt and T. Ma, *J. Mater. Chem.*, 2012, **22**, 11121-11127.
- 5 10. (a) Y. Hou, D. Wang, X. H. Yang, W. Q. Fang, B. Zhang, H. F. Wang, P. Hu, H. J. Zhao and H. G. Yang, *Nat. Commun.*, 2014, **4**, 1583. (b) L. Cheng, Y. Hou, B. Zhang, S. Yang, J. W. Guo, L. Wu and H. G. Yang, *Chem. Commun.*, 2013, **49**, 5945-5947.
- 10 11. (a) L. -Y. Chang, C. -P. Lee, K. -C. Huang, Y. -C. Wang, M. -H. Yeh, J. -J. Lin and K. -C. Ho, *J. Mater. Chem.*, 2012, **22**, 3185-3191. (b) G. Eda, H. Yamaguchi, D. Voiry, T. Fujita, M. Chen and M. Chhowalla, *Nano letters*, 2011, **11**, 5111-5116.
12. Y. H. Li, J. Xing, Z. J. Chen, Z. Li, F. Tian, L. R. Zheng, H. F. Wang, P. Hu, H. J. Zhao and H. G. Yang, *Nat. Commun.*, 2014, **4**, 2500.
13. R. K. Nomiya, M. J. Piotrowski and J. L. F. Da Silva, *Phys. Rev. B*, 2011, **84**, 100101.
14. J. Xing, H. B. Jiang, J. F. Chen, Y. H. Li, L. Wu, S. Yang, L. R. Zheng, H. F. Wang, P. Hu, H. J. Zhao and H. G. Yang, *J. Mater. Chem. A*, 2013, **48**, 15258-15264.
- 15 20 15. L. X. Yi, Y. Y. Liu, N. L. Yang, Z. Y. Tang, H. J. Zhao, G. H. Ma, Z. G. Su and D. Wang, *Energy Environ. Sci.*, 2013, **6**, 835-840.
16. X. Chen, Y. Hou, S. Yang, X. H. Yang and H. G. Yang *J. Mater. Chem. A*, DOI: 10.1039/C4TA03774J
- 25 17. J. W. Guo, B. Zhang, Y. Hou, S. Yang, X. H. Yang and H. G. Yang, *J. Mater. Chem. A*, 2013, **1**, 1982-1986.
18. (a) F. Pichot and B. A. Gregg, *J. Phys. Chem. B*, 1999, **104**, 6-10. (b) H. C. Sun, Y. H. Luo, Y. D. Zhang, D. M. Li, Z. X. Yu, K. X. Li and Q. B. Meng, *J. Phys. Chem. C*, 2010, **114**, 11673-11679. (c) H. H. Niu, S. X. Qin, X. L. Mao, S. W. Zhang, R. B. Wang, L. Wan, J. Z. Xu and S. D. Miao, *Electrochim. Acta*, 2014, **121**, 285-293.
- 30