

RSC Advances




This is an *Accepted Manuscript*, which has been through the Royal Society of Chemistry peer review process and has been accepted for publication.

Accepted Manuscripts are published online shortly after acceptance, before technical editing, formatting and proof reading. Using this free service, authors can make their results available to the community, in citable form, before we publish the edited article. This *Accepted Manuscript* will be replaced by the edited, formatted and paginated article as soon as this is available.

You can find more information about *Accepted Manuscripts* in the [Information for Authors](#).

Please note that technical editing may introduce minor changes to the text and/or graphics, which may alter content. The journal's standard [Terms & Conditions](#) and the [Ethical guidelines](#) still apply. In no event shall the Royal Society of Chemistry be held responsible for any errors or omissions in this *Accepted Manuscript* or any consequences arising from the use of any information it contains.

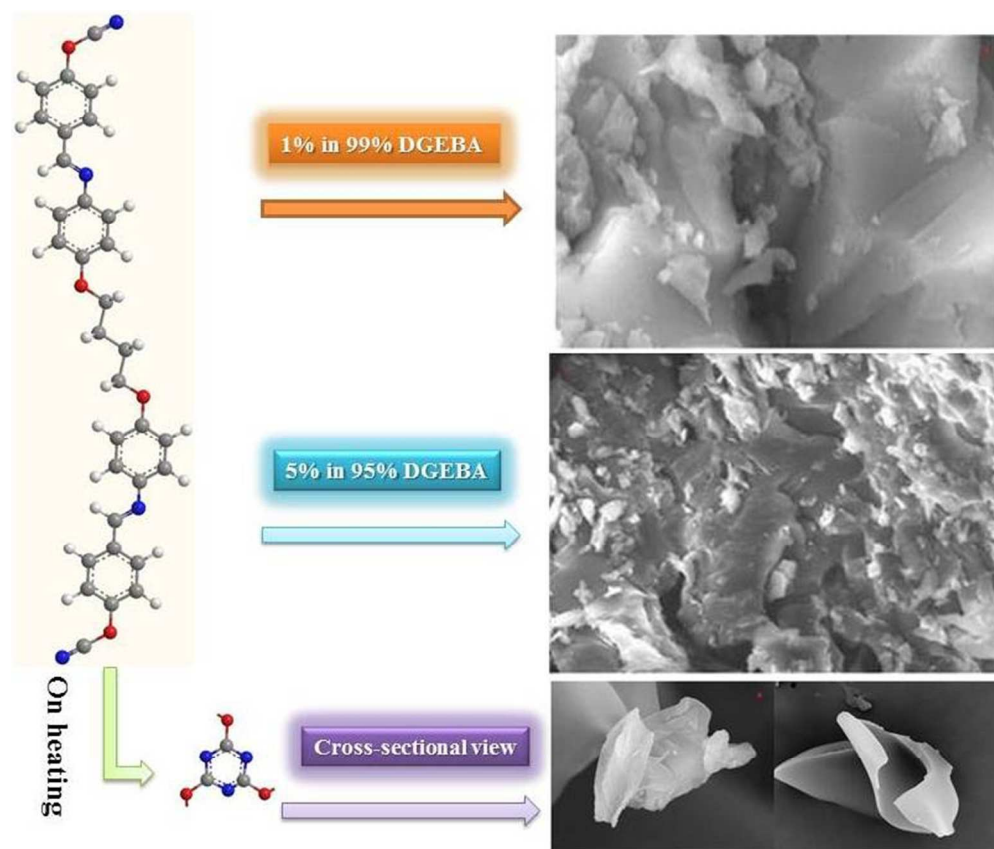

214x183mm (96 x 96 DPI)

Thermal and Mechanical Properties of Azomethine Functionalized Cyanate Ester/Epoxy Blends

C.P. Sakthidharan^{§‡}, Pudupadi R. Sundararajan[‡] and Muthusami Sarojadevi^{§*}

[§] Department of Chemistry, CEG, Anna University, Chennai, India – 600 025

[‡] Department of Chemistry, Carleton University, 1125 Colonel By Drive, Ottawa, Canada, K1S 5B6

*Corresponding author: msrde2000@yahoo.com

Abstract

A series of azomethine functionalized diols were synthesized by condensation reaction of aromatic diamines with 4-hydroxy benzaldehyde. Aromatic diamines with different alkyl chain lengths have been used to prepare the bisphenols. These bisphenols were converted to their corresponding cyanate esters by treating with cyanogen bromide (BrCN) in the presence of triethyl amine (Et₃N). The curing temperature was measured by using differential scanning calorimetry (DSC). The maximum curing temperature of these cyanate esters are in the range of 203-242 °C. Thermal properties of the cured cyanate ester were studied by using thermo gravimetric analysis (TGA). The polymers show excellent thermal stability (T₅ was found to be in the range of 358 to 465 °C and T₁₀ was found to be in the range of 508 to 525 °C) and the percentage of char yield at 800 °C was found to be in the range of 37.06 to 57.26. The flame retardancy of the cyanate ester resins have been evaluated using limiting oxygen index value which is in the range of 32.32 to 40.40 at 800 °C. Cyanate ester/epoxy blends were prepared and the morphology of the blends was studied by scanning electron microscopy. The mechanical properties and glass transition temperature of cyanate/epoxy ester blends were studied by using dynamic mechanical analysis (DMA) and the T_g was found to increase with increasing cyanate ester content (1 to 5%).

Keywords

Azomethine containing cyanate ester-epoxy blends

Thermal and mechanical properties

Introduction

Cyanate esters are one type of thermosetting resins. On heating or irradiation either in the presence or absence of catalyst, three units of cyanate ester monomer undergo cyclotrimerization and form symmetric triazine ring with nitrogen and carbon atom in which the carbon atoms are linked with oxygen atom.¹ Heat resistant character of cured cyanate esters (CE) make them more competing in high thermal applications.² The polycyanurates exhibit low dielectric constant and low dissipation factor. This character is well suited for making printed circuit boards in electronic industries.³⁻⁵ Radar transparency, low moisture absorption,⁶ very good adhesive character towards metal and high mechanical strength⁷⁻¹⁰ make cyanate esters more reliable for high end applications in aerospace industries. However, the cured CE is inherently brittle in nature and easily undergoes micro cracking under service loads. The fracture toughness of cyanate esters can be improved by blending with thermoplastic tougheners, rubber,¹¹ organic and inorganic fillers,^{6, 12} POSS¹³⁻¹⁵ and thermosetting resins such as epoxy¹⁶⁻²⁰, imides²¹⁻²⁴ and benzoxazines.²⁵⁻²⁶

Commercially available cyanate ester, Bisphenol A dicyanate ester (BADCY) is being widely used in various fields, but further modification is required to enhance its properties in performance and reduction of cost in production. The thermo oxidative stability and moisture resistance were improved by introducing silicon atom in BADCY.²⁷ On the addition of epoxy resin into the BADCY resin, mechanical and hot-wet properties were improved when the concentration ranges from 5 to 30 wt %²⁰. Epoxy resins also come under thermosetting resins category and they are widely used for making advanced composites because of their excellent adhesive nature towards metals, chemical resistance and outstanding mechanical properties²⁷ with superior dimensional stability. They undergo micro cracking, which makes them unfit for their requirement for high toughness applications (in engineering industries). Another disadvantage of epoxy resins is their moisture absorption.

Azomethine functionalized cyanate ester with shorter alkyl chain was prepared earlier,^{28,}²⁹ in this study, dicyanate esters with azomethine linkages and different alkyl chains with ether linkages were prepared and the effect of alkyl chain length between two aromatic groups on thermal stability has been studied. The prepared cyanate esters were blended with epoxy resin in

three different weight percentages. Thermal and thermo mechanical properties of the CE/epoxy blends were investigated by using thermo gravimetric analyzer (TGA) and dynamic mechanical analyzer (DMA). The morphology of the system was studied by scanning electron microscopy techniques (SEM).

2. Experimental Procedure

2.1. Materials

4-Acetamidophenol was purchased from Aldrich, USA. Acetone, 1, 4-dibromo butane, 1, 5-dibromo pentane, 1, 6-dibromo hexane, potassium carbonate (K_2CO_3), cyanogen bromide (CNBr) and 4- hydroxy benzaldehyde were purchased from Sisco Research Laboratories (SRL-India). Diglycidyl ether of bisphenol-A (DGEBA) was purchased from Huntsman (India). Diaminodiphenylmethane was purchased from Acros Organics (India). Ethanol and triethylamine (Et_3N) were purchased from Merck (India). All reagents were used as received. Triethylamine and acetone were distilled prior to use.


2.2. Measurement


Fourier transform infrared (FT-IR) spectra were recorded in ABB Bomem MB series FT-IR spectrometer using KBr pellet. 1H and ^{13}C nuclear magnetic resonance measurements were carried out with a Bruker AV III spectrometer (500 MHz). Samples were prepared in $CDCl_3$ and $DMSO-d_6$ solution. Melting temperatures were determined with a melting point apparatus IA 6304 at a heating rate of 4 °C/ min. Differential scanning calorimetric analysis (DSC) for curing studies was carried out using Perkin Elmer DSC 7 model at a heating rate of 5 °C/min under air atmosphere using aluminum pans. Thermo gravimetric analysis (TGA) was performed using a Perkin Elmer Diamond series model at a heating rate of 10 °C/min under flowing air in the range of 25-800 °C.

2.3. Synthesis of 1, 4-Bis (4-acetamidophenoxy) butane

4-acetamidophenol (5.0g, 0.0330mol) and 10.26 g of potassium carbonate (0.0742mol) in 100 mL of acetone were taken in a 250 mL round bottomed flask. To this 1, 4-dibromobutane (3.5708g, 0.0165mol) in 50 mL of acetone was added drop wise. The reaction was initiated by adding trace amounts of potassium iodide. Then, it was refluxed at 80 °C overnight. The mixture was cooled and poured into water (1000 mL). The white precipitate formed was separated and

recrystallized from ethanol.³⁰ Yield 89%, M.P.: 190 °C. IR (KBr, cm^{-1}): 3336 (CONH), 1053 (-C-O-C-), 1675 (C=O), 824 (p-substituted aromatic).

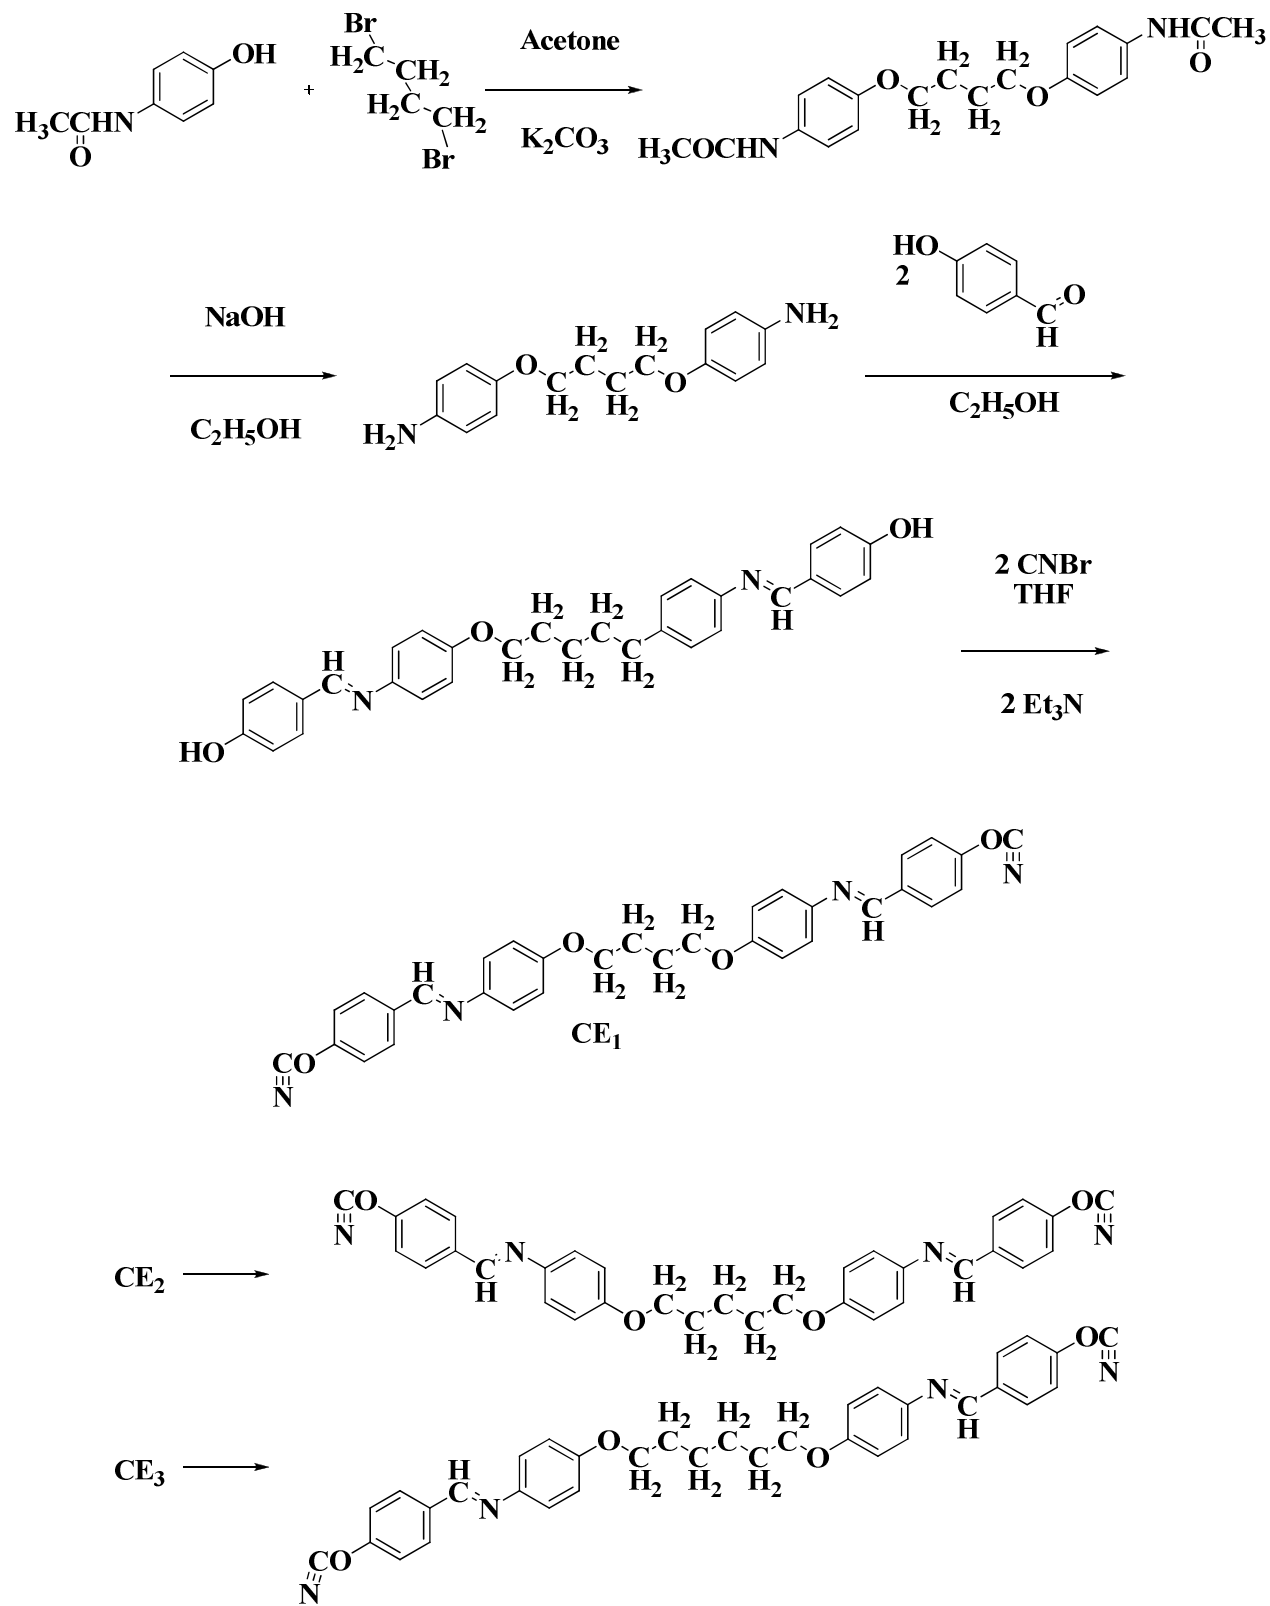

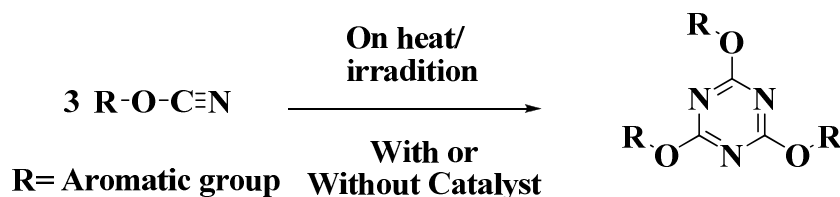

Scheme 1. Synthesis of dicyanate ester monomer

2.4. Synthesis of 1, 4-Bis (4-aminophenoxy) butane

1, 4-Bis (4-acetamidophenoxy) butane (4.0g, 0.0112 mol) in 100mL ethanol was taken in a 250 mL round bottomed flask. To this, 10.0g of sodium hydroxide (0.25mol) dissolved in water (35 mL) was added drop wise. After completion of the addition, the mixture was refluxed at 80 °C for 8 hr, cooled and poured into crushed ice. The resulting pale brown precipitate was filtered, washed with distilled water twice and recrystallized from ethanol. Yield 93%, M.P.: 140 °C. FT-IR (KBr, cm^{-1}): 3395, 3371 (aromatic NH_2), 2945 (OCH_2), 835 (p-substituted aromatic). $^1\text{H-NMR}$ (500 MHz, CDCl_3 , ppm): 3.7 (s, 4H, a (Ar-NH_2)), 6.6 (d, 4H, b), 7.2 (d, 4H, c), 3.8 (t, 4H, d (OCH_2CH_2)) 1.8 (m, 4H, e (OCH_2CH_2)). $^{13}\text{C-NMR}$ (CDCl_3 , ppm): C^1 -139.9, C^2 -115.7, C^3 -115.2, C^4 -149.3, C^5 -67.9, C^6 -28.8. Other two diamines were prepared in a similar way.

2.5.1. Synthesis of 1, 4-Bis [4(4-hydroxyphenylazomethyl)phenoxy] butane

1,4-Bis (4-aminophenoxy) butane (2.750g, 0.01 mol) was taken in a 250 mL round bottomed flask with 100 mL of ethanol and refluxed until it gets completely dissolved in ethanol. To this 2.4662g of 4-hydroxy benzaldehyde (0.0201 mol) in 50 mL of ethanol was added drop wise with constant stirring. The reaction was initiated by adding trace amounts of acetic acid. The mixture was refluxed for a further period of 3 hr. The mixture was then cooled and poured into cold water (1.0 L). The resulting yellow precipitate was collected and recrystallized from ethanol. Yield: 91%, M.P.: 83 °C. FT-IR (KBr, cm^{-1}): 3380 (OH), 2943 (OCH_2), 1680 (HC=N), 834 (p-substituted aromatic). $^1\text{H-NMR}$ ($\text{DMSO-}d_6$, ppm): 9.4 (s, 2H, a), 6.9 (d, 4H, b), 7.7 (d, 4H, c), 8.7 (s, 2H, d), 7.1 (d, 4H, e), 6.9 (d, 4H, f), 4.1 (t, 4H, g), 1.9 (m, 4H, h). $^{13}\text{C-NMR}$ (500 MHz, $\text{DMSO-}d_6$, ppm): C^1 -161.1, C^2 -116.8, C^3 -130.9, C^4 -130.1, C^5 -159.3, C^6 -145.9, C^7 -122.3, C^8 -116.8, C^9 -155.8, C^{10} -66.3, C^{11} -27.8.

2.5.2. 1,5-Bis[4(4-hydroxyphenylazomethyl)phenoxy]pentane

Yield: 83%, M.P.: 90 °C. FT-IR (KBr, cm^{-1}): 3414 (OH), 2945 (OCH_2), 1688 ($\text{HC}=\text{N}$), 836 (p-substituted aromatic). $^1\text{H-NMR}$ ($\text{DMSO-}d_6$, ppm): 9.2 (s, 2H, a), 6.8 (d, 4H, b), 7.8 (d, 4H, c), 8.6 (s, 2H, d), 7.2 (d, 4H, e), 7.0 (d, 4H, f), 4.0 (m, 4H, g), 1.8 (m, 4H, h), 1.8 (m, 2H, i). $^{13}\text{C-NMR}$ (500 MHz, $\text{DMSO-}d_6$, ppm): C^1 -160.5, C^2 -115.8, C^3 -131.2, C^4 -129.1, C^5 -159.9, C^6 -145.5, C^7 -122.5, C^8 -115.7, C^9 -158.5, C^{10} -67.3, C^{11} -29.8, C^{12} -22.8.

2.5.3. 1,6-Bis[4(4-hydroxyphenylazomethyl)phenoxy]hexane

Yield: 91%, M.P.: 109 °C. FT-IR (KBr, cm^{-1}): 3342 (OH), 2932 (OCH_2), 1676 ($\text{HC}=\text{N}$) 839 (p-substituted aromatic). $^1\text{H-NMR}$ ($\text{DMSO-}d_6$, ppm): 9.2 (s, 2H, a), 6.9 (d, 4H, b), 7.9 (d, 4H, c), 8.6 (s, 2H, d), 7.2 (d, 4H, e), 6.9 (d, 4H, f), 4.1 (t, 4H, g), 1.7 (m, 4H, h), 1.5 (m, 2H, i). $^{13}\text{C-NMR}$ (500 MHz, $\text{DMSO-}d_6$, ppm): C^1 -160.8, C^2 -116.1, C^3 -131.1, C^4 -128.9, C^5 -160.1, C^6 -144.8, C^7 -121.5, C^8 -115.9, C^9 -157.8, C^{10} -68.9, C^{11} -29.6, C^{12} -25.8.

2.6. Synthesis of cyanate ester monomers

A 250 mL, three-necked round bottomed flask, equipped with a magnetic stirring device and a nitrogen inlet was charged with 3.5g of the bisphenol (1,4-Bis[4(4-hydroxyphenylazomethyl)phenoxy]butane) (0.0114mol). The flask was maintained at -15 °C and then a solution of 2.3g (0.0228mol) of CNBr in acetone (50 mL) was added with constant stirring. To this mixture, 3.1 mL (0.0228mol) of triethyl amine was added in drops with continuous stirring. After complete addition of triethyl amine, the reaction mixture was stirred for a further period of 2 hr, while maintaining the bath temperature at -15 °C. The temperature was then raised to room temperature. The mixture was poured into cold distilled water to precipitate the cyanate ester. A light brown product (yield: 91%) was obtained. All other prepared bisphenols were converted into their corresponding dicyanate ester monomers in a similar way.

2.6.1. 1,4-Bis[4(4-cyanatophenylazomethyl)phenoxy]butane (CE_1)

Yield: 91%, M.P.: 91 °C. FT-IR (KBr, cm^{-1}): 2198, 2212 (OCN), 2945 (OCH_2), 1681 ($\text{HC}=\text{N}$), 834 (p-substituted aromatic). $^1\text{H-NMR}$ ($\text{DMSO-}d_6$, ppm): 6.9 (d, 4H, a), 7.6 (d, 4H, b), 8.6 (s, 2H, c), 7.1 (d, 4H, d), 6.9 (d, 4H, e), 4.0 (t, 4H, f), 1.9 (m, 4H, g). $^{13}\text{C-NMR}$ (500 MHz,

DMSO-*d*₆, ppm): C¹-109.1, C²-156.8, C³-115.9, C⁴-131.1, C⁵-135.9, C⁶-159.9, C⁷-143.3, C⁸-122.6, C⁹-116.8, C¹⁰-156.3, C¹¹-67.8, C¹²-28.7.

2.6.2. 1,5-Bis[4(4-cyanatophenylazomethyl)phenoxy]pentane (CE₂)

Yield: 87%, M.P.: 99 °C. FT-IR (KBr, cm⁻¹): 2226, 2240 (OCN), 2942 (OCH₂), 1688 (HC=N), 835 (p-substituted aromatic). ¹H-NMR (DMSO-*d*₆, ppm): 7.1 (d, 4H, a), 7.7 (d, 4H, b), 8.7 (s, 2H, c), 7.2 (d, 4H, d), 6.9 (d, 4H, e), 4.1 (t, 4H, f), 1.8 (m, 4H, g), 1.6 (m, 2H, h). ¹³C-NMR (500 MHz, DMSO-*d*₆, ppm): C¹-109.5, C²-155.8, C³-116.5, C⁴-131.1, C⁵-135.8, C⁶-161.1, C⁷-144.1, C⁸-121.9, C⁹-115.1, C¹⁰-157.1, C¹¹-68.9, C¹²-29.6, C¹³-22.1.

2.6.3. 1,6-Bis[4(4-cyanatophenylazomethyl)phenoxy]hexane (CE₃)

Yield: 93%, M.P.: 123 °C. FT-IR (KBr, cm⁻¹): 2219, 2242 (OCN), 2938 (OCH₂), 1680 (HC=N), 838 (p-substituted aromatic). ¹H-NMR (DMSO-*d*₆, ppm): 7.0 (d, 4H, a), 7.7 (d, 4H, b), 8.7 (s, 2H, c), 7.2 (d, 4H, d), 6.9 (d, 4H, e), 4.0 (t, 4H, f), 1.7 (m, 4H, g), 1.4 (m, 4H, h). ¹³C-NMR (500 MHz, DMSO-*d*₆, ppm): C¹-109.4, C²-156.3, C³-116.2, C⁴-131.9, C⁵-135.1, C⁶-160.1, C⁷-143.8, C⁸-121.8, C⁹-115.7, C¹⁰-157.9, C¹¹-68.5, C¹²-29.6, C¹³-25.9.

2.7. Preparation of cyanate ester /epoxy blends

1 wt. % of cyanate ester (0.200g) was taken with 99 wt. % of epoxy resin (19.80g) (cyanate ester: epoxy = 1:99) and stirred at 80 °C until the mixture turns homogeneous. 5.346 g (27 g of DDM taken for 100 g epoxy resin) amount of DDM (hardener) was added to the homogeneous mixture of cyanate/epoxy resin and immediately, the mixture was transferred to the mold and cured at 120 °C for 1 hr, 170 °C for 1 hr and post cured at 210 °C for 1 hr. The same procedure was adopted for the preparation of Cyanate ester + epoxy blends with 3% and 5% of cyanate ester.

3. Results and Discussion

The synthetic procedure for the preparation of dicyanate esters are presented in Scheme 1. The bisphenol precursors were prepared by the condensation reaction between aromatic aldehydes and diamine. The structure of the bisphenols was confirmed by FT-IR, ¹H-NMR, and ¹³C-NMR spectroscopy. The dicyanate esters were prepared from their precursor diols and CNBr in the presence of triethylamine. Fig.1 shows the FT-IR spectra of dicyanate esters. The

appearance of new bands at around 1680 cm^{-1} and disappearance of amine bands (around $3300\text{--}3400\text{ cm}^{-1}$) confirmed the formation of azomethine. The appearance of new bands at $2174\text{--}2240\text{ cm}^{-1}$ and disappearance of the band at $3300\text{--}3500\text{ cm}^{-1}$ due to hydroxyl group in the FT-IR spectrum confirms the conversion of hydroxyl group into dicyanate ester. The formation of -C-O-C linkage is confirmed by the presence of band at $1050\text{ to }1070\text{ cm}^{-1}$.³⁰ The signal at 3.7 ppm due to the amino protons disappears and a new signal at 8.7 ppm due to azomethine proton is formed indicating the conversion of the amino group to azomethine group. This is further supported by FT-IR spectrum. The strong absorption band due to the amino is missing and a new band is found at 1681 cm^{-1} .

The conversion of the hydroxyl group to the cyanate ester is confirmed by the disappearance of the hydroxyl proton signal at 9.4 ppm and the appearance of the signal due to cyanate ester carbon at 109.1 ppm^{13} from the NMR spectra. The chemical shifts of all the aromatic protons appear in the range of 6.9 to 7.6 ppm. The chemical shift at 4.0 ppm may be attributed to the methylene proton which is attached to aromatic ring through oxygen atom. The chemical shift at 1.9 ppm may be assigned to methylene protons which are present in the spacer group between the two aromatic rings. In the ^{13}C -NMR spectrum, the carbon atoms in azomethine linkage of the three cyanate esters show the chemical shift in the range of 115-116 ppm. Aromatic carbons appear in the range of 115.8-156.3 ppm. Hence, the proposed structure of the dicyanate ester is confirmed.

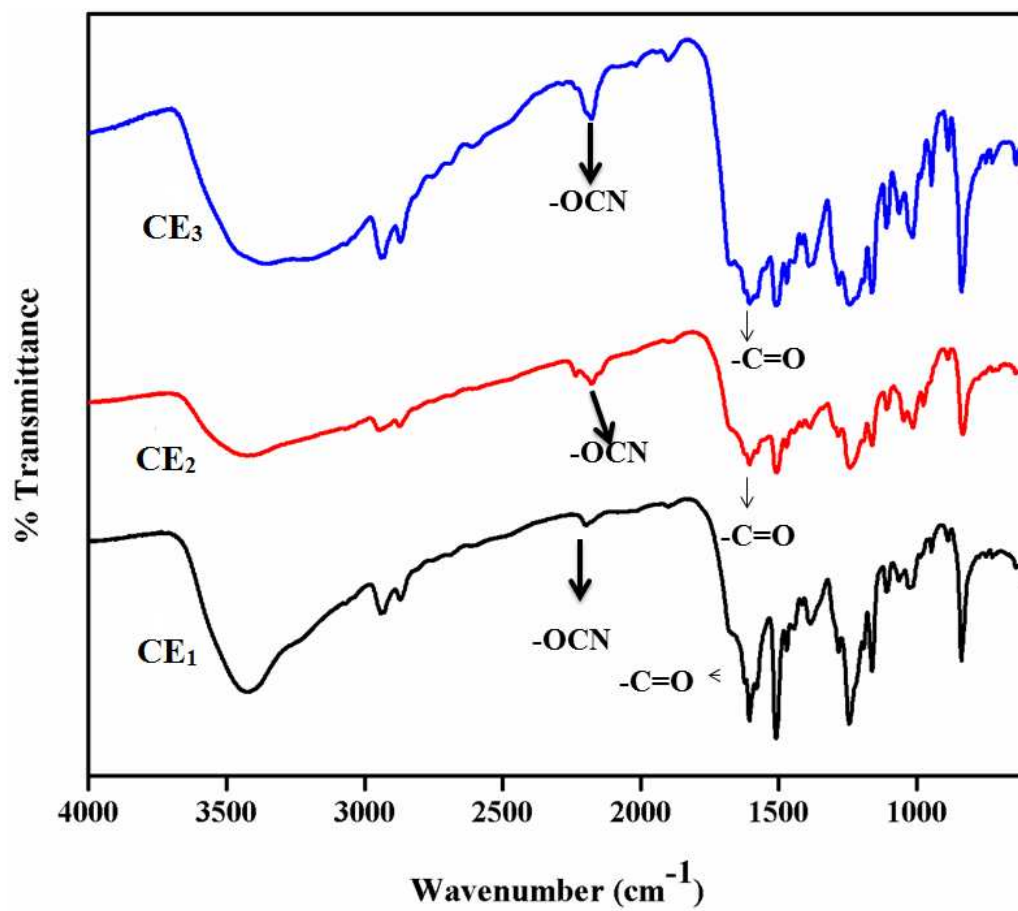


Figure 1. FT-IR spectrum of cyanate ester CE₁, CE₂ and CE₃.

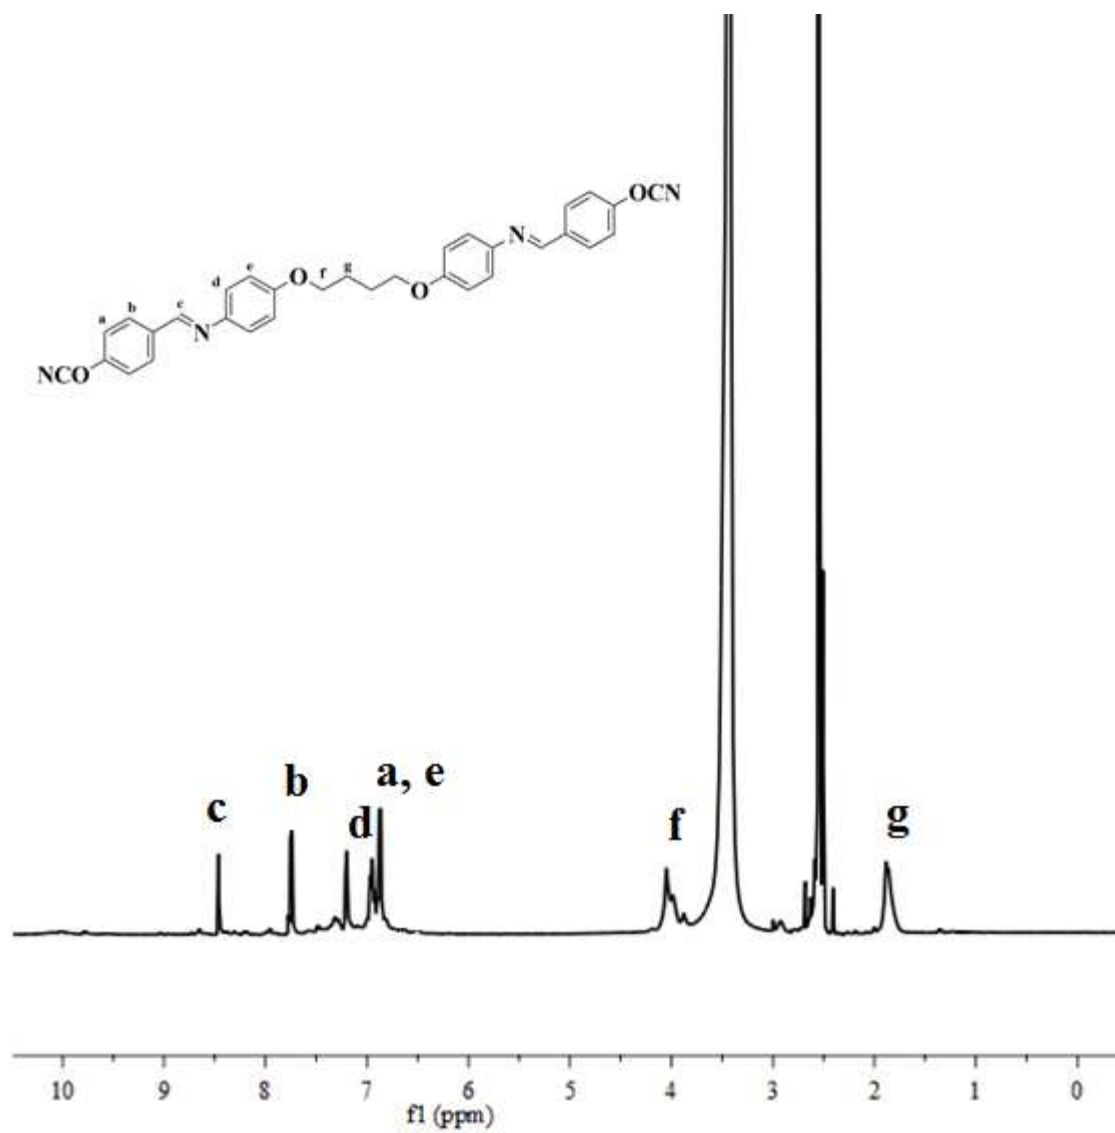


Figure 2. ¹H-NMR spectrum of cyanate ester (4,4'-(butane-1,4-diylbis(oxy))bis(N-(4-cyanatobenzylidene)aniline)) (CE₁)

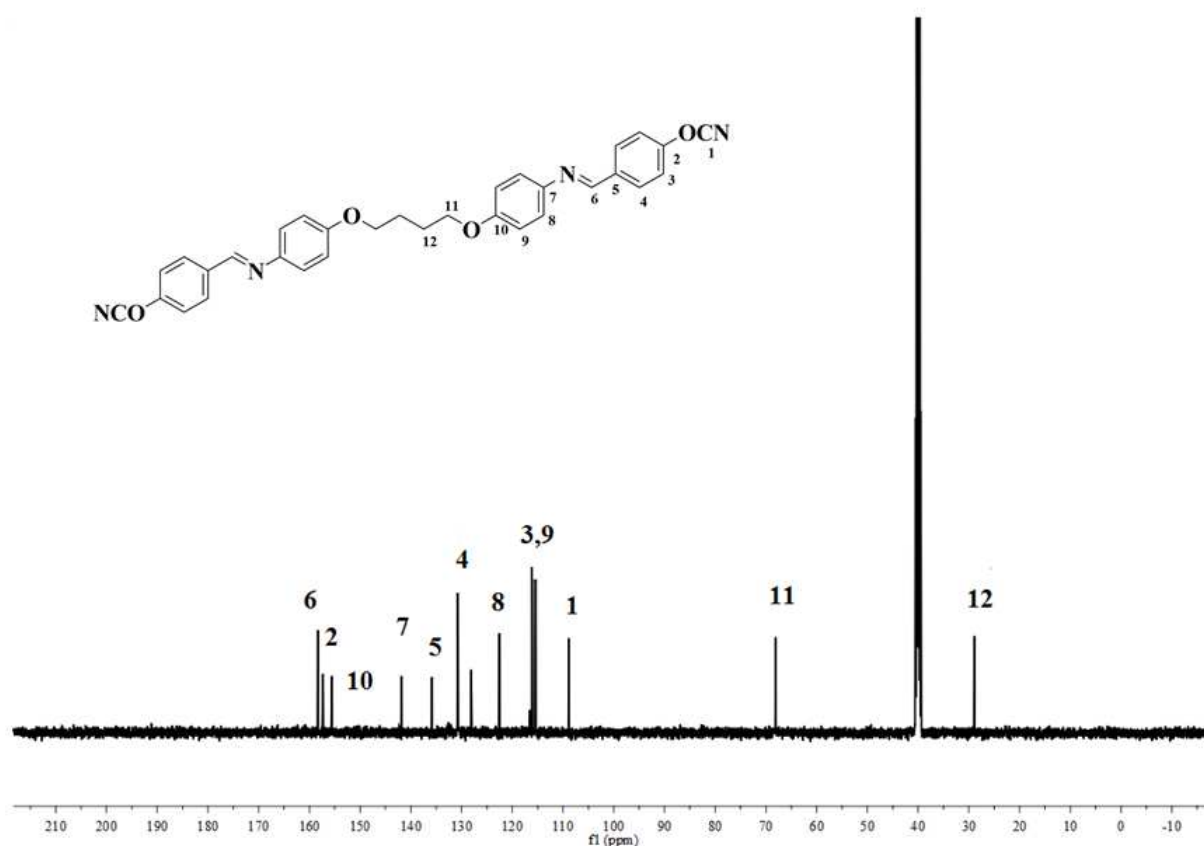


Figure 3. ^{13}C -NMR spectrum of cyanate ester (4,4'-(butane-1,4-diylbis(oxy))bis(N-(4-cyanatobenzylidene)aniline)) (CE_1)

3.1. DSC analysis

The cure behavior of the dicyanate esters was studied using differential scanning calorimetry. The DSC curves of the dicyanate esters CE_1 , CE_2 and CE_3 are shown in Fig. 4_a, 4_b and 4_c and the data are given in Table 1. The melting points of the dicyanate esters were found to be 91, 99 and 123 °C respectively. The initial (T_i) and maximum curing temperatures (T_{max}) were found to be in the range of 143 to 181 °C and 202 to 242 °C respectively. The cyanate ester CE_3 (1, 6-Bis [4(4-cyanatophenylazomethyl)phenoxy] hexane) shows the peak maximum curing temperature. The end cure temperatures were found to be in the range of 246 to 285 °C. The dicyanate ester CE_1 (1, 4-Bis [4(4-cyanatophenylazomethyl)phenoxy] butane) showed the highest end cure temperature of 285 °C. The curing temperature of BADCY is found to be at 281 °C² and all the three synthesised cyanate ester were cured at lower temperature when compared

with BADCY. The cyanate ester (CE_1) with shortest alkyl chain between the aromatic groups was found to cure at the lowest temperature. Glass transition temperature of the neat cured dicyanate ester was decreases with increase the alkyl chain length between two aromatic groups. No liquid crystallinity was observed for all the dicyanate esters.

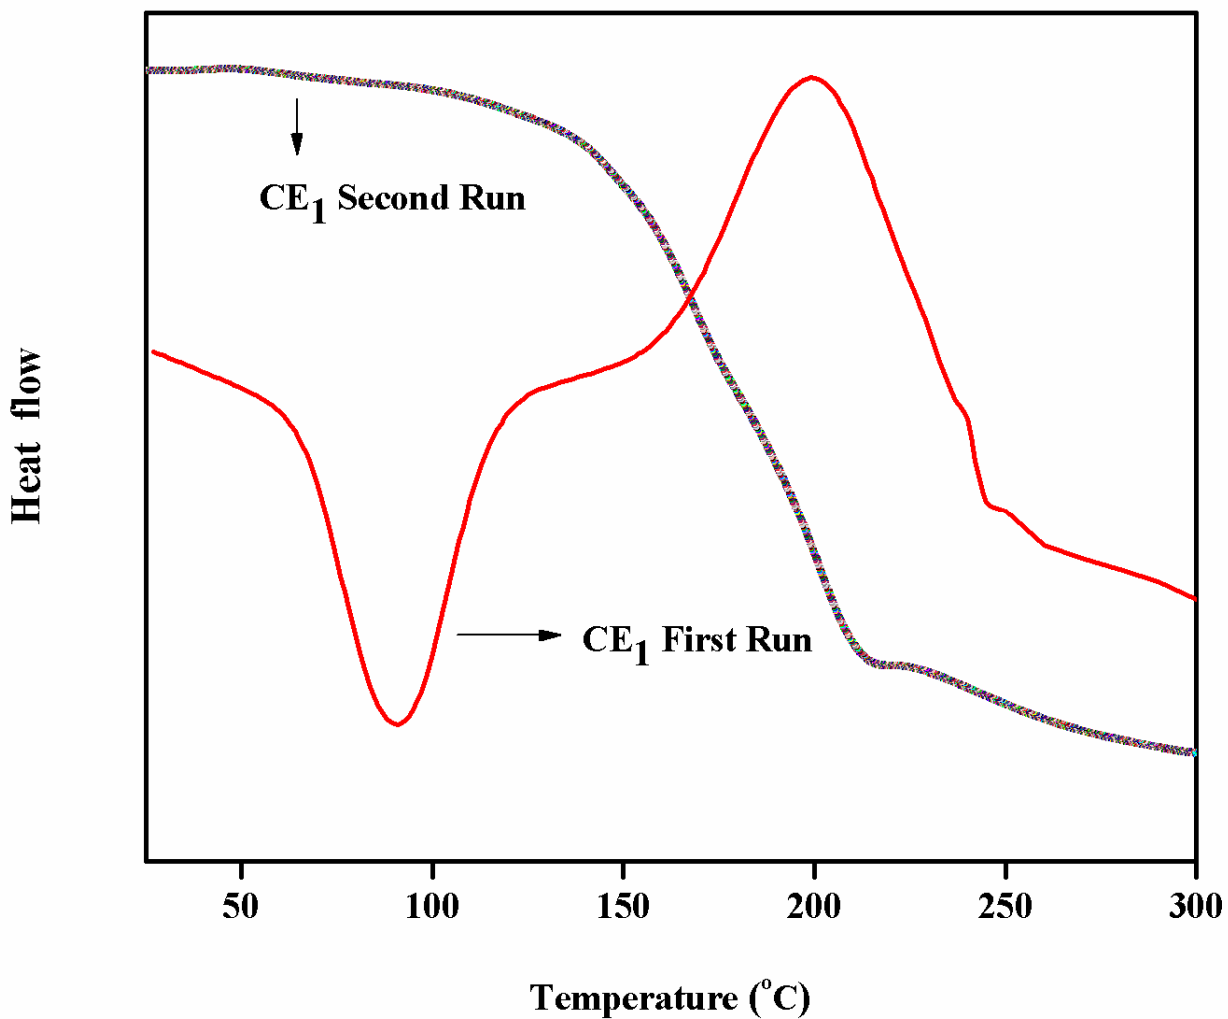


Figure 4_a. DSC thermogram data of cyanate ester (CE_1)

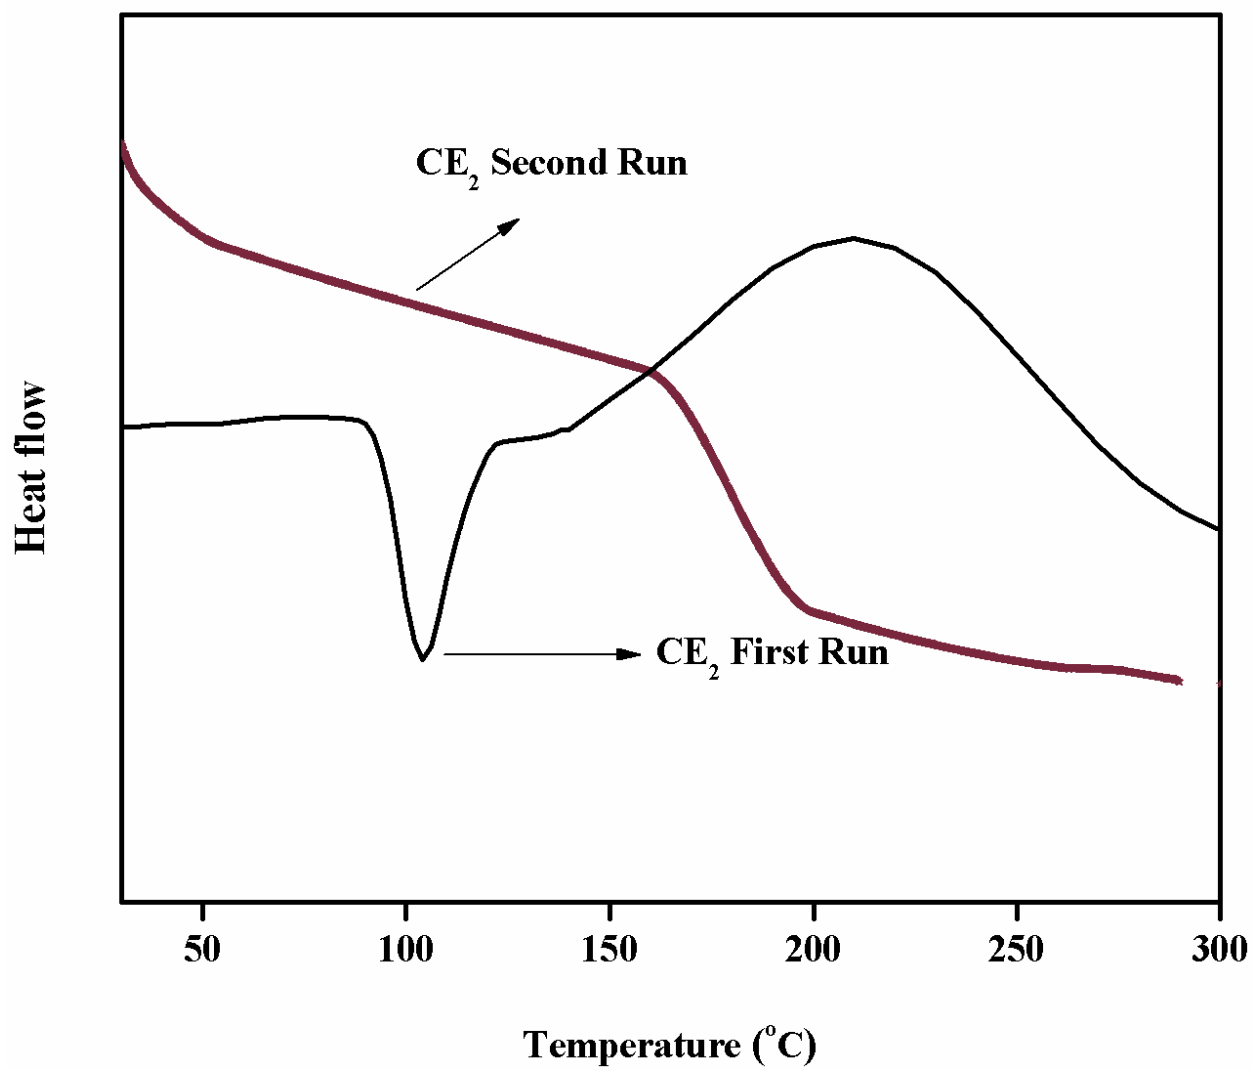


Figure 4_b. DSC thermogram data of cyanate ester (CE₂)

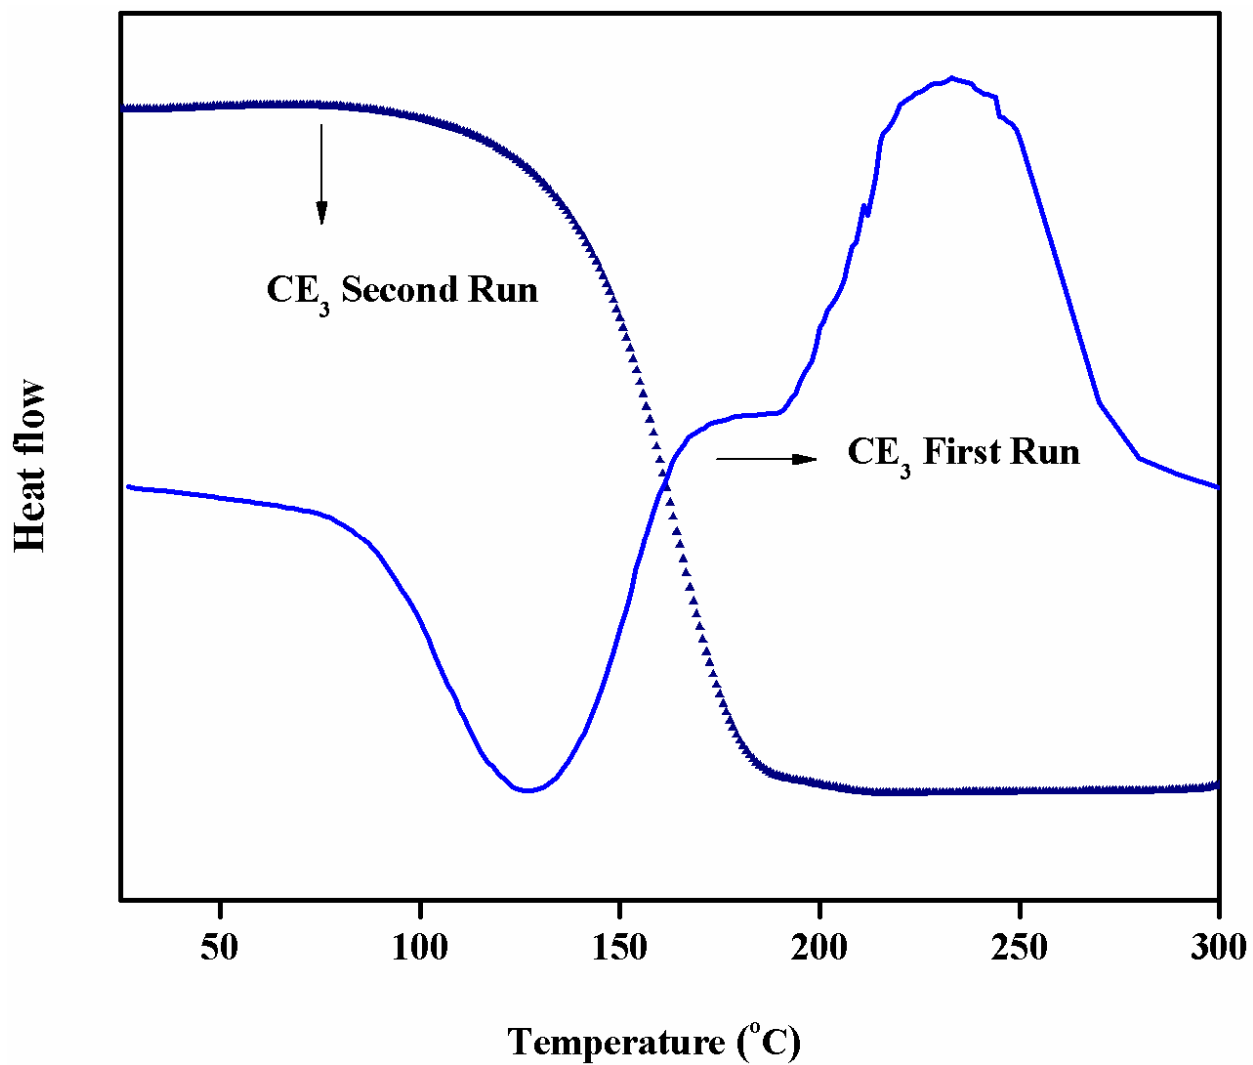


Figure 4_c. DSC thermogram data of cyanate ester (CE₃)

Table 1. DSC data of the cyanate ester

Sample Code	Melting Point (°C)	Onset of Cure (°C)	Maximum Cure (°C)	End of Cure (°C)
CE ₁	91	148	203	285
CE ₂	102	143	216	246
CE ₃	123	181	242	269

3.2. Thermogravimetric Analysis

Thermo gravimetric analysis (TGA) is the preferred technique for the evaluation of the thermal stability of the polymeric materials. The thermal stability of the cured cyanate esters was evaluated with its 5% weight loss ($T_{5\%}$), 10% weight loss temperatures ($T_{10\%}$) and the char yield at 800 °C. The TGA curves of various cured cyanate esters are given in the Fig. 5 and the data are given in Table 2. $T_{5\%}$ and $T_{10\%}$ of all the three neat cured cyanate esters found to be in the range of 358 to 465 °C and 508 to 525 °C respectively. The cured cyanate ester (CE_2) having alkyl chain length of five shows the least thermal stability ($T_{5\%}$ - 358 °C) and it lost 40% weight between 520 to 593 °C. The char yield was found to be in the range of 37.06 to 57.26 %. The cyanate ester having even number (CE_1 and CE_3) of alkyl chain length between two aromatic groups shows more stable than the dicyanate ester having odd number (CE_2) of spacer length between two aromatic groups from char yield and LOI values. Char yield of BADCY is found to be 42.5 at 800 °C², but char yield of CE_1 and CE_3 show higher char yield of 57.26 and 48.08 compared to commercially available dicyanate ester (BADCY). The cured cyanate ester having least alkyl chain length between two aromatic groups shows 5% weight loss at 465 °C. This is greater than that of other two cured cyanate ester. The 5 weight % of CE/epoxy blends show the 10% ($T_{10\%}$) weight loss temperature in the range of 392-410 °C and char yield in the range of 24.11 to 31.26 %. There are also reports by other authors that the thermal stability and char yield of cyanate ester/epoxy blend increases with increase of cyanate ester concentration in epoxy blends which is similar to our case¹³.

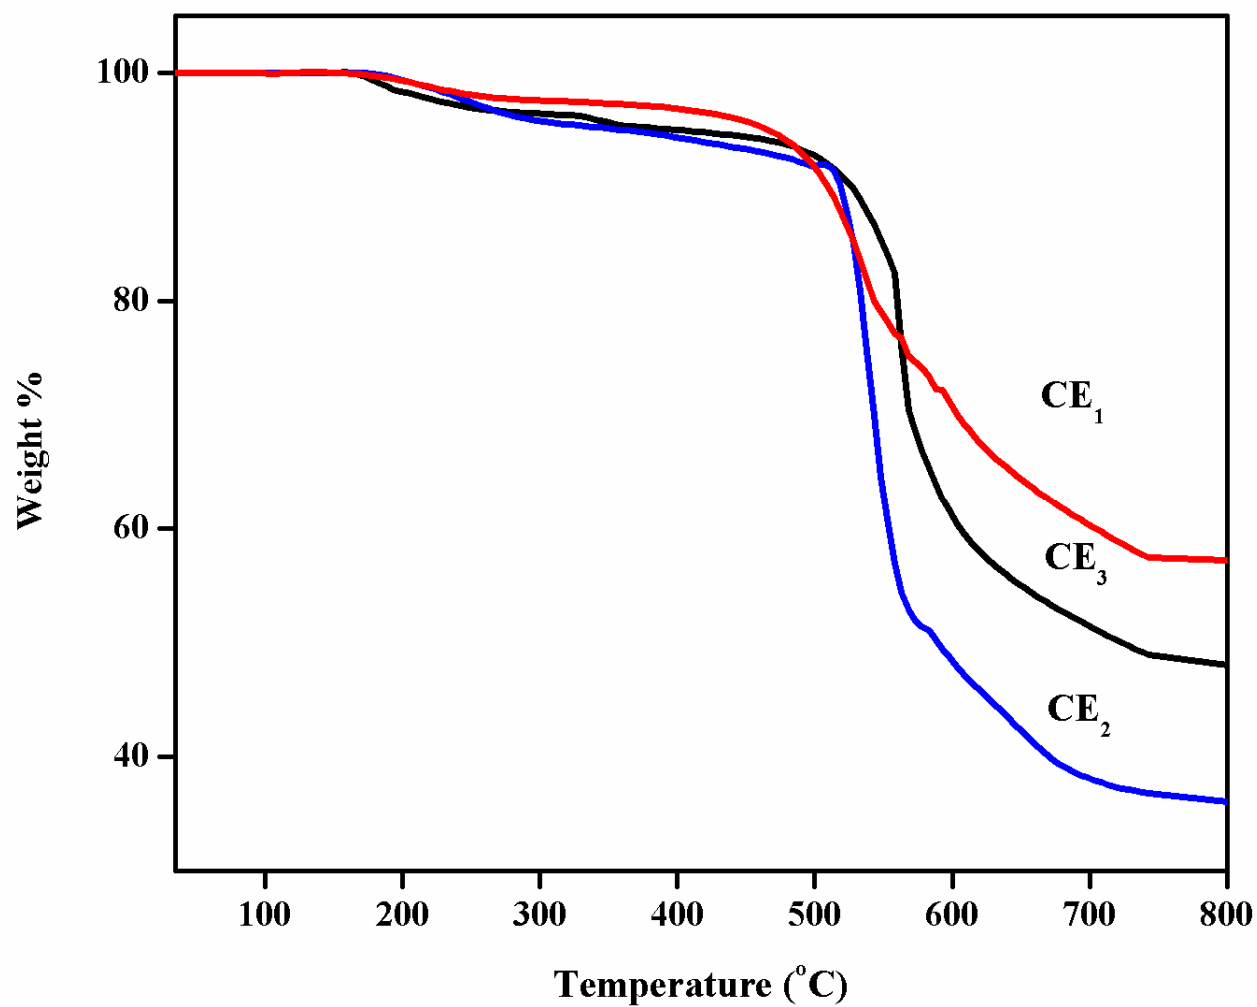


Figure 5. TGA thermogram data of cyanate ester

Table 2. TGA data of Polycyanurates

Sample Code	T ₅ (°C)	T ₁₀ (°C)	Char Yield %	LOI
CE ₁	465	508	57.26	40.40
CE ₂	358	520	37.06	32.32
CE ₃	399	525	48.08	36.73

Neat Epoxy	363	369	18.0	24.7
5% CE ₁ + 95% Epoxy	393	410	31.26	30.00
5% CE ₂ + 95% Epoxy	378	392	24.11	27.14
5% CE ₃ + 95% Epoxy	381	395	27.80	28.62


T₅ = 5% weight loss temperature

T₁₀ = 10% weight loss temperature

LOI = Limiting oxygen index

3.3. SEM Analysis

The cross-section (fracture surface) of CE/epoxy blend was studied by Scanning electron microscopy. The fractured surface of the neat CE and CE/epoxy blends was sputtered with gold to deionize the electrons on the surface. Figs. 6 (a, b and c) display the SEM images of cured neat cyanate ester CE₁, 1% cyanate ester + 99 % epoxy and 5% cyanate ester + 95 % epoxy respectively. The SEM images of the fractured surface of the CE₂ and CE₃ are given in figures 6 (d) and (e) respectively. CE₁ shows the curved hollow structure, CE₂ and CE₃ shows layered structure (on both lower and higher magnification). SEM images b and c illustrate the uniform distribution of the cyanate ester in the epoxy blends without any void. The DMA results show that toughening of epoxy was effected by adding CE. The neat CE₂ have similar morphology to poly cyanurate of bisphenol A dicyanate ester.³¹

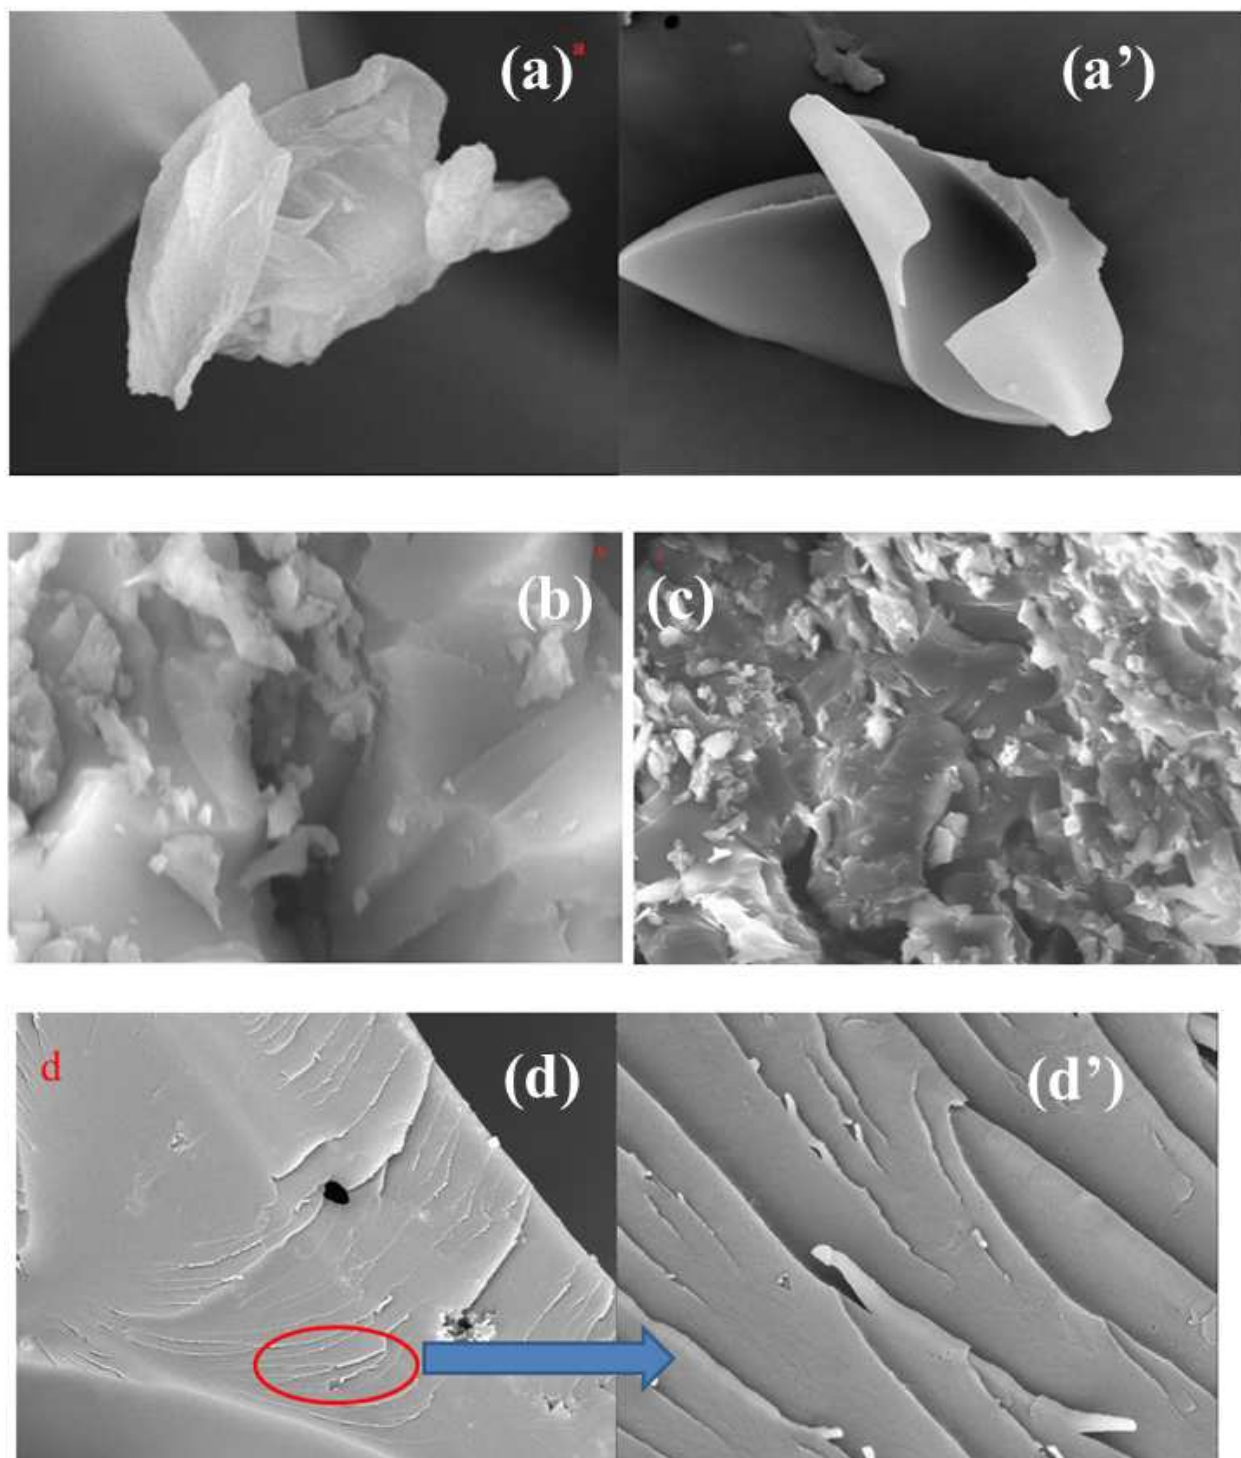

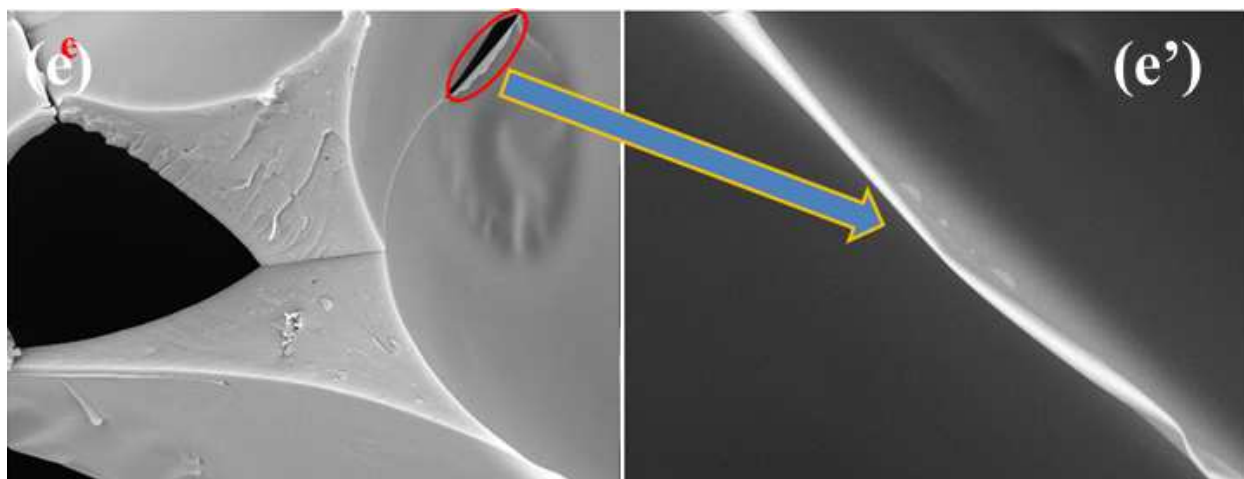


Figure 6. SEM images of (a) neat cyanate ester CE₁, (b) 1% Cyanate ester CE₁ + 99 % epoxy system and (c) 5% Cyanate ester CE₁ + 95 % epoxy system, (d) neat cyanate ester CE₂ and (e) neat cyanate ester CE₃.

3.4. Dynamic Mechanical Analysis (DMA)

Dynamic mechanical properties (Stress relaxation behavior) were measured for the CE/epoxy blend systems in order to find out the effect of increase of cyanate ester content. The storage modulus and tan delta of the blend with 5% cyanate ester (CE₁ CE₂ and CE₃) and 95% epoxy are given in the figures 7 and 8 respectively. The data obtained from DMA scans are furnished in Table 3. Storage modulus of the CE/epoxy blend increases with increase in the cyanate ester content (from 1 to 5% except 1% of CE₁/epoxy blend). The increase in storage modulus may be due to the increased cross-linking density of the blends as a result of increase in the CE content. Glass transition temperature of pure epoxy system was found to be 161 °C¹³. In the case of 1% CE₁ epoxy blend, the glass transition temperature was decreased to 158 °C from 161 °C for the neat cured epoxy. But on further addition of 5% CE₁ to the epoxy resin, the glass transition temperature was increased to 180 °C from 161 °C. The glass transition temperature of the blends slightly increases with increase in the cyanate ester content. This observation proves the fact that the co-reaction of cyanate ester with epoxy resin is almost complete with homogeneous state¹⁴ and the resultant oxazolidinone network²⁵ which enhance the thermal and mechanical property of the CE/epoxy blends. But some of the authors reported that the addition of POSS-CY in epoxy resin, leads to a decrease in the glass transition temperature from 161 to 155 due to the formation of the free volume in cyanate/epoxy blend system.¹³

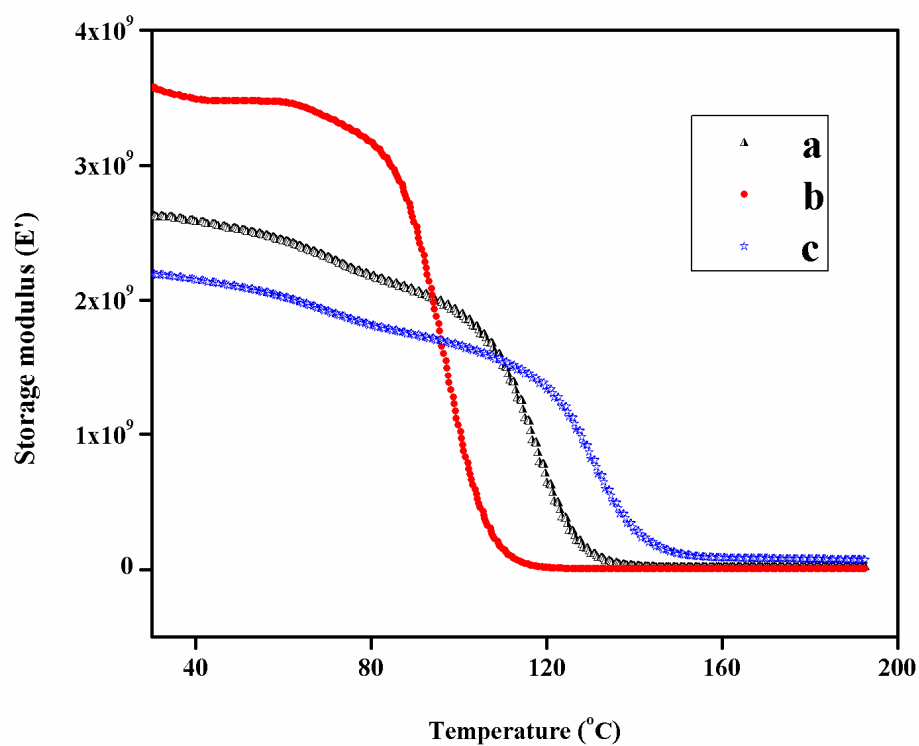


Figure 7. DMA analysis showing storage modulus (E') of the CE/Epoxy blends: a) 5% of CE_1 + 95 % epoxy, b) 5% of CE_2 + 95 % epoxy, c) 5% of CE_3 + 95 % epoxy.

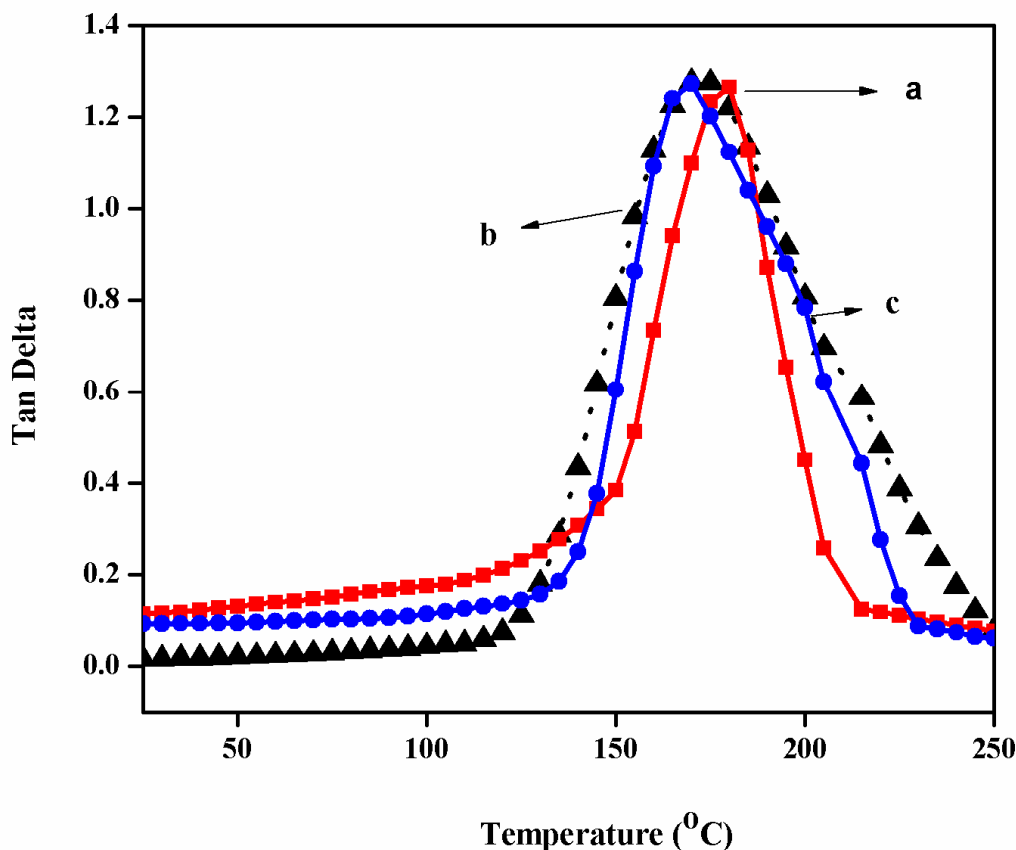


Figure 8. DMA analysis showing loss modulus of the CE/Epoxy blends: a) 5% of CE₁ + 95 % epoxy, b) 5% of CE₂ + 95 % epoxy, c) 5% of CE₃ + 95 % epoxy.

3.5. Crosslink density

The crosslink density or concentration of network chain (ν_e), is the number of moles of network chains per unit volume of the cured polymers. Crosslink density of highly crosslinked thermosets can be determined by modulus measurements in the rubbery plateau by using the equation of state for rubber elasticity³² as

$$\nu_e = E'/3RT$$

where,

- E' = tensile storage modulus in the rubbery plateau
- T = temperature in K corresponding to the storage modulus value
- R = gas constant

Table 3 shows the crosslink density of the CE/Epoxy blends. On addition of cyanate ester to the epoxy resin, the cross link density was increased. The CE₂ epoxy blends show the highest cross link density. The storage modulus of CE₂ blends (3.48 GPa, having odd number of alkyl chain length between aromatic groups) is higher compared to CE/epoxy blends (having even number of alkyl chain length between two aromatic groups) of CE₁ (2.52 GPa) and CE₃ (2.09 GPa).

Table 3. Values of crosslink density of CE + Epoxy blends
(from DMA values).

Sample Code	CE %	E' (GPa)	Temp k (273+50)	Cross link density $v_e \times 10^5$ (mol m ⁻³)
CE ₁ + Epoxy	5	2.52	323	3.13
CE ₂ + Epoxy	5	3.48	323	4.32
CE ₃ + Epoxy	5	2.09	323	2.59

3.6. Flame Retardancy

The resistance towards fire of CEs and CE/epoxy blends are expressed in terms of limiting oxygen index (LOI). LOI may be defined as the minimum fraction of oxygen in a mixture of O₂ and N₂ during fire. The LOI value should be higher than that of threshold value (value 26) for the polymer to behave as a self-extinguishing material or self-extinguisher. The LOI value is calculated by using Kregelven's equation.³³

$$\text{LOI} = 17.5 + 0.4 (\sigma).$$

where σ is the percentage of char yield. The LOI of the neat CE and CE/epoxy blends were found to be in the range of 32.32 to 40.40 and 27.14 to 30.00 respectively. The cured cyanate ester with least alkyl space length (CE₁) shows the highest LOI value and the cyanate ester (CE₂) with alkyl chain having five carbons shows the lowest LOI value. The LOI values of all the cured dicyanate esters indicate that they are very good fire retardant materials. From the

LOI values, it was found that the cured cyanate ester CE₁/epoxy blends show the best flame retardance.

Conclusions

Dicyanate esters with azomethine linkage were successfully synthesised. The structure of the monomers and precursors were characterized by FT-IR, ¹H-NMR and ¹³C-NMR spectroscopy, which clearly confirms the molecular structure. The morphology of the cured cyanate ester and CE/epoxy blends reveal the uniform distribution of cyanate ester in the epoxy resin. The cured cyanate ester and BADCY show the similar morphology. The DMA studies revealed that the glass transition temperature of epoxy was increased from 161 to 180 °C and storage modulus of the epoxy resin increases with increase in cyanate ester content. The crosslink density of the cyanate epoxy blends are calculated from the storage modulus value, which increases (from 3.98 to 4.32mol/m³ for CE₂) with increase in the weight ratio of CE in the blends. TGA results show that the char yield values of neat cyanate esters are in the range of 32.32 to 40%. The char yield increases with increase of CE content in the epoxy blend from 18 % to 30.0 %. This increase in char yield further suggests that the CE/epoxy blends can be used in high flame retardancy applications. The microwave curing and the effect of odd and even alkyl chain length (because CE₁ and CE₃ having even number of alkyl chain length between two aromatic rings showing better char yield and LOI values compared to CE₂ which is having odd number of alkyl chain between two aromatic rings.) between the two aromatic groups will be studied in future.

Acknowledgements

This work was supported by University Grants Commission (UGC), India and the Natural Sciences and Engineering Research Council (NSERC) of Canada.

References:

- 1 C. Dreyer, D. Söthje and M. Bauer, *Adv. Chem. Eng. Sci.*, 2014, **4**, 167–183.
- 2 S. Dai, D. Zhuo, A. Gu, G. Liang and L. Yuan, *Polym. Eng. Sci.*, 2011, **51**, 2236–2244.

- 3 Y. Shen, A. Gu, G. Liang and L. Yuan, *Compos. Part A Appl. Sci. Manuf.*, 2010, **41**, 1668–1676.
- 4 X.-Y. Zhao and M.-Z. Wang, *Plasma Chem. Plasma Process.*, 2012, **33**, 237–247.
- 5 X. Zhao, M. Wang, Z. Sun, C. Niu, J.-J. Xiao and E.-J. Tang, *Plasma Process. Polym.*, 2012, **9**, 468–472.
- 6 A. J. Guenther, G. R. Yandek, M. E. Wright, B. J. Petteys, R. Quintana, D. Connor, R. D. Gilardi and D. Marchant, *Macromolecules*, 2006, **39**, 6046–6053.
- 7 S. He, G. Liang, J. Wang and H. Yan, *Polym. Bull.*, 2008, **62**, 237–246.
- 8 B. Wang, Y. Jiao, A. Gu, G. Liang and L. Yuan, *Compos. Sci. Technol.*, 2014, **91**, 8–15.
- 9 X. Sheng, R. Hanus, A. Bauer and M. R. Kessler, *J. Appl. Polym. Sci.*, 2013, **130**, 463–469.
- 10 J. Li, Z. Wu, C. Huang, H. Liu, R. Huang and L. Li, *Compos. Sci. Technol.*, 2014, **90**, 166–173.
- 11 Y. Huang, X. Ma, X. Wang, X. He and L. Liu, *Mater. Chem. Phys.*, 2010, **121**, 241–248.
- 12 Y. Tada, N. Moriya, T. Inoue, A. Suzuki and S. Koyama, *Phosphorus. Sulfur. Silicon Relat. Elem.*, 2012, **187**, 1555–1567.
- 13 S. Rakesh, C. P. S. Dharan, M. Selladurai, V. Sudha, P. R. Sundararajan and M. Sarojadevi, *High Perform. Polym.*, 2012, **25**, 87–96.
- 14 Z. Zhang, G. Liang and X. Wang, *Polym. Int.*, 2014, **63**, 552–559.
- 15 Y. Tang, J. Gu, Y. Yu and J. Kong, *Polym. Compos.*, 2014, doi: 10.1002/pc.23111.
- 16 A. Idesaki, H. Uechi, Y. Hakura and H. Kishi, *Radiat. Phys. Chem.*, 2014, **98**, 1–6.
- 17 P. Brahmhatt, J. Unnikrishnan, J. D. Sudha and S. Pradhan, *J. Appl. Polym. Sci.*, 2012, **125**, 1068–1076.
- 18 R. Biju, C. Gouri and C. P. Reghunadhan Nair, *Eur. Polym. J.*, 2012, **48**, 499–511.
- 19 C. H. Lin, *Polymer*, 2004, **45**, 7911–7926.
- 20 G. Liang, P. Ren, Z. Zhang and T. Lu, *J. Appl. Polym. Sci.*, 2006, **101**, 1744–1750.
- 21 H.-J. Hwang, C.-H. Li and C.-S. Wang, *Polymer*, 2006, **47**, 1291–1299.

- 22 I. Hamerton, B. J. Howlin, S. L. Jewell and P. Patel, *React. Funct. Polym.*, 2012, **72**, 279–286.
- 23 N. J. Suman, *J. Reinf. Plast. Compos.*, 2005, **24**, 1105–1114.
- 24 A. Bauer, M. Thunga, K. Obusek, M. Akinc and M. R. Kessler, *Polymer*, 2013, **54**, 3994–4002.
- 25 X. Li, Y. Xia, W. Xu, Q. Ran and Y. Gu, *Polym. Chem.*, 2012, **3**, 1629.
- 26 K. S. Santhosh Kumar, C. P. Reghunadhan Nair and K. N. Ninan, *Eur. Polym. J.*, 2009, **45**, 494–502.
- 27 B. Francis, V. L. Rao, G. Vanden Poel, F. Posada, G. Groeninckx, R. Ramaswamy and S. Thomas, *Polymer*, 2006, **47**, 5411–5419.
- 28 G. Anuradha and M Sarojadevi, *Polym Compos.*, 2009, **30**, 782–790.
- 29 M. Ariraman, R. Sasi and M. Alagar, *J. Appl. Polym. Sci.*, 2014, **41097**, 1–10.
- 30 P. A. Henderson, R. T. Inkster, M. Seddon and C. T. Imrie, *J. Mater. Chem.*, 2001, 2722–2731.
- 31 L. Yuan, A. Gu and G. Liang, *Polym. Compos.*, 2008, **31**, NA–NA.
- 32 L. W. Hill, *Prog. Org. Coatings*, 1997, **31**, 235–243.
- 33 D. W. Van Krevelen, *Polymer*, 1975, **16**, 615–620.