

**IrOx core-shell nanocatalysts for cost- and energy-efficient electrochemical water splitting**

Journal:	<i>Chemical Science</i>
Manuscript ID:	SC-EDG-04-2014-001065
Article Type:	Edge Article
Date Submitted by the Author:	11-Apr-2014
Complete List of Authors:	Nong, Hong Nhan; Technical University Berlin, Department of Chemistry Gan, Lin; Technical University Berlin, Department of Chemistry Kudrenko, Elena; Fritz-Haber-Institute, Teschner, Detre; Fritz-Haber-Institute, Strasser, Peter; Technical University Berlin, Department of Chemistry

IrO_x core-shell nanocatalysts for cost- and energy-efficient electrochemical water splitting

*Hong Nhan Nong^a, Lin Gan^a, Elena Willinger^b,
Detre Teschner^{*,b}, Peter Strasser^{*,a}*

^a Department of Chemistry, Chemical and Materials Engineering Division, The Electrochemical Energy, Catalysis and Materials Science Laboratory, Technical University Berlin, Straße des 17. Juni 124, 10623 Berlin, Germany.

^b Fritz-Haber-Institut der Max-Planck-Gesellschaft, Department of Inorganic Chemistry, Faradayweg 4-6, D-14195 Berlin, Germany.

* corresponding authors

KEYWORDS: IrNi bimetallic catalysts, core-shell nanoparticles, oxygen evolution reaction, STEM, X-ray photoelectron spectroscopy

ABSTRACT

A family of dealloyed metal-oxide hybrid (M₁M₂@M₁O_x) core@shell nanoparticle catalysts is demonstrated to provide substantial advances toward more efficient and less expensive electrolytic water splitting. IrNi@IrO_x nanoparticles were synthesized from IrNi precursor alloys through selective surface Ni dealloying and controlled surface oxidation of Ir. Detailed depth-resolved insight into chemical structure, composition, morphology, oxidation state was obtained using spectroscopic, diffraction, and scanning microscopic techniques (XANES, XRD, STEM-EDX, XPS), which confirmed our structural hypotheses at the outset. A 3-fold catalytic activity enhancement for the electrochemical oxygen evolution reaction (OER) over Ir and RuO_x benchmark catalysts was observed for the core-shell catalysts on a noble metal mass basis. Also, the active site-based intrinsic turnover frequency (TOF) was greatly enhanced for the most active IrNi@IrO_x catalyst. This study documents the successful use of synthetic dealloying for the preparation of metal-oxide hybrid core-shell catalysts. The concept is quite general, can be applied to other noble metal nanoparticles, and points out a path forward to nanostructured proton-exchange-electrolyzer electrodes with dramatically reduced noble metal content.

1. INTRODUCTION

Electrocatalytic splitting of water is expected to play a key role in the future sustainable production of hydrogen from electricity. Combined with renewable electric power generation technologies, such as solar electric, solar-thermal, hydro, or wind power plants, it is expected to emerge as a low-emission method for storing excess electricity or for producing abundant quantities of hydrogen fuel as part of a solar refinery.¹⁻⁶ Electrocatalytic water splitting can be divided into two half redox reactions, hydrogen evolution reaction (HER) on cathode and oxygen evolution reaction (OER) on anode side. The challenge in electrocatalytic water splitting is the anodic multi-electron OER with its extremely sluggish surface kinetics on virtually all known materials. On Pt electrodes, for instance, the OER proceeds about 10^{10} times more slowly than the HER process.^{7,8} An important consequence of the low reaction rate of the electrochemical OER is that OER is currently considered as a major bottleneck, hampering the application of light conversion devices into storable fuels.⁶

In principle, the electrochemical OER can be carried out under a wide range of pH conditions.^{4,9-14} The selection of suitable electrocatalyst materials, however, is critically dependent on the pH of the electrolyte. Acid conditions are demanding in terms of electrode corrosion stability, requiring structurally stable catalysts up to an electrode potential as high as +1.8 V/NHE. This is why acid OER electrocatalysts typically contain noble metal oxides, such as RuO_x or IrO_x . This makes them expensive and of limited sustainability. Since Beer's early pioneering work,^{15,16} Ti-supported annealed films of bulk mixed-metal oxide of RuO_x , IrO_x and TiO_x have proven to be the most active and most stable OER electrocatalyst known to date. This family of bulk catalyst came to be known as the "dimensionally stable anode" (DSA). Suitable Ru-Ir mixed metal catalyst show overpotential of only about 200 mV. Since the early days, it represents the catalyst solution of choice for virtually all commercial acid Polymer Electrolyte Membrane (PEM) electrolyzers.¹⁷⁻²⁰

In order to make RuO_x and IrO_x -containing OER electrolyzer catalysts more efficient on both a thermodynamic and cost basis, new materials are sought with i) lowered overpotential (higher catalytic activity) and ii) reduced noble metal content.

Rossmesl et al. reported DFT-computational studies²¹⁻²⁵ on OER reactivity trends on well-defined pure metal oxides in terms of oxygen chemisorption energies, yielding a volcano type activity plot, in which Ru and Ir are near the top. From their analysis, oxide materials should exist with more favorable oxygen chemisorption coupled to higher OER reactivity and lower overpotentials than RuO_2 . However beyond pure metal oxide catalysts, other known correlations between structure and chemisorption can be invoked and combined with Rossmesl's concepts to design improved OER catalysts. For instance, it is known that coordinatively unsaturated surface atoms at defects, steps or kinks of surfaces tend to show varied chemisorption compared to terrace atoms and can be leveraged to optimize reactivity.²⁶⁻³⁵ In addition, tuning the d-band structure of RuO_x and IrO_x surfaces through non-noble transition metal atoms in underlying atomic layers is expected to be an effective

way to enhanced catalytic activities.³⁴ This may be based on short-range electronic interaction or based on longer-range geometric strain effects.³⁶

In order to lower the noble metal content (Ru and Ir in case of OER catalysts), mesoporous and nanostructure design of active phase has attracted much attention.^{3,37-41} RuO₂ nanoparticles (NPs) offer the lowest overpotentials for the OER, yet IrO₂ NPs show almost comparable activity and are far more stable³ and are, therefore, of great interest. Still, the extremely scarce nature of Ir renders the Ir NP architecture hardly viable, which is why novel strategies are critically needed to further reduce the amount of Ir in nanoparticle architectures. One strategy involves the well-known use of suitable corrosion-resistant high surface-area supports; another consists of the design of IrO_x-M hybrid core-shell architectures, where M represents an inexpensive abundant transition metal that helps tune the intrinsic electrocatalytic activity and lower the noble metal content alike. This is because concentrating Ir in a thin shell of the nanoparticles reduces the required amount of the scarce catalyst significantly. This contribution demonstrates a combination of both strategies.

In the present contribution, we demonstrate the viability and future potential of supported metal-oxide hybrid core-shell OER NP catalysts formed through a dealloying and selective oxidation procedure of bimetallic NPs.⁴² Exemplified by the IrNi-IrO_x system, we compare and contrast their facile preparation to earlier approaches and follow the stepwise emergence of the metal-oxide hybrid core-shell architecture through a combination of high resolution Atomic Dark Field Scanning Transmission Electron Microscopy coupled to Energy Dispersive X-ray Spectroscopy (ADF-STEM-EDX), depth-resolved synchrotron based Photoelectron Spectroscopy (XPS) and X-ray Absorption Spectroscopy (XAS).

The essential idea involves Ir-Ni precursor alloy nanoparticles that were selectively electrochemically dealloyed to form metallic core-shell NPs. Subsequently or simultaneously, they are selectively surface oxidized to form active metal-oxide hybrid core-shell NP catalysts with outstanding catalytic OER activities. Special emphasis is placed on the role of Ni in the alloy material. First, it enhances electrochemical active surface area (ECSA) of the catalysts during selective dealloying. Second, subsurface Ni caused electronic and strain effects resulting in higher intrinsic OER activity, and third, the high Ni core content significantly lowers the total Ir content of the catalyst. To the best of our knowledge, this is the first study on this family of dealloyed oxide-metal hybrid nanoparticle catalysts.

2. EXPERIMENTAL

2.1. Chemicals and materials

Commercially available reagents were used in the synthesis of the Ir and IrNi_x NPs as received. Nickel acetate tetrahydrate (Ni(ac)₂·4H₂O) was purchased from Alfa Aesar, and iridium (III) acetate (Ir(ac)₃) was purchased from Chempur. Oleic acid, oleylamine, 1,2-tetradecandiol, dichloromethane, dibenzyl ether and ethylene glycol were purchased from Sigma Aldrich. Vulcan XC-72 R carbon black (BET surface area ~ 250 m²/g) was purchased from Carbot.

2.2. Synthesis of Ir and IrNi_x bimetallic precursor nanoparticle alloys (PA-Ir and PA-IrNi)

Synthesis of supported IrNi_x bimetallic nanoparticles

Ni rich Ir-Ni bimetallic NPs were prepared using a previously reported polyol method⁴³ involving 1,2-tetradecadiol as reducing agent and oleylamine, oleic acid as capping ligands. The NPs were immobilized on high surface area carbon black Vulcan XC 72R from Carbot. Additional details about the synthesis procedure are given in the Supporting Information.

Synthesis of supported pure Ir nanoparticles

For comparison, carbon supported pure Ir nanoparticles were synthesized using ethylene glycol as reducing agent and solvent. The synthetic procedure was described elsewhere^{44,45} and detailed in Supporting Information.

2.3. Microscopic and spectroscopy characterization

XRD. XRD profiles were measured in Bragg–Brentano geometry in a D8 Advance X-ray diffractometer (Bruker AXS) using a Cu K α source, variable divergence slit, and a position sensitive device as detector.

ICP. ICP-OES compositional analysis was performed using a 715-ES-inductively coupled plasma (ICP) analysis system (Varian).

TEM. TEM micrographs were acquired using a FEI TECNAI G² 20 S-TWIN equipped with LaB6 cathode and GATAN MS794 P CCD camera.

STEM-EDX. High-resolution scanning transmission electron microscopy (STEM) and energy dispersive X-ray spectroscopy (EDX) line analysis were performed in FEI TITAN 80-300 electron microscope (300 kV) equipped with an image corrector (CEOS) and a high-angle annular dark field (HAADF) detector.

XPS-XAS. IrNi_x catalysts were characterized by X-ray photoelectron and X-ray absorption spectroscopy at the ISS beamline of the synchrotron facility BESSY of the Helmholtz-Zentrum Berlin.

More details to microscopic and spectroscopy characterization is given in Supporting Information.

2.4. Electrochemical measurements

Electrochemical setup

Electrochemical experiments were performed in a three-compartment glass cell with a rotating disk electrode (RDE, 5 mm in diameter of glassy carbon - GC, Pine Instrument) and a potentiostat (Biologic) at room temperature. A Pt-mesh and a Hg/Hg₂SO₄ electrode (in saturated K₂SO₄) were used as counter electrode and reference electrode, respectively. Details about working electrode preparation can be found in Supporting Information.

All electrochemical measurements were carried out in N₂-saturated 0.05M H₂SO₄ and repeated on three catalyst films for each catalyst.

Preparation of IrNi@IrO_x hybrid core-shell catalysts

The IrNi_x NP precursor alloys (PA- IrNi_x) were first electrochemically dealloyed to form dealloyed *metallic* core-shell NPs (“D- IrNi_x ”). Subsequently, they were selectively surface oxidized to form “SO- $\text{IrNi}@{\text{IrO}}_x$ ” metal oxide core-shell NPs. SO refers to the stepwise nature of the preparation (“SO- IrNi_x ”). The stepwise oxidized synthesis is depicted schematically in Figure 1 top. Alternatively, DO- $\text{IrNi}@{\text{IrO}}_x$ were prepared by directly, that is, coupled dealloying/oxidation (“DO- IrNi_x ”) as depicted in Figure 1 bottom. Note that in the following the SO- IrNi_x or DO- IrNi_x nomenclatures emphasize the stoichiometry of the parent precursor alloy, while the SO- $\text{IrNi}@{\text{IrO}}_x$ and DO- $\text{IrNi}@{\text{IrO}}_x$ nomenclature stress the chemical core-shell structure. The detailed electrochemical protocols for synthesizing IrNi_x core-shell nanoparticles are given in Supporting Information.

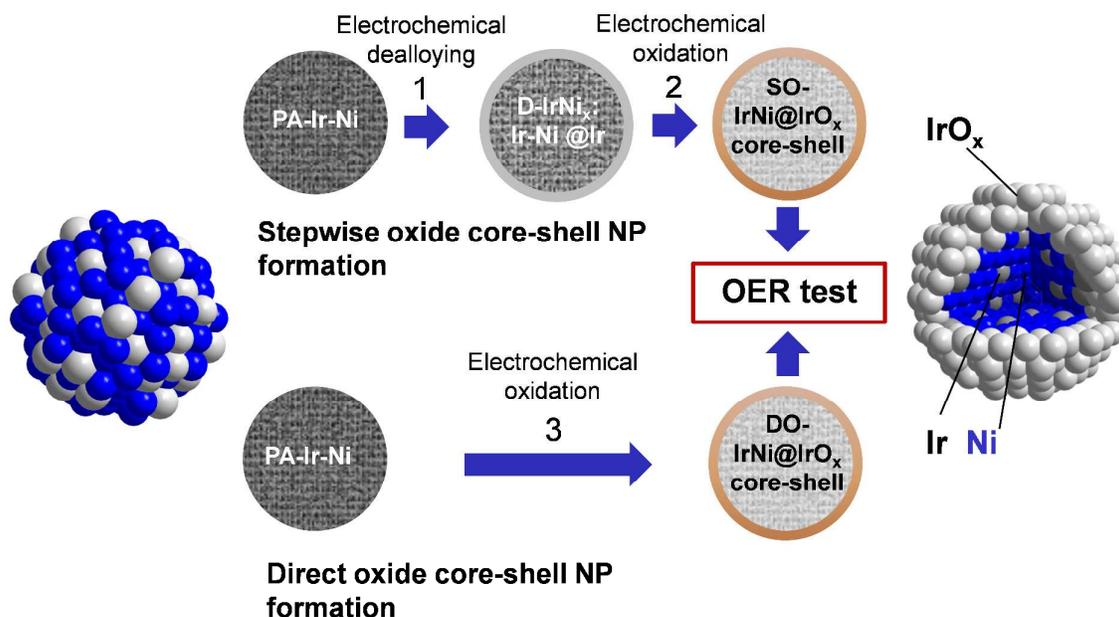


Figure 1. Synthetic protocol for the preparation of SO- $\text{IrNi}@{\text{IrO}}_x$ and DO- $\text{IrNi}@{\text{IrO}}_x$ hybrid core-shell nanoparticle catalysts. Precursor IrNi alloys (“PA- IrNi ”, and alloy scheme on left, blue: Ni, grey: Ir) are stepwise (SO) or directly (DO) dealloyed and surface oxidized. The “SO- IrNi_x ” or “DO- IrNi_x ” nomenclatures emphasize the original stoichiometry of the parent precursor alloy, while the “SO- $\text{IrNi}@{\text{IrO}}_x$ ” and “DO- $\text{IrNi}@{\text{IrO}}_x$ ” nomenclature stresses the chemical structure of the core-shell particles. A compositional depth-profile of the $\text{IrNi}@{\text{IrO}}_x$ particles is shown on right (light gray IrO_x , dark grey metallic Ir, blue metallic Ni).

Electrochemically active surface area (ECSA) evaluation. To estimate the ECSA of the Ir-Ni NP catalysts, the catalysts were immersed into the electrolyte under potential control and then scanned between the potentials of +0.05 V and +0.80 V at 20 mV/s for 3 cycles. ECSA was evaluated based on the H_{upd} peak in anodic scans, utilizing the previously reported conversion factor of $218 \mu\text{C}/\text{cm}^2$ between adsorbed hydrogen charge and real Ir based surface area.⁴⁶

Electrochemically accessible Ir redox sites(number of active sites) evaluation.

To estimate the number of accessible active sites, the catalysts were scanned between the potentials of + 0.4 V and + 1.4 V at 20 mV/s for 3 cycles. Number of active sites was estimated based on the anodic charge of Ir(III)-Ir(IV) peak with capacitance current subtraction.

Electrocatalytic activity of IrNi@IrO_x core-shell catalysts for the oxygen evolution reaction

The electrochemical catalytic activity of the IrNi@IrO_xNPs was recorded during cyclic sweep voltammetry between +1.0 V to +1.8 V with a scan rate of 5 mV/s under electrode rotation of 1600 rpm. PEIS (Potential Electrochemical Impedance Spectroscopy) was carried out before each OER measurement for IR correction. The Ir-mass based OER activity was evaluated at 0.25 V overpotential (+1.48 V vs. RHE) taking the average current density values of the IR-corrected and capacity-corrected anodic and cathodic scans. The capacitance currents were evaluated by the mean value of the current in the potential range of 1.0 to 1.23 V, where no faradaic process takes place. The specific OER activity was calculated taken the ratio of the IR- and capacitance- corrected currents at an overpotential of +0.25 V and the number of active Ir sites.

Stability test of IrNi@IrO_x core-shell catalysts

The catalytic stability was tested for the pure Ir NPs and directly oxidized IrNi_{3.3} core-shell NPs by chronopotentiometry technique, in which current density was held at 1 mA.cm⁻² for a period of 3 hours and corresponding potential was measured. The stability tested IrNi_{3.3} sample was then denoted as DO-IrNi_{3.3}-Stabil.

3. RESULTS AND DISCUSSION

3. 1. Synthesis and characterization of Ir-Ni precursor alloys (PA-IrNi_x)

Supported Ir-Ni bimetallic precursor alloy nanoparticles (denoted “PA-IrNi_x” in Figure 1) were synthesized with 3 different IrNi_x ratios ($x=2.3, 3.3, 5.7$). Supported pure Ir nanoparticles were used as benchmark catalysts. Morphology and structure of the PA-IrNi_xNPs were characterized by ICP-OES, powder X-ray diffraction and TEM.

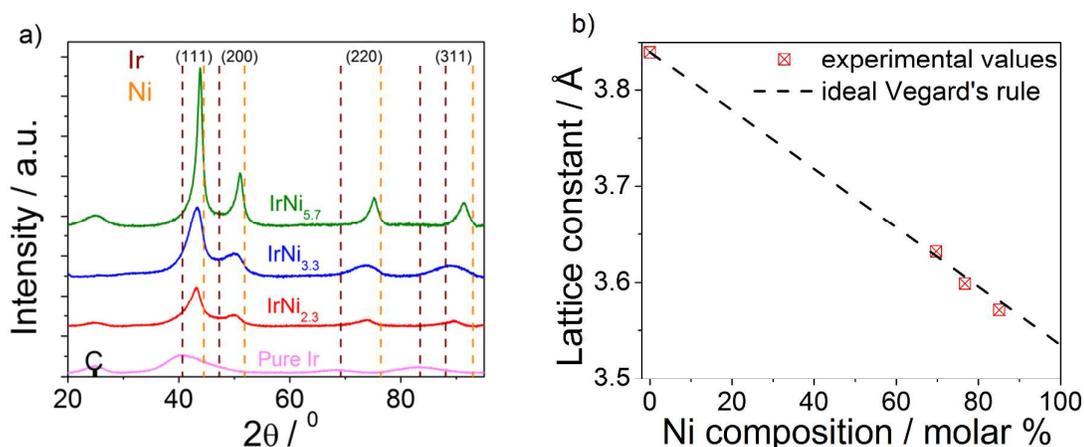


Figure 2. (a) Powder X-ray diffraction patterns of Ir, IrNi_{2.3}, IrNi_{3.3}, IrNi_{5.7} precursor alloy catalysts; C denotes a support reflection; vertical dashed lines indicate database reflections of pure Ir and pure Ni. (b) the relationship between lattice constant and Ni composition (red symbols) compared to Vegard's law (dashed line).

The XRD profiles of the IrNi_x and pure Ir NP catalysts (Fig. 2a) exhibit a peak pattern consistent with a face-centered cubic (fcc) crystal symmetry. There is no superlattice peak discernible below 35° indicating a substitutional solid solution structure throughout. Pure Ir, IrNi_{2.3} and IrNi_{3.3} materials exhibited single broad peaks suggesting homogeneous single-phase metallic (alloy) NPs with small crystallite size, on the other hand, IrNi_{5.7} showed sharper diffraction peaks, indicating larger crystalline size. All diffraction peaks of Ni-containing samples are shifted toward higher 2θ, indicating a contraction of the lattice with the increasing amount of smaller Ni atoms. The relationship between the lattice constant derived from the (111) planes and the composition of the annealed IrNi_x NPs (Fig. 2b) followed the Vegard's lattice constant–composition law surprisingly well.

Bright field TEM images and particle size histograms (Fig. 3) showed narrow particle size distribution of the pure Ir and IrNi_x bimetallic NPs up to the IrNi_{3.3} ratio. The mean particle size increased with increasing bulk Ni content. Composition, crystallite size and particle size of Ir and IrNi_x nanoparticles are tabulated in Table S1.

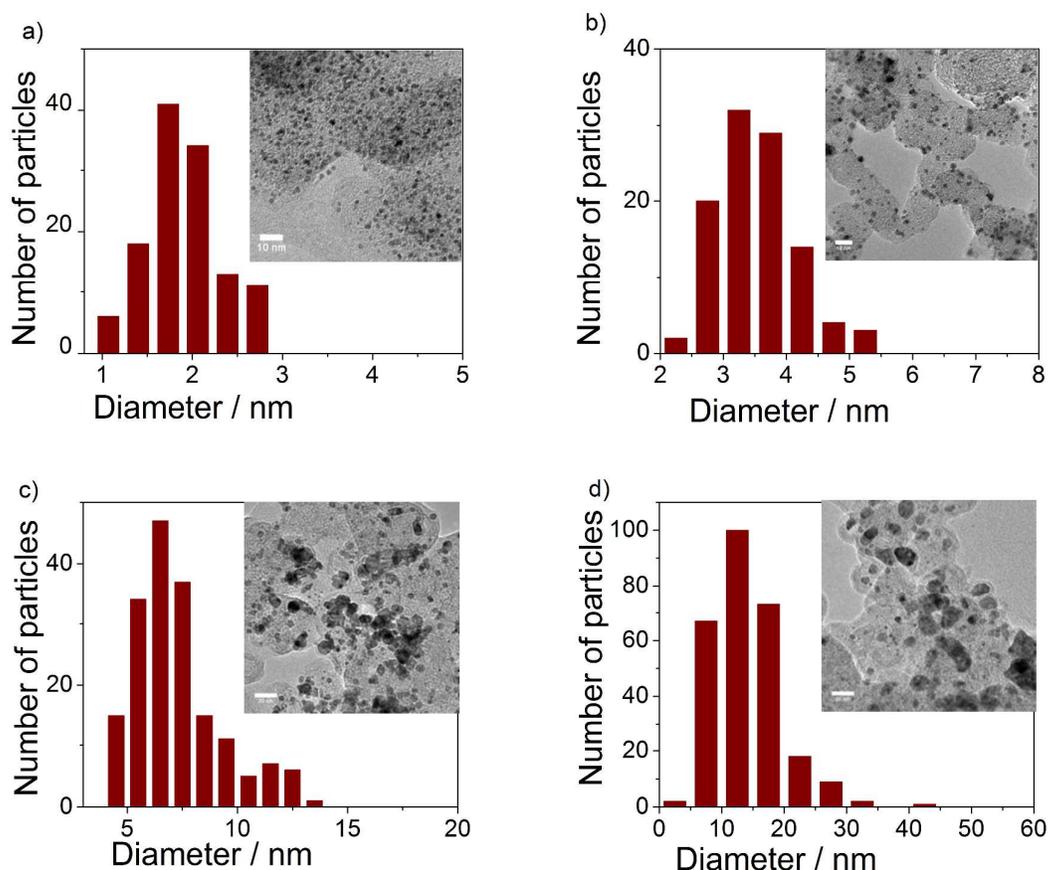


Figure 3. TEM images and particle size histograms of (a) Ir, (b) IrNi_{2.3}, (c) IrNi_{3.3}, and (d) IrNi_{5.7} precursor alloys.

3. 2. Preparation of IrNi@IrO_x hybrid core-shell nanoparticles

3.2.1 Dealloyed IrNi@Ir core-shell nanoparticles (“D-IrNi_x”)

As illustrated in Figure 1, the PA-IrNi_x (x = 2.3, 3.3, and 5.7) NPs were electrochemical dealloyed by potential cycling to form the corresponding dealloyed metallic IrNi@Ir core-shell nanoparticles, referred to as D-IrNi_{2.3}, D-IrNi_{3.3}, and D-IrNi_{5.7}, respectively. For comparison, the pure Ir NPs were treated in the same way.

Comparative inspection of the cyclic voltammograms (CVs) of the pristine PA-IrNi_x and dealloyed D-IrNi_x catalysts (Fig. 4a) showed the typical hydrogen surface electrochemistry of Ir manifested by underpotential hydrogen deposition (H_{upd}) and stripping peaks between +0.05 and +0.4 V. Unlike pure Ir, however, the first scans of the PA-IrNi_x catalysts (dashed lines) displayed an oxidative wave around +0.3 V (best seen for the Ni rich catalysts) evidencing the electrochemical dissolution of surface Ni atoms.³⁶ In the CV profiles of D-IrNi_x NPs (solid lines), however, these Ni oxidation features became absent restoring the typical pure Ir voltammetric shape; we can conclude that, at this point, the dissolution of

surface Ni atoms has yielded a stable metallic IrNi@Ir core-shell structure, which will be backed up below by spectroscopy.

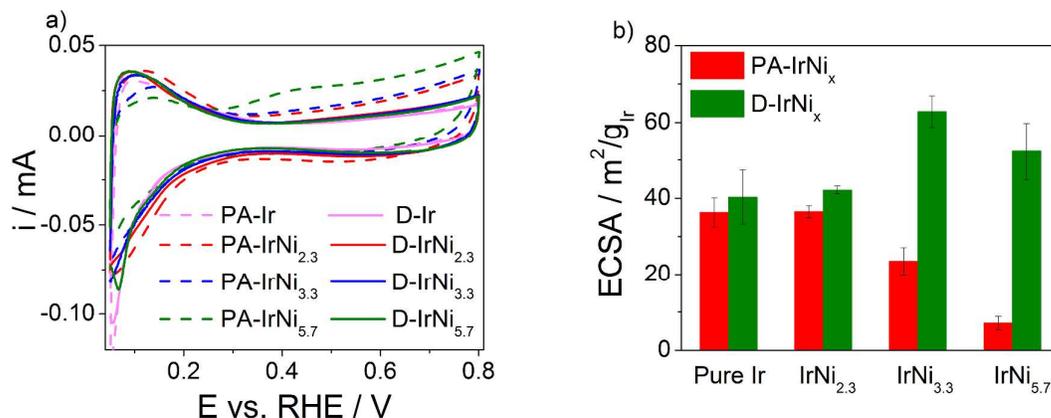


Figure 4. (a) Voltammetric profiles of the precursor alloy PA-IrNi_x NPs (dashed) and dealloyed D-IrNi_x NPs (solid) in N₂-saturated 0.05 M H₂SO₄ aqueous solution at 20 mVs⁻¹. (b) Comparison of the electrochemically active surface areas of PA-IrNi_x and D-IrNi_x NPs.

The initial electrochemical surface areas of the PA-IrNi_x NPs dropped with increasing Ni content (Figure 4b), which can be explained by increasing particle size and more Ni enriched particle surfaces. In contrast, dealloyed D-IrNi_{3.3} and D-IrNi_{5.7} NPs showed a 3 and 7 fold enhancement in the ECSA in comparison to their respective pristine state. The trend in ECSA of the dealloyed NPs with increasing Ni content is fully plausible considering that roughness and defect densities increase with more initial surface Ni content.³⁶

In order to confirm our hypothesis about the formation of a metallic core-shell structure, and to get further atomic-scale insight into the nanostructure of the catalysts before and after the dealloying, we performed high-angle annular dark-field imaging (HAADF)-STEM and STEM-EDX line scans of the IrNi_{3.3} material. Figure S1a shows dark field images of well-alloyed PA-IrNi_{3.3} catalyst particles with largely homogeneous chemical composition. On the other hand, dealloyed D-IrNi_{3.3} NPs (Figure S1b) exhibited bright Z-contrast shells surrounding darker inner parts (cores), evidencing the formation of IrNi@Ir core shell nanostructures. STEM-EDX line scans of PA-IrNi_{3.3} and D-IrNi_{3.3} NPs (Figure 5) corroborate these conclusions unambiguously.^{36,47} Upon dealloying, the homogeneous Ir, Ni distribution yields to a core shell type line scan of D-IrNi_{3.3} with two symmetric Ir shell peaks. Interestingly, the morphology of the dealloyed nanoparticles strongly depended on particle size, while smaller NPs favoring Ni-rich core-shell structures, larger NPs appear to undergo severe Ni leaching in their transition to core-shell structures.

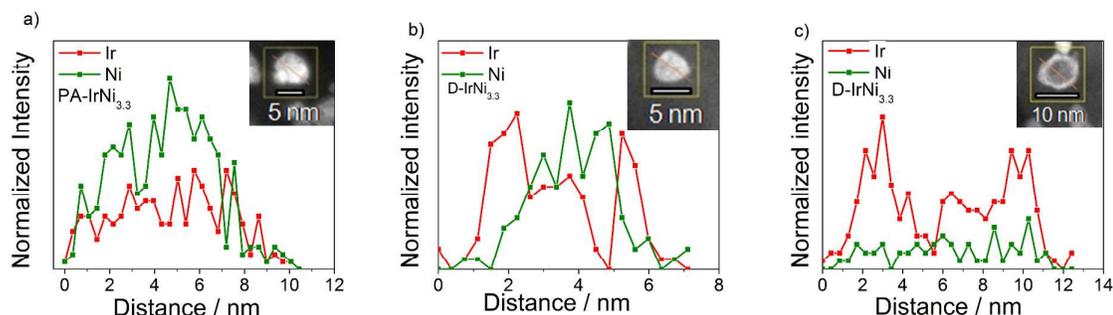


Figure 5. STEM-EDX line profiles of Ir and Ni in (a) PA-IrNi_{3.3} and (b and c) D-IrNi_{3.3}. The red arrows in the corresponding NPs (see insets) indicate the directions of the EDX line profiles.

To corroborate our core-shell structure hypothesis further for the metallic IrNi@Ir materials, we performed depth profiled X-ray Photoelectron Spectroscopy (XPS) at two different kinetic photoelectron energies (KE) as well as X-ray Absorption Near Edge Structure (XANES). Survey XPS spectra (FigureS2) confirmed the absence of impurities in the precursor alloy or any of the core-shell materials. The chemical state of the elements of interest (Ni and Ir) was examined in high resolution and depth resolved. The Ni 2p region of PA-IrNi_{3.3} (Figure 6a, red lines, solid: 210 eV KE, dotted: 550 eV KE) indicated the prevalence of oxidic Ni species highly reminiscent of NiO.⁴⁸ This is plausible given the high Ni content of the pristine NPs.

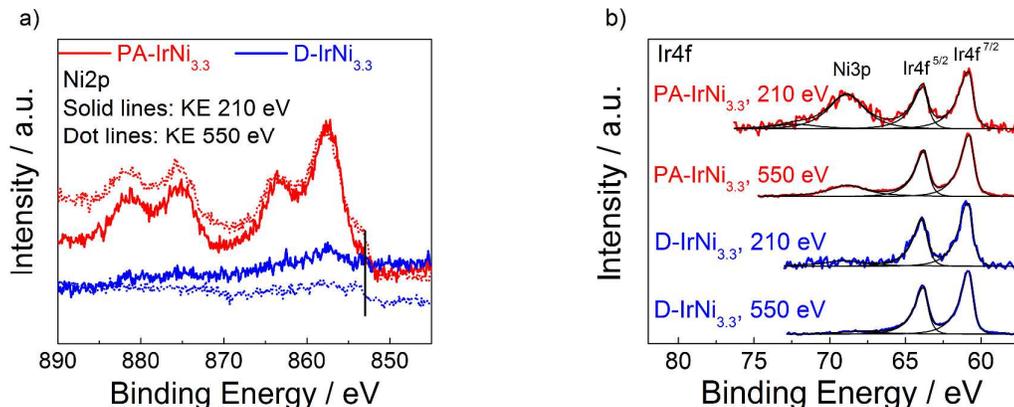


Figure 6. (a) Ni2p and (b) Ir4f XPS spectra of PA-IrNi_{3.3} and D-IrNi_{3.3} at photoelectron kinetic energy (KE) of 210 eV and 550 eV. Vertical line in a) marks the core level shift of metallic Ni.

A low binding-energy shoulder around 853 eV marked in Figure 6a indicates a minor metallic Ni contribution to the overall line shape. Depth profiling of Ni2p with two different kinetic energies (210 eV and 550 eV) clearly evidenced the metallic component of Ni being more abundant when probing deeper into the NPs. This is consistent with the notion that the core of the particle consists of metallic Ni, while the surface underwent oxidation. Song et al.⁴⁹ claimed the formation of ~1 nm oxide layer on Ni NPs occurred during the production or storage period, which might be caused by the non-uniform distribution of defects of nickel

crystal structures, i.e. areas with large defects could result in high oxidation levels and vice versa. Similarly, in our case, Ni in the near-surface region of PA-IrNi_{3.3} NPs was oxidized, probably in an amorphous XRD invisible state.

Upon dealloying, we recorded dramatically reduced NiO_x intensities (blue solid, 210 eV KE, and dotted lines, 550 eV KE), a nearly six-fold reduction in the estimated Ni/Ir molar ratio (see Table 1), and a sustained contribution of metallic Ni⁰ in the subsurface region. All these findings are in excellent agreement with expectations and microscopic data and strengthened our hypothesis as to the electrochemical formation of a metallic IrNi@Ir core-shell catalyst structure.

XANES Ni L edge spectra of PA-IrNi_{3.3} and D-IrNi_{3.3} (Figure S3a) revealed slight but characteristic differences, suggesting more NiO contribution (~855 eV) in the PA-IrNi_{3.3} catalyst, whereas more metallic Ni⁰ contributions in the D-IrNi_{3.3} material (satellite structure in Figure S3a and Figure S3b at 859 eV) in line with the XPS results.

The XPS Ir 4f region of the PA-IrNi_{3.3} and D-IrNi_{3.3} catalysts (see Figure 6b) indicated the prevalence of metallic Ir⁰ (BE ~60.8 eV). Interestingly, the Ir 4f region overlapped with the Ni 3p region. This is why Ni-related 3p peaks appear. These peaks corroborated our conclusions from the 2p region: Ni3p of the precursor alloy evidenced a NiO_x-covered surface. After dealloying, Ir remained in fully metallic state; however the intensity of Ni3p significantly decreased commensurate with the selective removal of Ni from the surface. Detailed quantitative evaluations using the XPS Ir 4f, Ni 2p and O 1s core levels at 550 eV KE in UHV are provided in Table 1. The increase in the O/(Ir+Ni) ratio upon dealloying (PA to D) despite the dissolution of NiO_x species is explained by the surface oxidation of the carbon support after potential cycling.

Table 1. Elemental ratios of pristine, metallic, and metal-oxide hybrid catalysts of the IrNi_{3.3} catalyst series derived from XPS at 550 eV kinetic energy.

Sample	Ni/Ir ratio at 550 eV KE	O/(Ir+Ni) ratio at 550 eV KE
PA-IrNi _{3.3}	6.1	1.6
D-IrNi _{3.3}	0.93	3.3
SO-IrNi _{3.3}	0.09	5.2
DO-IrNi _{3.3}	0.14	4.1
DO-IrNi _{3.3} -Stabil	0.045	6.0

3.2.2 SO-IrNi@IrO_x- and DO-IrNi@IrO_x hybrid core-shell nanoparticles

To prepare the catalytically active core shell structures, dealloyed IrNi@Ir metallic core shell particles (D-IrNi_{3.3}) were electrochemically cycled up to +1.5V where surface Ir atoms form irreversible oxide species.³ Given their stepwise oxidization preparation, these catalysts will be referred to as SO-IrNi_{3.3} to emphasize their precursor material, or equivalently as SO IrNi@IrO_x to emphasize their chemical structure. For comparison, the homogeneous precursor alloys PA-IrNi_{3.3} were subjected to the same cycling protocol in order to achieve simultaneous Ni dealloying and surface Ir oxidation. These samples are referred to as the directly oxidized catalysts, DO-IrNi_x, with a DO-IrNi@IrO_x core shell structure.

Figure S4a displays the evolution of the surface chemistry of the D-IrNi_{3.3} during voltammetric surface oxidation. The formation of irreversible Ir oxide is clearly evidenced by the diminishing hydrogen adsorption (+0.05 V to +0.4 V) with a strongly emerging Ir(III)/Ir(IV) redox wave (+0.8 V to +1.2 V). The characteristic Ir(III)/Ir(IV) redox couple (see Figure S4b) was used to estimate the molar amount of catalytically active Ir atoms for each catalyst as given in Table S2.^{50,51} While we are aware that the values in Table S2 likely represent an upper bound of the active OER sites, we used them to calculate intrinsic turnover-frequency (TOF) type kinetic rates, equivalent to lower bounds of the OER activity. DO-IrNi_x samples showed larger numbers of active Ir sites than SO-IrNi_x samples, presumably due to increased surface roughness and defects during the massive surface atomic rearrangements during simultaneous dealloying and oxidation.

To directly confirm the core shell structure of the SO-IrNi@IrO_x and DO-IrNi@IrO_x catalysts synchrotron-based depth-resolved XPS and XANES studies were performed. Flat spectra at both information depths in the XPS Ni 2p region of both SO-IrNi_{3.3} and DO-IrNi_{3.3} (Figure S5, green and orange lines) clearly proved an essentially complete removal of near surface Ni. Quantitative metal ratios are presented in Table 1. Similarly, Ni L Edge XANES spectra of both SO-IrNi_{3.3} and DO-IrNi_{3.3} (Figure S3a) resembled those of the NiO standards.

Depth resolved Ir4f core level spectra of the SO-IrNi_{3.3} and DO-IrNi_{3.3} catalysts (Figure 7) were clearly shifted to higher binding energy, consistent with the formation of surface IrO_x. The Ir XPS spectra at low KE 210 eV indicated that Ir atoms in the surface layer were completely oxidized, however, depth profiling at higher KE (550 and 1200 eV) also showed that Ir metallic components were present at larger information depth. This corroborates our structural hypothesis that the NP cores of the catalysts still contain metallic alloy. It should be noted here that the shape of the Ir4f peak lacks the characteristic asymmetry of IrO₂,⁵² suggesting that Ir oxide component here cannot be IrO₂ itself, but rather a mixture of ill-defined oxide-hydroxide, with potentially numerous defects and thus varying oxidation states.⁵³ Concerning the thickness and stability of the formed Ir oxide layer, as well as the real oxidation states of Ir during oxidation step and oxygen evolution reaction, further investigation is necessary.

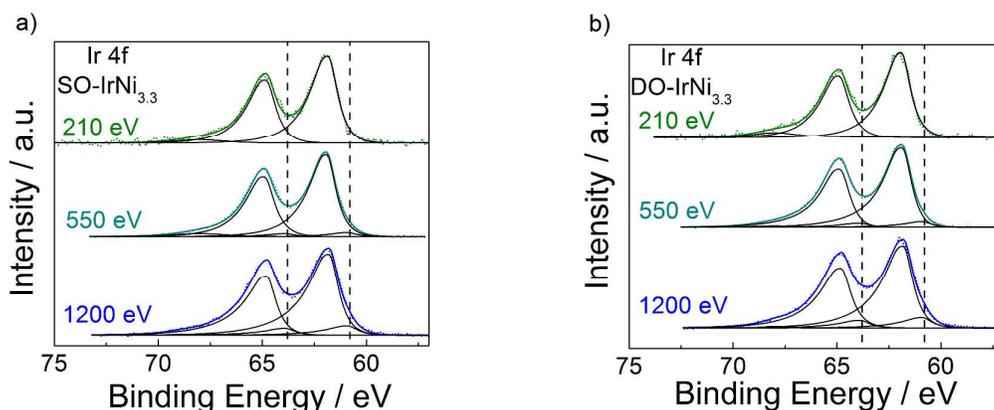


Figure 7. Ir 4f core level spectrum of (a) SO-IrNi_{3.3} and (b) DO-IrNi_{3.3} at photoelectron kinetic energy of 210, 550 and 1200 eV. Dash lines indicate peak position of metallic Ir as found in PA-IrNi_{3.3}.

All in all, the extensive and comprehensive HAADF-STEM, STEM-EDX, XANES, and XPS results evidence the successful synthesis of metallic and metal-oxide hybrid core-shell nanoparticle by selective removal of Ni and surface oxidation, which confirms our structural hypotheses illustrated in Figure 1.

3. 3. Electrochemical OER activity of IrNi@IrO_x core-shell nanoparticles

In order to correlate the structural and electronic parameters with surface catalytic activity for the oxygen evolution reaction (OER) activities under approximate conditions of membrane electrolyzers, the SO-IrNi@IrO_x and DO-IrNi@IrO_x core shell catalysts were subjected to a previously applied sweep voltammetry protocol in highly acidic electrolyte environment. The electrochemical activities were corrected for the uncompensated ohmic resistance of the set-up and electrolyte (IR correction) and for the capacitive current contribution. Finally the faradaic values were normalized by the Ir mass (mass specific activity) or on the molar amount of the accessible Ir redox centers (intrinsic activity). The sweep voltammetry of all catalyst along with their Ir-mass-based and specific activities at 0.25V overpotential are presented in Figure 8.

Quite obviously, all Ni-containing nanoparticle catalysts are significantly more active for the OER on a mass and active site-specific basis than pure Ir. The most active catalysts are the SO-IrNi_{3.3} and the DO-IrNi_{3.3} showing a 3 times higher mass activity compared to pure Ir. This implies a three times higher electrolyzer hydrogen output at constant input voltage. Directly oxidized core shell catalysts showed even slightly higher OER mass activity than that of stepwise oxidized samples, likely due to higher surface roughness and more catalytic sites.

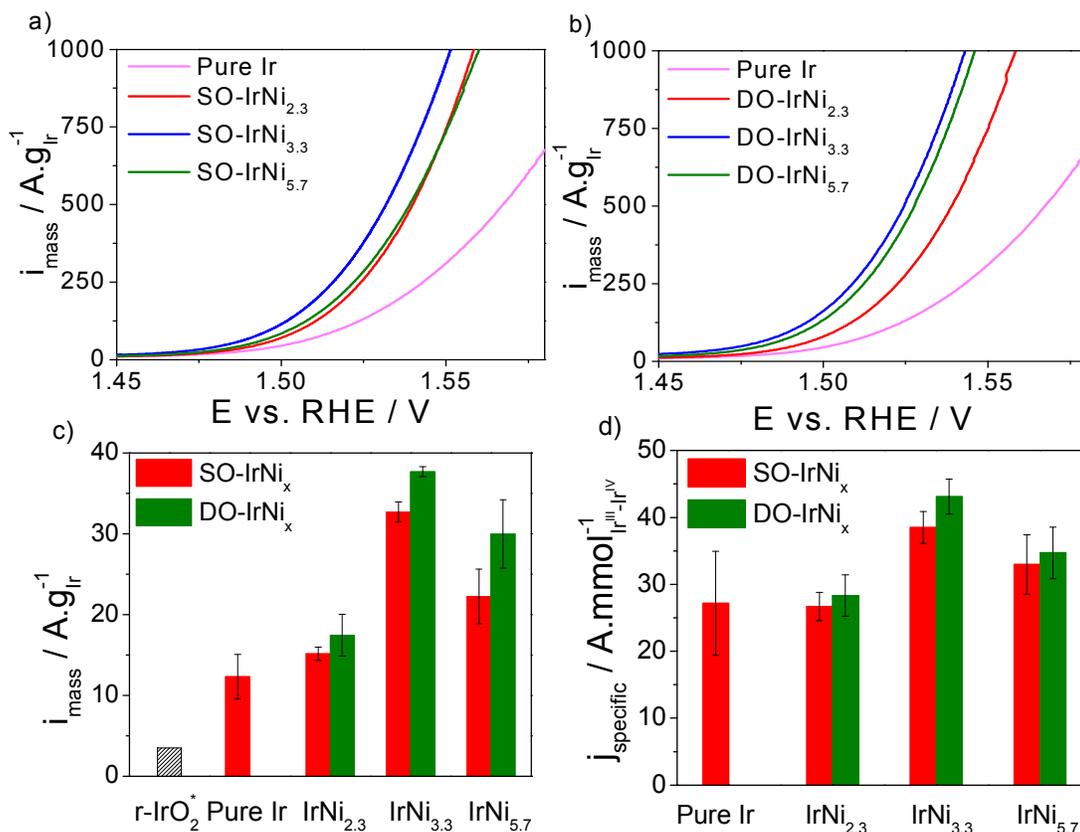


Figure 8. (a,b) Rotating Disk Electrode (RDE) sweep voltammetry and catalytic oxygen evolution reaction (OER) activities of stepwise oxidized (SO) IrNi_x and directly oxidized (DO) IrNi_x core shell nanoparticle catalysts, in comparison to pure Ir nanoparticles. (c) Ir mass based activities and (d) specific activities at 0.25V overpotential. Condition: 0.05M H₂SO₄, 1600 rpm, scan rate 5 mV/s. “r-IrO₂” denotes the Ir-mass based activity of IrO₂ rutile NPs at 0.25V overpotential.³⁷

In comparison to the open literature, our IrNi@IrO_x metal/oxide core shell catalysts nanoparticles showed substantially higher mass activity, even compared to a rutile iridium oxide particle catalyst (“r-IrO₂” in Figure 8), which is often taken as a benchmark Ir OER catalyst.³⁷ In particular, the DO-IrNi_{3.3} core shell catalyst exhibited a 10 times higher mass activity than r-IrO₂. Moreover, although ruthenium has been reported to be the most active catalyst for OER in acidic media, all of our Ni-containing catalysts are more active for OER than a commercial rutile r-RuO₂ nanoparticle catalyst (Ru mass activity of 11 A/g_{RuO2} or 14.5 A/g_{Ru} compared to 30-40 A/g_{Ir} for DO-IrNi_{3.3}, an almost 3 times activity enhancement).³⁷ At higher overpotentials, Wei Hu et al.⁵⁴ reported a noble metal mass activity of three-dimensional ordered macroporous IrO₂ of 500 A/g IrO₂ (or 583 A/g_{Ir}) at 1.60 V vs. RHE; for comparison, our DO-IrNi_{3.3} reaches this same value already at 1.530V vs. RHE corroborating the mass efficient OER catalysis.

In terms of Ir-site based specific activities, IrNi_{2,3} sample shows similar activity to pure Ir, while the two Ni-rich samples (IrNi_{3,3} and IrNi_{5,7}) showed substantially higher specific activity than Ir, however the enhancement remain below the mass-based value. This is explained by the fact that the number of active sites is an upper bound, rendering the specific activities a lower bound of actual OER rate.

In order to test stability of the nanocatalysts, chronopotentiometric measurements were carried out at room temperature in aqueous 0.05M H₂SO₄ electrolyte for the pure Ir and DO-IrNi_{3,3} nanoparticles (Figure 9). The potential increased slightly during the first 30 minutes and then remained constant throughout the tests, indicating stable behavior of the nanocatalysts.

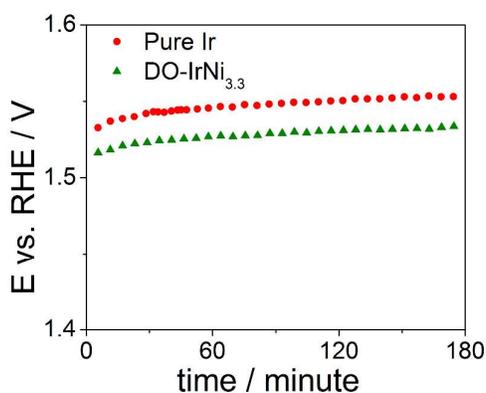


Figure 9. Chronopotentiometric measurements of pure Ir and directly oxidized (DO) IrNi_{3,3} core-shell nanoparticles at a current density of 1 mA.cm⁻².

XPS Ir4f spectra at KE 550 eV of directly oxidized IrNi_{3,3} before (denoted as DO-IrNi_{3,3}) and after stability test (denoted as DO-IrNi_{3,3}-Stabil) were compared (Figure S6). The Ir4f spectrum shapes were quite similar, though the fits suggest that a small metallic contribution of the DO-IrNi_{3,3} sample decreased further during the stability test. This indicates a prolonged oxidation of the particles from the outside in to even larger depths. Composition evaluation of DO-IrNi_{3,3}-Stabil (Table 1) gave an Ir/Ni ratio of 0.045, showing that some small Ni was further removed from the surface region during stability test.

4. CONCLUSIONS

We have presented a family of dealloyed metal-oxide hybrid (M₁M₂@M₁O_x) core@shell nanoparticle catalysts and have demonstrated, exemplified by the IrNi@IrO_x system, that this structural and compositional class of nanocatalysts offers substantial advances in terms of more efficient and less expensive electrolytic water splitting for acid electrolyzer applications.

Using extensive microscopic and spectroscopic analysis, largely with depth resolution, we followed the evolution of the IrNi@IrO_x metal oxide core shell particles step-by-step from

their IrNi bimetallic precursor stage, through the metallic core-shell stage to the final oxide shell/ alloy core architecture. The final catalysts have a nanometer scale almost pure IrO_x surface, while the inner core region became increasingly metallic and richer in Ni.

Correlating the structural characteristic with OER activity we concluded that the core shell catalyst perform substantially more active (about 3x higher compared to electrochemically oxidized Ir and commercial RuO_x, and 10x higher compared to rutile IrO_x) and thus thermodynamically more efficient on a noble metal mass and an active site basis during the electrocatalytic oxygen evolution.

The dealloyed metal-oxide hybrid (M₁M₂@M₁O_x) core shell catalyst concept represents a quite general strategy to lower the noble-metal content of nanoparticle oxide catalysts for other technologies or application, including but not limited to energy storage and conversion such as electrolyzers, supercapacitors, or metal-air batteries. Deploying the current catalysts in Polymer Electrolyte Membrane Electrolyzer Anodes, for instance, offers the prospect of lowering the required Ir content for a given hydrogen production rate by a full factor of 3.

ASSOCIATED CONTENT

Supporting Information. This material is available free of charge via the Internet at <http://pubs.acs.org>.

ACKNOWLEDGMENT

We thank Dr. M.G. Willinger for collaboration regarding the STEM-EDX data collection.

We thank the Zentraleinrichtung für Elektronenmikroskopie (Zelmi) of the Technical University Berlin for their support with TEM technique. Financial support by the German Research Foundation (DFG) through grant STR 596/3-1 under the Priority Program 1613 “Regeneratively formed fuels by light driven water splitting” is gratefully acknowledged.

Hong Nhan Nong acknowledges financial support by the Ministry of Education and Training of The Socialist Republic of Vietnam (MOET) and the German Academic Exchange Service (DAAD).

This project received partial funding from the Federal Ministry of Education and Research under the grant reference number 03SF0433A “MEOKATS”. Responsibility for the contents of this publication lies with the author.

REFERENCES

- (1) *Chemical Energy Storage* Schloegl, R., Ed.; De Gruyter Berlin, 2013.
- (2) Forgie, R.; Bugosh, G.; Neyerlin, K. C.; Liu, Z. C.; Strasser, P. *Electrochem. Solid State Lett.***2010**, *13*, D36.
- (3) Reier, T.; Oezaslan, M.; Strasser, P. *ACS Catalysis***2012**, *2*, 1765.
- (4) Bergmann, A.; Zaharieva, I.; Dau, H.; Strasser, P. *Energy Environ. Sci.***2013**, *6*, 2745.
- (5) Neyerlin, K. C.; Bugosh, G.; Forgie, R.; Liu, Z.; Strasser, P. *J. Electrochem. Soc.***2009**, *156*, B363.
- (6) Dau, H.; Limberg, C.; Reier, T.; Risch, M.; Roggan, S.; Strasser, P. *ChemCatChem***2010**, *2*, 724.
- (7) Hoare, J. P. *The Electrochemistry of Oxygen*; Wiley New York, 1968.
- (8) O'Hayre, R. C., S.-W.; Colella, W.; Prinz, F. B., *Fuel Cell Fundamentals*; Wiley: New York, 2006.
- (9) Wen, T. C.; Hu, C. C. *J. Electrochem. Soc.***1992**, *139*, 2158.
- (10) Kuznetsov, V. V.; Chepeleva, S. A.; Gol'din, M. M.; Kudryavtsev, V. N.; Fateev, V. N.; Volkov, A. G. *Russ. J. Electrochem.***2005**, *41*, 933.
- (11) Ma, H.; Liu, C.; Liao, J.; Su, Y.; Xue, X.; Xing, W. *Journal of Molecular Catalysis A: Chemical***2006**, *247*, 7.
- (12) Marshall, A.; Børresen, B.; Hagen, G.; Sunde, S.; Tsyppkin, M.; Tunold, R. *Russ. J. Electrochem.***2006**, *42*, 1134.
- (13) Marshall, A.; Børresen, B.; Hagen, G.; Tsyppkin, M.; Tunold, R. *Electrochimica Acta***2006**, *51*, 3161.
- (14) Panić, V. V.; Dekanski, A. B.; Milonjić, S. K.; Mišković-Stanković, V. B.; Nikolić, B. Ž. *Russ. J. Electrochem.***2006**, *42*, 1055.
- (15) Beer, H. B. United States, 1972; Vol. 3,632,498.
- (16) Beer, H. B. United States, 1973; Vol. 3, 711, 385.
- (17) Ma, L.; Sui, S.; Zhai, Y. *Int. J. Hydrog. Energy***2009**, *34*, 678.
- (18) Millet, P.; Ngameni, R.; Grigoriev, S. A.; Mbemba, N.; Brisset, F.; Ranjbari, A.; Etievant, C. *Int. J. Hydrog. Energy***2010**, *35*, 5043.
- (19) Millet, P.; Mbemba, N.; Grigoriev, S. A.; Fateev, V. N.; Aukauloo, A.; Etiévant, C. *Int. J. Hydrog. Energy***2011**, *36*, 4134.
- (20) Song, S.; Zhang, H.; Ma, X.; Shao, Z.; Baker, R. T.; Yi, B. *Int. J. Hydrog. Energy***2008**, *33*, 4955.
- (21) Nørskov, J. K.; Bligaard, T.; Rossmeisl, J.; Christensen, C. H. *Nat Chem***2009**, *1*, 37.
- (22) Man, I. C.; Su, H.-Y.; Calle-Vallejo, F.; Hansen, H. A.; Martínez, J. I.; Inoglu, N. G.; Kitchin, J.; Jaramillo, T. F.; Nørskov, J. K.; Rossmeisl, J. *ChemCatChem***2011**, *3*, 1159.
- (23) Rossmeisl, J.; Qu, Z. W.; Zhu, H.; Kroes, G. J.; Nørskov, J. K. *Journal of Electroanalytical Chemistry***2007**, *607*, 83.
- (24) Rossmeisl, J.; Logadottir, A.; Nørskov, J. K. *Chemical Physics***2005**, *319*, 178.
- (25) Rossmeisl, J.; Dimitrievski, K.; Siegbahn, P.; Nørskov, J. K. *The Journal of Physical Chemistry C***2007**, *111*, 18821.
- (26) Greeley, J.; Nørskov, J. K.; Mavrikakis, M. *Annual Review of Physical Chemistry***2002**, *53*, 319.
- (27) Greeley, J.; Stephens, I. E. L.; Bondarenko, A. S.; Johansson, T. P.; Hansen, H. A.; Jaramillo, T. F.; Rossmeisl, J.; Chorkendorff, I.; Nørskov, J. K. *Nat Chem***2009**, *1*, 552.
- (28) Strasser, P.; Koh, S.; Greeley, J. *Phys. Chem. Chem. Phys.***2008**, *10*, 3670.
- (29) Ferrin, P.; Nilekar, A. U.; Greeley, J.; Mavrikakis, M.; Rossmeisl, J. *Surface Science***2008**, *602*, 3424.
- (30) Stamenkovic, V.; Mun, B. S.; Mayrhofer, K. J. J.; Ross, P. N.; Markovic, N. M.; Rossmeisl, J.; Greeley, J.; Nørskov, J. K. *Angewandte Chemie International Edition***2006**, *45*, 2897.
- (31) Greeley, J.; Nørskov, J. K.; Kibler, L. A.; El-Aziz, A. M.; Kolb, D. M. *ChemPhysChem***2006**, *7*, 1032.
- (32) Greeley, J.; Jaramillo, T. F.; Bonde, J.; Chorkendorff, I.; Nørskov, J. K. *Nat Mater***2006**, *5*, 909.
- (33) Andersson, M. P.; Bligaard, T.; Kustov, A.; Larsen, K. E.; Greeley, J.; Johannessen, T.; Christensen, C. H.; Nørskov, J. K. *Journal of Catalysis***2006**, *239*, 501.
- (34) Greeley, J.; Nørskov, J. K. *Surface Science***2005**, *592*, 104.
- (35) Greeley, J.; Mavrikakis, M. *Nat Mater***2004**, *3*, 810.

- (36) Gan, L.; Heggen, M.; Rudi, S.; Strasser, P. *Nano Lett.* **2012**, *12*, 5423.
399. (37) Lee, Y.; Suntivich, J.; May, K. J.; Perry, E. E.; Shao-Horn, Y. *J. Phys. Chem. Lett.* **2012**, *3*, 399.
- (38) Nakagawa, T.; Beasley, C. A.; Murray, R. W. *J. Phys. Chem. C* **2009**, *113*, 12958.
- (39) Zhao, Y. X.; Hernandez-Pagan, E. A.; Vargas-Barbosa, N. M.; Dysart, J. L.; Mallouk, T. E. *J. Phys. Chem. Lett.* **2011**, *2*, 402.
- (40) Marshall, A.; Haverkamp, R. *Journal of Materials Science* **2012**, *47*, 1135.
- (41) Ortel, E.; Reier, T.; Strasser, P.; Kraehnert, R. *Chem. Mat.* **2011**, *23*, 3201.
- (42) Oezaslan, M.; Hasche, F.; Strasser, P. *J. Phys. Chem. Lett.* **2013**, *4*, 3273.
271. (43) Ahrenstorf, K.; Albrecht, O.; Heller, H.; Kornowski, A.; Görlitz, D.; Weller, H. *Small* **2007**, *3*, 271.
- (44) Ribeiro, V. A.; Correa, O. V.; Neto, A. O.; Linardi, M.; Spinacé, E. V. *Applied Catalysis A: General* **2010**, *372*, 162.
- (45) Rudi, S.; Tuae, X.; Strasser, P. *Electrocatalysis*, 1.
217. (46) Woods, R. *Journal of Electroanalytical Chemistry and Interfacial Electrochemistry* **1974**, *49*, 217.
- (47) Cui, C.; Gan, L.; Li, H.-H.; Yu, S.-H.; Heggen, M.; Strasser, P. *Nano Lett.* **2012**.
- (48) Alders, D.; Voogt, F. C.; Hibma, T.; Sawatzky, G. A. *Physical Review B* **1996**, *54*, 7716.
- (49) Song, P.; Wen, D.; Guo, Z. X.; Korakianitis, T. *Phys. Chem. Chem. Phys.* **2008**, *10*, 5057.
- (50) De Pauli, C. P.; Trasatti, S. *Journal of Electroanalytical Chemistry* **1995**, *396*, 161.
- 30, 625. (51) Lassali, T. A. F.; Boodts, J. F. C.; Bulhões, L. O. S. *Journal of Applied Electrochemistry* **2000**, *30*, 625.
- (52) Wertheim, G. K.; Guggenheim, H. J. *Physical Review B* **1980**, *22*, 4680.
- (53) Juodkazyte, J.; Sebeke, B.; Valsiunas, I.; Juodkazis, K. *Electroanalysis* **2005**, *17*, 947.
- (54) Hu, W.; Wang, Y.; Hu, X.; Zhou, Y.; Chen, S. *J. Mater. Chem.* **2012**, *22*, 6010.

TOC

