

Chemical Science

Accepted Manuscript



This is an *Accepted Manuscript*, which has been through the Royal Society of Chemistry peer review process and has been accepted for publication.

Accepted Manuscripts are published online shortly after acceptance, before technical editing, formatting and proof reading. Using this free service, authors can make their results available to the community, in citable form, before we publish the edited article. We will replace this *Accepted Manuscript* with the edited and formatted *Advance Article* as soon as it is available.

You can find more information about *Accepted Manuscripts* in the [Information for Authors](#).

Please note that technical editing may introduce minor changes to the text and/or graphics, which may alter content. The journal's standard [Terms & Conditions](#) and the [Ethical guidelines](#) still apply. In no event shall the Royal Society of Chemistry be held responsible for any errors or omissions in this *Accepted Manuscript* or any consequences arising from the use of any information it contains.



www.rsc.org/chemicalscience

ARTICLE

Photoinduced Single-Crystal-to-Single-Crystal Phase Transition and Photosalient Effect of a Gold(I) Isocyanide Complex with Shortening Intermolecular Auophilic Bonds

Cite this: DOI: 10.1039/x0xx00000x

Received 00th January 2012,
Accepted 00th January 2012

DOI: 10.1039/x0xx00000x

www.rsc.org/

Tomohiro Seki, Kenta Sakurada, Mai Muromoto, and Hajime Ito*

We report the first photoinduced single-crystal-to-single-crystal (SCSC) phase transition of a gold complex that involves shortening of intermolecular auophilic bonds. This is also the first solid state photochromism of a gold complex. Upon UV irradiation, blue-emitting crystals of gold(I) isocyanide complex **1** (**1B**) transform into the weakly yellow-emitting polymorph **1Y**. X-ray diffraction analyses reveal that this phase transition proceeds in an SCSC manner. After phase transition from **1B** to **1Y**, the intermolecular Au...Au separation decreases from 3.5041(14) to 3.2955(6) Å, resulting in a red-shifted emission. The photoinduced shortening of the auophilic bond in the excited state initiates the change in crystal structure from **1B** to **1Y**. Moreover, crystal **1B** showed a photosalient effect: the **1B** crystals jump upon irradiation with strong UV light owing to the phase transition into **1Y**. The auophilic bond formation in the crystal generates the mechanical movement of the crystal.

Introduction

Photochromic organic solid materials attract considerable attention because of their wide applicability in sensing and recording devices.¹ Changes in the solid structures of these materials are generally based on photochromic components exhibiting intramolecular photoinduced configurational alterations (e.g., stilbene² and azobenzene³) and intramolecular covalent bond formation/cleavage (e.g., diarylethene⁴ and spiropyran⁵). Moreover, some organometallic complexes show solid-state photoinduced molecular structural alteration through isomerization of their ligands.⁶ However, photochromic materials whose properties are based on changes in intermolecular noncovalent bonding interactions without chemical transformation or configurational alternation upon photoirradiation remain rare.

The luminescent properties of many gold complexes are sensitive to their molecular arrangements and intermolecular interaction patterns.⁷ In particular, auophilic interactions, which are noncovalent interactions between Au atoms, strongly affect the emission properties of gold complexes in both the solid state and solution.⁸ Gold complexes are currently considered to be an important research field because of their unique structural and luminescent properties and responses to stimuli.⁹ Single-crystal-to-single-crystal (SCSC) phase transitions of gold complexes can be induced by heating,¹⁰ pressure,¹¹ and contact with a solvent.¹² We recently reported that mechanical stimulation or solid seeding can also induce SCSC phase transitions of gold(I) isocyanide complexes.¹³ Theoretically, photoirradiation can change the auophilic bonding structure.¹⁴ Indeed, transient shortening and rapid

relaxation of auophilic bonding in solution has been reported.¹⁵ However, solid-state phase changes of gold complexes where the photoinduced change of auophilic interactions is a dominant factor have not been reported.¹⁶

Here, we report the first photoinduced SCSC phase transition of a gold(I) complex that is accompanied by a decrease of Au...Au distance. To the best of our knowledge, this report is also the first observation of solid-state photochromism in a gold complex.¹⁶ The colorless **1B** phase, a crystallized form of gold(I) isocyanide complex **1**, exhibits blue photoluminescence (Fig. 1). Strong UV irradiation transforms **1B** to the yellow **1Y** phase, which exhibits weak yellow emission upon excitation (Fig. 1b and c). X-ray diffraction (XRD) analyses confirmed the SCSC phase transition from **1B** to **1Y**. A comparison of these crystal structures revealed the shortening of the distance between Au atoms after the photoinduced SCSC phase transition. It is proposed that the SCSC phase transition of **1** proceeds through tightening of the auophilic bonds in the excited state, which has not been observed previously. Indeed, the DFT calculations based on the crystal structures indicate that the shortening of the Au...Au distance caused the red-shifted emission in **1Y** phase generated after photoirradiation of **1B**. In addition, **1B** exhibits a surprising "photosalient effect" upon irradiation with stronger UV light. To our knowledge, this report is the first observation of the photosalient effect which occurs through phase transition between polymorphs without chemical transformation or configurational alternations.¹⁷


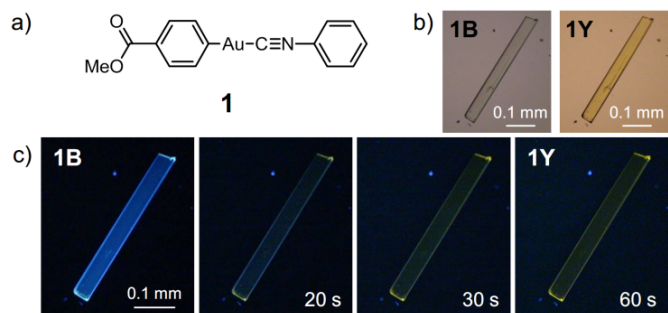


Fig. 1 a) Structure of complex **1**. b) Photographs of **1B** and **1Y** under ambient light. c) A series of photographs of the SCSC phase transition from **1B** to **1Y** induced by strong photoirradiation (367 nm, approx. 100 mW·cm⁻²) taken under excitation at 365 nm.

Results and discussion

Photoinduced single-crystal-to-single-crystal phase transition

Complex **1** was prepared by modification of our reported procedures (Scheme 1).^{13,18} Briefly, the (4-methoxycarbonylphenyl)zinc(II) iodide reagent¹⁹ was mixed with chloro(phenyl isocyanide) gold(I) at 0 °C under a nitrogen atmosphere for 1 h to afford analytically pure **1** in 98% yield after subsequent purification by column chromatography and recrystallization from CH₂Cl₂/hexane. **1** was fully characterized using ¹H and ¹³C NMR spectroscopy, high-resolution mass spectrometry and elemental analysis [see the Electronic Supplementary Information (ESI)]. The monomer of **1** in CH₂Cl₂ shows photoluminescence in the UV region and does not exhibit photochromism (Fig. S1 and S2).

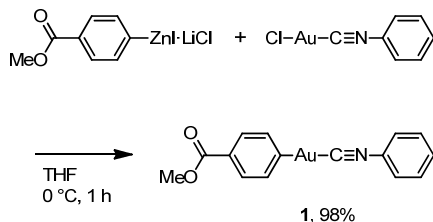

Scheme 1 Synthesis of **1**.

Crystallization of complex **1** from CH₂Cl₂/hexane gave the blue-emitting polymorph **1B** (Fig. 1c). The photoluminescence spectrum of **1B** obtained upon excitation at 370 nm shows an emission band ranging from 400 to 700 nm with a maximum at 448 nm (blue solid line in Fig. 2).²⁰ The absolute luminescent quantum yield Φ_{em} and average luminescent lifetime τ_{av} of **1B** were determined to be 2.2% and 34.2 μ s, respectively (Fig. S3 and Table S2). The excitation spectrum of **1B** detected at 450 nm confirmed the contribution from the absorption band at 371 nm (blue dashed line in Fig. 2). Both excitation and emission bands of **1B** are red shifted from those of monomeric **1** in solution because of the crystal packing in the solid phase.

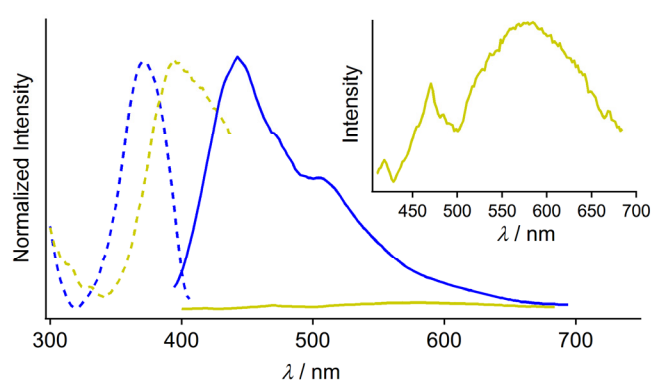


Fig. 2 Normalized excitation (blue dashed line, detected at 450 nm) and emission (blue solid line, λ_{ex} = 370 nm) spectra of **1B**. Normalized excitation (greenish yellow dashed line, detected at 590 nm) and emission (greenish yellow solid line, λ_{ex} = 390 nm) spectra of **1Y**. The inset shows a magnified emission spectrum of **1Y**.

The crystalline structure of polymorph **1B** was characterized using single-crystal X-ray analysis. A single crystal of **1B** suitable for the XRD required crystallization in the dark.^{21,22} **1B** crystallized in monoclinic space group *P*-1 [R_1 = 8.67%, wR_2 = 24.96%, GOF = 1.106, a = 7.381(2) Å, b = 11.755(2) Å, c = 15.940(3) Å, α = 102.912(5)°, β = 92.025(5)°, γ = 100.595(5)°, Z = 4, V = 1320.8(4) Å³, d = 2.189 g·cm⁻³] (Table 1 and S3). In many cases, the R_1 and wR_2 values observed in **1B** were slightly worse than those observed in **1Y**, even when the same crystal was used for **1B** and **1Y**. This result could be attributed to the small contamination of photoinduced phase **1Y** in the original **1B**. X-ray, elemental and thermal gravimetric analyses and ¹H NMR measurements revealed that no solvent was included in the crystalline lattice of **1B** (Fig. S5 and S6 and Table S3 and S4). There are two crystallographically independent molecules in the lattice that exhibit dihedral angles between two intramolecular benzene rings of 26.76° and 56.04° (Fig. 3a). These molecules form dimers with a head-to-tail orientation and an intermolecular Au...Au distance of 3.5041(14) Å, indicating the formation of a very weak aurophilic bond.^{7,8} These dimers further stack with a longer Au...Au distance of 4.451(2) Å and contact with adjacent columns to form flat sheet-like layer structures (Fig. 3b and c).

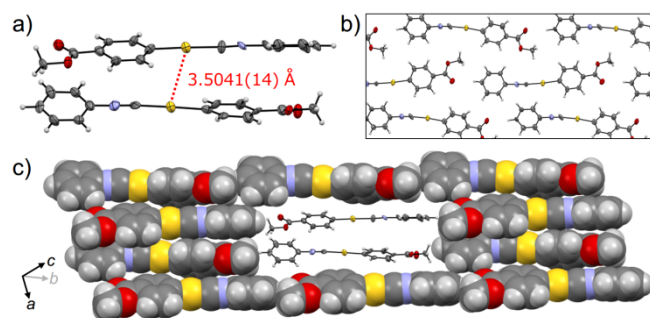


Fig. 3 The single-crystal structure of **1B**. a) ORTEP representation of a dimer unit. b) ORTEP and c) space-filling representations of packing structure viewed along the directions roughly parallel (in b) and perpendicular (in c) to the aurophilic bonding axis. A dimer unit in c) is shown as an ORTEP

diagram to aid visualization. The crystallographic axes a , b , and c are depicted by arrows.

Table 1 Summary of single crystal data of **1B** and **1Y**.

	1B	1Y
CCDC name	CCDC 987280	CCDC 987281
Crystal system	triclinic	triclinic
Space group	$P-1$ (#2)	$P-1$ (#2)
$a / \text{\AA}$	7.381(2)	6.0552(5)
$b / \text{\AA}$	11.755(2)	7.0297(6)
$c / \text{\AA}$	15.940(3)	15.969(2)
$\alpha / ^\circ$	102.912(5)	96.315(3)
$\beta / ^\circ$	92.025(5)	93.979(3)
$\gamma / ^\circ$	100.595(5)	90.279(3)
$V / \text{\AA}^3$	1320.8(4)	673.9(1)
Z value	4	2
$V/Z / \text{\AA}^3$	330.2	337.0
$D_{\text{calc}} / \text{g}\cdot\text{cm}^{-3}$	2.189	2.145
Residual $R_1 / \%$ ^a	8.67	5.42
Residual $wR_2 / \%$ ^b	24.96	13.30
GOF ^c	1.106	1.045

^a: For data with $I > 2.00\sigma(I)$. ^b: For all reflection data. ^c: Goodness of Fit. Residual electron density is mostly located near Au atoms because Au atoms have many electrons. See Supplementary Table S3 for more detail.

The photophysical properties of polymorph **1B** were altered upon photoirradiation. Upon photoirradiation of **1B** using a fluorescence microscope equipped with an ultrahigh-pressure mercury lamp (367 nm, approx. $100 \text{ mW}\cdot\text{cm}^{-2}$) for 60 s at room temperature, the emission color of the crystals gradually changed from blue to yellow because of the formation of polymorph **1Y** (Fig. 1c). During this process, the diffraction pattern also gradually changed (Fig. S7), and the transparency of the crystal was retained (Fig. 1b and S8). UV light with a lower power density requires a longer irradiation time to induce a transformation from **1B** to **1Y** (Table S1). As shown in Fig. 2, the intensity of emission from **1B** decreases under strong UV irradiation and becomes almost zero after 60 s under strong UV irradiation. The resulting **1Y** phase exhibits weak emission with a structureless maximum at 580 nm (inset in Fig. 2). This band is red shifted from that of **1B** by 132 nm. The polymorph **1Y** exhibits a very low Φ_{em} of $\sim 0.5\%$ (Table S2). The emission lifetime τ_{av} of **1Y** is 0.685 μs , which is a decrease of $\sim 2\%$ upon phase transition (Fig. S3 and Table S2). The excitation spectrum of **1Y** detected at 590 nm revealed the contribution from the absorption band at 394 nm (greenish yellow dashed line in Fig. 2). Because the excitation maximum is red shifted by 23 nm upon phase transition, the crystal becomes yellow (Fig. 1b).

XRD analyses indicate that **1Y** is formed through the SCSC phase transition of **1B**. The photoinduced SCSC phase transition reproducibly occurred from single crystals of **1B** to give **1Y** crystals of suitable quality for single-crystal X-ray analysis. After the single crystal X-ray analysis of **1B**, it was photoirradiated (367 nm, approx. $100 \text{ mW}\cdot\text{cm}^{-2}$, 60 s) to yield a crystal of **1Y**, and this sample was of sufficient quality for single crystal X-ray analysis [$P-1$, $R_1 = 5.42\%$, $wR_2 = 13.30\%$, $\text{GOF} = 1.045$, $a = 6.0552(5) \text{ \AA}$, $b = 7.0297(6) \text{ \AA}$, $c = 15.969(2) \text{ \AA}$, $\alpha = 96.315(3)^\circ$, $\beta = 93.979(3)^\circ$, $\gamma = 90.279(3)^\circ$, $Z = 2$, $V = 673.9(1) \text{ \AA}^3$, $d = 2.145 \text{ g}\cdot\text{cm}^{-3}$] (Table 1 and S3). X-ray, elemental, and thermal gravimetric analyses and ^1H NMR measurements revealed that decomposition of these compounds does not take place and that solvent is not included (Fig. S5 and

S6 and Table S3 and S4). **1Y** has a monoclinic space group $P-1$. Like **1B**, the molecules form dimers with a head-to-tail orientation. The intermolecular $\text{Au}\cdots\text{Au}$ distance in the dimer of **1Y** is $3.2955(6) \text{ \AA}$, which is a marked decrease of ca. 0.2 \AA upon crystalline structural transformation. This shorter distance indicates a stronger aurophilic bond in **1Y** compared with that in **1B**. The dihedral angle between the two benzene rings in a molecule is 47.01° (Fig. 4a). The isocyanide benzene ring participates in weak CH/π interactions with the adjacent benzene ring on the Au atom. The molecules adopt a severely distorted conformation: the structure of $-\text{Au}-\text{C}\equiv\text{N}-$ moieties deviate markedly from linearity, unlike in **1B**. The thermodynamic destabilization arising from the distortion of the molecule is probably compensated for by the formation of aurophilic bonds and weak CH/π interactions in the solid lattice (Fig. 4b and c).

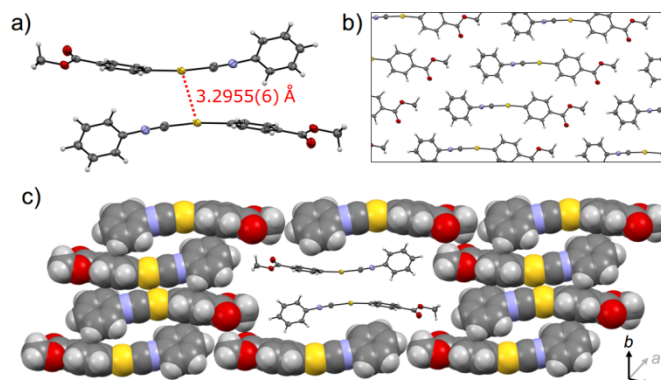


Fig. 4 The single-crystal structure of **1Y**. a) ORTEP representation of a dimer unit. b) ORTEP and c) space-filling representations of packing structure viewed along the directions roughly parallel (in b) and perpendicular (in c) to the aurophilic bonding axis. A dimer unit in c) is shown as an ORTEP diagram to aid visualization. Crystallographic axes a , b , and c are depicted by arrows.

Mechanistic studies of photoinduced single-crystal-to-single-crystal phase transition

To obtain further insights into the SCSC phase transition of **1**, a series of control experiments was performed. Upon heating, neither **1B** nor **1Y** showed thermal polymorph transformation, and both chemically decomposed at ca. 120°C (Fig. S9). The corresponding endothermic peaks were found in the differential scanning calorimetry profiles at 121°C for **1B** and 120°C for **1Y**, and no other peaks were observed even in the cooling profiles (Fig. 5a). This result confirms the absence of a thermal phase transition between **1B** and **1Y**. Thermal analyses using a thermography camera also confirmed that photogenerated heat was negligible (less than 2°C , Fig. S10 and S11). We also confirmed that the photoinduced SCSC phase transition of **1B** was not initiated by visible light (435 nm, approx. $200 \text{ mW}\cdot\text{cm}^{-2}$, Fig. 5b and S12). Moreover, upon UV irradiation (367 nm , approx. $100 \text{ mW}\cdot\text{cm}^{-2}$) of a local area of a **1B** crystal, the phase transition occurred only in the photoirradiated area and did not expand into the unirradiated region (Fig. 5c), indicating the absence of a “domino-like” mechanism.¹³ These control experiments confirmed that the phase transition of **1B** was induced by UV photoexcitation of the crystals.

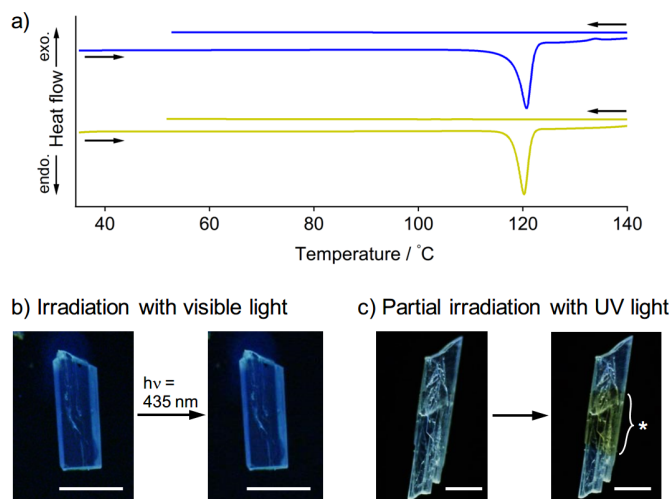


Fig. 5 a) DSC profiles of **1B** (blue line) and **1Y** (greenish yellow line) at heating and cooling rates of 10 and 2 °C min⁻¹, respectively. b) Photographs of crystal **1B** before and after strong photoirradiation at 435 nm for 5 min (approx. 200 mW·cm⁻²). These photographs are taken under weak UV light at 365 nm (approx. 1 mW·cm⁻²). The scale bars are 0.1 mm. These photographs show that emission color is unchanged after irradiation with visible light. c) Photograph of a crystal **1B** obtained after photoirradiation (367 nm, approx. 100 mW·cm⁻²) at a local area taken under ambient light. The mark “*” denotes the irradiation region of the crystal. The scale bars are 0.1 mm.

A schematic representation of aurophilic bonds and their simplified orbital levels are shown in Fig. 6. Aurophilic interactions arising from the correlation and relativistic effects of Au atoms produce filled $d_z^2\sigma$ and $d_z^2\sigma^*$ molecular orbitals and result in decreased excitation energy [(i) and (ii) in Fig. 6a].⁷ Aurophilic bonds shorten in the excited state because of the electronic transition from the filled antibonding $d_z^2\sigma^*$ orbital located on the aurophilic bond to an empty orbital of higher energy [(iii) in Fig. 6a]. Although theoretical studies on this topic have been reported,¹⁴ it has seldom been observed experimentally. Tahara's group observed aurophilic bond shortening using time-resolved spectroscopy of aqueous solutions of $[\text{Au}(\text{CN})_2^-]_n$ complexes.¹⁵ In this study, the trimeric species $[\text{Au}(\text{CN})_2^-]_3$ predominantly present in the ground state associated into larger oligomers upon photoexcitation through the excited $[\text{Au}(\text{CN})_2^-]_3^*$ state with shortening of the aurophilic bonds (Fig. 6b). However, in this case, the original ground state recovered when photoirradiation ceased (Fig. 6b) because the molecules have enough mobility in aqueous solution to reorient to their original structure.

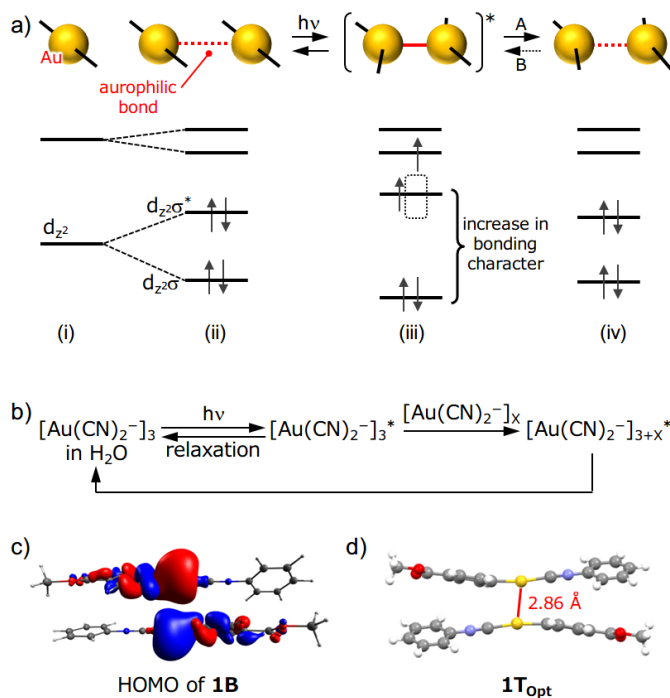


Fig. 6 a) Schematic representation of aurophilic bonds and their simplified orbital levels. An aurophilic bond produces $d_z^2\sigma$ and $d_z^2\sigma^*$ orbitals and shortens upon photoexcitation. b) Schematic representation of the relaxation pathway upon photoirradiation of $[\text{Au}(\text{CN})_2^-]_n$ complexes. See reference 15 for details. c) HOMO of the dimer derived from the single-crystal structure of **1B** (PBE/PBE/SDD). d) The structure of **1T_{Opt}** obtained using triplet excited-state optimization of a **1B** dimer in vacuum (PBE/PBE/SDD).

Although the detailed mechanism for the photoinduced SCSC phase transition of **1** is still unknown, we can provide some mechanistic insights by computational investigation (Fig. 6). A DFT calculation (PBE/PBE/SDD) of the dimer of **1** derived from the single-crystal structure of **1B** possesses a HOMO with antibonding character located between the two Au atoms even though the separation between Au atoms is on the limit of an aurophilic bond (Fig. 6c). TDDFT calculations based on the crystal structures **1B** and **1Y** qualitatively matched the experimental excitation and emission spectra (see the ESI and Fig. S14). Because the structural optimizations of the crystal structures of **1B** and **1Y** are very difficult in terms of the computational cost, quantitative estimation of the thermodynamic stability and luminescent properties could not be achieved. Geometry optimization of the dimer derived from **1B** in the triplet state (**1T_{Opt}**) in vacuum gave a marked decrease in the Au...Au separation (2.86 Å, Fig. 6d). The structures and molecular orbitals of **1T_{Opt}** are more similar to those of the dimer in **1Y** compared with those in **1B** (Fig. S13 and S15 and Table S7). These results indicate that the structure transformation from **1B** to **1Y** can be facilitated through the photoexcited state of **1B** [(ii)–(iv) in Fig. 6a]. Although the structural conversion from the photoexcited state to **1Y** (“A” in Fig. 6a) would compete with the relaxation to the original ground state **1B**, once the phase transformation to **1Y** occurred in a local area, the reverse phase transition from **1Y** to **1B** (“B” in Fig. 6a) does not proceed thermally, probably because the movement of the molecules in the **1Y** polymorph is restricted

by the relatively strong intermolecular interactions, such as CH/ π interactions and aurophilic interactions (Fig. 4). Irradiation of **1Y** could not cause it to revert to **1B** because the structure of the excited state would be more similar to **1Y** than the structure of **1B**. Thus, the entire **1B** crystal eventually transformed into the new phase **1Y** after a certain period of photoirradiation. Although many studies on transient shortening of metallophilic bonds (Pt, Rh, and Ir) in the photoexcited state have been reported, these structural changes reverted back to the original structures after photoirradiation ceased.²³ The present study is the first example of photoinduced SCSC transformation with shortening metallophilic bonds.

The first photosalient effect induced by phase transition between polymorphs

Recently, a rare dynamic phenomenon of organic crystals, the “salient effect”, has been attracting much attention.¹⁷ The thermosalient effect, in which organic crystals jump after the crystal is heated, was first reported in 1983.²⁴ A related phenomenon in which a crystal jumps due to irradiation with light is also referred to as the “photosalient effect”.¹⁷ The “salient effect” is produced by the internal crystal constraints imposed by changes in the crystalline shape and/or volume at the interface between the two phases upon the thermo- or photoinduced crystalline structural change. Recently, intense explorations of thermo- and photosalient effects have been made by Naumov and colleagues,^{17,25,26} however, compounds that show the photosalient effect are still very rare.^{17,26}

We found that the **1B** crystals show the “salient effect” upon strong UV light irradiation (367 nm, approx. 400 mW·cm⁻²). As shown in Fig. 7a–f and Supplementary Movie S1, the blue emission of the surface of crystal **1B** becomes yellow after 5 s of photoirradiation through the phase transition from **1B** to **1Y** (see Fig. 7a and b), and after 21 s the crystal jumps (see Fig. 7c–e). Not all crystals of **1B** showed this jumping phenomenon; approximately 1% of the irradiated crystals of **1B** jumped (see also Supplementary Movie S2 and Fig. 7g–l and S16) and approximately 10% of the irradiated crystals split (Supplementary Movie S3 and Fig. S17). Furthermore, more than 80% of irradiated crystals showed cracking (Fig. S18). These mechanical responses upon photoirradiation suggested that the transformation from **1B** to **1Y** is martensitic-type transition, similar to most salient-active materials, rather than phase transition through nucleation-elongation mechanism. In Naumov’s articles,^{17,25} the authors discussed the idea that the thermosalient phase transition generally occurs between two phases with an identical symmetry and space group. Thus, the overall packing and unit cell parameters of the two phases are only slightly, yet distinctly changed upon applying the external stimuli. This notion can also be applied to the photosalient phase transition of **1** because the crystalline structures of **1B** and **1Y** fulfil these requirements: the space groups of **1B** and **1Y** are both *P*-1, and their *V*/*Z* values are almost the same (**1B**: 330.2 Å³; **1Y**: 337.0 Å³, Table 1). The photosalient effect is generally induced by a photochemical reaction (chemical structural changes, e.g., [2+2] cycloaddition, ring closing reaction, etc).²⁷ Contrary, the present study is the first example of the photosalient effect induced by a phototriggered phase transition between polymorphs (packing structural change or molecular arrangement change) without chemical structural changes. As shown in the aforementioned control experiments, the heating effect that would accompany photoexcitation¹⁷ has negligible

influence on the phase transition of **1** (Fig. S10 and S11), and thus not related to its photosalient effect. This conclusion is also supported by the fact that **1B** does not show any thermal phase change below 120 °C (Fig. 5a). The aurophilic bonding formation in the crystal was induced by light irradiation and generated the macro-scale mechanical power that can sputter the crystals.

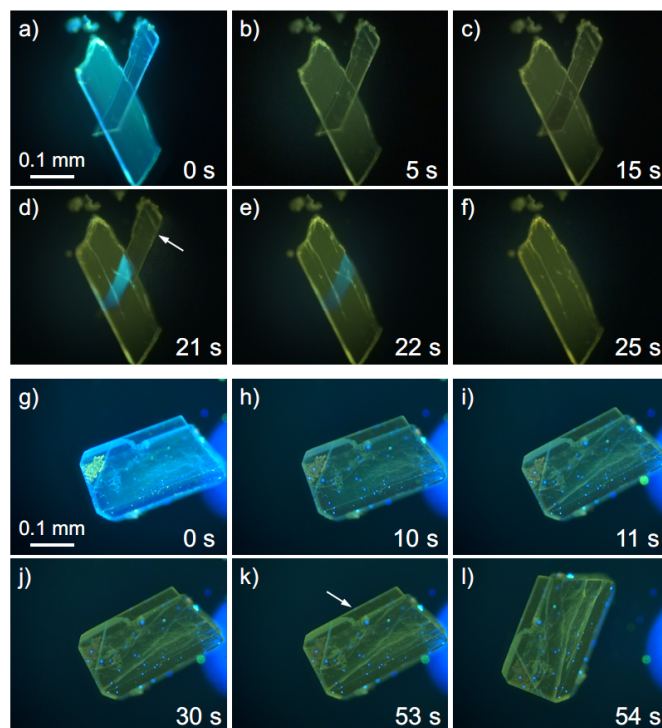


Fig. 7 A series of photographs of the photosalient effect of **1B** through the transformation into **1Y** induced by strong photoirradiation (367 nm, approx. 400 mW·cm⁻²). Photographs from a) to f) and g) to l) were cropped from Supplementary Movies S1 and S2, respectively. The arrows in d) and k) indicate the crystals just before the jump. The irradiation times are shown.

Conclusion

In summary, we have described the first photoinduced SCSC phase transition of gold(I) isocyanide complex **1** with a shortening of the aurophilic bond. This phase transformation was accompanied by a defined color change under UV light. We propose that the shortening of the aurophilic bond in the excited state is the driving force behind this transition; structural relaxation from the excited state to **1Y** is followed by immobilization of the structural change, including the short aurophilic bond, which inhibits reversal to the original **1B**. The first photosalient effect induced by polymorph transformation was also discovered. These findings could be an important lead in the design of novel photosensitive materials that exhibit reorganization of intermolecular interactions induced by photoirradiation.

Acknowledgements

This work was financially supported by the Funding Program for Next Generation World-Leading Researchers (NEXT

Program, No. G002) from the Japan Society for the Promotion of Science (JSPS) and the MEXT (Japan) program “Strategic Molecular and Materials Chemistry through Innovative Coupling Reactions” of Hokkaido University. JSPS KAKENHI Grant-in-Aid for Young Scientists (B), 26810042.

Notes and references

^a Division of Chemical Process Engineering and Frontier Chemistry Center (FCC), Graduate School of Engineering, Hokkaido University, Sapporo, Hokkaido 060-8628, Japan

† Electronic Supplementary Information (ESI) available: X-ray crystallographic data, optical properties, DFT calculations, and other additional information. See DOI: 10.1039/b000000x/.

- J. Zhang, Q. Zou and H. Tian, *Adv. Mater.*, 2013, **25**, 378–399.
- J. W. Chung, S.-J. Yoon, B.-K. An and S. Y. Park, *J. Phys. Chem. C*, 2013, **117**, 11285–11291.
- O. S. Bushuyev, A. Tomberg, T. Friščić and C. J. Barrett, *J. Am. Chem. Soc.*, 2013, **135**, 12556–12559.
- a) S. Kobatake, S. Takami, H. Muto, T. Ishikawa and M. Irie, *Nature*, 2007, **446**, 778–781; b) M. Morimoto and M. Irie, *J. Am. Chem. Soc.*, 2010, **132**, 14172–14178. c) D. Kitagawa, H. Nishi and S. Kobatake, *Angew. Chem. Int. Ed.*, 2013, **52**, 9320–9322.
- S. Iyengar and M. C. Biewer, *Cryst. Growth Des.*, 2005, **5**, 2043–2045.
- a) A. Y. Kovalevsky, K. A. Bagley and P. Coppens, *J. Am. Chem. Soc.*, 2002, **124**, 9241–9248; b) H. Nakai, M. Mizuno, T. Nishioka, N. Koga, K. Shiomi, Y. Miyano, M. Irie, B. K. Breedlove, I. Kinoshita, Y. Hayashi, Y. Ozawa, T. Yonezawa, K. Toriumi and K. Isobe, *Angew. Chem. Int. Ed.*, 2006, **45**, 6473–6476; c) A. Kobayashi, K. Komatsu, H. Ohara, W. Kamada, Y. Chishina, K. Tsuge, H. C. Chang and M. Kato, *Inorg. Chem.*, 2013, **52**, 13188–13198; d) L. E. Hatcher and P. R. Raithby, *Acta Cryst. C*, 2013, **69**, 1448–1456.
- For selected reviews and books on gold complexes, see: a) A. L. Balch, *Gold Bull.*, 2004, **37**, 45–50; b) P. Pykkö, *Angew. Chem. Int. Ed.*, 2004, **43**, 4412–4456; c) V. W.-W. Yam in *Photofunctional Transition Metal Complexes*, Springer-Verlag: Berlin/Heidelberg, 2007; d) J. M. López-de-Luzuriaga, in *Modern Supramolecular Gold Chemistry* (Ed.: A. Laguna), Wiley-VCH, Weinheim, 2008; e) V. W.-W. Yam and E. C. Cheng, *Chem. Soc. Rev.*, 2008, **37**, 1806–1813; f) M. J. Katz, K. Sakai and D. B. Leznoff, *Chem. Soc. Rev.*, 2008, **37**, 1884–1895; g) H. Schmidbaur and A. Schier, *Chem. Soc. Rev.*, 2008, **37**, 1931–1951; h) A. L. Balch, *Angew. Chem. Int. Ed.*, 2009, **48**, 2641–2644; i) X. He and V. W.-W. Yam, *Coord. Chem. Rev.*, 2011, **255**, 2111–2123; j) H. Schmidbaur and A. Schier, *Chem. Soc. Rev.*, 2012, **41**, 370–412.
- For selected reports on the correlation between the aurophilic interactions and emission properties of gold complexes, see: a) M. A. Rawashdeh-Omary, M. A. Omary, H. H. Patterson and J. P. Fackler, *J. Am. Chem. Soc.*, 2001, **123**, 11237–11247; b) W. Lu, N. Zhu and C. M. Che, *J. Am. Chem. Soc.*, 2003, **125**, 16081–16088; c) L. Rodríguez, M. Ferrer, R. Crehuet, J. Anglada and J. C. Lima, *Inorg. Chem.*, 2012, **51**, 7636–7641; d) S. H. Lim, J. C. Schmitt, J. Shearer, J. Jia, M. M. Olmstead, J. C. Fettinger and A. L. Balch, *Inorg. Chem.*, 2013, **52**, 823–831. For related studies, see: e) E. C.-C. Cheng, K.-H. Leung, V. M. Miskowski, V. W.-W. Yam and D. L. Phillips, *Inorg. Chem.*, 2000, **39**, 3690–3695; f) R. L. White-Morris, M. M. Olmstead, A. L. Balch, O. Elbjerrami and M. A. Omary, *Inorg. Chem.*, 2003, **42**, 6741–6748.
- a) J. C. Vickery, M. M. Olmstead, E. Y. Fung and A. L. Balch, *Angew. Chem. Int. Ed.*, 1997, **36**, 1179–1181; b) S. H. Lim, M. M. Olmstead and A. L. Balch, *J. Am. Chem. Soc.*, 2011, **133**, 10229–10238; c) M. A. Malwitz, S. H. Lim, R. L. White-Morris, D. M. Pham, M. M. Olmstead and A. L. Balch, *J. Am. Chem. Soc.*, 2012, **134**, 10885–10893.
- a) E. M. Gussenhoven, J. C. Fettinger, D. M. Pham, M. A. Malwitz and A. L. Balch, *J. Am. Chem. Soc.*, 2005, **127**, 10838–10839. For thermo-induced SCSC phase transition of a gold complex without emission color change, see: b) A. Deák, T. Tunyogi, Z. Károly, S. Klébert and G. Pálinkás, *J. Am. Chem. Soc.*, 2010, **132**, 13627–13629.
- C. H. Woodall, C. M. Beavers, J. Christensen, L. E. Hatcher, M. Intissar, A. Parlett, S. J. Teat, C. Reber and P. R. Raithby, *Angew. Chem. Int. Ed.*, 2013, **52**, 9691–9694.
- S. H. Lim, M. M. Olmstead and A. L. Balch, *Chem. Sci.* 2013, **4**, 311–318.
- a) T. Seki, K. Sakurada and H. Ito, *Angew. Chem. Int. Ed.*, 2013, **52**, 12828–12832; b) H. Ito, M. Muromoto, S. Kurenuma, S. Ishizaka, N. Kitamura, H. Sato and T. Seki, *Nat. Commun.*, 2013, **4**, 2009.
- For selected reports on theoretical studies of tightening aurophilic bonds under photoexcitation, see: a) Q.-J. Pan and H.-X. Zhang, *Inorg. Chem.*, 2004, **43**, 593–601; b) R. K. Arvapally, P. Sinha, S. R. Hettiarachchi, N. L. Coker, C. E. Bedel, H. H. Patterson, R. Elder, A. K. Wilson and M. A. Omary, *J. Phys. Chem. C*, 2007, **111**, 10689–10691; c) G. Cui, X. Y. Cao, W. H. Fang, M. Dolg and W. Thiel, *Angew. Chem. Int. Ed.*, 2013, **52**, 10281–10285.
- M. Iwamura, K. Nozaki, S. Takeuchi and T. Tahara, *J. Am. Chem. Soc.*, 2013, **135**, 538–541.
- For gold complex exhibiting photochromism in solution, see: J. B. Foley, A. Herring, B. Li and E. V. Dikarev, *Inorg. Chim. Acta*, 2012, **392**, 300–310.
- For highlight article on thermo- and photosalient effect of organic crystals as well as related mechanical responses to external stimuli, see: N. K. Nath, M. K. Panda, S. C. Sahoo and P. Naumov, *CrystEngComm*, 2014, **16**, 1850–1858.
- T. Seki, S. Kurenuma and H. Ito, *Chem. Eur. J.*, 2013, **19**, 16214–16220.
- A. Krasovskiy, V. Malakhov, A. Gavryushin and P. Knochel, *Angew. Chem. Int. Ed.*, 2006, **45**, 6040–6044.
- The power density of UV light for measuring photoluminescence spectra was less than 0.1 mW·cm⁻², under which **1B** is inert for hours (Table S1).
- Crystallization of **1** under ambient light gave blue-emitting crystals that were not suitable for single-crystal X-ray diffraction analyses, probably because ambient light, containing both UV and visible light, may create small amount of contamination of **1Y** during the course of crystallization. To prepare **1B** crystals of sufficient quality for X-ray analysis, crystallization should be conducted in the dark.
- Single crystal X-ray diffraction analyses of **1B** and **1Y** were performed at 123 K. Lowering temperature of **1B** and **1Y** does not induce their polymorph transformation. This is confirmed by luminescent spectroscopy of **1B** and **1Y** at low temperature,

- exhibiting spectra similar to those obtained at ambient temperature (Fig. S4).
- 23 For selected examples of transient shortening of metallophilic bonds, see: a) N. Yasuda, H. Uekusa and Y. Ohashi, *Bull. Chem. Soc. Jpn.*, 2004, **77**, 933–944; b) M. Christensen, K. Haldrup, K. Bechgaard, R. Feidenhans'l, Q. Kong, M. Cammarata, M. L. Russo, M. Wulff, N. Harrit and M. M. Nielsen, *J. Am. Chem. Soc.*, 2009, **131**, 502–508; c) R. M. van der Veen, C. J. Milne, A. E. Nahhas, F. A. Lima, V. T. Pham, J. Best, J. A. Weinstein, C. N. Borca, R. Abela, C. Bressler and M. Chergui, *Angew. Chem. Int. Ed.*, 2009, **48**, 2711–2714; d) K. Haldrup, T. Harlang, M. Christensen, A. Dohn, T. B. van Driel, K. S. Kjaer, N. Harrit, J. Vibenholt, L. Guerin, M. Wulff and M. M. Nielsen, *Inorg. Chem.*, 2011, **50**, 9329–9336. For transient shortening of the bonds between Au and ligands in gold complexes, see: e) M. Hoshino, H. Uekusa, S. Ishii, T. Otsuka, Y. Kaizu, Y. Ozawa and K. Toriumi, *Inorg. Chem.*, 2010, **49**, 7257–7265. As a related study, for reports on photocleavage of argentophilic (Ag \cdots Ag) bonds in the solid state which was mediated by 2+2 photocyclization of olefins, see: f) Q. Chu, D. C. Swenson and L. R. MacGillivray, *Angew. Chem. Int. Ed.*, 2005, **44**, 3569–3572.
- 24 M. C. Etter and A. R. Siedle, *J. Am. Chem. Soc.*, 1983, **105**, 641–643.
- 25 For comprehensive article of thermosalient effect, see: S. C. Sahoo, M. K. Panda, N. K. Nath and P. Naumov, *J. Am. Chem. Soc.*, 2013, **135**, 12241–12251.
- 26 For photosalient effect, see: a) P. Naumov, J. Kowalik, K. M. Solntsev, A. Baldrige, J.-S. Moon, C. Kranz and L. M. Tolbert, *J. Am. Chem. Soc.*, 2010, **132**, 5845–5857. b) P. Naumov, S. C. Sahoo, B. A. Zakharov and E. V. Boldyreva, *Angew. Chem. Int. Ed.*, 2013, **52**, 9990–9995. c) R. Medishetty, A. Husain, Z. Bai, T. Runčevski, R. E. Dinnebier, P. Naumov and J. J. Vittal, *Angew. Chem. Int. Ed.*, 2014, **53**, 5907–5911.