

Chemical Science

Accepted Manuscript



This is an *Accepted Manuscript*, which has been through the Royal Society of Chemistry peer review process and has been accepted for publication.

Accepted Manuscripts are published online shortly after acceptance, before technical editing, formatting and proof reading. Using this free service, authors can make their results available to the community, in citable form, before we publish the edited article. We will replace this *Accepted Manuscript* with the edited and formatted *Advance Article* as soon as it is available.

You can find more information about *Accepted Manuscripts* in the [Information for Authors](#).

Please note that technical editing may introduce minor changes to the text and/or graphics, which may alter content. The journal's standard [Terms & Conditions](#) and the [Ethical guidelines](#) still apply. In no event shall the Royal Society of Chemistry be held responsible for any errors or omissions in this *Accepted Manuscript* or any consequences arising from the use of any information it contains.

ARTICLE

Molecular Mapping of Poly(methyl methacrylate) Super-helix Stereocomplexes

Cite this: DOI: 10.1039/x0xx00000x

Andrew Joseph Christofferson,^{a†} George Yiapanis,^{a†*} Jing Ming Ren,^b Greg Guanghua Qiao,^b Kotaro Satoh,^c Masami Kamigaito^c and Irene Yarovsky^{a*}Received 00th January 2012,
Accepted 00th January 2012

DOI: 10.1039/x0xx00000x

www.rsc.org/

In this study, by using X-ray powder diffraction profiles as blueprints, we successfully mapped the most probable molecular-level structural arrangement of the PMMA super-helix stereocomplexes through molecular dynamic simulations. Molecular-level resolution of the PMMA triple-helix supramolecule was not previously achievable by experimental methods. After constructing molecular models of stereo-regular complexes composed of linear *it*- and *st*-PMMA, our all-atom molecular dynamics simulations identified the stereocomplex structure that best reproduces experimental diffraction profiles and thermodynamic properties as a double helix of isotactic (*it*-)PMMA with a helical pitch of 1.8 nm and 9 units per turn surrounded by a single helix of syndiotactic (*st*-)PMMA with an average helical pitch of 0.9 nm and 20 units per turn. The *it*-/*st*- complexing stoichiometry in the PMMA triple-helix is therefore 9:20. This presents the first all-atom model of the *it*-/*st*-PMMA triple-helix stereocomplex that accurately fits experimental X-ray diffraction profiles. In addition, the simulation results revealed the outer *st*-PMMA helix of the PMMA stereocomplex has a fiber diameter of at least 1.85 nm and adopts a non-ideal helical geometry. Furthermore, through dynamic simulations, surprising new sights into the effect of the structural configuration of the PMMA stereocomplex (i.e., helical pitch and direction, and tilt angle) on the physical properties of their crystal structures were obtained. Those crystal properties include X-ray diffraction profile, packing density, chain-chain spacing, chain width and cohesive energy density.

Introduction

Naturally occurring helical supramolecular assemblies, such as RNA, DNA and some protein sequences, regulate essential biological activities in living organisms. For example, the double helical structure of DNA is a determining factor in the storage, transmission and translation of genetic information, while the helical structure of collagen provides great tensile strength for tissue support.¹ Emerging technologies in polymer synthesis and developments in biomimicry have led to an increasing interest in synthetic polymers which are able to form helical structures. The ultimate goal of the research and development of artificial helical systems is to create advanced nanomaterials that mimic or replicate exquisite functions of their natural analogues.^{2,3}

One of the most intriguing synthetic super-helix is perhaps the poly(methyl methacrylate) (PMMA) stereocomplex, as multiple-strand synthetic helices are very rare. The unique supramolecular architecture provides the PMMA

stereocomplex with useful properties for a number of potential applications in life science and nanotechnology. For instance, PMMA stereocomplex formation has been exploited as an assembly mode for the fabrication of ultrathin films,^{4,5} nanoparticles,^{6,7} network and gel formations,⁸ as well as fibers⁹ and dialysis membranes.¹⁰ Moreover, other interesting and remarkable characteristics of PMMA stereocomplexes that have been explored, include stereospecific polymerization-templating,⁵ molecular recognition capability^{11,12} and helix-sense stereo-complexation.⁶

The structures of PMMA stereocomplexes have been studied since the 1950s, but to date, the exact structural arrangements of PMMA stereocomplexes at the molecular level still remain elusive.

In complexing solvents such as acetonitrile or acetone, isotactic PMMA (*it*-PMMA) can self-aggregate to form a double-stranded helix with definitive crystalline characteristics.^{13,14} Its aggregation depends strongly on the degree of stereoregularity, the nature of the solvent and on

temperature.¹⁵ Many attempts were made to elucidate the crystal structure using X-ray diffraction analysis, but due to the amorphous nature of the supramolecular assembly, conflicting results were obtained. For many years, the consensus based on X-ray results¹⁶⁻¹⁸ and early molecular models was that the *it*-PMMA structure consisted of two 10₁ helices (10 repeating MMA units per turn) of *it*-PMMA chains intertwined to form a double helix in the crystal with a helical pitch of 2.1 nm.

In addition to the double helix, *it*-PMMA can be combined with syndiotactic PMMA (*st*-PMMA) to form a stereocomplex.^{13,19,20} With an *it:st* complexing ratio (monomer ratio in the stereoregular region of the polymer) of 1:2,²¹ Schomaker and Challa proposed a model based on X-ray fiber diffraction of a 9₁ double-stranded helix of *it*-PMMA and *st*-PMMA in a 1:2 monomer ratio.²² While X-ray fiber diffraction gave a fiber identity period of 1.84 nm,^{22,23} consistent with a 9₁ helix, due to the poor quality of the diffraction patterns resulting from an inherently disordered structure a quantitative analysis was not possible and the proposed model was recommended as a starting point for further investigations. Interestingly, the authors found that stereocomplexes of atactic and isotactic PMMA gave fiber X-ray diffraction patterns with the main characteristics of the *it-st*-PMMA stereocomplex diffraction pattern still present, suggesting that the degree of tacticity of the *st*-PMMA is not critical to stereocomplexation.²²

More recently, the introduction of the Langmuir-Blodgett technique coupled with atomic force microscopy (AFM) analysis has enabled the direct observation of the *it-st*-PMMA stereocomplex.^{24,25} Based on their observations, Yashima and colleagues proposed a model of a 9₁ *it*-PMMA double-stranded helix with a helical pitch of 1.84 nm surrounded by a single helix of 18₁ *st*-PMMA with a helical pitch of 0.92 nm. These early works demonstrated that the exact arrangement of the supramolecular complex proved difficult to resolve based upon experimental methods.

In this work, we discovered that by using the X-ray diffraction profiles of the PMMA stereocomplex crystals as blueprints, the most probable molecular-level arrangements of the PMMA super-helix stereocomplexes can be successfully mapped through molecular dynamic (MD) simulations. Due to stereo-association being dominated by non-covalent interactions, MD simulation provides a unique method for resolving structural features of *it-st*-PMMA crystals and this becomes the only way to obtain an all-atom structural model compatible with X-ray diffraction results. More specifically, we constructed models of *it*-PMMA and *st*-PMMA crystals comprising double-stranded helices of *it*-PMMA and single-stranded *st*-PMMA with varying helical pitch and direction in excellent agreement with experimentally obtained diffraction data. Our results show that an average of 20 PMMA repeating units are required to form one helix turn for the *st*-PMMA in the triple-helix stereocomplex structure and this is distinguished from any previously reported results. Through MD simulation, other than mapping the structural features of the PMMA stereocomplexes, we obtained new insights into the effect of helical pitch and helix direction on the molecular structure and

stability of *it*- and *st*-PMMA crystals by analyzing the following properties: X-ray diffraction profiles, density, chain-chain spacing, chain width, and cohesive energy density.

Methods

Synthesis of *it*-PMMA, *st*-PMMA, and *it-st*-PMMA Stereocomplexes

The *it*-PMMA was synthesized by anionic polymerization according to previously published procedures,²⁶ and full details of the synthesis and characterization may be found elsewhere.²⁷ The general procedure employed for the synthesis of *it*-PMMA was as follows: the initiator solution (Grignard reagent, *t*-C₄H₉MgBr, [*t*-C₄H₉MgBr] = 286 mM in diethyl ether, 0.39 mL) was added to anhydrous toluene (5.4 mL) in a Schlenk tube at -78 °C under Ar. Methyl methacrylate (MMA) was then added slowly (1.2 mL in 5 min) causing the mixture to turn orange. The polymerization solution was kept at -78 °C for 126 h, and then anhydrous methanol (1 mL) was added to the Schlenk flask to quench the reaction. The reaction solution was diluted with toluene (20 mL), washed with 1 M HCl (20 mL × 3) and distilled water (20 mL × 3), dried over anhydrous magnesium sulphate (MgSO₄), filtered and precipitated into hexane to afford the *it*-PMMA (*it*-L_{10k}) as a white powder, 0.95 g (85 %); GPC: $M_n = 10.3$ kDa, $M_w/M_n = 1.12$; ¹H NMR: *mm/mr/rr* (%) = 93/3/4; DSC: $T_g = 53.6$ °C and $T_m = 137.5$ °C.

The procedure for synthesis of *st*-PMMA was adopted from previously published literature with modifications,²⁸⁻³⁰ and the full details may be found elsewhere.²⁷ In brief, copper(I) bromide (CuBr, 36.0 mg, 0.25 mmol) and copper(II) bromide (CuBr₂, 5.6 mg, 0.025 mmol) were added to a dry round-bottom flask equipped with a 3-way stopcock in a glovebox, followed by addition (under dry N₂) of 1,1,1,3,3,3-hexafluoro-2-phenyl-2-propanol (PhC(CF₃)₂OH, 8.4 mL), MMA (2.7 mL, 25.2 mmol), 2,2'-bipyridyl (bpy, 495 mM in toluene, 1.0 mL) and prop-2-ynyl 2-bromo-2-methylpropanoate (PgBr, 503 mM in toluene, 0.50 mL). The reaction was conducted at 0 °C with samples taken periodically under N₂. The polymerization was terminated after 11 h by cooling the reaction to -78 °C. A sample was extracted for ¹H NMR spectroscopic analysis, and the remaining product was diluted with ethyl acetate (EtOAc, 200 mL), washed with 1 M HCl (100 mL × 2), then distilled water (150 mL × 2). The extracted product was collected, concentrated and then precipitated in hexane, followed by drying *in vacuo* to afford the *st*-PMMA (*st*-L_{4k}) as a white solid, 0.88 g (87.8 %); ¹H NMR: MMA conversion = 33% (theoretical $M_n = 3.5$ kDa); GPC: $M_n = 4.2$ kDa, $M_w/M_n = 1.34$; ¹³C NMR: *mm/mr/rr* (%) = 2/26/72; DSC: $T_g = 98.6$ °C and $T_m = 99.5$ °C.

The general procedure employed for the synthesis of the PMMA stereocomplex was as follows:³¹ the *st*-PMMA (10 mg) and *it*-PMMA (10 mg) precursors were separately dissolved in an acetonitrile/water mixture (MeCN:H₂O = 9:1) at concentrations of 2 mg/mL and combined to an *it:st* molar ratio of 1:2. The solutions were left to stand at room temperature for

24 h. After removing the solvent *in vacuo*, the st - L_{4k}/it - L_{10k} stereocomplexes were dried under reduced vacuum (0.05 mmHg) for 24 h before DSC and XRD analysis; $T_m = 126.4$ °C.³²

Experimental X-ray scattering

The X-ray measurements were performed on a Rigaku R-AXIS IV detector system equipped with a Rigaku FR-E rotating-anode generator and confocal mirror monochromated CuK radiation (0.15418 nm) focused through a 0.5 mm pinhole collimator, which was supplied at 45 kV voltage and 45 mA current, equipped with a flat imaging plate having a specimen-to-plate distance of 200.0 mm. The dried powders were placed in a borosilicate glass capillary tube, and their X-ray diffractograms were taken at ambient temperatures (20 – 25 °C) from the edge-view position.

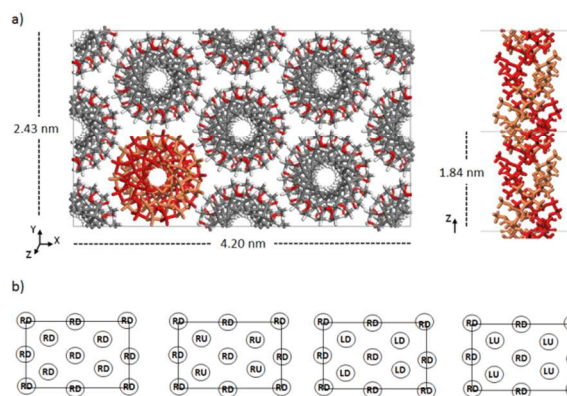


Figure 1. a) Initial model crystal structure of 9_1 *it*-PMMA, b) the four packing motifs examined in this study (from left to right): Right Down (RD), Right Down/Right Up (RD/RU), Right Down/Left Down (RD/LD), and Right Down/Left Up (RD/LU).

Construction of PMMA molecular models

Double-stranded helices of 10_1 and 9_1 *it*-PMMA (10 units per turn and 9 units per turn, respectively) were constructed based on reported bond lengths, bond angles and internal rotation angles.^{16,24} Crystal models were assembled by arranging eight identical double-stranded helices in a hexagonal packing mode within a periodically replicated orthorhombic unit cell (Figure 1a). The fiber axes of the chains were oriented in the z -direction and to eliminate the terminal melting propensity of finite polymeric chains, each *it*-PMMA fragment was connected to its periodic image in the z -direction, mimicking an infinite PMMA crystal (Figure 1a). Each cell displayed initial dimensions of 4.20 and 2.43 nm in the x - and y -directions respectively, and varied in length along the z -direction depending on the helical pitch of the chains; 2.10 and 1.84 nm for the 10_1 and 9_1 *it*-PMMA crystals respectively. We examined structural perturbations associated with the handedness (right or left) and orientation (down/down or up/down) of the helices by considering four packing motifs (Figure 1b).

Single-stranded helices of 18_1 *st*-PMMA with a helical pitch of 0.92 nm were constructed based on reported bond lengths, bond angles and internal rotation angles from the proposed Yashima model for the triple helix stereocomplex.²⁴ Similar to the *it*-PMMA, the fiber axes of the chains were oriented in the z -direction and each *st*-PMMA fragment was connected to its periodic image in the z -direction, mimicking an infinite PMMA crystal (Figure 2). For this model (9_1 -*it*-/ 18_1 -*st*-PMMA) only the Right Down packing motif was employed. In order to more closely reproduce the experimental stereocomplex synthesized in this work, additional *st*-PMMA fragments of 40 PMMA units were constructed, labeled 40mer-*st*, corresponding to the *l*-*st*-PMMA (*st*- L_{4k}) fragments. Each cell contained two *it*-PMMA double helices surrounded by a single *st*-PMMA helix of the same sense and direction in a hexagonal packing arrangement with initial cell dimensions of 3.98 and 2.36 nm in the x - and y -directions. The length along the z -direction depended on the helical pitch of the *it*-PMMA double helix; 2.10 and 1.84 nm for the 10_1 -*it*/40mer-*st* and 9_1 -*it*/40mer-*st* models respectively. For the 10_1 -*it*/40mer-*st* model only the Right Down packing motif was employed, while for the 9_1 -*it*/40mer-*st* model all four packing motifs (Figure 1b) were employed.

Computational Method

Simulations were carried out using the LAMMPS³³ software distributed by Sandia National Laboratories. Analysis was performed using the Materials Studio 6.1³⁴ software. The potential energy was calculated using the PCFF force field^{35,36} which has been shown to reproduce structural and thermodynamic properties of condensed phase polymeric systems well.³⁷⁻⁴⁰ Short-range non-bonded interactions were calculated using the atom-based summation method, with a cutoff radius of 15.5 Å. A long-range tail correction was applied for van der Waals interactions larger than the cut-off radius. The PPPM (particle-particle-particle-mesh) method⁴¹ was applied for long-range Coulomb interactions.

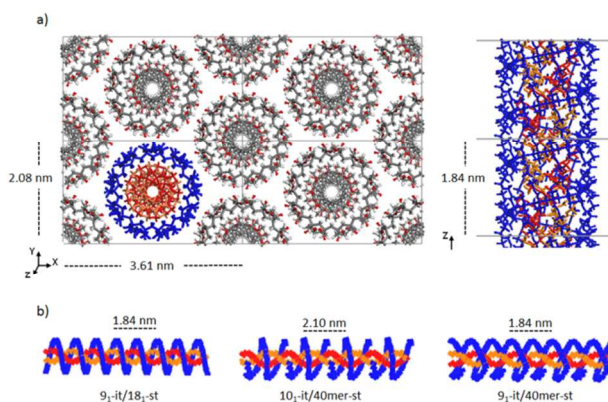


Figure 2. a) Initial model crystal structure of the 9_1 -*it*-/ 18_1 -*st*-PMMA stereocomplex, b) schematic representations of the three triple helix stereocomplex systems.

For all models, we initially performed energy minimization with unit cell dimensions fixed and a force convergence criterion of 0.01 kcal/mol/Å. Subsequently, we undertook

molecular dynamics (MD) simulations in the NPT ensemble (constant number of particles, pressure and temperature) for a total of 40 ns. For the *it*-*st*-PMMA stereocomplex simulations, atom coordinates of the *it*-PMMA were fixed for the first 20 ns, followed by 20 ns of simulation with all coordinates varying. The temperature and pressure were maintained at 298 K and 1 atm respectively using the Nose-Hoover thermostat and barostat.^{42,43} A time step of 1 fs was implemented, with atomic coordinates and thermodynamic quantities recorded every 10,000 steps. The models were considered equilibrated when the energy and density attained a steady value (standard deviation within 1%). The geometry of the equilibrated models was optimized by the energy minimization with a force convergence criterion of 0.001 kcal/mol/Å and the optimized structures were used for analysis of density, structural parameters, cohesive energy density and calculated X-ray diffraction profiles.

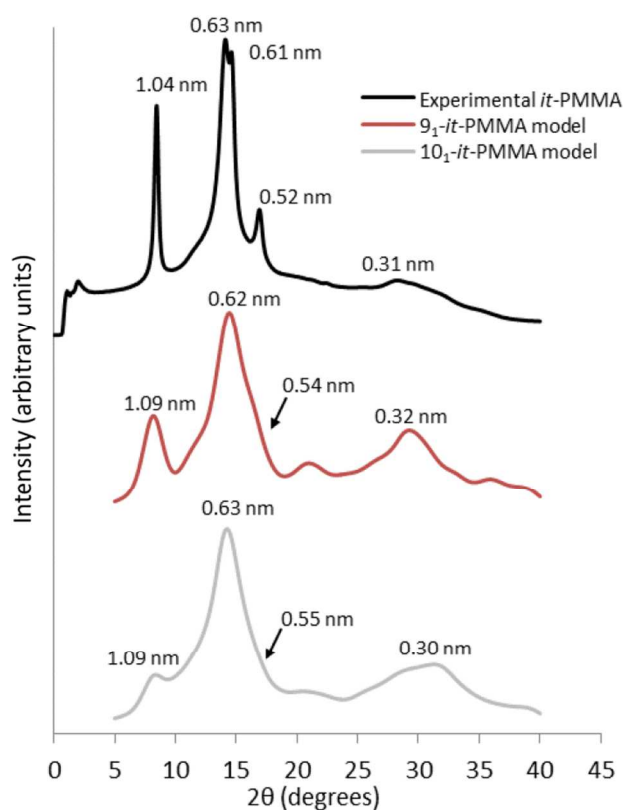


Figure 3. Wide angle X-ray scattering profiles obtained from powder diffraction experiments and molecular dynamics simulations for the *it*-PMMA double helix in the Right Down packing motif.

Results and discussion

The *it*-PMMA Double Helix Structure

Figure 3 presents the X-ray scattering plots of *it*-PMMA crystals obtained from the simulations and the XRD experiments. The simulated plots display similar features to those obtained from powder diffraction experiments, with the 9_1 *it*-PMMA model showing the most consistent agreement with experiment compared to the 10_1 *it*-PMMA model.

The experimental peak at 1.04 nm, which arises from the chain-chain spacing in the *x*- and *xy*-directions (see Figure 4), is reproduced by both the 9_1 and 10_1 models, but the former generates a greater peak intensity. The peak at 0.60 – 0.63 nm is likely associated with the chain-chain spacing in the *y*-direction and the pitch spacing along the fiber axis. The pitch spacing can be calculated from the helical pitch multiplied by the cosine of the tilt angle, where the tilt angle for an ideal helix is the helix diameter multiplied by π and divided by the helical pitch.⁴⁴ For a calculated tilt angle of 54° and helical pitch of 1.81 nm for the 9_1 double helix, the pitch spacing equals 0.73 nm. For the 10_1 double helix model, the tilt angle is closer to 50° and the pitch spacing is 0.80 nm. Based on these values we can conclude that while the peak is associated with the pitch spacing, it does not directly correspond to it.

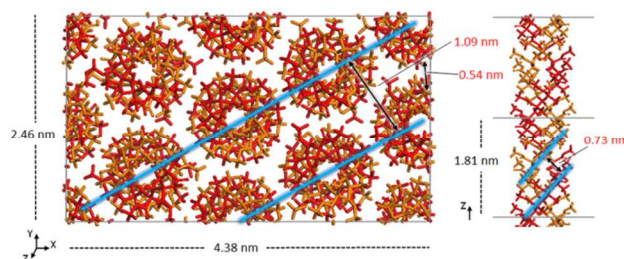


Figure 4. Model of the optimized crystal structure of 9_1 *it*-PMMA in the Right Down packing motif. The chain-chain spacing (left) and pitch spacing (right) are shown in light blue.

The peak at 0.52 nm arises primarily due to reflections from the *x*-plane. Finally, the peak at 0.31 nm corresponds to the inter-monomer spacing along the axis of the helix. Figure 3 shows that for the 9_1 *it*-PMMA model this particular peak is positioned just below 30° , in line with the experimental X-ray diffraction data, while for the 10_1 *it*-PMMA model the peak is positioned just above 30° .

We should note here that the peak intensities reflect contributions from various crystallographic planes, which makes it difficult to precisely determine the exact contribution to each peak. In general, however, we see an excellent agreement between the simulated and experimentally obtained diffraction patterns validating our models.

Table 1. Simulated and experimental structural and thermodynamic properties of *it*-PMMA double helix crystals of Right Down (RD), Right Down/Right Up (RD/RU), Right Down/Left Down (RD/LD) and Right Down/Left Up (RD/LU) packing motifs.

| Description | Packing motif | Density (g/cm ³) | Helical Pitch (nm) | Cohesive Energy Density (J/cm ³) |
|---------------------------------|---------------|------------------------------|---|--|
| Experiment | - | 1.23 ⁴⁵ | 1.84 (9 ₁) ²⁴ 2.10 (10 ₁) ¹⁶ | 361 ^a |
| 9 ₁ <i>it</i> -PMMA | RD | 1.235 ± 0.007 | 1.80 ± 0.01 | 385 ± 12 |
| | RD/RU | 1.240 ± 0.014 | 1.79 ± 0.01 | 281 ± 12 |
| | RD/LD | 1.220 ± 0.001 | 1.81 ± 0.01 | 221 ± 1 |
| | RD/LU | 1.240 ± 0.028 | 1.80 ± 0.03 | 285 ± 4 |
| 10 ₁ <i>it</i> -PMMA | RD | 1.225 ± 0.007 | 2.01 ± 0.09 | 302 ± 3 |
| | RD/RU | 1.215 ± 0.007 | 1.95 ± 0.15 | 281 ± 1 |
| | RD/LD | 1.235 ± 0.021 | 2.05 ± 0.01 | 227 ± 36 |
| | RD/LU | 1.255 ± 0.007 | 2.06 ± 0.01 | 271 ± 22 |

^a Experimental cohesive energy density of PMMA with unspecified tacticity.⁴⁶

Table 1 summarizes the simulated model properties and compares them with the experimental values available. For both the 9₁ and 10₁ double helices, densities ranged from 1.220 to 1.255 g/cm³, comparing well to an experimental density of 1.23 g/cm³.⁴⁵ To compare the relative thermodynamic stability of the model structures we calculated the cohesive energy density which is equal to the internal energy divided by the molar volume of a system, and describes the amount of energy required to remove a unit volume of molecules from their neighbors to infinite separation.⁴⁷

The 9₁ *it*-PMMA exhibits a larger cohesive energy density than the 10₁ *it*-PMMA in every case, with the Right Down 9₁ model at 385 ± 12 J/cm³ compared to 302 ± 3 J/cm³ for the 10₁. Interestingly, there was a range in cohesive energy density values for both the 9₁ and 10₁ models, with the Right Down packing motif providing the largest values for both models, although there appear to be no obvious trends between cohesive energy density and other properties, including structural parameters, density, and the experimental X-ray diffraction profiles for the different packing motifs.

In summary, based on the analyses of X-ray diffraction data, density, structural parameters and cohesive energy densities, the model that best agrees with the experimental data is a 9₁ *it*-PMMA double helix with a helical pitch of 1.80 ± 0.01 nm, a tilt angle of 54°, and a pitch spacing of 0.73 nm.

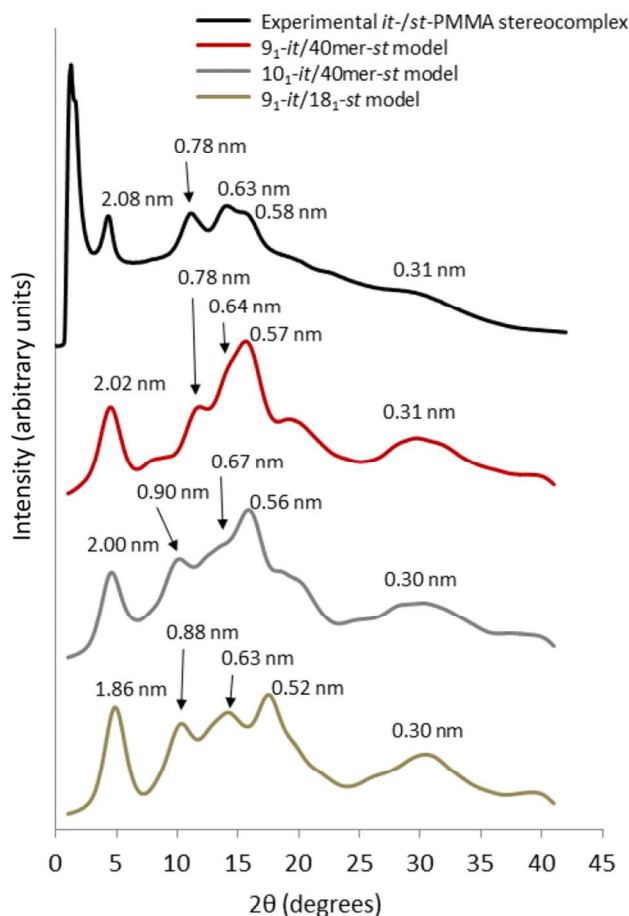


Figure 5. Wide angle X-ray scattering data obtained from powder diffraction experiments and molecular dynamic simulation for the *it*-*st*-PMMA stereocomplex in the Right Down packing motif.

Structure of the *it*-*st*-PMMA Stereocomplex.

For the simulated *it*-*st*-PMMA stereocomplex models, we can assign the experimental X-ray diffraction peaks as follows. The peak at 2.08 nm (Figure 5) is associated with the spacing between the triple helices in the *x*- and *xy*-planes. The peak at 0.78 nm is associated with the helical pitch of the *st*-PMMA, but does not directly correspond to it. The experimental peaks at 0.63 and 0.58 nm arise from multiple contributions, with the peak at 0.63 nm likely associated with the helical pitch of the *it*-PMMA, as well as spacings in the *x*- and *y*-planes. Similar to the *it*-PMMA models, the peak at 0.31 nm is associated with inter-monomer spacing. These three peaks were reproduced reasonably well by all models, and demonstrate that the *it*-PMMA double helix retains its structure when complexed with *st*-PMMA.

It can be seen from Figure 5 that the 9₁-*it*/18₁-*st* stereocomplex model (infinite *st*-PMMA with 18 units per turn complexed with infinite *it*-PMMA with 9 units per turn) failed to reproduce the experimental X-ray diffraction data. Most notably the experimentally observed peak of 2.08 nm is shifted to a shorter *d*-spacing of 1.86 nm. This suggests that the chain

width of this model is too narrow, resulting in a crystal that is overly compact. This is further supported by a density of $1.240 \pm 0.001 \text{ g/cm}^3$ calculated for this structure compared to the experimental density of 1.215 g/cm^3 .⁴⁵ In addition, this model fails to reproduce the helical pitch of the *st*-PMMA, with a value of $0.97 \pm 0.016 \text{ nm}$ for the model, compared to the experimentally measured value of $0.92 \pm 0.02 \text{ nm}$.²⁴ This is reflected by a shift in the associated peak *d*-spacing to 0.89 nm , compared to the experimental peak at 0.78 nm .

Previous *ab initio* calculations⁶ suggested that the helical pitch ratio for *it*-PMMA and *st*-PMMA is not exactly 2:1. Based on this, we constructed models of infinite *it*-PMMA with 40-unit *st*-PMMA fragments (40mer-*st*) which is in line with the size of the *st*-PMMA fragments used in our X-ray diffraction experiments. These 40mer-*st* fragments exhibited an average helical pitch of 20 MMA units, with gaps of approximately 1-2 units between fragments in the *z*-direction.

While the 10_1 *it*-PMMA complexed with 40-unit *st*-PMMA model (10_1 -*it*-/40mer-*st*) maintains the 1:2 *it:st* complexing

ratio, the model fails to reproduce the experimental helical pitch and experimental X-ray diffraction peak at 0.78 nm . Similar to the infinite triple helix model (9_1 -*it*/18₁-*st*), this peak is shifted to the left, associated with an increased pitch spacing. The density of this model was found to be $1.185 \pm 0.007 \text{ g/cm}^3$, well below the experimental value.

Figure 5 demonstrates that the 9_1 *it*-PMMA complex with 40-unit *st*-PMMA fragment model (9_1 -*it*/40mer-*st*) exhibits the best agreement with experimental X-ray diffraction profiles. The density range of $1.200 - 1.215 \text{ g/cm}^3$ for the four packing motifs is also in a good agreement with experiment, and the cohesive energy density range for this model is $387 - 399 \text{ J/cm}^3$, compared to values of $362 \pm 18 \text{ J/cm}^3$ and $287 \pm 9 \text{ J/cm}^3$ for the 10_1 -*it*/40mer-*st* and 9_1 -*it*/18₁-*st* models, respectively (Table 2).

Table 2. Simulated and experimental structural and thermodynamic properties of *it*-/*st*-PMMA stereocomplex crystals of Right Down (RD), Right Down/Right Up (RD/RU), Right Down/Left Down (RD/LD) and Right Down/Left Up (RD/LU) packing motifs.

| Description | Packing motif | Density (g/cm^3) | Helical Pitch <i>st</i> -PMMA (nm) | Cohesive Energy Density (J/cm^3) | Chain Width (nm) | Sum of Differences ^a (nm) |
|--|---------------|-----------------------------|------------------------------------|---|------------------|--------------------------------------|
| Experiment | - | 1.215 ⁴⁵ | 0.92 ± 0.02 ²⁴ | 361 ^b | - | - |
| 9_1 - <i>it</i> /18 ₁ - <i>st</i> | RD | 1.240 ± 0.001 | 0.97 ± 0.016 | 287 ± 9 | 1.68 ± 0.018 | 0.39 |
| 10_1 - <i>it</i> /40mer- <i>st</i> | RD | 1.185 ± 0.007 | 0.96 ± 0.007 | 362 ± 18 | 1.84 ± 0.007 | 0.27 |
| 9_1 - <i>it</i> /40mer- <i>st</i> | RD | 1.215 ± 0.007 | 0.90 ± 0.004 | 398 ± 2 | 1.85 ± 0.001 | 0.08 |
| 9_1 - <i>it</i> /40mer- <i>st</i> | RD/RU | 1.210 ± 0.001 | 0.89 ± 0.006 | 399 ± 1 | 1.85 ± 0.001 | 0.16 |
| 9_1 - <i>it</i> /40mer- <i>st</i> | RD/LD | 1.200 ± 0.001 | 0.90 ± 0.004 | 387 ± 1 | 1.86 ± 0.011 | 0.17 |
| 9_1 - <i>it</i> /40mer- <i>st</i> | RD/LU | 1.210 ± 0.001 | 0.90 ± 0.008 | 398 ± 2 | 1.84 ± 0.010 | 0.17 |

^a Sum of Differences refers to the sum of the numerical value differences between the peak positions of the simulated structures and the experimental X-ray diffraction. Thus, a smaller value indicates a better agreement with experiment. ^b Experimental cohesive energy density of PMMA with unspecified tacticity.⁴⁶

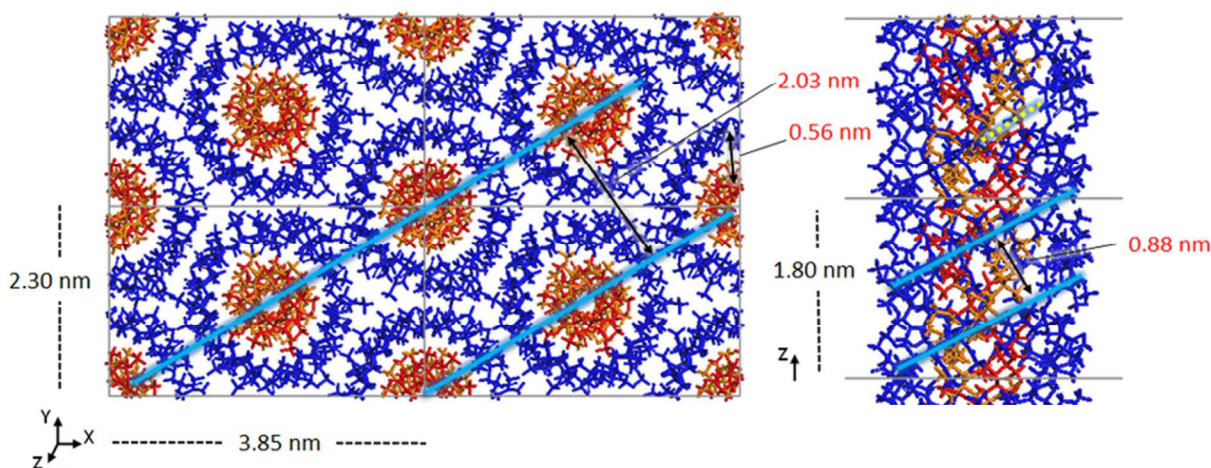


Figure 6. Optimized crystal structure model of 9_1 -*it*-/40mer-*st*-PMMA in the Right Down packing motif. The chain-chain spacing (left) and pitch spacing (right) are shown in light blue. The gap between 40-unit *st*-PMMA fragments is shown by a dotted yellow line.

Unlike the *it*-PMMA structures, there was little difference in density, cohesive energy density, or X-ray diffraction for the different packing motifs of the stereocomplex (Table 2). The average *st*-PMMA helical pitch of this model is $0.90 \pm 0.005 \text{ nm}$, in good agreement with the AFM measurements of $0.92 \pm$

0.02 ,²⁴ with approximately 20 MMA units per turn. While this results in an *it:st* complexing ratio of 9:20, it is important to note that the established *it:st* stoichiometric ratio of 1:2 is merely the best mixing ratio for complexation, and different mixing ratios still result in the same final stereocomplex.²¹

Additionally, the *it*-PMMA helical pitch of ~ 1.80 nm is in good agreement with the fiber X-ray diffraction experiments that show a fiber identity period of 1.84 nm.^{22,23} The optimized structure of the 9_1 -*it*/40mer-*st* model is shown in Figure 6.

When Yashima and colleagues proposed the triple helix model, they also proposed a quadruple helix model that could correspond to their AFM results with two strands of *st*-PMMA wrapped around an *it*-PMMA double helix.²⁴ We constructed models of the quadruple helix with 40-unit *st*-PMMA and both 9_1 and 10_1 *it*-PMMA (Figure S1, Supplementary Information), but the X-ray diffraction profiles and calculated densities of these models were in a lesser agreement with experiment (Figure S2, Table S1, Supplementary Information). While both the triple helix and quadruple helix models can in principle satisfy the AFM results as well as explain the observed weakness of the first-layer-line reflection (corresponding to a spacing of 1.84 nm) of the fiber X-ray diffraction,^{22,24} only the triple helix model fully reproduces the experimental density and powder X-ray diffraction profile.

Interestingly, the *st*-PMMA helix of the 9_1 -*it*/40mer-*st* model exhibits a distinct deviation from ideal helical geometry, not seen in either the 10_1 -*it*/40mer-*st* or 9_1 -*it*/18₁-*st* models (Figure 7). This non-ideal helical geometry is characterized by a broader distribution in backbone internal angles and torsions, as well as a small number of torsions evenly distributed approximately every 20 monomer units (2 per turn) of the *st*-PMMA chain that deviate widely from the standard values of around 180° for an ideal helix comprising 18 units per turn (Figure 8). Notably, this non-ideal geometry is required to reproduce the experimental X-ray diffraction peak at 0.78 nm, and is similar to the geometry found in the recently discovered and characterized stereocomplex of a cyclic form of 18-unit *st*-PMMA with linear double helix *it*-PMMA²⁷ (Figure 7c), which also exhibits an X-ray diffraction peak at 0.78 nm. The cyclic triple helix stereocomplex also has a similar fiber diameter to that of the 9_1 -*it*/40mer-*st* model (the linker unit of the cyclic *st*-PMMA corresponds to roughly two MMA units) and a corresponding X-ray diffraction peak at 2.08 nm.

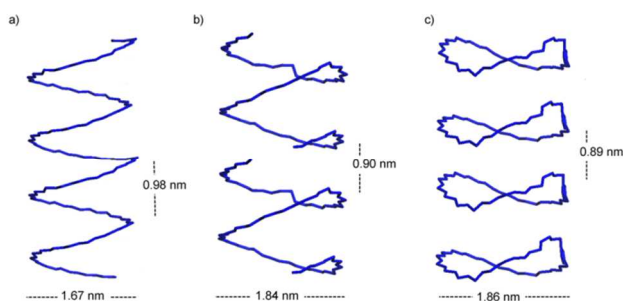


Figure 7. The syndiotactic helix backbone of the a) 9_1 -*it*/18₁-*st* b) 9_1 -*it*/40mer-*st* and c) 9_1 -*it*/cyclic-18mer-*st* stereocomplex models. The *it*-PMMA double helix is not shown. The larger diameter of the 9_1 -*it*/40mer-*st* and distinct helical curvature of this model enable the fit to the experimental X-ray diffraction peaks at 2.08 nm and 0.78 nm, respectively.

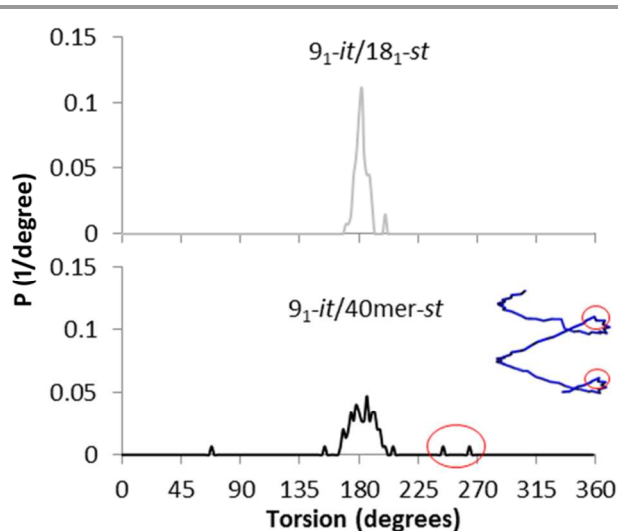


Figure 8. Backbone torsion distribution of the *st*-PMMA in the *it*-*st*-PMMA stereocomplex models. The 9_1 -*it*/18₁-*st* model represents an ideal helix, while the 9_1 -*it*/40mer-*st* model exhibits non-ideal helical geometry. The torsions associated with this non-ideal helical geometry are circled in red.

To further examine the PMMA stereocomplexation ratio, we constructed models of 36-unit *st*-PMMA fragments with infinite 9_1 -*it*-PMMA double helices (9_1 -*it*/36mer-*st*). While these systems maintained the 9:18 *it*- to *st*-PMMA monomer ratio of the Yashima model, the resulting structure had a density of 1.16 g/cm³; far below the predicted value. Interestingly, the overall structure resembled the non-ideal helical geometry of 9_1 -*it*/40mer-*st* model, but with wide gaps between the *st*-PMMA fragments.

We noted that the gap between successive *st*-PMMA fragments in the 9_1 -*it*/40mer-*st* model roughly corresponds to two MMA units. We thus constructed models of infinite *st*-PMMA with 21 units per turn. This 9_1 -*it*/21₁-*st* model exhibited a similar structure and X-ray diffraction profile to the 9_1 -*it*/40mer-*st* model, but had a cohesive energy density of 245 ± 21 J/cm³; far smaller than the predicted value. This further emphasizes that the helical pitch ratio cannot be exactly 2:1 (i.e. the *st*-PMMA cannot complete *exactly* two full turns in the distance required for the *it*-PMMA to complete one full turn).

In order to gain a better understanding of the interactions driving the stability of the supramolecular assembly, we determined the *st*:*it* contact area and total free volume of the 9_1 -*it*/40mer-*st* and 9_1 -*it*/18₁-*st* models. Our results show that both models exhibit similar free volume (approximately 10% of the total volume) and *st*:*it* contact area (approximately 35-36% of the total *st*-PMMA surface area is in contact with *it*-PMMA for both models). This suggests that the observed differences in thermodynamic and structural properties are not due to differences in the packing of the stereocomplexes. A decomposition of the cohesive energy density for the two models reveals that in particular the electrostatic interactions between the *st*- and *it*-PMMA of the 9_1 -*it*/18₁-*st* model are strongly unfavorable. Because the *it*- and *st*-PMMA have different helical pitches, a deviation from ideal helical

geometry is necessary to maximize the non-bond interactions as seen in the 9_1 -*it*/40mer-*st* model.

Conclusions

By using the X-ray diffraction profiles as blueprints, through MD simulation we have successfully mapped the most likely configuration of *it*-PMMA stereocomplex, which is a 9_1 double helix with a helical pitch of 1.8 nm and a tilt angle of 54° . For the *it*-*st*-PMMA triple-helix stereocomplex, the most likely configuration was determined to be a 9_1 *it*-PMMA double helix with a helical pitch of 1.85 nm surrounded by a single helix of *st*-PMMA with an average helical pitch of approximately 0.9 nm, and approximately 20 units per turn. Additionally, we found that the outer *st*-PMMA helix must have a fiber diameter of at least 1.8 nm and a non-ideal helical geometry to reach agreement with the experimental density and X-ray diffraction profile. A 1:2 *it*- to *st*-PMMA complexing ratio cannot simultaneously reproduce the structural features and the correct density. These results enabled us to suggest an all-atom model of the linear *it*-*st*-PMMA triple helix stereocomplex that accurately reproduces experimental X-ray diffraction profiles for the first time.

The molecular dynamic simulation described in this study provides a vital tool to resolve molecular-level arrangement of complex molecular structures, when experimental means are inadequate. Furthermore, the reported molecular mapping technique is expected to have a wide scope of applications in macro(supra)molecular chemistry, including design and synthesis, structural characterization and property simulation.

Acknowledgements

We acknowledge the generous allocation of high performance computational resources from the Australian National Computational Infrastructure (NCI), the Western Australian computational facility (iVEC), the Victorian Partnership for Advanced Computing (VPAC) and the Victorian Life Sciences Computational Initiative (VLSCI). We thank Dr. Qiao Sun for helpful comments on the manuscript. We also thank the reviewers for their comments and suggestions.

Notes and references

^a School of Aerospace, Mechanical and Manufacturing Engineering, RMIT University, GPO Box 2476, VIC 3001, Australia.

^b Department of Chemical and Biomolecular Engineering, University of Melbourne, Melbourne, VIC 3010, Australia

^c Department of Applied Chemistry, Nagoya University, Chikusa-ku, Nagoya 464-8603, Japan

[†] Current address: IBM Research Australia, 5/204 Lygon St, Melbourne, Victoria 3001, Australia

* Corresponding author: irene.yarovsky@rmit.edu.au

† A.C. and G.Y. contributed equally.


1 R. D. Harkness, *Biol. Rev.*, 1961, **36**, 399-455.

2 K. Matyjaszewski, *Science*, 2011, **333**, 1104-1105.

- 3 F. S. Bates, M. A. Hillmyer, T. P. Lodge, C. M. Bates, K. T. Delaney and G. H. Fredrickson, *Science*, 2012, **336**, 434-440.
- 4 T. Serizawa, K.-i. Hamada, T. Kitayama, N. Fujimoto, K. Hatada and M. Akashi, *J. Am. Chem. Soc.*, 2000, **122**, 1891-1899.
- 5 T. Serizawa, K.-i. Hamada and M. Akashi, *Nature*, 2004, **429**, 52-55.
- 6 T. Kawauchi, A. Kitaura, J. Kumaki, H. Kusanagi and E. Yashima, *J. Am. Chem. Soc.*, 2008, **130**, 11889-11891.
- 7 T. Kawauchi, J. Kumaki, A. Kitaura, K. Okoshi, H. Kusanagi, K. Kobayashi, T. Sugai, H. Shinohara and E. Yashima, *Angew. Chem. Int. Ed.*, 2008, **120**, 525-529.
- 8 T. Kawauchi, J. Kumaki and E. Yashima, *J. Am. Chem. Soc.*, 2006, **128**, 10560-10567.
- 9 M. Crne, J. O. Park and M. Srinivasarao, *Macromolecules*, 2009, **42**, 4353-4355.
- 10 C. Ronco, *Polymethylmethacrylate: a flexible membrane for a tailored dialysis/volume*, Karger, Basel; New York, 1999.
- 11 T. Serizawa, T. Sawada and T. Kitayama, *Angew. Chem. Int. Ed.*, 2007, **119**, 737-740.
- 12 T. Serizawa, T. Sawada, H. Matsuno, T. Matsubara and T. Sato, *J. Am. Chem. Soc.*, 2005, **127**, 13780-13781.
- 13 K. Könnicke and G. Rehage, *Colloid Polym. Sci.*, 1981, **259**, 1062-1069.
- 14 J. Spěváček and B. Schneider, *Adv. Colloid Interface Sci.*, 1987, **27**, 81-150.
- 15 S. Bistac and J. Schultz, *Macromol. Chem. Phys.*, 1997, **198**, 531-535.
- 16 H. Kusanagi, Y. Chatani and H. Tadokoro, *Polymer*, 1994, **35**, 2028-2039.
- 17 F. Bosscher, G. Tenbrinke, A. Eshuis and G. Challa, *Macromolecules*, 1982, **15**, 1364-1368.
- 18 H. Kusanagi, H. Tadokoro and Y. Chatani, *Macromolecules*, 1976, **9**, 531-532.
- 19 T. G. Fox, B. S. Garrett, W. E. Goode, S. Gratch, J. F. Kincaid, A. Spell and J. D. Stroupe, *J. Am. Chem. Soc.*, 1958, **80**, 1768-1769.
- 20 A. Y. Koshevnik, M. M. Kuskov, N. M. Lubman, L. I. Mekenitskaya, O. V. Orlova, A. A. Pasynskaya, E. A. Razumovskaya and L. M. Shul'pina, *Polym. Sci. USSR*, 1970, **12**, 2384-2390.
- 21 E. J. Vorenkamp, F. Bosscher and G. Challa, *Polymer*, 1979, **20**, 59-64.
- 22 E. Schomaker and G. Challa, *Macromolecules*, 1989, **22**, 3337-3341.
- 23 F. Bosscher, G. Ten Brinke and G. Challa, *Macromolecules*, 1982, **15**, 1442-1444.
- 24 J. Kumaki, T. Kawauchi, K. Okoshi, H. Kusanagi and E. Yashima, *Angew. Chem. Int. Ed.*, 2007, **46**, 5348-5351.
- 25 J. Kumaki, T. Kawauchi, K. Ute, T. Kitayama and E. Yashima, *J. Am. Chem. Soc.*, 2008, **130**, 6373-6380.
- 26 K. Hatada, K. Ute, K. Tanaka, T. Kitayama and Y. Okamoto, *Polym. J.*, 1985, **17**, 977-980.
- 27 J. M. Ren, K. Satoh, T. K. Goh, A. Blencowe, K. Nagai, K. Ishitake, A. J. Christofferson, G. Yiapanis, I. Yarovsky, M. Kamigaito and G. G. Qiao, *Angew. Chem. Int. Ed.*, 2014, **53**, 459-464.
- 28 T. Shibata, K. Satoh, M. Kamigaito and Y. Okamoto, *J. Polym. Sci. A Polym. Chem.*, 2006, **44**, 3609-3615.
- 29 Y. Miura, T. Satoh, A. Narumi, O. Nishizawa, Y. Okamoto and T. Kakuchi, *J. Polym. Sci. A Polym. Chem.*, 2006, **44**, 1436-1446.

- 30 Y. Miura, T. Satoh, A. Narumi, O. Nishizawa, Y. Okamoto and T. Kakuchi, *Macromolecules*, 2005, **38**, 1041-1043.
- 31 T. K. Goh, J. F. Tan, S. N. Guntari, K. Satoh, A. Blencowe, M. Kamigaito and G. G. Qiao, *Angew. Chem. Int. Ed.*, 2009, **48**, 8707-8711.
- 32 The melting temperature of PMMA stereocomplex is lower than expected due to the low tacticity and molecular weight of *st*-PMMA. Stereocomplexes made from low molecular weight polymers generally have low thermal stabilities. For review on this matter, please refer to: J. Spěvák, B. Schneider, *Adv. Colloid Interface Sci.* 1987, **27**, 81-150. 33 S. Plimpton, *J. Comput. Phys.*, 1995, **117**, 1-19.
- 34 Materials Studio 6.1, Accelrys Software Inc: San Diego, CA, USA, 2012.
- 35 PCFF is distributed along with Accelrys' software package Materials Studio. More information may be found on the Accelrys website: www.accelrys.com
- 36 H. Sun, S. J. Mumby, J. R. Maple and A. T. Hagler, *J. Am. Chem. Soc.*, 1994, **116**, 2978-2987.
- 37 S. Chunsrivirod and B. L. Trout, *Langmuir*, 2011, **27**, 6910-6919.
- 38 C. De Leener, E. Hennebicq, J.-C. Sancho-Garcia and D. Beljonne, *J. Phys. Chem. B*, 2009, **113**, 1311-1322.
- 39 I. Diaz, E. Diez, J. Camacho, S. León and G. Ovejero, *Fluid Phase Equilib.*, 2013, **337**, 6-10.
- 40 G. Yiapanis, A. J. Christofferson, M. Plazzer, M. Weir, E. L. Prime, G. G. Qiao, D. H. Solomon and I. Yarovsky, *Langmuir*, 2013, **29**, 14451-14459.
- 41 R. W. Hockney and J. W. Eastwood, *Computer Simulation Using Particles*, Adam Hilger, New York, 1989.
- 42 S. Nose, *J. Chem. Phys.*, 1984, **81**, 511-519.
- 43 W. G. Hoover, *Phys. Rev. A*, 1985, **31**, 1695-1697.
- 44 J. Ramos and T. Lazaridis, *Protein Sci.*, 2011, **20**, 1845-1855.
- 45 K. E. Min and D. R. Paul, *J. Polym. Sci. Pol. Phys.*, 1988, **26**, 1021-1033.
- 46 H. J. Vandenburg, A. A. Clifford, K. D. Bartle, R. E. Carlson, J. Carroll and I. D. Newton, *Analyst*, 1999, **124**, 1707-1710.
- 47 B. B. Sauer and G. T. Dee, *Macromolecules*, 2002, **35**, 7024-7030.

Table of contents entry

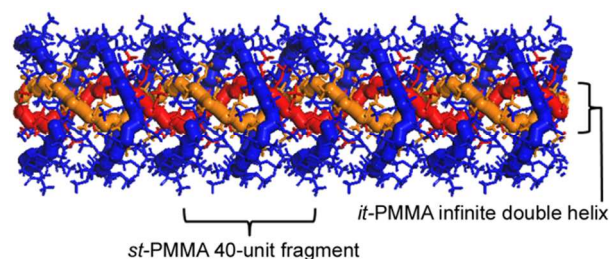

The structure of the *it*-/*st*-poly(methyl methacrylate) (PMMA) triple-helix stereocomplex is composed of a double helix of *it*-PMMA of 9 units per turn surrounded by a single helix of *st*-PMMA with an average of 20 units per turn.