

Soft Matter

Accepted Manuscript



This is an *Accepted Manuscript*, which has been through the Royal Society of Chemistry peer review process and has been accepted for publication.

Accepted Manuscripts are published online shortly after acceptance, before technical editing, formatting and proof reading. Using this free service, authors can make their results available to the community, in citable form, before we publish the edited article. We will replace this *Accepted Manuscript* with the edited and formatted *Advance Article* as soon as it is available.

You can find more information about *Accepted Manuscripts* in the [Information for Authors](#).

Please note that technical editing may introduce minor changes to the text and/or graphics, which may alter content. The journal's standard [Terms & Conditions](#) and the [Ethical guidelines](#) still apply. In no event shall the Royal Society of Chemistry be held responsible for any errors or omissions in this *Accepted Manuscript* or any consequences arising from the use of any information it contains.

Relating foam and interfacial rheological properties of β -lactoglobulin solutions

M. Lexis, N. Willenbacher

Department of Chemical Engineering, Karlsruhe Institute of Technology, 76131 Karlsruhe, Germany

Abstract

We have determined bulk rheology of β -lactoglobulin (BLG) foams and surface viscoelasticity of corresponding protein solutions varying pH as well as type, valency and concentration of added salt in a wide range. Foam rheology was characterized by the storage modulus G_0 , the apparent yield stress τ_y , and the critical strain $\gamma_{c,foam}$ defining the cessation of linear viscoelastic response. These quantities were determined at gas volume fractions ϕ between 82% and 96%. Surface viscoelasticity was characterized in shear and dilation, corresponding shear and dilational moduli G_i' , E' as well as the critical stress $\tau_{c,surface}$ and strain $\gamma_{c,surface}$ marking the onset of non-linear response in oscillatory surface shear experiments were determined at fixed frequency.

Beyond the widely accepted assumption that G_0 and τ_y are solely determined by the Laplace pressure within the droplets and the gas volume fraction we find that both quantities strongly depend on corresponding interfacial properties. G_0 increases linearly with G_i' and even stronger with E' , τ_y varies proportional to $\tau_{c,surface}$ and $\gamma_{c,foam}$ scales linearly with $\gamma_{c,surface}$. Furthermore, deviations from these simple scaling laws with significantly higher reduced G_0 and τ_y values are observed only for foams at pH 5 and when trivalent salt was added. Then also the dependence of these quantities on ϕ is unusually weak and we attribute these findings to protein aggregation and structure formation across the lamellae then dominating bulk rheology.

1. Introduction

Foams that are stabilized by proteins play an important role in the food industry. The aerated structure gives a special look, mouthfeel and taste to the product which is well accepted by the customers. The foam structure consisting of jammed gas bubbles is responsible for the peculiar rheological behavior. Under low stresses the bubble network is able to store energy. The bubbles get deformed but do not move past each other. Hence, in this regime the elastic properties dominate. When a certain stress, called yield stress, is exceeded, the bubbles start sliding past each other and the foam as a whole flows easily like a liquid. Foam properties like stability and rheology are important issues not only for the end product but also during processing, where transport, heating and mixing take place. Understanding and controlling the parameters influencing foam properties are of great interest in the food technology and many studies in this regard have been established. It is well known that the gas volume fraction, bubble size distribution and surface tension are the most important parameters influencing elastic properties and yield stress of so-called liquid foams including a low viscosity of the continuous phase (Eqs 1,2).¹⁻⁵ The latter was found to be additionally affected by the liquid viscosity.^{6,7} In Eqs 1 and 2 the predictions of the storage modulus and yield stress initially proposed by Mason et al. and extended in our previous study are shown.

$$G_0 = a \cdot \left(\frac{\sigma}{r_{32}}\right) \cdot \phi(\phi - \phi_c) \quad (1)$$

$$\tau_y = k \cdot \left(\frac{\sigma}{r_{32}}\right) \cdot \left(\frac{\eta_L}{\eta_w}\right)^{0.3} \cdot (\phi - \phi_c)^2 \quad (2)$$

where σ is the surface tension, r_{32} the Sauter mean radius, ϕ the gas volume fraction and ϕ_c represents the maximum packing fraction of the bubbles before they start to deform into non-spherical shapes. The latter has usually been an estimated value but can also be calculated from the measured bubble size distribution, as we proposed recently.⁷ The prediction of the yield stress includes an empirically determined factor for the (weak) contribution of the liquid viscosity, where η_L is the continuous phase viscosity and η_w the water viscosity at same conditions. This phenomenological extension of the model equation proposed by Mason et

al.^{1,2} has been derived from measurements on foams made from casein, whey protein isolate and a mixture of synthetic surfactants. The solvent viscosity was varied using different water / glycerol mixtures and sugar solutions.⁸ Each equation includes a numerical pre-factor, k and a respectively. Values between 0.5 and 1 have been used for these constants so far in the literature without further discussion.^{1,2,5} In a recent study we found k values between 1 and 7 and a values varying between 2 and 22.

The film dilational modulus is defined by $E = -A d\pi / dlnA$ where π is the surface pressure, and A is the area of the film. This modulus E is thus a measure of the resistance of a film to change in its area. Surface shear rheology gives information about the resistance of an adsorbed layer at the interface against shear. Hence, it is sensitive to the structural state of the adsorbed molecules. From a colloidal view a surface elastic modulus arises either from attractive interactions between neighboring particles or particles caging at high packing density.⁹ From interfacial oscillatory shear measurements another quantity can be extracted, the critical shear stress $\tau_{c,surface}$ which denotes the end of the linear viscoelastic regime. For $\tau > \tau_{c,surface}$ the deformation response becomes non-linear indicating a structural change in the surface layer.¹⁰ Surface shear rotational experiments also show yielding behavior for several protein solutions which was investigated by Martin et al.¹¹ They came to the conclusion that the critical shear stress indeed induces a fracture within the protein film and can therefore be regarded as intrinsic property of the protein layers. A higher critical stress represents a higher strength of the protein layer.

Surface rheology has been mainly discussed in terms of foam formation and stability.¹²⁻¹⁶ Little is known so far about the correlation between foam rheology and the surface viscoelasticity of corresponding protein solutions although these features must be coupled since shearing a foam induces stretching and compression of the lamellae and hence the surfactant layer at the air liquid interface. The group of Cohen-Addad has thoroughly investigated the linear viscoelastic response G^* of surfactant foams in a broad frequency range. Based on the model of Princen¹⁷ they propose a relationship between $G^*(\omega)$ and the

complex angular modulus $A^*(\omega)$ determined from dynamic compression tests of two adjacent bubbles connected by a single lamella. The quantity $A^*(\omega)$ is further assumed to be proportional to the dilational modulus $E^*=E'+iE''$. In particular they could show that the fast relaxation processes observed in foams are determined by the surfactant transport within the liquid films.¹⁸ The frequency ω_c characterizing the onset of this scaling regime is assumed to be proportional to the ratio of the dilational modulus E' and an effective interfacial viscosity including the surface viscosity E''/ω_c , the solution viscosity and the lamellar thickness as well as the bubble diameter. Different scaling laws relating ω_c to the foam modulus G are proposed for rigid and mobile interfaces and these scaling laws are confirmed experimentally for two different types of surfactant foams.¹⁹ Deviations from the simple $G^* \sim \omega^{1/2}$ scaling are observed for foams made from surfactants providing very rigid interfaces ($E^* \approx 102$ Pa).²⁰ So far a systematic comparison between foam plateau modulus and interfacial shear or dilational moduli for protein foams is missing.

The viscous stress in continuously sheared foams scales with the capillary number Ca as $\tau_v \sim Ca^n$ and the exponent n depends on surface mobility and viscoelasticity. For rigid interfaces $n = 1/4$ and for mobile interfaces $n = 1/2$ have been predicted theoretically and confirmed experimentally.²¹⁻²³

A direct empirical correlation between the yield stress and the interfacial dilation modulus E' of whey protein foams made at different pH, concentration and valency of added salt has been proposed by Davis et al.²⁴ However, they do not take into account the effect of bubble size (distribution) and gas volume fraction on τ_y , although pH and ionic strength are known to affect the absolute value of this quantity substantially. Dimitrova and Leal-Calderon²⁵ reported a correlation between shear modulus of concentrated emulsions stabilized by different proteins and dilational moduli of the corresponding protein solutions. But it should be noted that their E' values were taken from the literature probably determined at protein concentration, pH and ionic strength conditions different from those relevant for the probed emulsions. Finally, it should be mentioned that also for particle stabilized so-called Pickering

emulsions the modulus G_0 is not only determined by the interfacial tension between the liquid phases but also by an elastic contribution resulting from the attractive interaction among the stabilizing particles.²⁶

In this study we attempt to directly correlate surface and foam rheological properties of β -lactoglobulin (BLG) solutions. Therefore, the interfacial layer properties were systematically changed by varying the ionic strength, the type of salt and the solution pH. We propose a unique relationship between foam modulus G_0 and interfacial moduli G_i' or E' , between the foam yield stress τ_y and the critical stress or strain at which an interfacial layer structure breaks down. We demonstrate the validity of this correlation in a wide range of gas volume fraction irrespective of bubble size distribution and Laplace pressure. Finally we discuss the limitation of this approach in terms of structure formation across lamellae induced under certain conditions of ionic strength, ion valency and pH.

2. Experimental Details

2.1 Solution preparation and measurements

Solutions of 1 wt% β -lactoglobulin (BLG, used as received) were prepared by dissolving the protein powder kindly provided by the group of Ulrich Kulozik (University of Munich, Germany) in ultrapure water (Milipore, 18 M Ω). Variation of pH was achieved by adding appropriate amounts of NaOH or HCl (Carl Roth 1N standard solutions), respectively. Ionic strength was varied adding NaCl (99.5%, Roth Chemicals) between 10-100 mM NaCl. The influence of ion type and valency was investigated with addition of 50 mM KCl, LiCl, NH₄Cl (99%, Roth Chemicals), CaCl₂ (98%, Roth Chemicals) or NdCl₃ (99.9%, Alfa Aesar).

The surface tension of all solutions was measured with the pendant drop method (Krüss, DSA 100) at 21°C and a drop age of 30 min as described elsewhere.⁷

The liquid viscosities were measured with the Ares rotational rheometer (TA Instruments) using a Couette geometry (17/16.5 mm). All solutions showed Newtonian behavior in the range of imposed shear rates $\dot{\gamma}= 10\text{-}1000\text{ s}^{-1}$ with viscosities between 0.94-1.1 mPas.

Interfacial dilational elasticities were determined at 21°C and a drop age of 30 min using the oscillating bubble method (Krüss, DSA 100). The oscillations were generated by a piezo pump that pulsed with a frequency of 0.1 Hz and an amplitude of 0.3. The amplitude resulted in a drop deformation between 2 and 3 %, depending on the drop volume. As the drop was generated manually it was not possible to keep the volume for every measurement exactly the same. Oscillatory deformation was applied for a time period of 100 s and 1200 pictures were analyzed to calculate $E^* = E' + iE''$.

Interfacial shear viscoelastic properties were determined at 25 °C and a surface age of 30 min with a stress controlled rotational rheometer (TA Instruments, DHR3) using the double wall ring geometry ($D_{\text{ring}}=70\text{ mm}$). Details about this measuring geometry can be found in.²⁷ The viscoelastic properties were recorded at a frequency of 0.7 Hz and a deformation amplitude of 1%, which did not exceed the linear viscoelastic regime of any sample solution. From these measurements we determined the surface elastic modulus G'_i . Measurements with increasing deformation amplitude allowed for the determination of the width of linear viscoelastic regime (LVE). When non-linear deformation response sets in, G'_i starts to decrease and the end of the LVE was determined to be reached when $G'_i = 0.9 \cdot G'_{i\text{LVE}}$. At this point the critical deformation $\gamma_{c,\text{surface}}$ and shear stress $\tau_{c,\text{surface}}$ were extracted.

It should be noted that we have characterized the interfacial rheology of protein solutions at the same concentration at which foam preparation and foam rheology was done. This is in contrast to many other studies on interfacial rheology where experiments were done at much lower concentration of amphiphils in order to ensure a monolayer of surface active ingredient at the air/water interface. But one has to be aware that the structure of an interfacial layer, especially in the case of proteins, can substantially change with concentration and a correlation of foam and interfacial rheology can only be expected if the interfacial layer is the

same in both sets of experiments. However, multiple layers of proteins may be present at the surface, i.e. the thickness of the layer may not be negligible. Therefore, the measured quantities E' , G_i' have to be treated as apparent values.

2.2 Foam preparation and measurements

The protein solutions were preheated to 50 °C in a water bath to obtain foams that are stable enough for reproducible rheological measurements. The increase in temperature fastens adsorption kinetics but does not affect the protein structure. Foams were produced using a glass filter fused in a glass pipe as described elsewhere⁷ and nitrogen was purged through the pores with $\dot{V}= 60$ ml/min. As soon as the foam reached the column height the nitrogen flow was stopped and recording of the foam age was started.

The time dependent gas volume fraction was determined using a conductivity electrode with integrated temperature sensor (WTW, Cond 340i) as described in a previous study.⁷ The measuring gap of the electrode had a length of 2 cm. The foam volume within the gap is similar to that we used for rheological characterization. Hence, the measured conductivity is an appropriate average value. Conductivity measurements were performed in a region of the foam column close to that from where the samples for rheological measurements were taken.

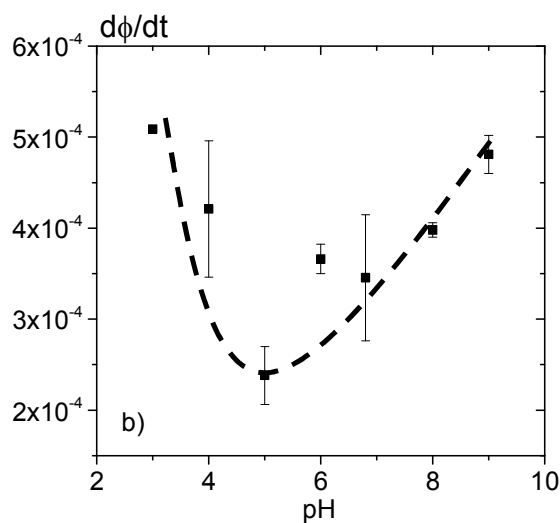
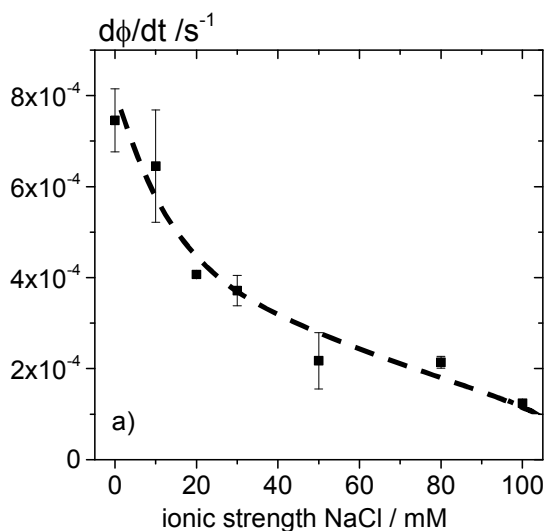


Figure 1: Drainage velocity of the protein foams with different ionic strengths (a) or pH (b). Data were calculated from the time period in which each foam drained from 85% to 86% gas volume fraction.

Fig.1 shows the drainage velocity for the protein foams with different ionic strengths and different pH. Increasing the amount of NaCl leads to slower liquid drainage. This is attributed to the reduced electrostatic repulsion between the proteins leading to closer protein packing and increased probability of aggregation. Such protein aggregates are able to plug the junctions of the Plateau borders so that the drainage of the liquid is slowed down. Moreover, the surface mobility can have an influence on foam drainage.^{28,29} As the interface is supposed to become more rigid with increasing ionic strength (at least upon addition of 20 mM as discussed in sec. 3.1.4) this might be an additional reason for the slower drainage. The pH dependent drainage velocity shows a minimum at pH 5. This is very close to the isoelectric point (IEP) where protein net charge is close to zero and therefore, aggregates plugging the liquid channels occur more frequently. Higher distance to the IEP increases the protein solubility and at the same time the drainage velocity.

The bubble size distribution was determined by taking pictures with an endoscopic CCD camera (Lumenera LU 160, resolution 1392 x 1040) that was placed inside the foam. The Sauter mean radius r_{32} was extracted from image analysis with the software iPS (Visiometrics, Germany).

Foam rheological measurements were carried out with a Rheoscope 1 (Thermofisher, Germany) using a parallel plate geometry with a diameter of 60 mm. The surfaces were covered with sandpaper to minimize wall slip effects and the gap was set to 6 mm. The measurement time was 60 s in order to limit time dependent changes in foam structure. Each foaming system was measured at different foam ages and hence, different gas volume fractions ϕ between 82-94%.

The apparent yield stress was determined from steady shear measurements where increasing stresses were applied. Depending on foam composition the initial stresses were set between 3 and 5 Pa and the final stresses between 50 and 125 Pa. As already extensively discussed in ⁷ the apparent yield stress is independent of start and end point of the stress ramp experiment as well as on the number of data points taken. In particular, it was shown that the sample deformation within the gap is non-uniform when the yield point is exceeded. We assume this effect is weak just around the yield point and experiments determining τ_y and γ_c were highly reproducible but the parameters should be treated as apparent values.

The moduli G' and G'' of the foam were determined from oscillatory shear measurements with varying stress amplitude at a frequency $f = 1$ Hz. The moduli did not show frequency dependence between 0.01-10 Hz. Hence, the measured G' -value in the linear viscoelastic regime is called plateau modulus G_0 . The deformation amplitude that decreased G' down to $0.9 \cdot G_0$ was taken as critical deformation $\gamma_{c,foam}$. It is worth noting that this critical deformation at which non-linear deformation sets in is well below the yield point γ_y at which bubbles start to flow past each other. This yielding occurs at the stress or deformation amplitude at which $G' = G''$.⁷

3. Results and discussion

3.1 Variation of ionic strength

3.1.1 Foam and solution properties

In Table 1 the values of the surface tension measured after 30 minutes surface aging, the mean Sauter radii of the foam bubbles and the range of gas volume fractions where foam rheology measurements took place are shown. The surface tension does not significantly change with addition of NaCl to the protein solutions. The initial mean bubble size decreases when adding 50 mM salt but does not change upon further addition of NaCl.

Ionic strength / mM	0	10	20	30	50	80	100	Max. error / %
σ / mN/m	51.5	50	49.5	49.6	50.1	49.5	49.9	1
r_{32} / μm	110-154	114	121	124	78-175	80-140	77-145	14
ϕ / %	87-96	89	89	89	86-93	85-93	84-91	1

Table 1: Surface tension of the protein solutions after 30 minutes surface aging, bubble radii and gas volume fractions in the range of foam ages where the rheological measurements took place. The maximum error is the standard deviation of three measurements at a given ionic strength.

3.1.2 Oscillatory shear measurements

In Fig. 2 oscillatory shear stress amplitude sweeps are shown for the BLG foams with different ionic strengths at similar gas volume fraction $\phi = 89\%$. For all foams G' and G'' stay nearly constant at low stresses in the linear viscoelastic regime. G' is always much higher than G'' and when G' increases, G'' also increases. All G' curves (Fig. 2a) show a decrease before they cross the G'' curve (intersections marked with crosses) with a negative slope increasing with increasing ionic strength. In the same stress amplitude range the G'' values (Fig. 2b) also show interesting behavior. For the foams without salt and with 10 mM NaCl the curves go through a local minimum and a subsequent local maximum just before crossing the G' curve. For higher ionic strengths the minimum in G'' essentially vanishes and the curves just exhibit a pronounced maximum which is shifted to higher stress amplitude values with increasing ionic strength. Such peaks have already been found for surfactant foams with gas volume fractions higher than 74%.³⁰ The foams with lower gas volume fractions did not

show this maximum which was explained by the occurrence of plastic deformation prior to yielding. Other studies^{31,32} consider the point where dissipation is maximal as transition point from elastic to viscous behavior, hence as the yield point. The simultaneous decrease of G' and G'' for salt concentrations up to 30 mM indicates a gradual structure break down. Video recordings of sheared foams reveal that the bubbles start to slide past each other, i.e. the foam yields, when the maximum in G'' or the crossover of G' and G'' is reached as also reported in earlier studies.^{31,32} Similar behavior has been reported for whey protein isolate foams⁷ and was explained as follows: In several studies BLG has been found to form aggregates in thin liquid films that are able to “glue” the surfaces together.^{33,34} The simultaneous decrease of both moduli was interpreted as a gradual destruction of the intralamellar protein networks before the bubbles start to move past each other. But there is no direct experimental proof for this intralamellar network and a structural break down might also occur within the interface where the proteins form aggregated networks due to dominant attractive interactions. This network structure seems to be fully developed at high ionic strengths (80 mM, 100 mM) and then provides a uniform rigid surface layer stabilizing the foam and leading to a sharp decay of G' and G'' and a well defined yield point. At lower ionic strength the moduli decay simultaneously in a broad range of stress amplitude values between the onset of non-linear deformation and final yielding. The extended range between the LVE regime and the yield point is attributed to a gradual breakdown of the non-uniform, imperfect network structure within the interface (and or across the lamellae) supposed to be present at lower ionic strength when attractive interactions are partly balanced by electrostatic repulsion.

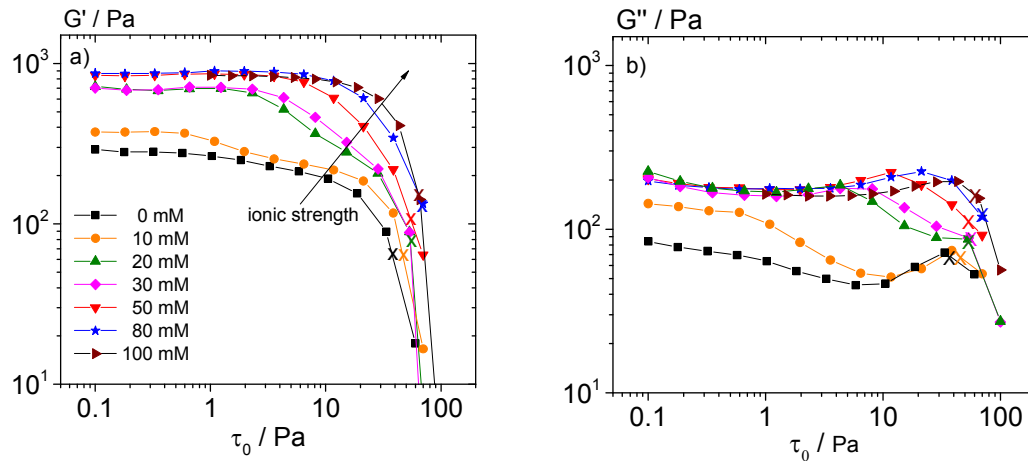


Figure 2: Oscillatory shear experiments at a fixed frequency $f = 1$ Hz but varying stress amplitude for BLG foams ($\phi = 89\%$) at different ionic strength of NaCl.

3.1.3 Yield Stress and Storage Modulus of the Foams

Fig. 3 shows the yield stress values and the storage moduli normalized by Laplace pressure σ/r_{32} and $(\phi - \phi_c)^2$ or $\phi(\phi - \phi_c)$, respectively and the critical deformation of the BLG foams for different NaCl concentrations. The normalization is derived from Eqs 1 and 2 and results in a collapse of data taken at different gas volume fractions ϕ to a single master curve. The normalized storage moduli increase sharply and then levels off to a constant value of about 12 at an ionic strength of 30 mM. At such high salt concentrations adsorption of the proteins at the interface is enhanced due to a reduced electrostatic repulsion. Also a change to a compact folded shape that allows closer packing at the interface and increased lateral attraction due to counterion screening may occur.³⁵ Accordingly, these closer packing of proteins increases the stress needed to deform the bubbles which corresponds to the measured storage modulus. Additionally the protein aggregates that might occur more frequently at higher ionic strength could improve network formation thus further adding a

mechanical strength. These effects are only observed up to 20 mM NaCl, higher ionic strength does not lead to further increase of the normalized G_0 values. In contrast, the normalized yield stress and critical deformation increase monotonically with increasing ionic strength.

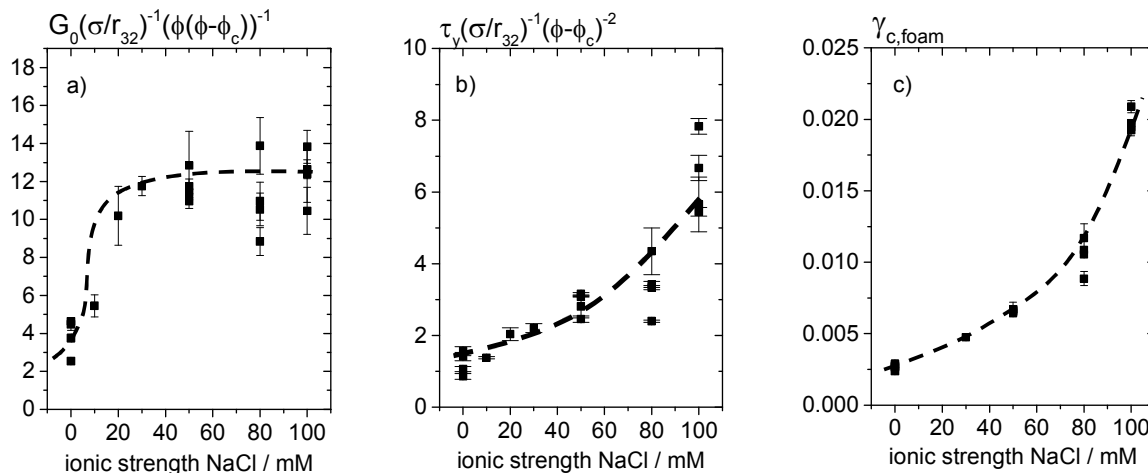


Figure 3: a) storage moduli normalized by Laplace pressure (σ/r_{32}) and $\phi(\phi-\phi_c)$ and b) yield stresses normalized by Laplace pressure and $(\phi-\phi_c)^2$ c) critical deformation of BLG foams. All rheological quantities are measured at various gas volume fractions (see Table 1) and different ionic strengths.

3.1.4 Surface Rheology

Fig. 4a shows the elastic moduli of the surfaces in dilation (E') and in shear (G'_i). Both quantities show the same trend when increasing the ionic strength. Adding 10 mM NaCl leads to an increase of E' and G'_i but further addition of salt does not have any effect. The increase of attractive interactions probably causes the higher E' and G'_i values after addition of salt. In Figs. 4b and c the critical shear stress $\tau_{c,surface}$ and deformation $\gamma_{c,surface}$ of the surface layer is plotted versus the ionic strength. In contrast to the surface elastic moduli, $\tau_{c,surface}$ increases monotonically, indicating that a higher stress is required to destroy the

interfacial layer structure formed at higher ionic strength. Finally, $\gamma_{c,surface} \approx \tau_{c,surface} / G_i'$ increases monotonically with increasing ionic strength. Hence, the stress needed to deform the protein structure at the interface is not affected by ionic strength higher than 10 mM but the stress and deformation that are needed to break the structure increase continuously with ionic strength in the range investigated here.

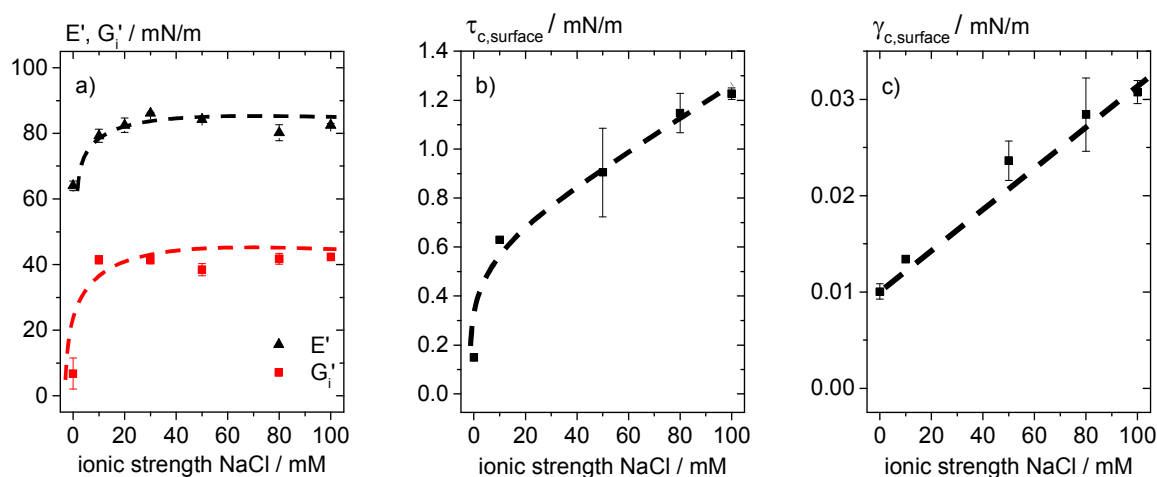


Figure 4: a) Surface elastic modulus in dilation (E') and shear (G_i'), b) critical shear stress $\tau_{c,surface}$ and c) critical deformation $\gamma_{c,surface}$ of the surface layer in dependence of the ionic strength for 1 % BLG solutions

3.2 Variation of the kind and the valency of the cation

3.2.1 Foam and solution properties

Tab. 2 shows the characteristic properties of the solutions and foams prepared with 50 mM salt of different type and valency. The surface tension is not significantly affected by the kind of added salt, whereas the initial bubble radii and the bubble size distribution increase with the valency of the cation. Especially when 50 mM $NdCl_3$ were added, the foams possess comparably big bubbles with a broad size distribution as reflected by the high ϕ_c value.⁷ This is most likely due to the occurrence of aggregated proteins as a consequence of the strongly suppressed electrostatic repulsion in the presence of trivalent ions. More and/or bigger protein clusters result in a lower affinity of the proteins to adsorb at the interface. Hence, not

all arising bubbles can be immediately stabilized what leads to an overall increase of the bubble size and a broader distribution.

	NH ₄ Cl	KCl	LiCl	CaCl ₂	NdCl ₃	Max. error / %
σ / mN/m	46.6	48.7	47.5	47.1	48.7	2
r_{32} / μm	93-183	84-175	93-145	105-278	220-270	10
ϕ / %	86-92	82-90	84-90	84-91	92-95	1
ϕ_c	71.5	71.3	70.7	73.0	84.9	4

Table 2: Surface tension of the protein solutions with different kinds of salt after 30 minutes surface aging. Bubble radii and gas volume fractions were determined at various times in the range of foam ages where the rheological measurements took place. In all cases the salt concentration was chosen to be 50 mM. The standard deviation of three measurements performed at a constant foam age and for a given kind of salt was calculated. The maximum standard deviation obtained from data for different foam ages and kinds of salt is listed here as maximum error.

3.2.3 Yield Stress and storage modulus of the foams

Figs 5a, b and c show the reduced storage moduli, reduced yield stresses and $\gamma_{c,\text{foam}}$ data, respectively for the different salts added. No difference is observed for the foams made from solutions including different monovalent salts. The addition of the divalent salt CaCl₂ leads to lower values in reduced G_0 but to higher values in reduced τ_y and $\gamma_{c,\text{foam}}$ compared to the monovalent salts. In particular, for the latter the difference is very pronounced. Each ion behaves differently when coming into contact with the protein. It is a balance between binding to the protein and preferential hydration (exclusion of the salt from the protein surface) of the protein.^{36,37} Ca²⁺ is known to bind very strongly to BLG which could lead to conformational changes of the protein resulting in an increase of the hydrophobic surface area leading to stronger protein-protein interactions. Also, the formation of ionic bridges cross-linking the protein molecules is likely to occur.^{38,39} The results for the foams made from BLG solutions with 50 mM NdCl₃ also differ strongly from those obtained for foams including

monovalent ions. For both, the reduced G_0 and τ_y , we find very high values, whereas $\gamma_{c,surface}$ is not significantly higher than for the monovalent ions. The reason for the high τ_y and G_0 values is again attributed to aggregation of proteins resulting from their low solubility at this high ionic strength. This is supported by the turbidity of the solutions observed after adding the salt. The mechanism that causes these high values of the rheological parameters is presumably again the formation of a structure across the lamellae. The reduced τ_y values additionally vary with gas volume fraction ϕ . In fact, the ϕ -dependence τ_y for these foams is lower than predicted by Eq. (2). We assume that the network structure is not destroyed as long as $\tau < \tau_y$ as it was the case for the foams investigated in⁷, but additionally contributes to the high yield stress. At lower ϕ and therefore thicker lamellae the protein network spanning the lamellae is expected to have more influence and hence causes high yield stress values leading to the unexpected weak variation of τ_y with ϕ . This phenomenon does not show up in the critical deformation of the foams. Finally, the different effect of divalent Ca^{2+} and trivalent Nd^{3+} on foam rheology clearly demonstrates that the corresponding protein structure and packing is strongly affected by the type and valency of the added ions.

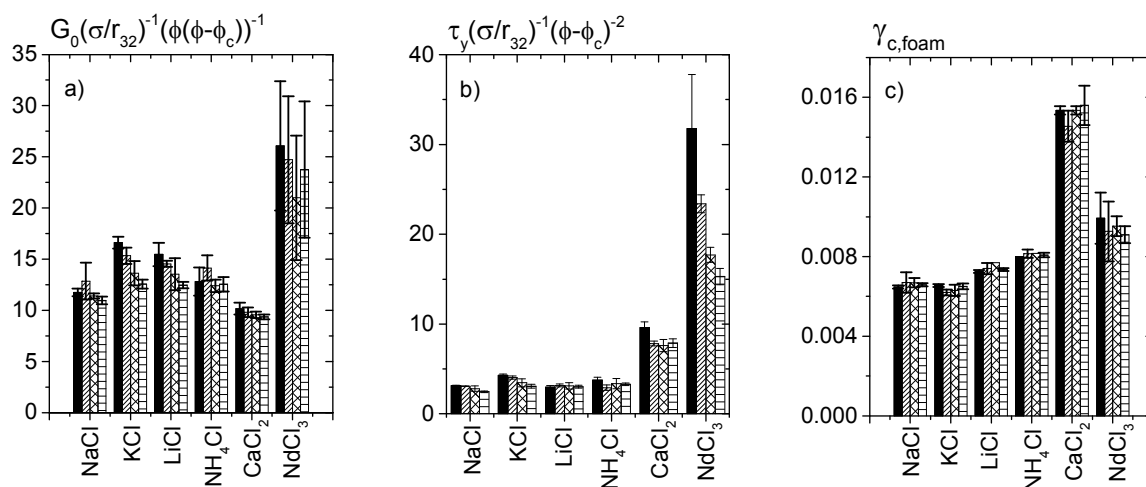


Figure 5: a) reduced storage moduli, b) reduced yield stresses and c) critical deformation for foams made from 1% BLG dissolved in an aqueous 50 mM salt solution measured at different gas volume fractions ϕ (see Tab. 2). For each salt ϕ increases from the left to the right.

3.2.4 Surface Rheology

In Figs. 6a, b and c the surface moduli E' and G'_i , the critical deformation of the surface layer $\gamma_{c,surface}$ and the critical stress of the surface layer $\tau_{c,surface}$ are shown for the protein solutions containing different salts. The results show similarities to those found for the foams (chapter 3.2.3). Monovalent ions affect E' , G'_i , $\gamma_{c,surface}$ and $\tau_{c,surface}$ in a similar way. CaCl_2 increases $\gamma_{c,surface}$ and $\tau_{c,surface}$ but not the surface elastic moduli. The stronger binding of Ca^{2+} , as described in chapter 3.2.3 may also explain why the critical stress and deformation needed to break the protein structure is higher with Ca^{2+} than for other ions. The solutions containing NdCl_3 show highest E' and G'_i values but low $\gamma_{c,surface}$ values similar to the monovalent case and $\tau_{c,surface}$ is in between the values for the monovalent ions and Ca^{2+} . In general, the effect of di- and trivalent ions on interfacial rheology is much less pronounced than on foam rheology. This strongly suggests that foam rheology in these cases is strongly determined by structure formation across the lamellae.

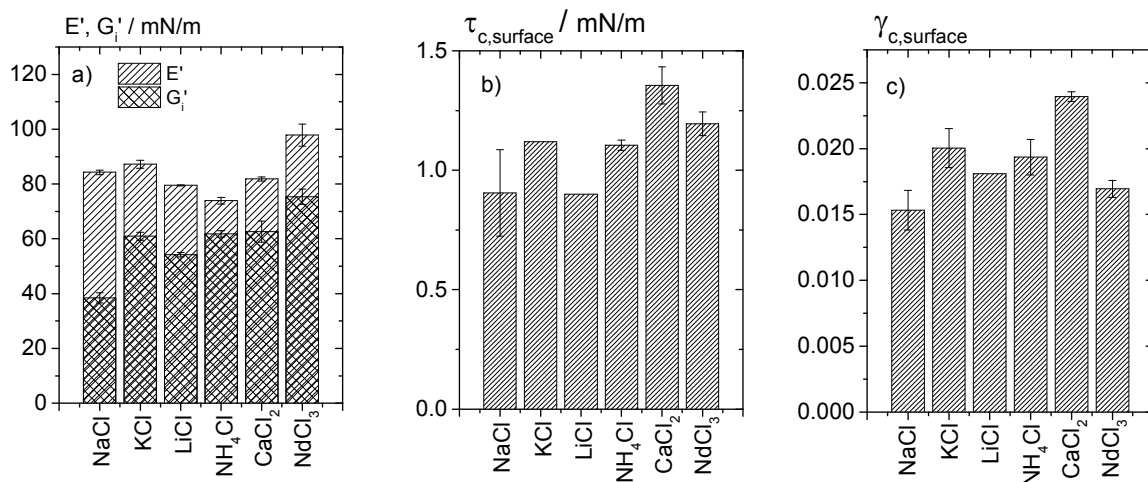


Figure 6: a) surface elastic modulus in dilation (E') and shear (G'_i), b) critical shear stress $\tau_{c,surface}$ and c) critical deformation $\gamma_{c,surface}$ of the surface layer for 1 % BLG solutions containing 50 mM salt of different type and valency.

3.3 Variation of pH

3.3.1 Foam and solution properties

Table 3 shows the characteristic properties of the BLG foams and solutions at different pH. The initial average bubble sizes and bubble size distributions ($\phi_c = 71.5 \pm 1.9$ for all foams) are practically independent of pH. Surface tension varies with a minimum at pH 5 as already found in.^{24,39}

pH	3	4	5	6	6.8	8	9	Max. error / %
$\sigma /$ mN/m	47.6	48.3	45.5	48.9	51.5	52.2	52.0	1
$r_{32} / \mu\text{m}$	104-109	118	93.8-145	102	110-154	103	106-175	7
$\phi / \%$	86-88.	88	84-91	89	87-96	88	87-94	0.4

Table 3: Surface tension of the protein solutions at various pH after 30 minutes surface aging, bubble radii and gas volume fractions in the range of foam ages where the rheological measurements took place. The maximum error is the maximum standard deviation of three measurements at a given pH.

3.3.2 Oscillatory shear stress amplitude sweeps

In Fig. 8 oscillatory shear stress amplitude sweeps for foams at pH values between 3 and 8 are shown. Interestingly, the curves possess different shapes at different pH. At and below the IEP (\approx pH 5) G' and G'' are almost constant before crossing (at pH 3 the foams are very unstable and therefore the moduli slightly decrease). The curves obtained at pH above the IEP can be divided in four regimes. After a short linear viscoelastic regime, both moduli decrease simultaneously, then G'' increases again before the moduli cross over and finally both decrease again. The simultaneous decrease of G' and G'' indicates a gradual structural break down as described in chapter 3.1.2.

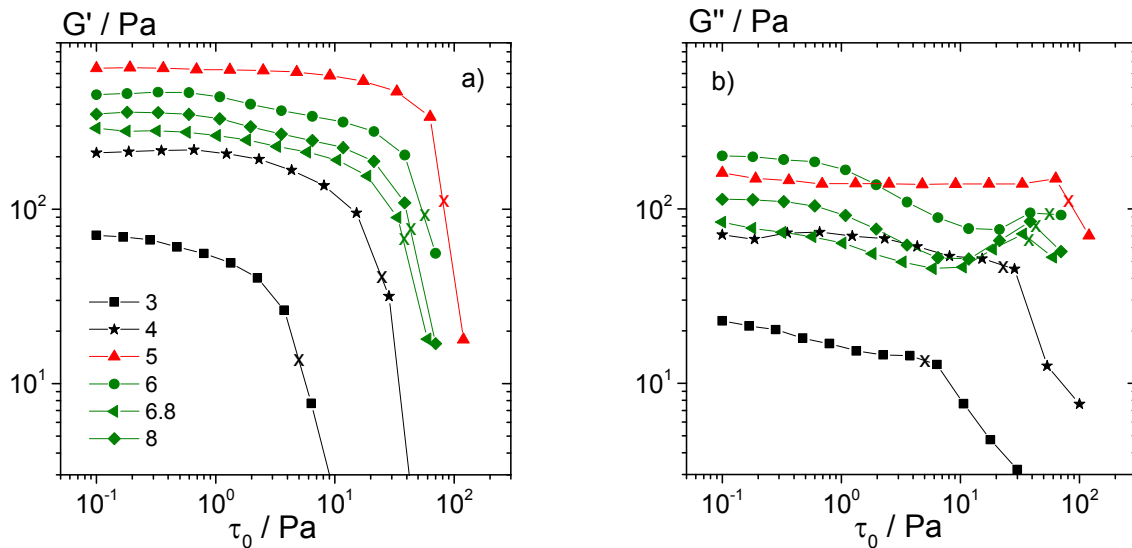


Figure 8: Oscillatory shear measurements with varying stress amplitude of BLG foams at different pH: a) storage modulus G' and b) loss modulus G'' versus the stress amplitude at fixed frequency $f = 1$ Hz. Intersection of G' and G'' marked with crosses.

3.3.3 Yield Stress and storage modulus of the foams

In Fig. 9 the plateau moduli and yield stresses of BLG foams at various gas volume fractions normalized by the Laplace pressure as well as the critical deformation are shown in dependence of the pH. Around the isoelectric point the foams exhibit maximum yield stress, elastic modulus and critical deformation. Low pH, especially pH 3, leads to very unstable foams that possess very low elasticity and yield stress whereas foams at high pH are fairly stable. This behavior has already been reported in³⁹ and was explained by conformational changes of the protein structure at different pH. Also, different electrostatic interactions between the proteins due to the change in their net charge across the IEP occur. At pH 5 the net charge vanishes which was shown to lead to thick disordered protein layers at the surface. The proteins also tend to aggregate at the isoelectric point. Once trapped in a foam lamella these protein clusters presumably support the network formation across two adjacent surfaces and give an additional mechanical strength to the foam structure resulting in such high values for storage modulus and yield stress. In⁷ the proposed network formation in

when whey protein isolate foam lamellae were found to increase G_0 but did not affect the yield stress. From oscillatory amplitude sweeps it could be concluded that the whey protein network is destroyed at $\tau < \tau_y$, as it is here the case here for every $\text{pH} \neq 5$. This suggests the existence of weak, non-uniform networks gradually destroyed as the stress amplitude increases. At $\text{pH} 5$ the destruction of the protein network seems to go along with yielding of the foam indicating a strong uniformly collapsing structure. Above $\text{pH} 6.8$ all three foam rheological parameters do not significantly depend on pH .

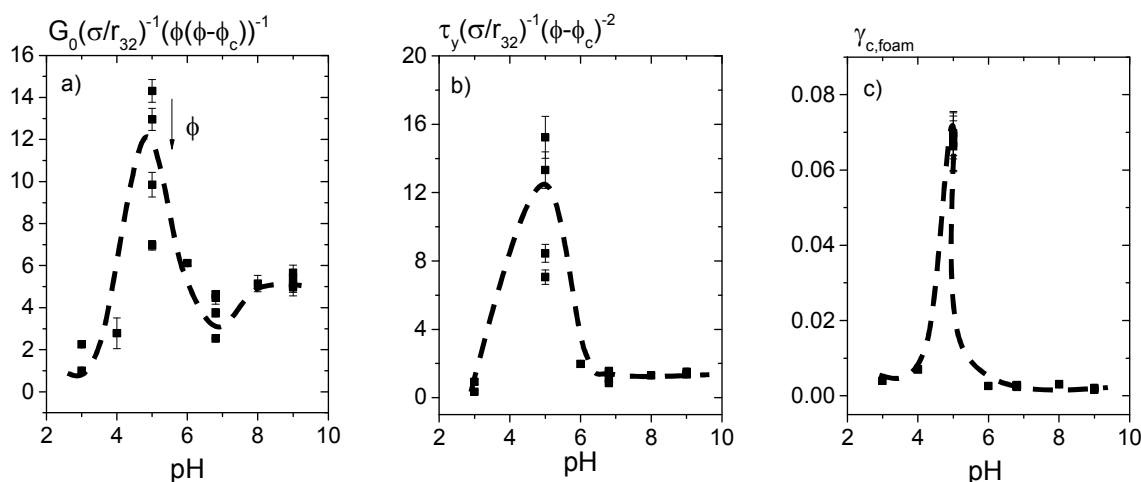


Figure 9: a) Storage moduli normalized by Laplace pressure (σ/r_{32}) and $\phi(\phi-\phi_c)$, b) yield stresses normalized by Laplace pressure and $(\phi-\phi_c)^2$, c) critical deformation of BLG foams. All rheological quantities are measured at various gas volume fractions (see Table 3) and different.

3.3.4 Surface Rheology

Fig. 10a shows the pH dependence of the surface elastic moduli in shear and dilation for the 1% BLG solutions. Both moduli increase up to $\text{pH} 6$ followed by a local minimum around $\text{pH} 7$. The minimum probably arises because this is the natural pH of the solution and no ions are added to adjust the pH . The maximum change in ionic strength due to adjusting pH is approximately 10 mM and according to Fig. 4a this corresponds to a drastic increase in G_i' as

well as E' . Against expectation, the surface moduli do not show a maximum around the IEP as it has been reported for various proteins including BLG in several studies of interfacial shear⁴¹⁻⁴⁴ and dilational properties.^{24,40,45} But note that the protein concentration used in those studies is much lower (at least 5-10 times) than the concentration used here which was chosen that high to meet the conditions used for foam preparation and foam rheology measurement. Burgess et al.³⁵ also worked with high protein concentrations of BSA and HI₉G similar to the concentrations used in this study and measured surface shear elasticities as function of pH. Surprisingly, they found a minimum in G'_i at the IEP and explained this phenomenon by low protein-protein interactions due to a compact shape of the proteins. This explanation is in disagreement with the other studies mentioned above which conclude strong attraction among proteins at the IEP. They attribute this attractive interactions due to close and effective contacts among proteins because of their low net charge.^{24,35} We think the difference in the reported results arises mainly from different protein concentrations. Exceeding a critical protein concentration results in the formation of multilayers at the surface. Wüstneck⁴⁶ measured surface elastic properties of gelatin layers and found the elastic modulus to decrease at a certain concentration that he attributed to the onset of multilayer formation. Also, the formation of protein aggregates, which becomes more significant as the protein concentration increases, can lead to a decrease in surface elasticity as we discussed extensively in a previous study.⁷ The reason for the lower values at pH 3 compared to the values at pH 6.8 despite the same distance to the isoelectric point is differences in protein structure and hydrophobicity as already discussed in^{24,40}.

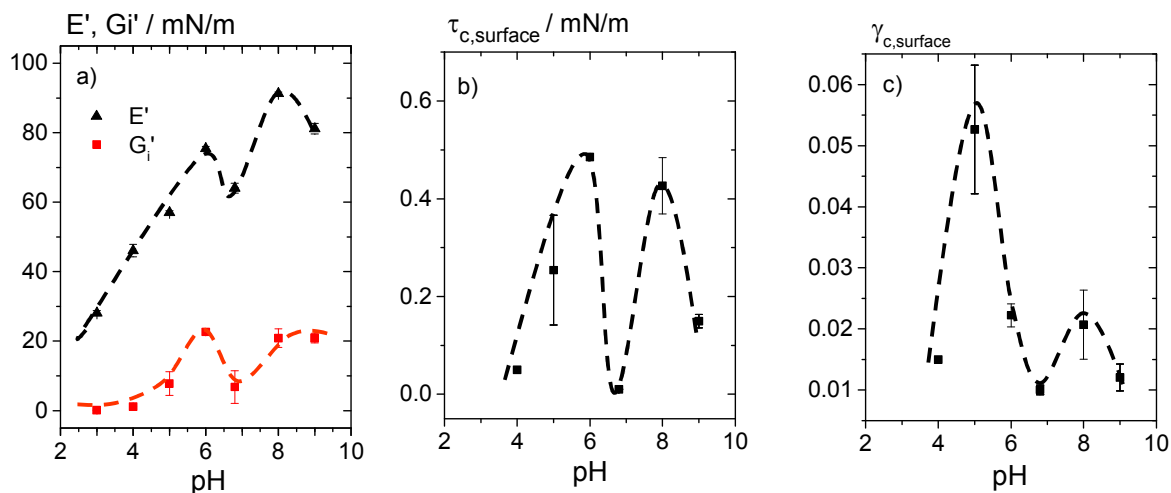


Figure 10: a) Surface elastic modulus in dilation (E') and shear (G_i'), b) critical shear stress $\tau_{c,surface}$ and c) critical deformation $\gamma_{c,surface}$ of the surface layer for 1 % BLG solutions at different pH

3.4 Correlation between interfacial and foam rheology

In Fig. 11 the normalized storage moduli of all foams investigated in this study are plotted versus the surface elastic moduli G_i' and E' . Additionally, data points for whey protein isolate foams (0.1% and 1%) and 3% casein foams (data taken from⁷) are included. A clear correlation is observed between the normalized foam moduli and surface moduli of the corresponding protein solutions except for the 1% BLG solutions at pH 5 and with NdCl_3 as well as the 1% WPI solution. The relationship between G_0 and G_i' is obviously linear whereas our data suggest a stronger quadratic or cubed dependence of G_0 on E' . These findings directly demonstrate that surface elasticity is another important parameter controlling foam elasticity besides the Laplace pressure inside the bubbles, gas volume fraction and bubble size distribution. Accordingly, the pre-factor a in Eq. 1 is solely determined by the surface elastic moduli G_i' or E' . For the three cases where deviations from the simple correlations between foam and surface elasticity are observed protein aggregation and structure or network formation across foam lamellae are supposed to be decisive for foam elasticity as already discussed in detail in sec. 3.2 and 3.3 as well as⁷.

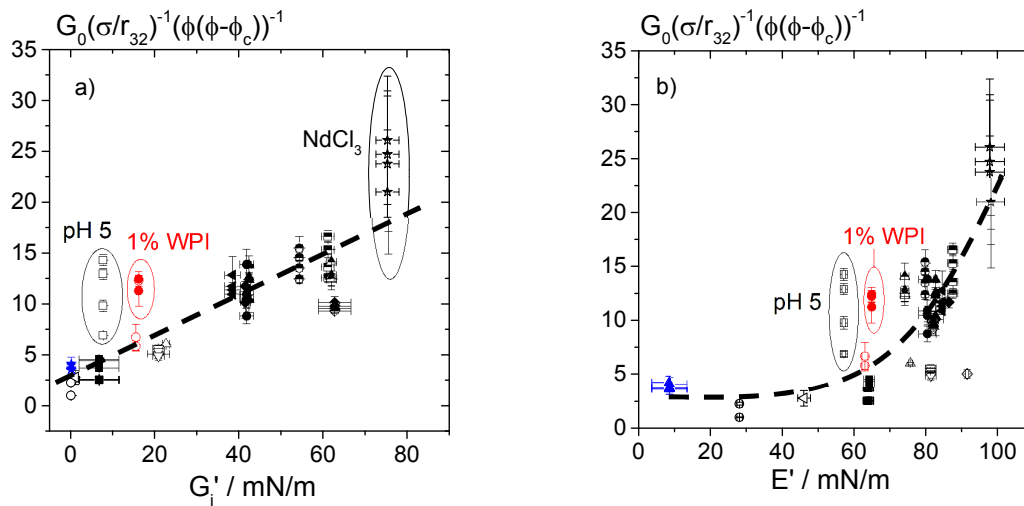


Figure 11: storage moduli normalized by Laplace pressure (σ/r_{32}) and $\phi(\phi-\phi_c)$ versus a) surface shear elastic modulus G'_1 and b) surface dilational elastic modulus E'

○ pH 3, △ pH 4, □ pH 5, △ pH 6, ◇ pH 8, ▽ pH 9,

pH 6.8 and NaCl: ■ 0 mM, ◆ 10 mM, ▲ 50 mM, ● 80 mM, ▲ 100 mM,

50 mM □ KCl, △ NH_4Cl , ● LiCl, ◆ CaCl_2 , ★ NdCl_3

○ 0.1% WPI, ● 1% WPI, ▲ 3% casein

Fig. 12 a and b display the reduced yield stresses of all investigated BLG foams as a function of the critical stress $\tau_{c,\text{surface}}$ or $\gamma_{c,\text{surface}}$ characterizing the onset of non-linear response of the corresponding protein solutions in interfacial shear rheology experiments. The relationship between the normalized foam yield stress and these characteristic surface rheological parameters can be approximated by a linear correlation as the simplest approach. This demonstrates that the parameter k in Eq. (2) is determined by surface rheological features of the corresponding BLG solutions. But again the foams made at pH 5 and those made from the BLG solutions including 50 mM NdCl_3 clearly deviate from this simple correlation and again we conclude that this is due to a structure or network formation across foam lamellae as discussed above which also dominates the yielding of the foam. Finally, Fig. 12c shows the correlation between the critical deformation $\gamma_{c,\text{foam}}$ characterizing the onset of non-linear

response during oscillatory shear of the foams and the critical deformation $\gamma_{c,surface}$ obtained in oscillatory surface shear experiments. Again, a clear correlation between characteristic foam and surface rheological properties is found including all investigated BLG systems except those at pH 5. This once more confirms that foam rheology is tightly related to surface rheological properties of the corresponding protein solutions. Moreover, the deviation of the data for the BLG systems at pH 5 from this correlation and the strong dependence of $\gamma_{c,surface}$ on gas volume fraction further supports the conclusion that in this case foam rheology is dominated by the structure across the foam lamellae instead of the opposing protein surfacelayers alone.

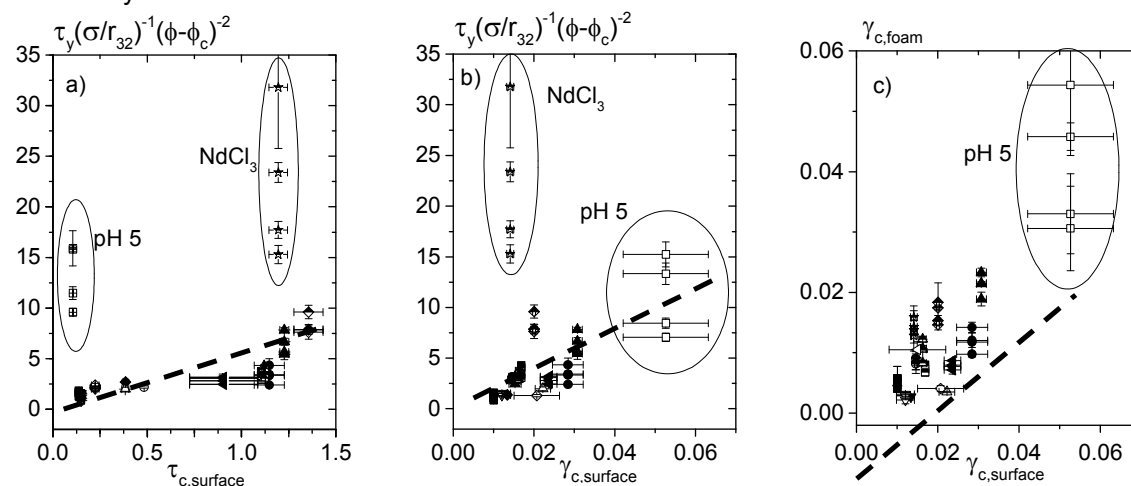


Figure 12: yield stresses normalized by Laplace pressure and $(\phi-\phi_c)^2$ versus a) critical shear deformation of the surface $\tau_{c,surface}$, b) critical shear deformation of the surface $\gamma_{c,surface}$ and c) critical deformation of the foams $\gamma_{c,foam}$ versus critical deformation of the surface $\gamma_{c,surface}$

○ pH 3, △ pH 4, □ pH 5, △ pH 6, ◇ pH 8, ▽ pH 9,

pH 6.8 and NaCl: ■ 0 mM, ◆ 10 mM, ▲ 50 mM, ● 80 mM, ▲ 100 mM,

50 mM □ KCl, ▲ NH_4Cl , ● LiCl, ◆ $CaCl_2$, ☆ $NdCl_3$

3.5 Conclusion

We have investigated the correlation between the rheological behavior of BLG foams and the surface shear and dilational viscoelastic properties of corresponding protein solutions. Foam rheology is characterized here in terms of the frequency independent storage modulus G_0 reflecting the elasticity of the foam “at rest” and the apparent yield stress τ_y determining the onset of flow, i.e. the stress at which bubbles start to slide past each other. Moreover, the transition from linear to non-linear response was characterized using stress amplitude sweep oscillatory shear experiments. From these experiments the critical strain γ_c defining the cessation of linear viscoelastic response was extracted. These foam rheological quantities were determined at gas volume fractions between 82% and 96%. Surface viscoelasticity was characterized in shear and dilation. Corresponding shear G'_i and dilational E' moduli as well as the critical strain γ_c and stress τ_c marking the onset of non-linear response in oscillatory surface shear experiments were determined at a fixed frequency. Solution pH as well as concentration, type and valency of added salt have been varied systematically thus varying foam rheology and surface viscoelasticity in a wide range.

Since protein conformation, solubility and aggregation in the bulk and at the surface may strongly change with protein concentration surface viscoelastic properties were determined at the same protein concentration as used for foam preparation.

Foam as well as interfacial moduli G_0 , G'_i and E' , respectively, strongly increase upon addition of salt to the protein solution but level off at an ionic strength of about 20-30 mM NaCl. The quantities τ_y , $\gamma_{c,foam}$, $\tau_{c,surface}$, $\gamma_{c,surface}$ characterizing the transition from linear to non-linear response increase monotonically with increasing ionic strength. A characteristic change from a gradual decrease of G' with increasing stress amplitude in oscillatory shear experiments to a sharp decrease at a higher critical stress is found when more and more salt is added. This indicates the formation of a stronger and more uniform structure of the foam

and the interfacial protein layers as the attractive interactions among proteins become dominant.

The type and valency of the added salt has little effect on the surface viscoelastic properties of the protein solutions. But foam rheology drastically changes when divalent (Ca^{2+}) or trivalent ions (Nd^{3+}) are added. Adding Nd^{3+} results in a drastic increase in G_0 and τ_y but also in an anomalously weak variation of τ_y with gas volume fraction not captured by Eq. (2). In contrast, addition of Ca^{2+} mainly shows up in a strong increase of $\gamma_{c,\text{foam}}$. These findings indicate the formation of an aggregated protein network structure across foam lamellae, which then determines the foam properties but does not show up in interfacial viscoelasticity. The different effect of Nd^{3+} and Ca^{2+} suggests that different structures are formed within the lamellae.

Variation of pH has little effect on foam rheological parameters G_0 , τ_y and $\gamma_{c,\text{foam}}$ except at pH 5 which is the isoelectric point. At this point all these quantities exhibit distinct maxima and again τ_y and G_0 show an unusually weak dependence on volume fraction not captured by the scaling laws (Eq. (1), (2)) confirmed in various previous studies. This again indicates the formation of a network structure of aggregated protein molecules across the lamellae and this is further supported by the non-monotonic variation of surface viscoelastic parameters not showing similar strong and distinct maxima at pH 5.

Finally, a unique correlation between foam rheological properties and surface viscoelasticity of corresponding BLG solutions could be established using all the collected data mentioned above. The reduced foam storage modulus increases monotonically with G'_i and E' except for the foams made at pH 5 and in the presence of the trivalent salt. Moreover, the correlation between the reduced apparent yield stress and $\tau_{c,\text{surface}}$ or $\gamma_{c,\text{surface}}$ is well approximated by a linear relationship and $\gamma_{c,\text{foam}}$ is proportional to $\gamma_{c,\text{surface}}$ within experimental uncertainty. Once more, the foam rheological parameters obtained at pH 5 and when Nd^{3+} is added are significantly higher than expected from these simple correlations.

In summary, we conclude that the widely accepted physical models predicting foam modulus and yield stress from the Laplace pressure within the gas bubbles and the gas volume fraction do not fully capture the physics of these phenomena. The pre-factors a and k in Eq. (1) and (2) are not just numerical constants on the order of one but are found to vary between $1 < a$ or $k < 30$. A unique correlation between foam rheological properties and surface viscoelastic parameters is found except in cases where attractive interactions among proteins are dominant and are supposed to be strong enough to form a network structure across foam lamellae.

Acknowledgments


The authors would like to thank the group of U. Kulozik (Technische Universität München, Germany) for the supply of high quality β -lactoglobulin and the group of W. Peukert (Universität Erlangen-Nürnberg, Germany) and M. Wilhelm (Karlsruhe Institute of Technology, Germany) for access to measuring equipment.

We acknowledge funding by the DFG-AiF cluster project “Mesoscale modeling of the rheology of foamed food products” Wi 3138/10-1.

References

- 1 T. G. Mason, J. Bibette and D. A. Weitz, *Phys. Rev. Lett.*, 1995, **75**, 2051–2054.
- 2 T. G. Mason, J. Bibette and D. A. Weitz, *Journal of Colloid and Interface Science*, 1996, **179**, 439–448.
- 3 H. M. Princen, *Journal of Colloid and Interface Science*, 1986, **112**, 427–437.
- 4 H. M. Princen and A. D. Kiss, *Journal of Colloid and Interface Science*, 1989, **128**, 176–187.
- 5 S. Marze, A. Saint-Jalmes and D. Langevin, *Colloids and Surfaces A: Physicochemical and Engineering Aspects*, 2005, **263**, 121–128.
- 6 M. Lexis and N. Willenbacher, *Chemie Ingenieur Technik*, 2013, **85**, 1317–1323.
- 7 M. Lexis and N. Willenbacher, *Colloids and Surfaces A: Physicochemical and Engineering Aspects*, 2014, **459**, 177–185.
- 8 N. Willenbacher and M. Lexis in “*Foam Films and Foams: Fundamentals and Application*”, R. Miller and L. Liggieri (Eds.), *Taylor and Francis*, in preparation (2014).
- 9 P. Cicuta and E. M. Terentjev, *Eur. Phys. J. E*, 2005, **16**, 147–158.
- 10 J. Krägel, S. Derkach and R. Miller, *Advances in Colloid and Interface Science*, 2008, **144**, 38–53.
- 11 A. Martin, M. Bos, M. Cohen Stuart and T. van Vliet, *Langmuir*, 2002, **18**, 1238–1243.
- 12 S. Rouimi, C. Schorsch, C. Valentini and S. Vaslin, *Food Hydrocolloids*, 2005, **19**, 467–478.
- 13 M. A. Bos, B. Dunnewind and T. van Vliet, *Colloids and Surfaces B: Biointerfaces*, 2003, **31**, 95–105.
- 14 A. Martin, K. Grolle, M. Bos, M. Stuart and T. van Vliet, *Journal of Colloid and Interface Science*, 2002, **254**, 175–183.
- 15 J. Maldonado-Valderrama, A. Martín-Rodríguez, M. J. Gálvez-Ruiz, R. Miller, D. Langevin and M. A. Cabrerizo-Vílchez, *Colloids and Surfaces A: Physicochemical and Engineering Aspects*, 2008, **323**, 116–122.
- 16 P. Wilde, *Current Opinion in Colloid & Interface Science*, 2000, **5**, 176–181.
- 17 H. M. Princen, *Journal of Colloid and Interface Science*, 1983, **91**.
- 18 S. Besson, G. Debrégeas, S. Cohen-Addad and R. Höhler, *Phys. Rev. Lett.*, 2008, **101**.
- 19 K. Krishan, A. Helal, R. Höhler and S. Cohen-Addad, *Phys. Rev. E*, 2010, **82**.
- 20 S. Costa, R. Höhler and S. Cohen-Addad, *Soft Matter*, 2012, **9**, 1100.
- 21 N. Denkov, S. Tcholakova, K. Golemanov, K. Ananthpadmanabhan and A. Lips, *Phys. Rev. Lett.*, 2008, **100**.
- 22 N. D. Denkov, S. Tcholakova, K. Golemanov, K. P. Ananthpadmanabhan and A. Lips, *Soft Matter*, 2009, **5**, 3389.
- 23 N. D. Denkov, V. Subramanian, D. Gurovich and A. Lips, *Colloids and Surfaces A: Physicochemical and Engineering Aspects*, 2005, **263**, 129–145.
- 24 J. Davis, E. Foegeding and F. Hansen, *Colloids and Surfaces B: Biointerfaces*, 2004, **34**, 13–23.
- 25 T. D. Dimitrova, F. Leal-Calderon, *Advances in Colloid and Interface Science*, 2004, **108-109**, 49-61.
- 26 S. Arditty, V. Schmitt, F. Lequeux, F. Leal-Calderon, *Eur. Phys. J. B*, 2005, **44**, 381-393.
- 27 S. Vandebriel, A. Franck, G. G. Fuller, P. Moldenaers and J. Vermant, *Rheol Acta*, 2010, **49**, 131–144.
- 28 A. Saint-Jalmes, Y. Zhang and D. Langevin, *Eur. Phys. J. E*, 2004, **15**, 53–60.
- 29 M. Durand and D. Langevin, *Eur. Phys. J. E*, 2002, 35–44.
- 30 A. Saint-Jalmes and D. J. Durian, *J. Rheol.*, 1999, **43**, 1411–1422.
- 31 S. Marze, R. M. Guillermic and A. Saint-Jalmes, *Soft Matter*, 2009, **5**, 1937.
- 32 N. Jager-Lézer, J.-F. Tranchant, V. Alard, C. Vu, J.-L. Grossiord and P. C. Tchoreloff, *Rheologica Acta*, 1998, **37**, 129–138.
- 33 B. Rullier, M. A. Axelos, D. Langevin and B. Novales, *Journal of Colloid and Interface Science*, 2009, **336**, 750–755.

- 34 B. Rullier, B. Novales and M. A. Axelos, *Colloids and Surfaces A: Physicochemical and Engineering Aspects*, 2008, **330**, 96–102.
- 35 D. J. Burgess and N. O. Sahin, *Journal of Colloid and Interface Science*, 1997, **189**, 74–92.
- 36 R. A. Curtis, J. M. Prausnitz and H. Blanch, *Biotechnology and Bioengineering*, 1998, **57**, 11–21.
- 37 S. N. Timasheff and T. Arakawa, *Journal of Crystal Growth*, 1988, **90**, 39–46.
- 38 H. Zhu and S. Damodaran, *J. Agric. Food Chem.*, 1994, **42**, 856–862.
- 39 C. A. Zittle, E. S. DellaMonica, R. K. Rudd and J. H. Custer, *J. Am. Chem. Soc.*, 1957, **79**, 4661–4666.
- 40 K. Engelhardt, M. Lexis, G. Gochev, C. Konnerth, R. Miller, N. Willenbacher, W. Peukert and B. Braunschweig, *Langmuir*, 2013, **29**, 11646–11655.
- 41 D. Graham and M. Phillips, *Journal of Colloid and Interface Science*, 1980, **76**, 240–250.
- 42 S. Pezennec, F. Gauthier, Alonso C., F. Graner, T. Croguennec, G. Brulé and A. Renault, *Food Hydrocolloids*, 2000, **14**, 463–472.
- 43 S. H. Kim and J. E. Kinsella, *Journal of Food Science*, 1985, **50**, 1526–1530.
- 44 S. A. Roberts, I. W. Kellaway, K. M. G. Taylor, B. Warburton and K. Peters, *Langmuir*, 2005, **21**, 7342–7348.
- 45 D. Graham and M. Phillips, *Journal of Colloid and Interface Science*, 1980, **76**, 227–239.
- 46 R. Wüstneck, *Colloid Polym Sci*, 1984, **262**, 821–826.

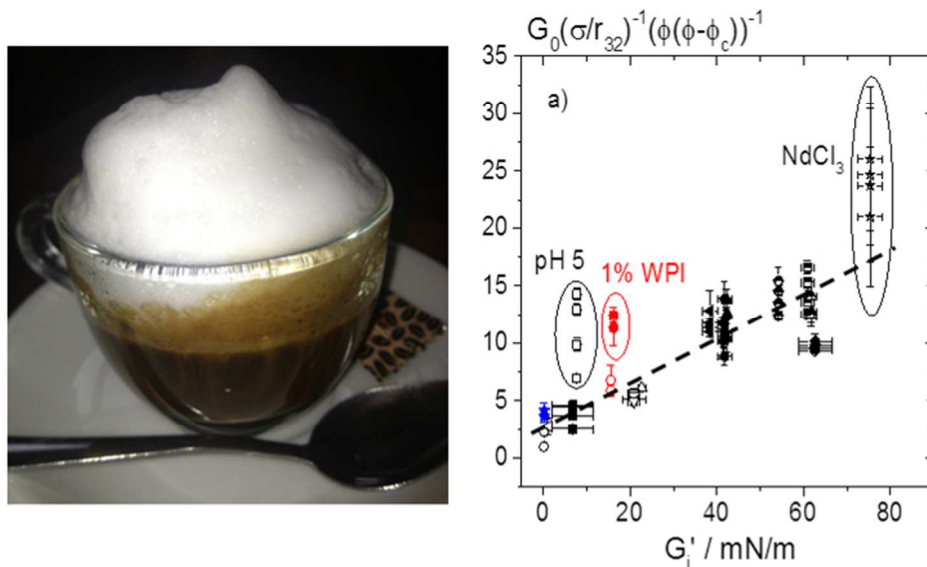

Interfacial elasticity can strongly increase the modulus and yield stress of protein foams by more than an order of magnitude compared to widely accepted model predictions only including contributions from Laplace pressure and gas volume fraction