

# Journal of Materials Chemistry A

Accepted Manuscript



This is an *Accepted Manuscript*, which has been through the Royal Society of Chemistry peer review process and has been accepted for publication.

*Accepted Manuscripts* are published online shortly after acceptance, before technical editing, formatting and proof reading. Using this free service, authors can make their results available to the community, in citable form, before we publish the edited article. We will replace this *Accepted Manuscript* with the edited and formatted *Advance Article* as soon as it is available.

You can find more information about *Accepted Manuscripts* in the [Information for Authors](#).

Please note that technical editing may introduce minor changes to the text and/or graphics, which may alter content. The journal's standard [Terms & Conditions](#) and the [Ethical guidelines](#) still apply. In no event shall the Royal Society of Chemistry be held responsible for any errors or omissions in this *Accepted Manuscript* or any consequences arising from the use of any information it contains.

Cite this: DOI: 10.1039/c0xx00000x

www.rsc.org/xxxxxx

ARTICLE TYPE

## Controllable synthesis of isorecticular pillared-layer MOFs: gas adsorption, iodine sorption and sensing small molecules

Xiao-Li Hu,<sup>a</sup> Fu-Hong Liu,<sup>a</sup> Hai-Ning Wang,<sup>a</sup> Chao Qin,<sup>\*a</sup> Chun-Yi Sun,<sup>a</sup> Zhong-Min Su<sup>\*a</sup> and Fu-Chen Liu<sup>\*b</sup><sup>5</sup> Received (in XXX, XXX) Xth XXXXXXXXX 20XX, Accepted Xth XXXXXXXXX 20XX

DOI: 10.1039/b000000x

Five isostructural pillared-layer MOFs (metal-organic frameworks) have been constructed by selection of layers and size-alterable pillar ligands. These MOFs show similar structures but different interlayer distances, pore volumes and pore surfaces functionalizations depending on the length and function of pillar ligands. **1-5** display a certain degree of framework stabilities, and also exhibit CO<sub>2</sub> uptakes. In addition, **1** can serve as a host for encapsulating I<sub>2</sub> and exhibit an outstanding performance in reversible adsorption of iodine molecules. Furthermore, **1-5** can be used to separate dye molecules based on size-exclusion effect and **3** can be employed as column-chromatographic filler to separate Rhodamine B (RB) and Methylene Blue (MB).

### 15 Introduction

Metal-organic frameworks (MOFs) have attracted tremendous attention in recent years and are being evaluated for diverse potential applications in gas adsorption, catalysis and selective separation.<sup>1-4</sup> These functions mainly depend on the pore characteristics of MOFs, including pore size and shape. Thus, the design and prediction of the MOF structure are critical for the construction of MOFs with desired properties and characteristics.<sup>5</sup> However, the controllable synthesis of MOFs still remains one of the most compelling challenges for chemists. Much effort has been dedicated to achieving MOFs with tunable pore sizes from micropore to mesopore. Employing size-alterable organic linkers to systematically modulate pore size and shape, is one of the most commonly used strategies.<sup>6</sup> As an important branch of MOFs, pillared-layer structures, have proved to be an efficient route to controllably construct frameworks.<sup>7,8</sup> In this way, the structures of a wide variety of MOFs can be predicted and systematically designed. Moreover, chemical functionality of the open frameworks such as hydrophilic/hydrophobic character, hydrogen bonding, and open metal site can be easily controlled via modification of the pillars.<sup>9</sup> Also, flexible pillars can be used for designing and preparing dynamic porous MOFs that can both shrink and expand in response to the presence and absence of guest molecules.<sup>10</sup>

Dyes are widely used in many industries such as paper, textiles, printing, plastics, cosmetics, and pharmaceuticals.<sup>11</sup> The discharge of dyes into water has received a considerable attention because of their overall environmental hazards. Usually, the dyes in water are difficult to degrade because of their poor biodegradability and complex structures.<sup>12</sup> From an environmental point of view, the removal of dyes from effluents before discharge into natural bodies is extremely important. So

far, numerous methods have been developed for the removal of dyes from aqueous environment.<sup>13</sup> The common adsorbents primarily include activated carbons, zeolites, biomass, clays and so on.<sup>12</sup> However, MOFs as potential adsorbents have received less attention.

We firstly employed 1,2,4-triazole and NH<sub>2</sub>bdc (amino-1,4-benzenedicarboxylate) ligands to successfully achieved **2**. To ensure formation of a series of pillared-layer MOFs, **2** was functionalized with organic groups -Br, -C<sub>6</sub>H<sub>5</sub> and its pore size was altered with the molecular struts CH=CH and diphenyl oxide. With progressively longer links fma (fumaric acid), NH<sub>2</sub>bdc to oba (4,4'-oxybis(benzoate)), the interlayer distances of **1**, **2**, **5** incrementally varied from 9.6, 11.7 to 17.1 Å. They show different dye absorption capacities because of different pore volumes resulting from size-alterable ligands.

### Experimental

#### Materials and physical measurements

All chemical materials were purchased from commercial sources and used without further purification. The FT-IR spectra were recorded from KBr pellets in the range 4000–400 cm<sup>-1</sup> on a Mattson Alpha-Centauri spectrometer. XRPD patterns were recorded on a Siemens D5005 diffractometer with Cu Kα (λ = 1.5418 Å) radiation in the range of 3–60° at a rate of 5°/min. The UV-Vis absorption spectra were examined on a Shimadzu UV-2550 spectrophotometer in the wavelength range of 200–800 nm. The C, H, and N elemental analyses were conducted on a Perkin-Elmer 2400CHN elemental analyzer. TG curves were performed on a Perkin-Elmer TG-7 analyzer heated from room temperature to 1000 °C at a ramp rate of 5 °C/min under nitrogen. The photoluminescence spectra were measured on a Perkin-Elmer FLS-920 Edinburgh Fluorescence Spectrometer.

### Preparation of C<sub>13</sub>H<sub>19</sub>N<sub>7</sub>O<sub>6</sub>Zn<sub>2</sub> (1)

A mixture of Zn(NO<sub>3</sub>)<sub>2</sub>·6H<sub>2</sub>O (60 mg, 0.2 mmol), 1, 2, 4-triazole (14 mg, 0.2 mmol), and fma (14 mg, 0.1 mmol) was dissolved in 6 mL of DMA (N,N-Dimethylacetamide)/MeOH (methanol) (1:1, v/v). The final mixture was placed in a Parr Teflon-lined stainless steel vessel (15 mL) under autogenous pressure and heated at 100 °C for 3 days. Colorless crystals were obtained, which were washed with mother liquid, and dried under ambient conditions. Elemental analysis: Anal. Calcd for C<sub>13</sub>H<sub>19</sub>N<sub>7</sub>O<sub>6</sub>Zn<sub>2</sub>: C 31.22; H 3.83; N 19.60. Found: C 31.23; H 3.80; N 19.62. IR (KBr, cm<sup>-1</sup>): 917.27 (w), 2939.87 (w), 805.24 (w), 475.97 (w), 3099.31 (w), 1039.13 (w), 984.09 (w), 590.97 (w), 1216.71 (w), 3446.43 (m), 1007.29 (m), 1169.45 (m), 705.63 (m), 1299.53 (m), 1522.98 (s), 1091.91 (s), 667.63 (s), 1398.55 (s), 1591.53 (s).

### 15 Preparation of C<sub>17</sub>H<sub>22</sub>N<sub>8</sub>O<sub>6</sub>Zn<sub>2</sub> (2)

The synthetic procedure is similar to that of **1** except that fma was replaced by NH<sub>2</sub>bdc. Zn(NO<sub>3</sub>)<sub>2</sub>·6H<sub>2</sub>O (60 mg, 0.2 mmol), 1, 2, 4-triazole (14 mg, 0.2 mmol), and NH<sub>2</sub>bdc (18 mg, 0.1 mmol) was dissolved in 6 mL of DMA/MeOH (1:1, v/v). The final mixture was placed in a Parr Teflon-lined stainless steel vessel (15 mL) under autogenous pressure and heated at 100 °C for 3 days. Colorless crystals were obtained, which were washed with mother liquid, and dried under ambient conditions. Elemental analysis: Anal. Calcd for C<sub>17</sub>H<sub>22</sub>N<sub>8</sub>O<sub>6</sub>Zn<sub>2</sub>: C 36.13; H 3.92; N 19.83. Found: C 36.15; H 3.90; N 19.80. IR (KBr, cm<sup>-1</sup>): 2482.90 (w), 704.90 (w), 3024.38 (w), 2933.65 (w), 922.51 (w), 474.17 (w), 816.50 (w), 891.30 (w), 3349.74 (w), 3468.22 (w), 588.49 (w), 3099.05 (w), 848.18 (w), 770.82 (m), 1214.62 (m), 1457.37 (m), 1307.27 (m), 1263.56 (m), 1389.83 (m), 1007.77 (m), 666.29 (s), 1085.64 (s), 1164.96 (s), 1517.23 (s), 1570.23 (s), 1624.15 (s).

### Preparation of C<sub>17</sub>H<sub>20</sub>N<sub>7</sub>O<sub>6</sub>BrZn<sub>2</sub> (3)

The synthetic procedure is similar to that of **1** except that fma was replaced by Brbdc (bromo-1,4-benzenedicarboxylate). Zn(NO<sub>3</sub>)<sub>2</sub>·6H<sub>2</sub>O (60 mg, 0.2 mmol), 1, 2, 4-triazole (14 mg, 0.2 mmol), and Brbdc (24 mg, 0.1 mmol) was dissolved in 6 mL of DMA/ MeOH (1:1, v/v). The final mixture was placed in a Parr Teflon-lined stainless steel vessel (15 mL) under autogenous pressure and heated at 100 °C for 3 days. Colorless crystals were obtained, which were washed with mother liquid, and dried under ambient conditions. Elemental analysis: Anal. Calcd for C<sub>17</sub>H<sub>20</sub>N<sub>7</sub>O<sub>6</sub>BrZn<sub>2</sub>: C, 32.46; H, 3.20; N, 15.59. Found: C 32.42; H 3.22; N 15.55. IR (KBr, cm<sup>-1</sup>): 3031.67 (w), 2936.11 (w), 475.43 (w), 3612.72 (w), 3443.61 (w), 918.39 (w), 586.53 (w), 1723.68 (w), 3100.03 (w), 770.76 (w), 841.36 (w), 1037.39 (w), 1217.73 (w), 1478.90 (w), 1007.56 (m), 1300.21 (m), 1523.48 (m), 1168.56 (m), 1090.59 (s), 667.24 (s), 1373.71 (s), 1623.82 (s).

### Preparation of C<sub>21</sub>H<sub>23</sub>N<sub>7</sub>O<sub>6</sub>Zn<sub>2</sub> (4)

The synthetic procedure is similar to that of **1** except that fma was replaced by 1,4-ndc (1,4-naphthalenedicarboxylate). Zn(NO<sub>3</sub>)<sub>2</sub>·6H<sub>2</sub>O (60 mg, 0.2 mmol), 1, 2, 4-triazole (14 mg, 0.2 mmol), and 1,4-ndc (21 mg, 0.1 mmol) was dissolved in 6 mL of DMA/ MeOH (1:1, v/v). The final mixture was placed in a Parr Teflon-lined stainless steel vessel (15 mL) under autogenous

pressure and heated at 100 °C for 3 days. Colorless crystals were obtained, which were washed with mother liquid, and dried under ambient conditions. Elemental analysis: Anal. Calcd for C<sub>21</sub>H<sub>23</sub>N<sub>7</sub>O<sub>6</sub>Zn<sub>2</sub>: C, 42.02; H, 3.86; N, 16.33. Found: C, 42.00; H, 3.90; N, 16.32. IR (KBr, cm<sup>-1</sup>): 3028.29 (w), 2933.41 (w), 589.42 (w), 3483.03 (w), 843.05 (w), 1259.74 (w), 1037.31 (w), 1219.44 (w), 3093.49 (w), 1457.92 (m), 1006.07 (m), 1664.19 (m), 794.25 (m), 1169.57 (m), 669.20 (m), 1300.76 (m), 1524.18 (s), 1362.69 (s), 1091.11 (s), 1566.98 (s), 1394.49 (s), 1622.57 (s).

### 65 Preparation of C<sub>26</sub>H<sub>30</sub>N<sub>8</sub>O<sub>7</sub>Zn<sub>2</sub> (5)

A mixture of Zn(NO<sub>3</sub>)<sub>2</sub>·6H<sub>2</sub>O (60 mg, 0.2 mmol), 1, 2, 4-triazole (14 mg, 0.2 mmol), and H<sub>2</sub>oba (25.8 mg, 0.1 mmol) was dissolved in 6 mL of DMA/MeOH/H<sub>2</sub>O (1:1:2, v/v/v). The final mixture was placed in a Parr Teflon-lined stainless steel vessel (15 mL) under autogenous pressure and heated at 100 °C for 3 days. Colorless crystals were obtained, which were washed with mother liquid, and dried under ambient conditions. Elemental analysis: Anal. Calcd for C<sub>26</sub>H<sub>30</sub>N<sub>8</sub>O<sub>7</sub>Zn<sub>2</sub>: C, 44.78; H, 4.34; N, 16.07. Found: C, 44.80; H, 4.32; N, 16.08. IR (KBr, cm<sup>-1</sup>): 474.14 (w), 629.14 (w), 516.54 (w), 698.03 (w), 802.83 (w), 843.49 (w), 590.73 (w), 434.30 (w), 768.13 (w), 2935.18 (m), 3477.63 (m), 1037.05 (m), 880.00 (m), 783.59 (m), 3099.41 (m), 1008.20 (m), 1300.10 (m), 1523.71 (s), 1560.99 (s), 1091.02 (s), 1161.85 (s), 667.56 (s), 1249.45 (s), 1394.78 (s), 1602.08 (s).

### 80 Single crystal X-ray diffraction

Single-crystal X-ray diffraction data for **1-5** were recorded on a Bruker Apex CCD II area-detector diffractometer with graphite-monochromated Mo-K $\alpha$  radiation ( $\lambda = 0.71073 \text{ \AA}$ ) at 296(2) K. Absorption corrections were applied using multi-scan technique. Their structures were solved by the direct method of SHELXS-97 and refined by full-matrix least-square techniques with the SHELXL-97 program.<sup>14</sup> Because guest molecules in the channels of **1-5** were highly disordered and could not be modeled properly, the SQUEEZE routine of PLATON was applied to remove their contributions to the scattering.<sup>15</sup> The reported refinements are of the guest-free structures obtained by the SQUEEZE routine, and the results were attached to the CIF file. The crystal data and structure refinement results of **1-5** are summarized in Table S1.

### 95 Gas sorption experiments

The N<sub>2</sub> and CO<sub>2</sub> sorption measurements were performed on automatic volumetric adsorption equipment (Belsorp mini II). Before gas adsorption measurements, the samples were immersed in CH<sub>2</sub>Cl<sub>2</sub> for 24 h, and the extracts were decanted. Fresh CH<sub>2</sub>Cl<sub>2</sub> was subsequently added, and the crystals were allowed to stay for an additional 24 h to remove the nonvolatile solvates (DMA). After the removal of dichloromethane by decanting, the samples were activated by drying under a dynamic vacuum at room temperature overnight. Before the measurement, the samples were dried again by using the 'outgas' function of the surface area analyzer for 12 h at 90 °C. Meanwhile, the activated samples **1a** were immersed in water, HCl (pH = 2) and NaOH (pH = 12) solutions. After the removal of water by decanting, the samples **1a** were tested N<sub>2</sub> sorption measurements.

### 110 Iodine sorption experiments

The fresh samples of **1** (80 mg) were immersed in a hexane (3 mL) solution of I<sub>2</sub> (0.01 mol L<sup>-1</sup>), to give I<sub>2</sub>@**1**. The photographs were used to determine the adsorption ability. The crystals of I<sub>2</sub>@**1** (10 mg) were soaked in dry ethanol (5 ml), and UV/Vis spectra and photographs were used to determine the desorption ability.

### Dye adsorption and separation

Freshly prepared **1-5** (20mg) were transferred to aqueous solutions (8 mL) of Methylene Blue (MB), Rhodamine B (RB), Methyl Orange (MO) and Congo Red (CR), respectively, in 10 mL sealed glass bottles. Meanwhile, freshly prepared **1, 2, 5** were transferred to aqueous solutions (8 mL) of mixtures of Methylene Blue (MB) and Rhodamine B (RB) in 10 mL sealed glass bottles. UV/Vis spectra and photographs were used to determine the selective adsorption ability of **1, 2, 5** after time intervals.

### Dye release


**1, 2** and **5** loaded with dye molecules were transferred to pure MeOH solution (5 mL) in 10 mL sealed glass bottles. UV/Vis spectra were used to determine the selective release of **1-5** after time intervals.

## Results and discussion

### Synthesis and crystal structure

The molecular structures of **1-5** were determined by X-ray crystallography. The crystallographic parameters of these compounds are given in Table S1. **1-5** are all pillared-layer structures based on the Zn-triazolate layers and dicarboxylate pillars. Two-dimensional layers of {Zn(trz)} form in the *ac* plane, which are connected by pillar ligands for five crystalline products, namely, [Zn<sub>2</sub>(trz)<sub>2</sub>(L)·DMA·MeOH]<sub>n</sub> [L = fma, **1**; NH<sub>2</sub>bdc, **2**; Brbdc, **3**; 1,4-ndc, **4**], [Zn<sub>2</sub>(trz)<sub>2</sub>(oba)·2DMA]<sub>n</sub> (**5**).

Single-crystal structure analysis reveals that **1** crystallizes in the tetragonal system, space group *P4/ncc*. As shown in Fig. 1a, the asymmetric unit of **1** contains one Zn atom, one-half fma ligand and one 1,2,4-triazole ligand. The Zn ion is five coordinated in a distorted trigonal-bipyramidal geometry with three nitrogen atoms from three triazole ligands and two carboxylate oxygen atoms from fma ligand (Zn-N 2.006 Å, Zn-O 1.960 Å). Each triazole ligand binds to three Zn atoms through 1,2,4-position N atoms, and the connection of triazole and Zn ion resulted in a two-dimensional (2D) layer with 4.8<sup>2</sup> topology. The adjacent {Zn(trz)} layers are further connected by the fma pillars to give rise to the overall 3D pillared-layer structure. Interestingly, the network contains channels running along the *a*, *b* and *c* axes. PLATON calculations show that the effective pore volume for **1** is about 52% (2214.4 Å<sup>3</sup>) per unit cell (4261.4 Å<sup>3</sup>), which is occupied by solvent molecules.<sup>16</sup> **5** have the similar pillared-layer structures as **1**, with the replacement of fma ligands by the longer carboxylate ligands oba. And both the entrance of the channels and the interlayer distance are enlarged. For the channels along the *b* axis, the dimensions of channels for **1, 2** and **5** have the sizes ranging from 9.6 Å × 6.5 Å<sup>2</sup>, 11.7 Å × 6.5 Å<sup>2</sup> to 17.1 × 6.5 Å<sup>2</sup> (*a* × *c*) (Fig. S1). Viewed along the *c* axis, **1-5** have the same channel dimension of 6.5 × 6.5 Å<sup>2</sup> (*a* × *b*) because of the same {Zn(trz)} layers. Meanwhile, **3** and **4** have the same structures as **2**, with benzene rings functionalized with the

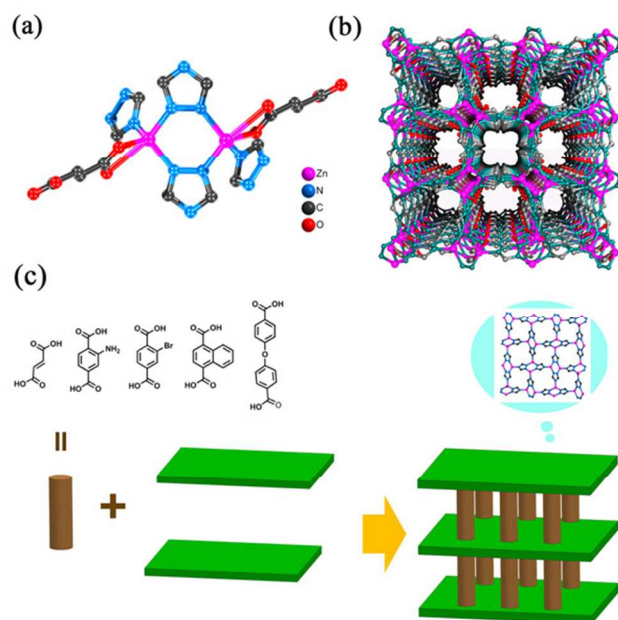


**Fig. 1** (a) The coordination environment of the Zn(II) center in **1**. The hydrogen atoms are omitted for clarity (Zn, pink; N, blue; C, gray; O, red). (b) 3D framework of **1** along the *c* axis. (c) Schematic representations of **1-5** structures and View of the wave-like 2D sheet by trz and Zn ions along the *c* axis.

substituent groups -Br, -C<sub>6</sub>H<sub>5</sub>. Notably, the uncoordinated functional groups of ligands are directed into the rectangular pores. Topologically, regarding {Zn(trz)} unit as a 6-connected node and dicarboxylate as the linker, the 3D structures of **1-5** can be simplified as isostructural **pcu** topologies. The **pcu** topology is a primitive cubic lattice net with Schläfli symbol (4<sup>12</sup>6<sup>3</sup>), such as NaCl and  $\alpha$ -po.<sup>17</sup>

### Thermal and chemical stability

The purities of the as-synthesized **1-5** were confirmed by similarities between simulated and experimental X-ray powder diffraction (XRPD) patterns (Fig. S2). The TG curve of **2** reveals a weight loss of 20.9 % from 50 to 280 °C, in agreement with the weight of DMA and CH<sub>3</sub>OH molecules (calcd 21.0 %). The TG curve indicates that **2** can be thermally stable around 350 °C (Fig. S3). As we know, a good gas storage (or separation) material must be stable toward moisture in practical applications.<sup>18</sup> Thus, we examined their stability to show whether these materials will be useful in practical applications. After soaking **1-5** in water for 24 h at ambient temperature and 100 °C, their XRPD patterns keep the same peak positions although their solid samples became not too transparent (Fig. S4). In addition, their abilities resistance to acid and alkali solution were also investigated. Apart from **4** that become floccule in hydrochloric acid solution, other four MOFs are stable in both hydrochloric acid solution (pH = 2) and sodium hydroxide solution (pH = 12), as confirmed by the XRPD patterns of these samples (Fig. S5). More remarkably, even exposed to air for three months, their XRPD patterns have similar shape and intensity.

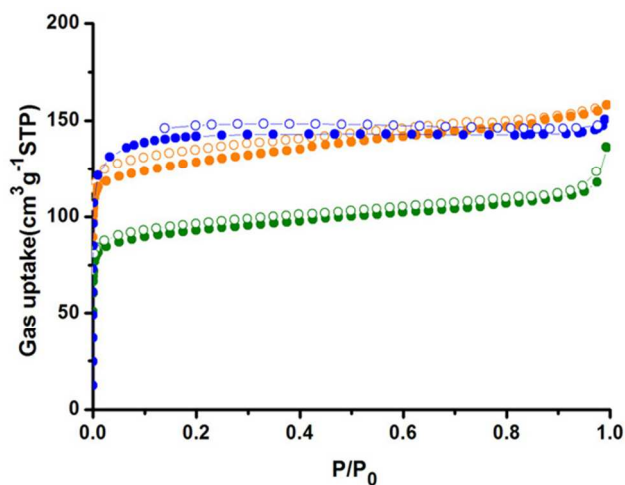

**Fig. 2** The nitrogen sorption isotherms of **1a** (green), **2a** (blue) and **3a** (yellow) at 77 K.

### Gas adsorption properties


To study the porosity of compounds,  $N_2$  and  $CO_2$  adsorption were performed. The activated samples were prepared by exchanging the solvent in the as-synthesized **1-5** with  $CH_2Cl_2$ , followed by evacuation under vacuum. Samples of **1-5** were evacuated under vacuum at room temperature over night to completely remove the solvent  $CH_2Cl_2$  molecules and thus to form guest-free phases **1a-5a**. The XRPD patterns of **1a-5a** show that the broadened peaks keep the positions, indicating the maintenance of the frameworks (Fig. S2).

The architectural stability and permanent porosity of **1a-3a** were confirmed by measuring the  $N_2$  adsorption experiments at 77 K, displaying type I adsorption isotherms characteristic of microporous solids. The nitrogen adsorptions showed good reversibility. The  $N_2$  adsorption amounts of **1a-3a** at 1 bar were about 118.5, 150.3, 158.2  $cm^3 g^{-1}$ , which correspond to 21.2, 30.3, 35.6  $N_2$  per cell (Fig. 2). For **1a-3a**, the apparent BET areas were 363, 453, 506  $m^2 g^{-1}$ , based on the nitrogen adsorption isotherms. The total pore volumes were 0.212, 0.320, 0.245  $cm^3 g^{-1}$ , lower than the theoretical pore volume calculated by PLATON based on the single crystal X-ray diffraction data (Table S2).<sup>19</sup> Corresponding adsorption analyses of **1a-3a** were summarized in Table 1. Meanwhile, **1a** as an example was performed  $N_2$  sorption studies after water, HCl (pH = 2) and NaOH (pH = 12)

**Table 1** Structural information and  $N_2$  adsorption analyses.

	$N_2$ adsorption amount ( $cm^3/g$ )	void (%)	pore volume ( $cm^3 g^{-1}$ )	$S_{BET}$ ( $m^2 g^{-1}$ )
<b>1a</b>	118.5	52.0	0.212	363
<b>2a</b>	150.3	45.6	0.320	453
<b>3a</b>	158.2	46.6	0.245	506

treatment, in order to further testify the stability of MOFs. The  $N_2$  adsorptions showed adsorption amount and surface area have a decrease (Fig. S6 and Table S3). It can be explained that water

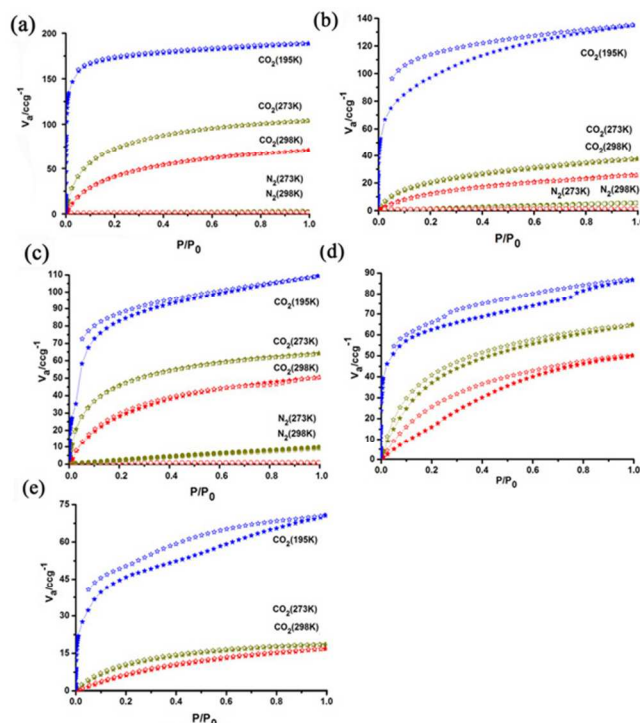

**Fig. 3**  $CO_2$  and  $N_2$  sorption isotherms for (a) **1a**, (b) **2a**, (c) **3a**, (d) **4a** and (e) **5a** at 195, 273 and 298 K.

and acid/alkaline solutions destroyed the framework in a certain degree, although XRPD patterns keep the same. Subsequently we carried out  $CO_2$  adsorption experiments on **1a-5a**. As shown in Fig. 3, the  $CO_2$  sorption isotherms for **1a-5a** were measured at 195, 273 and 298 K, respectively. **1a-5a** have  $CO_2$  uptakes at 1 bar with saturation of 188.5  $cm^3/g$ , 136.3  $cm^3/g$ , 108.9  $cm^3/g$ , 86.88  $cm^3/g$ , 70.68  $cm^3/g$  at 195K, 103.7  $cm^3/g$ , 37.7  $cm^3/g$ , 63.9  $cm^3/g$ , 64.3  $cm^3/g$ , 18.6  $cm^3/g$  at 273 K, and 70.2  $cm^3/g$ , 25.7  $cm^3/g$ , 50.5  $cm^3/g$ , 50.1  $cm^3/g$ , 17.2  $cm^3/g$  at 298 K (Fig. 3 and Table 2). For **1-5**, the isosteric heats of adsorption ( $Q_{st}$ ) of  $CO_2$  were calculated by using the Clausius–Clapeyron equation to quantitatively evaluate the binding strengths (Fig. S8-S12).<sup>20</sup> The  $Q_{st}$  at zero coverage of  $CO_2$  of **1** was about 33  $KJ mol^{-1}$ , thus indicating strong interactions between  $CO_2$  and the framework. The  $CO_2$ -uptakes and enthalpy of adsorption for selected MOFs and **1** are listed in the Table S4. Unexpectedly, the  $CO_2$  uptakes for **1a-3a** are quite high while  $N_2$  sorption was hardly adsorbed at 273 and 298 K (Fig. 3).

### Iodine sorption

The permanent porosity of **1-5** demonstrated by  $N_2$  sorption studies prompted us to search for absorbing some molecules.<sup>21</sup> Among the five isostructural compounds, we selected **1** as an example. When the fresh samples of **1** (80 mg) were immersed in a hexane (3 mL) solution of  $I_2$  (0.01  $mol L^{-1}$ ), we observed that the color of the crystals intensified from light yellow to darker brown, while the dark brown solution of  $I_2$  faded gradually to pale red in hours. The entry of  $I_2$  into the **1** host framework results in a distinct decrease of the fluorescence emission intensity ( $\lambda_{ex} = 311$  nm and  $\lambda_{em} = 405$  nm), which may attribute to

Cite this: DOI: 10.1039/c0xx00000x

www.rsc.org/xxxxxx

## ARTICLE TYPE


**Table 2** CO<sub>2</sub> adsorption analyses for **1a-5a**.

	195K		273K		298K	
	cm <sup>3</sup> /g	mmol g <sup>-1</sup>	cm <sup>3</sup> /g	mmol g <sup>-1</sup>	cm <sup>3</sup> /g	mmol g <sup>-1</sup>
<b>1a</b>	188.5	8.42	103.7	4.63	70.2	3.13
<b>2a</b>	136.3	6.08	37.7	1.68	25.7	1.15
<b>3a</b>	108.9	4.86	63.9	2.85	50.5	2.25
<b>4a</b>	86.88	3.88	64.3	2.87	50.1	2.24
<b>5a</b>	70.68	3.16	18.6	0.83	17.2	0.77

<sup>a</sup> Footnote text.

the host-guest photoinduced electron transfer effect (Fig. S13).<sup>22</sup> The decline of the fluorescence intensity also indicates that **1** can quickly adsorb iodine. When the crystals of I<sub>2</sub>@**1** were soaked in dry ethanol, the color of the crystals changed gradually from dark brown to light yellow and the color of the ethanol solution deepened gradually from colorless to darker yellow, as represented in Fig. 4. To further investigate the kinetics of I<sub>2</sub> delivery of **1** in crystal transformation, UV/vis spectrum was recorded at room temperature. The absorbance of I<sub>2</sub> in ethanol increases linearly with time. The releasing rate becomes slower later because the concentration of I<sub>2</sub> in ethanol increases with time. To verify the repeatability, the reversible I<sub>2</sub> sorption process was tested for two cycles. The photographs, UV and luminescent spectrum for **1** releasing I<sub>2</sub> demonstrate that the I<sub>2</sub> sorption process is reversible and repeatable (Fig. 4 and Fig. S14).

The integrity of the framework is confirmed by the XRPD data (Fig. S15). It was worthy to say that when the crystals were soaked in the solution of I<sub>2</sub> for about 60 minutes, some peaks of XRPD patterns become weak. While, the peaks appeared again when the I<sub>2</sub> was removed from the framework upon immersing of the crystals in ethanol. This phenomenon can be well explained that the high amount of iodine in **1** has a significant impact on the sensitivity of X-ray.

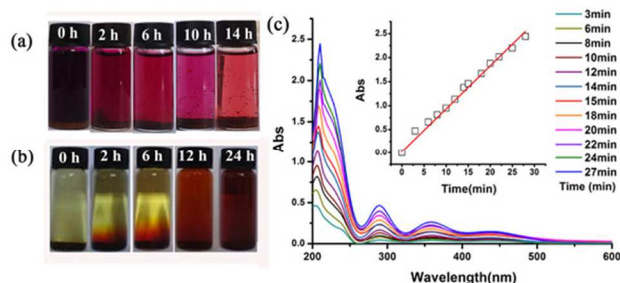

**Fig. 4** (a) Photographs showing the color change when **1** (80 mg) was soaked in hexane solution of I<sub>2</sub> (3 mL, 0.01 mol/L). (b) The I<sub>2</sub> release process when I<sub>2</sub>@**1** (50 mg) was immersed in EtOH (3 mL). (c) The UV/vis spectra of I<sub>2</sub>@**1** for the releasing process of iodine.

### Dye sorption from aqueous solution

To investigate the abilities of **1-5** to separate dye molecules, we


used them to capture dyes in water. Two types of dyes with different charges: positively charged Methylene Blue (MB) and Rhodamine B (RB), and negatively charged Methyl Orange (MO) and Congo Red (CR) were chosen as models of pollutants. Typically, when 30 mg of **1-5** were soaked in 3 mL of dye-contaminated water ( $2 \times 10^{-5}$  mol L<sup>-1</sup>), respectively, some dye molecules could be efficiently adsorbed over a period of time and the colorless crystals gradually became colored, while some dye molecules could not be incorporated (Fig. S16). As depicted in Table 3, corresponding adsorption analyses of **1-5** were summarized.

**Table 3** The list of dye adsorption analyses of **1-5**.

Adsorbate /Samples	MB	MO	RB	CR
<b>1</b>	×	×	×	×
<b>2</b>	√	√	×	×
<b>3</b>	√	√	×	×
<b>4</b>	√	√	×	×
<b>5</b>	√	√	√	√

√ = absorbed; × = excluded  
MB = Methylene Blue; MO = Methyl Orange; RB = Rhodamine B; CR = Congo Red.

**1**, **2** and **5** were designed with tunable channels by using size-alterable organic linkers, while **3** and **4** have the similar interlayer distances to **2** despite of different functional groups. Considering the above cases, we chose **1**, **2** and **5** for dye molecules inclusion study. RB and MB with different sizes were selected for these experiments. When refreshed **1**, **2** and **5** were soaked in water of mixture of two kinds of dyes, different phenomena were observed. Because that the pore size of **1** is smaller than that of RB and MB, scarcely any amount of adsorbed dyes were detected (Fig. 5a). As shown in Fig. 5b, the continuing decrease of characteristic absorbance for MB reveals its successful incorporation whereas unchanged peak of RB suggests its exclusion by the channels of **2**. This phenomenon can be ascribed to that the pore size of **2** is bigger than that of MB but smaller than that of RB. While the

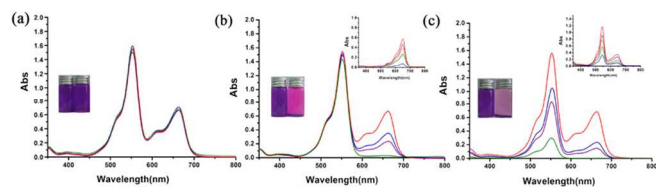


**Fig. 5** Photographs and UV/Vis spectra of aqueous solutions of mixture of RB and MB dyes with (a) **1**, (b) **2** and (c) **5** (UV/Vis spectra of dye releasing in MeOH are showed at the top).

continuing decreases of characteristic absorbance for MB and RB reveal that **5** has the ability to incorporate these two dye molecules (Fig. 5c). The differences in adsorptions may be caused by size factors, since the channel windows in the order of  $5 > 2 > 1$ . The capabilities of **1**, **2** and **5** to adsorb dyes from water were evaluated through UV/Vis spectroscopy and confirmed in Fig. 5. To confirm that selective absorptions are repeatable, dye releasing experiments were performed in MeOH measured by UV/Vis spectroscopy. This showed that, the dye molecules can be gradually released because dye molecules are more easily dissolved in MeOH. The results indicate that **1-5** show excellent adsorption properties and repeatabilities.

Considering the above results in mind, **2-4** all have the abilities to separate large dye molecules based on the size-exclusion effect (Table 3).<sup>23</sup> **3** was employed as column-chromatographic filler for separation of RB and MB based on the size-exclusion effect. As displayed in Fig. 6, the larger and unincorporated RB was transported through the column along with the water stream while the incorporated MB was retained inside the MOF channels for longer time, thus resulting in the separation, which was not only observable by the naked eye but was also confirmed by UV-vis spectra of the effluent.

## Conclusion

In summary, we utilized an already established and powerful approach for the targeted manipulation of an important family of pillared-layer MOFs. The resulted MOFs show similar structures but different interlayer distances, pore volumes and pore surfaces functionalizations depending on the length and function of pillar linkers. **1-5** display a certain amount of CO<sub>2</sub> uptakes, since CO<sub>2</sub> uptakes of **2** and **5** can definitely not considered to be high. With the merit of microporous, **1** was selected as an example to carry out I<sub>2</sub> adsorption experiment which exhibited a rapidly reversible process. Interestingly, **1-5** were investigated for capturing dyes in water. They show different dye absorption capacities because of different pore volumes resulting from size-alterable ligands, and repeatabilities. Meanwhile, **3** has been demonstrated to be a column-chromatographic filler for the separation of bulk dye molecules. The synthetic strategy presents a progressive evolution for the construction of pillared-layer frameworks and the MOFs materials for functional applications are currently underway.

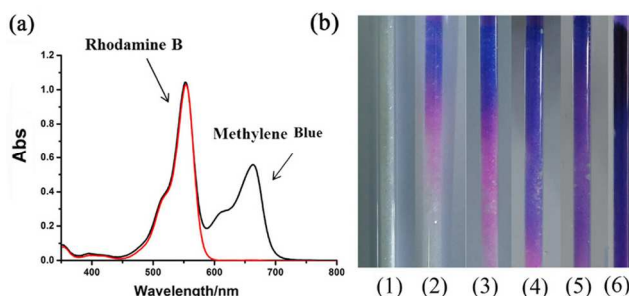

**Fig. 6** (a) UV-vis spectra of the original effluent (black) and effluent passing through the MOF chromatographic column (red) of the dye mixture of RB and MB. (b) Photograph records for **3**-filled column-chromatographic separation process for RB and MB dyes, in which (1) **3**-filled column, (2-5) separation process with gradually changed color, and (6) complete separation with only MB retained.

## Acknowledgements

This work was financially supported by the NSFC of China (No. 21001022, 21171033, 21131001, 21222105, 20801041), PhD Station Foundation of Ministry of Education (20100043110003), The Foundation for Author of National Excellent Doctoral Dissertation of P.R.China (FANEDD) (No. 201022), The Science and Technology Development Planning of Jilin Province (20111803).

## Notes and references

- <sup>a</sup> Institute of Functional Material Chemistry, Key Laboratory of Polyoxometalate Science of Ministry of Education, Northeast Normal University, Changchun, 130024 Jilin, People's Republic of China. E-mail: [qinc703@nenu.edu.cn](mailto:qinc703@nenu.edu.cn); [zmsu@nenu.edu.cn](mailto:zmsu@nenu.edu.cn) Fax: +86 431-85684009; Tel: +86 431-85099108.
- <sup>b</sup> School of Chemistry and Chemical Engineering, Tianjin University of Technology, Tianjin, 300384, P. R. China. E-mail: [fuchenliutj@yahoo.com](mailto:fuchenliutj@yahoo.com)
- † Electronic Supplementary Information (ESI) available: XRPD, TG, Isothermic heats spectra, UV-vis spectra, photoluminescence spectra and additional figures. CCDC-945490 (**1**), CCDC-945492 (**2**), CCDC-945493 (**3**), CCDC-945494 (**4**), CCDC-945495 (**5**). For ESI and crystallographic data in CIF or other electronic format see DOI: 10.1039/b000000x/
- 1 (a) O. M. Yaghi, M. O'Keeffe, N. W. Ockwig, H. K. Chae, M. Eddaoudi and J. Kim, *Nature*, 2003, **423**, 705; (b) G. Férey, *Chem. Soc. Rev.*, 2008, **37**, 191; (c) M. J. Zaworotko, *Nature*, 2008, **451**, 410; (d) C. Volkringer, D. Popov, T. Loiseau, N. Guillou, G. Férey, M. Haouas, F. Taulelle, C. Mellot-Draznieks, M. Burghammer and C. Riekel, *Nat. Mater.*, 2007, **6**, 760; (e) S. J. Dalgarno, N. P. Power and J. L. Atwood, *Coord. Chem. Rev.*, 2008, **252**, 825; (f) M. P. Suh, Y. E. Cheon and E. Y. Lee, *Coord. Chem. Rev.*, 2008, **252**, 1007; (g) S. Kitagawa and R. Matsuda, *Coord. Chem. Rev.*, 2007, **251**, 2490; (h) X. L. Wang, C. Qin, S. X. Wu, K. Z. Shao, Y. Q. Lan, S. Wang, D. X. Zhu, Z. M. Su and E. B. Wang, *Angew. Chem.*, 2009, **121**, 5395; *Angew. Chem., Int. Ed.*, 2009, **48**, 5291.
- 2 (a) H. K. Chae, D. Y. Siberio-Perez, J. Kim, Y. B. Go, M. Eddaoudi, A. J. Matzger, M. O'Keeffe and O. M. Yaghi, *Nature*, 2004, **427**, 523; (b) X. Zhao, B. Xiao, A. J. Fletcher, K. M. Thomas, D. Bradshaw and M. J. Rosseinsky, *Science*, 2004, **306**, 1012; (c) J. A. R. Navarro, E. Barea, A. Rodriguez-Dieguez, J. M. Salas, C. O. Ania, J. B. Parra, N. Masciocchi, S. Galli and A. Sironi, *J. Am. Chem. Soc.*, 2008, **130**, 3978; (d) C. D. Wood, B. Tan, A. Trewin, F. Su, M. J. Rosseinsky, D. Bradshaw, Y. Sun, L. Zhou and A. I. Cooper, *Adv. Mater.*, 2008,

- 20, 1916; (e) F. Nouar, J. F. Eubank, T. Bousquet, L. Wojtas, M. J. Zaworotko and M. Eddaoudi, *J. Am. Chem. Soc.*, 2008, **130**, 1833.
- 3 (a) S. Horike, M. Dincă, K. Tamaki and J. R. Long, *J. Am. Chem. Soc.*, 2008, **130**, 5854; (b) M. Fujita, J. Y. Kwon, S. Washizu and K. Ogura, *J. Am. Chem. Soc.*, 1994, **116**, 1151; (c) J. S. Seo, D. Whang, H. Lee, S. I. Jun, J. Oh, Y. J. Jeon and K. Kim, *Nature*, 2000, **404**, 982; (d) C. D. Wu and W. Lin, *Angew. Chem., Int. Ed.*, 2007, **46**, 1075; (e) T. M. McDonald, W. R. Lee, J. A. Mason, B. M. Wiers, C. S. Hong and J. R. Long, *J. Am. Chem. Soc.*, 2012, **134**, 7056; (f) P. Horcajada, R. Gref, T. Baati, P. K. Allan, G. Maurin, P. Couvreur, G. Férey, R. E. Morris and C. Serre, *Chem. Rev.*, 2012, **112**, 1232.
- 4 (a) X. L. Hu, C. Y. Sun, C. Qin, X. L. Wang, H. N. Wang, E. L. Zhou, W. E. Li and Z. M. Su, *Chem Commun.*, 2013, **49**, 3564; (b) R. Matsuda, R. Kitaura, S. Kitagawa, Y. Kubota, R. V. Belosludov, T. C. Kobayashi, H. Sakamoto, T. Chiba, M. Takata, Y. Kawazoe and Y. Mita, *Nature*, 2005, **436**, 238; (c) S. Ma, X. S. Wang, D. Yuan and H. C. Zhou, *Angew. Chem., Int. Ed.*, 2008, **47**, 4130; (d) L. Pan, D. H. Olson, L. R. Ciemmolonski, R. Heddy and J. Li, *Angew. Chem., Int. Ed.*, 2006, **45**, 616; (e) T. K. Maji, R. Matsuda and S. Kitagawa, *Nat. Mater.*, 2007, **6**, 142; (f) B. L. Chen, Y. Yang, F. Zapata, G. N. Lin, G. D. Qian and E. B. Lobkovsky, *Adv. Mater.*, 2007, **19**, 1693.
- 5 (a) S. G. Férey, C. Mellot-Draznieks, F. Millange, S. Surblé, J. Dutour and I. Margiolaki, *Angew. Chem., Int. Ed.*, 2004, **43**, 6296; (b) C. Mellot-Draznieks, J. Dutour and G. Férey, *Angew. Chem., Int. Ed.*, 2004, **43**, 6290; (c) H. L. Jiang, Y. Tatsu, Z. H. Lu and Q. Xu, *J. Am. Chem. Soc.*, 2010, **132**, 5586; (d) G. S. Yang, M. N. Li, S. L. Li, Y. Q. Lan, W. W. He, X. L. Wang, J. S. Qin and Z. M. Su, *J. Mater. Chem.*, 2012, **22**, 17947.
- 6 (a) A. Schoedel, W. Boyette, L. Wojtas, M. Eddaoudi and M. J. Zaworotko, *J. Am. Chem. Soc.*, 2013, **135**, 14016; (b) M. Eddaoudi, J. Kim, N. Rosi, D. Vodak, J. Wachter, M. O'Keeffe and O. M. Yaghi, *Science*, 2002, **295**, 469; (c) D. Denysenko, M. Grzywa, M. Tonigold, B. Stoppel, I. Krkljus, M. Hirscher, E. Mugnaioli, U. Kolb, J. Hanss and D. Volkmer, *Chem. Eur. J.*, 2011, **17**, 1837; (d) D. Yuan, D. Zhao and H. C. Zhou, *Inorg. Chem.*, 2011, **50**, 10528; (e) H. Furukawa, Y. B. Go, N. Ko, Y. K. Park, F. J. Uribe-Romo, J. Kim, M. O'Keeffe and O. M. Yaghi, *Inorg. Chem.*, 2011, **50**, 9147; (f) X. Lin, I. Tepele, A. I. Blake, A. Dailly, C. M. Brown, J. M. Simmons, M. Zoppi, G. S. Walker, K. M. Thomas, T. J. Mays, P. Hubberstey, N. R. Champness and M. Schröder, *J. Am. Chem. Soc.*, 2009, **131**, 2159.
- 7 (a) T. J. Prior, D. Bradshaw, S. J. Teat and M. J. Rosseinsky, *Chem. Commun.*, 2003, 500; (b) J. L. Song, H. H. Zhao, J. G. Mao and K. R. Dunbar, *Chem. Mater.*, 2004, **16**, 1884; (c) Z. J. Zhang, J. C. Liu, Z. Li and J. Li, *Dalton Trans.*, 2012, **41**, 4232; (d) Z. Chang, D. S. Zhang, Q. Chen, R. F. Li, T. L. Hu and X. H. Bu, *Inorg. Chem.*, 2011, **50**, 7555; (e) I. H. Park, K. Kim, S. S. Lee and J. J. Vittal, *Cryst. Growth Des.*, 2012, **12**, 3397.
- 8 (a) H. N. Wang, X. Meng, C. Qin, X. L. Wang, G. S. Yang and Z. M. Su, *Dalton Trans.*, 2012, **41**, 1047; (b) D. R. Xiao, E. B. Wang, H. Y. An, Y. G. Li, Z. M. Su and C. Y. Sun, *Chem. Eur. J.*, 2006, **12**, 6528; (c) M. J. Zaworotko, *Chem. Commun.*, 2001, **40**, 2111; (d) H. L. Ngo and W. Lin, *J. Am. Chem. Soc.*, 2002, **124**, 14298; (e) R. Kitaura, K. Fujimoto, S. i. Noro, M. Kondo and S. Kitagawa, *Angew. Chem., Int. Ed.*, 2002, **114**, 141; (f) Y. Diskin-Posner, S. Dahal and I. Goldberg, *Angew. Chem., Int. Ed.*, 2000, **112**, 1344.
- 9 (a) C. Zhang, Y. Cao, J. Zhang, S. Meng, T. Matsumoto, Y. Song, J. Ma, Z. Chen, K. Tatsumi and M. G. Humphrey, *Adv. Mater.*, 2008, **20**, 1870; (b) S. Horike, S. Bureekaew and S. Kitagawa, *Chem. Commun.*, 2008, 471; (c) T. Shiga, H. Okawa, S. Kitagawa and M. Ohba, *J. Am. Chem. Soc.*, 2006, **128**, 16426; (d) B. Liu, M. Ma, D. Zacher, A. Bétard, K. Yusenko, N. Metzler-Nolte, C. Wöll and R. A. Fischer, *J. Am. Chem. Soc.*, 2011, **133**, 1734.
- 10 (a) R. Matsuda, R. Kitaura, S. Kitagawa, Y. Kubota, T. C. Kobayashi, S. Horike and M. Takata, *J. Am. Chem. Soc.*, 2004, **126**, 14063; (b) T. K. Maji, K. Uemura, H. C. Chang, R. Matsuda and S. Kitagawa, *Angew. Chem., Int. Ed.*, 2004, **116**, 3331; (c) S. Henke, A. Schneemann, A. Wütscher and R. A. Fischer, *J. Am. Chem. Soc.*, 2012, **134**, 9464.
- 11 B. Adhikari, G. Palui, A. Banerjee, *Soft Matter*, 2009, **5**, 3452.
- 12 (a) C. Y. Sun, X. L. Wang, C. Qin, J. L. Jin, Z. M. Su, P. Huang and K. Z. Shao, *Chem. Eur. J.*, 2013, **19**, 3639; (b) C. Zou, Z. J. Zhang, X. Xu, Q. H. Gong, J. Li and C. D. Wu, *J. Am. Chem. Soc.*, 2012, **134**, 87; (c) M. A. Al-Ghouthi, M. Khraisheh, S. J. Allen and M. N. Ahmad, *J. Environ. Manage.*, 2003, **69**, 229; (d) L. Zhou, C. Gao and W. Xu, *ACS Appl. Mater. Interfaces.*, 2010, **2**, 1483.
- 13 (a) W. X. Chen, W. Y. Lu, Y. Y. Yao and M. H. Xu, *Environ. Sci. Technol.*, 2007, **41**, 6240; (b) D. Mahanta, G. Madras, S. Radhakrishnan and S. Patil, *J. Phys. Chem. B*, 2008, **112**, 10153; (c) Y. C. He, J. Yang, W. Q. Kan and J. F. Ma, *CrystEngComm*, 2013, **15**, 848.
- 14 G. M. Sheldrick, SHELXS 97, *Program for Crystal Structure Analysis*, University of Göttingen, Germany, 1997.
- 15 (a) G. M. Sheldrick, SHELXS 97, *Program for Crystal Structure Refinement*, University of Göttingen, Germany, 1997; (b) P. van der Sluis and A. L. Spek, *Acta Crystallogr. Sect. A* 1990, **46**, 194; (c) A. L. Spek, *J. Appl. Crystallogr.* 2003, **36**, 7.
- 16 A. L. Spek, PLATON, *A multipurpose crystallographic tool* Utrecht University, The Netherlands, 2003.
- 17 (a) M. O'Keeffe and B. G. Hyde, *Crystal Structures I: Patterns and Symmetry*, Mineralogical Society of America, Washington, DC, 1996; (b) F. X. Sun, G. S. Zhu, Q. R. Fang and S. L. Qiu, *Inorg. Chem. Commun.*, 2007, **10**, 649.
- 18 (a) H. Liu, Y. G. Zhao, Z. J. Zhang, N. Nijem, Y. J. Chabal, H. P. Zeng and J. Li, *Adv. Funct. Mater.*, 2011, **21**, 4754; (b) J. W. Zhang, H. T. Zhang, Z. Y. Du, X. Q. Wang, S. H. Yu and H. L. Jiang, *Chem. Commun.*, 2014, **50**, 1092; (c) L. Mu, B. Liu, H. Liu, Y. T. Yang, C. Y. Sun and G. J. Chen, *J. Mater. Chem.*, 2012, **22**, 12246.
- 19 J. Park, J. R. Li, Y. P. Chen, J. Yu, A. A. Yakovenko, Z. U. Wang, L. B. Sun, P. B. Balbuena and H. C. Zhou, *Chem. Commun.*, 2012, **48**, 9995.
- 20 (a) J. S. Qin, D. Y. Du, W. L. Li, J. P. Zhang, S. L. Li, Z. M. Su, X. L. Wang, Q. Xu, K. Z. Shao and Y. Q. Lan, *Chem. Sci.*, 2012, **3**, 2114; (b) S. S. Kaye and J. R. Long, *J. Am. Chem. Soc.*, 2005, **127**, 6506; (c) J. P. Zhang and X. M. Chen, *J. Am. Chem. Soc.*, 2009, **131**, 5516.
- 21 (a) M. H. Zeng, Q. X. Wang, Y. X. Tan, S. Hu, H. X. Zhao, L. S. Long and M. Kurmoo, *J. Am. Chem. Soc.*, 2010, **132**, 2561; (b) Q. K. Liu, J. P. Ma and Y. B. Dong, *Chem. Commun.*, 2011, **47**, 7185; (c) L. Chen, K. Tan, Y. Q. Lan, S. L. Li, K. Z. Shao and Z. M. Su, *Chem. Commun.*, 2012, **48**, 5919; (d) J. H. Cui, Z. Z. Lu, Y. Z. Li, Z. J. Guo and H. G. Zheng, *Chem. Commun.*, 2012, **48**, 7967; (e) L. E. Kreno, K. Leong, O. K. Farha, M. Allendorf, R. P. Van Duyne and J. T. Hupp, *Chem. Rev.*, 2012, **112**, 1105.
- 22 (a) B. Zhao, X. Y. Chen, P. Cheng, D. Z. Liao, S. P. Yan and Z. H. Jiang, *J. Am. Chem. Soc.*, 2004, **126**, 15394; (b) W. W. He, S. L. Li, G. S. Yang, Y. Q. Lan, Z. M. Su and Q. Fu, *Chem. Commun.*, 2012, **48**, 10001.
- 23 (a) F. Pu, X. Liu, B. L. Xu, J. S. Ren and X. G. Qu, *Chem. Eur. J.*, 2012, **18**, 4322; (b) H. L. Jiang, Y. Tatsu, Z. H. Lu and Q. Xu, *J. Am. Chem. Soc.*, 2010, **132**, 5586.



## Controllable synthesis of isorecticular pillared-layer MOFs: gas adsorption, iodine sorption and sensing small molecules

Xiao-Li Hu,<sup>a</sup> Fu-Hong Liu,<sup>a</sup> Hai-Ning Wang,<sup>a</sup> Chao Qin,<sup>\*a</sup> Chun-Yi Sun,<sup>a</sup> Zhong-Min Su<sup>\*\*a</sup> and Fu-Chen Liu<sup>\*b</sup>

Five isostructural ‘pillared-layer’ MOFs have been constructed depending on the adjustable length and function of pillar ligands. In addition, **1-5** can be used to separate dye molecules based on size-exclusion effect.

