

Journal of Materials Chemistry A

Accepted Manuscript



This is an *Accepted Manuscript*, which has been through the Royal Society of Chemistry peer review process and has been accepted for publication.

Accepted Manuscripts are published online shortly after acceptance, before technical editing, formatting and proof reading. Using this free service, authors can make their results available to the community, in citable form, before we publish the edited article. We will replace this *Accepted Manuscript* with the edited and formatted *Advance Article* as soon as it is available.

You can find more information about *Accepted Manuscripts* in the [Information for Authors](#).

Please note that technical editing may introduce minor changes to the text and/or graphics, which may alter content. The journal's standard [Terms & Conditions](#) and the [Ethical guidelines](#) still apply. In no event shall the Royal Society of Chemistry be held responsible for any errors or omissions in this *Accepted Manuscript* or any consequences arising from the use of any information it contains.

COMMUNICATION

3D Hybrid of Layered MoS₂/Nitrogen-Doped Graphene Nanosheet Aerogels: an Effective Catalyst for Hydrogen Evolution in Microbial Electrolysis Cells

Cite this: DOI: 10.1039/x0xx00000x

Received 00th January 2012,
Accepted 00th January 2012Yang Hou^{a,§} Bo Zhang,^{b,§} Zhenhai Wen,^a Shumao Cui,^a Xiaoru Guo,^a Zhen He,^{c,*} and Junhong Chen^{a,*}

DOI: 10.1039/x0xx00000x

www.rsc.org/

Cost-effective catalysts are the key to the successful deployment of microbial electrolysis cells (MECs) for hydrogen production from organic wastes. Herein, we report a novel catalyst for hydrogen evolution in MECs based on a 3D hybrid of layered MoS₂/nitrogen-doped graphene nanosheet aerogels (3D MoS₂/N-GAs) that were prepared by a facile hydrothermal approach. A high output current density of 0.36 mA cm⁻² with a hydrogen production rate of 0.19 m³ H₂ m⁻³ d⁻¹ was achieved for the hybrid at a 0.8 V bias, significantly higher than that of MoS₂ nanosheets and N-GAs alone and comparable to that of the Pt/C catalyst when being applied in MECs. The outstanding performance of the hybrid benefits from its 3D conductive networks, porous structure, and strong synergic effects between MoS₂ nanosheets and N-GAs, making it a promising catalyst for hydrogen production from wastewater through bio-electrochemical reactions.

Microbial electrolysis cells (MECs) are a bio-electrochemical device in which electrogenic bacteria oxidize organic matters and transfer the generated electrons to a cathode to reduce protons for hydrogen production.¹⁻⁶ The energy barrier of proton reduction needs to be overcome with the aid of a catalyst, and the Pt-based materials have been the most effective cathode catalysts for MECs;⁷ however, high cost and low-abundance hinder the use of Pt catalysts for developing large-scale MEC systems. It is thus attractive to develop cost-effective alternatives that are suitable for MECs; a few successful examples are bulk MoS₂,⁸ N-Fe/Fe₃C@C,³ stainless steel,⁹ nickel alloys,¹⁰ and carbon felt¹¹ materials. Recently, layer-structured MoS₂ has attracted significant interest due to their unique two-dimensional (2D) structure and excellent electrocatalytic activity for hydrogen

production.^{8, 12-14} It has been considered as a promising alternative for Pt-based catalysts. However, poor intrinsic conductivity of MoS₂ limits the overall electrocatalytic performance.^{15, 16} The most effective pathway to address the above issues is to combine layered MoS₂ with 2D graphene or its derivatives.^{17, 18} Within the graphene family, nitrogen-doped graphene (NG) is one of the promising candidates because of its excellent electrical conductivity, high chemical stability, and moderate catalytic activity for hydrogen evolution.^{19, 20} More importantly, the matching layer structure between layered MoS₂ and NG not only increases the contact area for efficient charge transfer across the interface, but also shortens the charge transport time and distance,²¹ thereby improving the electrocatalytic activity.

Because the properties of catalysts are dependent on both their composition and structures, the assembly of 2D nanosheets into 3D framework architectures may open up new opportunities for further enhancing catalytic properties because of their rich porosity, large surface area, and excellent network structures compared with 1D or 2D materials.²²⁻²⁴ Graphene-based aerogels are highly porous 3D carbon material with an interconnected structure, large open pores, and good electrical conductivity that have wide applications in many fields such as batteries and catalysis.^{25, 26} Thus, it is anticipated that using graphene-based aerogels as a loading matrix would improve the activity of the embedded electrocatalysts. To the best of our knowledge, there has been no report on controllable synthesis of 3D layered MoS₂/NG nanosheet aerogels (3D MoS₂/N-GAs) as a catalyst for hydrogen production in MECs.

Herein, we report for the first time a facile approach to synthesizing a novel 3D MoS₂/N-GAs hybrid as an active electrocatalyst for hydrogen production in MECs. Benefiting from its large surface area, porous structure, and high electrical conductivity, this hybrid exhibits significantly enhanced catalytic


activity for bio-electrochemical hydrogen evolution that outperforms both bare MoS₂ nanosheets (MoS₂-NS) and N-GAs alone.

Scheme 1 illustrates the preparation procedure for the 3D MoS₂/N-GAs hybrid. First, MoS₂-NS was fabricated through a liquid exfoliation process using layered MoS₂ as the precursor. Subsequently, the resulting MoS₂-NS was mixed with graphene oxide (GO) and ammonia dispersions, and then the ternary mixture were hydrothermally assembled to form a 3D MoS₂/N-GAs hybrid (details in the Experimental Section). In this way, the MoS₂-NS was encapsulated and anchored on graphene nanosheets with the simultaneous reduction of GO and the incorporation of nitrogen species into the graphene framework.

Figure 1a shows a digital image of the monolithic 3D MoS₂/N-GAs hybrid. The morphology of the 3D hybrid architecture is similar to those reported for graphene and GO aerogels.²⁷ A typical field emission scanning electron microscopy (FESEM) image of N-GAs network shows that a well defined and interconnected 3D porous N-GAs network with continuous macropores of several-hundred nanometers in diameter was clearly discerned (Figure 1b). The porous networks would favor mass transfer and reduce transport limitation of electrolyte at the cathode. After the formation of 3D MoS₂/N-GAs architecture, the thin and rigid MoS₂-NS was grown within the N-GAs networks (Figure 1c), which can efficiently prevent the aggregation and restacking of MoS₂-NS; no apparent aggregates appeared. Since the graphene-like morphology of the 3D MoS₂/N-GAs hybrid makes it difficult to distinguish MoS₂-NS and N-GAs, energy dispersive X-ray (EDX) spectroscopy was carried out (Inset

of Figure 1c). The results revealed that main elements of the hybrid are Mo, S, C, N and O, which further confirms the formation of MoS₂-NS inside the 3D N-GAs network. The content of MoS₂-NS (29.0 wt.%) in the 3D MoS₂/N-GAs hybrid was confirmed by thermogravimetric analysis (TGA) (Figure S1).

Further insights into the morphology of the hybrid were obtained from transmission electron microscopy (TEM) and high-resolution TEM (HRTEM) images. The 3D MoS₂/N-GAs hybrid displayed a laminar structured MoS₂ (black stripes) dispersed on the surface of the crumpled NG sheets (Figure 1d). The corresponding selected area electron diffraction (SAED) pattern presented several diffraction rings, which can be well indexed to the planes of hexagonal-phase MoS₂ and N-GAs sheets (Inset of Figure 1e).²¹ The HRTEM images of the hybrid show that the layered MoS₂ (4-7 layers) with a lattice spacing of 0.63 nm was dispersed on the surface of the N-GAs sheets (Figure 1e and 1f). Atomic force microscopy (AFM) indicated that the MoS₂ had a 2D nanosheet structure and the typical thickness was about 5.83 nm, which agrees well with the 9-layer MoS₂-NS (Figure S2).²⁸ In addition, the thickness of the N-GAs nanosheets was about 1 nm, which corresponds to 3 layers of graphene based on the theoretical thickness of a single-layer of graphene (~0.34 nm). Importantly, the HRTEM image also shows a distinguished and coherent interface between the MoS₂-NS and N-GAs (Figure 1f), indicating that an intimate contact might be formed, which could result in more efficient electron transfer within the hybrid and improve the overall catalytic activity for MECs.

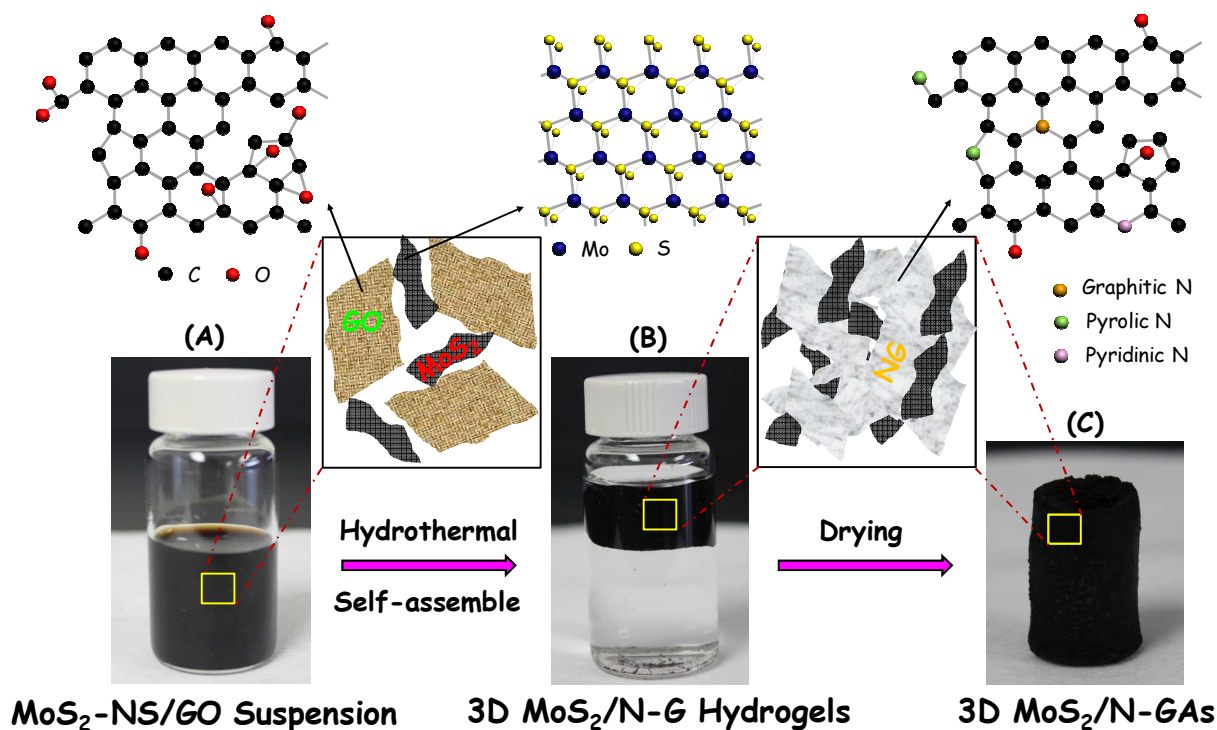

Scheme 1. Schematic illustration of the synthesis process of 3D MoS₂/N-GAs.

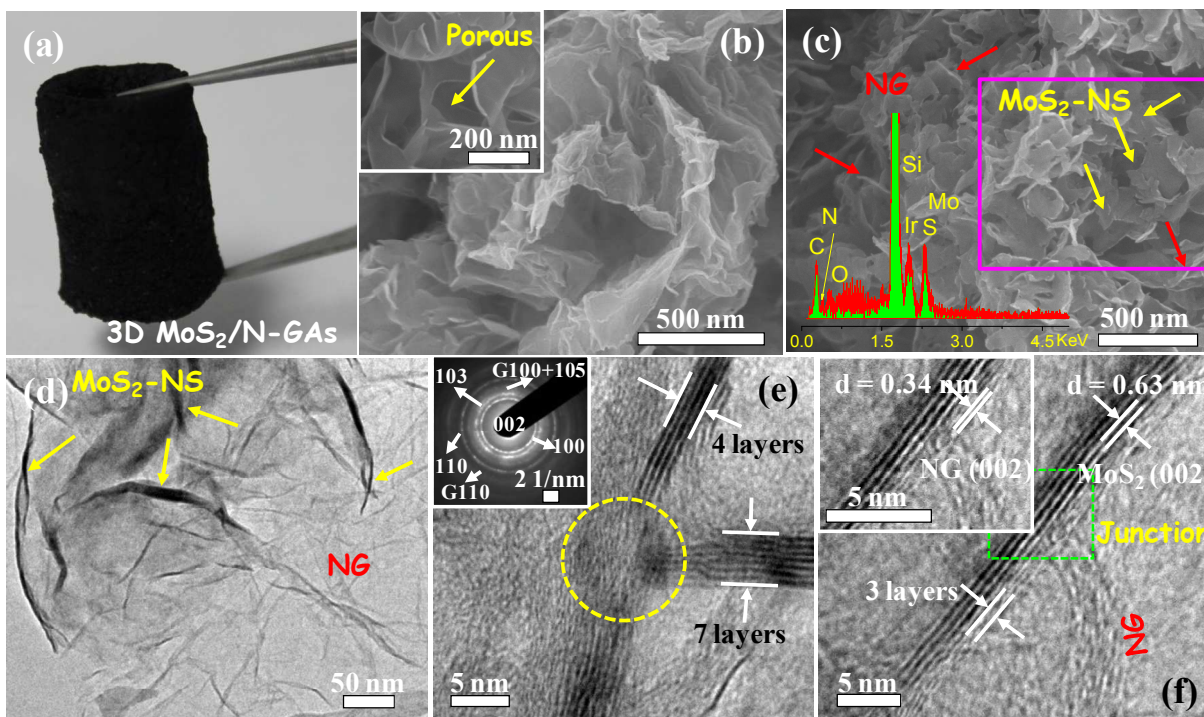


Figure 1. Photograph of 3D MoS₂/N-GAs (a). FESEM images of N-GAs (b) and 3D MoS₂/N-GAs (c). The inset of (b) shows the high magnification FESEM image of N-GAs; Inset in (c): the corresponding EDX spectrum of 3D MoS₂/N-GAs. (d-f) TEM and HRTEM images of 3D MoS₂/N-GAs. Inset in (e) is the corresponding SAED pattern. Inset in (f) shows the lattice spacing of 3D MoS₂/N-GAs.

The XRD patterns of the 3D MoS₂/N-GAs hybrid (Figure S3) indicate that the GO has been reduced to NG nanosheets after the hydrothermal treatment and that the MoS₂-NS was in the form of hexagonal crystal structures (JCPDS 37-1492). The results confirmed the co-existence of MoS₂-NS and N-GAs. X-ray photoelectron spectroscopy (XPS) revealed the presence of Mo, S, C, N, and O elements in the 3D MoS₂/N-GAs hybrid with a Mo/S atomic ratio of ~1:2, which is in good agreement with the theoretical value of MoS₂ (Figure S4a). The Mo 3d and S 2p spectra can be fitted by two spin-orbit doublets characteristic of Mo⁴⁺ and S²⁻, respectively (Figure S4b and S4c).²¹ For the high-resolution XPS spectrum of N 1s (Figure S5), it is difficult to distinguish the N 1s signal from N-doping or the presence of MoS₂ because the N 1s peak overlapped with the strong Mo 2p_{3/2} signal. However, the N 1s peak can be clearly observed from the 3D hybrid without MoS₂-NS loading (Figure S6). Considering that the presence of MoS₂ has almost no effect on N-doping during the hydrothermal process,²⁹ one can draw the conclusion that the N-atoms has been successfully incorporated into the 3D MoS₂/N-GAs hybrid. In addition, the results of the C 1s XPS spectrum confirmed the reduction of GO and the successful nitrogen doping in the 3D hybrid (Figure S7). Raman spectra show that the 3D MoS₂/N-GAs hybrid has two distinct bands at 378 and 403 cm⁻¹, which belong to the E_{2g} and A_{1g} modes of

MoS₂, respectively (Figure S8).³⁰ The characteristic disorder-induced D and graphitic-G bands of graphene are observed at 1,334 and 1,591 cm⁻¹, respectively, indicating the presence of graphene in the hybrid. The apparent increase in the I_D/I_G ratios from GO (0.99) to the 3D MoS₂/N-GAs hybrid (1.03) confirms the successful conversion of GO to N-GAs with more disorderly stacked graphene sheets.³¹ Moreover, the downshift of the G peak from GO (1,604 cm⁻¹) to RGO (1,599 cm⁻¹) can be attributed to the restoration of the conjugated structure.³² The further downshift of the G peak in the 3D MoS₂/N-GAs hybrid (1,591 cm⁻¹) may be related to the incorporation of N heteroatoms.³³ Previous studies showed that the substitution of carbon atoms with nitrogen could cause n-type doping, resulting in the down-shift of the G band.³⁴ The above results provide evidence for the incorporation of N atoms into graphene. The nitrogen adsorption-desorption isotherm (Figure S9) of the 3D MoS₂/N-GAs hybrid indicates that it possesses a typical mesoporous structure and that the Brunauer–Emmett–Teller (BET) surface area is about 43 m² g⁻¹, with an average pore size of 71 nm, which is essential for diffusion of the electrolyte and increasing contact between the electrolyte and the catalyst.³⁵

The electrocatalytic activity of the 3D MoS₂/N-GAs hybrid toward the hydrogen evolution reaction (HER) was investigated in neutral

media (100 mM phosphate buffer solution (PBS)) by linear sweep voltammetry using a three-electrode setup (Figure 2a). The 3D MoS₂/N-GAs hybrid exhibited a small onset overpotential of 236 mV/decade (all electrochemical potentials reported herein are relative to a reversible hydrogen electrode (RHE)), beyond which the cathodic current rose rapidly under more negative potentials. In contrast, both MoS₂-NS and N-GAs showed much less HER activity, with onset potentials of 337 and 495 mV, respectively, indicating that both the 3D N-GAs and MoS₂-NS are important to enhance the electrocatalytic activity for the HER. Additionally, the hybrid exhibited a high current density of 40.7 mA cm⁻² at -0.4 V, which was much higher than that observed for MoS₂-NS (11.4 mA cm⁻²) and N-GAs (4.9 mA cm⁻²), although it was lower than commercial Pt/C catalyst (10% Pt on Vulcan XC-72) at the same potential. Moreover, the overpotentials required for the 3D MoS₂/N-GAs hybrid to produce cathodic current densities of 10 and 5 mA cm⁻² were 261 and 167 mV, respectively. These overpotentials compared favorably with some of the best non-noble metal HER catalysts for neutral media that have been reported to date. For example, amorphous molybdenum sulfide showed a lower current density of 5 mA cm⁻² at ~370 mV,³⁶ and electrodeposited cobalt-sulfide required an overpotential of ~120 mV for HER.³⁷ Moreover, cobalt-embedded nitrogen-rich carbon nanotubes gave a current density of 10 mA cm⁻² at 540 mV.³⁸

Due to the HER's inherently slow kinetics under neutral media,³⁹ a relatively small Tafel slope of 230 mV/decade was observed for

the 3D MoS₂/N-GAs hybrid, but was still much smaller than the values obtained for MoS₂-NS and N-GAs, which were 372 and 487 mV/decade, respectively (Figure 2b). For practical applications, a small Tafel slope is desirable as it will enable a faster increase of the HER rate with increasing overpotentials. The low Tafel slope of the 3D MoS₂/N-GAs hybrid may be attributed to the strong electronic coupling between MoS₂-NS and N-GAs, permitting efficient electron transport from the active sites to the underlying electrode substrate. This hypothesis was further confirmed by electrochemical impedance spectroscopy (EIS). The 3D MoS₂/N-GAs hybrid showed a smaller semicircle than did the MoS₂-NS (Figure 2c), suggesting a smaller charge transfer resistance in the 3D MoS₂/N-GAs hybrid,⁴⁰ likely due to the introduction of N-GAs that enhances the electrical conductivity of 3D MoS₂/N-GAs hybrid and decreases the electron transfer resistance between MoS₂-NS. This reduced resistance implies much faster HER kinetics with the 3D MoS₂/N-GAs hybrid.⁴¹ After a long period of 6,000 s, only a slight decrease in the current density was observed for the 3D MoS₂/N-GAs hybrid, suggesting superior stability (Figure 2d). The slow decline may be due to the continuous consumption of H⁺ and the potential loss of the dropcast material from the surface of the electrode.⁴² Moreover, the typical serrate shape can be attributed to the alternating processes of H₂ bubble accumulation and release.⁴³

To further evaluate the performance of the hybrid in MECs, we compared the current generation and hydrogen production of different electrodes. When applying 0.8 V to the MECs,

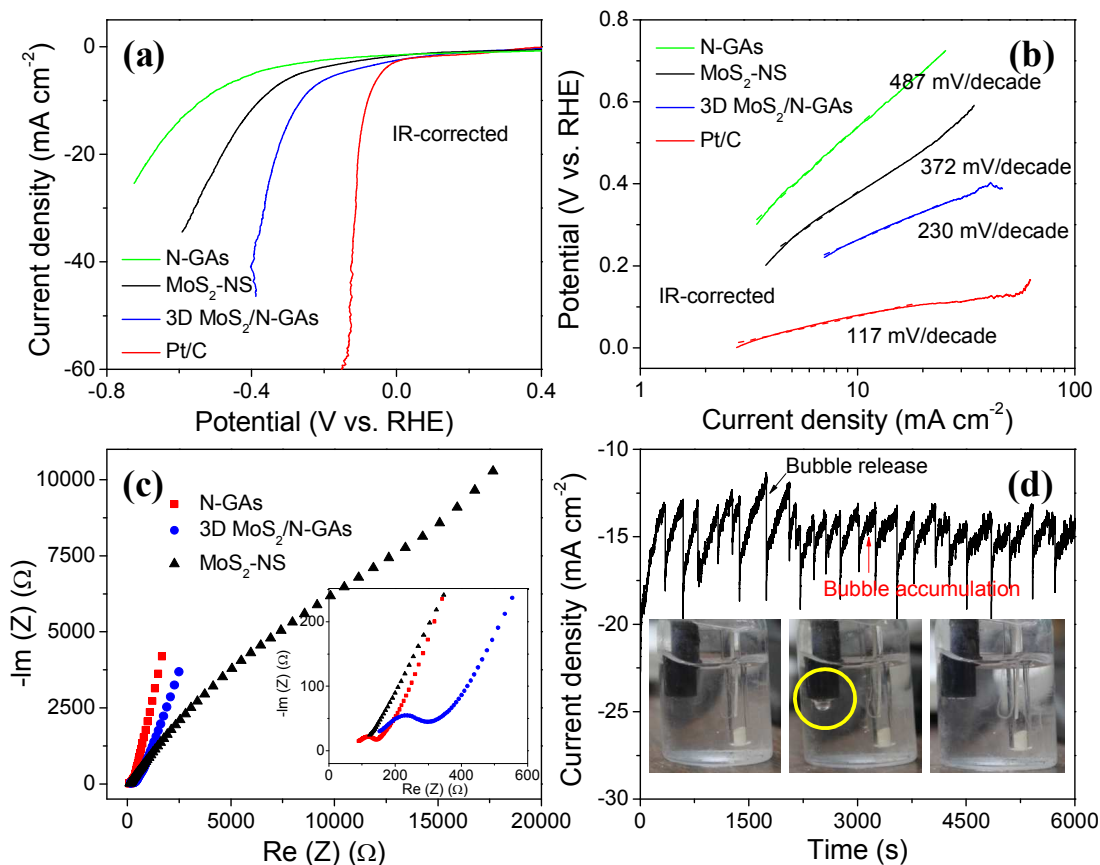


Figure 2. (a) Polarization curves, (b) corresponding Tafel plots, and (c) EIS Nyquist plots of MoS₂-NS, N-GAs, 3D MoS₂/N-GAs, and Pt/C at 5 mV s⁻¹ in 100 mM PBS. The iR drop was corrected. (d) Time dependence of cathodic current density during electrolysis at -0.3 V.

COMMUNICATION

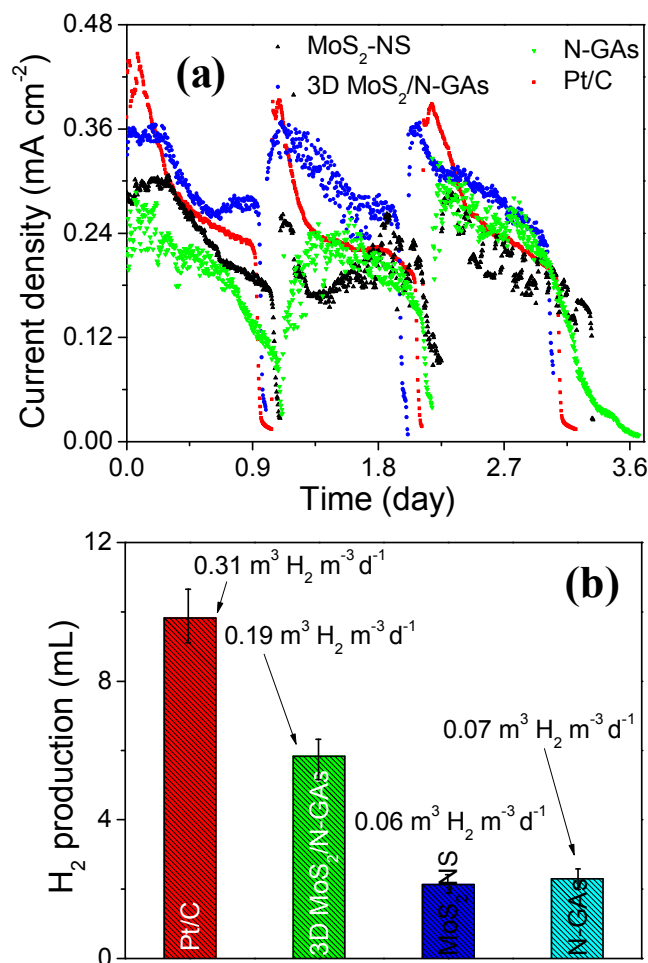


Figure 3. (a) Current generation and (b) hydrogen production with MoS₂-NS, N-GAs, 3D MoS₂/N-GAs, and Pt/C cathodes in the MECs at an external resistor of 1 Ω and an applied voltage of 0.8 V.

an electric current was generated that was directly related to bio-electrochemical hydrogen production via electron transfer. Figure 3a shows the current generation in MECs when different catalysts were employed. The MECs with the 3D MoS₂/N-GAs hybrid generated a peak current density of 0.36 mA cm⁻², which was about 1.29 and 1.44 times greater than those for MoS₂-NS (0.28 mA cm⁻²) and N-GAs (0.25 mA cm⁻²), respectively, and close to that of the Pt/C catalyst (0.40 mA cm⁻²). Moreover, the MEC with 3D MoS₂/N-GAs exhibited higher cathodic efficiencies as well (Table S1). Combining these results, it was confirmed that the hybrid catalyst had a higher catalytic activity towards the HER than did MoS₂-NS and MoS₂/N-GAs alone.

As a result of the higher current density and cathodic efficiency, the hydrogen production rate of 0.19 m³ H₂ m⁻³ d⁻¹ was observed in the

3D MoS₂/N-GAs hybrid MEC (Figure 3b). This rate exceeded those obtained with MoS₂-NS alone and N-GAs alone by more than 3.17 and 2.71 times, respectively. Although the 3D MoS₂/N-GAs hybrid (43 m² g⁻¹) had a smaller BET surface area than N-GAs (83 m² g⁻¹), the catalytic activity of the hybrid was much higher than the N-GAs, further confirming that the structure of the hybrid catalyst gave it excellent catalytic performance. Additionally, visual observation and photography confirm the formation of bubbles on the cathode, suggesting the hydrogen production from the MECs (Figure S10).

Even though the loading rate of the 3D MoS₂/N-GAs was roughly 1/4th that of the Pt/C catalyst and the surface area was 1/5th of it, the 3D MoS₂/N-GAs hybrid reached a peak current level almost the same as the Pt/C catalyst. However, due to a lower cathodic efficiency, the MEC with the 3D MoS₂/N-GAs hybrid catalyst generated less hydrogen than the MEC with the Pt/C catalyst did. Notably, the hybrid possessed the highest Coulombic efficiency of ~24.28% among the four samples tested (Table S1). The increased MEC performance with the hybrid is obvious when compared with the MoS₂-NS and N-GAs. We believe that the high electrocatalytic activity for MECs originated from synergistic effects within the aerogel structure with large surface areas, layered MoS₂ for abundant catalytic active sites, and 3D N-GAs networks for efficient charge transfer, the detailed contributions of which are currently being investigated.

Conclusions

In summary, we have designed and fabricated a novel 3D MoS₂/N-GAs hybrid using a facile two-step method through self-assembly of a mixture of GO and MoS₂-NS in the presence of an ammonia solution for high-performance bio-cathode materials in MECs. Benefiting from the unique structure, the hybrid exhibited a large output current density, a high hydrogen production rate, and excellent cycling stability, superior to those of individual MoS₂-NS and N-GAs. This work provides fundamental insights for further design and construction of other 3D layered hybrid aerogel catalysts for bio-electrochemical hydrogen evolution in MECs.

Acknowledgements

Financial support for this work was provided by the U.S. Department of Energy (DE-EE0003208) and the Research Growth Initiative Program of the University of Wisconsin-Milwaukee (UWM).

Notes and references

^a Department of Mechanical Engineering, University of Wisconsin-Milwaukee, 3200 North Cramer Street, Milwaukee, Wisconsin 53211, USA. E-mail: jhchen@uwm.edu

^b Key Laboratory of Environmental Biotechnology, Research Center for Eco-Environmental Sciences, Chinese Academy of Science, Beijing 100085, China


^c Department of Civil and Environmental Engineering, Virginia Polytechnic Institute and State University, Blacksburg, VA 24061, USA. E-mail: zhenhe@vt.edu

[§]These authors have contributed equally.

Electronic Supplementary Information (ESI) available: See DOI: 10.1039/c000000xl.

- 1 A. W. Jeremiasse, H. V. M. Hamelers, M. Saakes and C. J. N. Buisman, *Int. J. Hydrogen Energy*, 2010, **35**, 12716-12723.
- 2 Y. Kim and B. E. Logan, *Proc. Natl. Acad. Sci. U. S. A.*, 2011. DOI: 10.1073/pnas.1106335108.
- 3 L. Xiao, Z. Wen, S. Ci, J. Chen and Z. He, *Nano Energy*, 2012, **1**, 751-756.
- 4 M. Sun, G. P. Sheng, L. Zhang, C. R. Xia, Z. X. Mu, X. W. Liu, H. L. Wang, H. Q. Yu, R. Qi, T. Yu and M. Yang, *Environ. Sci. Technol.*, 2008, **42**, 8095-8100.
- 5 A. W. Jeremiasse, H. V. M. Hamelers and C. J. N. Buisman, *Bioelectrochemistry*, 2010, **78**, 39-43.
- 6 B. E. Logan, D. Call, S. Cheng, H. V. M. Hamelers, T. H. J. A. Sleutels, A. W. Jeremiasse and R. A. Rozendal, *Environ. Sci. Technol.*, 2008, **42**, 8630-8640.
- 7 J. Y. Nam, R. D. Cusick, Y. Kim and B. E. Logan, *Environ. Sci. Technol.*, 2012, **46**, 5240-5246.
- 8 J. C. Tokash and B. E. Logan, *Int. J. Hydrogen Energy*, 2011, **36**, 9439-9445.
- 9 D. F. Call, M. D. Merrill and B. E. Logan, *Environ. Sci. Technol.*, 2009, **43**, 2179-2183.
- 10 P. A. Selembo, M. D. Merrill and B. E. Logan, *J. Power Sources*, 2009, **190**, 271-278.
- 11 H. S. Lee, C. I. Torres, P. Parameswaran and B. E. Rittmann, *Environ. Sci. Technol.*, 2009, **43**, 7971-7976.
- 12 H. I. Karunadasa, E. Montalvo, Y. Sun, M. Majda, J. R. Long and C. J. Chang, *Science*, 2012, **335**, 698-702.
- 13 T. F. Jaramillo, K. P. Jorgensen, J. Bonde, J. H. Nielsen, S. Horch and I. Chorkendorff, *Science*, 2007, **317**, 100-102.
- 14 D. Merki and X. Hu, *Energy Environ. Sci.*, 2011, **4**, 3878.
- 15 J. Xie, J. Zhang, S. Li, F. Grote, X. Zhang, H. Zhang, R. Wang, Y. Lei, B. Pan and Y. Xie, *J. Am. Chem. Soc.*, 2013, **135**, 17881-17888.
- 16 M. A. Lukowski, A. S. Daniel, F. Meng, A. Forticaux, L. Li and S. Jin, *J. Am. Chem. Soc.*, 2013, **135**, 10274-10277.
- 17 F. Meng, J. Li, S. K. Cushing, M. Zhi and N. Wu, *J. Am. Chem. Soc.*, 2013, **135**, 10286-10289.
- 18 U. Maitra, U. Gupta, M. De, R. Datta, A. Govindaraj and C. N. R. Rao, *Angew. Chem. Int. Ed.*, 2013, **52**, 13057-13061.
- 19 H. Wang, T. Maiyalagan and X. Wang, *ACS Catal.*, 2012, **2**, 781-794.
- 20 L. Qu, Y. Zhao, C. Hu, L. Song, L. Wang, G. Shi and L. Dai, *Energy Environ. Sci.*, 2014, DOI: 10.1039/C4EE00106K.
- 21 Y. Hou, Z. Wen, S. Cui, X. Guo and J. Chen, *Adv. Mater.*, 2013, **25**, 6291-6297.
- 22 Z. S. Wu, S. Yang, Y. Sun, K. Parvez, X. Feng and K. Müllen, *J. Am. Chem. Soc.*, 2012, **134**, 9082-9085.
- 23 Y. Gong, S. Yang, Z. Liu, L. Ma, R. Vajtai and P. M. Ajayan, *Adv. Mater.*, 2013, **25**, 3979-3984.
- 24 J. Biener, M. Stadermann, M. Suss, M. A. Worsley, M. M. Biener, K. A. Rose and T. F. Baumann, *Energy Environ. Sci.*, 2011, **4**, 656-667.
- 25 W. Chen, S. Li, C. Chen and L. Yan, *Adv. Mater.*, 2011, **23**, 5679-5683.
- 26 H. P. Cong, X. C. Ren, P. Wang and S. H. Yu, *ACS Nano*, 2012, **6**, 2693-2703.
- 27 C. Li and G. Shi, *Adv. Mater.*, 2014, DOI: 10.1002/adma.201306104.
- 28 H. Li, X. Qi, J. Wu, Z. Zeng, J. Wei and H. Zhang, *ACS Nano*, 2013, **7**, 2842-2849.
- 29 K. Chang, D. Geng, X. Li, J. Yang, Y. Tang, M. Cai, R. Li and X. Sun, *Adv. Energy Mater.*, 2013, **3**, 839-844.
- 30 Y. Li, H. Wang, L. Xie, Y. Liang, G. Hong and H. Dai, *J. Am. Chem. Soc.*, 2011, **133**, 7296-7299.
- 31 Y. Hou, F. Zuo, A. Dagg and P. Feng, *Nano Lett.*, 2012, **12**, 6464-6473.
- 32 K. N. Kudin, B. Ozbas, H. C. Schniepp, R. K. Prud'homme, I. A. Aksay and R. Car, *Nano Lett.*, 2007, **8**, 36-41.
- 33 Z. Lin, G. Waller, Y. Liu, M. Liu and C. P. Wong, *Adv. Energy Mater.*, 2012, **2**, 884-888.
- 34 H. L. Guo, P. Su, X. Kang and S. K. Ning, *J. Mater. Chem. A*, 2013, **1**, 2248-2255.
- 35 H. Yin, C. Zhang, F. Liu and Y. Hou, *Adv. Funct. Mater.*, 2014, DOI: 10.1002/adfm.201303902.
- 36 D. Merki, S. Fierro, H. Vruble and X. Hu, *Chem. Sci.*, 2011, **2**, 1262-1267.
- 37 Y. Sun, C. Liu, D. C. Grauer, J. Yano, J. R. Long, P. Yang and C. J. Chang, *J. Am. Chem. Soc.*, 2013, **135**, 17699-17702.
- 38 X. Zou, X. Huang, A. Goswami, R. Silva, B. R. Sathe, E. Mikmeková and T. Asefa, *Angew. Chem. Int. Ed.*, 2014, DOI: 10.1002/ange.201311111.
- 39 H. Vruble and X. Hu, *Angew. Chem. Int. Ed.*, 2012, **51**, 12703-12706.
- 40 Y. Hou, F. Zuo, A. P. Dagg, J. Liu and P. Feng, *Adv. Mater.*, 2014, DOI: 10.1002/adma.201401032.
- 41 Y. Hou, T. Huang, Z. Wen, S. Mao, S. Cui and J. Chen, *Adv. Energy Mater.*, 2014, DOI: 10.1002/aenm.201400337.
- 42 E. J. Popczun, C. G. Read, C. W. Roske, N. S. Lewis and R. E. Schaak, *Angew. Chem. Int. Ed.*, 2014, **53**, 5427-5430.
- 43 J. Xie, H. Zhang, S. Li, R. Wang, X. Sun, M. Zhou, J. Zhou, X. W. Lou and Y. Xie, *Adv. Mater.*, 2013, **25**, 5807-5813.

Table of contents entry

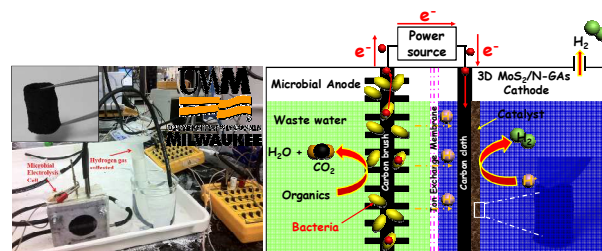

A novel 3D hybrid of layered MoS₂/nitrogen-doped graphene nanosheet aerogels exhibits significantly enhanced catalytic activity for bio-electrochemical hydrogen evolution.