

Journal of Materials Chemistry A

Accepted Manuscript



This is an *Accepted Manuscript*, which has been through the Royal Society of Chemistry peer review process and has been accepted for publication.

Accepted Manuscripts are published online shortly after acceptance, before technical editing, formatting and proof reading. Using this free service, authors can make their results available to the community, in citable form, before we publish the edited article. We will replace this *Accepted Manuscript* with the edited and formatted *Advance Article* as soon as it is available.

You can find more information about *Accepted Manuscripts* in the [Information for Authors](#).

Please note that technical editing may introduce minor changes to the text and/or graphics, which may alter content. The journal's standard [Terms & Conditions](#) and the [Ethical guidelines](#) still apply. In no event shall the Royal Society of Chemistry be held responsible for any errors or omissions in this *Accepted Manuscript* or any consequences arising from the use of any information it contains.

Room Temperature Sequential Ionic Deposition (SID) of Ag₂S Nanoparticles on TiO₂ Hierarchical Spheres for Enhanced Catalytic Efficiency

Wei Li Ong,^a Yee-Fun Lim^b and Ghim Wei Ho^{*a,b}

^a*Department of Electrical and Computer Engineering, National University of Singapore, Singapore 117576, Singapore.*

^b*Institute of Materials Research and Engineering, A*STAR (Agency for Science, Technology and Research), 3 Research Link, 117602, Singapore.*

*Corresponding author: elehgw@nus.edu.sg; Fax: +65 67754710; Tel: +65 65168121

† Electronic supplementary information (ESI) available.

Keywords: TiO₂, Ag₂S, hierarchical spheres, photocatalyst, water splitting, methyl orange

Abstract

Porous TiO₂ hierarchical spheres with high surface area synthesized *via* solvothermal method were successfully modified with Ag₂S co-catalyst by a sequential ionic deposition (SID) method at room temperature. The presence of Ag₂S facilitated efficient charge separation, thus reducing recombination and enhancing photocatalytic activity of the photocatalyst. The enhanced photocatalytic performance was demonstrated by water splitting where hydrogen (H₂) gas was produced at an evolution rate of 708 μmol h⁻¹ g⁻¹ and methyl orange was degraded with a rate constant of 0.018 min⁻¹. This is the first time that photocatalytic water splitting using a suspension system has been demonstrated on a Ag₂S/TiO₂ hierarchical heterostructure and the material shows stability in its photocatalytic performance despite being recycled several times. The composite material presents properties which are highly promising for generation of clean energy and environment clean up applications.

Introduction

There is currently a pressing demand around the globe for photocatalysts capable of generating H₂ as a form of clean and renewable energy source, and also respond to environmental cleaning needs (e.g. wastewater treatment). Titanium (IV) dioxide (TiO₂) has always been a material highly regarded for its photocatalytic properties on top of being cheap, non-toxic and environmentally friendly.¹ Degussa P25 may have demonstrated decent

performance in photocatalysis,² but hierarchical structures such as hierarchical spheres have shown enhanced performance in photocatalytic H₂ production due to its high surface area, and also the ability to entrap incident radiation due to the light scattering effect.³ Moreover, such hierarchical spheres possess the advantages of short diffusion length for photocatalytic reactions, and high porosity and stability offered by the robust 3D architecture.⁴ However, the performance is still far from satisfactory when compared to other photocatalytic materials and the two main reasons are the wide band gap of TiO₂ and high recombination rate of the photogenerated electrons and holes.⁵ To enhance the photocatalytic performance, co-catalysts can be loaded on the TiO₂ hierarchical structures to solve both problems. Besides loading nanoparticles of expensive noble metals,⁶ metal-oxides and sulfides which are equally if not more effective, can also be used as a cheaper alternative.^{7,8} In recent years, the development of sulfides as both the core photocatalytic material as well as co-catalysts have attracted increasing amounts of attention.⁹⁻¹¹ Silver sulfide (Ag₂S) having a direct band gap of 1.0 eV,¹² is a potential candidate as co-catalyst to TiO₂. Its conduction band (-0.3 eV) is less anodic than the corresponding TiO₂ band (-0.1 eV), and its valence band (+0.7 eV) is more cathodic than the TiO₂ valence band (+3.1 eV).¹³ In addition, α -Ag₂S possesses negligible toxicity compared to other commonly used narrow band gap materials.¹⁴ Several papers have reported Ag₂S loading on TiO₂, however, most of them only demonstrated photocatalytic degradation of dyes and organic materials,^{15, 16} or use it for photoelectrochemical water splitting.¹⁷⁻²⁰ To the best of our knowledge, no paper has reported or investigated its use for photocatalytic water splitting in the photocatalyst suspension system.

One way of synthesizing Ag₂S nanoparticles is *via* the SID method which is a simple fabrication methodology that can be carried out at room temperature and normal atmospheric pressure. The overall process is not only cost-effective, it also does not include any toxic by-product making it environmentally friendly, and the density of nanoparticles deposited can be easily controlled by merely varying the deposition cycles. A typical process involves immersing the host photocatalytic material into silver nitrate (AgNO₃) and thiourea (SC(NH₂)₂) solutions successively for as many cycles as desired to produce a uniform deposition of Ag₂S nanoparticles on the host material with good heterojunction. The good interface will promote transfer of charge carriers between the host photocatalytic material and the co-catalysts, hence producing excellent photocatalytic performance.

In this paper, Ag_2S is synthesized as a co-catalyst to TiO_2 hierarchical spheres using the SID method. The number of loading cycles is varied to investigate the various loading densities and derive the optimal density of Ag_2S nanoparticles for photocatalytic water splitting. The best sample was recycled for 5 times to demonstrate its reusability and stability. The performance of the $\text{Ag}_2\text{S}/\text{TiO}_2$ composite in degradation of organic pollutant was also demonstrated *via* the photodegradation of methyl orange (MO).

Experimental

Synthesis of TiO_2 hierarchical spheres

The TiO_2 hierarchical spheres were synthesized by a solvothermal method following Wu *et al.*'s work.⁴ 6 ml of dimethylformamide (DMF, Alfa Aesar) was mixed with 20 ml of isopropanol (IPA, HPLC grade, Tokyo Chemical) by stirring. 1 ml of titanium n-butoxide (TBT, Sigma Aldrich) was then added to the mixture and stirred. The mixture was transferred to a Teflon-lined autoclave and heated at 200 °C for 3 h. The synthesized product was washed and centrifuged 3 times with ethanol. After drying at 90 °C for 3 h, the TiO_2 hierarchical spheres were annealed at 450 °C for 2 hours with a ramp rate of 5 °C min^{-1} to obtain anatase TiO_2 hierarchical spheres.

Loading of Ag_2S nanoparticles

The Ag_2S nanoparticles were loaded on the TiO_2 hierarchical spheres at room temperature using the SID method. AgNO_3 serves as the precursor for Ag^+ ions, while $\text{SC}(\text{NH}_2)_2$ is the precursor for S^{2-} ions. AgNO_3 was dissolved in ethanol to produce a solution of 0.05 M concentration while $\text{SC}(\text{NH}_2)_2$ was dissolved in methanol to produce a 0.05 M solution. Ethanol and methanol were used instead of water as solvents because of their lower surface tension and high wetting ability which promotes superior penetration ability of the reacting solution deeply into the pores, resulting in uniform assembling of Ag_2S nanoparticles on the TiO_2 hierarchical spheres. The TiO_2 hierarchical spheres were dispersed in the AgNO_3 solution and magnetically stirred for 1 min as shown in Scheme 1(a). The hierarchical spheres were then centrifuged and washed with ethanol to remove loosely bound and excess precursor solution, before placing into the $\text{SC}(\text{NH}_2)_2$ solution and stirring for 3 min. The rinsing step also helps to prevent homogeneous precipitation of Ag_2S in the solution. The hierarchical spheres were then centrifuged and washed with methanol. This entire process constitutes as 1 cycle of Ag_2S loading. The TiO_2 hierarchical spheres were loaded with Ag_2S

through 1 to 5 loading cycles, and the samples are denoted as n-Ag₂S/TiO₂, where n represents the number of loading cycles. The photocatalyst became darker in colour as the number of cycles increased (Scheme 1(b)). The samples were then dried at 60 °C for 2 hours to complete the loading process.

Photocatalytic testing (water splitting and MO degradation)

The photocatalytic activity of the composites was investigated by dispersing the photocatalysts in a methanol/water solution and illuminating with simulated solar light. 2 mg of n-Ag₂S/TiO₂ was dispersed in 10 ml of 10% v/v methanol/water solution by sonication in a cylindrical quartz reaction cell (volume 25 ml) which was sealed with a rubber septum. The cell was purged with argon (Ar) gas for 10 min then irradiated with a 300 W Xenon arc lamp (intensity 100 mW cm⁻²) with magnetic stirring. Gas samples were extracted using a 100 µl gas tight syringe and analyzed with a gas chromatograph (GC2010). For the photodegradation of MO, 15 mg of photocatalyst was dispersed in 15 ml of 0.015 mM aqueous MO solution in the cylindrical quartz reaction cell by sonication. The mixture was then magnetically stirred in the dark for 30 min to attain complete adsorption-desorption equilibrium, before being illuminated with a 300 W Xenon arc lamp. The concentration of MO was determined using a UV-VIS-NIR spectrophotometer and the maximum absorbance peak value at 462.5 nm was used to plot the amount of MO degraded and thus, determine the photodegradation activity of the composite. Photocatalytic experiments under visible irradiation was carried out with a cut-off filter ($\lambda > 400$ nm). After completion of the photocatalytic experiments, the reaction mixtures were centrifuged to separate the photocatalysts from the reaction mixture and disposed properly.

Materials characterisation

The morphology of the n-Ag₂S/TiO₂ composite was characterized by scanning electron microscopy (SEM, JEOL FEG JSM 7001F) operated at 15 kV. The crystal structure of the composite was investigated with transmission electron microscopy (TEM, Philips FEG CM300) operated at 200 kV and X-ray diffraction (XRD, D5005 Bruker X-ray diffractometer equipped with graphite-monochromated Cu K α radiation at $\lambda = 1.541$ Å). Elemental composition was studied using energy-dispersive X-ray spectroscopy (EDX, Oxford Instruments) while the valence states of the various elements were determined through X-ray photoelectron spectroscopy (XPS). UV-VIS-NIR spectrophotometer (UV-VIS, Shimadzu UV-3600) was used to measure the absorbance characteristics of the composites and MO

solution. The gas samples from the photocatalytic experiments were analyzed by gas chromatography (Shimadzu GC2010 TCD) to determine the amount of H₂ gas produced. Brunauer–Emmett–Teller (BET, Quantachrome Nova 1200) measurements were conducted with nitrogen (N₂) as the adsorbate at liquid nitrogen temperature.

Results and discussion

The TiO₂ nanostructures initially obtained from the solvothermal synthesis were layered protonated titanate hierarchical spheres (LTHSs) constructed from thin curved nanosheets.⁴ After annealing at 450 °C in air, the LTHSs were converted to porous titania hierarchical spheres (PTHs) which were assembled from small anatase crystallites as shown in Fig. 1(a) and (b). The disappearance of the nanosheets in PTHs could probably be attributed to the recrystallization of pristine LTHSs into anatase phase and the sintering process that takes place in the relatively fragile ultrathin nanosheets. The structure of the PTHs could be observed more clearly in TEM (Fig. 1(c) and (d)). The clear lattice fringes observed in Fig. 1(d) indicates the crystallinity of the TiO₂ hierarchical spheres, and the lattice spacing of 0.35 nm is in agreement with the values for the (101) lattice planes of tetragonal anatase TiO₂.²¹ The TiO₂ hierarchical spheres exhibits better H₂ production performance as compared to commercial Degussa P25 and TiO₂ nanotubes (synthesized based on previous work)²² as shown in Fig. 1(e). The SEM images in insets of Fig. 1(e) show the morphologies of the various TiO₂ nanostructures. P25 has a H₂ evolution rate of 70 μmol h⁻¹ g⁻¹ while TiO₂ nanotubes produced H₂ at a higher rate of 100 μmol h⁻¹ g⁻¹. The as-synthesized TiO₂ hierarchical spheres could produce H₂ at an improved rate of 167 μmol h⁻¹ g⁻¹. BET measurements of the 3 TiO₂ nanostructures revealed specific surface areas of 48, 71 and 154 m² g⁻¹ for the P25, TiO₂ nanotubes and TiO₂ hierarchical spheres respectively. Despite not having the highest surface area, TiO₂ hierarchical spheres still showed the highest H₂ evolution rate due to the faster electron transport rates and slower recombination rates, and also the considerable surface area which facilitates better access and diffusion of liquid and gaseous reactants, which is beneficial for photocatalytic activity.²³ The hierarchical structure also favors the harvesting of light due to multiple scattering within the framework.²⁴⁻²⁶ The photocatalytic performance of the TiO₂ hierarchical spheres can be further improved by loading Ag₂S as a co-catalyst on it. Ag₂S nanoparticles were loaded onto the TiO₂ hierarchical spheres as co-catalyst by the SID method at room temperature. When the TiO₂ hierarchical spheres are dispersed in AgNO₃

solution and magnetically stirred, the Ag^+ ions are adsorbed on the surface of the TiO_2 crystallites. The loosely bounded and excess Ag^+ ions were then removed by rinsing in ethanol. The Ag^+ coated TiO_2 hierarchical spheres were subsequently stirred in $\text{SC}(\text{NH}_2)_2$ solution which provides the S^{2-} ions to form Ag_2S nanoparticles. The Ag^+ ions react with the S^{2-} ions to form Ag_2S nanoparticles on the surface of the TiO_2 hierarchical spheres. The density of Ag_2S nanoparticles deposited on the surface of the TiO_2 hierarchical spheres can be varied by varying the number of loading cycles from 1 to 5. The EDX spectra in Fig. 2(a) shows the presence of Ag and S in 3- $\text{Ag}_2\text{S}/\text{TiO}_2$, indicating that Ag_2S nanoparticles were successfully deposited. Prominent peaks of Ti $L\alpha_{1,2}$ at 0.45 keV, Ti $K\alpha_{1,2}$ at 4.51 keV and Ti $K\beta_{1,3}$ at 4.93 eV due to the TiO_2 hierarchical spheres were clearly observed in the spectra. Several peaks related to Ag and S were also detected: Ag L_1 at 2.63 keV, Ag $L\alpha_1$ at 2.98 keV, Ag $L\beta_1$ at 3.15 keV, S $K\alpha_{1,2}$ at 2.31 keV and S $K\beta_1$ at 2.46 keV. The Pt peaks originated from the sputtering Pt to enhance the image contrast. From the EDX spectra, it can be seen that the SID method is a reliable method to deposit Ag_2S nanoparticles onto TiO_2 hierarchical spheres. The atomic% of Ag and S on the $\text{Ag}_2\text{S}/\text{TiO}_2$ composites are presented in Table 1. The atomic% of Ag and S on the TiO_2 hierarchical spheres was noted to increase as the number of loading cycles increases, indicating a higher density of Ag_2S nanoparticles with more loading cycles. This observation is supported by the TEM images in Fig. 2(b)-(e) which show the distribution and density of Ag_2S on the LTHSs with loading cycles of 1, 3 and 5 respectively at both low and high (insets of Fig. 2(b)-(e)) magnifications. From the TEM images, the density of Ag_2S nanoparticles is observed to increase with increasing number of loading cycles. It should be noted that the Ag_2S nanoparticles were intentionally loaded on LTHSs instead of PTHSs solely for TEM imaging purposes. In so doing, the darker contrast of the Ag_2S nanoparticles could be seen clearly against the lighter contrast of the nanosheets in the LTHSs. All other characterizations and performance measurements were conducted using PTHSs loaded with Ag_2S .

Fig. 3(a) shows a HRTEM image of 3- $\text{Ag}_2\text{S}/\text{TiO}_2$ where the lattice planes of the anatase TiO_2 and the Ag_2S can be clearly observed, indicating that the composite is highly crystalline and a good interface exists between Ag_2S and TiO_2 . The diameter of the Ag_2S nanoparticle was measured to be about 5 nm. A lattice spacing of 0.35 nm was determined by the fast Fourier transform (FFT) pattern (Fig. 3(b)) and could be attributed to the (101) plane of anatase TiO_2 ²¹ while the d -spacing of 0.23 nm corresponds to the (-112) plane of Ag_2S (Fig. 3(c)).²⁷ The crystalline structure of the composite is also shown by the XRD spectra in Fig. 3(d). The




peaks at 25.45, 38.05, 48.25, 54.15, 55.15 and 62.95°, can be indexed to the (101), (004), (200), (105), (211) and (204) crystal planes of the anatase phase of TiO₂ (JCPDS card No. 21-1272) respectively, and these peaks are present in both TiO₂ and 3-Ag₂S/TiO₂. The (111), (-112), (-121), (121), (-103), (200) and (-131) diffraction peaks at 28.97, 31.52, 34.38, 36.81, 37.72, 43.41 and 45.42° respectively can be indexed to monoclinic Ag₂S (JCPDS card No. 14-0072).

XPS was also carried out to determine the valence states of the elements present in TiO₂ (not shown here) and the 3-Ag₂S/TiO₂ composite (Fig. 4). Ti and O were detected in TiO₂ and the 3-Ag₂S/TiO₂ composite as shown in Fig. 4(a) and (b). The Ti 2p_{3/2} and 2p_{1/2} peaks observed at 458.8 and 464.4 eV respectively indicate that Ti is present as Ti⁴⁺ in the form of TiO₂. The O1s peak located at 529.7 eV is attributed to the Ti-O-Ti bond, reinforcing the presence of TiO₂.²⁸ Ag and S were not detected in the XPS spectra of the TiO₂ hierarchical spheres but were present in the 3-Ag₂S/TiO₂ composite. The Ag 3d_{5/2} and 3d_{3/2} peaks (Fig. 4(c)) were observed to be located at 368.2 and 374.2 eV respectively. The Ag 3d peaks located at these 2 energy levels indicate the presence of Ag in the state of Ag⁺. No metallic Ag was present in the composite. The S 2p peak (Fig. 4(d)) can be deconvoluted into S 2p_{3/2} (159.6 eV) and 2p_{1/2} (160.8 eV) which indicates that S is present as S²⁻. From the Ag 3d and S 2p peaks, it can be concluded that Ag and S are present as Ag₂S.¹⁷


BET measurements were carried out on the TiO₂ hierarchical spheres and 3-Ag₂S/TiO₂ to investigate the textural characteristics. The N₂ adsorption-desorption isotherms are shown in Fig. 5(a) and (b), and the insets show the corresponding pore size distribution. The isotherms can be categorized as type IV with small hysteresis loops observed at a relative pressure of 0.4 to 0.9. The BET specific surface area obtained from the TiO₂ hierarchical spheres is 71 m² g⁻¹ with a total pore volume of 0.28 cm³ g⁻¹ while that of 3-Ag₂S/TiO₂ is 63 m² g⁻¹ with a total pore volume of 0.33 cm³ g⁻¹. The TiO₂ hierarchical spheres have pores with diameters of 5.78 nm while the 3-Ag₂S/TiO₂ has larger pore size at 12.49 nm. The slight decrease in the surface area can be attributed to the deposition of Ag₂S nanoparticles in the pores of the TiO₂ hierarchical spheres. This suggests that the photocatalytic activity is not affected by the slight decrease in surface area of the composite, and the enhancement in performance is mainly due to the alignment of the energy levels and charge transfer at the Ag₂S/TiO₂ interface. The absorption spectra of the n-Ag₂S/TiO₂ composite are shown in Fig. 5(c). The TiO₂ hierarchical spheres exhibited an absorption band edge at 380 nm which is in accordance with its large band gap of 3.2 eV, and the absorption in the visible range was weak. However, after

loading Ag₂S, the absorption in the visible range increased without any observable shift in the band gap. The increase in absorption is attributed to the narrow band gap of Ag₂S nanoparticles. With an increased absorption in the visible wavelength, more electron-hole pairs will be generated in the composite under UV-visible illumination.

The photocatalytic performance of the composites with different loading cycles for water splitting is shown in Fig. 6(a). After one loading cycle of Ag₂S, the H₂ evolution rate improved from 167 to 412 μmol h⁻¹ g⁻¹, demonstrating the effectiveness of Ag₂S as a co-catalyst. The H₂ evolution rate continued to increase with more loading cycles and peaked at 708 μmol h⁻¹ g⁻¹ for 3 loading cycles but subsequently decreased for higher loading cycles, plummeting to 330 μmol h⁻¹ g⁻¹ for 5 loading cycles. Despite the drop in performance, the H₂ evolution rate is still higher than that of the pristine TiO₂ hierarchical spheres, indicating that the presence of Ag₂S on TiO₂ as a co-catalyst will aid in improving the photocatalytic performance regardless of the amount. In this case, 3 loading cycles provided the highest enhancement to the H₂ evolution rate, and the H₂ evolution rate of 708 μmol h⁻¹ g⁻¹ was about 4 times better than that of pristine TiO₂ hierarchical spheres. The improved performance is due to the charge transfer between Ag₂S and TiO₂ as shown in Fig. 6(b) which favors the separation of photo-induced electron-hole pairs in the photosensitized TiO₂. When the composite is illuminated with UV-visible light, the electrons generated are transferred from conduction band (CB) of Ag₂S to CB of TiO₂, whereas the holes are transferred from valence band (VB) of TiO₂ to VB of Ag₂S (corresponding to Eq. (1)-(3)).



This transfer process is thermodynamically more favorable because both the CB and VB of Ag₂S lie above that of TiO₂, and the electron-hole transfer process is faster than its recombination. The holes will react with methanol in a stepwise reaction producing H⁺ and several intermediates in the process which were eventually oxidized to CO₂, while the electrons reduce the H⁺ ions to form H₂ according to Eq. (4) and (5).²⁹⁻³¹





When the number of loading cycles was increased to more than 3 times, the density of Ag₂S nanoparticles populating the surface of the TiO₂ hierarchical spheres is too high causing conglomeration. This can be seen from the TEM image of 5-Ag₂S/TiO₂ which appears much darker than the as-synthesized TiO₂ hierarchical spheres, 1-Ag₂S/TiO₂ and 3-Ag₂S/TiO₂ (Fig. 2). The darker contrast is attributed to the high density of Ag₂S nanoparticles populating the TiO₂ hierarchical spheres. This will prevent the photo-induced electrons in Ag₂S from fast injection into TiO₂, resulting in inefficient separation of the electron-hole pairs and more occurrence of recombination. The high density of Ag₂S nanoparticles will also block out the light from TiO₂, resulting in fewer photogenerated electrons and holes for the generation of H₂. These effects will result in a decline in the H₂ evolution rate.³² Besides the H₂ evolution rate, another property of the photocatalyst that is of great importance is the stability and consistency of the photocatalytic performance over repeated use. To determine this, the 3-Ag₂S/TiO₂ composite was tested for H₂ evolution repeatedly over 5 cycles (Fig. 6(c)). After each cycle, the photocatalyst was washed with DI water, re-dispersed in a newly prepared 10% v/v methanol/water solution, and purged with Ar gas before irradiating with the Xenon arc lamp again. The H₂ evolution rate exhibited only a slight drop from 708 to 628 μmol h⁻¹ g⁻¹ after 5 cycles, proving that the photocatalyst is stable and can be recycled over repeated runs.

Besides photocatalytic water splitting, the n-Ag₂S/TiO₂ composites can also be used for photodegradation of MO, which is akin to demonstrating its wastewater treatment capabilities. The degradation kinetics of MO was measured *via* the changes in their concentration, which was calculated from the absorbance peaks at 462.5 nm. From the plot in Fig. 7(a), the TiO₂ hierarchical spheres needed 180 min to fully degrade MO. After loading with Ag₂S nanoparticles, the time needed to fully degrade MO was reduced to 150 min. The 3-Ag₂S/TiO₂ composite performed the best and was able to degrade MO completely in 120 min. The photodegradation activity was further analyzed by studying the pseudo-first order kinetics of the various photocatalysts as shown in Fig. 7(b). This quantitative analysis is derived using the pseudo-first order model³³ as follows:

$$\ln(C_0/C_t) = kt \quad (6)$$

where C_0 and C_t are the concentrations of MO at time 0 and t respectively, and k is the pseudo-first order rate constant. The pseudo-first order rate constants, k , of the TiO₂ hierarchical spheres and n-Ag₂S/TiO₂ composites are summarized in Table 2. The constant k

of TiO₂ is the lowest at 0.011 min⁻¹, but it increases with Ag₂S loading. The 3-Ag₂S/TiO₂ composite has the highest *k* constant at 0.018 min⁻¹, indicating its enhanced dye degradation capability. The degradation results clearly show that the photodegradation of MO improved after loading Ag₂S on TiO₂ hierarchical spheres, and the 3-Ag₂S/TiO₂ composite produced the highest rate of photodegradation. This is most likely attributed to the optimal loading of Ag₂S nanoparticles on TiO₂, where the light harvesting ability is the best and the recombination rate is the lowest. The enhancement in photodegradation is also due to the charge transfer between Ag₂S and TiO₂, and the reduced recombination between the photo-generated electron-hole pairs (Fig. 7c). The generated electrons react with dissolved oxygen molecules and produce oxygen peroxide radicals (Eq. (7)), while the positively charged holes (h⁺) react with OH⁻ derived from H₂O to form hydroxyl radicals OH[•] (Eq. (8) and (9)). O₂^{•-} and OH[•] are powerful oxidizing agents capable of degrading most pollutants.^{34, 35} The MO molecules can be photodegraded by the O₂^{•-} and OH[•] radicals to CO₂, H₂O, or other mineralization (Eq. (10)).



The Ag₂S/TiO₂ composite material is also capable of showing photocatalytic activity under visible illumination. 3-Ag₂S/TiO₂ was used to photodegrade MO under visible light irradiation. The MO was completely degraded after 210 min and from the analysis of the pseudo-first order kinetics, the rate constant *k* of the Ag₂S-TiO₂ composite was determined to be 0.011 min⁻¹ as shown in Fig. S1†. This shows that the Ag₂S-TiO₂ composite material is photoactive towards visible light irradiation, and it is a promising candidate for photocatalytic applications under visible light.

Conclusions

Ag₂S nanoparticles were successfully deposited on TiO₂ hierarchical spheres at room temperature *via* the SID method. The efficient charge separation induced by Ag₂S helped to reduce recombination, thus enhancing photocatalytic activity of the photocatalyst. The Ag₂S nanoparticles deposited over 3 loading cycles gave the best performance and could produce

H₂ gas at an evolution rate of 708 $\mu\text{mol h}^{-1} \text{g}^{-1}$. The composite material also exhibited stability when it was recycled 5 times for photocatalytic water splitting without any drastic drop in performance. The 3-Ag₂S/TiO₂ composite was capable of degrading organic pollutants, and it photodegraded MO fully within 2 hours with a rate constant of 0.018 min^{-1} . The photocatalytic activity of the composite towards visible light illumination was also demonstrated.

Acknowledgements

This work is supported by the A*STAR grant R-263-000-A96-305 and National University of Singapore (NUS) R-263-000-653-731/654-112.

Notes and references

- 1 A. L. Linsebigler, G. Q. Lu and J. T. Yates, *Chem. Rev.*, 1995, **95**, 735.
- 2 G. Wang, L. Xu, J. Zhang, T. Yin and D. Han, *Int. J. Photoenergy*, 2012, **2012**, 9.
- 3 Z. Haider and Y. S. Kang, *ACS Appl. Mater. Interfaces*, 2014, **6**, 10342.
- 4 H. B. Wu, X. W. Lou and H. H. Hng, *Chem. Eur. J.*, 2012, **18**, 2094.
- 5 M. Ni, M. K. H. Leung, D. Y. C. Leung and K. Sumathy, *Renew. Sust. Energ. Rev.*, 2007, **11**, 401.
- 6 R. Liu and A. Sen, *J. Am. Chem. Soc.*, 2012, **134**, 17505.
- 7 W. J. Foo, C. Zhang and G. W. Ho, *Nanoscale*, 2013, **5**, 759.
- 8 J. Shen, Y. L. Meng and G. Xin, *Rare Metals*, 2011, **30**, 280.
- 9 T. Zhu, C. K. N. Peh, M. H. Hong and G. W. Ho, *Chem. Eur. J.*, 2014, **20**, 11505.
- 10 J. Hong, Y. Wang, Y. Wang, W. Zhang and R. Xu, *ChemSusChem*, 2013, **6**, 2263.
- 11 H. Sheng, L. Yu, Y. Jian-Hua and Y. Ying, *Nanotechnology for Sustainable Energy*, American Chemical Society, 2013, 219.
- 12 Y. Xie, S. H. Heo, Y. N. Kim, S. H. Yoo and S. O. Cho, *Nanotechnology*, 2010, **21**, 015703.
- 13 M. C. Neves, J. M. F. Nogueira, T. Trindade, M. H. Mendonça, M. I. Pereira and O. C. Monteiro, *J. Photochem. Photobiol., A*, 2009, **204**, 168.
- 14 Y. P. Du, B. Xu, T. Fu, M. Cai, F. Li, Y. Zhang and Q. B. Wang, *J. Am. Chem. Soc.*, 2010, **132**, 1470.
- 15 L. Zhu, Z. Meng, G. Trisha and W. C. Oh, *Chin. J. Catal*, 2012, **33**, 254.
- 16 L. Zhu, Z. D. Meng and W. C. Oh, *J. Nanomater.*, 2012, **2012**, 1.
- 17 M. Gholami, M. Qorbani, O. Moradlou, N. Naseri and A. Z. Moshfegh, *RSC Adv.*, 2014, **4**, 7838.
- 18 W. G. Fan, S. Jewell, Y. Y. She and M. K. H. Leung, *Phys. Chem. Chem. Phys.*, 2014, **16**, 676.
- 19 Z. Shan, D. Clayton, S. Pan, P. S. Archana and A. Gupta, *J. Phys. Chem. B*, 2014.
- 20 Y. Xie, S. H. Yoo, C. Chen and S. O. Cho, *Mater. Sci. Eng., B*, 2012, **177**, 106.
- 21 W. G. Yang, F. R. Wan, Q. W. Chen, J. J. Li and D. S. Xu, *J. Mater. Chem.*, 2010, **20**, 2870.
- 22 W. L. Ong, M. Gao and G. W. Ho, *Nanoscale*, 2013, **5**, 11283.
- 23 J. Y. Liao, B. X. Lei, D. B. Kuang and C. Y. Su, *Energ. Environ. Sci.*, 2011, **4**, 4079.
- 24 A. Usami, *Chem. Phys. Lett.*, 1997, **277**, 105.

- 25 J. Ferber and J. Luther, *Sol. Energ. Mat. Sol. C.*, 1998, **54**, 265.
- 26 G. Rothenberger, P. Comte and M. Gratzel, *Sol. Energ. Mat. Sol. C.*, 1999, **58**, 321.
- 27 J. L. Wang, H. Feng, K. M. Chen, W. L. Fan and Q. Yang, *Dalton Trans.*, 2014, **43**, 3990.
- 28 Y. F. Gao, Y. Masuda, Z. F. Peng, T. Yonezawa and K. Koumoto, *J. Mater. Chem.*, 2003, **13**, 608.
- 29 L. S. Yoong, F. K. Chong and B. K. Dutta, *Energy*, 2009, **34**, 1652.
- 30 T. Sreethawong and S. Yoshikawa, *Catal. Commun.*, 2005, **6**, 661.
- 31 H. J. Choi and M. Kang, *Int. J. Hydrogen Energy*, 2007, **32**, 3841.
- 32 B. K. Liu, D. J. Wang, Y. Zhang, H. M. Fan, Y. H. Lin, T. F. Jiang and T. F. Xie, *Dalton Trans.*, 2013, **42**, 2232.
- 33 J. M. Herrmann, H. Tahiri, Y. Ait-Ichou, G. Lassaletta, A. R. González-Elipe and A. Fernández, *Appl. Catal., B*, 1997, **13**, 219.
- 34 M. Kaneko and I. Okura, *Photocatalysis: Science and Technology*, Springer, 2002.
- 35 A. J. Bard, R. Parsons and J. Jordan, *Standard Potentials in Aqueous Solution*, Taylor & Francis, 1985.

Figure Captions

Scheme 1 (a) Schematic illustration of SID process in each cycle of Ag₂S deposition and (b) changes in the color of the composite with increasing number of cycles.

Fig. 1 (a) and (b) SEM images, (c) TEM and (d) HRTEM images of TiO₂ hierarchical spheres. (e) H₂ evolution rates of various types of TiO₂ nanostructures. Insets show SEM images of the various TiO₂ nanostructures (scale bar indicates 100 nm).

Fig. 2 (a) EDX spectrum of 3-Ag₂S/TiO₂. (b)-(e) Low magnification TEM images of TiO₂, 1-, 3- and 5-Ag₂S/TiO₂ respectively. Insets show high magnification TEM images of the corresponding composite.

Table 1 EDX elemental microanalysis of the n-Ag₂S/TiO₂ composites.

Fig. 3 (a) HRTEM image of 3-Ag₂S/TiO₂. FFT of (b) TiO₂ and (c) 3-Ag₂S/TiO₂. (d) XRD spectra of TiO₂ and 3-Ag₂S/TiO₂.



Fig. 4 XPS spectra of 3-Ag₂S/TiO₂ composite. (a) Ti 2p, (b) O 1s, (c) Ag 3d and (d) S 2p.

Fig. 5 BET of (a) TiO₂ and (b) 3-Ag₂S/TiO₂. The insets show the corresponding pore size distributions obtained from desorption isotherms. (c) Absorbance spectra of n-Ag₂S/TiO₂ composites.

Fig. 6 (a) H₂ evolution rates of n-Ag₂S/TiO₂ composites. (b) Schematic diagram of the charge-transfer processes between Ag₂S and TiO₂ during water splitting. (c) H₂ production cycling of 3-Ag₂S/TiO₂.

Fig. 7 (a) Degradation kinetics and (b) pseudo-first order kinetics of time evolution MO photodegradation study in the presence of n-Ag₂S/TiO₂ composites. (c) Schematic diagram of the charge-transfer processes between Ag₂S and TiO₂ during MO photodegradation.

Table 2 Pseudo-first order rate constants *k* of the n-Ag₂S/TiO₂ composites.

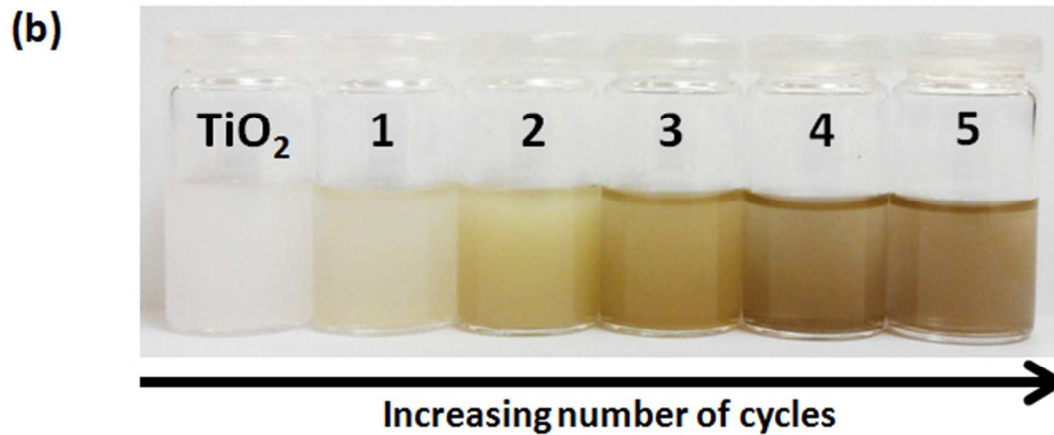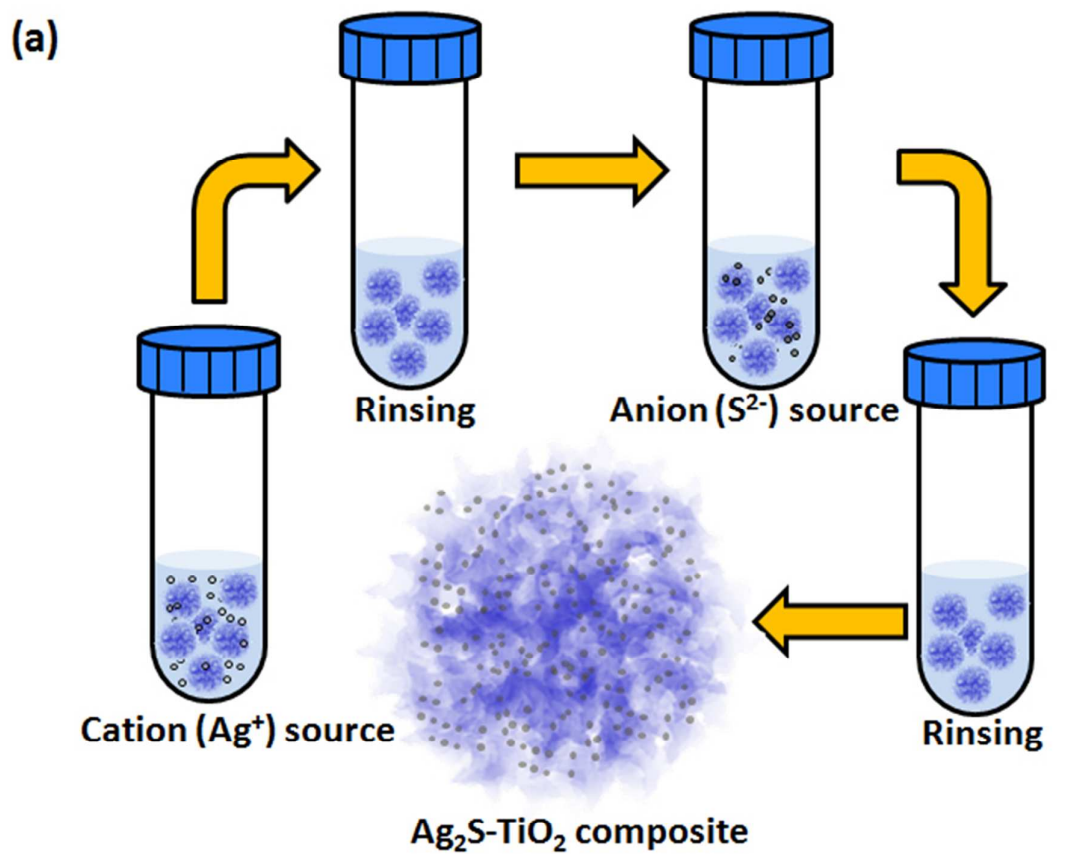

Scheme 1

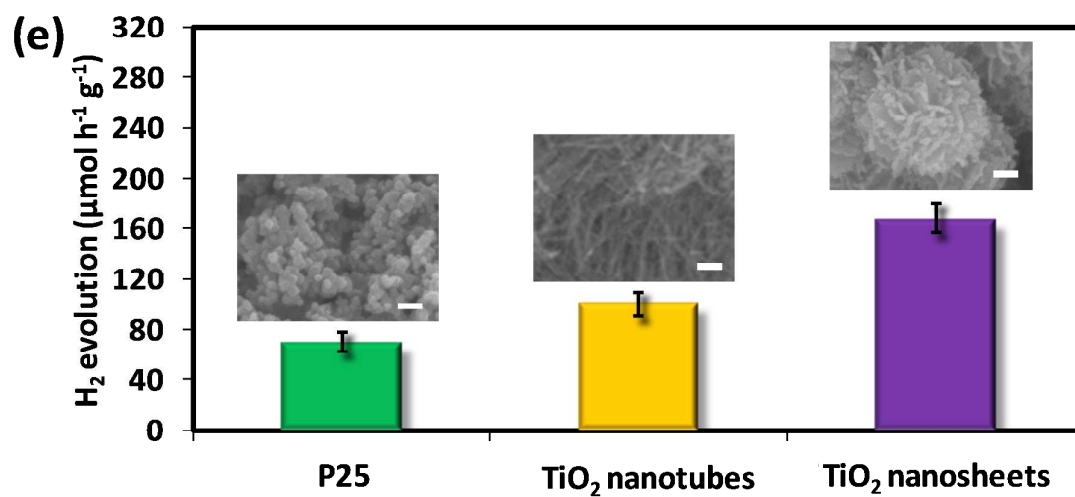
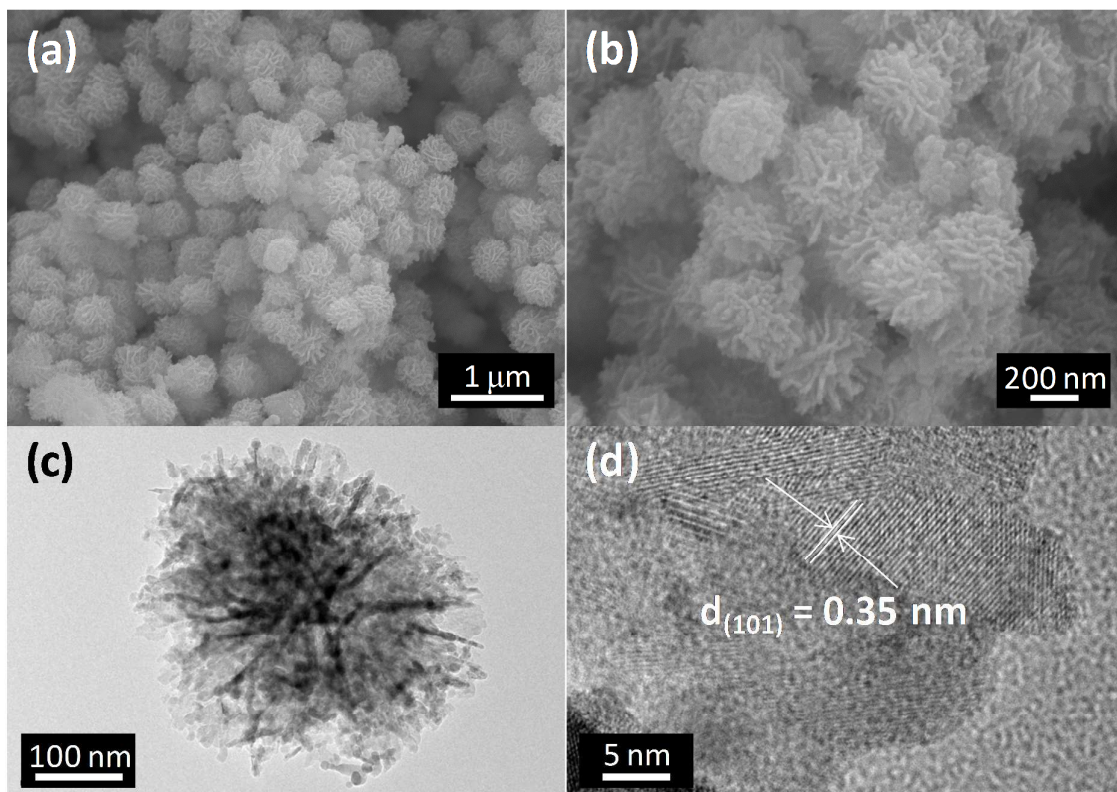


Fig. 1

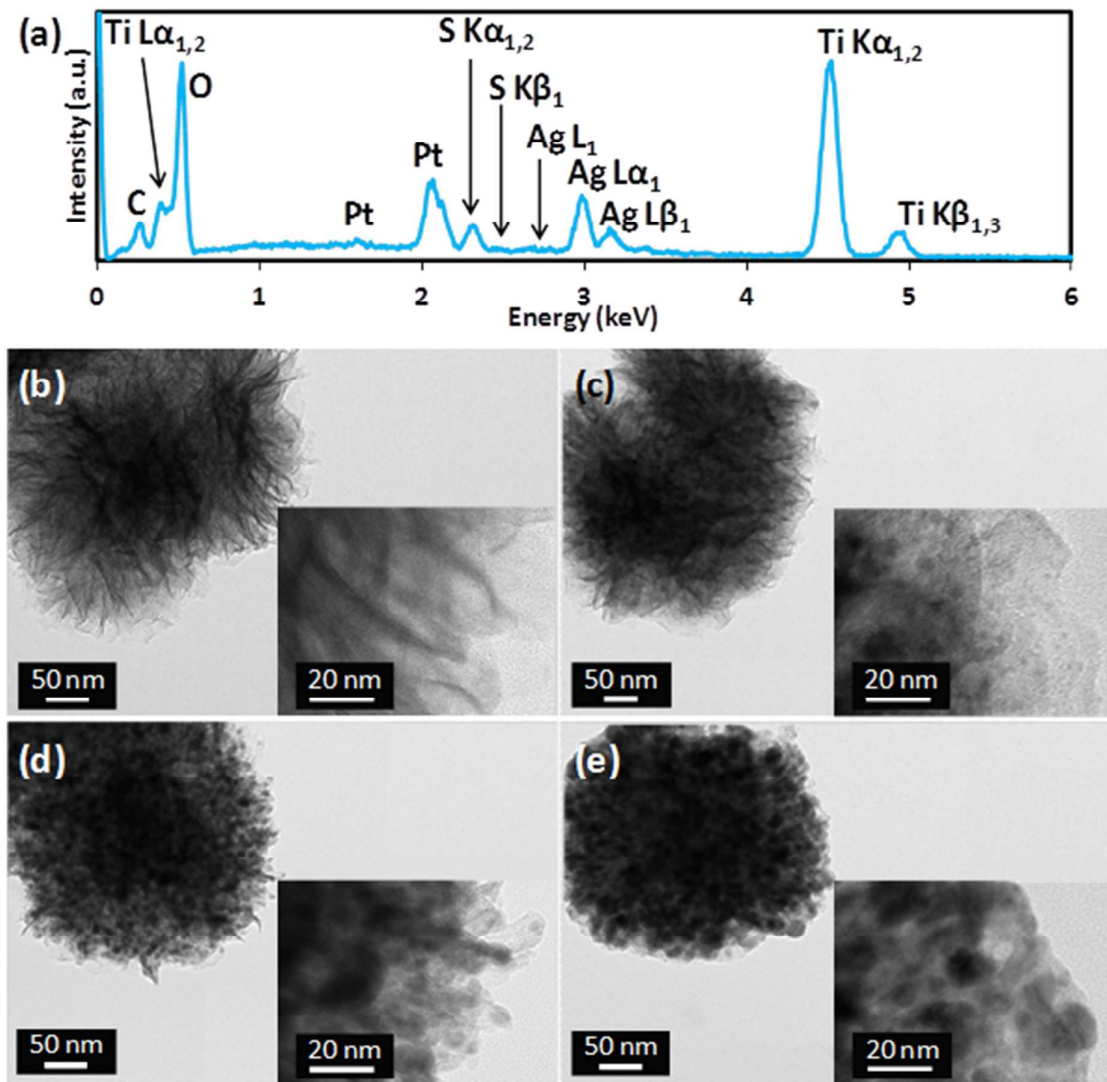


Fig. 2

Table 1

Sample Name	Atomic %	
	Ag (%)	S (%)
1-Ag ₂ S/TiO ₂	0.15	0.06
2-Ag ₂ S/TiO ₂	0.87	0.41
3-Ag ₂ S/TiO ₂	1.37	0.66
4-Ag ₂ S/TiO ₂	1.95	0.98
5-Ag ₂ S/TiO ₂	2.67	1.23

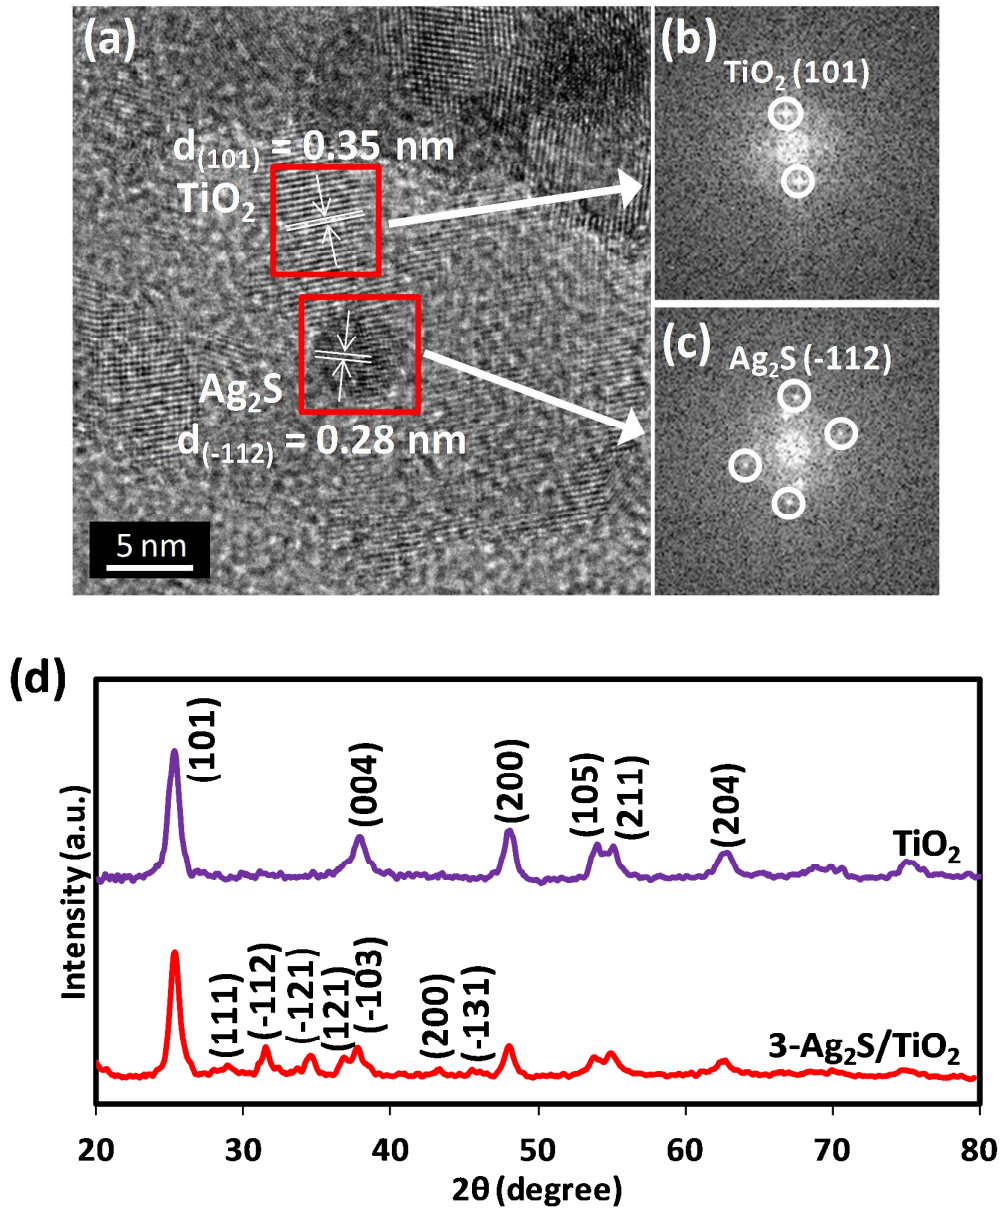


Fig. 3

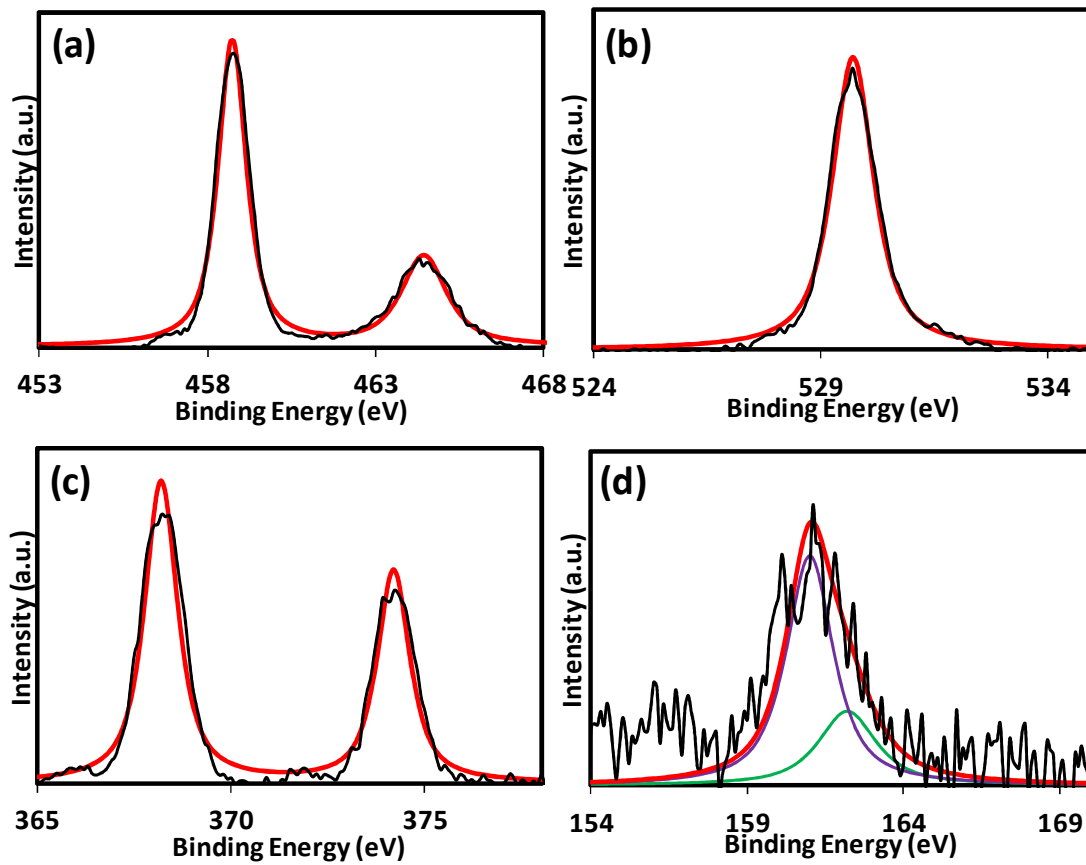


Fig. 4

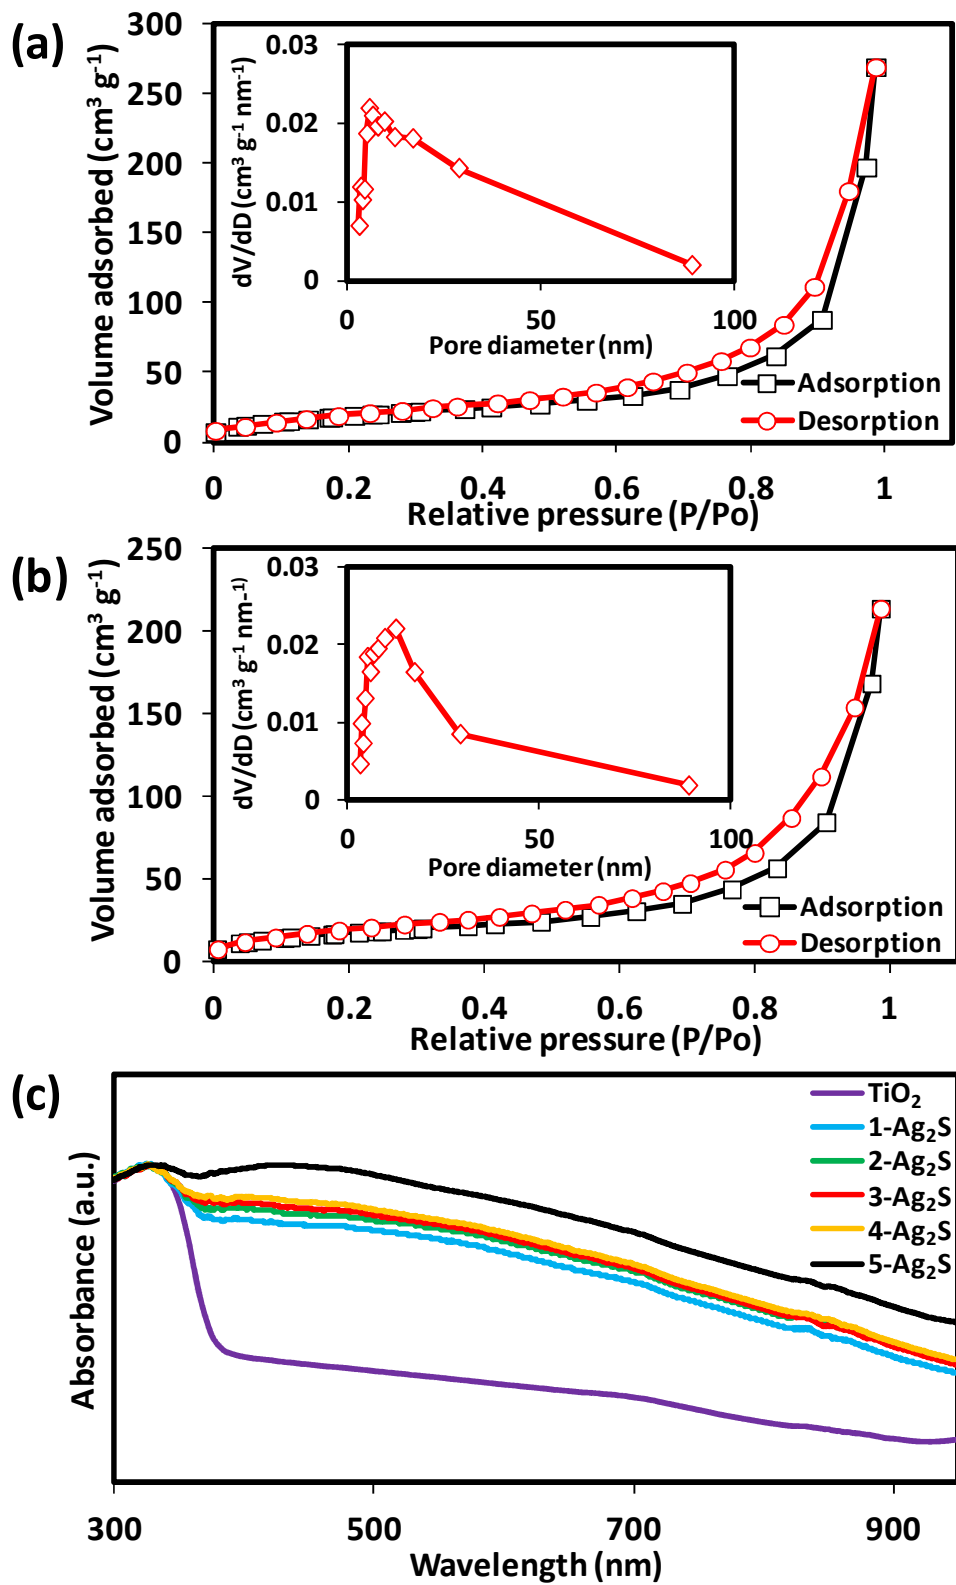


Fig. 5

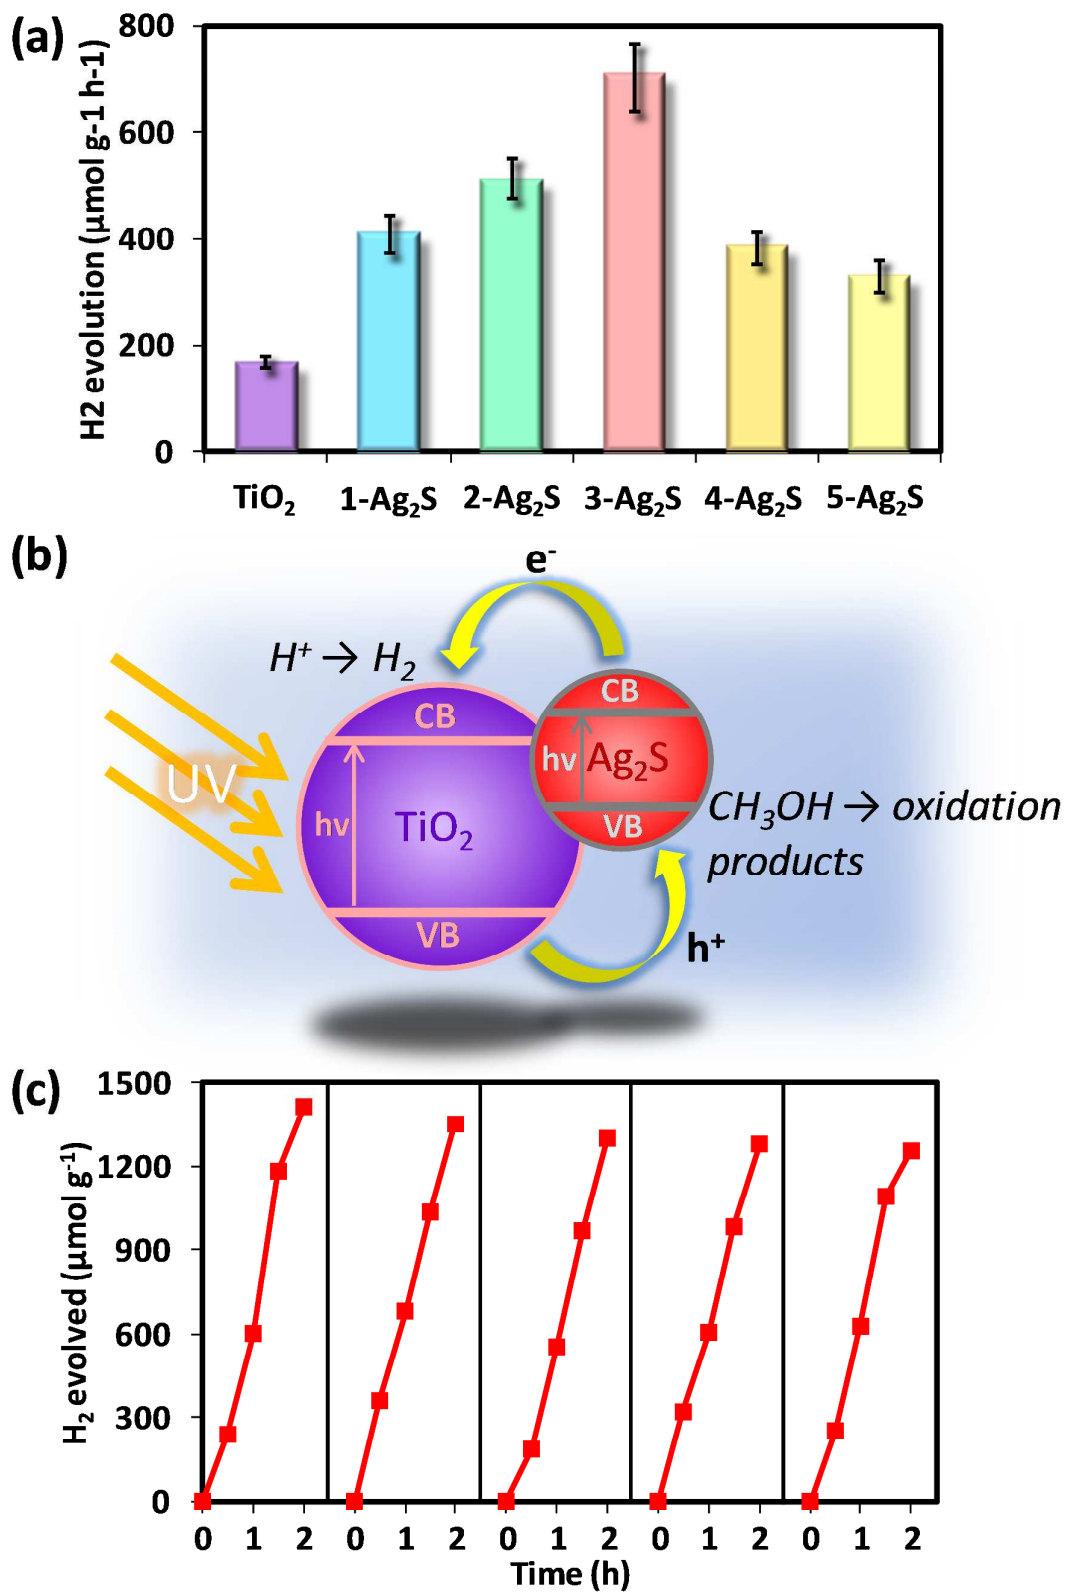


Fig. 6

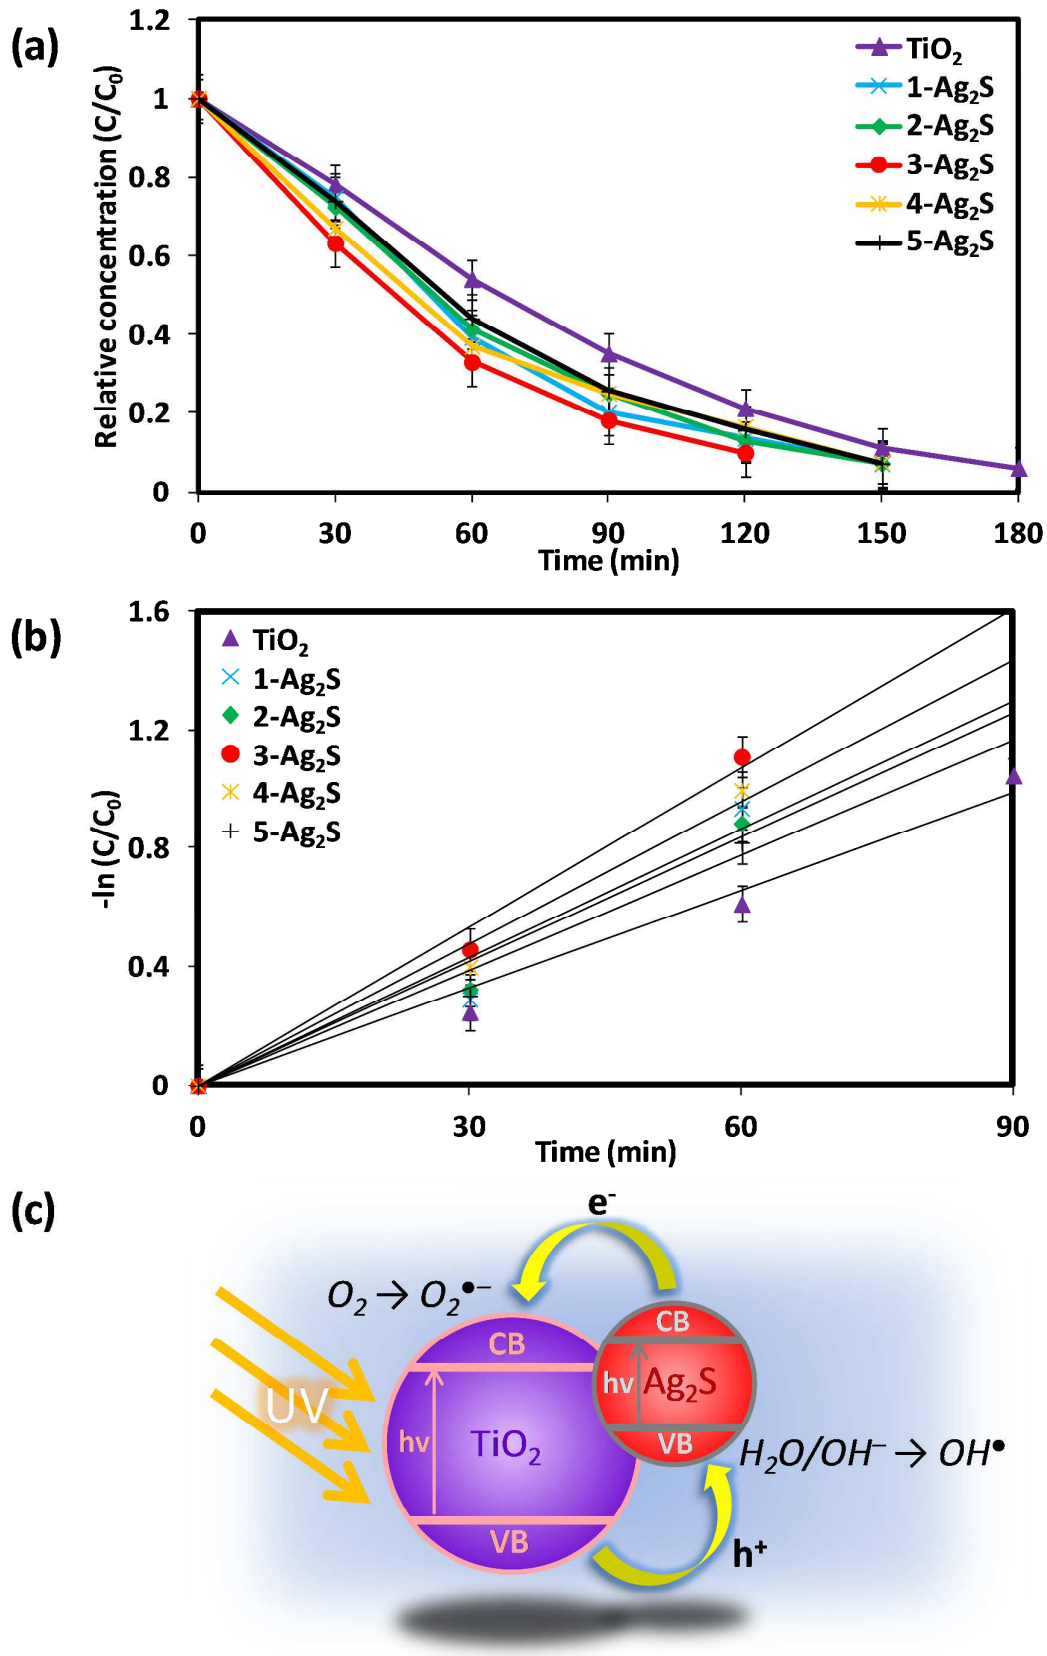


Fig. 7

Table 2

Photocatalysts	Kinetic constants, k (min ⁻¹)	Correlation coefficient, R^2
TiO ₂	0.011	0.981
1-Ag ₂ S/TiO ₂	0.014	0.945
2-Ag ₂ S/TiO ₂	0.014	0.972
3-Ag ₂ S/TiO ₂	0.018	0.988
4-Ag ₂ S/TiO ₂	0.016	0.985
5-Ag ₂ S/TiO ₂	0.013	0.973