

Journal of Materials Chemistry C

Accepted Manuscript



This is an *Accepted Manuscript*, which has been through the Royal Society of Chemistry peer review process and has been accepted for publication.

Accepted Manuscripts are published online shortly after acceptance, before technical editing, formatting and proof reading. Using this free service, authors can make their results available to the community, in citable form, before we publish the edited article. We will replace this *Accepted Manuscript* with the edited and formatted *Advance Article* as soon as it is available.

You can find more information about *Accepted Manuscripts* in the [Information for Authors](#).

Please note that technical editing may introduce minor changes to the text and/or graphics, which may alter content. The journal's standard [Terms & Conditions](#) and the [Ethical guidelines](#) still apply. In no event shall the Royal Society of Chemistry be held responsible for any errors or omissions in this *Accepted Manuscript* or any consequences arising from the use of any information it contains.

Two-Photon Excited Fluorescence of BF₂ Complexes of Curcumin Analogues: Toward NIR-to-NIR Fluorescent Organic Nanoparticles

Anthony D'Aléo,^{*[a]} Abdellah Felouat,^[a] Vasile Heresanu,^[a] Alain Ranguis,^[a]
Damien Chaudanson,^[a] Artak Karapetyan,^[a,b] Michel Giorgi,^[c] Frédéric Fages^[a]

[a] Aix Marseille Université, CNRS, CINaM UMR 7325, 13288 Marseille, France. [b] NAS Armenia, Inst Phys Res, Ashtarak 2, Armenia. [c] Aix Marseille Université, CNRS, Spectropole FR 1739, 13397 Marseille, France. E-mail : daleo@cinam.univ-mrs.fr

Abstract

The synthesis of borondifluoride complexes of curcuminoids and one- and two-photon absorption properties of **1** and **2** are described. These compounds allow the preparation of organic nanoparticles that were characterized using DLS, TEM and AFM revealing sizes around 50-60nm for **2**. The fluorescence emission spectra of the nanoparticles are red-shifted compared to those of the dye diluted in dichloromethane solution reaching the NIR region of the spectrum. This effect stems from the occurrence of π - π interactions in the solid state, as revealed from the X-ray crystal structure analysis of **1**. Those dyes exhibit significant two-photon absorption cross section in solution and nanoparticles suspension in water. The nanoparticles are shown to behave as NIR-to-NIR fluorescent nanomaterials that could be potentially used for studies in the biological transparency window. Two-photon brightnesses of *ca.* 13-14GM are obtained for both dyes, which is amongst some of the highest values reported to date for NIR-to-NIR luminophores.

Introduction

The design of two-photon absorbing fluorophores with both large two-photon absorption (TPA) cross section (σ^2) and high fluorescence quantum yield (Φ_f) remains a very active field of research because of the ever increasing demand for improved bioimaging technologies.¹⁻⁷ Considerable progress has enabled the generation of diverse classes of molecular probes that are widely used for solution-state applications of two-photon-excited fluorescence (TPEF) spectroscopy.⁸⁻¹⁴ Recently, luminescent nanoparticles have received great attention in bioimaging,^{15, 16} but organic nanoparticles that exhibit TPEF have been less investigated than the molecular counterparts. The main reason stems from the generally low fluorescence emission capability of organic dyes in the condensed phase. The photophysics of electronically excited organic nanoparticles or nanocrystals is governed by bulk and surface traps that contribute actively to fluorescence quenching depending on particle size or morphology.^{17, 18} On the other side, Z-scan studies have shown that obtaining TPA response is not the main limitation and it has even been observed that intermolecular interactions can be exploited to cooperatively enhance TPA efficiency in assemblies of aggregated dyes.¹⁹⁻²⁵ Yet, designing organic nanoparticles having a large TPEF brightness ($B^2_{max} = \sigma^2 \times \Phi_f$) for practical applications remains challenging.^{2, 26-31}

Among the set of recognized attributes of TPEF spectroscopy,¹⁻⁷ this technique enables excitation of chromophores in the near infrared (NIR), the so-called biological transparency window (*i.e.* 700-1000nm), which is mandatory for *in vivo* and *in vitro* imaging, but also for other applications requiring in-depth measurements. Conversely, for the same reason, achieving emitted light collection in the same energy range would optimize the sensitivity of detection. This would imply for the dye to have a large TPEF

brightness in the NIR, which adds another degree of complexity to the molecular design. While one-photon excited fluorescence (OPEF) emission in the NIR has been commonly observed in organic molecules^{32, 33} or quantum dots,³⁴⁻³⁶ examples of dyes combining both NIR TPA and NIR TPEF, coined NIR-to-NIR dyes, are still rare. Maury *et al.*³⁷ and Wong *et al.*³⁸ developed NIR-to-NIR imaging agents based on Yb(III) complexes that absorb at 800 nm and 860 nm, respectively, and emit around 1000 nm. Although cyanines represent interesting candidates,^{39, 40} their one-photon absorption (OPA) is often too far in the visible resulting in NIR TPA response out of the biological window.

Recently, we have reported the synthesis and photophysical properties of borondifluoride complexes of curcuminoids,⁴¹ a family of π -conjugated dyes that feature a central β -diketone unit. Curcuminoid ligands have been used as labels in various imaging applications,⁴²⁻⁴⁴ including those based on TPA.^{45, 46} Whereas there exists a variety of BF_2 complexes of molecules containing the acetylacetonate moiety showing unique optical and electronic properties⁴⁷⁻⁵⁵ TPA properties,^{23, 56, 57} and potential for biological imaging,⁵⁸ reports on borondifluoride-containing curcuminoids are still scarce.^{41, 59-61} Recently, related water-soluble derivatives have allowed bioimaging based on OPEF emission in the visible.⁶² BF_2 complexes of curcuminoids bearing two electron donor (D) end-groups and the strong electron acceptor (A) dioxaborine central ring display the donor-acceptor-donor (D-A-D) structure frequently found in TPA active chromophores.⁸⁻¹⁴

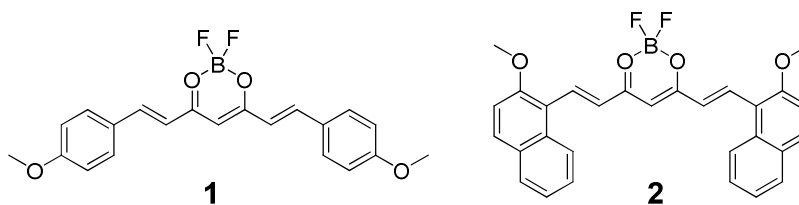


Chart 1. Chemical structure of the borondifluoride curcuminoids **1** and **2**.

We report herein the first characterization of TPEF properties of BF₂ complexes of curminoids, in solution and in the solid state, using two dyes, **1** and **2** (Chart 1). We describe the synthesis of **2**, containing the 2-methoxynaphthyl group as electron donor end-unit. In our previous publication,⁴¹ compound **1** has been reported to form nanoparticles showing OPEF in the NIR region. We describe herein the X-ray structure analysis of **1**, and the preparation and characterization of organic nanoparticles obtained with **1** and **2**. These nanomaterials are shown to be efficient NIR-to-NIR fluorophores.

Results and discussion

Solid-state characterizations. Single crystals of **1** were obtained by slow evaporation of ethylacetate.⁶³ A single crystal was mounted on a glass fibre, and diffraction data were acquired using a Mo K α radiation source ($\lambda = 0.71073 \text{ \AA}$). Detailed crystallographic parameters are included in Table S1. Dye **1** (P-1, Z = 2) crystallizes in the triclinic system with two independent molecules in the asymmetric unit. The two molecules differ by the torsion angle between anisole planes and dioxaborine plane, one conformer being almost planar and the other highly distorted (torsion angles *ca.* 16° and 28°). As observed for other types of BF₂ complexes,⁶⁴ the dye molecules are tightly packed in the solid state. They form staggered stacks parallel to the *c*-axis to minimize dipolar interactions and favour anisole donor-dioxaborine acceptor interactions. Within the stacks, one observes the formation of dimers involving the two planar conformers that are at the Van der Waals distance (Figure 1a). Two distorted conformers interact with

one dimer forming a kind of tetrameric structure in which the four dyes experience π - π overlap. The interactions between adjacent tetramers are weak because they involve the distorted species (Figure 1b). Moreover, we checked that the experimental powder diffraction pattern of a microcrystalline sample of **1** obtained by rapid precipitation matches the one calculated from the single crystal structure (Figure S5).

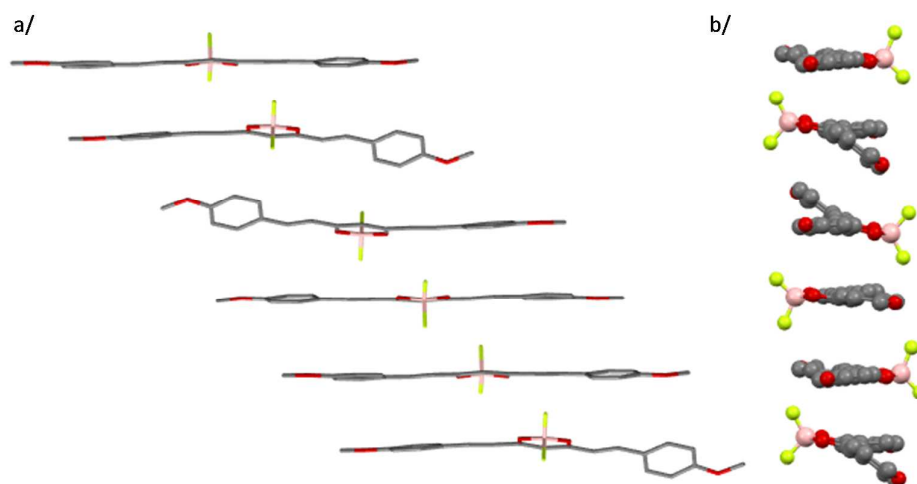


Figure 1. Crystal packing diagram of **1** down the c-axis direction (a), illustrating π - π stacking interactions, and the long molecular axis (b).

Nanoparticles were prepared by quickly adding a concentrated THF solution of the dyes into water according to the classical reprecipitation method.⁶⁵ In order to optimize the particle size, we prepared THF solutions at six different concentrations for each dye (from *ca.* 1.85×10^{-6} to 6.5×10^{-6} M for **1** and 1.3×10^{-6} to 4.4×10^{-6} M for **2**). In all samples, the final THF-to-water volume ratio was kept below 1% (v/v) and the suspensions were stored at room temperature. From dynamic light scattering (DLS) measurements (Figure 2), we noticed that increasing the concentration of the mother solution (*i.e.* the final dye concentration) strongly influences the particle size distribution for dye **1**, with hydrodynamic diameter values increasing from 170 to 285 nm. On the opposite, under the same conditions, dye **2** forms smaller nanoparticles

(from 64 to 79 nm) whose size is rather insensitive to concentration (Figure 2). Using electronic absorption spectroscopy and DLS, we could check that the nanoparticle suspensions were stable for at least for three weeks at room temperature.

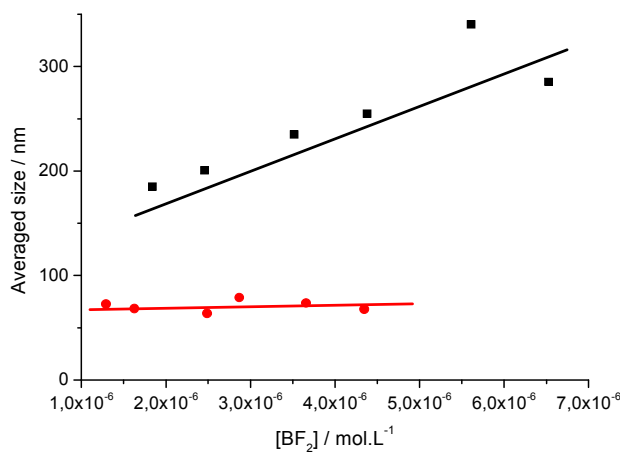


Figure 2. Variation of the averaged size determined by DLS for dye **1** (black) and dye **2** (red) as a function of the total dye concentration.

Transmission electron microscopy (TEM) and atomic force microscopy (AFM) were performed using one sample concentration (4.4×10^{-6} M). Complementary information was obtained from TEM observations for samples prepared by depositing $1 \mu\text{L}$ of a hundred times diluted solution of 4.4×10^{-6} M of the nanoparticle suspension in water onto a carbon grid and drying was performed at room temperature. For AFM scanning, the sample drop was deposited onto a glass plate and quickly dried in an oven at 120°C . Under these conditions, both techniques show the occurrence of isolated nanoparticles and agglomerates. Particles with sizes of *ca.* 200 nm and 50 nm are observed for **1** (Figure 3 a and c and Figure S7a) and **2** (Figure 3 b and d and Figure S7b), respectively. These values are smaller than those given by DLS at this concentration, 235 nm and 67 nm for **1** and **2**, respectively, which stems from the fact

that DLS leads to a hydrodynamic diameter of aggregates solvated by a shell of water molecules. We conclude therefore that all techniques give consistent results revealing that dye **2** particles are much smaller (*ca.* 50-60 nm) than those of **1**.

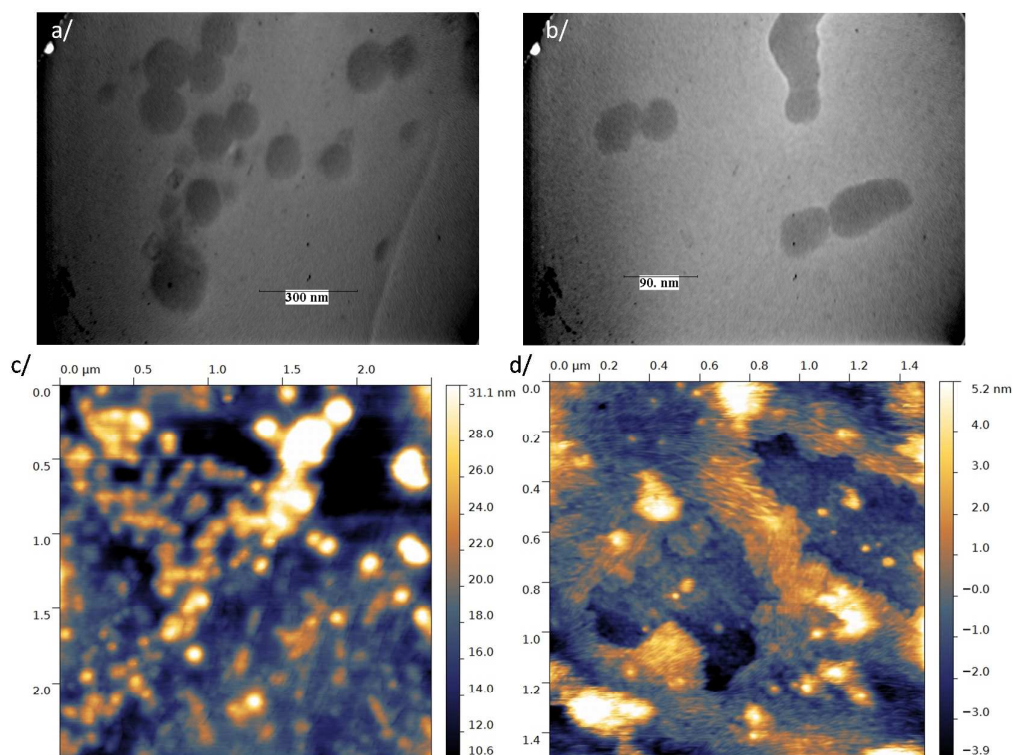


Figure 3. TEM images of the particles of a/ dye **1** and b/ dye **2** and tapping mode topographical AFM images of c/ dye **1** and d/ dye **2**.

One-photon spectroscopic properties. The electronic absorption and fluorescence emission of **1** in dichloromethane (DCM) were published elsewhere.⁴¹ Figure 4 presents the spectra of **2** and the spectroscopic data are collected in Table 2. Dye **2** exhibits OPA and OPEF features in line with those obtained for related dyes.⁴¹ Especially, those spectra show positive solvatochromism and lose their vibronic structure in polar solvents. Using Lippert-Mataga formalism, linear plots with positive slope values (Figure S8) that are close for **1** and **2** were obtained.⁶⁶⁻⁶⁸ These data show that the two dyes present similar charge transfer characteristics in the ground- and excited-state and

behave as dipolar rather than quadrupolar systems.⁶⁹ From the fluorescence lifetime values measured in DCM, the fluorescence radiative kinetic constants rate k_f were calculated and found superior to 10^8 s^{-1} for dyes **1** and **2** showing that the one-photon low-energy transition is highly allowed.⁴¹

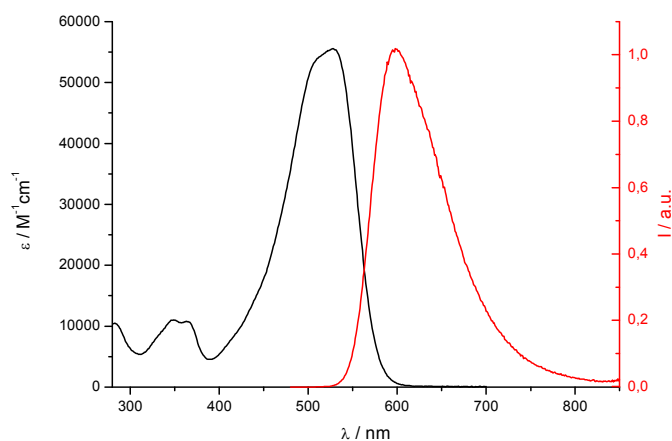


Figure 4. Electronic absorption (conc. $\approx 10^{-5} \text{ M}$, black) and corrected fluorescence emission (conc. $\approx 10^{-6} \text{ M}$, λ_{exc} at the absorption maximum, red) spectra of **2** in DCM.

A preliminary investigation showed fluorescence emission of a colloidal suspension of dye **1**.⁴¹ The solid-state optical properties of dyes **1** and **2** are investigated herein in more detail (Figure 5, Table 2). Upon adding incremental volumes of water into a THF solution of the dyes, a gradual red-shift of the absorption and emission spectra can be seen (Figures S9 and S10). The change in Stokes shift linearly parallels that of the solvent polarity parameter (Δf) in the Lippert-Mataga plots until the polarity of the solvent mixture reaches a threshold (Figure S11). Above this critical value, nanoparticles form, inducing an abrupt change in the Lippert-Mataga slope and a modification of the absorption profile.

Table 2. Spectroscopic data, photophysical and TPEF properties of compounds **1** and **2** in DCM and nanoparticles in water at room temperature.^a

compound	Absorption		Fluorescence							TPEF		
	λ_{abs}	ϵ_{max}	λ_{em}	$\Delta\nu_{ST}$	Φ_f	B_{max}	τ_f	k_f	k_{nr}	λ^2_{abs}	σ^2	B^2_{max}
1 (DCM)	488	75480	538	1904	0.44	33211	1.30	3.4	4.3	770	155	68
2 (DCM)	528	55580	598	2217	0.20	11116	1.59	1.2	5.8	890	195	39
1 (water)	451	34170	710 (718) ^b	8088	0.06 (0.05) ^b	2734	6.44	0.09	1.5	780	210	13
2 (water)	520	24780	717 (718) ^b	5284	0.045 (0.125) ^b	1115	1.4 2.8 ^c	-	-	900	305	14

^a Absorption maximum wavelengths λ_{abs} (nm), molar absorption coefficients ϵ_{max} ($M^{-1} cm^{-1}$), fluorescence maximum wavelengths λ_{em} (nm), Stokes shifts $\Delta\nu_{ST}$ (cm^{-1}), fluorescence quantum yields Φ_f , optical brightness $B_{max} = \Phi_f \times \epsilon$ ($M^{-1} cm^{-1}$), fluorescence lifetimes τ_f (ns), radiative k_f ($10^8 s^{-1}$) and nonradiative $k_{nr} = (1 - \Phi_f)/\tau_f$ ($10^8 s^{-1}$) rate constants, TPA maximum wavelengths λ^2_{abs} (nm), TPA cross section at maximum σ^2 (GM) and two-photon brightness $B^2_{max} = \Phi_f \times \sigma^2$ (GM); ^b on powder sample; ^c biexponential decay was found.

The electronic absorption spectrum of nanoparticles of **1** is blue shifted relative to solution and its shape is characteristic of excitonically-coupled chromophores in an H-type arrangement, in agreement with the X-ray structure analysis. In the case of **2**, compared to **1**, the OPA solid-state spectrum is less affected than that of the solution, a red-shifted shoulder being observed. The solid-state OPEF emission spectra display a structureless symmetrical band that is sharper for the microcrystalline powder than for nanoparticles, especially in the case of **2**. The maximum emission wavelengths are red-shifted compared to the one on DCM solution and found in the NIR, above 710 nm. The shape of the spectra is typical of strongly interacting dipolar dyes and is due to strong π -overlap in the crystal leading to broad emission with strong charge transfer character.¹⁷ Such behaviour was especially noticed for BF₂ complexes of 2'-hydroxychalcone derivatives.⁶⁴ The fluorescence quantum yields are around 5 % for nanoparticle suspensions, which represents a quite high value for aggregated organic dyes emitting in the NIR. We emphasize that the value of 12.5 % obtained for a microcrystalline powder sample of **2** emitting at 718 nm is not common.

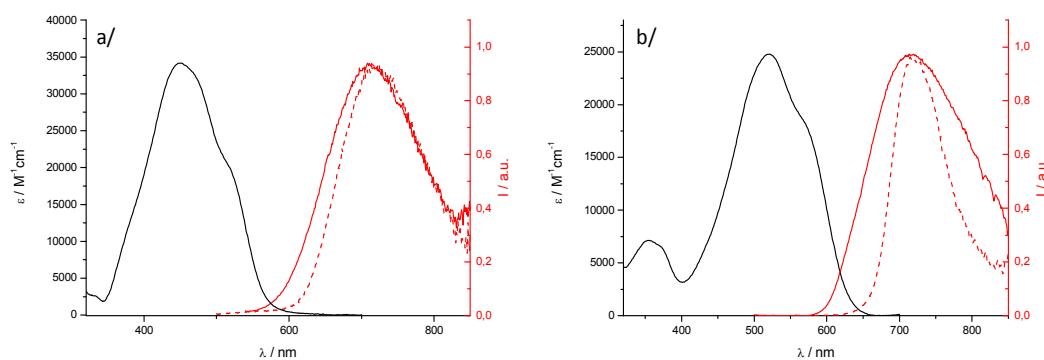


Figure 5. Electronic absorption of nanoparticles (—) and fluorescence emission spectra (—) of nanoparticles in water and powder samples (---) for a/ **1** and b/ **2**.

The fluorescence lifetimes of the nanoparticles were measured in water. The fluorescence decay of **2** is fitted by a bi-exponential curve (Figure S12). The associated lifetimes are short, with one component being close to the solution-state value, which considering also the shape of the absorption spectrum, may indicate the presence of non-perturbed chromophores in the aggregates. Such spectroscopic heterogeneity is frequent in small size aggregates where chromophores can exist in different environments.¹⁸ Consistently, the fluorescence decay of nanoparticles of **1**, whose size is four times larger than that of **2**, follows a mono-exponential behaviour. The long lifetime value of 6.44 ns leads to a drop of k_f by at least one order of magnitude relative to the DCM solution, which is in keeping with the less allowed low-energy transition in a H-type solid-state arrangement.

TPEF properties. Two-photon emission and excitation spectra were recorded in the 700-1000 nm wavelength range using a femtosecond Ti-Sapphire pulsed laser source, according to the experimental protocol described by Webb.⁷⁰ The observation of a quadratic dependence of the fluorescence intensity *versus* incident laser power at several wavelengths unambiguously confirmed that the origin of the fluorescence emission can be assigned to a TPA process in both DCM solution and water suspension (Figure S13). In the experimental laser power range used for these measurements, we checked that no saturation or photodegradation occurred. Figure 6 shows the two-photon excitation spectra of **1** and **2** in DCM, calibrated using coumarin-307 and rhodamine B as a reference.⁷⁰ Dye **1** has a TPA cross section σ^2 of 155 GM at 770 nm (Table 2) while dye **2** has its maximum red-shifted to 890 nm and a similar value of σ^2 . Therefore the nature of the electron-donor end-group has a strong influence on the TPA maximum wavelength in solution. It is noteworthy that the OPA maxima of **1** and **2** differ by only 40 nm.

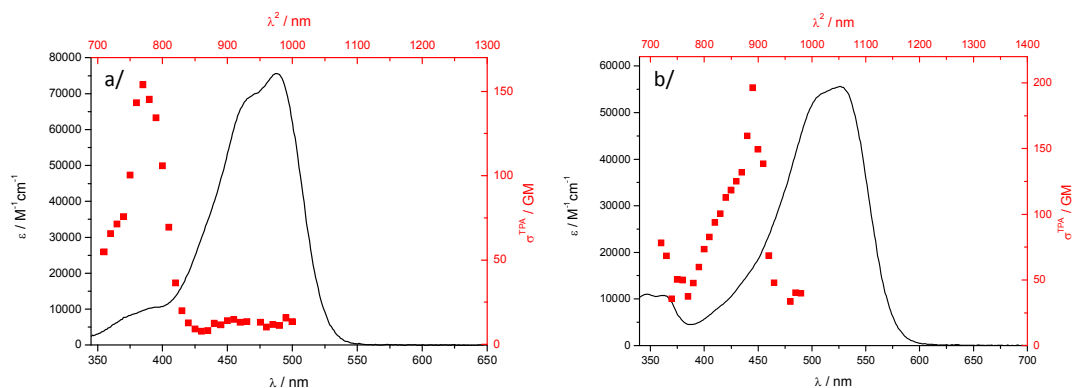


Figure 6. Two-photon excitation (■, higher x-coordinate and —, right y-coordinate), OPA spectra (—, lower x-coordinate and —, left y-coordinate) in DCM: a/ **1** and b/ **2**.

The nonlinear absorption band is found strongly blue-shifted for both dyes and clearly does not match the S_0 - S_1 OPA transition, which is often observed for D-A-D chromophores.^{39, 69, 71, 72} It has been assigned to a TPA-allowed transition lying at higher energy,⁷¹ or to localization of the excitation in one of the two halves of the chromophore as a result of vibration- or polar solvation-induced symmetry breaking in the ground- or excited-state as observed for cyanine derivatives for example.^{39, 69, 72} The lowest-energy transition in **1** energy is not completely TPA forbidden, a σ^2 of *ca.* 10-15 GM being determined (Figure 6a). The same observation probably holds for **2** but the TPA spectrum in this wavelength range is not experimentally accessible with our experimental setup.

The two-photon excitation spectra of nanoparticle suspensions of **1** and **2** are given in Figure 7. Nanoparticles do exhibit a strong nonlinear response in water and the TPA cross sections are 40 to 50 % larger than those in DCM. Such enhancement of σ^2 in aggregated chromophores has already been observed for other chromophores.¹⁹⁻²⁵ As noticed for TPA in DCM, the two-photon excitation band does not match the lowest-energy OPA transition and is located at higher energy. Actually, this result is fortunate

yielding two-photon excitation that remains below 1000 nm (*i.e.* the upper transparency limit of the biological window). The TPA maxima are almost at the same position than in DCM, a bathochromic shift of 10 nm being noticed. The TPA brightnesses of 13 GM ($\lambda^2_{\text{abs}} = 780 \text{ nm}$) and 14 GM ($\lambda^2_{\text{abs}} = 900 \text{ nm}$) for **1** and **2**, respectively are smaller than those in DCM solution. This stems from the lower Φ_f for the aggregated dyes (Table 2). However, the B^2_{max} of **1** and **2** remain larger than those determined for the only cases of NIR-to-NIR probes reported to date. For ytterbium complexes, it is the low luminescence quantum yield of the lanthanide species that limits the TPEF response. Water-soluble heptamethine cyanines instead display high Φ_f (up to 30%) but limited TPA cross sections.⁷³ In all these literature cases, B^2_{max} did not exceed 10 GM, which anyway allowed using them as NIR-to-NIR labels for bioimaging purposes.

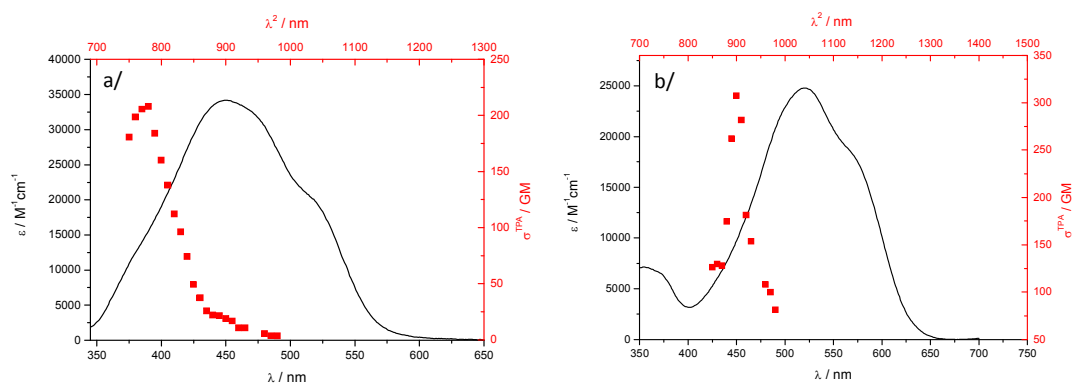


Figure 7. Two-photon excitation spectra (■, higher x-coordinate and —, right y-coordinate) and OPA absorption spectra (—, lower x-coordinate and —, left y-coordinate) of particles in water: a/ **1** and b/ **2**.

Conclusions

We have presented the first investigation of the TPEF properties of two borondifluoride complexes of curcuminoids. The data show that these compounds

possess effective TPA cross sections, making them interesting candidates as TPEF reporters. The two dyes under investigation form nanoparticles in water that combine NIR TPEF and NIR TPA with practical values of the TPA brightness (14 GM), which are, to the best of our knowledge, among the highest values for dyes with emission maxima above 700 nm. These molecules represent a new class of NIR-to-NIR fluorophores. This study also shows that the choice of the aromatic endgroup is crucial to the control of a number of parameters: hydrophylic/lipophylic balance, particle size, exciton coupling within the aggregate, solid-state packing, absorption and emission maximum wavelengths, solution- and solid-state values of B^2_{max} , to mention the main ones. We are currently working at the optimization of those parameters by changing the chemical structure of the curcuminoid end-groups and introducing substituents at the *meso* position of the dioxaborine ring.⁴¹

Experimental section :

Two-Photon Excited Fluorescence Measurements: The TPA cross-section spectra were obtained by up-conversion fluorescence using a tunable mode-locked Ti:sapphire femtosecond laser oscillator (Mai-Tai HP Spectra Physics) at repetition rate of 80 MHz in the range 690-1060 nm. The excitation beam is focalized with a microscope objective (20X/0.40, LD Epiplan Zeiss) at the middle of the fluorescence cell (10 mm). The average power of the fundamental laser beam was controller by a glan polarizer combined with a $\lambda/2$ wave plate. The fluorescence, collected at 90° to the excitation beam, was focused using a short focus, large diameter quartz lens into a gated intensified CCD device (Pi-Max2, Princeton Instruments) coupled to a double grating monochromator (Acton SP500i, Princeton Instruments). The luminescence light was transmitted through an

appropriate optical filter to eliminate the scattered excitation light. Photoluminescence spectra were recorded for one broad band excitation wavelength in the range 710 - 1000 nm, keeping the excitation laser power constant. The incident beam intensity was adjusted to 50 mW in DCM solution and 75 mW for particles in water in order to ensure an intensity-squared dependence of the fluorescence over the whole spectral range. The detector integration time was fixed to 1 second. Calibration of the spectra was performed by comparison with the published 700-1000 nm Coumarin-307 and RhodamineB two-photon absorption spectra.⁷⁰ The measurements were done three times independently at room temperature in dichloromethane and in water at optical density varying from 0.1 to 0.3. The detector was corrected according to the procedure described by Parker.⁷⁴ The observed photomultiplier output A_1 was recorded at wavelength λ , which corresponds to the apparent emission spectrum. A_1 is given by [Eq. (1)], where F_1 and S_1 are the corrected emission spectrum and the spectroscopic sensitivity factor of the monochromator-photomultiplier setup, respectively.

$$A_1 = (F_1)(S_1)/\lambda^2 \quad (1)$$

To calculate S_1 , we used 4-N,N-dimethylamino-4'-nitrostilbene (DMANS) as a standard NIR fluorophore for which its corrected emission spectrum has been precisely determined.⁷⁵

Acknowledgments

The authors want to thank Dr Wladimir Marine for his help in setting up the two-photon excitation set-up and Dr Serge Nitsche for his help in the TEM measurements.

References

1. C. Andraud and O. Maury, *Eur. J. Inorg. Chem.*, 2009, **2009**, 4343-4343.
2. X. Wang, A. R. Morales, T. Urakami, L. Zhang, M. V. Bondar, M. Komatsu and K. D. Belfield, *Bioconjugate Chem.*, 2011, **22**, 1438-1450.
3. S. Yao and K. D. Belfield, *Eur. J. Inorg. Chem.*, 2012, **2012**, 3199-3217.
4. E. De Meulenaere, W.-Q. Chen, S. Van Cleuvenbergen, M.-L. Zheng, S. Psilodimitrakopoulos, R. Paesen, J.-M. Taymans, M. Ameloot, J. Vanderleyden, P. Loza-Alvarez, X.-M. Duan and K. Clays, *Chem. Sci.*, 2012, **3**, 984-995.
5. A. D'Aléo, F. Pointillart, L. Ouahab, C. Andraud and O. Maury, *Coord. Chem. Rev.*, 2012, **256**, 1604-1620.
6. X. J. Feng, P. L. Wu, F. Bolze, H. W. C. Leung, K. F. Li, N. K. Mak, D. W. J. Kwong, J.-F. Nicoud, K. W. Cheah and M. S. Wong, *Org. Lett.*, 2010, **12**, 2194-2197.
7. H. Ftouni, F. Bolze, H. de Rocquigny and J.-F. Nicoud, *Bioconjugate Chem.*, 2013, **24**, 942-950.
8. G. S. He, L.-S. Tan, Q. Zheng and P. N. Prasad, *Chem. Rev.*, 2008, **108**, 1245-1330.
9. F. Terenziani, C. Katan, E. Badaeva, S. Tretiak and M. Blanchard-Desce, *Adv. Mater.*, 2008, **20**, 4641-4678.
10. J. M. Hales, J. Matichak, S. Barlow, S. Ohira, K. Yesudas, J.-L. Brédas, J. W. Perry and S. R. Marder, *Science*, 2010.
11. O. V. Przhonska, S. Webster, L. A. Padilha, H. Hu, A. D. Kachkovski, D. J. Hagan and E. W. Van Stryland, in *Advanced Fluorescence Reporters in Chemistry and Biology I*, Springer series on Fluorecence, 2010, vol. 8, pp. 105-147.
12. Z. Li, Y. Liu, H. Kim, J. M. Hales, S.-H. Jang, J. Luo, T. Baehr-Jones, M. Hochberg, S. R. Marder, J. W. Perry and A. K. Y. Jen, *Adv. Mater.*, 2012, **24**, OP326-OP330.
13. K. Matsui, Y. Segawa, T. Namikawa, K. Kamada and K. Itami, *Chem. Sci.*, 2013, **4**, 84-88.


14. K. Kamada, S.-I. Fuku-en, S. Minamide, K. Ohta, R. Kishi, M. Nakano, H. Matsuzaki, H. Okamoto, H. Higashikawa, K. Inoue, S. Kojima and Y. Yamamoto, *J. Am. Chem. Soc.*, 2013, **135**, 232-241.
15. A. Kaeser and A. P. H. J. Schenning, *Adv. Mater.*, 2010, **22**, 2985–2997.
16. S. Fery-Forgues, *Nanoscale*, 2013, **5**, 8428-8442.
17. J. Gierschner and S. Y. Park, *J. Mater. Chem. C*, 2013, **1**, 5818-5832.
18. J. Gierschner, L. Lüer, B. Milián-Medina, D. Oelkrug and H.-J. Egelhaaf, *J. Phys. Chem. Lett.*, 2013, **4**, 2686-2697.
19. E. Collini, *Phys. Chem. Chem. Phys.*, 2012, **14**, 3725–3736.
20. S. Kim, Q. Zheng, G. S. He, D. J. Bharali, H. E. Pudavar, A. Baev and P. N. Prasad, *Adv. Funct. Mater.*, 2006, **16**, 2317-2323.
21. Z. Xu, Q. Liao, Y. Wu, W. Ren, W. Li, L. Liu, S. Wang, Z. Gu, H. Zhang and H. Fu, *J. Mater. Chem.*, 2012, **22**, 17737–17743.
22. G. D'Avino, F. Terenziani and A. Painelli, *J. Chem. Phys B* 2006, **110**, 25590-25592.
23. H. Hu, D. A. Fishman, A. O. Gerasov, O. V. Przhonska, S. Webster, L. A. Padilha, D. Peceli, M. Shandura, Y. P. Kovtun, A. D. Kachkovski, I. H. Nayyar, A. m. E. Masunov, P. Tongwa, T. V. Timofeeva, D. J. Hagan and E. W. Van Stryland, *J. Phys. Chem. Lett.*, 2012, **3**, 1222-1228.
24. Y. Zhang, B. Kim, S. Yao, M. V. Bondar and K. D. Belfield, *Langmuir*, 2013, **29**, 11005–11012.
25. T. Ishi-i, S. Amemori, C. Okamura, K. Yanaga, R. Kuwahara, S. Mataka and K. Kamada, *Tetrahedron*, 2013, **69**, 29-37.
26. J. Geng, K. Li, D. Ding, X. Zhang, W. Qin, J. Liu, B. Z. Tang and B. Liu, *Small*, 2012, **8**, 3655-3663.

27. V. Parthasarathy, S. Fery-Forgues, E. Campioli, G. Recher, F. Terenziani and M. Blanchard-Desce, *Small*, 2011, **7**, 3219-3229.
28. E. Ishow, A. Brosseau, G. Clavier, K. Nakatani, P. Tauc, C. Fiorini-Debuisschert, S. Neveu, O. Sandre and A. Léaustic, *Chem. Mater.*, 2008, **20**, 6597-6599.
29. Y. Jiang, Y. Wang, J. Hua, J. Tang, B. Li, S. Qian and H. Tian, *Chem. Commun.*, 2010, **46**, 4689-4691.
30. S. B. Noh, R. H. Kim, W. J. Kim, S. Kim, K.-S. Lee, N. S. Cho, H.-K. Shim, H. E. Pudavar and P. N. Prasad, *J. Mater. Chem.*, 2010, **20**, 7422-7429.
31. J. Massin, A. Charaf-Eddin, F. Appaix, Y. Bretonnière, D. Jacquemin, B. van der Sanden, C. Monnereau and C. Andraud, *Chem. Sci.*, 2013, **4**, 2833-2843.
32. S. A. Hilderbrand and R. Weissleder, *Curr. Opin. Chem. Biol.*, 2010, **14**, 71-79.
33. A. Yuan, J. Wu, X. Tang, L. Zhao, F. Xu and Y. Hu, *J. Pharma. Sci.*, 2013, **102**, 6-28.
34. R. G. Aswathy, Y. Yoshida, T. Maekawa and D. S. Kumar, *Anal. Bioanal. Chem.* , 2010, **397**, 1417-1435.
35. J. Gao, X. Chen and Z. Cheng, *Curr. Top. Med. Chem.*, 2010, **10**, 1147-1157.
36. Q. Ma and X. Su, *Analyst*, 2010, **135**, 1867-1877.
37. A. D'Aléo, A. Bourdolle, S. Brustlein, T. Fauquier, A. Grichine, A. Duperray, P. L. Baldeck, C. Andraud, S. Brasselet and O. Maury, *Angew. Chem. Int. Ed.*, 2012, **51**, 6622-6625.
38. T. Zhang, X. Zhu, C. C. W. Cheng, W.-M. Kwok, H.-L. Tam, J. Hao, D. W. J. Kwong, W.-K. Wong and K.-L. Wong, *J. Am. Chem. Soc.*, 2011, **133**, 20120-20122.
39. H. Hu, O. V. Przhonska, F. Terenziani, A. Painelli, D. Fishman, T. R. Ensley, M. Reichert, S. Webster, J. L. Bricks, A. D. Kachkovski, D. J. Hagan and E. W. Van Stryland, *Phys. Chem. Chem. Phys.*, 2013, **15**, 7666-7678.

40. L. A. Padilha, S. Webster, O. V. Przhonska, H. Hu, D. Peceli, T. R. Ensley, M. V. Bondar, A. O. Gerasov, Y. P. Kovtun, M. P. Shandura, A. D. Kachkovski, D. J. Hagan and E. W. V. Stryland, *J. Phys. Chem. A*, 2010, **114**, 6493-6501.
41. A. Felouat, A. D'Aléo and F. Fages, *J. Org. Chem.*, 2013, **78**, 4446-4455.
42. M. Garcia-Alloza, L. A. Borrelli, A. Rozkalne, B. T. Hyman and B. J. Bacskai, *J. Neurochem.*, 2007, **102**, 1095-1104.
43. D. Yanagisawa, T. Amatsubo, S. Morikawa, H. Taguchi, M. Urushitani, N. Shirai, K. Hirao, A. Shiino, T. Inubushi and I. Tooyama, *Neuroscience*, 2011, **184**, 120-127.
44. J. Chittigori, A. Kumar, L. Li, S. Thota, A. Kokil, L. A. Samuelson, D. J. Sandman and J. Kumar, *Tetrahedron*, 2014, **70**, 991-995.
45. A. Kunwar, A. Barik, B. Mishra, K. Rathinasamy, R. Pandey and K. I. Priyadarsini, *BBA-Gen. Subjects*, 2008, **1780**, 673-679.
46. A. Kumar, L. Li, A. Chaturvedi, J. Brzostowski, J. Chittigori, S. Pierce, L. A. Samuelson, D. Sandman and J. Kumar, *Appl. Phys. Lett.*, 2012, **100**, 203701-203704.
47. H. Maeda, Y. Bando, K. Shimomura, I. Yamada, M. Naito, K. Nobusawa, H. Tsumatori and T. Kawai, *J. Am. Chem. Soc.*, 2011, **133**, 9266-9269.
48. K. Ono, A. Nakashima, Y. Tsuji, T. Kinoshita, M. Tomura, J.-i. Nishida and Y. Yamashita, *Chem. Eur. J.*, 2010, **16**, 13539-13546.
49. G. Zhang, J. Lu, M. Sabat and C. L. Fraser, *J. Am. Chem. Soc.*, 2010, **132**, 2160-2162.
50. G. Zhang, J. Chen, S. J. Payne, S. E. Kooi, J. N. Demas and C. L. Fraser, *J. Am. Chem. Soc.*, 2007, **129**, 8942-8943.
51. J. M. Hales, S. Zheng, S. Barlow, S. R. Marder and J. W. Perry, *J. Am. Chem. Soc.*, 2006, **128**, 11362-11363.

52. C. Risko, E. Zojer, P. Brocorens, S. R. Marder and J. L. Brédas, *Chem. Phys.*, 2005, **313**, 151-157.
53. B. Domercq, C. Grasso, J.-L. Maldonado, M. Halik, S. Barlow, S. R. Marder and B. Kippelen, *J. Phys. Chem. B*, 2004, **108**, 8647-8651.
54. J. Fabian and H. Hartmann, *J. Phys. Org. Chem.*, 2004, **17**, 359-369.
55. Y. L. Chow, C. I. Johansson, Y.-H. Zhang, R. Gautron, L. Yang, A. Rassat and S.-Z. Yang, *J. Phys. Org. Chem.*, 1996, **9**, 7-16.
56. M. Halik, W. Wenseleers, C. Grasso, F. Stellacci, E. Zojer, S. Barlow, J.-L. Bredas, J. W. Perry and S. R. Marder, *Chem. Commun.*, 2003, 1490-1491.
57. E. Cogné-Laage, J.-F. Allemand, O. Ruel, J.-B. Baudin, V. Croquette, M. Blanchard-Desce and L. Jullien, *Chem. Eur. J.*, 2004, **10**, 1445-1455.
58. A. Pfister, G. Zhang, J. Zareno, A. F. Horwitz and C. L. Fraser, *ACS Nano*, 2008, **2**, 1252-1258.
59. K. Liu, J. Chen, J. Chojnacki and S. Zhang, *Tetrahedron Lett.*, 2013, **54**, 2070-2073.
60. C. Ran, X. Xu, S. B. Raymond, B. J. Ferrara, K. Neal, B. J. Bacskai, Z. Medarova and A. Moore, *J. Am. Chem. Soc.*, 2009, **131**, 15257-15261.
61. X. Zhang, Y. Tian, Z. Li, X. Tian, H. Sun, H. Liu, A. Moore and C. Ran, *J. Am. Chem. Soc.*, 2013, **135**, 16397-16409.
62. G. Bai, C. Yu, C. Cheng, E. Hao, Y. Wei, X. Mu and L. Jiao, *Org. Biomol. Chem.*, 2014, **12**, 1618.
63. Crystal structure data of **1** have been deposited with the Cambridge Crystallographic Data Centre under CCDC 987442. These data can be obtained free of charge from the Cambridge Crystallographic Data Centre via www.ccdc.cam.ac.uk/data_request/cif.

64. A. D'Aléo, D. Gachet, V. Heresanu, M. Giorgi and F. Fages, *Chem. Eur. J.*, 2012, **18**, 12764-12772.
65. H. Kawai, H. S. Nalwa, H. Oikawa, S. Okada, H. Matsuda, N. Minami, A. Kakuda, K. Ono, A. Mukoh and H. Nakanishi, *Jpn. J. Appl. Phys.*, 1992, **31**, L1132-L1134.
66. E. Lippert, *Naturforsch.*, 1955, **10a**, 541-545.
67. E. Z. Mataga, Y. Kaifu and M. Koizumi, *Bull. Chem. Soc. Jpn.*, 1956, **29**, 465-470.
68. E. Lippert, 61, 962, *Z. Elektrochem.*, 1957, **61**, 962-975.
69. F. Terenziani, A. Painelli, C. Katan, M. Charlot and M. Blanchard-Desce, *J. Am. Chem. Soc.*, 2006, **128**, 15742-15755.
70. C. Xu and W. W. Webb, *J. Opt. Soc. Am. B*, 1996, **13**, 481-491.
71. W. M. McClain, *Acc. Chem. Res.*, 1974, **7**, 129-135.
72. Q. Bellier, N. S. Makarov, P.-A. Bouit, S. Rigaut, K. Kamada, P. Feneyrou, G. Berginc, O. Maury, J. W. Perry and C. Andraud, *Phys. Chem. Chem. Phys.*, 2012, **14**, 15299-15307.
73. L. Wang, J. Jin, X. Chen, H.-H. Fan, B. K. F. Li, K.-W. Cheah, N. Ding, S. Ju, W.-T. Wong and C. Li, *Org. Biomol. Chem.*, 2012, **10**, 5366-5370.
74. C. A. Parker, *Photoluminescence of Solutions*, Elsevier Publishing, Amsterdam, 1969.
75. J. R. Lakowicz, *Principles of Fluorescence Spectroscopy*, Kluwer, New-York (NY), 2006

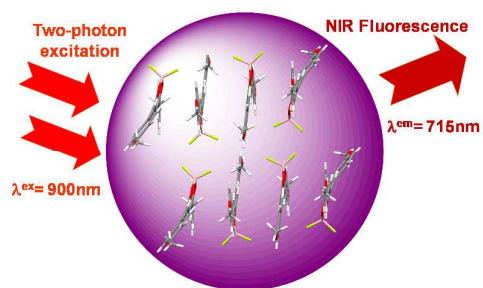

Two-photon excitation of curcuminoids borondifluoride nanoparticles in water results in rather efficient luminescence in the near infrared due to high two-photon cross section.