

# ChemComm

Accepted Manuscript



This is an *Accepted Manuscript*, which has been through the Royal Society of Chemistry peer review process and has been accepted for publication.

*Accepted Manuscripts* are published online shortly after acceptance, before technical editing, formatting and proof reading. Using this free service, authors can make their results available to the community, in citable form, before we publish the edited article. We will replace this *Accepted Manuscript* with the edited and formatted *Advance Article* as soon as it is available.

You can find more information about *Accepted Manuscripts* in the [Information for Authors](#).

Please note that technical editing may introduce minor changes to the text and/or graphics, which may alter content. The journal's standard [Terms & Conditions](#) and the [Ethical guidelines](#) still apply. In no event shall the Royal Society of Chemistry be held responsible for any errors or omissions in this *Accepted Manuscript* or any consequences arising from the use of any information it contains.

## COMMUNICATION

# Rationally Designed Amino-Borane Complex in Metal Organic Framework: A Novel Reusable Hydrogen Storage and Size-Selective Reduction Material

Cite this: DOI: 10.1039/x0xx00000x

Received 00th January 2012,  
Accepted 00th January 2012


DOI: 10.1039/x0xx00000x

www.rsc.org/

Xinbo Wang, Linhua Xie, Kuo-wei Huang and Zhiping Lai\*

**A novel amino-borane complex inside a stable metal organic framework was synthesized for the first time. It releases hydrogen at temperature 78°C with no volatile contaminants and can be well reused. Its application as a size-selective reduction material in organic synthesis was also demonstrated.**

Over the past several decades, hydrogen has emerged as an ideal successor to gasoline because of its lightweight and clean combustion properties<sup>1</sup>. The current hydrogen storage approaches such as high pressure and cryogenics, however, have suffered from disadvantages including a large bulky size as well as high safety risks. One of the milestones for hydrogen storage was the development of light-weight solids that could reversibly release H<sub>2</sub>. Especially ammonia-borane (AB) (NH<sub>3</sub>BH<sub>3</sub>), which releases hydrogen upon heating according to reaction (1), is considered to be a promising hydrogen storage material due to its stability and high gravimetric content of hydrogen (19.6 wt%)<sup>2</sup>. However, several issues still need to be addressed before it can be used, involving decreasing the dehydrogenation temperature below 85 °C, and preventing the formation of volatile by-products, such as borazine (N<sub>1</sub>B<sub>x</sub>H<sub>x</sub>), ammonia, and diborane, etc. The current methods to overcome these issues can be summarized into three general approaches. One is to chemically modify AB in the form of RNHBH<sub>3</sub><sup>3-6</sup>, where R can be an alkyl group, heterocycles, ionic liquid, or a metal cation. A second approach is catalytic dehydrogenation of AB with different mechanistic pathways<sup>7-11</sup>, including activation by base, acid, ionic liquids, transition metal complexes, or metal nanoparticles. A third approach is to physically load AB into microporous materials such as mesoporous silicas<sup>12</sup> and metal organic frameworks (MOFs)<sup>13-21</sup>. The nano-confinement as well as the unique interactions between AB and the framework were found beneficial to reduce the dehydrogenation temperature and the formation of by-products.



Since AB can be formed by the reaction between borane and ammonia, so if a microporous material functionalized with amino groups, then borane should be able to react with the

amino group to form the amino-borane complex inside the framework. Based on this idea, here we report for the first time the storage of borane in a stable amino-substituted MOF, UiO-66-NH<sub>2</sub>, and its reversible release of hydrogen. Our approach can be explained as follows. Borane first adsorbs in UiO-66-NH<sub>2</sub> by reacting with the amino group to form amino-borane complexes inside the UiO-66 structure, which is named as UiOAB. Hydrogen is then released from UiOAB by thermolysis. The dehydrogenation product is removed by methanol and UiO-66-NH<sub>2</sub> is regenerated. The strong covalent bonding between borane and amino groups as well as the nano confinement will improve the borane loading rate, reduce the dehydrogenation temperature and the formation of volatile species during the process of dehydrogenation. Furthermore, the isolated and uniformly distributed amino binding sites will enhance the hydrogen release kinetics and prevent polymerization of dehydrogenation products, so they can be easily reacted and then dissolved in methanol and been removed. As a result, the dehydrogenation temperature was found to be as low as 78°C and no volatile by-product was generated during this process.

The recent developed MOFs are very attractive for adsorption not only because of their high surface area, high porosity, tunable pore size, but also because of their easy functionality that allows to introduce functional groups to their frameworks by design<sup>23-24</sup>. In fact, functional groups have been widely used to enhance the adsorption loading rate, and to fine tune the adsorption/desorption kinetics. A number of amino substituted MOFs have been reported in literature<sup>25-27</sup>, such as IRMOF-3, DMOF-1-NH<sub>2</sub>, UMCM-1-NH<sub>2</sub> and UiO-66-NH<sub>2</sub>, etc. Therefore, our approach in principle can serve as a general method to utilize MOFs as a platform to store borane. However, UiO-66-NH<sub>2</sub> is of particular interest because of its good stability. UiO-66-NH<sub>2</sub> is constructed with hexameric Zr<sub>6</sub>O<sub>4</sub>(OH)<sub>4</sub>(-CO<sub>2</sub>)<sub>12</sub> clusters and 2-aminoterephthalic acid containing tetrahedral (approximately 8 Å) and octahedral cavities (approximately 11 Å) accessible by microporous triangular windows (approximately 6 Å)<sup>28</sup>. The framework of UiO-66-NH<sub>2</sub> is stable at temperatures up to 300 °C. It is also stable in most organic solvents, water, and acidic aqueous solutions due to strong bonding between oxophilic Zr<sup>4+</sup> ions and carboxylate groups of the ligands as well as the inherent

high connectivity of its framework<sup>27</sup>. The good stability of UiO-66-NH<sub>2</sub> has enabled its wide applications in such as post-synthetic modifications<sup>27</sup>, metal nanoparticle dispersions<sup>29</sup>, and direct usage in heterogeneous catalysis<sup>30</sup>, etc.

The UiOAB complex can also find potential usage in organic synthesis. Borane-amine adducts are important stock compounds that have found broad applications in academic and industrial processes, such as hydroboration of olefins, reduction of carbonyl compounds, and as precursors for polyaminoboranes<sup>31</sup>. Unlike other diborane compounds, such as borane-tetrahydrofuran (BH<sub>3</sub>-THF) and borane-dimethyl sulfide (BH<sub>3</sub>-Me<sub>2</sub>S), that often suffer from low stability, high volatility, flammability and sometimes an unpleasant odor, borane-amine adducts are typically stable in air, easy to handle, and environmentally benign<sup>32</sup> due to a tighter boron-nitrogen bond. Although enantioselective reduction of carbonyl compounds has been well established with borane reagents such as the CBS-reduction reaction<sup>33</sup>, to the best of our knowledge, a general substrate-size-selective protocol has not been previously reported for either borane or borane-amine adducts. The UiOAB complex contains borane-amine substructures inside its uniform cavity may offer a good opportunity to achieve this goal with a molecular sieving effect that has been observed in other MOFs and zeolite systems<sup>34-36</sup>. To demonstrate this idea, the selective reduction of aldehyde compounds with different molecular sizes was selected as a prototype system.

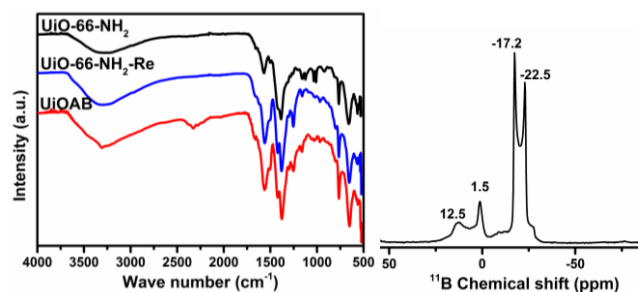


Fig. 1. Left: FTIR spectra of UiO-66-NH<sub>2</sub> (black), UiOAB (red) and UiOAB after thermolysis at 90 °C and washing with methanol, which is referred to as UiO-66-NH<sub>2</sub>-Re (blue). Right: Solid state <sup>11</sup>B NMR of UiOAB.

The MOF-Amino-borane complex, namely UiOAB, was obtained by simply treating UiO-66-NH<sub>2</sub> with borane in diethyl ether medium (see the experimental details in ESI. †). Elemental analysis using ICP-OES (Table S1) revealed that 4.55% of borane was loaded in UiOAB, which is equivalent to 1.2 borane per amine group inside the framework. The more than stoichiometric amount of borane loading indicates that there are at least two types of amine-borane complexes formed. The solid state <sup>11</sup>B NMR of UiOAB (Fig. 1, right) contains two main peaks at -17.2 and -22.5 ppm, which indicated that there were two types of boron states corresponding to -NH<sub>2</sub>BH<sub>3</sub> and -NH<sub>2</sub>B<sub>2</sub>H<sub>5</sub>, respectively. The FTIR spectrum (Fig. 1, left) of UiOAB exhibited a new broad peak near 2300 cm<sup>-1</sup>, which is due to the characteristic peak of B-H symmetric stretching vibrations and indicates that UiO-66-NH<sub>2</sub> has reacted with borane to yield UiOAB. After thermolysis and washing with methanol, this band disappeared in UiO-66-NH<sub>2</sub>-Re. In fact, the FTIR spectrum of UiO-66-NH<sub>2</sub>-Re contained nearly the same peaks as UiO-66-NH<sub>2</sub>. In addition, the ICP-OES and <sup>11</sup>B NMR spectrum of UiO-66-NH<sub>2</sub>-Re exhibit no additional signals for

boron, indicating that the adsorbed borane was completely removed. All of these characterization results confirmed that the desired MOF-amino-borane complex UiOAB was formed.

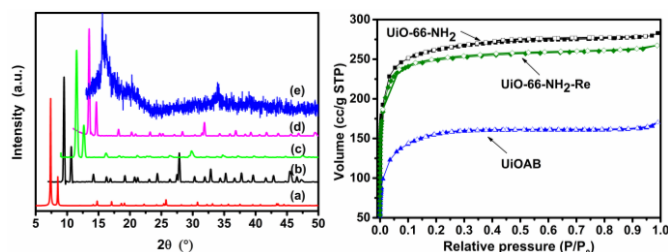


Fig. 2. Left: PXRD patterns of UiO-66-NH<sub>2</sub> at different stages. Each pattern was shifted 2 degrees from each other to the right for clarity. (a) simulated UiO-66-NH<sub>2</sub> pattern from cif-file CCDC 837796, (b) as-synthesized UiO-66-NH<sub>2</sub>, (c) as-synthesized UiOAB, (d) UiO-66-NH<sub>2</sub>-Re, and (e) UiOAB after TGA-QMS analysis during which UiOAB was heated from room temperature to 200 °C at a ramping rate of 1 °C/min under 20 ml/min argon flow. Right: N<sub>2</sub> uptake isotherm at 77 K; adsorption (filled) and desorption (open).

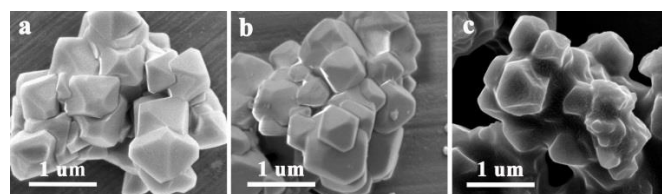


Fig. 3. SEM images of (a) UiO-66-NH<sub>2</sub>, (b) UiOAB, and (c) UiO-66-NH<sub>2</sub>-Re.

Borane is a well-known reductant that may react with carboxylate groups, which is one of the main building blocks of UiO-66-NH<sub>2</sub>, and possibly lead to a structural collapse<sup>37</sup>. Therefore, PXRD was recorded in each step to monitor the structure change. The PXRD pattern (Fig. 2, left) of UiO-66-NH<sub>2</sub> matches well with simulated UiO-66. The XRD patterns of UiOAB and UiO-66-NH<sub>2</sub>-Re are nearly identical to that of UiO-66-NH<sub>2</sub>. All of the patterns have sharp diffraction peaks and flat baselines, which indicate that the synthesized UiO-66-NH<sub>2</sub> powder exhibited good crystallinity and remained intact during borane loading and hydrogen release. However, the PXRD peaks of UiOAB after TGA analysis during which it was heated to 200 °C and maintained at this temperature for 6 hours, nearly disappeared, which indicates the structure collapsed at this temperature. This temperature is much lower than that reported in the literature<sup>27</sup> (i.e., approximately 300 °C, which was determined from TGA analysis). The lower decomposition temperature is most likely due to two reasons. First, the structural collapse temperature determined by PXRD is typically lower than that determined by TGA analysis. Second, boron can promote radical oxidation of the carboxylate group in the framework, which has been commonly observed in organic chemistry<sup>38-39</sup>. Nevertheless, since the temperatures for borane loading and for hydrogen release (which will be discussed in the next paragraph) are much below 200°C, so UiOAB is stable enough for borane storage and reuse.

Fig. 3 shows the SEM images of the crystal morphologies at different stages. The as-synthesized UiO-66-NH<sub>2</sub> particles have an octahedral morphology with an average particle size of 1 micrometer. The size and morphology were well preserved in UiOAB. However, some particles were broken into

approximately half their original size after hydrogen release in UiO-66-NH<sub>2</sub>-Re, which is most likely due to the volume change that occurs during the adsorption/desorption process. This volume change is a common challenge for adsorption process. The BET surface area and pore volume of the as-synthesized UiO-66-NH<sub>2</sub> was determined to be 976 m<sup>2</sup>/g and 0.4377 cm<sup>3</sup>/g, respectively, which is similar to the values reported in the literature<sup>27</sup>. After loading with borane, these values sharply decreased to 298 m<sup>2</sup>/g and 0.1618 cm<sup>3</sup>/g, respectively, in UiOAB, which demonstrated that the pores were largely occupied by borane. For UiO-66-NH<sub>2</sub>-Re, these two values recovered to 834 m<sup>2</sup>/g and 0.4136 cm<sup>3</sup>/g, respectively. Therefore, most of the pores were re-opened after hydrogen release. Both the BET adsorption (Fig. 2, right) and PXRD data demonstrated the excellent stability and reusability of UiO-66-NH<sub>2</sub> in our hydrogen production strategy.

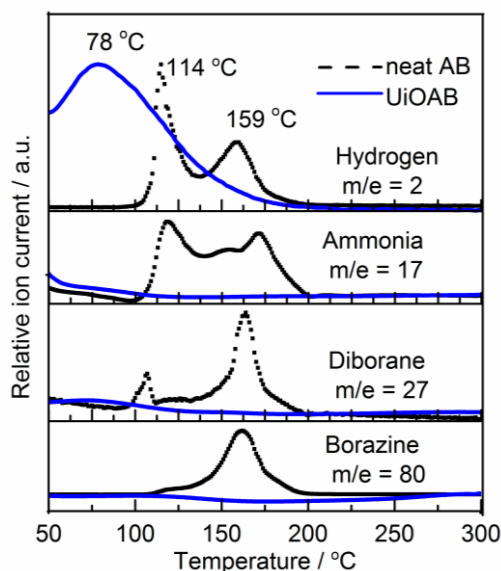


Fig. 4. TGA-QMS spectra of neat AB (black dashed line) and UiOAB (blue solid line) during the dehydrogenation process.

Thermogravimetric analysis coupled with quadrupole mass spectrometry (TGA-QMS) was used to investigate hydrogen release (Fig. 4) from both neat AB and UiOAB. The results indicated that neat AB releases hydrogen mainly at two temperatures. The first temperature is at 114 °C, and the second at 149 °C. Neat AB also produces a large quantity of volatile by-products, such as ammonia, diborane, and borazine. In contrast, the dehydrogenation of UiOAB started at a temperature below 50 °C, which is the lowest detectable limit of the equipment, and only one temperature peak was observed at 78 °C. Therefore, in comparison to neat AB, the dehydrogenation temperature was significantly reduced. In contrast to the approach where AB is physically absorbed inside the mesoporous silica or MOF channels, the amine-borane complex of UiOAB can be considered a single point of molecular AB. This may explain why there is only one hydrogen releasing peak in our system. The strong chemical bonding between borane and amino group also explains why there is no volatile by-products generated during the decomposition process.

The area under the two hydrogen peaks of neat AB in Fig. 4 is equivalent to approximately 10 wt% of hydrogen, as reported in the literature<sup>13</sup>. Using this as a reference, the total amount of

hydrogen released from UiOAB is approximately 2.2 wt%. Because the borane loading in UiOAB is 4.55%, as determined by ICP-OES, therefore, almost all hydrogen in borane adsorbed in UiOAB are released. Strong reducing agents such as LiAlH<sub>4</sub> and hydrazine and harsh conditions are always required to regenerate AB from the dehydrogenation products of polyborazylene<sup>40</sup>. While in our system, the AB complexes are spatially separated with each other so that polymerization is fundamentally avoided. After dehydrogenation, UiO-66-NH<sub>2</sub> can be regenerated by simply soaking in methanol, as confirmed by IR, solid <sup>11</sup>B NMR/MAS, N<sub>2</sub> isothermal physisorption as well as by SEM as above mentioned. Table S2 summarize the reported hydrogen release results from AB physically loaded in different MOF systems. Compared to most reported results, our work showed higher hydrogen loading rate and lower hydrogen release temperature. From all of these results it can clearly see that no matter whether AB is physically loaded, as reported in the literature, or chemically bonded, as reported in our studies, the nano-confinement provided by MOF structure played an important role in reducing the hydrogen release temperature and the generation of contaminants.

$$\text{R}-\text{CHO} \xrightarrow[\text{MeOH, 60 }^\circ\text{C, 4h}]{\text{UiOAB}} \text{R}-\text{CH}_2\text{OH}$$

Entry	Substrates	Product	Conversion <sup>(a)</sup> / %
1			99
2			95
3			35 (80) <sup>(b)</sup>
4			0
5			90/2

Table 1. Substrate-specific reduction of aldehydes using UiOAB. (a) Conversion determined by GC. (b) The reaction was continued after 4 hours by adding another 1 eq. of UiOAB and extending the reaction time for another 12 hours.

DFT calculations of the N<sub>2</sub> physisorption isotherm data indicated a decrease in pore size from 7.3 Å in UiO-66-NH<sub>3</sub> to 5.3 Å in UiOAB. This pore size is bigger than the kinetic diameter of linear alkyl aldehydes such as propanal (~4.7 Å) and butyral (~5.0 Å), but smaller than aromatic aldehydes such as benzaldehyde (~5.9 Å) and phenanthrene-9-carbaldehyde (~8.9 Å). So a substrates size selective reduction was expected and demonstrated. The aldehyde reduction reactions were conducted in methanol at 60 °C for 4 hours. Under this condition our control experiments showed that when borane, sodium borane hydride and ammonia borane were used as reducing agent all of these aldehydes were converted quantitatively to

the related alcohol products without notable selectivity. However, when UiOAB used as a reducing agent, the results in Table 1 show that for small sized propanal and butyral, the conversion is more than 95%, but for large benzaldehyde, the conversion decreased to 35%. The results indicate that propanal and butyral can freely enter the pores of UiOAB. Benzaldehyde can also enter the pores, presumably due to the structure flexibility that commonly observed in MOF structure, but in much slow rate. For this reaction we further extended the reaction time to another 12 hours. Since as shown in Fig. 4, UiOAB starts to decompose at temperature below 60 °C, to maintain enough amount of UiOAB in the reaction medium, we added another 1 eq. of UiOAB. At the end, the conversion of benzaldehyde was increased to 80%. When a more steric bulky molecule, phenanthrene-9-carbaldehyde, is used, no product was detected. To further demonstrate the size-selective effect, a mixture of propanal and benzaldehyde in 1:1 mol ratio was studied under the standard reaction condition (Table 1, Entry 5). A high product selectivity of 49 was obtained. All of these results clearly demonstrated the potential usage of UiOAB as a size-selective reduction agent for organic synthesis.

In summary, a microporous metal-organic framework UiOAB, which contains amino-borane complexes chemically bonded to its internal framework, was rationally designed and synthesized. This novel material can act as both a reusable hydrogen chemical storage material and a size-selective reduction agent. The dehydrogenation temperature was substantially decreased from 114 °C to 78 °C compared to neat AB, and also no volatile by-products was generated during the process. The enhancement in dehydrogenation kinetics and inhibition of volatile compounds confirmed the nano-confinement effect of the spatial isolation by chemical immobilization. In the reduction reactions, large substrates exhibited significantly reduced activities and conversions compared to small substrates, demonstrating that the reaction occurs primarily within the pores which leads to a sharp molecular sieving effect.

## Acknowledgments

Financial support by KAUST Competitive Grant URF/1/1378 and Baseline fund BAS/1/1375 is gratefully acknowledged.

## Notes and references

*Division of Physical Science and Engineering, King Abdullah University of Science and Technology (KAUST), Thuwal, 23955-6900 (Saudi Arabia)*

† Electronic Supplementary Information (ESI) available: Experimental details and additional figures. See DOI: 10.1039/c000000x/

E-mail: zhiping.lai@kaust.edu.sa

## Uncategorized References

- L. Schlappbach and A. Zuttel, *Nature*, 2001, **414**, 353.
- F. H. Stephens, V. Pons and R. T. Baker, *Dalton T*, 2007, 2613.
- M. E. Bowden, I. W. Brown, G. J. Gainsford and H. Wong, *Inorg Chim Acta*, 2008, **361**, 2147.
- S. Li, Z. Tang, Q. Gong, X. Yu, P. R. Beaumont and C. M. Jensen, *J. Mater. Chem.*, 2012, **22**, 21017.
- G. Chen, L. N. Zakharov, M. E. Bowden, A. J. Karkamkar, S. M. Whittemore, E. B. Garner, T. C. Mikulas, D. A. Dixon, T. Autrey and S.-Y. Liu, *J. Am. Chem. Soc.*, 2015, **1**, 134.
- W. Luo, P. G. Campbell, L. N. Zakharov and S.-Y. Liu, *J. Am. Chem. Soc.*, 2011, **133**, 19326.
- F. H. Stephens, R. T. Baker, M. H. Matus, D. J. Grant and D. A. Dixon, *Angew. Chem. Int. Ed.*, 2007, **46**, 746.
- J. M. Yan, X. B. Zhang, S. Han, H. Shioyama and Q. Xu, *Angew. Chem. Int. Ed.*, 2008, **47**, 2287.
- M. E. Bluhm, M. G. Bradley, R. Butterick, U. Kusari and L. G. Sneddon, *J. Am. Chem. Soc.*, 2006, **128**, 7748.
- D. W. Himmelberger, C. W. Yoon, M. E. Bluhm, P. J. Carroll and L. G. Sneddon, *J. Am. Chem. Soc.*, 2009, **131**, 14101.
- R. J. Keaton, J. M. Blacquire and R. T. Baker, *J. Am. Chem. Soc.*, 2007, **129**, 1844.
- A. Gutowska, L. Y. Li, Y. S. Shin, C. M. M. Wang, X. H. S. Li, J. C. Linehan, R. S. Smith, B. D. Kay, B. Schmid, W. Shaw, M. Gutowski and T. Autrey, *Angew. Chem. Int. Ed.*, 2005, **44**, 3578.
- L. Gao, C.-Y. V. Li, H. Yung and K.-Y. Chan, *Chem. Commun.*, 2013, **49**, 10629.
- S. Gadipelli, J. Ford, W. Zhou, H. Wu, T. J. Udovic and T. Yildirim, *Chem. Eur. J.*, 2011, **17**, 6043.
- R.-Q. Zhong, R.-Q. Zou, T. Nakagawa, M. Janicke, T. A. Semelsberger, A. K. Burrell and R. E. Del Sesto, *Inorg Chem*, 2012, **51**, 2728.
- X.-I. Si, L.-x. Sun, F. Xu, C.-I. Jiao, F. Li, S.-s. Liu, J. Zhang, L.-f. Song, C.-h. Jiang and S. Wang, *Int. J. Hydrogen Energy*, 2011, **36**, 6698.
- G. Srinivas, J. Ford, W. Zhou and T. Yildirim, *Int. J. Hydrogen Energy*, 2012, **37**, 3633.
- G. Srinivas, W. Travis, J. Ford, H. Wu, Z.-X. Guo and T. Yildirim, *J. Mater. Chem. A*, 2013, **1**, 4167.
- Z. Li, G. Zhu, G. Lu, S. Qiu and X. Yao, *J. Am. Chem. Soc.*, 2010, **132**, 1490.
- H. M. Jeong, W. H. Shin, J. H. Park, J. H. Choi and J. K. Kang, *Nanoscale*, 2014, **6**, 6526.
- Z. Li, W. Liu, H. Yang, T. Sun, K. Liu, Z. Wang and C. Niu, *Rsc Adv*, 2015, **5**, 10746.
- Y.-J. Xu and J.-Q. Li, *Appl. Surf. Sci.*, 2006, **252**, 5855.
- M. Eddaoudi, J. Kim, N. Rosi, D. Vodak, J. Wachter, M. O'Keeffe and O. M. Yaghi, *Science*, 2002, **295**, 469.
- H. Furukawa, N. Ko, Y. B. Go, N. Aratani, S. B. Choi, E. Choi, A. O. Yazaydin, R. Q. Snurr, M. O'Keeffe, J. Kim and O. M. Yaghi, *Science*, 2010, **329**, 424.
- M. Savonnet, D. Bazer-Bachi, N. Bats, J. Perez-Pellitero, E. Jeanneau, V. Lecocq, C. Pinel and D. Farrusseng, *J. Am. Chem. Soc.*, 2010, **132**, 4518.
- C. J. Doonan, W. Morris, H. Furukawa and O. M. Yaghi, *J. Am. Chem. Soc.*, 2009, **131**, 9492.
- S. J. Garibay and S. M. Cohen, *Chem. Commun.*, 2010, **46**, 7700.
- P. A. P. Mendes, F. Ragon, A. E. Rodrigues, P. Horcajada, C. Serre and J. A. C. Silva, *Micropor Mesopor Mat*, 2013, **170**, 251.
- L. Shen, W. Wu, R. Liang, R. Lin and L. Wu, *Nanoscale*, 2013, **5**, 9374.
- F. Vermoortele, R. Ameloot, A. Vimont, C. Serre and D. De Vos, *Chem. Commun.*, 2011, **47**, 1521.
- A. Staubitz, A. P. Robertson, M. E. Sloan and I. Manners, *Chem. Rev.*, 2010, **110**, 4023.
- W. J. Atkins, E. R. Burkhardt and K. Matos, *Org Process Res Dev*, 2006, **10**, 1292.
- E. J. Corey, R. K. Bakshi and S. Shibata, *J. Am. Chem. Soc.*, 1987, **109**, 5551.
- S. Horike, M. Dinca, K. Tamaki and J. R. Long, *J. Am. Chem. Soc.*, 2008, **130**, 5854.
- J. M. Roberts, B. M. Fini, A. A. Sarjeant, O. K. Farha, J. T. Hupp and K. A. Scheidt, *J. Am. Chem. Soc.*, 2012, **134**, 3334.
- A. V. A. Kumar and S. K. Bhatia, *Phys. Rev. Lett.*, 2006, **96**.
- N. M. Yoon, C. S. Pak, H. C. Brown, Krishnam.S and T. P. Stocky, *J. Org. Chem.*, 1973, **38**, 2786.
- C. Ollivier and P. Renaud, *Chem. Rev.*, 2001, **101**, 3415.
- P. Renaud, A. Beauseigneur, A. Brecht-Forster, B. Becattini, V. Darmency, S. Kandhasamy, F. Montermini, C. Ollivier, P. Panchaud, D. Pozzi, E. M. Scanlan, A.-P. Schaffner and V. Weber, *Pure Appl Chem*, 2007, **79**, 223.
- A. D. Sutton, A. K. Burrell, D. A. Dixon, E. B. Garner, J. C. Gordon, T. Nakagawa, K. C. Ott, J. P. Robinson and M. Vasiliu, *Science*, 2011, **331**, 1426.