

# ChemComm

Accepted Manuscript



This is an *Accepted Manuscript*, which has been through the Royal Society of Chemistry peer review process and has been accepted for publication.

*Accepted Manuscripts* are published online shortly after acceptance, before technical editing, formatting and proof reading. Using this free service, authors can make their results available to the community, in citable form, before we publish the edited article. We will replace this *Accepted Manuscript* with the edited and formatted *Advance Article* as soon as it is available.

You can find more information about *Accepted Manuscripts* in the [Information for Authors](#).

Please note that technical editing may introduce minor changes to the text and/or graphics, which may alter content. The journal's standard [Terms & Conditions](#) and the [Ethical guidelines](#) still apply. In no event shall the Royal Society of Chemistry be held responsible for any errors or omissions in this *Accepted Manuscript* or any consequences arising from the use of any information it contains.

## COMMUNICATION

# An *N*-ethylated barbituric acid end-capped bithiophene as an electron-acceptor material in fullerene-free organic photovoltaics

Cite this: DOI: 10.1039/x0xx00000x

Received 00th January 2012,

Accepted 00th January 2012

DOI: 10.1039/x0xx00000x

www.rsc.org/

**A new evaporable electron acceptor material for organic photovoltaics based on *N*-ethyl barbituric acid bithiophene (EBB) has been demonstrated. Bilayer devices fabricated with this non-fullerene acceptor and boron subphthalocyanine chloride (SubPc) donor produce power conversion efficiencies as high as 2.6% with an extremely large open-circuit voltage approaching 1.4 V.**


The field of organic photovoltaics (OPVs) has witnessed rapid advances over the last few years driven by the promise of low-cost, environmentally friendly power. The design and synthesis of new p-type donor materials for use with fullerene acceptors has seen efficiencies in solution processed bulk heterojunction and evaporated OPVs rising to over 9%.<sup>1,2</sup> In addition, progress has been achieved by the concurrent development of new device architectures and processing methods, leading to an improved understanding of the role of energetics and microstructure on device performance.<sup>3</sup>

To further enhance the performance of OPVs, recent efforts have focused on the development of novel non-fullerene acceptors. Fullerene derivatives make excellent electron accepting materials due to their highly degenerate lowest unoccupied molecular orbitals (LUMO) and moderately high electron mobility. However they are not without their problems, notably their relatively weak absorption profile, deep-lying LUMO levels and relatively narrow band-gaps which, whilst good for charge separation, can result in excessive potential losses and limited open-circuit voltages ( $V_{oc}$ ).<sup>4</sup>

The development and identification of both p- and n-type materials with electronic, optical, chemical and physical properties suitable for solution processing or vacuum deposition is of paramount importance. Initially small molecule n-type materials were designed specifically for solution processing, based on polyaromatic hydrocarbon diimides, diketopyrrolopyrrole, benzothiazadiazole, and oligothiophene derivatives functionalised with acceptor moieties,<sup>2,5</sup> and have achieved efficiencies over 2% as drop in replacements for 6,6-phenyl-C<sub>61</sub>-butyric acid methyl esters (PCBM) with the prototypical donor material poly-3-

hexylthiophene (P3HT). Encouragingly, in the last year, solution processable non-fullerene n-type materials have been coupled with high performance p-type materials with efficiencies approaching 7%.<sup>6</sup> In contrast, vacuum evaporable n-type materials to replace C<sub>60</sub> are limited, although some progress has been made identifying alternative materials for this role including perylene, oligothiophene<sup>7</sup> and subphthalocyanine derivatives. The gradual development of subphthalocyanines as acceptor materials has seen initial power conversion efficiencies of ~2.5%<sup>8,9</sup> increase to 8.4% in evaporated multi-layered devices.<sup>10</sup> The dearth of suitable non-fullerene acceptors available to be studied with different and promising vacuum compatible p-type materials makes this a key area of research.

We have used structure-property relationships (SPRs) in the design of p- and n-type materials for organic field effect transistors (OFETs)<sup>11,12</sup> and OPVs.<sup>13,14</sup> Recently we reported a SPR study of a family of functionalised acceptor-donor-acceptor derivatives, where bis-(diethyl-barbituric acid)-2,2'-bithiophene (EBB) **1**, (Fig. 1) was identified as a lead material exhibiting an electron mobility of 0.26 cm<sup>2</sup>/Vs in a vacuum deposited OFET.<sup>12</sup> The HOMO and LUMO energy levels of EBB are -6.28 eV and -4.23 eV respectively, highlighting this material as a potential fullerene<sup>15</sup> replacement material for OPVs.

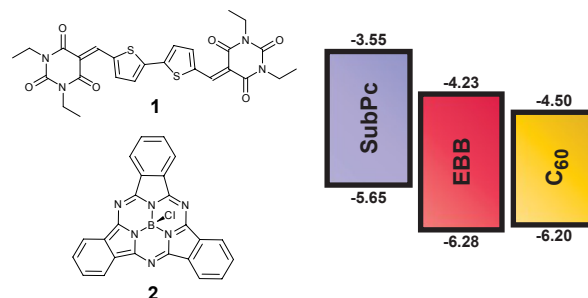

**Fig. 1:** Chemical structures of EBB **1** and SubPc **2** and corresponding energy levels including C<sub>60</sub>.

In this communication we report the use of EBB **1** as an electron accepting material with boron subphthalocyanine chloride (SubPc) **2**<sup>9,16</sup> as the donor in evaporated bilayer OPV devices. OPV devices are investigated in both regular and inverted geometry with performance optimisation completed through the use of a hole-transporting optical spacer layer in the inverted geometry to achieve the highest efficiencies of 2.6% for an oligothiophene n-type acceptor compound, and highest reported open circuit voltage ( $V_{OC}$ ) of 1.38V for a non-fullerene bilayer device.

The synthesis of EBB was recently reported.<sup>12</sup> This compound can be accessed on multi-gram quantities and high yield by Knoevenagel condensation of diformyl-2,2'-bithiophene with diethyl barbituric acid. The compound is extremely insoluble, but thermally stable up to ~415 °C (DSC) and therefore easily purified by vacuum sublimation. Importantly, compared to C<sub>60</sub> EBB has a similar HOMO level but a slightly higher lying LUMO level, which suggests this should favour greater open circuit voltages (Fig. 1).

The normalised UV/Vis absorption profiles of films of EBB and SubPc evaporated onto ITO substrates are shown in Fig. 2. SubPc shows an intense absorption at 598 nm with a secondary shoulder at 550 nm and is consistent with previous observations.<sup>10,16,17</sup> EBB films show a peak absorption at 481 nm with an additional shoulder out to 550 nm that is consistent with our earlier studies on glass.<sup>14</sup> Although the two materials show significant absorption overlap in the range 525-575 nm, peak absorbances are separated sufficiently to allow a determination of the role of each material in a bilayer device, and provide relatively broad total absorption.

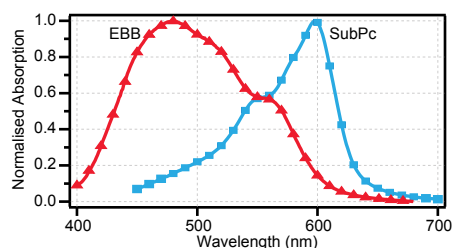


Fig. 2. Normalised UV/Vis absorption profiles of EBB and SubPc on ITO.

Photoluminescence (PL) studies of bilayer thin films of SubPc and EBB were undertaken to determine if effective current generation could be extracted from this excitonic pair (Fig. 3). Excitation of SubPc at 590 nm in the presence of an EBB layer results in a 65% decrease in PL intensity (Fig. 3a), consistent with that seen in other planar heterojunction systems demonstrating strong dissociation of excitons.<sup>18</sup> Likewise excitation of EBB at 450 nm in the presence of a SubPc layer results in a 46% decrease in PL intensity (Fig. 3b). Exciton dissociation from the SubPc should be driven by  $\Delta_{LUMO}$  (0.68 eV) (i.e. the difference in LUMO energy between the two materials), whilst dissociation from EBB should be driven by  $\Delta_{HOMO}$  (0.63 eV). Both of these values are greater than the 0.3-0.6 eV required for efficient exciton separation and consistent with these PL results.

To determine electron mobility in the EBB films, electron-only devices with structure ITO / Zr(acac) / EBB (100 nm) / Al (200 nm) were fabricated and the mobility measured by the space-charge limited current (SCLC) method. Zr(acac) has recently been shown as an effective electron transport layer for a range of active materials.<sup>19</sup> A

Mott-Gurney fit to the  $J$ - $V$  data (Fig. S1) yields a zero-field mobility of  $\mu_0 = 1.25 \times 10^{-7} \text{ cm}^2 \text{ V}^{-1} \text{ s}^{-1}$ . The OPV orientation (perpendicular) electron mobility in C<sub>60</sub> is typically reported as high as  $5.1 \times 10^{-2} \text{ cm}^2 \text{ V}^{-1} \text{ s}^{-1}$ ,<sup>20,21</sup> significantly higher than that of EBB. However, there is evidence that matched mobility between donor and acceptor material can be more critical than absolute mobility,<sup>22</sup> and so with a reported hole mobility in SubPc of  $4.5 \times 10^{-8} \text{ cm}^2 \text{ V}^{-1} \text{ s}^{-1}$ ,<sup>21</sup> the value may not provide a significant bottleneck to performance.

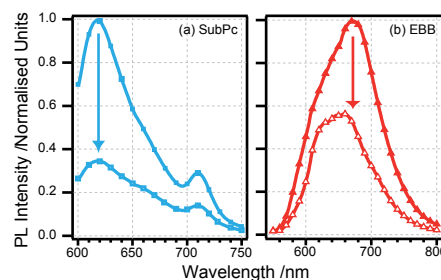


Fig. 3. Photoluminescence spectra of a) 25 nm SubPc film excited at 590 nm with (filled squares) and without (open squares) a 20 nm EBB quenching layer and b) 25 nm EBB film excited at 450 nm with (filled triangles) and without (open triangles) a 20 nm SubPc quenching layer. In both cases the plots are normalised to the peak in the non-quenched spectrum.

The precise crystallographic and morphological structure of a small molecule film can significantly impact its absorption and charge transport properties, and this can sometimes be controlled through the underlying layer or substrate.<sup>23,24</sup> Analysis of EBB thin films deposited onto ITO and various interlayers used in this work were significantly different to EBB films deposited onto octadecylsilane (ODTS) self-assembled surfaces used in the OFET studies.<sup>12</sup> An AFM image of an EBB (50 nm) film grown on ITO is shown in Fig. S2, and shows features of ~100 nm in size with a surface roughness of 13.8 nm, consistent with the surface structure observed in OFET studies. However, XRD traces (Fig. S3) of EBB films (100 nm) grown on ITO, ITO/SubPc and ITO/Zr(acac) do not show any discernible diffraction peaks, in stark contrast to those from OFET films which showed a strong peak at  $2\theta = \sim 6.2^\circ$ . Although the ITO itself produces a series of characteristic peaks, these can be assigned across all samples and are usually not sufficiently intense to mask peaks from a subsequent layer.<sup>23</sup> The data suggests that the highly crystalline films formed in the OFET study were driven by a favourable interaction between the EBB and ODTS treated surface, whilst in this work the rougher underlying films do not show a similar interaction and lead to significantly less crystalline, even amorphous films. The lower mobility observed with these EBB films is consistent with this lower degree of crystallinity.

The SubPc / EBB system was evaluated in OPV devices based on the regular architecture of ITO / MoO<sub>x</sub> (5 nm) / SubPc (15 nm) / EBB (20 or 40 nm) / BCP (8 nm) / Al (200 nm), with  $J$ - $V$  curves, EQE and reflective geometry absorption profiles shown in Fig. 4., and performance parameters for all devices in Table S1. Measuring absorption profiles in a reflective geometry, whereby the probe beam enters the structure through the transparent electrode, reflects from the back electrode and then passes through the transparent electrode before being measured, provides a total absorption profile of a complete OPV device as it would be under operation.<sup>25</sup> This is particularly important for OPV devices containing thin discrete layers where deviation from

Beer-Lambert behaviour is likely through optical interference effects which can dominate the absorption profile. At an EBB thickness of 20 nm a short-circuit current density ( $J_{SC}$ ) of 2.34 mA cm<sup>-2</sup>,  $V_{OC}$  of 1.38 V and fill factor ( $FF$ ) of 0.4 are produced resulting in a power conversion efficiency  $\eta_p = 1.28$  %. This  $V_{OC}$  is the highest reported for single junction devices to date, exceeding that of recent high  $V_{OC}$  devices using subphthalocyanine acceptor materials.<sup>9</sup> The fact the  $V_{OC}$  is equal to the calculated interface gap of the system (the difference between the donor HOMO and acceptor LUMO) is unexpected as a minimum 0.3 eV loss is usual. However, although the HOMO levels are determined through UPS, LUMO levels are only estimated via optical band measurements and are thus prone to significant error.<sup>12,17</sup> A similar result is observed with SubPc/C<sub>60</sub> junction cells which typically show  $V_{OC}$  values  $\sim 1.1$  V, hence the absolute change in  $V_{OC}$  upon replacing C<sub>60</sub> with EBB is consistent.<sup>9</sup> The EQE of the 20 nm EBB device shows a dominant SubPc contribution to the photocurrent with only a weak contribution from the EBB at  $\sim 400$ -500 nm. The reflective geometry absorption spectrum confirms that this is largely a result of poor absorption in this region as it is also dominated by the SubPc peak at  $\sim 590$  nm. To address the low absorption profile a thicker layer of EBB (40 nm) was examined. Unfortunately the increased absorbance is met with a decrease in  $J_{SC}$  and  $FF$ , with the latter caused by a significant kink in the  $J$ - $V$  curve. This is indicative of a charge accumulation site forming in the device, likely caused by the poor electron mobility of the EBB at these thicker layers. With the acceptor thickness therefore limited to around 20 nm an alternative strategy was investigated to enhance current generation.

Optical interference effects in discrete layer OPVs utilising reflective back electrodes are increasingly well understood. In particular it is known that an optical field intensity node is formed at the reflective electrode interface, limiting the optical intensity, and hence absorption, close to this interface.<sup>3</sup> In regular architecture bilayer devices the optimum acceptor layer thickness tends to be significantly greater than the optimum donor layer thickness, and this is likely due to the need to move the active interface away from this low absorption region.<sup>9</sup> This is effective only when the electron mobility of the acceptor is sufficiently high (such as for C<sub>60</sub>), but for EBB the regular architecture devices show this to not be a viable solution. Optically transparent, charge transporting spacer layers have been used extensively in tandem OPV cells to control the positioning of sub-cells within the optical field,<sup>26,27</sup> and have seen some use in single junction devices where increasing layer thicknesses has not been desirable.<sup>28</sup> Replacing the BCP with an electron-transporting spacer layer would be ideal, however hole-transporting spacer layers are more developed and so we investigate an inverted architecture using an NPD:MoO<sub>x</sub> hole-transporting spacer layer.<sup>26</sup>

A series of inverted devices of structure ITO / Zr(acac) / EBB (20 nm) / SubPc (20 nm) / NPD:MoO<sub>x</sub> (6:1, 10-50 nm) / Al (200 nm) were fabricated. By keeping the thickness of both active layers fixed at 20 nm the effect of the spacer layer could be monitored as the distance from the reflective electrode to the D/A interface changed from 30-70 nm.  $J$ - $V$ , EQE and reflective geometry absorption plots are also shown in Fig. 4 with key parameters again in Table S1. The  $V_{OC}$  of the inverted devices was in the range 1.24-1.28 V,  $\sim 0.1$  V lower than those recorded for regular architecture devices. The  $J_{SC}$  showed a significant improvement over regular architecture devices, with 3.85 mA cm<sup>-2</sup>

obtained at a spacer layer thickness of 20 nm, then decreasing at both increasing and decreasing spacer thickness. The  $FF$  was also significantly higher ( $\sim 0.5$ ) than regular architecture devices, resulting in an average peak power conversion efficiency of 2.39 % (2.57 % best pixel) with a 20 nm spacer layer which compares favourably to an optimised SubPc/C<sub>60</sub> planar junction device (3 %).<sup>9</sup> EQE and reflective geometry absorption measurements provide an insight into the origin of this improvement in  $J_{SC}$ . Comparing the inverted architecture device with a 20 nm spacer layer to the regular architecture device with a 20 nm EBB layer an improvement in EQE is observed across the spectrum, with an increase from 0.28 to 0.36 at the peak around 585 nm (approximately the peak absorption of SubPc) and from 0.13 to 0.27 at 480 nm (the peak absorption of EBB).

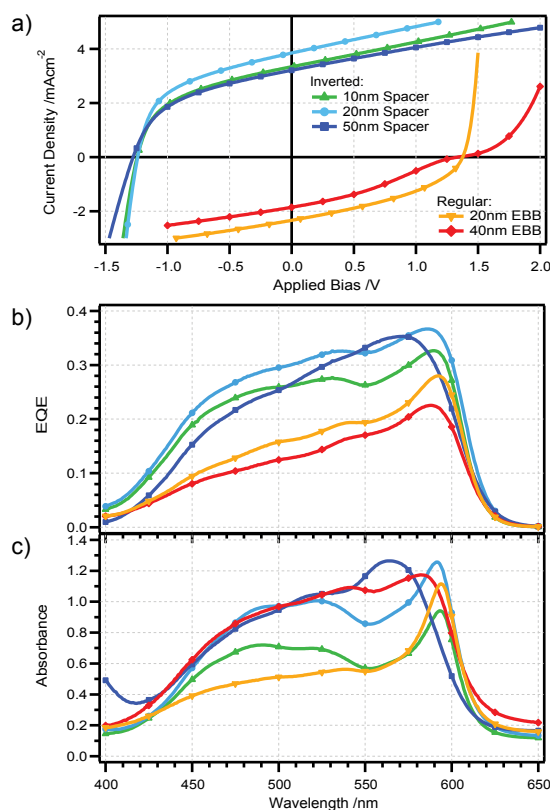


Fig. 4. (a)  $J$ - $V$  (b) EQE and (c) reflective geometry absorption plots for regular and inverted architecture devices.

## Conclusions

In summary, we have demonstrated a new type of electron acceptor material for evaporable organic photovoltaics based on an *N*-ethyl barbituric acid bithiophene derivative. The material, having frontier orbital energies comparable to the commonly used fullerene derivatives, was demonstrated to effectively quench excitons in both directions when combined with a SubPc donor material. Devices employing this donor/acceptor combination showed exceptionally high  $V_{OC}$  values up to 1.38 V; amongst the highest reported for single junction devices. Despite a relatively low OPV-geometry electron mobility, inverted architecture cells employing a hole transporting optical spacer layer achieved power conversion efficiencies of almost 2.6%. Whilst modest in terms of current state of the art devices, it is



worth noting that this efficiency is ~86% of that obtained from an optimised SubPc/C<sub>60</sub> based device, proving the potential of the these types of n-type material to compete with fullerene derivatives when used in higher performing multijunction and cascade devices.

## Acknowledgements

This work was supported by the Engineering and Physical Sciences Research Council [Grant Numbers EP/J500057/1 and EP/H021388/1] and the Flexible Electronic Theme at CSIRO Manufacturing Flagship. The Panalytical® MRD diffractometer used in this research was obtained through the Science City Advanced Materials Project: Creating and Characterizing Next Generation Advanced Materials, with support from Advantage West Midlands (AWM) and part funded by the European Regional Development Fund (ERDF).

## Notes and references

<sup>a</sup> Department of Chemistry, University of Warwick, Coventry, CV4 7AL, UK. Tel: +44 2476 522188; E-mail: p.j.sullivan@warwick.ac.uk

<sup>b</sup> Advanced Fibres and Chemical Industries, CSIRO Manufacturing Flagship, Melbourne, Private Bag 10, VIC, 3169, Australia. Tel: +61 3 9545 2458; E-mail: Gavin.Collis@csiro.au

† Electronic Supplementary Information (ESI) available: contains information on materials, film characterisation, device fabrication, UV/Visible, photoluminescence, electron mobility, AFM, XRD and OPV device data. See DOI: 10.1039/b000000x/

- (a) J. You, L. Dou, K. Yoshimura, T. Kato, K. Ohya, T. Moriarty, K. Emery, C.-C. Chen, J. Gao, G. Li and Y. Yang, *Nature Commun.*, 2013, **4**, 1446; (b) X. Che, X. Xiao, J. D. Zimmerman, D. Fan and S. R. Forrest, *Adv. Energy Mater.*, 2014, **4**, 1400568; (c) Z. He, C. Zhong, S. Su, M. Xu, H. Wu and Y. Cao, *Nature Photonics*, 2012, **6**, 591; (d) A. Mishra and P. Bäuerle, *Angew. Chem. Int. Ed.*, 2012, **51**, 2020; (e) Y. Lin, Y. Li and X. Zhan, *Chem. Soc. Rev.*, 2012, **41**, 4245.
- A. F. Eftaiha, J.-P. Sun, I. G. Hill and G. C. Welch, *J. Mater. Chem. A*, 2014, **2**, 1201.
- W. Cao and J. Xue, *Energy Environ. Sci.*, 2014, **7**, 2123.
- J. C. Bijleveld, R. A. M. Verstrijden, M. M. Wienk and R. A. J. Janssen, *App. Phys. Lett.*, 2010, **97**, 073304.
- (a) P. Sonar, J. P. F. Lim and K. L. Chan, *Energy Environ. Sci.*, 2011, **4**, 1558; (b) F. Zhang, D. Wu, Y. Xu and X. Feng, *J. Mater. Chem.*, 2011, **21**, 17590; (c) Y. Lin and X. Zhan, *Mater. Horiz.*, 2014, **1**, 470.
- (a) J. Zhao, Y. Li, H. Lin, Y. Liu, K. Jiang, C. Mu, T. Ma, J. Y. L. Lai, H. Hu, D. Yuc and H. Yan, *Energy Environ. Sci.*, 2015, **8**, 520; (b) Y. Lin, J. Wang, Z.-G. Zhang, H. Bai, Y. Li, D. Zhu and X. Zhan, *Adv. Mater.*, 2015, **27**, 1170.
- C. Uhrich, R. Schueppel, A. Petrich, M. Pfeiffer, K. Leo, E. Brier, P. Kilickiran and P. Bäuerle, *Adv. Funct. Mater.*, 2007, **17**, 2991.
- B. Verreet, B. P. Rand, D. Cheyns, A. Hadipour, T. Aernouts, P. Heremans, A. Medina, C. G. Claessens and T. Torres, *Adv. Energy Mater.*, 2011, **1**, 565.
- P. Sullivan, A. Duraud, I. Hancox, N. Beaumont, G. Mirri, J. H. R. Tucker, R. A. Hatton, M. Shipman and T. S. Jones, *Advanced Energy Materials*, 2011, **1**, 352.
- K. Cnops, B. P. Rand, D. Cheyns, B. Verreet, M. A. Empl and P. Heremans, *Nature Commun.*, 2014, **5**, 1.
- (a) K. B. Burke, Y. Shu, P. Kemppinen, B. Singh, M. Bown, I. Liaw, R. M. Williamson, L. Thomsen, P. Dastoor, W. Belcher, C. Forsyth, K. N. Winzenberg and G. E. Collis, *Cryst. Growth Des.*, 2012, **12**, 725; (b) Y. Shu, G. E. Collis, C. J. Dunn, P. Kemppinen, K. N. Winzenberg, R. M. Williamson, A. Bilic, T. B. Singh, M. Bown, C. R. McNeill and L. Thomsen, *J. Mater. Chem. C*, 2013, **1**, 6299.
- Y. Shu, A. Mikosch, K. N. Winzenberg, P. Kemppinen, C. D. Easton, A. Bilic, C. M. Forsyth, C. J. Dunn, T. B. Singh and G. E. Collis, *J. Mater. Chem. C*, 2014, **2**, 3895.
- K. N. Winzenberg, P. Kemppinen, G. Fanchini, M. Bown, G. E. Collis, C. M. Forsyth, K. Hegedus, T. B. Singh and S. E. Watkins, *Chem. Mater.*, 2009, **21**, 5701.
- K. N. Winzenberg, P. Kemppinen, F. H. Scholes, G. E. Collis, Y. Shu, T. B. Singh, A. Bilic, C. M. Forsyth and S. E. Watkins, *Chem. Commun.*, 2013, **49**, 6307.
- C.-W. Chu, V. Shrotriya, G. Li and Y. Yang, *App. Phys. Lett.*, 2006, **88**, 153504.
- K. L. Mutolo, E. I. Mayo, B. P. Rand, S. R. Forrest and M. E. Thompson, *J. Am. Chem. Soc.*, 2006, **128**, 8108.
- N. Beaumont, S. W. Cho, P. Sullivan, D. Newby, K. E. Smith and T. S. Jones, *Adv. Funct. Mater.*, 2012, **22**, 561.
- N. Beaumont, J. S. Castrucci, P. Sullivan, G. E. Morse, A. S. Paton, Z.-H. Lu, T. P. Bender and T. S. Jones, *Journal of Physical Chemistry C*, 2014, **118**, 14813.
- Z. Tan, S. Li, F. Wang, D. Qian, J. Lin, J. Hou and Y. Li, *Sci. Rep.*, 2014, **4**, 4691.
- B. P. Rand, J. Xue, S. Uchida and S. R. Forrest, *J. Appl. Phys.*, 2005, **98**, 124902.
- R. Pandey, A. A. Gunawan, K. A. Mkhoyan and R. J. Holmes, *Adv. Funct. Mater.*, 2012, **22**, 617.
- W. Tress, A. Petrich, M. Hummert, M. Hein, K. Leo and M. Riede, *App. Phys. Lett.*, 2011, **98**, 063301.
- P. Sullivan, T. S. Jones, A. J. Ferguson and S. Heutz, *App. Phys. Lett.*, 2007, **91**, 233114.
- (a) L. Li, W. Hiu, H. Fuchs and L. Chi, *Adv. Energy Mater.*, 2011, **1**, 188; (b) C. Schünemann, D. Wynands, K.-J. Eichhorn, M. Stamm, K. Leo and M. Riede, *J. Phys. Chem. C*, 2013, **117**, 11600.
- G. F. Burkhard, E. T. Hoke and M. D. McGehee, *Adv. Mater.*, 2010, **22**, 3293.
- E. New, T. Howells, P. Sullivan and T. S. Jones, *Org. Electron.*, 2013, **14**, 2353.
- R. Schueppel, R. Timmreck, N. Allinger, T. Mueller, M. Furno, C. Uhrich, K. Leo and M. Riede, *J. Appl. Phys.*, 2010, **107**, 044503.
- R. Fitzner, E. Reinold, A. Mishra, E. Mena-Osteritz, H. Ziehlke, C. Körner, K. Leo, M. Riede, M. Weil, O. Tsaryova, A. Weiß, C. Uhrich, M. Pfeiffer and P. Bäuerle, *Adv. Funct. Mater.*, 2011, **21**, 897.