

ChemComm

Accepted Manuscript



This is an *Accepted Manuscript*, which has been through the Royal Society of Chemistry peer review process and has been accepted for publication.

Accepted Manuscripts are published online shortly after acceptance, before technical editing, formatting and proof reading. Using this free service, authors can make their results available to the community, in citable form, before we publish the edited article. We will replace this *Accepted Manuscript* with the edited and formatted *Advance Article* as soon as it is available.

You can find more information about *Accepted Manuscripts* in the [Information for Authors](#).

Please note that technical editing may introduce minor changes to the text and/or graphics, which may alter content. The journal's standard [Terms & Conditions](#) and the [Ethical guidelines](#) still apply. In no event shall the Royal Society of Chemistry be held responsible for any errors or omissions in this *Accepted Manuscript* or any consequences arising from the use of any information it contains.

COMMUNICATION

Two-dimensional honeycomb Coordination Network Based on Fused Triacontanuclear Heterometallic {Co₁₂Mn₁₈} Wheels

Cite this: DOI: 10.1039/x0xx00000x

Received 00th January 2012,
Accepted 00th January 2012Jiang Liu,^a Mei Qu,^a Rodolphe Clérac^{b,c*} and Xian Ming Zhang^{a*}

DOI: 10.1039/x0xx00000x

www.rsc.org/

An unprecedented two-dimensional honeycomb network based on fused triacontanuclear heterometallic wheels of 3.4 nm, [Co₂(Mn₃O)(N₃)₂(pic)₆(NO₃)₂]₆ (Hpic = picolinic acid), has been assembled. The hexagonal {Co₁₂Mn₁₈} wheel motif is composed of six oxo-centered {Mn₃} trinuclear and six {Co₂} dinuclear moieties acting as nodes and linkers, respectively. The paramagnetic properties of this compound observed down to 1.8 K result from the competition of Mn...Mn, Mn...Co and Co...Co interactions in combination with spin-orbit coupling and single-ion behavior of the Co(II) centers.

High-nuclearity complexes of paramagnetic 3d metal ions attract significant interests due to their intriguing geometrical characteristics (large size, high symmetry, aesthetically pleasing shapes and architectures) and fascinating physical properties.¹ As a subgroup of these complexes, polynuclear wheels have been extensively studied for their single-molecule magnet (SMM) properties (induced by the combination of their large spin ground state and an easy-axis magnetic anisotropy)^{1a, 1e, 2} but also as model systems for spin frustration and quantum effects or as candidates for quantum-information processing (QIP).³ In particular antiferromagnetically coupled heterometallic wheels (AF-wheels) have recently focused attention due to their potential non-diamagnetic ground state that could be used as “qubit” in QIP devices.⁴ For example, Winpenny et al have reported {Cr₇M} heterometallic AF-wheels for a coherent manipulation of the electron spin.⁵ Another crucial consideration for carrying out future quantum computation with these types of complexes is the control of the exchange interactions between these wheels, which depends partially

on the nature of their connectivity. Therefore coordination networks of heterometallic AF-wheel units may be nice systems to probe the effects of the inter-molecular interactions on the intrinsic properties of these complexes. The majority of the reported heterometallic wheels are discrete and small species,⁶ and only a few wheel-based coordination networks have been documented so far.⁷ No obvious and definite strategy has been established to synthesize these extended coordination architectures, and most of the approaches rely on serendipity. Therefore the synthesis of these polynuclear wheels and their derivative coordination networks remains a great synthetic challenge.

Serendipitous self-assembly is a well-used “bottom up” approach for elaborating coordination architectures, which often gives unexpected and exciting results.⁸ In this self-assembly approach, the key step is always the judicious selection of the organic ligand to stabilize polynuclear wheels^{1g, 2c, 9} and even in some cases wheel-based coordination networks.^{7f, 7g, 7h, 10} In most of the examples, the bridging ligands possess N and/or O donor atoms,^{1a, 5b, 7g, 7h, 11} and alkali metal ions assist the assembling of the wheels, which can also be considered as coordinating metallocrowns.^{7h, 12} Herein we report a unprecedented trimetallic two-dimensional coordination network, Na[Co₂(Mn₃O)(pic)₆(N₃)₂(NO₃)₂] (**1**), which consists of fused hexagonal triacontanuclear heterometallic [Co₂(Mn₃O)(N₃)₂(pic)₆(NO₃)₂]₆ wheels of 3.4 nm separated by interlayer Na ions. The elementary building units are oxo-centered {Mn₃} trinuclear and {Co₂} dinuclear moieties, which are further assembled by picolinate ligands to create calixarene-like hydrophilic sites occupied by the sodium cations. Interestingly, this compound can be viewed as a coordination assembly of the so-far largest cobalt-manganese wheel.

Compound **1** was solvothermally obtained as single-crystals in a 12-ml Teflon-lined stainless steel container in high yield (ca. 76%) by treatment of a mixture of Co(NO₃)₂, Mn(CH₃COO)₂, picolinic acid and NaN₃ in ethanol at 140 °C. It is worth mentioning that similar reactions by using a single transition metal precursor were unsuccessful. The purity of **1** was confirmed by elemental analysis, infra-red spectroscopy as well as by powder X-ray diffraction pattern (Figure S1). Single-crystal X-ray diffraction analysis reveals that **1** crystallizes in the $R\bar{3}$ trigonal space group and the asymmetric unit contains only one Co, one Mn, one Na, one μ_3 -O, an azido anion, two pic⁻ ligands and two nitrate groups (Figure S2). The Na cation and two nitrates are located on a threefold axis, which implies

^a School of chemistry & Material Science, Shanxi Normal University, Linfen, 041004, P. R. China. Fax & Tel : Int. code +86 357 2051402; E-mail: zhangxm@dns.sxnu.edu.cn

^b CNRS, CRPP, UPR 8641, F-33600 Pessac (France) Tel (+33) 5 56 84 56 50. Fax: (+33) 5 56 84 56 00; E-mail: clerac@crpp-bordeaux.cnrs.fr

^c Univ. Bordeaux, CRPP, UPR 8641, F-33600 Pessac (France).

† Electronic supplementary information (ESI) available: Additional crystallographic and magnetic data. CCDC 1014152. For ESI and crystallographic data in CIF or other electronic format see DOI: 10.1039/c0cc00000x

disordered nitrate anions. The Co(II) site possesses a distorted octahedral coordination sphere occupied by two azido groups in *cis* positions, two N and two O atoms from two N,O-chelating picolinate ligands. The Co-X (X = O,N) bond lengths fall between 2.058(6) and 2.173(7) Å with an average Co-X distance of 2.110 Å. Two {Co(pic)₂} moieties are connected by a double μ_{1,1}-azido bridge to form the dinuclear [Co₂(pic)₄(N₃)₂]²⁻ unit with short Co...Co distance of 3.159 Å (Figure 1a). The Mn(II) site adopts a strongly distorted octahedral geometry, coordinated by three carboxylate O atoms, one nitrate O atom, one μ₃-O and one azido anion. The Mn-O bond lengths are in the 2.147-2.251 Å range. The coordinating N atom from the azido anion is only weakly interacted with the Mn metal ion with a long Mn-N distance of 2.485 Å. The average Mn-X

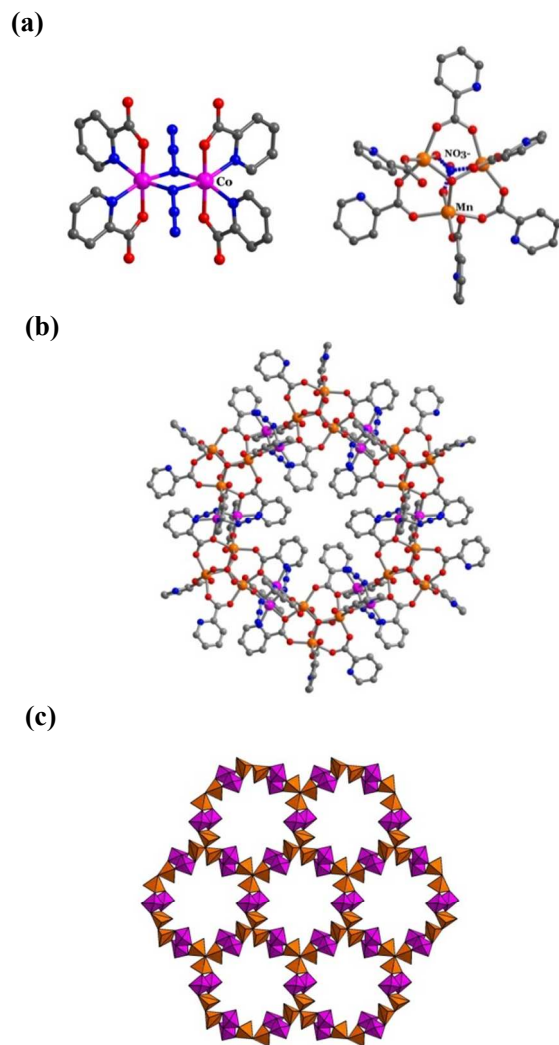


Fig 1. (a) Ball and stick view of the [Co₂(pic)₄(N₃)₂]²⁻ and [Mn₃O(pic)₆(NO₃)₃]³⁻ units in **1**; (b) View of triacontanuclear heterometallic [Co₂(Mn₃O)(pic)₆(NO₃)₆]₆ wheel motif observed in **1** with a dimension of 3.2 × 0.8 nm and an hydrophobic inner diameter of 0.6 nm; (c) Polyhedral-type view of the hexagonal network of [Co₂Mn₂]₆ icositetranuclear rings. The Co and Mn polyhedra are shown in purple and brown colors, respectively. Color code: Co purple, Mn orange, Na dark green, O red, N blue, C grey. Hydrogen atoms have been omitted for clarity.

bond length is thus relatively large at 2.249 Å. In agreement with the d⁵ and d⁷ electronic configuration of the Mn(II) and Co(II) metal ions and their usual coordination radius, the average Mn-X

is larger than the Co-X one. In addition, the coexistence of Mn(II) and Co(II) metal ions in **1** was also confirmed by EDS (Figure S3) and supported by magnetic measurements (vide infra). Meanwhile, the +2 oxidation state of the Mn ion was determined by bond-valence sum (BVS) calculation (Table S3),¹³ charge-balance consideration and inspection of coordination sphere.^{2b, 14} Three Mn metal ions and six picolinate ligands assemble around a central μ₃-O atom to form a 3-fold oxo-centered [Mn₃O(pic)₆]²⁻ unit with a unique Mn...Mn distance of 3.587 Å (Figure 1a). This [Mn₃O(pic)₆]²⁻ moiety has in the same time available coordination sites occupied by one nitrate ion and oxygen donor atoms (from the picolinate ligands), which coordinate a sodium cation capped by an additional nitrate. The NO₃⁻ and Na(O₃N) groups are lying on each side of the [Mn₃O(pic)₆]²⁻ moiety along the three-fold axis to form a [NaMn₃O(pic)₆(NO₃)₂]³⁻ unit shown in Figure S4. Each [NaMn₃O(pic)₆(NO₃)₂]³⁻ unit is linked to three [Co₂(pic)₄(N₃)₂]²⁻ moieties *via* sharing oxygen atoms of picolinate ligands to form a two-dimensional neutral honeycomb coordination network, Na[Co₂(Mn₃O)(pic)₆(N₃)₃(NO₃)₂], that can be seen as resulting from the fusion of triacontanuclear heterometallic [Co₂(Mn₃O)(N₃)₂(pic)₆(NO₃)₃]₆ wheels (Figure 1b and S5). Each wheel unit has a dimension of 3.2 × 0.8 nm and a hydrophobic inner diameter of 0.6 nm. This 2-D network can also be described as inorganic hexagonal layer of {Co₂Mn₂}₆ icositetranuclear rings (Figure 1c) with picolinate ligands projecting inward the ring motifs as well as on both sides of the inorganic sheet. The center of each [Co₂Mn₂]₆ icositetranuclear ring is occupied by six picolinate ligands to create a small hydrophobic central cavity. More interestingly, the three interlayer pic⁻ groups in combination with [Mn₃O]⁴⁺ units create multiple calixarene-like hydrophilic cavities (Figure S6) pointing on both side of the sheets. The three carboxylate oxygen atoms from these cavities form an equilateral triangle with O...O distance of 3.26 Å, which chelate a Na⁺ ion. Due to the smaller O...O distance, the Na⁺ site is non-coplanar with the three oxygen atoms and is lying above the mean oxygen plane at 1.106 Å.^{7b}

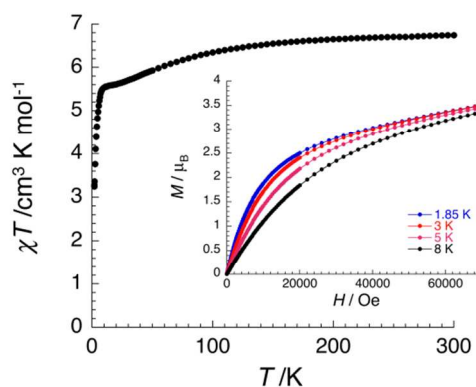


Fig 2. Temperature dependence of χT product at 1000 Oe (where χ is the molar magnetic susceptibility equal to the ratio between the magnetization and the applied magnetic field, M/H , per mole of {CoMn} pair) between 1.85 and 300 K for a polycrystalline sample of **1**. Inset: M vs H plot for **1** between 1.85 and 8 K at magnetic fields between 0 and 7 T with sweep-rates of 100 – 200 Oe/min. The solid line is a guide for eyes.

The magnetic susceptibility measurements of **1** were performed between 1.85 and 300 K (Figure 2). At room temperature, the χT product is 6.7 cm³K/mol, which is in good agreement with the presence of one Mn^{II} ($C = 4.375$ cm³K/mol) and one Co^{II} ($S = 3/2$, $C = 2.325$ cm³K/mol and $g = 2.22$) metal ions.¹⁵ Upon decreasing the temperature, the χT product decreases gradually until 10 K and then declines more rapidly at low temperatures to reach 3.2 cm³K/mol at 1.85 K. The complicated nature of the 2-D coordination network, the

many different magnetic pathways between Mn^{II} and Co^{II} magnetic centers and also the intrinsic Co^{II} paramagnetism (strongly influenced by strong spin-orbit coupling) preclude a detailed analysis of the magnetic properties and thus the development of a convincing magnetic model. Nevertheless, the nonzero plateau (residual paramagnetism) observed around 10 K in the χT vs. T data (Figure 2) is clearly highlighting the non-compensation of the magnetic centers for the 2-D coordination network.^{5b, 16} The field dependence of magnetization measured below 8 K (Figures 3 and S7) is also informative. The increase of the magnetization at high field without clear saturation, even at 1.8 K and under 7 T, confirms the expected presence of the Co^{II} magnetic anisotropy^{1b, 10a, 16} and the possible influence of low-lying excited states induced by weak antiferromagnetic interactions. It is also worth mentioning that the 1.85 K magnetization reaches 3.5 μ_B at the highest field of 7 T, that is far below to the expected saturation value for one Co^{II} and one Mn^{II} metal ions revealing the presence of operative antiferromagnetic interactions in the material. Even if the M vs H data do not exhibit any hysteresis effect (at the field sweep-rates of 50-400 Oe/min used in commercial magnetometers), the magnetization dynamics for **1** has been also investigated by ac susceptibility measurements (Figure S8). In our temperature (1.8-300 K) and ac frequency (0.1-10000 Hz) experimental windows, it was impossible to detect a significant out of phase ac signal, excluding the possibility of any magnet-type behavior in this system.

In summary, an unprecedented two-dimensional honeycomb paramagnetic network based on fused triacontanuclear heterometallic nanometric wheels, [Co₂(Mn₃O)(N₃)₂(pic)₆(NO₃)₆]⁻⁶, has been successfully synthesized and structurally characterized. The oxo-centered {Mn₃} trinuclear and {Co₂} dinuclear units are respectively located at the corners and edges of these hexagonal wheels. Importantly, the successful synthesis of **1** not only confirms the feasibility of synthesizing novel multimetallic complexes through a judicious choice of appropriate ligands and different metal ions but also provides an interesting strategy to develop the synthesis of wheel-based systems for potential QIP applications. In addition, the calixarene-like hydrophilic active sites could be potentially used for ion recognition or exchange. Therefore, synthetic strategies to selectively substitute the Na⁺ ions but also the Co²⁺ and/or Mn²⁺ metal ions with other species are currently underway in our laboratory.

This work was supported by National Basic Research Program of China (973 Program 2012CB821701), IRT1156, National Science Fund for Distinguished Young Scholars (20925101), the University of Bordeaux, the Région Aquitaine and the CNRS.

Notes and references


† Synthesis of Na[Co₂(Mn₃O)(pic)₆(N₃)₂(NO₃)₆] (**1**). A suspension of Co(NO₃)₂·3H₂O (0.163 g, 0.56 mmol), Mn(CH₃COO)₂ (0.100 g, 0.54 mmol), picolinic acid (0.086 g, 0.7 mmol), NaN₃ (0.052 g, 0.8 mmol) in ethanol (5 ml) was sealed in a 12 ml Teflon-lined stainless steel container that was heated to 140 °C and held at this temperature for 96 hours. After cooling to room temperature, red columnar single crystals of **1** (76 %) were obtained. Elemental analysis (%). Anal. Calcd for C₃₆H₂₄Co₂Mn₃N₁₇NaO₁₉: C, 31.76; H, 1.77; N, 17.46. Found: C, 31.88; H, 1.53; N, 17.53. IR (KBr): 3433s, 2029m, 1639s, 1377s, 1124w, 1038w, 837w, 761w, 700w.

‡ Crystal data for **1**: C₃₆H₂₄Co₂Mn₃N₁₇NaO₁₉, Trigonal, space group $R\bar{3}$, $a = 17.343(7)$, $c = 31.6652(19)$ Å, $V = 8248.2(7)$ Å³, $T = 293(2)$ K, $Z = 6$, $\rho = 1.714$ g cm⁻³, ($R_{\text{int}} = 0.0329$), $R_1 = 0.0883$, $wR_2 = 0.2323$ (for $I > 2\sigma(I)$), GOF = 1.064).

- (a) A. J. Tasiopoulos, A. Vinslava, W. Wernsdorfer, K. A. Abboud and G. Christou, *Angew. Chem., Int. Ed.*, 2004, **43**, 2117; (b) P. Alborés and E. Rentschler, *Angew. Chem., Int. Ed.*, 2009, **48**, 9366; (c) T. Liu, Y.-J. Zhang, Z.-M. Wang and S. Gao, *J. Am. Chem. Soc.*, 2008, **130**, 10500; (d) D. Fenske, J. Ohmer and J. Hachgenei, *Angew. Chem. Int. Ed. Engl.*, 1985, **24**, 993; (e) M. Murugesu, M. Habrych, W. Wernsdorfer, K. A. Abboud and G. Christou, *J. Am. Chem. Soc.*, 2004, **126**, 4766; (f) Z.-M. Zhang, Y.-G. Li, S. Yao, E.-B. Wang, Y.-H. Wang and R. Clérac, *Angew. Chem., Int. Ed.*, 2009, **48**, 1581; (g) S.-T. Zheng, T. Wu, B. Irfanoglu, F. Zuo, P. Feng and X. Bu, *Angew. Chem., Int. Ed.*, 2011, **50**, 8034; (h) C.-M. Liu, D.-Q. Zhang, X. Hao and D.-B. Zhu, *Chem. Eur. J.*, 2011, **17**, 12285; (i) M. Murugesu, R. Clérac, C. E. Anson and A. K. Powell, *Inorg. Chem.*, 2004, **43**, 7269; (j) Z.-M. Zhang, S. Yao, Y.-G. Li, R. Clérac, Y. Lu, Z.-M. Su and E.-B. Wang, *J. Am. Chem. Soc.*, 2009, **131**, 14600.
- (a) E. M. Rumberger, S. J. Shah, C. C. Beedle, L. N. Zakharov, A. L. Rheingold and D. N. Hendrickson, *Inorg. Chem.*, 2005, **44**, 2742; (b) M. Manoli, R. Inglis, M. J. Manos, V. Nastopoulos, W. Wernsdorfer, E. K. Brechin and A. J. Tasiopoulos, *Angew. Chem., Int. Ed.*, 2011, **50**, 4441; (c) R. W. Saalfrank, A. Scheurer, R. Prakash, F. W. Heinemann, T. Nakajima, F. Hampel, R. Leppin, B. Pilawa, H. Rupp and P. Müller, *Inorg. Chem.*, 2007, **46**, 1586; (d) S. Koizumi, M. Nihei, M. Nakano and H. Oshio, *Inorg. Chem.*, 2005, **44**, 1208; (e) M. Murugesu, J. Raftery, W. Wernsdorfer, G. Christou and E. K. Brechin, *Inorg. Chem.*, 2004, **43**, 4203.
- (a) M. N. Leuenberger and D. Loss, *Nature*, 2001, **410**, 789; (b) G. A. Timco, E. J. L. McInnes and R. E. P. Winpenny, *Chem. Soc. Rev.*, 2013, **42**, 1796; (c) F. Troiani and M. Affronte, *Chem. Soc. Rev.*, 2011, **40**, 3119.
- (a) V. Bellini and M. Affronte, *J. Phys. Chem. B*, 2010, **114**, 14797; (b) G. A. Timco, T. B. Faust, F. Tuna and R. E. P. Winpenny, *Chem. Soc. Rev.*, 2011, **40**, 3067.
- (a) M. Affronte, S. Carretta, G. A. Timco and R. E. P. Winpenny, *Chem. Commun.*, 2007, 1789; (b) F. K. Larsen, E. J. L. McInnes, H. El Mkami, J. Overgaard, S. Piligkos, G. Rajaraman, E. Rentschler, A. A. Smith, G. M. Smith, V. Boote, M. Jennings, G. A. Timco and R. E. P. Winpenny, *Angew. Chem., Int. Ed.*, 2003, **42**, 101.
- (a) V. V. Semenaka, O. V. Nesterova, V. N. Kokozay, R. I. Zibatyuk, O. V. Shishkin, R. Boca, D. V. Shevchenko, P. Huang and S. Styring, *Dalton Trans.*, 2010, **39**, 2344; (b) T. Guidi, J. R. D. Copley, Y. Qiu, S. Carretta, P. Santini, G. Amoretti, G. Timco, R. E. P. Winpenny, C. L. Dennis and R. Caciuffo, *Phys. Rev. B*, 2007, **75**, 014408; (c) C. Plenk, T. Weyhermuller and E. Rentschler, *Chem. Commun.*, 2014, **50**, 3871; (d) X. Y. Chen, Y. Bretonniere, J. Pecaut, D. Imbert, J. C. Bunzli and M. Mazzanti, *Inorg. Chem.*, 2007, **46**, 625; (e) R. W. Saalfrank, R. Prakash, H. Maid, F. Hampel, F. W. Heinemann, A. X. Trautwein and L. H. Bottger, *Chem. Eur. J.*, 2006, **12**, 2428; (f) Z.-M. Zhang, L.-Y. Pan, W.-Q. Lin, J.-D. Leng, F.-S. Guo, Y.-C. Chen, J.-L. Liu and M.-L. Tong, *Chem. Commun.*, 2013, **49**, 8081; (g) O. Cador, D. Gatteschi, R. Sessoli, F. K. Larsen, J. Overgaard, A.-L. Barra, S. J. Teat, G. A. Timco and R. E. P. Winpenny, *Angew. Chem., Int. Ed.*, 2004, **43**, 5196; (h) X.-Y. Wang, A. V. Prosvirin and K. R. Dunbar, *Angew. Chem., Int. Ed.*, 2010, **49**, 5081; (i) K. Mitsumoto, M. Nihei, T. Shiga and H. Oshio, *Chem Lett*, 2008, **37**, 966.
- (a) G. A. Timco, E. J. L. McInnes, R. G. Pritchard, F. Tuna and R. E. P. Winpenny, *Angew. Chem., Int. Ed.*, 2008, **47**, 9681; (b) W.-H.

- Fang, J.-W. Cheng and G.-Y. Yang, *Chem. Eur. J.*, 2014, **20**, 2704;
- (c) R. W. Saalfrank, H. Maid and A. Scheurer, *Angew. Chem., Int. Ed.*, 2008, **47**, 8794; (d) J. W. Cheng, J. Zhang, S. T. Zheng and G. Y. Yang, *Chem. Eur. J.*, 2008, **14**, 88; (e) Z.-H. Ni, L.-F. Zhang, V. Tangoulis, W. Wernsdorfer, A.-L. Cui, O. Sato and H.-Z. Kou, *Inorg. Chem.*, 2007, **46**, 6029; (f) X. J. Gu and D. F. Xue, *Inorg. Chem.*, 2007, **46**, 5349; (g) C. du Peloux, A. Dolbecq, P. Mialane, J. Marrot, E. Rivière and F. Sécheresse, *Angew. Chem., Int. Ed.*, 2001, **40**, 2455; (h) C. du Peloux, A. Dolbecq, P. Mialane, J. Marrot, E. Rivière and F. Sécheresse, *Inorg. Chem.*, 2002, **41**, 7100.
- 8 M. Fujita, *Chem. Soc. Rev.*, 1998, **27**, 417.
- 9 (a) J. A. Hoshiko, G. Wang, J. W. Ziller, G. T. Yee and A. F. Heyduk, *Dalton Trans.*, 2008, 5712; (b) S. Sanz, J. M. Frost, T. Rajeshkumar, S. J. Dalgarno, G. Rajaraman, W. Wernsdorfer, J. Schnack, P. J. Lusby and E. K. Brechin, *Chem. Eur. J.*, 2014, **20**, 3010; (c) M. M. Ali and F. M. MacDonnell, *J. Am. Chem. Soc.*, 2000, **122**, 11527; (d) H. N. Miras, I. Chakraborty and R. G. Raptis, *Chem. Commun.*, 2010, **46**, 2569.
- 10 (a) J. Li, J. Tao, R.-B. Huang and L.-S. Zheng, *Inorg. Chem.*, 2012, **51**, 5988; (b) C.-Z. Ruan, R. Wen, M.-X. Liang, X.-J. Kong, Y.-P. Ren, L.-S. Long, R.-B. Huang and L.-S. Zheng, *Inorg. Chem.*, 2012, **51**, 7587; (c) S.-D. Han, W.-C. Song, J.-P. Zhao, Q. Yang, S.-J. Liu, Y. Li and X.-H. Bu, *Chem. Commun.*, 2013, **49**, 871.
- 11 (a) T. Nakajima, K. Seto, F. Horikawa, I. Shimizu, A. Scheurer, B. Kure, T. Kajiwara, T. Tanase and M. Mikuriya, *Inorg. Chem.*, 2012, **51**, 12503; (b) Y. Thio, S. W. Toh, F. Xue and J. J. Vittal, *Dalton Trans.*, 2014, **43**, 5998; (c) A. Mueller, E. Krickemeyer, J. Meyer, H. Boegge, F. Peters, W. Plass, E. Diemann, S. Dillinger, F. Nonnenbruch, M. Randerath and C. Menke, *Angew. Chem. Int. Ed. Engl.*, 1995, **34**, 2122; (d) E. Cadot, A. Dolbecq, B. Salignac and F. Sécheresse, *J. Phys. Chem. Solids*, 2001, **62**, 1533.
- 12 T. B. Faust, P. G. Heath, C. A. Muryn, G. A. Timco and R. E. P. Winpenny, *Chem. Commun.*, 2010, **46**, 6258.
- 13 W. Liu and H. H. Thorp, *Inorg. Chem.*, 1993, **32**, 4102.
- 14 S. Zartilas, C. Papatriantafyllopoulou, T. C. Stamatatos, V. Nastopoulos, E. Cremades, E. Ruiz, G. Christou, C. Lampropoulos and A. J. Tasiopoulos, *Inorg. Chem.*, 2013, **52**, 12070.
- 15 R. Carlin, in *Magnetochemistry*, Springer Berlin Heidelberg, 1986, pp. 65-67.
- 16 Z.-G. Gu and S. C. Sevov, *Inorg. Chem.*, 2009, **48**, 8066.

Table of Contents

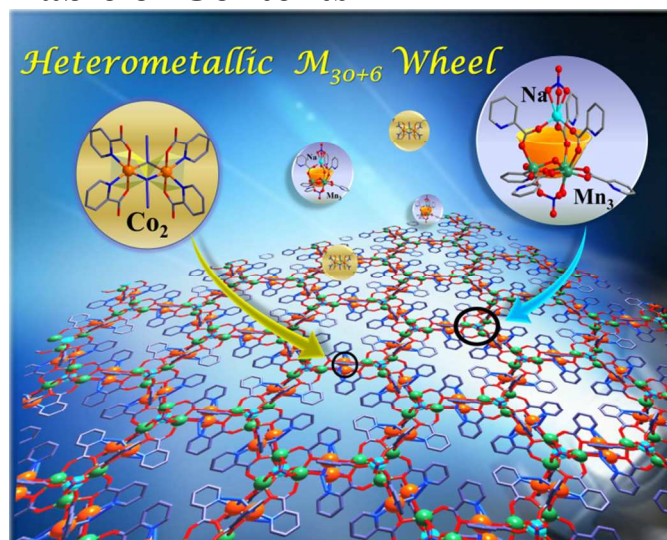

An unprecedented two-dimensional honeycomb paramagnetic network based on fused triacontanuclear heterometallic wheels of 3.4 nm, $[\text{Co}_2(\text{Mn}_3\text{O})(\text{N}_3)_2(\text{pic})_6(\text{NO}_3)]_6$ has been assembled. The hexagonal $\{\text{Co}_{12}\text{Mn}_{18}\}$ wheel motif is composed of six oxo-centered $\{\text{Mn}_3\}$ trinuclear and six $\{\text{Co}_2\}$ dinuclear moieties acting as nodes and linkers, respectively.