

ChemComm

Accepted Manuscript



This is an *Accepted Manuscript*, which has been through the Royal Society of Chemistry peer review process and has been accepted for publication.

Accepted Manuscripts are published online shortly after acceptance, before technical editing, formatting and proof reading. Using this free service, authors can make their results available to the community, in citable form, before we publish the edited article. We will replace this *Accepted Manuscript* with the edited and formatted *Advance Article* as soon as it is available.

You can find more information about *Accepted Manuscripts* in the [Information for Authors](#).

Please note that technical editing may introduce minor changes to the text and/or graphics, which may alter content. The journal's standard [Terms & Conditions](#) and the [Ethical guidelines](#) still apply. In no event shall the Royal Society of Chemistry be held responsible for any errors or omissions in this *Accepted Manuscript* or any consequences arising from the use of any information it contains.

COMMUNICATION

A Low Molecular Weight Hydrogel with Unusual Gel Aging

Cite this: DOI: 10.1039/x0xx00000x

Emily R. Draper,^a Tom O. McDonald^a and Dave J. Adams^{a*}Received 00th January 2012,
Accepted 00th January 2012

DOI: 10.1039/x0xx00000x

www.rsc.org/

We describe a dipeptide hydrogel with unusual aging characteristics. Over time, a transformation from a turbid gel to a transparent gel occurs which is initiated from the air-water interface. Here, we investigate this transition and discuss the implications of this aging on the bulk properties of the gel.

The self-assembly of low molecular weight gelators (LMWGs) is a useful method to produce well-defined materials with many potential applications, including tissue engineering, drug delivery and organic electronics.¹⁻⁴ Gelation generally occurs when a trigger is applied to a freely dissolved LMWG, leading to the assembly of the molecules into long fibrous structures that then entangle and trap the solvent, forming a gel. These LMWGs are of interest due to the large variety of gelator structures reported, as well as being relatively cheap to produce and simple to scale up.

Generally, the aging of these gels is rarely discussed in the literature. The properties of gels are often reported without stating the age of the material, despite there being examples in the literature showing that gel network formation is not necessarily the thermodynamic minimum.⁵⁻⁸ For example, Smith and Yu have both reported gel systems that show gel-to-crystal transitions over time,^{9, 10} which are attributed to gel formation being a balance between amorphous aggregation and well-ordered crystallisation. In general, gelation is described as the kinetically controlled process, whereas with time the more thermodynamically stable crystallization occurs. This type of gel aging leads to the deformation or weakening of rheological properties of the gel due to disruption of the gel matrix. Other examples of gel aging show Ostwald ripening, where smaller structures fuse together to form larger, more stable structures.¹¹⁻¹⁴ Additional LMWGs have been shown to form aggregates when gelation is triggered. Over time these aggregates rearrange or 'self-correct' to form a more stable and

homogeneous network.¹⁵⁻¹⁷ These gel-to-gel transitions often lead to gels with increased rheological strength. Changes in the gel network may not be a visible process yet could affect the gel properties with time. The stability of gels is important when considering the material for a specific application.¹⁸ Monitoring the aging of gels may also offer insight into gel network formation.¹⁹ Here we report a LMWG that has extremely unusual aging properties caused by a gel-to-gel transition.

A solution of the LMWG, 2-thiophene diphenylalanine (Fig. 1a), was dissolved in deionised water at pH 11 using sodium hydroxide to give a transparent solution (Fig. 1b). Glucono- δ -lactone (GdL) was then used to lower the pH slowly and trigger gelation.^{20, 21} We have previously shown that this method allows the formation of uniform gels, and the slow hydrolysis allows the assembly process to be followed.^{20, 22} After one hour, the initially transparent solution became turbid. After six hours, an opaque self-supporting gel was formed (Fig. 1c). Unusually, the gel then started to become transparent, starting from the air-water interface (Fig. 1d) and was completely transparent after three days (Fig. 1e).

The transparent, aged gel showed significantly stronger rheological properties than the turbid gel (Fig. S1, ESI). Scanning electron microscope (SEM) images showed that the turbid gel contained spherical structures of around 1 μm in diameter (Fig. 2a and 2b), whereas the transparent gel showed a continuous network of fibres (Fig. 2c and 2d). The decrease in size of structures accounts for the change in turbidity, with the larger structures scattering more light. The spherical structures appear to be formed from bundles of fibres, but it is also possible that these fibres could have been formed as the gel dried. Imaging of the gels using an optical microscope shows that these spherical structures are present in the hydrated gel, but there is insufficient resolution to detect the fibrous structures (Fig. S2, ESI). This apparent change in microstructure is highly unusual as there are very few gel-to-gel

transitions reported. Furthermore, the change from larger to smaller structures would seem to be energetically unfavourable.

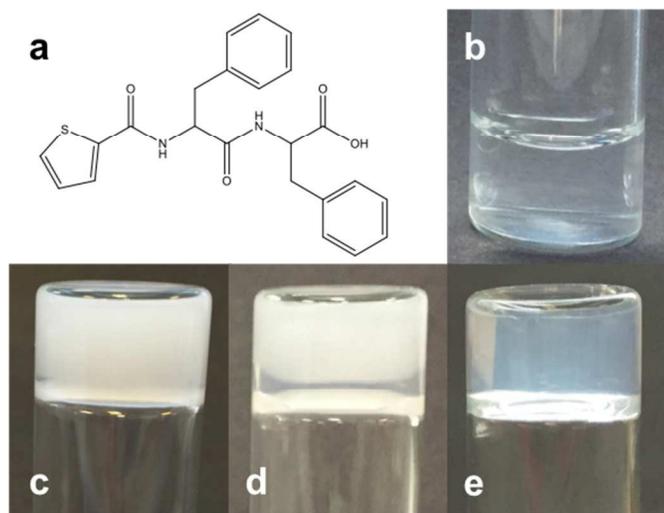


Figure 1 (a) Structure of the LMWG, 2-thiophene diphenylalanine. (b) LMWG in high pH water. (c) Turbid gel formed after 8 hours. (d) The gel becoming transparent after 16 hours. (e) A completely transparent gel is formed after 3 days.

The evolution of the gel network was monitored after the addition of GdL by measuring the rheological properties, the change in turbidity and by recording the pH over time (Fig. 3). The change in turbidity (strictly we have measured the change in absorbance at 600 nm as a proxy for turbidity) after an hour indicates that self-assembly began before the pH had reached the apparent pK_a of the molecule (the apparent pK_a was determined from the plateau in the pH titration data as we have described elsewhere²³). For related LMWGs, we have shown that assembly occurs at the apparent pK_a of the gelator, with gelation generally beginning at a pH at or just below this pK_a .²²⁻²⁴

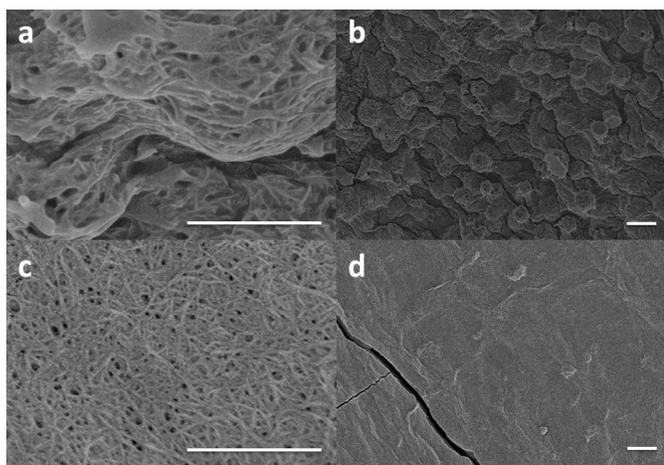


Figure 2. (a) and (b) SEM images of the turbid gel. (c) and (d) SEM images of the transparent gel. In (a) and (c), the scale bar represents 1 μm . In (b) and (d) the scale bar represents 2 μm .

Here, the increase in turbidity occurred before any gelation occurred, as shown by the rheological data (Fig. 3). As expected from our previous work, the storage modulus (G') and the loss modulus (G'') began to increase at the apparent pK_a .²³ The gel developed by a two-stage process as we have observed many times before.^{23, 25} Interestingly however, the gel became transparent after the pH had equilibrated, and the rheological properties continued to increase over an extended period. These results suggest that the changes observed in the gel network at longer times are not simply a result of changes in the pH of the bulk gel.

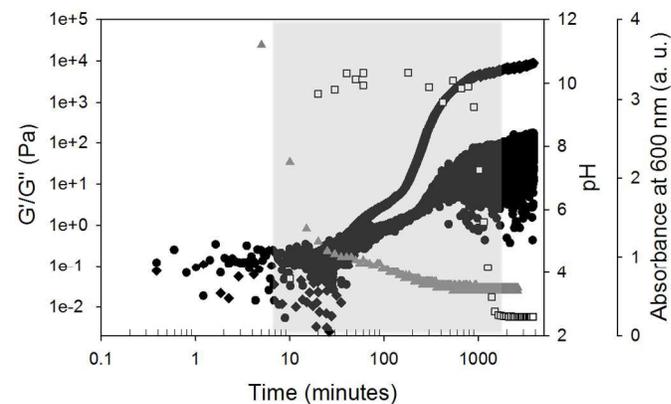


Figure 3. Graph showing the evolution of the gel network. The circles represent the storage modulus, diamonds represent the loss modulus. pH is represented by grey triangles. The change in absorbance at 600 nm (turbidity) is represented by open squares. The grey area indicates that the solution or gel is optically turbid.

The higher the surface area of the air-water interface, the quicker the gel became transparent (Fig. S3, ESI). Additionally, the rate of change was affected by the concentration of gelator used (Fig. S4, ESI). This suggests that the change in gel structure is influenced by air, presumably due to an atmospheric gas such as carbon dioxide or oxygen. This was further confirmed by degassing a solution of gelator and adding it to a pre-weighed amount of GdL under a nitrogen atmosphere. The gel still underwent a turbid to transparent transition, but it took much longer for the gel to become completely transparent compared to a gelation exposed to air (Fig. S5 and S6, ESI). For these experiments in a sample tubes and cuvettes suitable for our forms of analysis, complete sealing and exclusion of atmospheric gases was difficult. When we carried out the gelation under strict conditions, no decrease in turbidity was observed over 4 days (Fig. S7, ESI).

The same process was then carried out under an enriched carbon dioxide atmosphere. This gel showed a much quicker change from turbid to transparent compared to the gel exposed to air (Fig. S8, ESI). This indicates that the gel aging is influenced by the diffusion of CO_2 into the solution, presumably forming carbonates. This carbonate formation could either subtly change the pH, which could cause a rearrangement in the gel network, or the carbonate may change the salt concentration, which could also cause a change within the gel structure. To see whether a local pH change was causing

the transition, an acid-sensitive pH indicator, bromophenol blue, was added during the gelling process. The pH indicator showed no difference in pH at both the transparent and turbid part of the gel (Fig. S9, ESI). To investigate whether carbonate concentration was the cause of the gel aging, the gelator was dissolved at high pH using potassium carbonate instead of sodium hydroxide and again gelled with GdL. The gel went through the same turbidity and gelation process as with the sodium hydroxide, however the length of time the gel was in the turbid phase was much shorter (Fig. S10 and Fig. S11, ESI). The pH change and rheology of this gel was also recorded and showed similar observations to the sodium hydroxide prepared gels (Fig. S12, ESI). Self-assembly took longer to begin due to a slower drop in pH resulting from the use potassium carbonate (as expected, the rate of GdL hydrolysis is dependent on the salt concentration).²¹ To rule out a cation effect, the gelation was carried out using potassium hydroxide to dissolve the LMWG. Here, the rheological and turbidity data matched that for sodium hydroxide, showing that the differences are due to the carbonate rather than the potassium ions (Fig. S13, ESI). Preparing gelator solutions with potassium bicarbonate again resulted in an increase in the rate at which the gel changed from turbid to transparent compared to the solutions prepared with sodium hydroxide.

This LMWG therefore shows an extremely unusual aging profile. As noted above, discussion of aging of such gels is rarely discussed. Shi *et al.* observed a phenylalanine based gelator that underwent a turbid to transparent transition.¹⁶ This transition was attributed to a reversible molecular rearrangement of the gelator molecules. Considering the hydrophobicity of the LMWG used here, we expect that the solubility in water is very low at the final pH of the gel. Hence, it is unlikely that the gel is changing due to dissolution of the LMWG. Instead, we hypothesise that subtle re-arrangements are occurring that lead to the transition from the turbid gel to the transparent gel. Also, after freeze-drying and dissolving in deuterated DMSO, the NMR spectrum of both the turbid and transparent gels showed no change to the gelator (Fig. S14 and S15, ESI), as did mass spectrometry (Fig. S16 and S17, ESI). Infrared spectroscopy of the turbid and transparent gels also showed no change in packing on the molecular level (Fig. S18, ESI) suggesting any transition observed in the gel must be due to a purely morphological rearrangement of the fibres and not a chemical change on the molecular scale.

Perhaps the closest comparison to our system is that reported by Mallia *et al.*, where opaque to transparent gel-to-gel transitions were observed for CCl₄ organogels.²⁶ The transitions were ascribed to the reversible inclusion of further solvent molecules between the fibres, resulting in a decrease in turbidity, as the opaque gels were heated. Another example of an opaque to transparent transition was shown by Saha *et al.* this process was reversible with heat cycling but the opaque gel showed weaker rheological properties than the transparent gel.²⁷ A number of LMWG are known to be salt sensitive. For example, Nebot *et al.* have shown that there can be changes in turbidity when specific anions are added to the top of pre-

formed gels, which was related to changes in the solubility of the LMWG *via* the Hofmeister series,²⁸ which again could lead to changes in the hydrophilicity of the gelator and hence the amount of included / bound water. We hypothesise that the addition of carbonate affects the hydrophilicity of the fibres, reducing the inter-fibre interactions and changing the amount of bound water molecules. This leads to a reduction in the highly scattering aggregated fibres and hence a reduction in turbidity.

In summary, the change in turbidity for the gels reported here appear to be driven by a rearrangement of fibres in the gel from large spherical structures to randomly orientated fibrous network. This gel-to-gel transition occurs due to an increased carbonate concentration as a result of CO₂ in the air dissolving into solution. This rate of process could be increased by adding carbonate into the solution prior to gelation. We stress that this is very different to the CO₂-triggered gelation reported elsewhere,²⁹ since gelation occurs under nitrogen; rather it is the gel-to-gel transition that seems to be triggered by the presence of carbonate. These results highlight the importance in gel aging for such systems. Other systems may also go through less visually obvious gel-to-gel transitions that may affect the properties of the gel, something which is important when gels are used for specific applications.

Acknowledgements

ED thanks the EPSRC for a DTA studentship. DA thanks the EPSRC for a Fellowship (EP/L021978/1).

Notes and references

^a Department of Chemistry, University of Liverpool, Crown Street, Liverpool, L69 7ZD, UK. E-mail: d.j.adams@liverpool.ac.uk

Electronic Supplementary Information (ESI) available: Full synthetic details for the LMWG, photographs of gelation under different conditions, further rheological data. See DOI: 10.1039/c000000x/

1. K. J. Skilling, F. Citossi, T. D. Bradshaw, M. Ashford, B. Kellam and M. Marlow, *Soft Matter*, 2014, **10**, 237-256.
2. V. B. R. Prashant P. Kalshetti, Deepashree N. Dixit, Pranav P. Parekh, *Int. J. Pharm. Pharm. Sci.*, 2012, **4**, 1-7.
3. C. Yu, M. Xue, K. Liu, G. Wang and Y. Fang, *Langmuir*, 2014, **30**, 1257-1265.
4. D. Buenger, F. Topuz and J. Groll, *Prog. Polym. Sci.*, 2012, **37**, 1678-1719.
5. J. Cui, Z. Shen and X. Wan, *Langmuir*, 2009, **26**, 97-103.
6. K. A. Houton, K. L. Morris, L. Chen, M. Schmidtmann, J. T. A. Jones, L. C. Serpell, G. O. Lloyd and D. J. Adams, *Langmuir*, 2012, **28**, 9797-9806.
7. J. H. van Esch, *Langmuir*, 2009, **25**, 8392-8394.
8. J. Raeburn, A. Zamith Cardoso and D. J. Adams, *Chem. Soc. Rev.*, 2013, **42**, 5143-5156.
9. J. R. Moffat and D. K. Smith, *Chem. Commun.*, 2008, **29**, 2248-2250.
10. Y. Wang, L. Tang and J. Yu, *Cryst. Growth Des.*, 2008, **8**, 884-889.
11. L. Yan, Y. Xue, G. Gao, J. Lan, F. Yang, X. Su and J. You, *Chem. Eur. J.*, 2010, **16**, 2250-2257.
12. M. Lescanne, P. Grondin, A. d'Aléo, F. Fages, J. L. Pozzo, O. M. Monval, P. Reinheimer and A. Colin, *Langmuir*, 2004, **20**, 3032-3041.
13. S. A. Jamieson, K. W. K. Tong, W. A. Hamilton, L. He, M. James and P. Thordarson, *Langmuir*, 2014, **30**, 13987-13993.
14. R. G. Weiss, *J. Am. Chem. Soc.*, 2014, **136**, 7519-7530.

15. M. M. Smith and D. K. Smith, *Soft Matter*, 2011, **7**, 4856-4860.
16. J. Shi, Y. Gao, Z. Yang and B. Xu, *Beilstein J. Org. Chem.*, 2011, **7**, 167-172.
17. F. Rodriguez-Llansola, J. F. Miravet and B. Escuder, *Chem. Commun.*, 2009, **2**, 209-211.
18. C. Yan and D. J. Pochan, *Chem. Soc. Rev.*, 2010, **39**, 3528-3540.
19. A. Aufderhorst-Roberts, W. J. Frith, M. Kirkland and A. M. Donald, *Langmuir*, 2014, **30**, 4483-4492.
20. D. J. Adams, M. F. Butler, W. J. Frith, M. Kirkland, L. Mullen and P. Sanderson, *Soft Matter*, 2009, **5**, 1856-1862.
21. Y. Pocker and E. Green, *J. Am. Chem. Soc.*, 1973, **95**, 113-119.
22. L. Chen, S. Revel, K. Morris, L. C. Serpell and D. J. Adams, *Langmuir*, 2010, **26**, 13466-13471.
23. L. Chen, K. Morris, A. Laybourn, D. Elias, M. R. Hicks, A. Rodger, L. Serpell and D. J. Adams, *Langmuir*, 2009, **26**, 5232-5242.
24. K. L. Morris, L. Chen, J. Raeburn, O. R. Sellick, P. Cotanda, A. Paul, P. C. Griffiths, S. M. King, R. K. O'Reilly, L. C. Serpell and D. J. Adams, *Nat. Commun.*, 2013, **4**, 1480.
25. C. Colquhoun, E. R. Draper, E. G. B. Eden, B. N. Cattoz, K. L. Morris, L. Chen, T. O. McDonald, A. E. Terry, P. C. Griffiths, L. C. Serpell and D. J. Adams, *Nanoscale*, 2014, **6**, 13719-13725.
26. V. A. Mallia, P. D. Butler, B. Sarkar, K. T. Holman and R. G. Weiss, *J. Am. Chem. Soc.*, 2011, **133**, 15045-15054.
27. S. Saha, J. Bachl, T. Kundu, D. Diaz Diaz and R. Banerjee, *Chem. Commun.*, 2014, **50**, 7032-7035.
28. V. J. Nebot, J. J. Ojeda-Flores, J. Smets, S. Fernández-Prieto, B. Escuder and J. F. Miravet, *Chem. Eur. J.*, 2014, **20**, 14465-14472.
29. M. George and R. G. Weiss, *J. Am. Chem. Soc.*, 2001, **123**, 10393-10394.