

# ChemComm

Accepted Manuscript



This is an *Accepted Manuscript*, which has been through the Royal Society of Chemistry peer review process and has been accepted for publication.

*Accepted Manuscripts* are published online shortly after acceptance, before technical editing, formatting and proof reading. Using this free service, authors can make their results available to the community, in citable form, before we publish the edited article. We will replace this *Accepted Manuscript* with the edited and formatted *Advance Article* as soon as it is available.

You can find more information about *Accepted Manuscripts* in the [Information for Authors](#).

Please note that technical editing may introduce minor changes to the text and/or graphics, which may alter content. The journal's standard [Terms & Conditions](#) and the [Ethical guidelines](#) still apply. In no event shall the Royal Society of Chemistry be held responsible for any errors or omissions in this *Accepted Manuscript* or any consequences arising from the use of any information it contains.

## COMMUNICATION

# Oxocentered Cu(II) lead selenite honeycomb lattices hosting Cu(I)Cl<sub>2</sub> groups obtained by chemical vapor transport reactions†

Cite this: DOI: 10.1039/x0xx00000x

 Vadim M. Kovrugin,<sup>a,b</sup> Marie Colmont,<sup>b</sup> Oleg I. Siidra,<sup>a</sup> Olivier Mentré,<sup>b</sup> Alexander Al-Shuray,<sup>a</sup> Vladislav V. Gurzhiy<sup>a</sup> and Sergey V. Krivovichev\*<sup>a</sup>


 Received 00th January 2015,  
 Accepted 00th January 2015

DOI: 10.1039/x0xx00000x

www.rsc.org/

Chemical vapor transport (CVT) reactions were used to prepare three modular mixed-valent Cu(I)–Cu(II) compounds, (Pb<sub>2</sub>Cu<sup>2+</sup><sub>9</sub>O<sub>4</sub>)(SeO<sub>3</sub>)<sub>4</sub>(Cu<sup>+</sup>Cl<sup>2</sup>)Cl<sub>5</sub> (1), (PbCu<sup>2+</sup><sub>5</sub>O<sub>2</sub>)(SeO<sub>3</sub>)<sub>2</sub>(Cu<sup>+</sup>Cl<sub>2</sub>)Cl<sub>3</sub> (2), and (Pb<sub>x</sub>Cu<sup>2+</sup><sub>(6-x)</sub>O<sub>2</sub>)(SeO<sub>3</sub>)<sub>2</sub>(Cu<sup>+</sup>Cl<sub>2</sub>)K<sub>(1-x)</sub>Cl<sub>(4-x)</sub> (x = 0.20) (3). In their crystal structures chains of anion-centered (OCu<sup>2+</sup><sub>4</sub>) and (OCu<sup>2+</sup><sub>3</sub>Pb) tetrahedra form honeycomb-like double layers with cavities occupied by linear [Cu<sup>+</sup>Cl<sub>2</sub>]<sup>−</sup> groups.

Inorganic copper oxocompounds attract considerable attention due to their interesting structural and physical properties<sup>1</sup> as well as mineralogical and geochemical importance.<sup>2</sup> Of special interest are mixed-valent Cu(I)–Cu(II) systems with separate symmetrically independent monovalent and divalent copper sites due to their contrasted coordinations combined in one crystal structure. Herein we report on the synthesis and characterization of three novel Cu(I)–Cu(II) lead oxoselenite chlorides inspired by mineralogical discoveries in such unusual geological conditions as volcanic fumaroles.<sup>2g,3</sup> Here copper oxoselenites form from volcanic gases emanating from cooling magmatic chambers deep under the Earth's surface long after the period of eruptive activities. The formation of such Cu compounds in fumaroles provides a useful hint for their synthesis under laboratory conditions, in particular, the chemical vapor transport (CVT) method.<sup>4</sup> The specific feature of many Cu oxoselenites is the presence in their crystal structures of oxocentered (μ<sub>4</sub>-O)Cu<sub>4</sub> tetrahedral units that polymerize to form extended structural complexes.<sup>2g,3</sup> Likely, during these reactions the selenites and metal halides play the role of transport agent.<sup>5</sup> In order to reproduce natural exhalative chemistry, in this work, we investigate formation of phases in the PbO–Cu<sup>2+</sup>Cl<sub>2</sub>–Cu<sup>+</sup>Cl–Cu<sup>2+</sup>O–SeO<sub>2</sub> system containing Pb<sup>2+</sup> cations that possess stereochemically active 6s<sup>2</sup> lone electron pairs favouring formation segregation of structural compartments occupied by these pairs.<sup>6</sup> In addition, the preference of Pb<sup>2+</sup> ions for similar OPb<sub>4</sub> tetrahedral units is an asset for creation of more complex edifices.

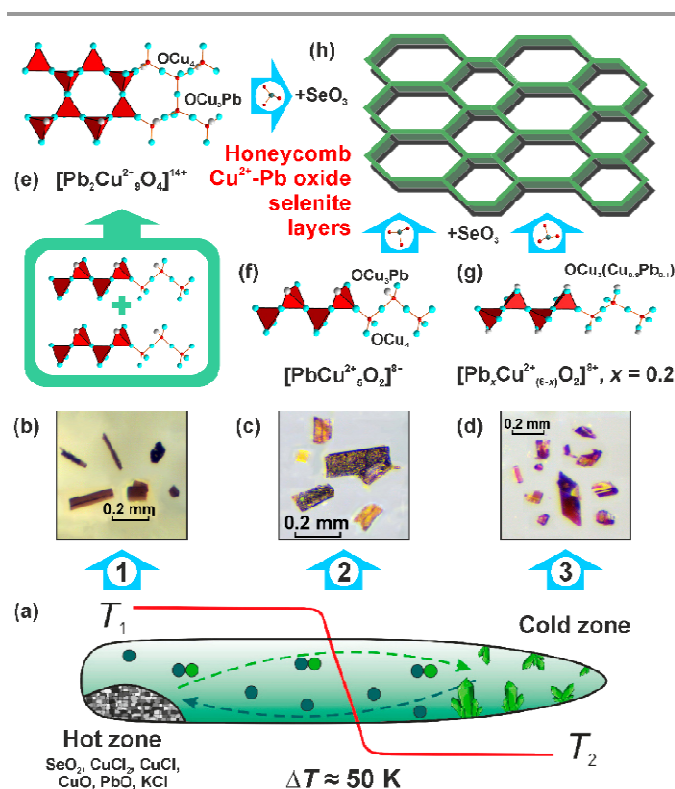

**Fig. 1** General scheme of syntheses by the method of CVT reactions (a), the crystals of **1**, **2** and **3** (b–d), and the scheme of formation of honeycomb Cu<sup>2+</sup>–Pb selenite layers (e–h). The types of oxo-centered 1-dimensional units (shown in red) formed by corner-sharing OCu<sub>4</sub> and OCu<sub>3</sub>Pb tetrahedra in the structures of **1**, **2** and **3** are shown. (Legend: Cu = cyan balls; Pb = grey balls). See text for details.

Crystallographic information for three novel compounds synthesized by the CVT reactions method (Fig. 1a) is summarized in Table 1. Schematic representations of coordination environments of cations in the crystal structures of **1–3** are shown in Fig. S1, ESI†. In all the compounds, Cu<sup>+</sup> cations form two relatively short Cu<sup>+</sup>–Cl bonds (2.058–2.118 Å), which result in the formation of tightly bonded

[CuCl<sub>2</sub>]<sup>-</sup> anionic groups that can be considered as separate structural entities. The Cu<sup>2+</sup> cations have mixed oxochloride coordinations that have previously been observed in Cu oxochloride compounds,<sup>2a</sup> with typical trends of *Jahn-Teller* d<sup>9</sup> ions. The Cu(1) and Cu(2) sites in **1**, the Cu(4) site in **2**, and Cu(3) site in **3** form [CuO<sub>4</sub>Cl<sub>2</sub>] distorted octahedra with four short equatorial Cu–O and two long apical Cu–Cl bonds. The Cu(3) site in **1**, the Cu(2) and Cu(3) sites in **2**, and the Cu(1) site in **3** are octahedrally coordinated with [CuO<sub>3</sub>Cl] squares complemented by two long Cu–Cl bonds. The Cu(4) site in **1** forms a [CuO<sub>4</sub>Cl] trigonal bipyramids, whereas the Cu(1) site in **2** and the Cu(4) site in **3** form [CuO<sub>3</sub>Cl<sub>2</sub>] trigonal bipyramids. The Pb atoms have asymmetrical coordinations consisting of three strong Pb–O bonds (2.356–2.420 Å) located in one coordination hemisphere and four long Pb–Cl in another. This coordination of Pb<sup>2+</sup> cations is typical for lead oxohalide compounds<sup>7</sup> and is consistent with the presence of stereoactive lone electron pairs. In all the compounds under consideration, Se<sup>4+</sup> cations form standard (SeO<sub>3</sub>)<sup>2-</sup> selenite triangular pyramidal oxo-anions (Se–O = 1.688–1.726 Å). The structure of **3** has one symmetrically independent K site with the site-occupation factor (s.o.f.) equal to 0.8. Its coordination polyhedron can be described as a distorted hexagonal bipyramid. Bond-valence sums<sup>8</sup> calculated for all the sites in the crystal structures of **1–3** are in full agreement with their expected oxidation states (in valence units): Cu<sup>+</sup> sites – 1.00–1.16, Cu<sup>2+</sup> sites – 1.96–2.14, Pb<sup>2+</sup> sites – 1.95–1.96, Se<sup>4+</sup> sites – 4.03–4.16, K<sup>+</sup> site – 0.80.


**Table 1** Crystallographic data for **1**, **2**, and **3**

	<b>1</b>	<b>2</b>	<b>3</b>
Empirical formula	(Pb <sub>2</sub> Cu <sup>2+</sup> <sub>9</sub> O <sub>4</sub> )(SeO <sub>3</sub> ) <sub>4</sub> (Cu <sup>+</sup> Cl <sub>2</sub> )Cl <sub>5</sub>	(PbCu <sup>2+</sup> <sub>5</sub> O <sub>2</sub> )(SeO <sub>3</sub> ) <sub>2</sub> (Cu <sup>+</sup> Cl <sub>2</sub> )Cl <sub>3</sub>	(Pb <sub>x</sub> Cu <sup>2+</sup> <sub>(6-x)</sub> O <sub>2</sub> )(SeO <sub>3</sub> ) <sub>2</sub> (Cu <sup>+</sup> Cl <sub>2</sub> )K <sub>(1-x)}</sub> Cl <sub>(4-x)</sub> , x = 0.20
crystal system		C2/m	
space group		monoclinic	
a (Å)	18.605(17)	18.4956(4)	15.116(1)
b (Å)	6.204(6)	6.1454(1)	6.1850(4)
c (Å)	12.673(11)	15.2985(4)	9.2672(9)
β (deg)	109.87(2)	119.311(1)	95.965(5)
V (Å <sup>3</sup> )	1376(2)	1516.25(6)	861.72(12)
ρ <sub>calc</sub> (g cm <sup>-3</sup> )	4.514	4.607	3.840
μ (mm <sup>-1</sup> )	25.78	25.02	15.52
reflection collected	7722	6910	4817
independent reflections (R <sub>int</sub> )	1301 (0.069)	1924 (0.024)	974 (0.029)
goodness-of-fit	0.791	1.231	1.121
R <sub>1</sub> [I > 2σ(I)]	0.0257	0.0260	0.0412
wR <sub>2</sub>	0.0349	0.0761	0.1172
R <sub>1</sub> (all data)	0.0475	0.0267	0.0496
wR <sub>2</sub>	0.0378	0.0761	0.1176
largest diff. peak and hole [e Å <sup>-3</sup> ]	0.951, -0.988	3.783, -2.942	4.244, -1.592

$$^a R_1 = \frac{\sum |F_o| - |F_c|}{\sum |F_o|}; wR_2 = \left\{ \frac{\sum [w(F_o^2 - F_c^2)]}{\sum [w(F_o^2)]} \right\}^{1/2}.$$

The high variability of cation coordinations in the structures of **1–3** makes their uniform description in terms of cation coordination polyhedra a difficult task. It is therefore more reasonable to look for more mundane consideration, e.g. in terms of cation arrays or coordination of anions.<sup>9</sup> In addition to the O atoms associated with the SeO<sub>3</sub> groups, all three compounds contain additional O<sub>a</sub> atoms (oxo-anions) not bonded to Se<sup>4+</sup> cations and tetrahedrally coordinated by four metal atoms (Cu and Pb). In the crystal structure of **1** there are two additional O atoms, O(2) and O(4), that form (OCu<sup>2+</sup><sub>3</sub>Pb) and (OCu<sup>2+</sup><sub>4</sub>) tetrahedra, respectively. The oxo-centered tetrahedra share common corners to form [O<sub>4</sub>Pb<sub>2</sub>Cu<sup>2+</sup><sub>9</sub>]<sup>4+</sup> double chains depicted in Fig. 1e. These chains are growing parallel to the *b*-axis, and its common value

for the three compounds (*b* ~ 6.2 Å) denote similar arrangement between the oxo-centered building units in the full series. This type of chains of anion-centered tetrahedra is original and has not been observed in inorganic compounds previously. The SeO<sub>3</sub> groups are attached to the triangular bases of oxo-centered tetrahedra that results in formation of complex 1-dimensional {[O<sub>4</sub>Pb<sub>2</sub>Cu<sup>2+</sup><sub>9</sub>](SeO<sub>3</sub>)<sub>4</sub>]<sup>6+</sup> interconnected via Pb–O bonds into 2-dimensional metal-oxide double layers (Fig. 2b). The projection of the layers in the (*bc*) plane lead to an Honeycomb-like lattice of tetrahedra, even though this idealized vision neglects the disconnections occurring at the oxocentered-oxoanion contacts. In contrast, monometallic [O<sub>2</sub>Cu<sub>5</sub>] honeycomb-layers are reported in several compounds based upon anion-centered tetrahedra.<sup>9</sup> The layers are surrounded by Cl<sup>-</sup> anions in the interleaves and accommodate both linear [Cu<sup>+</sup>Cl<sub>2</sub>]<sup>-</sup> anions and Cl<sup>-</sup> ions in the larger and smaller honeycomb-windows, respectively. The interactions between the Cl<sup>-</sup> ions of the [Cu<sup>+</sup>Cl<sub>2</sub>]<sup>-</sup> groups and host cationic networks are restricted to rather weak Cu<sup>2+</sup>–Cl<sup>-</sup> (> 2.975 Å), Pb<sup>2+</sup>–Cl<sup>-</sup> (> 3.396 Å) and K<sup>+</sup>–Cl<sup>-</sup> (> 3.478 Å) bonds with bond-valences not exceeding 0.08 valence units (Tables S1–S3). Taking into account relative strength of the Cu<sup>+</sup>–Cl bonds and weak interactions between them and the rest of the structure, these units may be considered as guest anions embedded into complex metal oxochloride matrix based upon anion-centered tetrahedra.

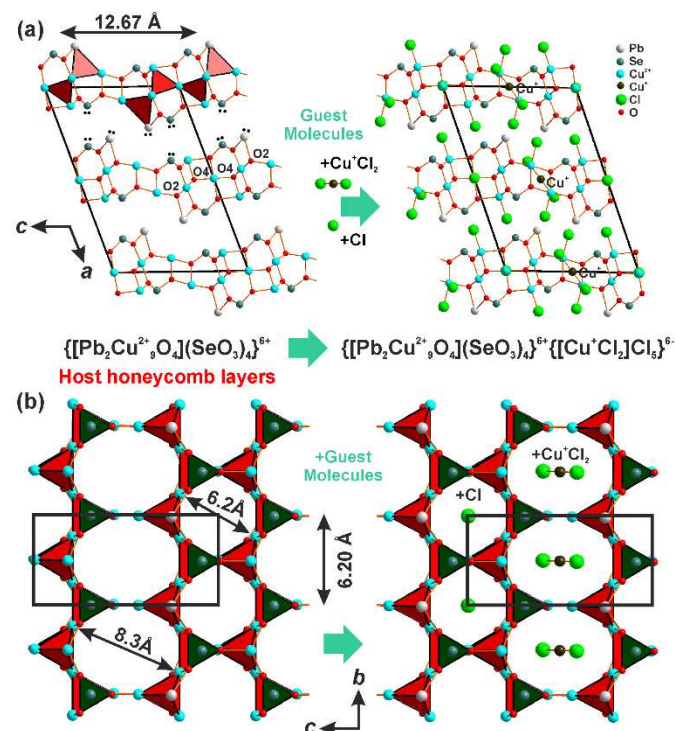


**Fig. 2** General projections of the structure of **1** along the *b* and *a* axis – (a) and (b). Honeycomb layers of {[Pb<sub>2</sub>Cu<sup>2+</sup><sub>9</sub>O<sub>4</sub>](SeO<sub>3</sub>)<sub>4</sub>]<sup>6+</sup> composition are hosts for the [Cu<sup>+</sup>Cl<sub>2</sub>]<sup>-</sup> guest species localized in the layer cavities. The {[Pb<sub>2</sub>Cu<sup>2+</sup><sub>9</sub>O<sub>4</sub>](SeO<sub>3</sub>)<sub>4</sub>]<sup>6+</sup> layers are formed via interconnection of the [Pb<sub>2</sub>Cu<sup>2+</sup><sub>9</sub>O<sub>4</sub>] oxo-centered chains (red) and isolated SeO<sub>3</sub> groups (dark-green). The O(2) and O(4) designated in (a) are central oxygen atoms in OCu<sub>4</sub> and OCu<sub>3</sub>Pb tetrahedra, respectively.


A very similar 'host-guest' principle is at work in the structures of **2** and **3** as well. Here the (OCu<sup>2+</sup><sub>3</sub>Pb) and (OCu<sup>2+</sup><sub>4</sub>) tetrahedra share corners to produce single chains extending along the common *b*-parameter that have the [O<sub>2</sub>PbCu<sub>5</sub>]<sup>8+</sup> and [O<sub>2</sub>Pb<sub>x</sub>Cu<sup>2+</sup><sub>(6-x)</sub>]<sup>8+</sup> compositions, respectively (Fig. 1f,g). Together with SeO<sub>3</sub> groups, these chains form 1-dimensional {[O<sub>2</sub>M<sub>6</sub>](SeO<sub>3</sub>)<sub>2</sub>]<sup>4+</sup> metal-oxide (*M* = Cu, Pb) backbones of the structures that are arranged to form pseudo honeycomb layers. Due to the elementary single-chains, only large honeycomb windows are created that accommodate the [Cu<sup>+</sup>Cl<sub>2</sub>]<sup>-</sup> guest anions (Fig. 3) as observed in **1**. The structure of **3** contains additional K<sup>+</sup> cations located in the interlayer space between the metal



oxoselenite chloride layers. In all three structures, lone electron pairs on the  $\text{Pb}^{2+}$  and  $\text{Se}^{4+}$  cations are oriented toward interlayer space, thus conforming the 'chemical scissor' principle of structural organization in compounds with lone-electron-pair cations.<sup>10</sup> It is noteworthy that the compounds **1** and **2** are closely chemically related that can be described by the equation:



From the structural viewpoint, transition from **1** to **2** is associated with the reconstruction of the metal-oxide backbone, *i.e.* in depolymerization of anion-centered tetrahedra and splitting of the double  $[\text{O}_4\text{Pb}_2\text{Cu}^{2+}_9]^{14-}$  chains into single  $[\text{O}_2\text{PbCu}_5]^{8-}$  chains. This kind of structural reconstruction accompanied with the inclusion of imaginary ionic component  $\text{Cu}^+\text{Cu}^{2+}\text{Cl}_3$  into metal-oxide matrix is in good agreement with the principle of dimensional reduction.<sup>11</sup> It should also be noted that **2** is a synthetic analogue of allochalcocelite, the mineral first described from volcanic fumaroles of the Tolbachik volcano (Kamchatka peninsula, Russia).<sup>3d</sup>

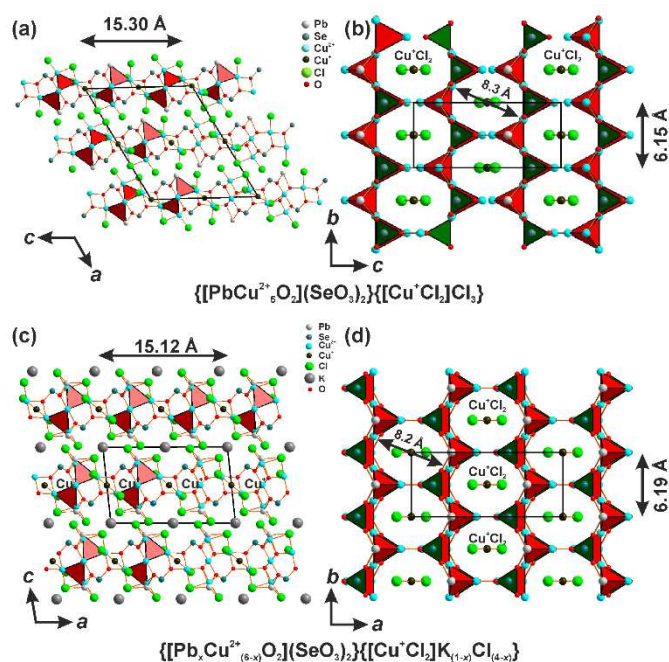

**Fig. 3** General projections of the structure of **2** (a, b) and **3** (c, d). In **2**, the  $\text{OCu}_4$  and  $\text{OCu}_3\text{Pb}$  tetrahedra (red) form single  $[\text{O}_2\text{PbCu}_5]$  chains, which results in the enlargement of the  $c$ -parameter value from 12.67 Å (in **1**) to 15.30 Å (in **2**). In **3**, K atoms are located in the interlayer under and above the pseudo-hexagonal voids filled by the  $[\text{Cu}^+\text{Cl}_2]$  groups. The layers (b, d) are characterized by only one type of pores with 8.3 Å and 8.2 Å in diameter in **2** and **3**, respectively.

To summarize, three novel  $\text{Cu}^{2+}\text{--Cu}^+$  Pb oxoselenite chlorides were obtained by the chemical vapor transport reactions, which proves the efficiency of this method for the synthesis of new mixed  $\text{Cu}^{2+}\text{--Cu}^+$  based oxyhalide compounds. These compounds described herein are based upon oxocentered mixed  $\text{Pb--Cu}^{2+}$  one-dimensional units of different architectures. These units determine basic topologies of the structures and influence their stability and properties. For instance, in the three compounds only corner-sharing  $\text{OCu}_4$  and  $\text{OCu}_3\text{Pb}$  are found into chains and double chains forming hollow voids. It follows that in all the compounds, the role of the tightly bonded  $[\text{Cu}^+\text{Cl}_2]^-$  anions is that of guest complexes incorporated inside metal oxide chloride units. The present study also points out that the  $\text{Cu}^+\text{Cl}_2$  groups may serve as transport agents of  $\text{Cu}^+$  in Cl-rich gaseous environments such as that observed in natural volcanic fumaroles.

This work was financially supported by the Russian Science Foundation through the grant 14-17-00071. Technical support by the

SPbSU X-Ray Diffraction Resource Centre is gratefully acknowledged. This work was carried out under the framework of the Multi-InMaDe project supported by the ANR (Grant ANR 2011-JS-08 003 01). V.M.K. thanks l'Ambassade de France en Russie and l'Agence Campus France (contracts n° 768231K, 779116K 794852B, 808399A, 808400J) for the partial support of this work.

## Notes and references

<sup>a</sup> Department of Crystallography, St. Petersburg State University, University Emb. 7/9, 199034 St. Petersburg, Russia.

E-mail: s.krivovichev@spbu.ru

<sup>b</sup> UCCS, UMR 8181, Université Lille Nord de France, USTL, F-59655 Villeneuve d'Ascq, France.

† Electronic Supplementary Information (ESI) available: CIF files, experimental section, IR spectra, tables with bond-valence analysis for **1–3**. See DOI: 10.1039/c000000x/

- (a) N.V. Kuratieva, M. Banki, A.A. Tsirlin, J. Eckert, H. Ehrenberg and D. Mikhailova, *Inorg. Chem.*, 2013, **52**, 13974; (b) A.A. Tsirlin, O. Janson, S. Lebernegg and H. Rosner, *Phys. Rev.*, 2013, **B87**, 064404; (c) S. Tamilarasan, D. Sarma, S. Bhattacharjee, U.V. Waghmare, S. Natarajan and J. Gopalakrishnan, *Inorg. Chem.*, 2013, **52**, 5757; (d) P.S. Berdonosov, O. Janson, A.V. Olenov, S.V. Krivovichev, H. Rosner, V.A. Dolgikh and A.A. Tsirlin, *Dalton Trans.*, 2013, **42**, 9547; (e) T.-T. Zhu, W. Sun, Y.-X. Huang, Z.-M. Sun, Y. Pan, L. Balents and J.-X. Mi, *J. Mater. Chem. C*, 2014, **2**, 8170; (f) H.L. Feng, M. Arai, Y. Matsushita, Y. Tsujimoto, Y. Yuan, C.I. Sathish, J. He, M. Tanaka and K. Yamaura, *J. Solid State Chem.*, 2014, **217**, 9; (g) S. Hu, A. Mace, M. Johnsson, V. Gnezdilov, P. Lemmens, J. Tapp and A. Moeller, *Inorg. Chem.*, 2014, **53**, 7661
- (a) S.V. Krivovichev, S.K. Filatov and L.P. Vergasova, *Mineral. Petrol.*, 2013, **107**, 235; (b) I.V. Pekov, M.E. Zelenski, V.O. Yapaskurt, Yu.S. Polekhovskiy and M.N. Murashko, *Eur. J. Mineral.*, 2013, **25**, 91; (c) I.V. Pekov, N.V. Zubkova, M.E. Zelenski, V.O. Yapaskurt, Yu.S. Polekhovskiy, O.A. Fadeeva and D.Yu. Pushcharovskiy, *Mineral. Mag.*, 2013, **77**, 107; (d) I.V. Pekov, O.I. Siidra, N.V. Chukanov, V.O. Yapaskurt, D.I. Belakovskiy, M.N. Murashko and E.G. Sidorov, *Eur. J. Mineral.*, 2014, **26**, 597; (e) I.V. Pekov, N.V. Zubkova, V.O. Yapaskurt, D.I. Belakovskiy, I.S. Lykova, M.F. Vigasina, E.G. Sidorov and D.Yu. Pushcharovskiy, *Mineral. Mag.*, 2014, **78**, 905; (f) I.V. Pekov, N.V. Zubkova, V.O. Yapaskurt, P.M. Kartashov, Yu.S. Polekhovskiy, M.N. Murashko and D.Yu. Pushcharovskiy, *Eur. J. Mineral.*, 2014, **26**, 667; (g) L.P. Vergasova, T.F. Semenova, S.V. Krivovichev, S.K. Filatov, A.A. Zolotarev, Jr. and V.V. Ananiev, *Eur. J. Mineral.*, 2014, **26**, 439.
- (a) S.V. Krivovichev, S.K. Filatov, T.F. Semenova, and I.V. Rozhdestvenskaya, *Z. Kristallogr.*, 1998, **213**, 645; (b) S.V. Krivovichev, R.R. Shuvalov, T.F. Semenova and S.K. Filatov, *Z. Kristallogr.*, 1999, **214**, 135; (c) P.C. Burns, S.V. Krivovichev and S.K. Filatov, *Can. Mineral.*, 2002, **40**, 1587; (d) S.V. Krivovichev, S.K. Filatov, P.C. Burns and L.P. Vergasova, *Can. Mineral.*, 2006, **44**, 507; (e) S.V. Krivovichev, S.K. Filatov, P.C. Burns and L.P. Vergasova, *Can. Mineral.*, 2007, **45**, 929; (f) R.R. Shuvalov, L.P. Vergasova, T.F. Semenova, S.K. Filatov, S.V. Krivovichev, O.I. Siidra and N.S. Rudashevskiy, *Amer. Mineral.*, 2013, **98**, 463.

- 4 M. Binnewies, R. Glaum, M. Schmidt and P. Schmidt, *Z. Anorg. Allg. Chem.*, 2013, **639**, 219.
- 5 A. Aliev, V.M. Kovrugin, M. Colmont, C. Terryn, M. Huvé, O.I. Siidra, S.V. Krivovichev and O. Mentré, *Cryst. Growth Des.*, 2014, **14**, 3026.
- 6 O.I. Siidra, D.S. Zenko and S.V. Krivovichev, *Amer. Mineral.*, 2014, **99**, 817.
- 7 (a) S.V. Krivovichev, O.I. Siidra, E.V. Nazarchuk, P.C. Burns and W. Depmeier, *Inorg. Chem.*, 2006, **45**, 3846; (b) O.I. Siidra, D.O. Zinyakhina, A.I. Zadoya, S.V. Krivovichev and R.W. Turner, *Inorg. Chem.*, 2013, **52**, 2799; (c) O.I. Siidra, S.V. Krivovichev, R.W. Turner, M.S. Rumsey and J. Spratt, *Am. Mineral.*, 2013, **98**, 248; (d) O.I. Siidra, S.V. Krivovichev, R.W. Turner, M.S. Rumsey and J. Spratt, *Am. Mineral.*, 2013, **98**, 256; (e) O.I. Siidra, D.S. Zenko, A.N. Suknotova and S.V. Krivovichev, *Mineral. Mag.*, 2013, **77**, 3239.
- 8 (a) N.E. Brese and M. O’Keeffe, *Acta Crystallogr.*, 1991, **B47**, 192; (b) S.V. Krivovichev and I.D. Brown, *Z. Kristallogr.*, 2001, **216**, 245.
- 9 S.V. Krivovichev, O. Mentré, O.I. Siidra, M. Colmont and S.K. Filatov, *Chem. Rev.*, 2013, **113**, 6459.
- 10 (a) R. Becker, M. Johnsson, R.K. Kremer and P. Lemmens, *Solid State Sci.*, 2003, **5**, 1411; (b) Z. Mayerova, M. Johnsson and S. Lidin, *Angew. Chem., Int. Ed.*, 2006, **45**, 5602; (c) V. Jo, M.K. Kim, D.W. Lee, I.W. Shim, K.M. Ok, *Inorg. Chem.*, 2010, **49**, 2990.
- 11 E.G. Tulsky and J.R. Long, *Chem. Mater.*, 2001, **13**, 1149.

### Table of contents entry

Three different mixed Cu(I)–Cu(II) Pb selenite chlorides were obtained using chemical vapor transport reactions. Their structures belong to three different but related structure types based on oxo-centered tetrahedral units with  $\text{Cu}^{2+}$  and  $\text{Pb}^{2+}$ . Metal-oxide selenite honeycomb layers with pores varying in diameter from 6.2 to 8.3 Å are filled by the  $[\text{Cu}^+\text{Cl}_2]^-$  anions and  $\text{Cl}^-$  ions.

