



**Supramolecular pentapeptide-based fullerene nano  
fibers: effect of molecular chirality**

Journal:	<i>ChemComm</i>
Manuscript ID:	CC-COM-03-2015-001991.R2
Article Type:	Communication
Date Submitted by the Author:	30-Apr-2015
Complete List of Authors:	Insuasty, Alberto; Facultad de Quimicas, Departamento de Quimica Organica Atienza, Carmen; Facultad de Quimicas, Departamento de Quimica Organica López, Juan Luis; Facultad de Quimicas, Departamento de Quimica Organica Martin, Nazario; Facultad de Quimica, Departamento de Quimica Organica

## COMMUNICATION

## Supramolecular pentapeptide-based fullerene nanofibers: effect of molecular chirality

Cite this: DOI: 10.1039/x0xx00000x

Alberto Insuasty,<sup>a</sup> Carmen Atienza,<sup>a</sup> Juan Luis López<sup>a</sup> and Nazario Martín<sup>a,b\*</sup>

Received 00th January 2012,  
Accepted 00th January 2012

DOI: 10.1039/x0xx00000x

www.rsc.org/

**Supramolecular organization of new fullerene derivatives endowed with peptides as biomolecular templates forming efficiently ordered nanofibers of several micrometres length based on hydrogen bonds and  $\pi$ - $\pi$  interactions.**


The control in the formation of nanostructures by self-assembly of electroactive molecules is an important issue in the search for applications such as photovoltaics and organic electronics, where morphology plays a critical role.<sup>1</sup> In this regard, the self-organization of electroactive fullerenes has attracted considerable attention because of their singular shape, high electron affinity and capacity for charge transport, which make them important 3D building blocks in supramolecular chemistry.<sup>2</sup> Furthermore, self-organization of fullerenes has resulted in remarkable charge carrier mobilities within highly ordered domains, which have found applications in organic electronic devices such as field effect transistors (FETs) and organic solar cells (OSCs), to name a few.<sup>3</sup>

The assembly of fullerene derivatives has given rise to a variety of nanostructures with different sizes and shapes. Some of these are based on suitably functionalized fullerenes endowed with large side chains to form amphiphilic systems, and others consist in copolymers and coassemblies giving rise, as well, to ordered electroactive domains.<sup>4</sup> However, the use of biomolecular templates as an alternative concept for organizing fullerenes has been barely explored.<sup>5</sup> In this regard, biomolecular templates are attractive target molecules to form highly complex supramolecular structures due to its well-defined chemical, physical and structural properties. In particular, peptide-based tubular systems or DNA have been successfully used to arrange photo and electroactive carbon nanostructures such as fullerenes or single wall carbon nanotubes (SWCNT). As a matter of fact, the resulting hybrids exhibit outstanding redox and optoelectronic properties.<sup>6</sup>

Among the different biomolecular templates, peptides have frequently been used in supramolecular chemistry. Thus, short peptides units allow the access to a variety of morphologies at nano-

and meso-scale and, therefore, make these units an important tool to be considered when different kind of nanostructures are desirable.<sup>7,8</sup> Additionally, supramolecular chemistry based on peptides has found applications in biomedical purposes with promising results in a variety of research fields.<sup>9</sup>

In this context, we describe the straightforward formation of C<sub>60</sub>-nanofibers by using different peptide sequences as biomolecular templates capable of self-assemble through multiple hydrogen-bonding interactions resulting in stable supramolecular architectures. For this purpose, we have synthesized a new series of fullerene derivatives (**1-3**) based on their covalent linkage to pentapeptide units (Figure 1).

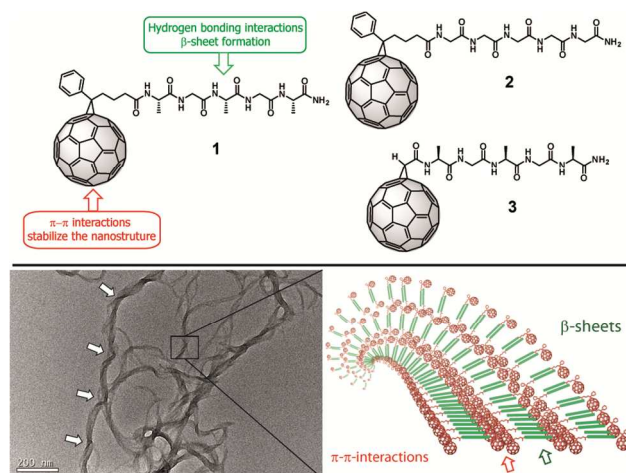

**Figure 1.** Chemical structures of novel C<sub>60</sub>-pentapeptide compounds **1-3** (Top). TEM image of compound **1** in TCE:DMSO (10%) and a cartoon of its assembly showing  $\beta$ -sheets and  $\pi$ - $\pi$  interactions between C<sub>60</sub> units stabilizing the formed nanostructure (Bottom).


It is important to remark that in this molecular design, we have considered two main issues: i) the presence of the peptide ensures the formation of the  $\beta$ -sheet as a secondary structure which stabilizes the nanostructure formed, and ii) the use of non-planar 3D units such as [60]fullerene derivatives allow stabilizing, through intermolecular  $\pi$ - $\pi$  interactions, the obtained nanostructures. Furthermore, fullerenes are in turn excellent n-type organic semiconductors of interest for a variety of purposes.

Compounds **1** and **2** are based on [6,6]-phenyl- $C_{61}$ -butyric acid methyl ester derivative (PCBM) functionalized with a chiral pentapeptide (L-Ala-Gly-L-Ala-Gly-L-Ala-NH<sub>2</sub>) and an achiral (Gly-(Gly)<sub>3</sub>-Gly-NH<sub>2</sub>) one, respectively. Compound **3** is, however, a [6,6]-carboxymethano [60]fullerene derivative comprising the same chiral pentapeptide as compound **1**. The aim of using these [60]fullerene derivatives with different chemical diversity is to compare the morphological changes stemming from the peptide's chirality (referred to compounds **1** and **2**) as well as the effect of the proximity of the chiral pentapeptide to the  $C_{60}$  surface (referred to compounds **1** and **3**).

Pentapeptides L-Ala-Gly-L-Ala-Gly-L-Ala-NH<sub>2</sub> and Gly-(Gly)<sub>3</sub>-Gly-NH<sub>2</sub> were synthesized by fluorenylmethoxycarbonyl (Fmoc) solid-phase synthesis on a 4-methylbenzhydrylamine (MBHA) resin. Removal of the Fmoc group and subsequent cleavage from the resin afforded the desired peptides, bearing amine and amide groups at the N- and C- termini, respectively. Finally, amidation reaction between pentapeptides and PCBM carboxylic acid or [6,6]-carboxymethano[60]fullerene afforded **1-3** in good yields. For synthetic details, see supporting information.

Compounds **1-3** showed only good solubility in dimethyl sulfoxide (DMSO) and a partial solubility in *N,N*-dimethylformamide. Therefore, we used a mixture of 1,1,2,2-tetrachloroethane (TCE) and 10% of DMSO (v/v), conditions in which their self-assembly is efficiently achieved. The supramolecular structures resulting from the self-assembly of **1-3** have been investigated through spectroscopic, chiroptical and microscopic techniques.


Transmission electron microscopy (TEM) imaging obtained by drop casting solutions of **1-3** in the mixture TCE:DMSO (10% v/v) showed the formation of nanofibers with several micrometers long in all cases, as shown in figures 1 and 2. It is possible to appreciate differences between the compounds **1-3**. In the case of compound **1**, figure 1 shows clearly how the fibers are twisted in some points along the fiber (see white arrows in Figure 1 and Figure S3) while in the case of compound **2** straight fibers are obtained instead (Figure 2A).

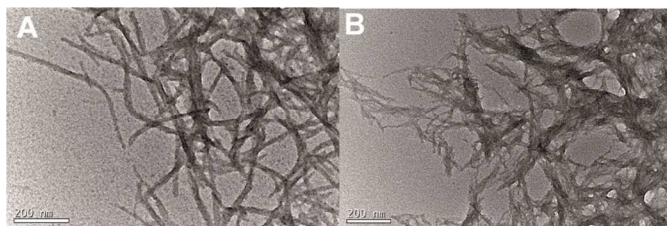

**Figure 2.** TEM images of compounds **2** (A) and **3** (B) in TCE:DMSO (10%).

At this point, it is important to remark that it is very difficult to correlate chirality with the nanostructure obtained. As it has previously been described in the literature, two important aspects should be considered: i) chiral peptides endowed with planar units can lead to twisted arrangements at nano and mesoscale.<sup>10</sup> However, this is not a general trend and non-twisted nanostructures can be formed as well; and ii) achiral molecules, could give rise to twisted arrangements.<sup>11</sup>

In this regard, considering the non-planar chemical structures of compounds **1** and **2** (Figures 1 and 2), we hypothesize that this nanostructural difference could be accounted for by the role of peptide's chirality, which is expressed at the nanoscale in the supramolecular structure. However, in the case of compound **3** the fibers formed seemed to be straighter, shorter and more aggregated than those obtained from compounds **1** and **2**. We believe that these features might be presumably attributed to the suppression of the alkyl chain of three carbon atoms of the PCBM, making **3** a more rigid system when compared to **1** and **2**. This more rigid system in **3** allows better packing between  $\beta$ -sheets strands through  $\pi$ - $\pi$  interactions between  $C_{60}$  molecules, whereas in **1** and **2** these molecules have a higher degree of freedom with respect to the  $\beta$ -sheet owed to the presence of the alkyl chain. With the aim of obtaining a better insight of the fine structure of the nanofibers, high-resolution transmission electron microscopy (HRTEM) images were obtained. Unfortunately, after several attempts, no clear pattern could be observed (see Figure S4 in the supporting information).

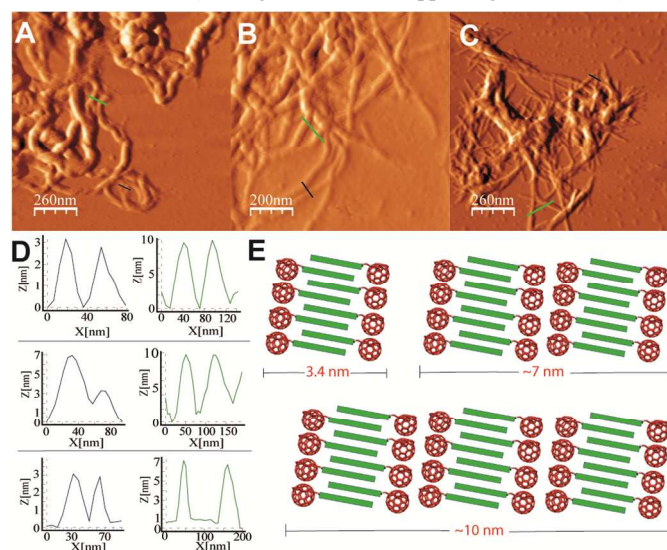


**Figure 3.** AFM images obtained by drop casting over freshly cleaved mica. (A), (B) and (C) correspond to the nanofibers obtained from compounds **1**, **2** and **3**, respectively. (D) Height profiles corresponding to the lines marked in figures A-C. Upper, middle and lower part correspond to figures A, B and C, respectively. (E) Cartoon accounting for the height profiles observed in AFM corresponding to one, two and three strands of  $\beta$ -sheets.

Complementary studies performed by Atomic force microscopy (AFM) showed very similar trends to those observed in TEM regarding morphological features as it can be discerned in figure 3.

Formation of long fibers and agglomerated structures were observed in all cases. Inspection in heights over the nanofibers revealed that the smaller ones correspond to the expected heights for one ( $\sim 3.4$  nm), two ( $\sim 7$  nm) or three ( $\sim 10$  nm) strands of  $\beta$ -sheets as shown in the height profiles in figure 3D-E. The agglomerated structures should consist of several packed strands, which are further stabilized by  $\pi$ - $\pi$  interactions between  $C_{60}$  units.

Fourier-transform infrared (FTIR) spectroscopy measurements were performed in order to confirm the formation of  $\beta$ -sheets as secondary structure for **1-3**. A strong amide I ( $\nu_{C=O}$ ) band at  $1630\text{ cm}^{-1}$  together with a weak shoulder around  $1690\text{ cm}^{-1}$  were observed, which is in agreement with the existence of intermolecular  $\beta$ -sheets. These features, as it has previously been reported, correspond to peptide units interacting in an antiparallel mode.<sup>7,10b,12</sup> In some cases the band at  $1650\text{ cm}^{-1}$  was barely observed which indicates the existence of random aggregates (Figure S1 in the supporting information).

The optical properties of **1-3** were measured in DMSO and TCE:DMSO (10% v/v). In DMSO, UV-Vis spectra of **1-3** showed the typical fullerene bands at 330 and 430 nm, the latter associated to the saturation of a C-C double bond in fullerene monoadducts.<sup>13</sup> However, UV-Vis spectra of **1-3** in the mixture TCE:DMSO revealed a depletion of the band at 330 nm together with an increase in absorbance around  $\sim 450$  nm (see red arrows in Figure 4A-C). This trend has also been observed in fullerene aggregates,<sup>14</sup> films<sup>15</sup> or  $C_{60}$  molecules packed within constrained channels<sup>16</sup> and has been attributed to interactions between  $C_{60}$  units,<sup>17</sup> thus, being indicative of the aggregation of fullerene moieties. In the case of compound **3**, the broadening is more significant than the other compounds, losing the feature band at 430 nm. This feature might be in accordance with higher packing of  $C_{60}$  molecules in compound **3** when compared to **1** and **2** owed to the higher rigidity of the system.

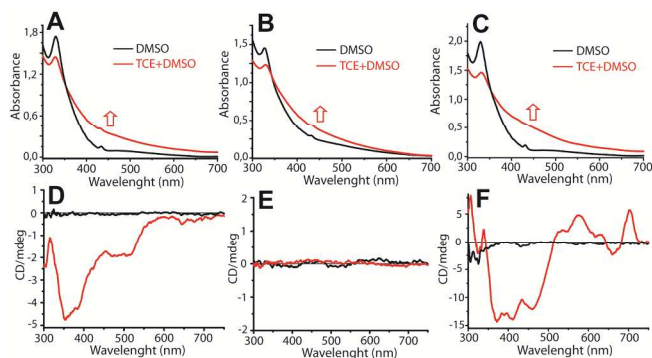

**Figure 4.** UV-Vis spectra in DMSO (black lines) and the mixture TCE:DMSO (10% v/v, red lines) for compounds **1** (A), **2** (B) and **3** (C). The red arrows show the increase in absorbance around 450 nm. Circular dichroism spectra in DMSO (black lines) and in the mixture TCE:DMSO (10% v/v, red lines) for compounds **1** (D), **2** (E) and **3** (F).

The self-assembly of **1-3** was also monitored by circular dichroism (CD) in DMSO and the mixture TCE:DMSO. The CD spectra in DMSO showed no optical activity for compounds **1** and **2**, and a weak dichroic signal for compound **3** as shown in figure 4D-F (black lines). Here, it is important to remark that despite compounds **1** and

**3** are covalently bonded to a chiral peptide, dichroic signal was solely observed for compound **3**. This fact could be attributed to the proximity effect of the first chiral center (Ala) when compared to molecule **1**, in which its chiral center is farther from the  $\pi$ -cloud of the [60]fullerene.<sup>18</sup> These low CD responses could be in agreement with the presence of disaggregated compounds. However, CD studies for **1** and **3** in TCE:DMSO exhibited a notable negative Cotton effect in the range of fullerene absorptions. These experimental findings resemble to that observed for a related system when the molecule is assembled.<sup>7</sup> Thus, the results support the existence of supramolecular aggregates in which a transfer of chirality occurs from the peptide to the fullerene. It is worth to mention that in the case of compound **3** the response in CD measurements is higher when compared with compound **1**. This outcome could be accounted for by the proximity effect of the peptide chain to the  $C_{60}$  sphere when compared to compound **1**. As a matter of fact, in the case of compound **2** the lack of chirality in the peptide chain does not trigger any response in CD measurements in any case, neither disaggregated (DMSO) nor assembled (TCE:DMSO).

Fluorescence studies for compounds **1-3** were performed in DMSO and the mixture TCE:DMSO (Figure 2S in the supporting information). The intensity of the [60]fullerene fluorescence with maxima at  $\sim 709$  nm decreased and shifted slightly in the mixture TCE:DMSO compared to that obtained in DMSO. This slight fluorescence quenching can be presumably attributed to the fact that fluorescence is more deactivated when  $C_{60}$  molecules are closer, that is, in the mixture TCE:DMSO. However, due to the fact that fluorescence changes are very weak in all cases, any clear conclusion can be derived.

## Conclusions

In summary, the present study shows that pentapeptide biomolecular templates serve as effective tools to organize fullerene molecules. The nanofibers are stabilized through the  $\beta$ -sheet along with  $\pi$ - $\pi$  interactions between  $C_{60}$  molecules. Moreover, a study on nanofiber's morphology based on molecular features such as peptide's chirality and peptide's distance to the  $C_{60}$  unit has been performed by using different techniques (UV-Vis, fluorescence, FTIR, CD, TEM and AFM). Interestingly, CD studies in TCE:DMSO show a strong negative Cotton effect in the range of fullerene absorptions which reveals an efficient chirality transfer from the chiral peptide unit to the  $C_{60}$  moiety. Furthermore, this effect depends of the distance existing between them.

The highly ordered electroactive materials formed as well as the ease experimental procedure reveal that the use of biomolecular templates is a very attractive approach in the search for supramolecularly organized fullerenes. Since fullerene assemblies are required for a variety of applications in different devices, we feel that our results pave the way to the supramolecular organization of electroactive 3D fullerenes based in bio-inspired H-bonds and  $\pi$ - $\pi$  interactions.

## ACKNOWLEDGMENTS

Financial support by the European Research Council (ERC-320441-Chirallcarbon), the Ministerio de Economía y Competitividad (MINECO) of Spain (projects CTQ 2011-24652/BQU and the CAM (PHOTOCARBON project S2013/MIT-2841)) are acknowledged. Ramón y Cajal contract to C.A, UCM pre-doctoral fellowship granted to A.I. and N. M. thanks to the Alexander von Humboldt Foundation.

## Notes and references

<sup>a</sup> Departamento de Química Orgánica, Facultad de C. C. Químicas, Universidad Complutense de Madrid, 28040 Madrid (Spain).

Fax: (+34) 91-394-4227.

<sup>b</sup> IMDEA-nanociencia

28049 Madrid (Spain)

Fax: (+34) 91-394-4103

E-mail: [nazmar@ucm.es](mailto:nazmar@ucm.es)

† Electronic Supplementary Information (ESI) available. See DOI: 10.1039/c000000x/

- 1 a) S. I. Stupp, L. C. Palmer, *Chem. Mater.*, 2014, **26**, 507-508; b) A. Bakulin, A. Rao, V. G. Pavelyev, P. H. M. van Loosdrecht, M. S. Pshenichnikov, D. Niedzialek, J. Cornil, D. Beljonne, R. H. Friend, *Science* 2012, **335**, 1340-1344; c) Y. Che, H. Huang, M. Xu, Ch. Zhang, B. R.; Bunes, X.; Yang, L. Zang, *J. Am. Chem. Soc.*, 2011, **133**, 1087-1091; d) J. H. van Esch, *Nature* 2010, **466**, 193-194.
- 2 a) R. Charvet, Y. Yamamoto, T. Sasaki, J. Kim, K. Kato, M. Takata, A. Saeki, S. Seki, T. Aida, *J. Am. Chem. Soc.*, 2012, **134**, 2524-2527; b) F. G. Brunetti, J. L. López, C. Atienza, N. Martín, *J. Mater. Chem.*, 2012, **22**, 4188-4205; c) B. C. Thompson, J. M. J. Fréchet, *Angew. Chem. Int. Ed.*, 2008, **47**, 58-77.
- 3 a) Y. Zhang, M. Wang, S. D. Collins, H. Zhou, H. Phan, C. Proctor, A. Mikhailovsky, F. Wudl, T-Q. Nguyen, *Angew. Chem. Int. Ed.*, 2014, **53**, 244-249; b) B. C. Schroeder, M. A. Brady, G. C. Faria, R. S. Ashraf, C. J. Takacs, J. S. Cowart, D. T. Duong, K. H. Chi, C-H. Tan, J. T. Cabral, A. Salleo, M. L. Chabiny, J. R. Durrant, I. McCulloch, *Angew. Chem. Int. Ed.*, 2014, **53**, 12870-12875; c) C-C. Chu, G. Raffy, D. Ray, A. Del Guerso, B. Kauffmann, G. Wantz, L. Hirsch, D. M. Bassani, *J. Am. Chem. Soc.*, 2010, **132**, 1217-12723; d) C. Yang, S. Cho, Al J. Heeger, F. Wudl, *Angew. Chem. Int. Ed.*, 2009, **48**, 1592-1595; f) D. M. Guldi, B. M. Illescas, C. M. Atienza, M. Wielopolski, N. Martín, *Chem. Soc. Rev.*, 2009, **38**, 1587-1597; f) N. Martín, L. Sánchez, M. A. Herranz, B. Illescas, D. M. Guldi, *Acc. Chem. Res.*, 2007, **40**, 1015-1024.
- 4 a) R. Charvet, Y. Yamamoto, T. Sasaki, J. Kim, K. Kato, M. Takata, A. Saeki, S. Seki, T. Aida, *J. Am. Chem. Soc.*, 2012, **134**, 2224-2527; b) S. S. Babu, H. Möhwald, T. Nakanishi, *Chem. Soc. Rev.*, 2010, **39**, 4021-4035.
- 5 A. Muñoz, B. Illescas, M. Sanchez-Nazarro, J. Rojo, N. Martín, *J. Am. Chem. Soc.*, 2011, **133**, 16758-16761.
- 6 a) J. López-Andarias, J. L. López, C. Atienza, F. Brunetti, C. Romero-Nieto, D. M. Guldi, N. Martín, *Nat. Comm.*, 2014, doi:10.1038/ncomms4763; b) F. G. Brunetti, C. Romero-Nieto, J. López-Andarias, C. Atienza, J. L. López, D. M. Guldi, N. Martín, *Angew. Chem. Int. Ed.*, 2013, **52**, 2180-2184; c) C. Reiriz, R. J. Brea, R. Arranz, J. L. Carrascosa, A. Garibotti, B. Manning, J. M. Valpuesta, R. Eritja, L. Castedo, J. R. Granja, *J. Am. Chem. Soc.*, 2009, **131**, 11335-11337; b) Ch. Doe, H-S. Jang, T-H. Kim, S. R. Kline, S.-M. Choi, *J. Am. Chem. Soc.*, 2009, **131**, 16568-16572; R. J. Brea, L. Castedo, J. R. Granja, M. Angeles Herranz, L. Sánchez, N. Martín, W. Seitz, D. M. Guldi, *PNAS* 2007, **104**, 5291-5294.
- 7 J. L. López, C. Atienza, A. Insuasty, J. López-Andarias, C. Romero-Nieto, D. M. Guldi, N. Martín, *Angew. Chem. Int. Ed.*, 2012, **51**, 3857-3861.
- 8 a) J. D. Tovar, *Acc. Chem. Res.*, 2013, **46**, 1527-1537; b) H. Shao, T. Nguyen, N. C. Romano, D. A. Modarelli, J. R. Parquette, *J. Am. Chem. Soc.*, 2009, **131**, 16374-16376.
- 9 a) S. Bartocci, D. Mazzier, A. Moretto, M. Mba, *Org. Biomol. Chem.* 2015, **13**, 348-352; b) R. H. Zha, S. Sur, S. I. Stupp, *Adv. Healthcare Mater.*, 2013, **2**, 126-133; c) M. J. Webber, J. Tongers, C. J. Newcomb, K-J. Marquardt, J. Bauersachs, D. W. Losordo, S. I. Stupp, *PNAS*, 2011, **108**, 13438-13443; d) H. Jintoku, T. Sagawa, K. Miyamoto, M. Takafuji, H. Ihara, *Chem. Commun.*, 2010, **46**, 7208-7210.
- 10 a) V. Castelletto, I. W. Hamley, *J. Phys. Chem. B* 2010, **114**, 8002-8008; b) R. Matmour, I. D. Cat, S. J. George, W. Adriaens, P. Leclère, P. H. H. Bomans, N. A. J. M. Sommerdijk, J. C. Gielen, P. C. M. Christianen, J. T. Heldens, J. C. M. van Hest, D. W. P. M. Löwik, S. D. Feyter, E. W. Meijer, A. P. H. J. Schenning, *J. Am. Chem. Soc.* 2008, **130**, 14576-14583; c) V. Jayawarna, M. Ali, T. A. Jowitt, A. F. Miller, A. Saiani, J. E. Gough, R. V. Ulijn, *Adv. Mater.* 2006, **18**, 611-614.
- 11 a) F. Aparicio, E. Matesanz, L. Sánchez, *Chem. Eur. J.* 2014, **20**, 14599-14603; b) J. L. López, C. Atienza, W. Seitz, D. M. Guldi, N. Martín, *Angew. Chem. Int. Ed.* 2010, **49**, 9876-9880; c) S. Zhang, S. Yang, J. Lan, S. Yang, J. You, *Chem. Commun.* 2008, 6170-6172.
- 12 a) H. Shao, J. R. Parquette, *Chem. Comm.*, 2010, **46**, 4285-4287.
- 13 a) E. E. Maroto, S. Filippone, A. Martín-Domenech, M. Suárez, N. Martín, *J. Am. Chem. Soc.*, 2012, **134**, 12936-12938; b) K. Swai, Y. Takano, M. Izquierdo, S. Filippone, N. Martín, Z. Slanina, N. Mizorogi, M. Waelchli, T. Tsuchiya, T. Akasaka, S. Nagase, *J. Am. Chem. Soc.*, 2011, **133**, 17746-17752; c) S. Filippone, E. E. Maroto, A. Martín-Domenech, M. Suárez, N. Martín, *Nat. Chem.*, 2009, **1**, 578-582.
- 14 R. V. Bensasson, E. Bienvenue, M. Dellinger, S. Leach, P. Seta, *J. Phys. Chem.*, 1994, **98**, 3492-3500.
- 15 W. Kratschmer, L. D. Lamb, K. Fostiropoulos, D. R. Huffman, *Nature* 1990, **347**, 354-358.
- 16 G. Dan Pantos, J. L. Wietor, J. K. M. Sanders, *Angew. Chem. Int. Ed.*, 2007, **46**, 2238-2240.
- 17 F. Diederich, J. Effing, U. Jonas, L. Jullien, T. Plesniviy, H. Ringsdorf, C. Thilgen, D. Weinstein, *Angew. Chem. Int. Ed.*, 1992, **31**, 1599-1602.
- 18 a) A. Ruiz, J. Coro, L. Almagro, J. A. Ruiz, D. Molero, E. E. Maroto, S. Filippone, M. A. Herranz, R. Martínez-Álvarez, J. C. Sancho-García, F. D. Meo, M. Suárez, N. Martín, *J. Org. Chem.*, 2013, **78**, 2819-2826; b) J. Coro, H. Rodríguez, D. G. Rivera, M. Suárez, D. Molero, M. A. Herranz, R. Martínez-Álvarez, S. Filippone, N. Martín, *Eur. J. Org. Chem.*, 2009, **28**, 4810-4817.