

# ChemComm

Accepted Manuscript



This is an *Accepted Manuscript*, which has been through the Royal Society of Chemistry peer review process and has been accepted for publication.

*Accepted Manuscripts* are published online shortly after acceptance, before technical editing, formatting and proof reading. Using this free service, authors can make their results available to the community, in citable form, before we publish the edited article. We will replace this *Accepted Manuscript* with the edited and formatted *Advance Article* as soon as it is available.

You can find more information about *Accepted Manuscripts* in the [Information for Authors](#).

Please note that technical editing may introduce minor changes to the text and/or graphics, which may alter content. The journal's standard [Terms & Conditions](#) and the [Ethical guidelines](#) still apply. In no event shall the Royal Society of Chemistry be held responsible for any errors or omissions in this *Accepted Manuscript* or any consequences arising from the use of any information it contains.

## COMMUNICATION

# The role of surface hydrolysis of ferricyanide anions in crystal growth of snowflake-shaped $\alpha$ -Fe<sub>2</sub>O<sub>3</sub>

Cite this: DOI: 10.1039/x0xx00000x

Received 00th January 2012,  
Accepted 00th January 2012

DOI: 10.1039/x0xx00000x

www.rsc.org/

Zhong Liu,<sup>a,b</sup> Chang-Yang Chiang,<sup>b</sup> Wu Li,<sup>a</sup> and Wuzong Zhou<sup>\*b</sup>

**Selective adsorption and surface hydrolysis of [Fe(CN)<sub>6</sub>]<sup>3-</sup> anions on  $\alpha$ -Fe<sub>2</sub>O<sub>3</sub> crystals was found to be a crucial process in the formation of a snowflake-like morphology, and the established mechanism is complementary to the classical theories of crystal growth.**

Formation of high symmetric polyhedral morphologies of crystals can normally be explained using a kinetic approach of Bravais-Friedel-Donnay-Harker law, *i.e.* appearance of facets of a crystal is attributed to the slow growth rates along these directions. Another theory gives a thermodynamic approach: the equilibrium shape of a free crystal is the shape that minimizes its surface free energy. Both of these classical theories deal with the bonding energy of crystal structures without considering external effects, and therefore, cannot explain the formation mechanisms of many unusual crystal morphologies, *e.g.* polyhedra of polycrystalline particles of calcite and MOFs,<sup>1</sup> complicated snowflake-shaped hematite ( $\alpha$ -Fe<sub>2</sub>O<sub>3</sub>).<sup>2</sup> The anisotropy of the crystal structure of hematite cannot justify the only active crystal growth directions of six equivalent zone axes, parallel to the (*ab*) plane of the hexagonal unit cell.

Hematite, as the most stable iron oxide under ambient conditions, is a good candidate for application in many fields, including catalysis, gas sensors, lithium battery, magnetic materials production, electromagnetic devices and pigments, *etc.*<sup>3</sup> In recent years, it has been found that these applications are greatly affected by the microstructures and morphologies of the crystals.<sup>4</sup> ‘Snowflake’  $\alpha$ -Fe<sub>2</sub>O<sub>3</sub> with hyperbranches has been investigated because of their large surface areas and unique hierarchical structures.<sup>5</sup> However, the formation mechanism of these morphologies is yet to be studied.

Herein, we report our recent re-synthesis of ‘snowflake’  $\alpha$ -Fe<sub>2</sub>O<sub>3</sub> crystals via a hydrolysis process of [Fe(CN)<sub>6</sub>]<sup>3-</sup>. The growth directions of  $\langle 11\bar{2}0 \rangle$  instead of commonly reported  $\langle 10\bar{1}0 \rangle$  are detected from selected area electron diffraction (SAED) patterns and high resolution transmission electron microscopic (HRTEM) images. The growth direction was found to be governed by highly selective surface adsorption followed by on-site hydrolysis of ferricyanide anions. Addition of octylamine in the synthetic solution led to a change of the favourite growth directions from  $\langle 11\bar{2}0 \rangle$  to  $\langle 10\bar{1}0 \rangle$  and induced a morphology evolution from ‘snowflake’ to ‘starfish’, ‘flower’ and finally to hexagonal plate, offering further support to the newly established mechanism.

‘Snowflake’  $\alpha$ -Fe<sub>2</sub>O<sub>3</sub> particles were synthesized according to the reported method.<sup>2</sup> 1.52 mmol K<sub>3</sub>Fe(CN)<sub>6</sub> were dissolved in 40 mL deionized water. The solution was subsequently sealed in a 50 mL

autoclave, and maintained at 180 °C for 20 h, followed by cooling down to room temperature gradually. Almost all the particles in the red precipitate have a snowflake-like shape (Fig. S1a,b, ESI†). XRD pattern of the product shows a single phase of  $\alpha$ -Fe<sub>2</sub>O<sub>3</sub> with all the diffraction peaks indexed onto the hexagonal unit cell with *a* = 5.0356 and *c* = 13.7489 Å (Fig. S2a, ESI†).


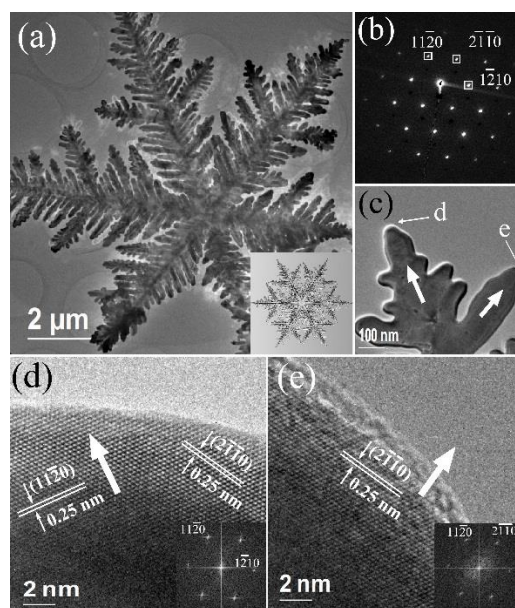


Fig. 1 (a) TEM image of a typical snowflake-like particle of  $\alpha$ -Fe<sub>2</sub>O<sub>3</sub>. The inset is a photo of a real snowflake for comparison. (b) The corresponding SAED pattern. (c) An enlarged TEM image of a tip. (d) and (e) HRTEM images from the tip areas marked ‘d’ and ‘e’ in (c), respectively. The arrows indicate the crystal growth directions. The insets are the corresponding FFT patterns.

A TEM image of a typical ‘snowflake’ particle is shown in Fig. 1(a), revealing more microstructural details. Although the constructed hyperbranched microstructure of the particle looks quite complicated, the corresponding SAED pattern (Fig. 1b) indicates that the whole particle can be regarded as a single crystal, and the viewing direction perpendicular to the face of the ‘snowflake’ is along the [0001] zone axis of  $\alpha$ -Fe<sub>2</sub>O<sub>3</sub>. In other words, all the branches and subbranches in the particle are linked through a crystalline connection. Comparable examples are mesoporous single crystals of metal oxides.<sup>6</sup> It can be

also confirmed by HRTEM images that the crystal growth directions are the six  $\langle 11\bar{2}0 \rangle$  zone axes (Fig. 1d, e). The whole particle is quite flat with a smooth (0001) surface, while the diameter of the ‘snowflake’ particles is about 10  $\mu\text{m}$ , which is much larger than the particle sizes of other specimens as shown in Fig. S1, ESI†. It again implies that the growth along the  $\langle 11\bar{2}0 \rangle$  directions is fast. If the diffusion rates and attachment behaviour of the building units, such as  $\text{Fe}^{3+}$  and  $\text{OH}^-$ , to various crystal surfaces are similar, such highly selective directions of crystal growth cannot be explained based on the crystallographic anisotropy of  $\alpha\text{-Fe}_2\text{O}_3$ .

We assume, in the initial stage, some nuclei of  $\alpha\text{-Fe}_2\text{O}_3$  form in the solution of  $\text{K}_3\text{Fe}(\text{CN})_6$  via the following hydrolysis process.



SEM and HRTEM investigations of time-dependant specimens (Fig. S3, ESI†) indicate that the processes of nucleation and growth of spherical crystallites are very slow. Further crystal growth of the branches is much faster. The latter process relies on attachment of precursor ions/molecules on the crystal surface. Since the solubility of  $[\text{Fe}(\text{CN})_6]^{3-}$  in water is extremely low with the dissociation constant,  $K_s = 1.0 \times 10^{-42}$ , there are almost no  $\text{Fe}^{3+}$  free cations in the solution. On the other hand, hydrolysis of  $[\text{Fe}(\text{CN})_6]^{3-}$  results in a reduction of pH value from 7.27 to 6.76 (see Table S1, ESI†) and, therefore, the concentration of  $\text{OH}^-$  anions is also very low. The principal precursor ions in the solution are  $[\text{Fe}(\text{CN})_6]^{3-}$ . These ferricyanide anions contain six lone pairs of electrons on the outer surface, which can bond on the crystal surface if the latter contains some exposed positive charged sites or Lewis acidic sites.


Under the hydrothermal synthetic conditions, surface of metal oxide crystals is normally terminated with hydroxyl groups. Close examination of the terminal atomic planes on the principal facets of  $\alpha\text{-Fe}_2\text{O}_3$ , such as the  $\{10\bar{1}0\}$ ,  $\{11\bar{2}0\}$ , and  $\{0001\}$  planes, has been previously performed and their electronic structures been calculated.<sup>7</sup> The charge of the hydroxyl groups depends on the local configuration, *i.e.* the number of Fe coordination. If a hydroxyl group is coordinated by only one Fe cation, it is negatively charged, designated site I or  $\text{OH}^{0.5-}$ . A doubly coordinated hydroxyl group is neutralized, designated site II or  $\text{OH}^0$ , while that in a triple coordination is positively charged, designated site III or  $\text{OH}^{0.5+}$ . The  $\{0001\}$  surfaces of hematite contain only doubly coordinated hydroxyl groups with a density of  $13.7/\text{nm}^2$ , which are neutral and inactive in surface adsorption of ferricyanide anions. The  $\{10\bar{1}0\}$  surfaces have both singly and doubly coordinated hydroxyls ( $5.8/\text{nm}^2$  and  $2.9/\text{nm}^2$ , respectively) and are, therefore, overall negatively charged, which is also inactive for bonding with the ferricyanide anions. The  $\{11\bar{2}0\}$

surfaces contain all the three types of co-ordinations ( $5.0/\text{nm}^2$  for each type of sites). The positively charged  $\text{OH}^{0.5+}$  in the triply coordinated hydroxyl groups can act as Lewis acidic sites, offering a chance to bond with  $[\text{Fe}(\text{CN})_6]^{3-}$ . This is probably the most important factor of the selective crystal growth along the  $\langle 11\bar{2}0 \rangle$  directions.


Fig. 2(a) shows a top view of the  $\{11\bar{2}0\}$  surface. The hydroxyl groups having different Fe coordinations (sites I, II and III) are indicated with the triply coordinated oxygen highlighted by a pink shadow. Fig. 2(b) is a profile view of the  $\{11\bar{2}0\}$  surface via rotation of the model in Fig. 2(a) around the Z axis for  $90^\circ$ . H atoms on the sites III are shown. When a  $[\text{Fe}(\text{CN})_6]^{3-}$  anion is adsorbed on the  $\{11\bar{2}0\}$  surface as shown in the middle of Fig. 2, bonding with  $\text{OH}^{0.5+}$ , partial electron transfer from a  $\text{CN}^-$  ligand to the crystal surface weakens the Fe-C bond, enhancing the surface hydrolysis of the  $[\text{Fe}(\text{CN})_6]^{3-}$  anion. All the  $\text{CN}^-$  ligands would eventually leave Fe on the surface sites followed by dehydrogenation and dehydration, leading to deposition of  $\alpha\text{-Fe}_2\text{O}_3$  as shown in Fig. 2(c & d). The original triply coordinated oxygen atoms become four coordinated and the singly coordinated sites become triply coordinated, *i.e.* new sites III. The process can go on. Since such a surface hydrolysis only takes place on the  $\{11\bar{2}0\}$  surfaces, and the growth on the  $\{10\bar{1}0\}$  and  $\{0001\}$  surfaces are greatly depressed, the final morphology of the crystals becomes two dimensional thin snowflake-like. When the hydrolysis is not completed, a small amount of  $\text{CN}^-$  might remain on the crystal surface, as having been detected by XPS (Fig. S4a, ESI†).

When octylamine was added into the solution with a concentration of 0.12 mol/L, the morphology of product changed from ‘snowflake’ to ‘starfish’ with six arms, while the particle size decreases to about 3  $\mu\text{m}$  (Fig. S1c,d, ESI†). Although six primary branches were also developed in each crystal, the details of the hyperbranched structure, as seen in a TEM image in Fig. 3(a), is different from ‘snowflake’ crystals. First, the secondary branches are close each other, leaving no room for growth of the tertiary branches. Secondly, the thickness of the primary branches along  $[0001]$  increases significantly. Therefore, the particles are no longer thin and flat. Finally and most importantly, a careful analysis of SAED and HRTEM revealed that the principal crystal growth directions have been shifted from  $\{11\bar{2}0\}$  to  $\{10\bar{1}0\}$ , as presented in Fig. 3(a,b).

With further increase of octylamine to 0.24 mol/L and 0.36 mol/L, the hyperbranched structure completely disappears. The centres of the particles grow out, showing a hexagonal flower-like morphology. The diameters of the particles further decrease to 1  $\mu\text{m}$  and below (Fig. S1e-h, ESI†). Fig. 3(c,d) show TEM and HRTEM images of a typical flower-like particle. Analysis of both the corresponding SAED pattern and d-spacings in the HRTEM image confirm that the principal growth directions are along the  $\langle 10\bar{1}0 \rangle$  zone axes.

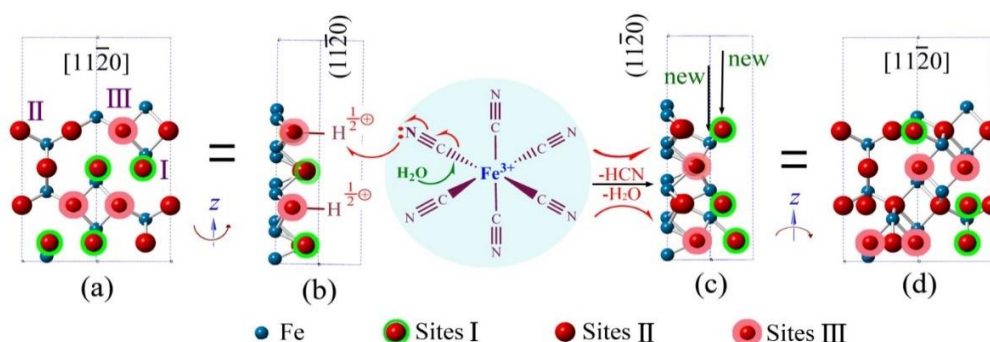


**Fig. 2** Schematic drawing of surface adsorption of a  $[\text{Fe}(\text{CN})_6]^{3-}$  anion to the positively charged triply coordinated hydroxyl group on the  $\{11\bar{2}0\}$  surface and its surface hydrolysis into  $\alpha\text{-Fe}_2\text{O}_3$ . (a), (b) Top view and profile view with H on sites III of the  $\{11\bar{2}0\}$  surface. (c), (d) Profile view and top view of the surface with a newly deposited layer of  $\alpha\text{-Fe}_2\text{O}_3$ .

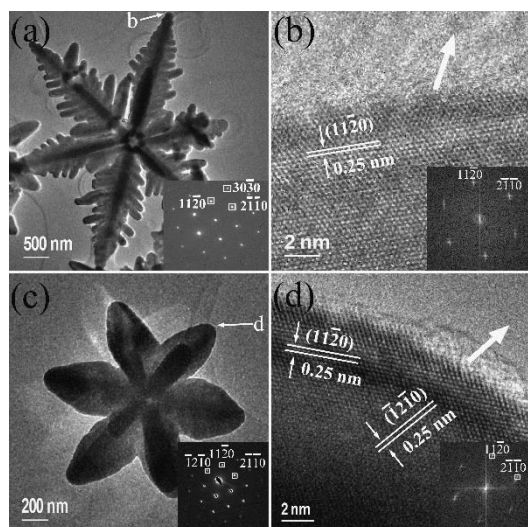

**Fig. 3** (a) TEM image of a typical 'starfish' particle from the sample prepared with 0.12 mol/L octylamine. The inset is the corresponding SAED pattern. (b) HRTEM image of a tip area, marked by 'b', of the particle in (a). (c) TEM image of a 'flower'  $\alpha$ -Fe<sub>2</sub>O<sub>3</sub> particle from the sample prepared with 0.24 mol/L octylamine. The inset is the corresponding SAED pattern. (d) HRTEM image from a tip area, marked by 'd', of the particle in (c). The insets in (b) and (d) are the FFT pattern from the whole areas. The arrows in (b) and (d) indicate the crystal growth directions of  $[10\bar{1}0]$ .

The effects of octylamine can be understood in two aspects. The overall reaction of hydrolysis of  $[\text{Fe}(\text{CN})_6]^{3-}$  can be written as



As a weak alkali capping agent, octylamine can enhance the above reaction. Consequently, the concentration of  $[\text{Fe}(\text{CN})_6]^{3-}$  anions in the solution would be reduced. On the other hand, octylamine ( $\text{pK}_b = 3.35$ ) is a relatively stronger alkaline compound than ferricyanide anions ( $\text{pK}_b = 4.86$ ).<sup>8</sup> Therefore, octylamine can directly bond with the  $\text{OH}^{0.5+}$  on sites III of the  $\{11\bar{2}0\}$  surfaces, blocking these surfaces. The surface hydrolysis of ferricyanide anions as described in Fig. 2 is greatly suppressed. XPS of flower-like crystals shows a small N 1s peak at binding energies of 399.47 eV (Fig. S4a, ESI<sup>†</sup>), which has a significantly higher intensity than that from snowflake crystals (Fig. S4b, ESI<sup>†</sup>) and can be attributed to the surface adsorption of octylamine.<sup>9</sup>

Another effect of amine on the surface hydroxyl configuration is from the alkaline property of the solution, as seen in Table S1, ESI<sup>†</sup>. The  $\text{OH}^{0.5+}$  groups on the  $\{11\bar{2}0\}$  surfaces would be more or less neutralized. When NaOH was added instead of octylamine, no 'snowflake' were produced, and both the particle size and morphology changed with the concentration of NaOH.

The transformation of  $[\text{Fe}(\text{CN})_6]^{3-}$  to Fe<sub>2</sub>O<sub>3</sub> cannot be a direct process. It may be achieved via formation of series intermediate ions, e.g.  $[\text{Fe}(\text{H}_2\text{O})_x(\text{CN})_{6-x}]^{x+3-}$  ( $x = 1$  to 6). The charge of the Fe-containing ions changes from 3- to 3+ step-by-step. When the sites III are no longer available for adsorption of negatively charged ions, the sites I with  $\text{OH}^{0.5-}$  become the active sites to attract positively charged ions. In other words, Fe-containing cations would go to the  $\{11\bar{2}0\}$  and  $\{10\bar{1}0\}$  surfaces. Bearing in mind the former is blocked by octylamine, the most active surface for crystal growth would be the latter. This proposed mechanism explains why the crystal growth

directions shifted from the  $\langle 11\bar{2}0 \rangle$  to  $\langle 10\bar{1}0 \rangle$  the zone axes when octylamine was added.

When the concentration of octylamine were increased to 0.48 and 0.60 mol/L, pH value of the solution increased further. The charge difference of the hydroxyl groups on all the surfaces became less obvious. The hydrolysis of  $[\text{Fe}(\text{CN})_6]^{3-}$  only took place in the solution. The crystal growth turned to a normal process, and the morphology of the produced particles gradually changed to hexagonal plates as shown in Fig. S1(i-1), ESI<sup>†</sup>. The average diameters of the particles reduced to 500 nm to 400 nm, respectively, while their thickness increased significantly. TEM and HRTEM images in Fig. S5, ESI<sup>†</sup> confirm such a crystal morphology.

In summary, from the formation of snowflake-shaped  $\alpha$ -Fe<sub>2</sub>O<sub>3</sub>, we learnt a new phenomenon of crystal growth, interaction of precursor ions with the crystal surface produces the building units for crystals on selective sites, leading to specific growth directions. Low dimensional and complicated morphologies can form in free crystals with no templates nor surface modification with ligands. This mechanism may be used to explain formation of many novel crystal morphologies.

This work was supported by the NNSF of China (No. 51302280), NSF of Qinghai (2014-ZJ-936Q), and Young Scholar Project of Qinghai Institute of Salt Lakes, Chinese Academy of Sciences. WZ thanks EPSRC for financial support to the Electron Microscopy Laboratory (EP/F019580/1).

## Notes and references

<sup>a</sup> Key Laboratory of Salt Lake Resources and Chemistry, Qinghai Institute of Salt Lakes, Chinese Academy of Sciences, Xining 810008, China.

<sup>b</sup> EaStChem, School of Chemistry, University of St Andrews, St Andrews, KY16 9ST, United Kingdom; E-mail: wzhou@st-andrews.ac.uk

<sup>†</sup> Electronic Supplementary Information (ESI) available: More SEM, TEM, HRTEM images, XRD patterns and XPS spectra of  $\alpha$ -Fe<sub>2</sub>O<sub>3</sub> specimens. See DOI: 10.1039/c000000x/

- 1 A. Ritchie, M. Watson, R. Turnbull, Z. Lu, M. Telfer, J. Gano, K. Self, H. F. Greer and W. Z. Zhou, *CrystEngComm*, 2013, **15**, 10266; C. M. Zheng, H. F. Greer, C.-Y. Chiang and W. Z. Zhou, *CrystEngComm*, 2014, **16**, 1064.
- 2 Z. Liu, B. L. Lv, D. Wu, Y. Zhu and Y. H. Sun, *CrystEngComm*, 2012, **14**, 4074.
- 3 N. D. Carbonare, V. Cristino, S. Berardi, S. Carli, R. Argazzi, S. Caramori, L. Meda, A. Tacca and C. A. Bignozzi, *ChemPhysChem*, 2014, **15**, 1164; X. L. Gou, G. X. Wang, J. Park, H. Liu and J. Yang, *Nanotechnology*, 2008, **19**, 125606; Z. Y. Wang, D. Y. Luan, S. Madhavi, C. M. Li and X. W. Lou, *Chem. Commun.*, 2011, **47**, 8061; C. Z. Wu, P. Yin, X. Zhu, C. Z. OuYang and Y. Xie, *J. Phys. Chem. B*, 2006, **110**, 17806; Y. Kim, J. H. Pee, J. H. Chang, K. Choi, K. J. Kim and D. Y. Jung, *Chem. Lett.*, 2009, **38**, 842.
- 4 B. L. Lv, Z. Y. Liu, H. Tian, Y. Xu, D. Wu and Y. H. Sun, *Adv. Funct. Mater.*, 2010, **20**, 3987.
- 5 M. H. Cao, T. F. Liu, S. Gao, G. B. Sun, X. L. Wu, C. W. Hu and Z. L. Wang, *Angew. Chem. Int. Ed.*, 2005, **44**, 4197.
- 6 W. B. Yue and W. Z. Zhou, *Prog. Nat. Sci.*, 2008, **18**, 1329.
- 7 R. M. Cornell and U. Schwertman, *The Iron Oxides: Structure, Properties, Reaction, Occurrences and Use*, (Second ed.), WILEY VCH GmbH&Co.KG&A, 2003. pp222; V. Barron and J. Torrent, *J. Colloid Interface Sci.*, 1996, **177**, 407; C. H. Rochester and S. A. Topham, *J. Chem. Soc. Farad. Trans. 1*, 1979, **75**, 1073.
- 8 Z. Wan, W. L. Luan and S. T. Tu, *J. Phys. Chem. C*, 2011, **115**, 1569.
- 9 Z. Liu, B. L. Lv, D. Wu, Y. H. Sun and Y. Xu, *Eur. J. Inorg. Chem.*, 2012, 4076.

**The Table of Contents (TOC)**

The role of surface hydrolysis of ferricyanide anions in crystal growth of snowflake-shaped  $\alpha$ - $\text{Fe}_2\text{O}_3$

Zhong Liu, Chang-Yang Chiang, Wu Li and Wuzong Zhou

Selective adsorption and surface hydrolysis of  $[\text{Fe}(\text{CN})_6]^{3-}$  anions on  $\alpha$ - $\text{Fe}_2\text{O}_3$  crystals was found to be a crucial process in the formation of a snowflake-like morphology, and the established mechanism is complementary to the classical theories of crystal growth.

