

ChemComm

Accepted Manuscript



This is an *Accepted Manuscript*, which has been through the Royal Society of Chemistry peer review process and has been accepted for publication.

Accepted Manuscripts are published online shortly after acceptance, before technical editing, formatting and proof reading. Using this free service, authors can make their results available to the community, in citable form, before we publish the edited article. We will replace this *Accepted Manuscript* with the edited and formatted *Advance Article* as soon as it is available.

You can find more information about *Accepted Manuscripts* in the [Information for Authors](#).

Please note that technical editing may introduce minor changes to the text and/or graphics, which may alter content. The journal's standard [Terms & Conditions](#) and the [Ethical guidelines](#) still apply. In no event shall the Royal Society of Chemistry be held responsible for any errors or omissions in this *Accepted Manuscript* or any consequences arising from the use of any information it contains.

COMMUNICATION

Oxygen electroreduction promoted by quasi oxygen vacancies in metal oxide nanoparticles prepared by photoinduced chlorine doping

Cite this: DOI:
10.1039/x0xx00000x

Nan Wang,^{a†} Wenhan Niu,^{a†} Ligui Li,^{a*} Ji Liu,^a Zhenghua Tang,^a Weijia Zhou,^a and Shaowei Chen^{a, b*}

Received 00th January 2015,
Accepted 00th January 2015

DOI: 10.1039/x0xx00000x

www.rsc.org/


Quasi oxygen-deficient indium tin oxide nanoparticles (ITO NPs) were prepared by photoinduced chlorine doping, and exhibited much enhanced electrocatalytic activity for oxygen reduction reaction (ORR) in alkaline media, as compared with pristine ITO.

Metal oxides¹ and their perovskites^{2, 3} have been attracting extensive research interest as emerging potential catalysts for ORR in alkaline fuel cells and rechargeable metal-air batteries, mainly because of their low costs, widespread availability, ease of preparation, appealing catalytic activity and high stability in the working potential range. Nevertheless, metal oxides are generally much less active than noble-metal catalysts, especially in terms of overpotential, diffusion limited current and the capability to catalyze four-electron reduction. It has been found that the ORR activity may be enhanced by oxygen vacancies on the oxide surface, which are generally formed by high-temperature calcination.^{1, 2} Yet this is incompatible with materials that are not stable at high temperatures. Therefore, it remains of high demand to explore novel, effective methods to the preparation of oxygen-deficient metal oxide catalysts under mild conditions from both industrial and academic points of view. This is the primary motivation of the present study.

ITO is a highly conductive semiconductor that exhibits relatively high stability in harsh environments and strong resistance to oxidation at high potentials, as compared with carbon-based materials such as porous carbons, graphene and carbon nanotubes.⁴ Therefore, there is an increasing interest of using ITO NPs as novel catalyst supports^{5, 6} or stabilizers⁴ for metal catalysts. However, studies of the catalytic activity of ITO itself, in particular for ORR, have been scarce, to the best of our knowledge.

Herein, we carried out a systematic study of the ORR activity of ITO NPs and use them as an illustrating example to examine the effect of photoinduced chlorine doping, which led to the formation of quasi oxygen vacancies, on the corresponding ORR activity. The resulting nanoparticles showed rather remarkable ORR activity in alkaline media, a performance much higher than that of pristine ITO NPs.

Experimentally, ITO NPs were prepared according to a literature procedure⁴ based on solvothermal treatment of indium acetylacetonate [In(acac)₃] and tin(IV) tert-butoxide [Sn(OtBu)₄] in benzyl alcohol at controlled temperatures. Chlorine-doped ITO (Cl-ITO) NPs were then prepared by UV photoirradiation of the ITO NPs for 5 min in *o*-dichlorobenzene (ODCB),⁷ as depicted in Scheme 1 (details in ESI).

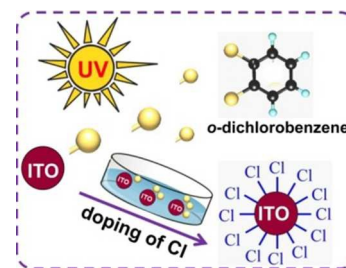

Scheme 1. Schematic of the preparation of Cl-ITO NPs.

Fig. 1a shows a representative TEM image of the Cl-ITO nanoparticles. It can be seen that the nanoparticles were mostly spherical in shape with the diameters in the range of 5 to 10 nm. From high-resolution TEM measurements in Fig. 1b, one can see clearly-defined lattice fringes with a spacing of 0.29 nm, which is consistent with the *d*-spacing of the (222) crystalline planes of ITO, indicating highly crystalline nature of the Cl-ITO NPs and the retention of the ITO crystalline structure after

chlorine doping (Fig. S1). Statistical analysis based on about two hundred nanoparticles shows that the average diameter of the Cl-ITO NPs is ca. 7.03 ± 0.51 nm, as manifested by the core size histogram in Fig. 1c. This is almost the same as that of the pristine ITO NPs (Fig. S1). Consistent results were obtained in X-ray diffraction (XRD) studies, as depicted in Fig. 1d, where all the diffraction peaks can be indexed to the cubic bixbyite phase of In_2O_3 (PDF No. 6-416).⁸ Note that no peaks can be assigned to SnO_2 , indicating the formation of a solid solution rather than a mixture of indium oxide and tin oxide⁴ in Cl-ITO. The size of the crystallites along the [222] direction was estimated to be 7.51 ± 0.23 nm by using the Scherrer equation, in good agreement with the TEM result in Fig. 1a.

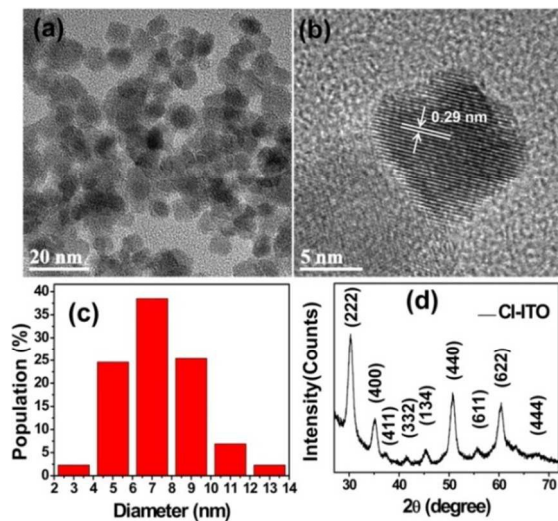


Fig. 1. (a) TEM and (b) HRTEM images of Cl-ITO NPs, with (c) the corresponding core size histogram and (d) XRD diffraction profile.

X-ray photoelectron spectroscopy (XPS) measurements were then conducted to probe the elemental composition of the nanoparticles. In the survey spectrum of ITO nanoparticles (black curve, Fig. 2a), only the elements of In, Sn, and O can be identified. Consistent spectral features can be seen with the Cl-ITO samples (red curve). Importantly, the latter also exhibited two additional peaks at 284.10 eV and 199.06 eV (indicated by blue triangles), which may be assigned to the Cl 2s and 2p electrons, respectively, suggesting effective doping of Cl into the ITO nanoparticles. Note that these Cl signals were absent in the as-prepared ITO NPs or the ITO NPs that were immersed into ODCB but without UV photoirradiation (Fig. S2), indicating that Cl was actually chemically bonded to the ITO nanoparticle surface in Cl-ITO after UV treatments. Furthermore, high-resolution scan of the Cl 2p electrons in Cl-ITO (Fig. 2b) yielded only a doublet at 200.56 eV and 199.06 eV, consistent with the $\text{Cl}2p_{1/2}$ and $\text{Cl}2p_{3/2}$ electrons in InCl_3 , respectively. This suggests a uniform bonding configuration of Cl in the sample. Similar behaviors have been observed previously.⁷ In addition, based on the integrated peak areas, the loading of Cl dopants in Cl-ITO was estimated to be 3.9 at%. Because of this low concentration of Cl doping, the UV-vis

absorption spectra of ITO and Cl-ITO NPs were virtually identical (Fig. S3).

Interestingly, the Cl-ITO NPs exhibited apparent electrocatalytic activity for ORR (experimental details in ESI). Cyclic voltammetric measurements were first carried out in N_2 - and O_2 -saturated 0.1 M KOH solutions at a mass loading of $102.0 \mu\text{g}/\text{cm}^2$ on a glassy carbon electrode. As depicted in Fig. 3a, in the N_2 -saturated electrolyte solution (black dashed curves), both ITO and Cl-ITO exhibited largely a featureless double-layer charging profile. In contrast, when the solution was saturated with O_2 (red solid curves), two apparent cathode peaks emerged at +0.50 V and +0.19 V, suggesting effective ORR activity of the oxide nanoparticles. More significantly, the peak currents of the Cl-ITO NPs ($0.18 \text{ mA}/\text{cm}^2$ at +0.50 V, $0.22 \text{ mA}/\text{cm}^2$ at +0.19 V) were markedly higher than those of the pristine ITO ($0.15 \text{ mA}/\text{cm}^2$ at +0.50 V, $0.20 \text{ mA}/\text{cm}^2$ at +0.19 V), signifying much enhanced ORR activity by Cl doping.

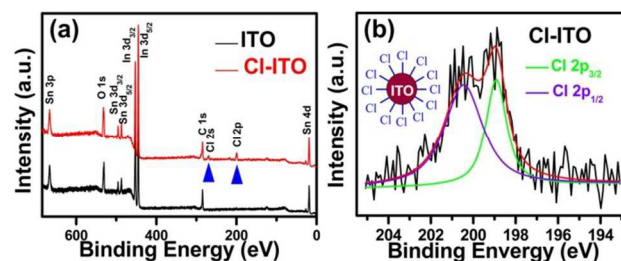


Fig. 2. (a) XPS survey spectra of Cl-ITO and (b) the high-resolution scan of Cl 2p electrons. Inset is the sketch of a Cl-ITO NP.

The ORR activity and kinetics were further examined by using rotating disk electrode (RDE) voltammetry in the same O_2 -saturated 0.1 M KOH solution. From Fig. 3b, one can see that for both pristine ITO and Cl-ITO NPs, nonzero cathodic currents started to appear when the electrode potential was swept negatively beyond +0.67 V; yet, a much higher limiting current was observed with Cl-ITO. For instance, at 0 V, the limiting current density was only $2.05 \text{ mA}/\text{cm}^2$ for ITO, but increased markedly to $2.64 \text{ mA}/\text{cm}^2$ for Cl-ITO, again signifying enhanced ORR activity by surface Cl doping.

Fig. 3c depicts the RRDE voltammograms of the Cl-ITO NPs-modified electrode where the ring potential was set at +1.5 V (the data for pristine ITO NPs were included in Fig. S3). One can see that the disk currents increased with increasing electrode rotation rate and the ring currents were about one-order of magnitude lower than those at the disk, suggesting rather effective reduction of oxygen catalyzed by the Cl-ITO NPs, as manifested by the number of electron transfer (n , eq. 1) and the H_2O_2 yield (eq. 2) involved in ORR,

$$n = \frac{4I_{\text{Disk}}}{I_{\text{Ring}}/N + I_{\text{Disk}}} \quad (1)$$

$$\text{H}_2\text{O}_2\% = \frac{200I_{\text{Ring}}/N}{I_{\text{Ring}}/N + I_{\text{Disk}}} \quad (2)$$

where N is the collection efficiency (37%), I_{Disk} and I_{Ring} are the voltammetric currents at the disk and ring electrodes, respectively. From Fig. 3d (top), one can see that the n values for ITO were in the range of 2.3 to 2.8 at 0.3 – 0.0 V, but

increased markedly to 2.9 to 3.4 with Cl-ITO. This observation indicates that ORR on Cl-ITO mostly proceeded via the 4-electron reduction route (fully reduced to OH^-) while on ITO it followed predominantly a 2-electron process with peroxides as the predominant final products. In fact, the percent yield of H_2O_2 decreased by about 30% with Cl-ITO as compared to that of ITO (Fig. 3d, bottom). This suggests that Cl doping indeed served as an effective method for the enhancement of the ORR activity of ITO.

Note that extending the UV irradiation time to, for example 15 min, led to virtually no change of the n values or H_2O_2 yield (Fig. 3d), indicating that a 5-min exposure time for Cl doping was enough to produce the best Cl-ITO electrocatalyst within the present experimental context.

The corresponding Koutecky–Levich (K–L) plots were depicted in Fig. 3e which exhibit good linearity and parallelism over the potential range from 0.00 to +0.40 V, suggesting first-order reaction kinetics of ORR with respect to oxygen concentration in the solution. Similar behaviors were observed with the pristine ITO as well (Fig. S4). The corresponding Tafel plots were depicted in Fig. 3f, where one can see that the slopes of Cl-ITO (58 mV/dec) and ITO (75 mV/dec) were rather close, indicating a similar reaction mechanism with the rate-determining step being the first electron reduction of oxygen. Yet, Cl-ITO exhibited a markedly higher current density than ITO. For instance, at +0.25 V, the kinetic current density was 1.68 mA/cm^2 with Cl-ITO but only 1.19 mA/cm^2 with ITO,

signifying that the chlorine doping indeed enhanced the ORR activity.

Experimentally a gradual loss of the Cl dopants was observed. For instance, after 100 cycles within the potential range of -0.03 to $+1.12$ V at the potential sweep rate of 10 mV/s, the concentration of Cl dopants was found to decrease to 2.0 at.% (Fig. S5). However, chronoamperometric measurements (Fig. S6) showed that during more than 8 h's continuous operation, the ORR performance of Cl-ITO NPs remained superior to that of pristine ITO NPs.

Although the mechanism is not yet fully understood, it is likely that the enhanced ORR activity of Cl-ITO, as compared with that of pristine ITO, may be attributed to Cl doping that led to the formation of surface defects with variable oxygen stoichiometry. As shown in Scheme 2, in the crystalline lattice of In_2O_3 , each In atom coordinates with six O atoms, and each O atom with two In atoms. The substitution of one O atom (electronegativity 3.44) by Cl (electronegativity 3.16) decreases the local O:In stoichiometric ratio, leading to the formation of quasi oxygen-deficient sites that were advantageous for oxygen binding,^{1, 2, 9} a critical first step in ORR. Further research is desired to unravel the mechanism of ORR on Cl-ITO.

Note that whereas the performance of Cl-ITO remains subpar as compared to that of state-of-the-art Pt/C catalysts,^{10,11} the fact that Cl-modification of ITO surfaces markedly improved the ORR activity suggests that the electrocatalytic performance might be further enhanced by deliberate engineering of the ITO nanoparticle surfaces with other dopants.


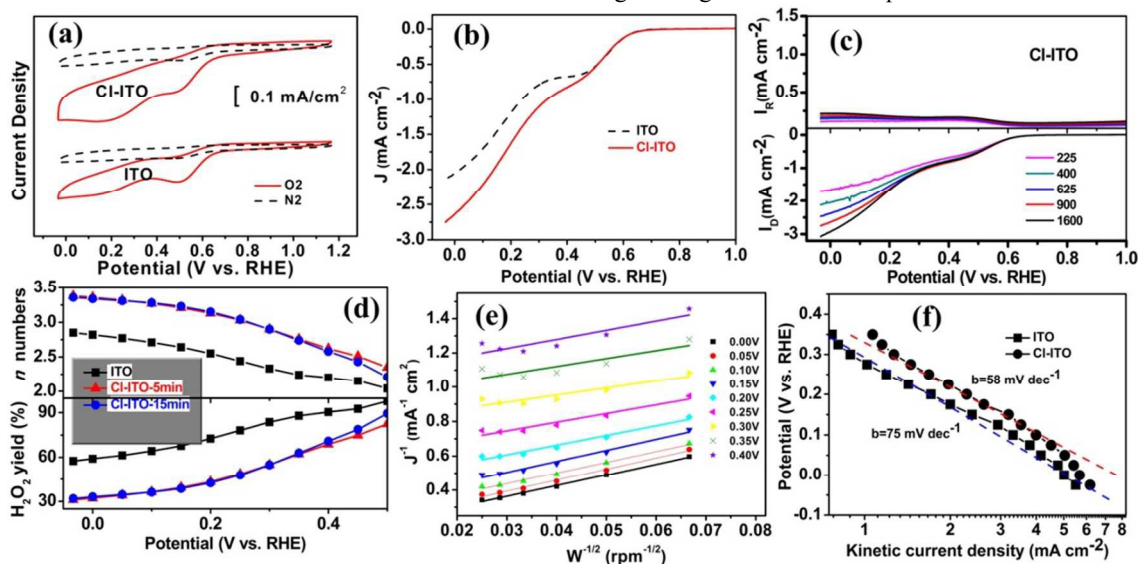


Fig. 3. (a) Cyclic and (b) RDE voltammograms of ITO and Cl-ITO at an electrode rotation rate of 900 rpm, (c) RRDE of Cl-ITO at different rotation rates (specified in figure legends); (d) plots of number of electron transfer and H_2O_2 yield at ITO and Cl-ITO. (e) K-L plots of Cl-ITO, and (f) Tafel plots at ITO and Cl-ITO. Measurements were all conducted on a glassy carbon electrode at a catalyst loading of $102.0 \mu\text{g}/\text{cm}^2$ in O_2 -saturated 0.1 M KOH at a potential sweep rate of 10 mV/s.

COMMUNICATION

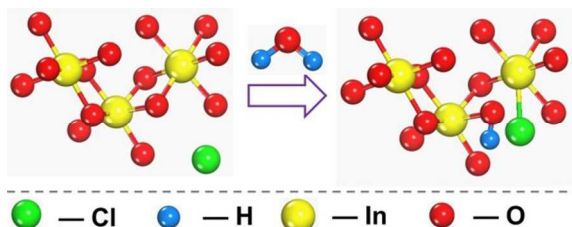

Scheme 2. Formation of local quasi-oxygen vacancy due to the substitution of O by Cl at the In atom in the right.

In Summary, Cl-ITO NPs were successfully prepared by UV photo irradiation of ITP NPs in the presence of ODCB. Electrochemical measurements showed that the electrocatalytic activity of Cl-ITO in ORR was substantially enhanced as compared with that of pristine ITO, within the context of diffusion limiting current and number of electron transfer involved in ORR. This was likely due to the formation of quasi oxygen-deficient sites on Cl-ITO surfaces that were advantageous for oxygen binding. Results from the present work suggest a novel and facile method to the improvement of the ORR activity of metal oxides.

This work was supported by the National Recruitment Program of Global Experts. L.G.L acknowledges support from the National Natural Science Foundation of China (NSFC 51402111) and the Fundamental Research Funds for the Central Universities (SCUT Grant No. 2013ZM0019). S. W. C. thanks the National Science Foundation (CHE-1265635 and DMR-1409396) for partial support of the work.

Notes and References

^a New Energy Research Institute, College of Environment and Energy, South China University of Technology, Guangzhou Higher Education Mega Center, Guangzhou 510006, China. E-mail: esguili@scut.edu.cn (L.G.L.).

^b Department of Chemistry and Biochemistry, University of California, 1156 High Street, Santa Cruz, California 95064, United States. E-mail: shaowei@ucsc.edu (S.W.C).

† These authors contribute equally to this work.

Electronic Supplementary Information (ESI) available: Experimental procedures, and additional TEM, spectroscopic and voltammetric data. See DOI: 10.1039/c000000x/

¹ F. Cheng, T. Zhang, Y. Zhang, J. Du, X. Han, and J. Chen, *Angew. Chem. Int. Ed.*, 2013, **52**, 2474.

² J. Kim, X. Yin, K.-C. Tsao, S. Fang, and H. Yang, *J. Am. Chem. Soc.*, 2014, **136**, 14646.

³ J. Suntivich, H. A. Gasteiger, N. Yabuuchi, H. Nakanishi, J. B. Goodenough, and Y. Shao-Horn, *Nat. Chem.*, 2011, **3**, 546.

⁴ R. Kou, Y. Shao, D. Mei, Z. Nie, D. Wang, C. Wang, V. V. Viswanathan, S. Park, I. A. Aksay, Y. Lin, Y. Wang, and J. Liu, *J. Am. Chem. Soc.*, 2011, **133**, 2541–2547.

⁵ G. Chang, M. Oyama, and K. Hirao, *J. Phys. Chem. B*, 2006, **110**, 1860.

⁶ Y. Song, Y. Ma, Y. Wang, J. Di, and Y. Tu, *Electrochim. Acta*, 2010, **55**, 4909.


⁷ M. G. Helander, Z. B. Wang, J. Qiu, M. T. Greiner, D. P. Puzzo, Z. W. Liu, and Z. H. Lu, *Science*, 2011, **332**, 944.

⁸ Y. Hao, G. Meng, C. Ye, and L. Zhang, *Cryst. Growth Design*, 2005, **5**, 1617.

⁹ X. Han, Y. Hu, J. Yang, F. Cheng, and J. Chen, *Chem. Commun.*, 2014, **50**, 1497.

¹⁰ Y. Song, S. W. Chen, *ACS Appl. Mater. Interface*, 2014, **6**, 14050–14060.

¹¹ G. Q. He, Y. Song, K. Liu, A. Walter, S. Chen, S. W. Chen, *ACS Catal.* 2013, **3**, 831–838.

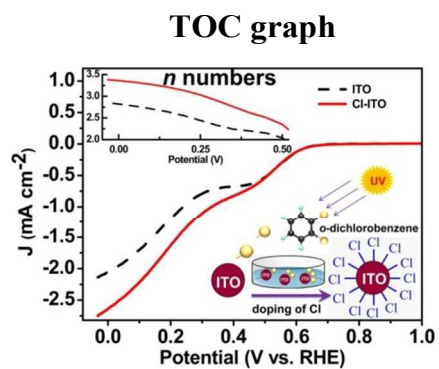

Quasi oxygen vacancies on ITO nanoparticles were prepared by photoinduced chlorine doping to promote oxygen electroreduction in alkaline media.